



Cite this: *Chem. Sci.*, 2023, 14, 11830 All publication charges for this article have been paid for by the Royal Society of ChemistryReceived 29th August 2023  
Accepted 3rd October 2023

DOI: 10.1039/d3sc04532c

rsc.li/chemical-science

# Ion sieving membrane for direct seawater anti-precipitation hydrogen evolution reaction electrode†

Qianfeng Liu, Zhao Yan,  Jianxin Gao, Hefei Fan, Min Li and Erdong Wang \*

In seawater, severe hydroxide-based precipitation on the hydrogen evolution reaction (HER) electrode surface is still a major stumbling block for direct seawater electrolysis. Here, we design a direct seawater HER electrode with excellent anti-precipitation performance based on an  $\text{Ni}(\text{OH})_2$  nanofiltration membrane *in situ* grown on nickel foam (NF) at room temperature. The positively charged  $\text{Ni}(\text{OH})_2$  membrane with nanometer-scale cracks realises an ion sieving function, which apparently hinders the transfer of  $\text{Mg}^{2+}/\text{Ca}^{2+}$  ions to suppress precipitation, while rapidly transporting  $\text{OH}^-$  and  $\text{H}_2\text{O}$  to ensure HER mass transfer. Therefore, the  $\text{Ni}(\text{OH})_2$ -membrane-decorated seawater HER electrode reduces precipitation by about 98.3% and exhibits high activity and stability. Moreover, in the application of a direct seawater electrolyser and magnesium seawater battery, the  $\text{Ni}(\text{OH})_2$  membrane-decorated electrode also shows low precipitation and high stability. This work highlights a potential strategy to solve HER electrode precipitation in seawater via an ingenious electrode structure design.

## Introduction

Hydrogen, a carbon-free fuel, can provide a practicable strategy to mitigate climate change and achieve carbon neutrality,<sup>1–4</sup> since it is generated through water electrolysis powered by clean energy, such as seawater electrolysis powered by off-shore wind power.<sup>5–7</sup> Compared with conventional alkaline and proton exchange membrane (PEM) water electrolysis, seawater electrolysis directly uses the seawater as a waterhead, which reduces the cost of hydrogen production by getting rid of the equipments to produce ultra-pure water.<sup>8,9</sup> However, impurity ions in seawater, e.g.  $\text{Cl}^-$  (20.06 g  $\text{kg}^{-1}$   $\text{H}_2\text{O}$ ) and  $\text{Mg}^{2+}$  (1.33 g  $\text{kg}^{-1}$   $\text{H}_2\text{O}$ ), are known to bring about challenges of the chlorine evolution reaction (CLER) on the oxygen evolution reaction (OER) electrode, equipment corrosion by  $\text{Cl}^-$ , and the precipitation of hydroxides on the hydrogen evolution reaction (HER) cathode.<sup>10–13</sup> Due to the effect of blanket cathode precipitation on the size of the active area, over 50% of the HER electrode current density is lost after only 24 hours of operation.<sup>14,15</sup> Moreover, HER electrode precipitation also causes problems for other applications, such as electrochemical sewage treatment, sodium hypochlorite production from seawater, and metal seawater batteries.<sup>16–21</sup> Therefore, an ideal method to solve HER electrode precipitation is urgently needed for applications.

The development of reported methods for solving HER electrode precipitation caused by  $\text{Mg}^{2+}$  and  $\text{Ca}^{2+}$  ions in seawater can be categorized into four types: (i) the addition of acid or inhibitor to the electrolyte, which avoids the formation of precipitate on the HER electrode, such as sulfuric acid to prevent precipitation and  $\text{CO}_2$  to dissolve  $\text{CaCO}_3$ ;<sup>22–25</sup> (ii) optimizing the operating conditions or electrolyser structure, such as current density, electrolyte flow rate, and ion exchange membrane, that can scour the precipitate on the electrode by hydrogen gas bubbles and electrolyte, or an  $\text{Na}^+$  exchange membrane to alleviate the formation of  $\text{Mg}^{2+}$  and  $\text{Ca}^{2+}$  precipitates;<sup>26–28</sup> (iii) washing with acid, that can dissolve the alkaline precipitate;<sup>15</sup> and (iv) direct pre-removal of  $\text{Mg}^{2+}$  and  $\text{Ca}^{2+}$  ions, which eliminates the main precipitate-forming ions, as used in the chlor-alkali industry for example.<sup>29</sup> Some of these methods can efficiently prevent the formation of precipitate, but incidental problems make large-scale application for seawater electrolysis difficult, such as acid consumption and corrosion because of acid addition or wash, and the high cost of the pre-removal of the ions. If the HER electrode surface could itself prevent the formation of precipitate, such as a  $\text{Cr}_2\text{O}_3$  Lewis acid layer, which hinders the transfer of the  $\text{OH}^-$  produced by the HER electrode to lower the electrode surface pH,<sup>30</sup> this would be more significant for real applications. Several groups have revealed this phenomenon and the reason for the precipitation adsorption on the HER electrode, but studies of how to obtain an anti-precipitation HER electrode in seawater are limited.<sup>31</sup>

Herein, an  $\text{Ni}(\text{OH})_2$  ion sieving membrane coated on the surface of 3D NF was *in situ* fabricated as an anti-precipitation

Dalian National Laboratory for Clean Energy, Dalian Institute of Chemical Physics, Chinese Academy of Sciences, Dalian 116023, China. E-mail: edwang@dicp.ac.cn

† Electronic supplementary information (ESI) available. See DOI: <https://doi.org/10.1039/d3sc04532c>

HER electrode in seawater. Combined theoretical calculation and experimental tests, the  $\text{Ni}(\text{OH})_2$  ion sieving membrane can efficiently hinder the transfer of  $\text{Mg}^{2+}/\text{Ca}^{2+}$  ions and rapidly convey the HER related  $\text{OH}^-$  and  $\text{H}_2\text{O}$  due to the positive charge and nanometer-scale cracks. Due to the excellent anti-precipitation performance, rapid mass transfer, and synergistic effect between  $\text{Ni}(\text{OH})_2$  and NF, the  $\text{Ni}(\text{OH})_2$ -NF electrode can reduce most of the precipitation on the surface, and exhibit higher HER performance than that of an NF electrode. In application to a direct seawater electrolyser and magnesium seawater battery, the  $\text{Ni}(\text{OH})_2$ -membrane-coated electrode also obviously adsorbed less precipitation and displayed higher stability.

## Results and discussion

### Precipitation on a seawater HER electrode

To understand which ion in seawater led to the precipitation, the seawater-related  $\text{Mg}^{2+}$ ,  $\text{Ca}^{2+}$ ,  $\text{SO}_4^{2-}$  and  $\text{HCO}_3^-$  ions were separated. As shown in Fig. 1a, the NF-based HER electrodes were measured in 3.5% NaCl without or with the different ions at the

same concentration in seawater under  $1 \text{ mA cm}^{-2}$  for 200 h. Distinctly, the precipitation was mainly caused by the  $\text{Mg}^{2+}$  ion and partly by the  $\text{Ca}^{2+}$  ion, because the precipitation mass on the electrode surface suddenly increased from  $1.4\text{--}9.0 \text{ mg cm}^{-2}$  to  $215\text{--}229 \text{ mg cm}^{-2}$  when the electrolytes contained  $\text{Mg}^{2+}$  ions, and the HER electrodes were fully covered by a burly white precipitate. The main components of the precipitate on the electrode surface were  $\text{Mg}(\text{OH})_2$  and adsorbed NaCl, as identified by XRD (Fig. 1b). It is speculated that the pH on the seawater HER electrode surface would increase rapidly at the beginning of HER operation, as schematically illustrated in Fig. 1c, which was much higher than the pH of  $\text{Mg}(\text{OH})_2$  deposition.<sup>32,33</sup> Therefore, the  $\text{Mg}^{2+}$  ions in seawater would preferentially deposit on the surface of the HER electrode, and then the  $\text{Mg}(\text{OH})_2$  precipitate on the electrode would act as deposition sites for the newly formed  $\text{Mg}(\text{OH})_2$ .<sup>26</sup> As a result, the seawater HER electrode would be covered with  $\text{Mg}(\text{OH})_2$ -based precipitate.

### Synthesis and characterization of the $\text{Ni}(\text{OH})_2$ membrane

To solve the precipitation on a direct seawater HER electrode, an  $\text{Ni}(\text{OH})_2$  membrane was *in situ* synthesized on NF ( $1 \text{ cm} \times 2$



Fig. 1 (a) Mass of precipitation on the electrode in different electrolytes (inset: photographs of the HER electrode after measurement). (b) XRD pattern of the precipitation. (c) A schematic illustration of the precipitation mechanism on the HER electrode surface in seawater.

cm) *via* a simple soaking process in 0.1 M  $\text{NiCl}_2$  for 3 days at  $25 \pm 1^\circ\text{C}$ , as schematically illustrated in Fig. 2a. During the soaking period, the NF was etched by the dissolved oxygen and  $\text{Cl}^-$ , and then the generated  $\text{OH}^-$  reacted with the excess  $\text{Ni}^{2+}$  to generate a positively charged  $\text{Ni}(\text{OH})_2$  membrane ( $\zeta = +23.8$  mV in 1 mM NaOH, Fig. 2b) on the NF surface. Due to the positive charge, the  $\text{Ni}(\text{OH})_2$  membrane can hinder the passage of  $\text{Mg}^{2+}$  and  $\text{Ca}^{2+}$  ions through the membrane from the electrolyte to the NF surface, as will be discussed in detail below.

As disclosed in Fig. 2c, the diffraction peaks appearing at  $19.3^\circ$ ,  $33.1^\circ$ ,  $38.5^\circ$ , and  $52.1^\circ$  were assigned to the characteristic (001), (100), (101) and (102) facets for  $\text{Ni}(\text{OH})_2$  (JCPDS no. 74-

2075), respectively. It is noteworthy that the *c*-axis-related diffraction peaks were broadened due to the disordered and expanded  $\text{Ni}(\text{OH})_2$  layers. The higher redox peak current of  $\text{Ni}(\text{II})$  to  $\text{Ni}(\text{III})$  for the  $\text{Ni}(\text{OH})_2$ -NF electrode compared to the NF electrode further verified that the NF surface was covered with  $\text{Ni}(\text{OH})_2$  (Fig. S1†). The morphology of the  $\text{Ni}(\text{OH})_2$  membrane on NF was studied with field emission scanning electron microscopy (SEM). As shown in Fig. 2d,  $\text{Ni}(\text{OH})_2$  was uniformly coated around the 3D NF surface to form the membrane. The surface of the  $\text{Ni}(\text{OH})_2$  membrane was formed by continuous scarf-like  $\text{Ni}(\text{OH})_2$  sheets with rugged pores (Fig. 2e). In the membrane matrix, with a thickness of  $\sim 520$  nm (Fig. 2f), the

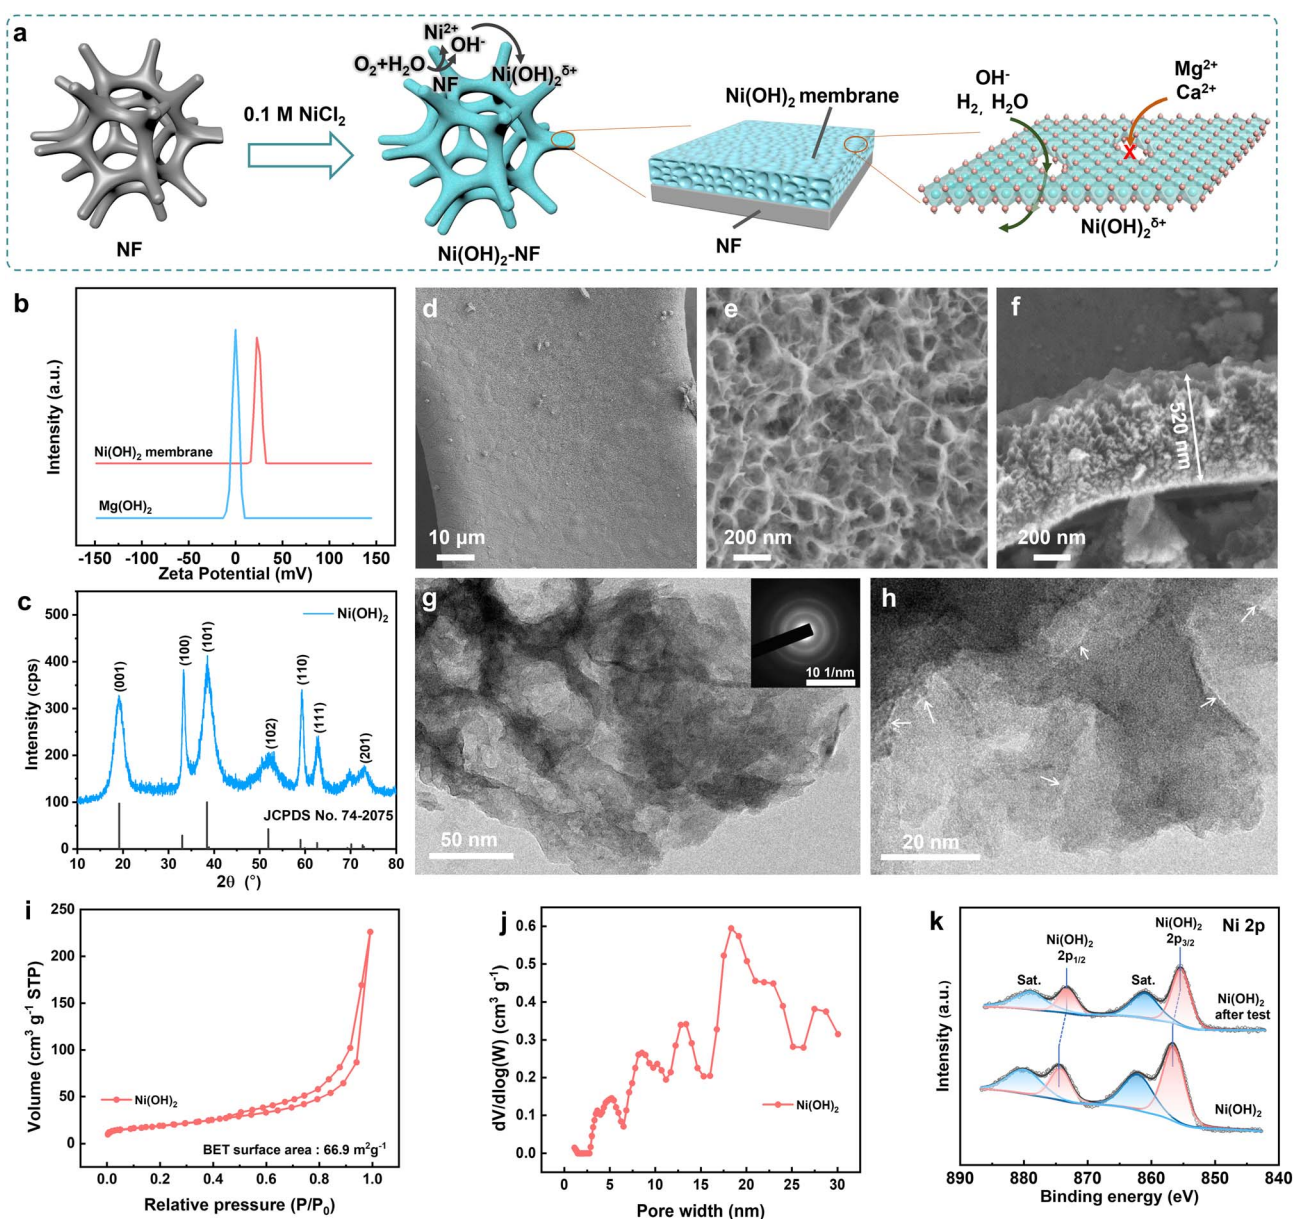


Fig. 2 (a) Schematic illustration of *in situ* growth of the  $\text{Ni}(\text{OH})_2$  membrane on NF. (b) Zeta potential of the  $\text{Ni}(\text{OH})_2$  membrane stripped from  $\text{Ni}(\text{OH})_2$ -NF electrodes and precipitated  $\text{Mg}(\text{OH})_2$ . (c) XRD pattern of the  $\text{Ni}(\text{OH})_2$  membrane. (d-f) Typical SEM, and (g, h) TEM images of the  $\text{Ni}(\text{OH})_2$  membrane (inset: SADE). (i)  $\text{N}_2$  isothermal absorption/desorption and (j) pore size distribution curves of the  $\text{Ni}(\text{OH})_2$  membrane stripped from the  $\text{Ni}(\text{OH})_2$ -NF electrodes. (k) High-resolution XPS spectra for Ni 2p of the  $\text{Ni}(\text{OH})_2$  membrane before and after testing in seawater.



rugged pores were completely filled with amorphous  $\text{Ni}(\text{OH})_2$ . Therefore, the solutions must pass through the amorphous  $\text{Ni}(\text{OH})_2$  sheets to cross over the membrane, but not through the pores. To obtain detailed structural information about the  $\text{Ni}(\text{OH})_2$  membrane, a transmission electron microscopy (TEM) investigation was carried out. The TEM and selected area electron diffraction (SAED) results further verified the porous and amorphous structure of the  $\text{Ni}(\text{OH})_2$  membrane (Fig. 2g). Under higher magnification (Fig. 2h), the crack-like defects were randomly distributed on the  $\text{Ni}(\text{OH})_2$  sheets with a width of 0.4–2.0 nm and a length of 7.9–26.2 nm. The defects supply enough high-speed channels for the water and ions to cross over the  $\text{Ni}(\text{OH})_2$  membrane, which will be discussed in detail *via* the simulation below.

Brunauer–Emmett–Teller (BET) analysis showed that the  $\text{Ni}(\text{OH})_2$  membrane possessed a specific area of  $66.9 \text{ m}^2 \text{ g}^{-1}$  (Fig. 2i); the pore size was distributed over 2.5 nm and centred around 20 nm (Fig. 2j), which was in agreement with the TEM results. The surface chemical state of the  $\text{Ni}(\text{OH})_2$  membrane was investigated with X-ray photoelectron spectroscopy (XPS). As revealed in Fig. S2,† the  $\text{Ni}(\text{OH})_2$  membrane contained only Ni, O, and C elements. For the Ni 2p XPS spectra (Fig. 2k), the two spin-orbit doublet peaks at 856.4 and 874.3 eV with two shake-up satellites at 862.0 and 880.0 eV belong to  $\text{Ni}(\text{OH})_2$ . The absence of an Ni(0) binding energy peak in Fig. 2k further confirmed that the surface of NF was fully coated with the  $\text{Ni}(\text{OH})_2$  membrane. The species of  $\text{Ni}(\text{OH})_2$  was also demonstrated by the O 1s XPS spectra at a binding energy of 531.7 eV (Fig. S3†). Moreover, impurities of  $\text{H}_2\text{O}$  and  $\text{CO}_3^{2-}$  were found in the  $\text{Ni}(\text{OH})_2$  membrane in the O 1s XPS spectra (the  $\text{CO}_3^{2-}$  can also be confirmed by the C 1s XPS spectra, Fig. S4†). The impurity mass was calculated to be about 5.8% from the thermal gravimetric analysis (TGA, Fig. S5†) curves. In short, the positively-charged  $\text{Ni}(\text{OH})_2$  membrane with nanometer-scale cracks was *in situ* uniformly coated on the 3D NF.

### Anti-precipitation performance

Firstly, we studied the precipitation mass influenced by the thickness of the  $\text{Ni}(\text{OH})_2$  membrane on the NF electrode, which was controlled by soaking time. From 1 to 5 days (Fig. S6†), the thickness of the  $\text{Ni}(\text{OH})_2$  membrane grew from  $\sim 350 \text{ nm}$  to  $\sim 1010 \text{ nm}$ , as detected by SEM. During the measurement, we found that the Ni flake, Ti mesh and graphite rod as counter electrode (CE) in seawater all suffered from corrosion and a chlorine evolution reaction. To avoid or reduce the effect of the CE on the working electrode (WE) as much as possible, we chose a pure Mg rod as the counter electrode. During the test, the Mg CE would be oxidized into  $\text{Mg}^{2+}$ . When the WE was separated from the CE by AEM, the generated  $\text{Mg}^{2+}$  would not affect the WE. Without the AEM, the  $\text{Mg}^{2+}$  would diffuse to the WE cell to supplement the consumed  $\text{Mg}^{2+}$ . Compared to an NF electrode, the  $\text{Ni}(\text{OH})_2$ -NF electrodes deposited less precipitation after 12 h of measurement at  $10 \text{ mA cm}^{-2}$  in seawater when the WE and CE were separated with AEM (marked as SW + AEM, Fig. 3a, S7 and S8†). Due to the lower precipitation, the  $\text{Ni}(\text{OH})_2$ -NF electrodes exhibited higher stability than the NF electrode

(Fig. S9†). With increasing soaking time, the precipitation mass reached a minimum value of  $3.2 \text{ mg cm}^{-2}$  for the  $\text{Ni}(\text{OH})_2$ -NF-3d electrode. In detail, the porous precipitation of Mg/Ca-based hydroxide or carbonate with a thickness of  $6.1 \mu\text{m}$  was evenly distributed on the surface of the  $\text{Ni}(\text{OH})_2$  membrane (Fig. S2, S10–S12†). It is worth noting that the Mg and Ca elements were only distributed on the surface of the  $\text{Ni}(\text{OH})_2$  membrane (Fig. S11†), indicating that the  $\text{Ni}(\text{OH})_2$  membrane can hinder the transfer of  $\text{Mg}^{2+}$  and  $\text{Ca}^{2+}$  from seawater to the NF substrate. Moreover, the  $\text{Ni}(\text{OH})_2$ -NF electrodes displayed higher HER performance than NF because of the synergistic effect between  $\text{Ni}(\text{OH})_2$  and NF to accelerate the Volmer step of HER.<sup>34,35</sup> Therefore, the potential of  $\text{Ni}(\text{OH})_2$ -NF electrodes ( $-1.078$  to  $-1.067 \text{ V vs. SCE}$ , saturated calomel electrode) was more positive with 24 to 35 mV than that of the NF electrode ( $-1.102 \text{ V vs. SCE}$ ) at a current density of  $10 \text{ mA cm}^{-2}$  (Fig. 3b). The smaller Tafel slopes and  $R_{\text{CT}}$  in EIS of the  $\text{Ni}(\text{OH})_2$ -NF electrodes also confirmed the higher HER activity for  $\text{Ni}(\text{OH})_2$ -NF electrodes (Fig. S13†). Just to be clear, the electrolyte pH kept rising from  $\sim 8.1$  to 12.8 during the measurement, so the SCE was better able to act as the reference electrode but not as a reversible hydrogen electrode (RHE).

To further reduce the precipitation on the electrode surface, we then added  $\text{Mg}(\text{OH})_2$  powder in seawater to obtain a saturated  $\text{Mg}(\text{OH})_2$  seawater solution, denoted SW +  $\text{Mg}(\text{OH})_2$ . The  $\text{Mg}(\text{OH})_2$  particles were expected to supply nucleation sites in seawater electrolyte for the newly formed  $\text{Mg}(\text{OH})_2$ , resulting in new  $\text{Mg}(\text{OH})_2$  precipitate being deposited in the electrolyte but not on the HER electrode surface. As shown in Fig. 3c and S14,† the precipitation on the  $\text{Ni}(\text{OH})_2$ -NF electrode in SW + AEM ( $3.2 \text{ mg cm}^{-2}$ ) obviously decreased after the addition of  $\text{Mg}(\text{OH})_2$  in seawater (SW +  $\text{Mg}(\text{OH})_2$  + AEM,  $0.4 \text{ mg cm}^{-2}$ ), but the effect on the NF electrode was insignificant. Additionally, the electrolytic cell without AEM was also investigated, in which case the working electrode chamber would be sustainably supplied with  $\text{Mg}^{2+}$  ions from the counter electrode during the measurement. As a result, in seawater, the precipitation mass for the  $\text{Ni}(\text{OH})_2$ -NF electrode increased significantly from  $3.2$  to  $38.5 \text{ mg cm}^{-2}$ , but only increased slightly from  $0.4$  to  $0.9 \text{ mg cm}^{-2}$  in SW +  $\text{Mg}(\text{OH})_2$  (Fig. 3c). It was demonstrated that the  $\text{Ni}(\text{OH})_2$  membrane assisted by saturated  $\text{Mg}(\text{OH})_2$  in seawater can dramatically reduce the precipitation on the HER surface, and the reduction in mass percentage reached 98.3%. Therefore, the lower precipitation on the electrode brought about higher stability for the  $\text{Ni}(\text{OH})_2$ -NF electrode (Fig. S15†).

We then evaluated the stability of the  $\text{Ni}(\text{OH})_2$  membrane by prolonging the test time. As demonstrated in Fig. 3d and S16,† the NF and  $\text{Ni}(\text{OH})_2$ -NF electrodes were measured under SW +  $\text{Mg}(\text{OH})_2$  + AEM conditions every 20 h to obtain the precipitation mass over a total time of 100 h. The precipitation mass of the  $\text{Ni}(\text{OH})_2$ -NF electrode was much lower than that of NF over the whole test time. At the time of 100 h, the precipitation mass of the  $\text{Ni}(\text{OH})_2$ -NF electrode was  $5.3 \text{ mg cm}^{-2}$ , which was only 10.9% that of the NF electrode ( $48.5 \text{ mg cm}^{-2}$ ). Due to the accumulation of precipitation, the NF electrode exhibited poor stability with an increased overpotential of 56 mV compared to



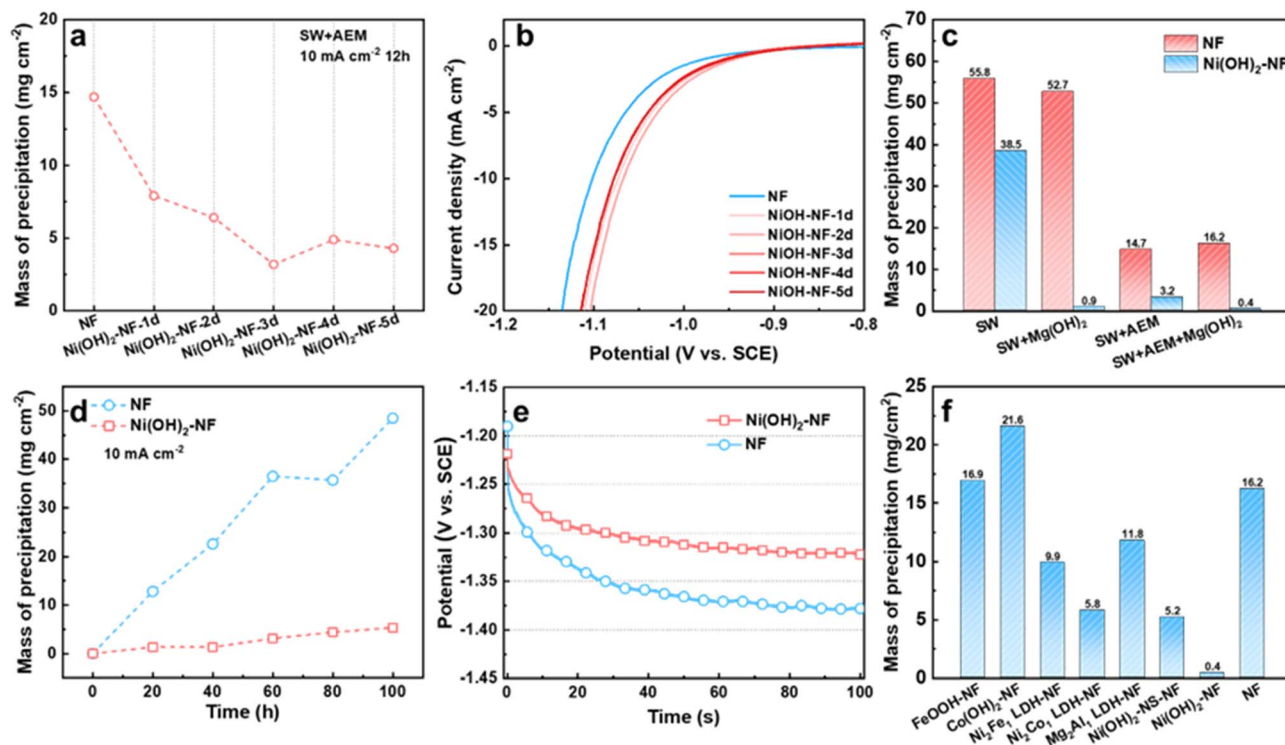


Fig. 3 (a) Mass of precipitation on the electrodes, and (b) the LSV curves of the electrodes under different deposition times. Mass of precipitation on the NF and Ni(OH)<sub>2</sub>-NF electrodes, (c) under different conditions, and (d) with different measure times. (e) Chronopotentiometry curves of NF and Ni(OH)<sub>2</sub>-NF electrodes with the electrolyte replaced every 20 h under a current density of 10 mA cm<sup>-2</sup>. (f) Mass of precipitation on the different kinds of hydroxide-decorated electrodes.

the Ni(OH)<sub>2</sub>-NF electrode at the measurement time of 100 h for the continuous test (Fig. 3e).

Finally, we also tried to obtain other hydroxide membranes decorated on NF with the same fabrication conditions as the Ni(OH)<sub>2</sub> membrane, such as FeOOH-NF, Co(OH)<sub>2</sub>-NF, Ni<sub>2</sub>Fe<sub>1</sub> LDH-NF, Ni<sub>2</sub>Co<sub>1</sub> LDH-NF, and Mg<sub>2</sub>Al<sub>1</sub> LDH-NF electrodes. For these electrodes, only the Ni<sub>2</sub>Co<sub>1</sub> LDH/NF electrode formed an Ni(OH)<sub>2</sub>-membrane-like structure (Fig. S17†), which exhibited higher anti-precipitation performance than the other electrodes, but much lower than that of the Ni(OH)<sub>2</sub>-NF electrode under SW + Mg(OH)<sub>2</sub> + AEM conditions (Fig. 3f, S18†). When the Ni(OH)<sub>2</sub> membrane was changed to nanosheets, such as an Ni(OH)<sub>2</sub>-NS-NF electrode, it displayed similar anti-precipitation performance to the Ni<sub>2</sub>Co<sub>1</sub> LDH-NF electrode. This indicated that the excellent anti-precipitation performance of the Ni(OH)<sub>2</sub>-NF electrode arose from the special structure of the Ni(OH)<sub>2</sub> membrane. Moreover, these hydroxide membranes would reduce the HER performance of NF, or display lower HER performance than that of the Ni(OH)<sub>2</sub>-NF electrode (Fig. S19†).

### Anti-precipitation mechanism

As described above, the Ni(OH)<sub>2</sub> membrane reduces the precipitation by hindering the transfer of Mg<sup>2+</sup> from the electrolyte to the electrode surface. To understand the mechanism, we quantified the transfer rate of Mg<sup>2+</sup> and compared it with the other ions. For the Ni(OH)<sub>2</sub> membrane on NF it was difficult to obtain the mass transfer rate of Mg<sup>2+</sup>, so we fabricated

numerous Ni(OH)<sub>2</sub>-NF electrodes and treated them with ultrasound to obtain an Ni(OH)<sub>2</sub> membrane turbid liquid. Via a vacuum filtration method,<sup>36</sup> an Ni(OH)<sub>2</sub> membrane with a thickness of 1.4 μm on a nylon filter membrane was prepared (Fig. S20†).

The Ni(OH)<sub>2</sub> membrane was then sealed with a 2 cm<sup>2</sup> opening in copper tape, and clamped in the test setup (Fig. 4a and S21†). Prior to the conductivity test, the relationship between conductivity (σ) and concentration (c) was determined for NaOH, NaCl, KCl, CaCl<sub>2</sub>, MgCl<sub>2</sub>, NaNO<sub>3</sub>, Na<sub>2</sub>CO<sub>3</sub>, and Na<sub>2</sub>SO<sub>4</sub> solutions, which was log(σ) = a + log(c) (Fig. S22†). Then the conductivity change with time was measured for different concentrations of NaOH and MgCl<sub>2</sub> solutions (Fig. S23†). Finally, the ion permeation rate through the nylon membrane (substrate) and the Ni(OH)<sub>2</sub>-membrane-coated substrate was obtained. As shown in Fig. 4b, the ion permeation rate of the NaOH solution increased linearly with concentration for both substrate and Ni(OH)<sub>2</sub>-membrane-coated substrate, and the slopes for these two lines were very close. This suggested that the NaOH passed through the Ni(OH)<sub>2</sub> membrane almost without resistance, as the ion difference values of the permeation rates between the Ni(OH)<sub>2</sub>-membrane-coated substrate and the substrate were the ion hindrance rates in the Ni(OH)<sub>2</sub> membrane. However, for MgCl<sub>2</sub> solution (Fig. 4c), the linear slope of the Ni(OH)<sub>2</sub>-membrane-coated substrate was much lower than that of the substrate, indicating the obvious resistance for MgCl<sub>2</sub> to pass through the Ni(OH)<sub>2</sub> membrane. The



Fig. 4 (a) Schematic of  $\text{Ni}(\text{OH})_2$  membrane test setup. Ion permeation rates under different concentrations of (b)  $\text{NaOH}$  and (c)  $\text{MgCl}_2$  solutions. (d) Ion permeation rate versus ion hydrated diameter of the substrate and  $\text{Ni}(\text{OH})_2$ -membrane-coated substrate. (e) The calculated ion hindrance rate for the  $\text{Ni}(\text{OH})_2$  membrane. (f) XRD patterns of  $\text{Ni}(\text{OH})_2$  membrane powder after immersion in different solutions.

other solutions were measured at a concentration of 1 M using the same method (Fig. S24<sup>†</sup>), and the ion permeation rates for the  $\text{K}^+$ ,  $\text{Na}^+$ ,  $\text{Ca}^{2+}$ ,  $\text{Mg}^{2+}$ ,  $\text{NO}_3^-$ ,  $\text{SO}_4^{2-}$  and  $\text{CO}_3^{2-}$  passing through the substrate and  $\text{Ni}(\text{OH})_2$ -membrane-coated substrate were calculated. As listed in Fig. 4d, the cation permeation rates decreased with increasing hydrated diameter when passing through the  $\text{Ni}(\text{OH})_2$ -membrane-coated substrate, but with slight change through the substrate. For anions, the permeation rates decreased with the increasing hydrated diameter both in the substrate and in the  $\text{Ni}(\text{OH})_2$ -membrane-coated substrate. The difference in values of the ion permeation rates between the  $\text{Ni}(\text{OH})_2$  membrane-coated substrate and the substrate is the ion hindrance rate, which represents the ion transfer rate in the  $\text{Ni}(\text{OH})_2$  membrane. As displayed in Fig. 4e, the ion hindrance rates of  $\text{Mg}^{2+}$  and  $\text{Ca}^{2+}$  ( $2.97$  and  $2.84 \text{ mol m}^{-2} \text{h}^{-1}$ ) were much higher than those of  $\text{Na}^+$  and  $\text{K}^+$  ( $0.45$  and  $0.12 \text{ mol m}^{-2} \text{h}^{-1}$ ), which increased with the hydrated ion diameter. However,  $\text{NO}_3^-$ ,  $\text{SO}_4^{2-}$  and  $\text{CO}_3^{2-}$  exhibited similar hindrance rates ( $0.29$ – $0.37 \text{ mol m}^{-2} \text{h}^{-1}$ ), which were close to that of  $\text{Na}^+$ . The ion hindrance feature of the  $\text{Ni}(\text{OH})_2$  membrane, strong resistance for high-valence ions ( $\text{Mg}^{2+}$  and  $\text{Ca}^{2+}$ ) but weak resistance for low-valence ions ( $\text{K}^+$  and  $\text{Na}^+$ ) and reverse ions ( $\text{NO}_3^-$ ,  $\text{SO}_4^{2-}$  and  $\text{CO}_3^{2-}$ ), is consistent with the nanofiltration membrane.

The interlayer distance of the  $\text{Ni}(\text{OH})_2$  nanosheets was about  $0.46 \text{ nm}$  as calculated with the Bragg equation, even though the atom size was ignored, which was smaller than the hydrated diameters of the ions as described before, especially for the anions of  $\text{NO}_3^-$ ,  $\text{SO}_4^{2-}$  and  $\text{CO}_3^{2-}$ . The narrow interlayer distance would result in strong resistance to the transfer of the

anions. If the interlayering of  $\text{Ni}(\text{OH})_2$  nanosheets could transfer the ions rapidly, the interlayer distance should be expanded by ions such as  $\text{GO}$  or  $\alpha\text{-Ni}(\text{OH})_2$ , which could be obviously detected by XRD.<sup>37–39</sup> However, as shown in Fig. 4f, the position and width of the XRD diffraction peaks of the  $\text{Ni}(\text{OH})_2$  membrane were unchanged even though the  $\text{Ni}(\text{OH})_2$  membrane had been immersed in  $\text{H}_2\text{O}$  solution with 1 M of  $\text{NaCl}$ ,  $\text{NaOH}$ ,  $\text{NaNO}_3$ ,  $\text{Na}_2\text{CO}_3$  and  $\text{MgCl}_2$  for over one month. This suggested that no or only a very small amount of water or ions could be inserted in the layer space for the  $\text{Ni}(\text{OH})_2$  sheets. Therefore, it is very difficult for the ions to pass through the  $\text{Ni}(\text{OH})_2$  membrane via the interlayer of  $\text{Ni}(\text{OH})_2$  sheets, which is in accord with reports.<sup>40–43</sup> For the nanometer-scale cracks in Fig. 2i, the size of cracks with a width of  $0.4$ – $2.0 \text{ nm}$  was larger than the hydrated diameters of the ions, which ensured high permeation for all the tested ions.<sup>44</sup> However, the high-value cations of  $\text{Mg}^{2+}$  and  $\text{Ca}^{2+}$  encountered obviously higher resistance than anions with a similar hydrated diameter, which might be hindered by electrostatic repulsion due to the positively charged  $\text{Ni}(\text{OH})_2$  membrane.

In light of the molecular dynamics simulation, we investigated the ion transfer rate as the ions passed through the  $\text{Ni}(\text{OH})_2$  membrane and were affected by the positive charge. The optimized model of a monolayer  $\text{Ni}(\text{OH})_2$  sheet with an opening of  $3 \times 5$  Ni atoms is displayed in Fig. 5a. To simulate the transfer rate of  $\text{Mg}^{2+}$ ,  $\text{Na}^+$ ,  $\text{Cl}^-$ ,  $\text{OH}^-$  and  $\text{H}_2\text{O}$ , and to avoid the deposition interference between  $\text{Mg}^{2+}$  and  $\text{OH}^-$ , the simulation was divided into  $\text{MgCl}_2$  and  $\text{NaOH}$  solution systems, as shown in Fig. 5b and c. The  $\text{MgCl}_2$  and  $\text{NaOH}$  solution was up to



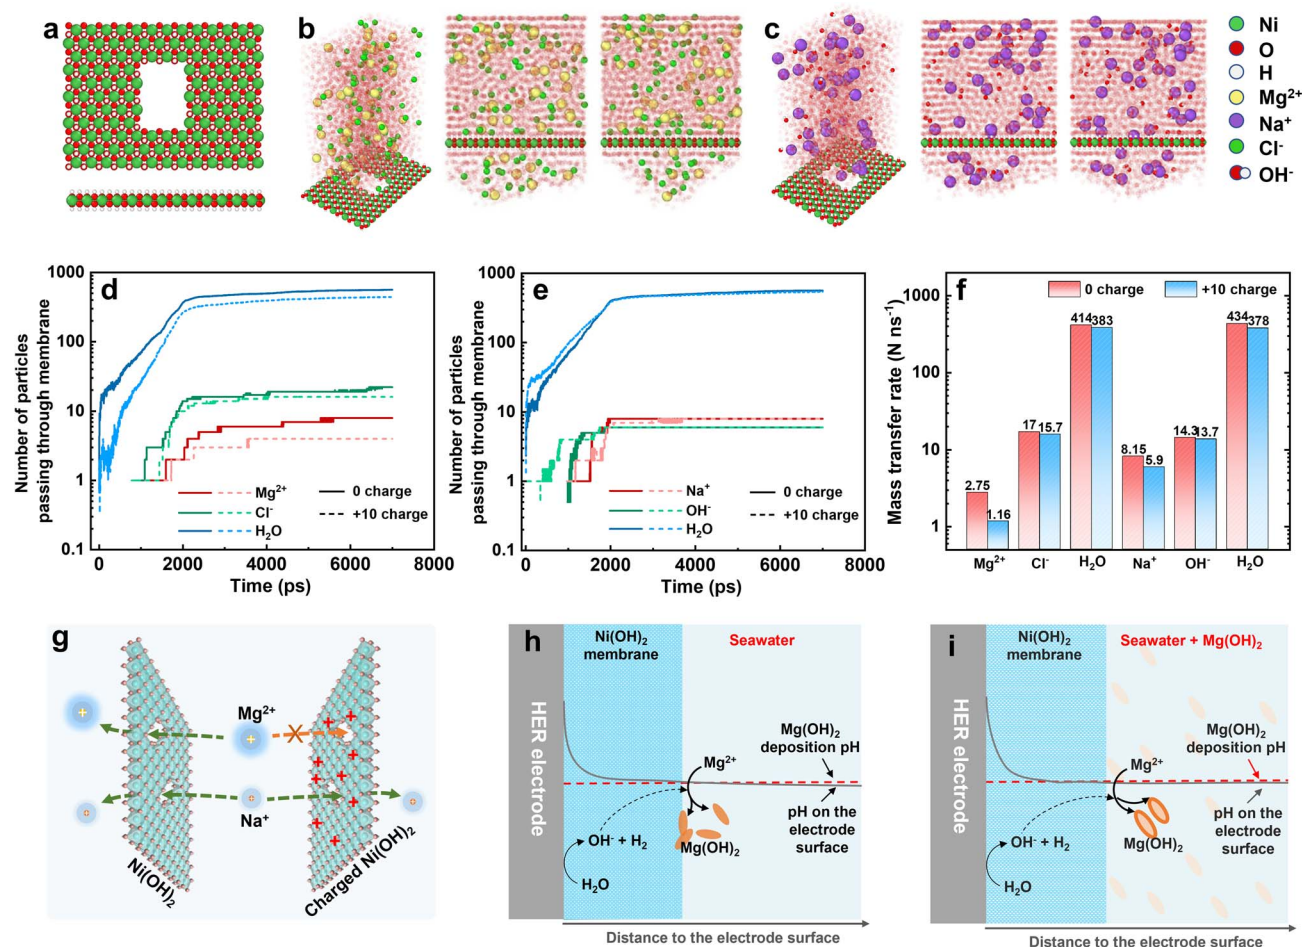


Fig. 5 Simulations of ion sieving for the Ni(OH)<sub>2</sub> membrane. (a) The optimized opening monolayer Ni(OH)<sub>2</sub> nanosheet structure in top and side view. Initial and final simulation snapshots of the (b) MgCl<sub>2</sub> and (c) NaOH solutions. The number of (d) Mg<sup>2+</sup>, Cl<sup>-</sup>, and H<sub>2</sub>O, (e) Na<sup>+</sup>, OH<sup>-</sup>, H<sub>2</sub>O, and (f) mass transfer rates of the simulated particles passing through the charged and uncharged Ni(OH)<sub>2</sub> nanosheet. (g) Ion sieving mechanism for the Ni(OH)<sub>2</sub> nanosheets with and without positive charge. Schematic illustration of (h) the precipitation mechanism on the HER electrode without an Ni(OH)<sub>2</sub> membrane in seawater, and (i) anti-precipitation mechanism for the Ni(OH)<sub>2</sub>-membrane-decorated HER electrode in seawater with saturated Mg(OH)<sub>2</sub>.

the Ni(OH)<sub>2</sub> sheet at 300 K and 1 atm and bounded with a simulation box. At the top of the MgCl<sub>2</sub> and NaOH solution, a transparent wall with 1 atm pressure drove the solution to pass through the opening on the Ni(OH)<sub>2</sub> sheet (Fig. S25 and S26†). The number of ions and water molecules that passed was counted by the LAMMPS software package and recorded in Fig. 5d and e, including the 0-charged and +10-charged Ni(OH)<sub>2</sub> models. Apart from Mg<sup>2+</sup>, the number of other ions and water molecules passing through the Ni(OH)<sub>2</sub> sheet with or without positive charge was unchanged or changed insignificantly. According to the slope, the number of ions or water molecules passing through the Ni(OH)<sub>2</sub> sheet with increasing time, the mass transfer rate was calculated as shown in Fig. 5f. When the Ni(OH)<sub>2</sub> sheet was positively charged, the mass transfer rate of Mg<sup>2+</sup> dropped by 57.8% from 2.75 to 1.16 no. ns<sup>-1</sup>, while Na<sup>+</sup> dropped by only 27.6% from 8.15 to 5.90 no. ns<sup>-1</sup>. The anions of Cl<sup>-</sup> and OH<sup>-</sup> and the water molecules were almost unchanged. This suggested that the positive charge on the Ni(OH)<sub>2</sub> sheet obviously changed the ion sieving behaviour, hindering high-

valence cations with much stronger resistance than those of low-valence cations, anions and molecules.

Therefore, the positively charged Ni(OH)<sub>2</sub> membrane can sieve out Mg<sup>2+</sup> with higher efficiency. For the Ni(OH)<sub>2</sub> membrane without charge, Mg<sup>2+</sup> and Na<sup>+</sup> can rapidly pass through the Ni(OH)<sub>2</sub> nanosheet *via* the crack-like defects, but not through the interlayer between Ni(OH)<sub>2</sub> layers (left-hand side of Fig. 5g). But for the Ni(OH)<sub>2</sub> membrane with positive charge, the electrostatic repulsive force between Mg<sup>2+</sup> ions and the Ni(OH)<sub>2</sub> nanosheet would lower the transfer rate of Mg<sup>2+</sup> ions, and evidently reduce the mass transfer rate of Mg<sup>2+</sup> ions passing through the Ni(OH)<sub>2</sub> membrane (right-hand side of Fig. 5g). This should illustrate that the higher mass transfer rate of water and Cl<sup>-</sup> was beneficial to passing a greater number of these than of Mg<sup>2+</sup>, Na<sup>+</sup> or OH<sup>-</sup>. Therefore, normalizing the mass transfer rates to the number (percentage transfer rate) makes the comparison easier. As listed in Table S1,† the rank of ion transfer rate was OH<sup>-</sup> > Cl<sup>-</sup> > Na<sup>+</sup> > Mg<sup>2+</sup>, which is associated with the ionic diffusion coefficient.<sup>45</sup>





Fig. 6 (a) A schematic illustration of a direct seawater electrolyser equipped with an  $\text{Ni}(\text{OH})_2\text{-Pt-NF}$  electrode. (b) The polarization curves of an  $\text{Ni}(\text{OH})_2\text{-Pt-NF}$ -electrode-equipped electrolyser in different electrolytes. (c) Galvanostatic discharge curves of electrolyzers at a current density of  $100 \text{ mA cm}^{-2}$  and (d) mass of precipitation on the  $\text{Ni}(\text{OH})_2\text{-Pt-NF}$  and  $\text{Pt-NF}$  electrodes (inset: photographs of the HER electrodes after 100 h of measurement).

Combining the anti-precipitation performance and ion transfer behaviour of the  $\text{Ni}(\text{OH})_2$  membrane, the anti-precipitation mechanism of the  $\text{Ni}(\text{OH})_2\text{-NF}$  electrode is illustrated below. For the HER electrode with an  $\text{Ni}(\text{OH})_2$  membrane in seawater (Fig. 5h), the pH on the surface would increase dramatically at the begin of HER process, but the  $\text{Mg}^{2+}$  could not pass through the  $\text{Ni}(\text{OH})_2$  membrane to form the precipitate. With increasing time, the out-diffusion of  $\text{OH}^-$  would raise the pH on the interface between the  $\text{Ni}(\text{OH})_2$  membrane and seawater to reach the deposition pH, so the formed  $\text{Mg}(\text{OH})_2$  would be deposited both on the  $\text{Ni}(\text{OH})_2$  membrane and in seawater. Hence, in seawater, the  $\text{Ni}(\text{OH})_2$  membrane could reduce the electrode precipitation, but the effect was slight.

When the seawater had saturated  $\text{Mg}(\text{OH})_2$  added (Fig. 5i), the pH on the  $\text{Ni}(\text{OH})_2$  membrane surface would reach the  $\text{Mg}(\text{OH})_2$  deposition pH at the initial operation time. After operation, the seawater pH near the  $\text{Ni}(\text{OH})_2$  membrane surface would soon be slightly higher than the  $\text{Mg}(\text{OH})_2$  deposition pH to deposit  $\text{Mg}^{2+}$ . Meanwhile, the saturated  $\text{Mg}(\text{OH})_2$  particles in the seawater supplied abundant nucleation sites for the newly formed  $\text{Mg}(\text{OH})_2$ . Therefore, most of the  $\text{Mg}(\text{OH})_2$  was deposited in the saturated  $\text{Mg}(\text{OH})_2$  seawater, and only a little  $\text{Mg}(\text{OH})_2$  was adsorbed on the  $\text{Ni}(\text{OH})_2$  membrane surface. This

is the mechanism whereby the  $\text{Ni}(\text{OH})_2\text{-NF}$  electrode exhibits excellent anti-precipitation performance in saturated  $\text{Mg}(\text{OH})_2$  seawater. If the HER electrode without an  $\text{Ni}(\text{OH})_2$  membrane was operated directly in saturated  $\text{Mg}(\text{OH})_2$  seawater (Fig. S27<sup>†</sup>), the much higher pH on the electrode surface would also make it a faster nucleation site than that in seawater, which could not decrease the precipitation on the electrode surface.

### Anti-precipitation membrane application

To broaden the application scope of the  $\text{Ni}(\text{OH})_2$  membrane and enhance its seawater HER performance, we chose Pt-based  $\text{Ni}(\text{OH})_2\text{-Pt-NF}$  and  $\text{Pt-NF}$  electrodes to replace the  $\text{Ni}(\text{OH})_2\text{-NF}$  and  $\text{NF}$  electrodes. As displayed in Fig. S28<sup>†</sup>, the Pt nanoparticles were uniformly dispersed on the surface of NF for the  $\text{Pt-NF}$  electrode, and the covered  $\text{Ni}(\text{OH})_2$  membrane exhibited similar structure and thickness to those of the  $\text{Ni}(\text{OH})_2\text{-NF}$  electrode. Due to the high activity of Pt, the  $\text{Pt-NF}$  and  $\text{Ni}(\text{OH})_2\text{-Pt-NF}$  electrodes as expected displayed obviously higher performance than that of the  $\text{NF}$  electrode (Fig. S29<sup>†</sup>). To further verify the anti-precipitation performance of the membrane-decorated electrode in application, we assembled a flow-type direct seawater electrolyser equipped with an





Ni(OH)<sub>2</sub>-Pt-NF HER electrode and Cr<sub>2</sub>O<sub>3</sub>-IrRuO<sub>2</sub>-Ti OER electrode (Fig. 6a) with a working area of 10 cm<sup>2</sup>. Moreover, to lessen the trapped bulky Mg(OH)<sub>2</sub> particles in the NF pores of the HER electrode, we chose a PP/PE porous membrane as a diaphragm, and the electrolyte was fed only into the anode side to filter the bulky particles. Due to the higher pH of SW + Mg(OH)<sub>2</sub>, the electrolyser in SW + Mg(OH)<sub>2</sub> exhibited much higher performance than that in seawater (Fig. 6b). The cell voltage (with 75% *iR* compensation) at 40 °C of the electrolyser in SW + Mg(OH)<sub>2</sub> was only 2.69 V at a current density of 500 mA cm<sup>-2</sup>, while it was over 3.1 V in seawater and 2.29 V in seawater with 1 M NaOH. For the 100 h stability test at a current density of 100 mA cm<sup>-2</sup>, the seawater electrolyser equipped with Ni(OH)<sub>2</sub>-Pt-NF and Pt-NF electrodes had a similar cell voltage close to 2.4 V at the beginning (Fig. 6c). With increasing time, the seawater electrolyser voltage of the Pt-NF electrode increased faster than that of the Ni(OH)<sub>2</sub>-Pt-NF electrode. For example, at a time of 100 h, the voltage reached 2.97 V for the Pt-NF-electrode-equipped seawater electrolyser, but it was only 2.48 V for the Ni(OH)<sub>2</sub>-Pt-NF electrode. That means the Ni(OH)<sub>2</sub>-Pt-NF electrode is much more stable than the Pt-NF electrode in seawater. Combined with the result in Fig. 3, the higher voltage of the Pt-NF-electrode-equipped seawater electrolyser was mainly caused by the greater precipitation on the electrode (Fig. 6d and S30†). At 100 h, the precipitation mass on the Ni(OH)<sub>2</sub>-Pt-NF electrode was 0.82 mg cm<sup>-2</sup>, which was only 8.1% that of the Pt-NF electrode (10.06 mg cm<sup>-2</sup>). Besides, the Ni(OH)<sub>2</sub>-Pt-NF electrode also exhibited higher anti-precipitation performance and stability than the Pt-NF electrode in a magnesium seawater battery (Fig. S31†). The results once again confirmed that an Ni(OH)<sub>2</sub> membrane on the electrode can obviously decrease the electrode surface precipitation to enhance its stability.

## Conclusions

In summary, an Ni(OH)<sub>2</sub> nanofiltration membrane *in situ* grown on a 3D NF-based electrode was fabricated at room temperature *via* a simple chemical soaking method. Simulations and experiments revealed that the positively charged Ni(OH)<sub>2</sub> membrane with nanometer-scale cracks evidently hindered the transfer of Mg<sup>2+</sup> and Ca<sup>2+</sup>, while rapidly transferring OH<sup>-</sup> and H<sub>2</sub>O. In seawater, the Ni(OH)<sub>2</sub>-membrane-decorated Ni(OH)<sub>2</sub>-NF HER cathode reduced the Mg<sup>2+</sup>-ion-induced precipitation on the electrode surface compared to the NF cathode. Due to the abundant nucleation sites from the added saturated Mg(OH)<sub>2</sub> in seawater at the initial operation, the Ni(OH)<sub>2</sub>-NF cathode further dramatically reduced the precipitation by about 98.3%. Moreover, the Ni(OH)<sub>2</sub>-NF electrode exhibited slightly higher HER activity and stability than the NF electrode due to the rapid transfer of OH<sup>-</sup> and H<sub>2</sub>O, the synergistic effect between Ni(OH)<sub>2</sub> and the Ni substrate, and the excellent anti-precipitation performance. In the application of a direct seawater electrolyser and MSWB, the Ni(OH)<sub>2</sub>-Pt-NF electrode also displayed high anti-precipitation performance and good stability for 100 h of measurement. We believe that this work highlights a potential

strategy to solve HER electrode precipitation in seawater *via* an ingenious electrode structure design.

## Data availability

Data will be made available on request.

## Author contributions

Q. Liu: conceptualization, methodology, investigation, writing – original draft preparation, writing – review & editing, funding acquisition. Z. Yan: methodology, funding acquisition. J. Gao: methodology. H. Fan: methodology. M. Li: methodology. E. Wang: funding acquisition, project administration.

## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

The authors greatly acknowledge the financial support from the National Natural Science Foundation of China (22202203), the Strategic Priority Research Program of the Chinese Academy of Sciences (XDA 22010601), and the National Natural Science Foundation of China (grant no. 22005299). The authors would also like to thank Prof. Zhenbo Wang from the School of Chemistry and Chemical Engineering, Harbin Institute of Technology for help with the writing.

## References

- 1 X. Li, C. Deng, Y. Kong, Q. Huo, L. Mi, J. Sun, J. Cao, J. Shao, X. Chen, W. Zhou, M. Lv, X. Chai, H. Yang, Q. Hu and C. He, *Angew. Chem., Int. Ed.*, 2023, **62**, e202309732.
- 2 X. Li, H. Zhang, Q. Hu, W. Zhou, J. Shao, X. Jiang, C. Feng, H. Yang and C. He, *Angew. Chem., Int. Ed.*, 2023, **62**, e202300478.
- 3 Q. Hu, K. Gao, X. Wang, H. Zheng, J. Cao, L. Mi, Q. Huo, H. Yang, J. Liu and C. He, *Nat. Commun.*, 2022, **13**, 3958.
- 4 J. Tang, X. Xu, T. Tang, Y. Zhong and Z. Shao, *Small Methods*, 2022, **6**, 2201099.
- 5 M. S. Genc, M. Celik and I. Karasu, *Renewable Sustainable Energy Rev.*, 2012, **16**, 6631–6646.
- 6 M. Chatenet, B. G. Pollet, D. R. Dekel, F. Dionigi, J. Deseure, P. Millet, R. D. Braatz, M. Z. Bazant, M. Eikerling, I. Staffell, *et al.*, *Chem. Soc. Rev.*, 2022, **51**, 4583–4762.
- 7 G. Calado and R. Castro, *Appl. Sci.*, 2021, **11**, 5561.
- 8 S. Dresch, F. Dionigi, M. Klingenhof and P. Strasser, *ACS Energy Lett.*, 2019, **4**, 933–942.
- 9 W. M. Tong, M. Forster, F. Dionigi, S. Dresch, R. S. Erami, P. Strasser, A. J. Cowan and P. Farras, *Nat. Energy*, 2020, **5**, 367–377.
- 10 Y. Kuang, M. J. Kenney, Y. T. Meng, W. H. Hung, Y. J. Liu, J. E. Huang, R. Prasanna, P. S. Li, Y. P. Li, L. Wang, *et al.*, *Proc. Natl. Acad. Sci. U. S. A.*, 2019, **116**, 6624–6629.



- 11 S. Bolar, S. Shit, N. Chandra Murmu and T. Kuila, *Sustainable Energy Fuels*, 2021, **5**, 5915–5945.
- 12 S. Khatun, H. Hirani and P. Roy, *J. Mater. Chem. A*, 2021, **9**, 74–86.
- 13 D. W. Kirk and A. E. Ledas, *Int. J. Hydrogen Energy*, 1982, **7**, 925–932.
- 14 J. H. Han, *ChemSusChem*, 2022, **15**, e202200372.
- 15 X. Y. Lu, J. Pan, E. Lovell, T. H. Tan, Y. H. Ng and R. Amal, *Energy Environ. Sci.*, 2018, **11**, 1898–1910.
- 16 Z. T. Li, X. T. Xu, X. R. Sheng, P. Lin, J. Tang, L. K. Pan, Y. V. Kaneti, T. Yang and Y. Yamauchi, *ACS Nano*, 2021, **15**, 12535–12566.
- 17 U. G. M. Ekanayake, D. H. Seo, K. Faershteyn, A. P. O'Mullane, H. Shon, J. MacLeod, D. Golberg and K. Ostrikov, *Sustainable Mater. Technol.*, 2020, **25**, e00181.
- 18 J. H. Han, *Ind. Eng. Chem. Res.*, 2022, **61**, 9165–9170.
- 19 P. Srimuk, X. Su, J. Yoon, D. Aurbach and V. Presser, *Nat. Rev. Mater.*, 2020, **5**, 517–538.
- 20 E. Jwa, N. Jeong, J. Y. Nam and J. I. Han, *Water Res.*, 2022, **220**, 118681.
- 21 Q. F. Liu, Z. Yan, E. D. Wang, S. L. Wang and G. Q. Sun, *Int. J. Hydrogen Energy*, 2017, **42**, 23045–23053.
- 22 I. W. P. Chen, C. H. Hsiao, J. Y. Huang, Y. H. Peng and C. Y. Chang, *ACS Appl. Mater. Interfaces*, 2019, **11**, 14159–14165.
- 23 W. L. Yu, Z. Chen, Y. L. Fu, W. P. Xiao, B. Dong, Y. M. Chai, Z. X. Wu and L. Wang, *Adv. Funct. Mater.*, 2022, **33**, 2210855.
- 24 J. H. Han, E. Jwa, H. Lee, E. J. Kim, J. Y. Nam, K. S. Hwang, N. Jeong, J. Choi, H. Kim, Y. C. Jeung, *et al.*, *Chem. Eng. J.*, 2022, **429**, 132383.
- 25 Y. Li, L. Xie and T. Su, *Carbon Manage.*, 2023, **14**, 2202167.
- 26 F. H. Adnan, S. Pontvianne, M. N. Pons and E. Mousset, *Chem. Eng. J.*, 2022, **431**, 133413.
- 27 O. Oloye and A. P. O'Mullane, *ChemSusChem*, 2021, **14**, 1767–1775.
- 28 H. Shi, T. Wang, J. Liu, W. Chen, S. Li, J. Liang, S. Liu, X. Liu, Z. Cai, C. Wang, D. Su, Y. Huang, L. Elbaz and Q. Li, *Nat. Commun.*, 2023, **14**, 3934.
- 29 T. F. O'Brien, T. V. Bommaraju and F. Hine, *Handbook of Chlor-Alkali Technology*, Springer, 2005.
- 30 J. Guo, Y. Zheng, Z. Hu, C. Zheng, J. Mao, K. Du, M. Jaroniec, S. Z. Qiao and T. Ling, *Nat. Energy*, 2023, **8**, 264–272.
- 31 M. Mohammad and M. Kaukhab, *J. Chem. Soc. Pak.*, 2011, **33**, 166–170.
- 32 I. Katsounaros, J. C. Meier, S. O. Klemm, A. A. Topalov, P. U. Biedermann, M. Auinger and K. J. J. Mayrhofer, *Electrochem. Commun.*, 2011, **13**, 634–637.
- 33 M. Auinger, I. Katsounaros, J. C. Meier, S. O. Klemm, P. U. Biedermann, A. A. Topalov, M. Rohwerder and K. J. Mayrhofer, *Phys. Chem. Chem. Phys.*, 2011, **13**, 16384–16394.
- 34 N. Danilovic, R. Subbaraman, D. Strmcnik, K. C. Chang, A. P. Paulikas, V. R. Stamenkovic and N. M. Markovic, *Angew. Chem., Int. Ed.*, 2012, **51**, 12495–12498.
- 35 X. W. Yu, J. Zhao, L. R. Zheng, Y. Tong, M. Zhang, G. C. Xu, C. Li, J. Ma and G. Q. Shi, *ACS Energy Lett.*, 2018, **3**, 237–244.
- 36 H. Ang and L. Hong, *J. Mater. Chem. A*, 2017, **5**, 20598–20602.
- 37 Q. Yang, Y. Su, C. Chi, C. T. Cherian, K. Huang, V. G. Kravets, F. C. Wang, J. C. Zhang, A. Pratt, A. N. Grigorenko, *et al.*, *Nat. Mater.*, 2017, **16**, 1198–1202.
- 38 J. Abraham, K. S. Vasu, C. D. Williams, K. Gopinadhan, Y. Su, C. T. Cherian, J. Dix, E. Prestat, S. J. Haigh, I. V. Grigorieva, *et al.*, *Nat. Nanotechnol.*, 2017, **12**, 546–550.
- 39 D. S. Hall, D. J. Lockwood, C. Bock and B. R. MacDougall, *Proc. R. Soc. A*, 2015, **471**, 20140792.
- 40 Y. Qu, Q. G. Zhang, F. Soyekwo, R. S. Gao, R. X. Lv, C. X. Lin, M. M. Chen, A. M. Zhu and Q. L. Liu, *Nanoscale*, 2016, **8**, 18428–18435.
- 41 J. Hu, X. Tang, Q. Dai, Z. Liu, H. Zhang, A. Zheng, Z. Yuan and X. Li, *Nat. Commun.*, 2021, **12**, 3409.
- 42 L. Shi, Z. Ying, A. Xu and Y. Cheng, *J. Phys. Chem. C*, 2021, **125**, 1240–1248.
- 43 P. Sun, R. Ma, X. Bai, K. Wang, H. Zhu and T. Sasaki, *Sci. Adv.*, 2017, **3**, e1602629.
- 44 L. Wang, M. S. H. Boutilier, P. R. Kidambi, D. Jang, N. G. Hadjicostantinou and R. Karnik, *Nat. Nanotechnol.*, 2017, **12**, 509–522.
- 45 W. M. Haynes, D. R. Lide and T. J. Bruno, *CRC Handbook of Chemistry and Physics*, CRC Press, 95th edn, 2014, pp. 1–2666.

