


PAPER

[View Article Online](#)
[View Journal](#) | [View Issue](#)Cite this: *Nanoscale Adv.*, 2024, 6, 2328Stability and photocurrent enhancement of photodetectors by using core/shell structured CsPbBr₃/TiO₂ quantum dots and 2D materials†Chathurika Maduwanthi,^a Chao-An Jong,^b Waleed S. Mohammed^c and Shu-Han Hsu *^a

Ultra-stable CsPbBr₃ perovskite quantum dots (QDs) were prepared, and the performance of the photodetector fabricated from them was enhanced by 2D material incorporation. This multi-component photodetector appears to have good stability in the ambient utilization environment. All inorganic CsPbBr₃ QDs are potential candidates for application in photodetection devices. However, QDs have several issues such as defects on the QD surface, degradation under environmental conditions, and unfavorable carrier mobility limiting the high performance of the photodetectors. This work addresses these issues by fabricating a core/shell structure and introducing 2D materials (MXenes, Ti₃C₂T_x) into the device. Here, three types of photodetectors with QDs only, QDs with a core/shell structure, and QDs with a core/shell structure and MXenes are fabricated for systematic study. The CsPbBr₃/TiO₂ photodetector demonstrated a two times photocurrent enhancement compared to bare QDs and had good device stability after TiO₂ shell coating. After introducing Ti₃C₂T_x into CsPbBr₃/TiO₂, a significant photocurrent enhancement from nanoampere (nA) to microampere (μA) was observed, revealing that MXenes can improve the photoelectric response of perovskite materials significantly. Higher photocurrent can avoid signal interference from environmental noise for better practical feasibility. This study provides a systematic understanding of the photocurrent conversion of perovskite quantum dots that is beneficial in advancing optoelectronic device integration, especially for flexible wearable device applications.

Received 19th December 2023
Accepted 18th March 2024

DOI: 10.1039/d3na01129a

rsc.li/nanoscale-advances

1. Introduction

In recent years, hybrid organic–inorganic perovskite materials have attracted tremendous attention, owing to their outstanding photoelectronic properties such as large absorption cross-section, long photo carrier diffusion lengths and high charge carrier mobilities.^{1,2} Inorganic perovskite materials are emerging with all the above superiorities while exhibiting enhanced stability compared to hybrid organic–inorganic perovskites.³ There are many studies on fully inorganic cesium-based perovskite (CsPbX₃; X = Cl/Br/I) quantum dots (QD) due to their excellent optical and electrical properties.

Quantum dots (QDs) are nano-sized semiconductor crystals that have garnered significant attention due to their distinctive

characteristics, particularly their optical properties, leading to extensive applications in diverse fields such as solar cells, light-emitting diodes, laser technology, as well as biological and biomedical domains.^{4–6} The unique attributes of QDs include their small size (ranging from 4 to 12 nm in diameter), size-tunable photoluminescence (PL) emission, high extinction coefficient, elevated fluorescence quantum yield, resistance to photobleaching, and the occurrence of fluorescence intermittency.^{7,8} However, perovskite QDs degrade faster when exposed to moisture, oxygen, elevated temperatures, or UV light. Besides, environmental concerns are particularly significant issues in most perovskite QDs due to the presence of lead (Pb), a heavy metal.⁹ The research community made significant efforts to enhance the stability of perovskite by embedding QDs within a polymer matrix or inorganic salts, surface modification with waterproof capping ligands, introduction of long-chain ligands to passivate QDs, and fabrication of a core/shell structure to enhance QD stability.^{10,11}

Among the different methods to improve the perovskite QDs' stability, metal oxide encapsulation is considered to be the most beneficial. It not only protects from environmental degradation but can also serve as an efficient photocurrent transfer path. To the best of our knowledge, only a few studies were carried out to

^aSchool of Integrated Science and Innovation, Sirindhorn International Institute of Technology, Thammasat University, Pathum Thani, 12120, Thailand. E-mail: shuhanhsu@siit.tu.ac.th

^bTaiwan Semiconductor Research Institute, National Applied Research Laboratories, Hsinchu 300091, Taiwan, ROC

^cCenter of Research in Optoelectronics, Communication and Control Systems (BU-CROCCS), Bangkok University, Pathum Thani 12120, Thailand

† Electronic supplementary information (ESI) available. See DOI: <https://doi.org/10.1039/d3na01129a>

encapsulate CsPbBr₃ nanocrystals (NCs) with a titanium precursor to obtain a CsPbBr₃/TiO₂ core/shell structure. Z. J. Li *et al.* demonstrated the photostability improvement of TiO₂ shell coated CsPbBr₃ core/shell NCs with excellent water stability for over 12 weeks.¹⁰ H. Chen *et al.* demonstrated a long lifetime of CsPbBr₃/TiO₂ nanocrystals of about 4.04 ns of photoluminescence, and it remains stable after a period of two months in air.¹² Among different phases of TiO₂, the anatase phase of TiO₂ demonstrates higher electron extraction properties, providing an efficient pathway to transport excited electrons from QDs. Furthermore, TiO₂ can protect QDs from degradation from external factors, which is crucial for developing optoelectronic devices.¹³

In recent years, perovskite layer-based photodetectors (PDs) have received tremendous attention due to the perovskite's exceptional optoelectronic properties. Flexible photodetectors (FPDs), which form the core elements of flexible optoelectronic systems, play vital roles in various areas such as modern industrial production, scientific research, medical diagnosis and military defense.¹⁴ MXenes are a relatively new branch of 2D materials, which has the common formula of M_{n+1}X_nT_x (*n* = 1, 2 or 3). Ti₃C₂T_x is the most common and easily synthesized type of MXene. T_x denotes the surface functional groups such as -O, -OH, and -F which determine the exceptional properties of hydrophilic surfaces, high surface reactivity, and excellent optoelectronic properties. Ti₃C₂T_x is observed to be a p-type semiconductor and displays exceptional electrical conductivity, due to the diverse surface groups and the underlying metal layers.¹⁵ Recently, several researchers have reported the development of FPDs featuring perovskites/MXene heterojunctions. Pan *et al.* developed a simple photodetector based on the CsPbBr₃/Ti₃C₂T_x nanocomposites, revealing that MXene can effectively facilitate the transportation of photoexcited carriers and is a promising candidate for contact materials. Furthermore, it was demonstrated that photoluminescence (PL) quenching in CsPbBr₃/Ti₃C₂T_x indicates the presence of efficient nonradiative pathways for the integrated materials.^{16–18}

In spite of the fact that several previous studies stated the possibility of sufficiently enhancing the photocurrent by using a TiO₂ shell, there were no direct reports of photodetector devices fabricated to provide systematic validation. Hence, this work aims to develop a photodetector made of perovskite-based core/shell structure quantum dots with MXenes. This combines

the advantage of TiO₂ as a core/shell structure for stability improvement with 2D conductive MXene nanomaterials for efficient electron transfer to achieve higher photocurrent generation. This could have the potential to advance the field of FPDs in future applications. In order to demonstrate the improvement of the individual factors, three types of photodetectors (PDs) were fabricated: a photodetector with CsPbBr₃ QDs (CsPbBr₃ QD PD), photodetector with a CsPbBr₃/TiO₂ core/shell structure (CsPbBr₃/TiO₂ PD) and photodetector with a CsPbBr₃/TiO₂ core/shell structure with MXenes (CsPbBr₃/TiO₂/MXene PD). A schematic 3D view of the three PDs is shown in Fig. 1. Full material characterization was performed such as PL intensity, UV-vis absorption and photocurrent stability and enhancement after confinement of QDs by using a TiO₂ layer. Furthermore, a CsPbBr₃/TiO₂/MXene PD was proposed and fabricated to investigate the improvement of photocurrent achieved due to efficient carrier transfer.

2. Experimental

2.1 Material preparation

Materials. Lead bromide (PbBr₂, 99.99%, Aladdin), cesium bromide (CsBr, 99.99%, Aladdin), oleylamine (OAm, >99%, Aladdin), titanium(IV) butoxide (TBOT, 99.99%, Aladdin), and dimethylformamide (DMF) (99.8% extra dry over) were purchased from Thermo Fisher Scientific Inc, USA. Oleic acid (OA) (extra pure) and toluene (99.5%) were received from Quality Reagent Chemical Company, New Zealand.

Synthesis of CsPbBr₃ QDs. 0.1428 g of PbBr₂ (0.4 mmol) and 0.0425 g of CsBr (0.2 mmol) were dissolved in 5 ml of DMF to prepare a precursor solution. 0.5 ml of OA and 0.25 ml of OAm were added to the precursor solution for stabilization.¹⁹ Then 1 ml of the precursor solution was added to 10 ml of toluene under vigorous stirring (800 rpm) for 30 seconds. The supernatant from the obtained solution was separated by centrifugation at 6000 rpm for 10 minutes. Then the supernatant was kept for 2–3 days, to obtain the yellow color of CsPbBr₃ QDs. The whole experiment was conducted at room temperature.

Synthesis of the CsPbBr₃/TiO₂ core-shell structure. 10 ml of CsPbBr₃ QD solution (~1 mg ml⁻¹) was prepared by dissolving QDs in toluene. 10 μl of TBOT was dissolved in 1 ml of toluene and added to the QD solution dropwise. Then the solution was stirred for 2 hours for hydrolysis under controlled humidity

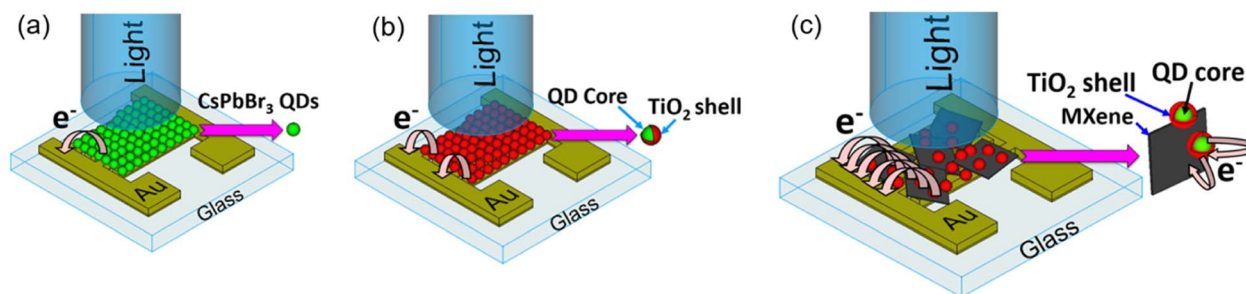


Fig. 1 Schematic 3D view of the fabricated photodetectors: (a) CsPbBr₃ QD device, (b) CsPbBr₃/TiO₂ device and (c) CsPbBr₃/TiO₂/MXene device.



conditions at 60–70% relative humidity (RH) at room temperature. The experiment was conducted inside a glove bag to control the humidity. The precipitate was collected by centrifugation at 5000 rpm for 5 minutes. Then the precipitate was calcined at 400 °C for 3 hours under an argon atmosphere.

Synthesis of $\text{Ti}_3\text{C}_2\text{T}_x$. Titanium-based MXene $\text{Ti}_3\text{C}_2\text{T}_x$ was synthesized through a minimally intensive layer delamination (MILD) method, from Ti_3AlC_2 phases. The synthesis process involved using a combination of lithium fluoride (LiF) and hydrochloric acid (HCl) as an *in situ* etchant. To enhance the quality of the etched and delaminated $\text{Ti}_3\text{C}_2\text{T}_x$, the synthesis was carried out with two etching cycles, each lasting 24 hours, using the same ratios of the MAX phase and LiF $\sim 1:7.5$. The first etching cycle took place at room temperature. In the second etching cycle, the reaction temperature was adjusted to 45 °C for the initial 6 hours, and then maintained at room temperature for the remaining time. The product solution was washed with DI water until pH reached around 5–6 and the resulting sediments were collected and dried at 70 °C for 24 hours to obtain the as-synthesized $\text{Ti}_3\text{C}_2\text{T}_x$ particles for further modification. For intercalation, the as-synthesized $\text{Ti}_3\text{C}_2\text{T}_x$ particles were dispersed in DMSO solvent at room temperature for 24 hours, with a ratio of 0.2 g $\text{Ti}_3\text{C}_2\text{T}_x$ in 15 ml DMSO. After multiple washing cycles with DI water, the delaminated $\text{Ti}_3\text{C}_2\text{T}_x$ was collected and dried at 60 °C for 24 hours.^{15,20}

2.2 Device fabrication

The glass substrate was cleaned using acetone. Then 30 nm/80 nm Cr/Au planar interdigitated electrodes were fabricated on the substrate by sputter deposition. The finger pattern is defined to be 200 μm in width and 200 μm in separation. Three different devices were used for the experiment: one with CsPbBr_3 QDs (CsPbBr_3 QDs PD), one with a $\text{CsPbBr}_3/\text{TiO}_2$ core/shell structure ($\text{CsPbBr}_3/\text{TiO}_2$ PD) and a photodetector with a $\text{CsPbBr}_3/\text{TiO}_2$ core/shell structure with MXenes ($\text{CsPbBr}_3/\text{TiO}_2/\text{MXene}$ PD). A blue laser was used as an excitation source with a spot area of 12.57 mm^2 that covers the whole sample. DMM6500 and SMU2450 were used to measure the corresponding current. CsPbBr_3 QDs (~ 10 mg) were drop cast onto the device. For the device with a core/shell structure, the sample synthesized from the same amount of QDs (~ 10 mg) was drop cast, and a further 2.5 mg of MXene was introduced with the core/shell structure sample.

2.3 Characterization

Transmission electron microscopy (TEM) of the QDs and the core/shell was performed using a JEM-2100 Plus with an accelerating voltage of 200 kV. Surface morphologies of photodetectors were examined using a field emission scanning electron microscope (SEM, VEGA3, TESCAN, Czech) with an acceleration voltage between 200 V and 30 kV, fitted with an EDX mapping tool (XMAX 80, OXFORD instruments). UV-vis spectra were collected using a Thermo Scientific GENESYS 10S spectrophotometer in the range from 300 nm to 700 nm, at 1 nm intervals. X-ray diffraction (XRD) (Bruker AXS model D8 Advance, Germany) was used to identify the crystal structure of QDs and core/

shell structured QDs. Photoluminescence (PL) was measured by using an optical spectrometer (Compact CCD spectrometer, Thorlabs, Newton, NJ, USA) connected to a multimode glass optical fiber (Thorlabs SMA multimode fiber, M35L01). Current and time responses of the perovskite devices were recorded using a digital multimeter (Keithley DMM6500). The device was biased using a regulated DC power supply (TPR3003T-3C, 0–30 V). The current–voltage characteristics of PDs were recorded by using a source measure unit (Keithley SMU2450). A blue dot laser ($\lambda = 450$ nm, 50 mW) was used as the light source for the photovoltaic (I – V) and time response measurements.

3. Results and discussion

3.1 Material characterization

The precursor solution for the synthesis of QDs was prepared by dissolving CsBr and PbBr_2 in a molar ratio of 1:2. This was done with the intention of obtaining pure QDs while avoiding the formation of Cs_4PbBr_6 .^{21–25} Fig. S1† shows the material characterization of QDs prepared by using a molar ratio of 1:1 of CsBr : PbBr_2 (ESI†). Fig. 2(a) illustrates the crystal structure of the CsPbBr_3 QDs with long ligands of OAm and OA. TBOT was selected as the Ti precursor, for coating of QDs with a TiO_2 layer. The hydrolysis process facilitated the gradual deposition of a titanium matrix (TiO_x) onto the surface of the QDs. Subsequently, a calcination process performed to dehydrate and remove the organic component at 400 °C, which was reported as the most suitable temperature for the calcination step without any decomposition of QDs.¹³

Fig. 2(b)–(d) illustrate CsPbBr_3 QDs, and QDs after the hydrolysis process and calcination process in toluene, respectively. CsPbBr_3 QDs, $\text{CsPbBr}_3/\text{TiO}_x$, and $\text{CsPbBr}_3/\text{TiO}_2$ samples are shown in Fig. 2(e)–(g) in the solid state. The samples of CsPbBr_3 QD after capping with TBOT still appear to be yellow. They however turn darker after calcination. This could be due to the fact that the originally obtained samples were in a powder form. Since the calcination process was carried out in an argon environment, the absence of oxygen during annealing resulted in an incomplete burning of carbon and organic residues on the surface of the $\text{CsPbBr}_3/\text{TiO}_2$ nanocrystals. This is evident from the dark appearance of the $\text{CsPbBr}_3/\text{TiO}_2$ powder after the calcination process.¹⁰

Fig. 2(h) shows the transmission electron microscopy (TEM) image of CsPbBr_3 QDs with a size of 9 ± 2 nm while Fig. 2(i) illustrates the TEM image of the core–shell structure of QDs. EDS characterization of the core–shell was performed further to validate the chemical composition of quantum dots and the TiO_2 structure (see ESI, Fig. S2†). Fig. 2(i) shows that CsPbBr_3 QDs are wrapped with a core/shell TiO_2 structure.²⁶ Some QDs, however, are surrounded interconnectedly by TiO_2 . This phenomenon is attributed to the incomplete hydrolysis of high-concentration TBOT on the surface of CsPbBr_3 QDs. Fig. 2(j) illustrates the lattice fringe pattern of $\text{CsPbBr}_3/\text{TiO}_2$. It depicts the 0.4 nm lattice fringe of CsPbBr_3 QDs and the 0.25 nm lattice fringe of TiO_2 . This observation highlights the establishment of a tight interface between CsPbBr_3 and TiO_2 .²⁷



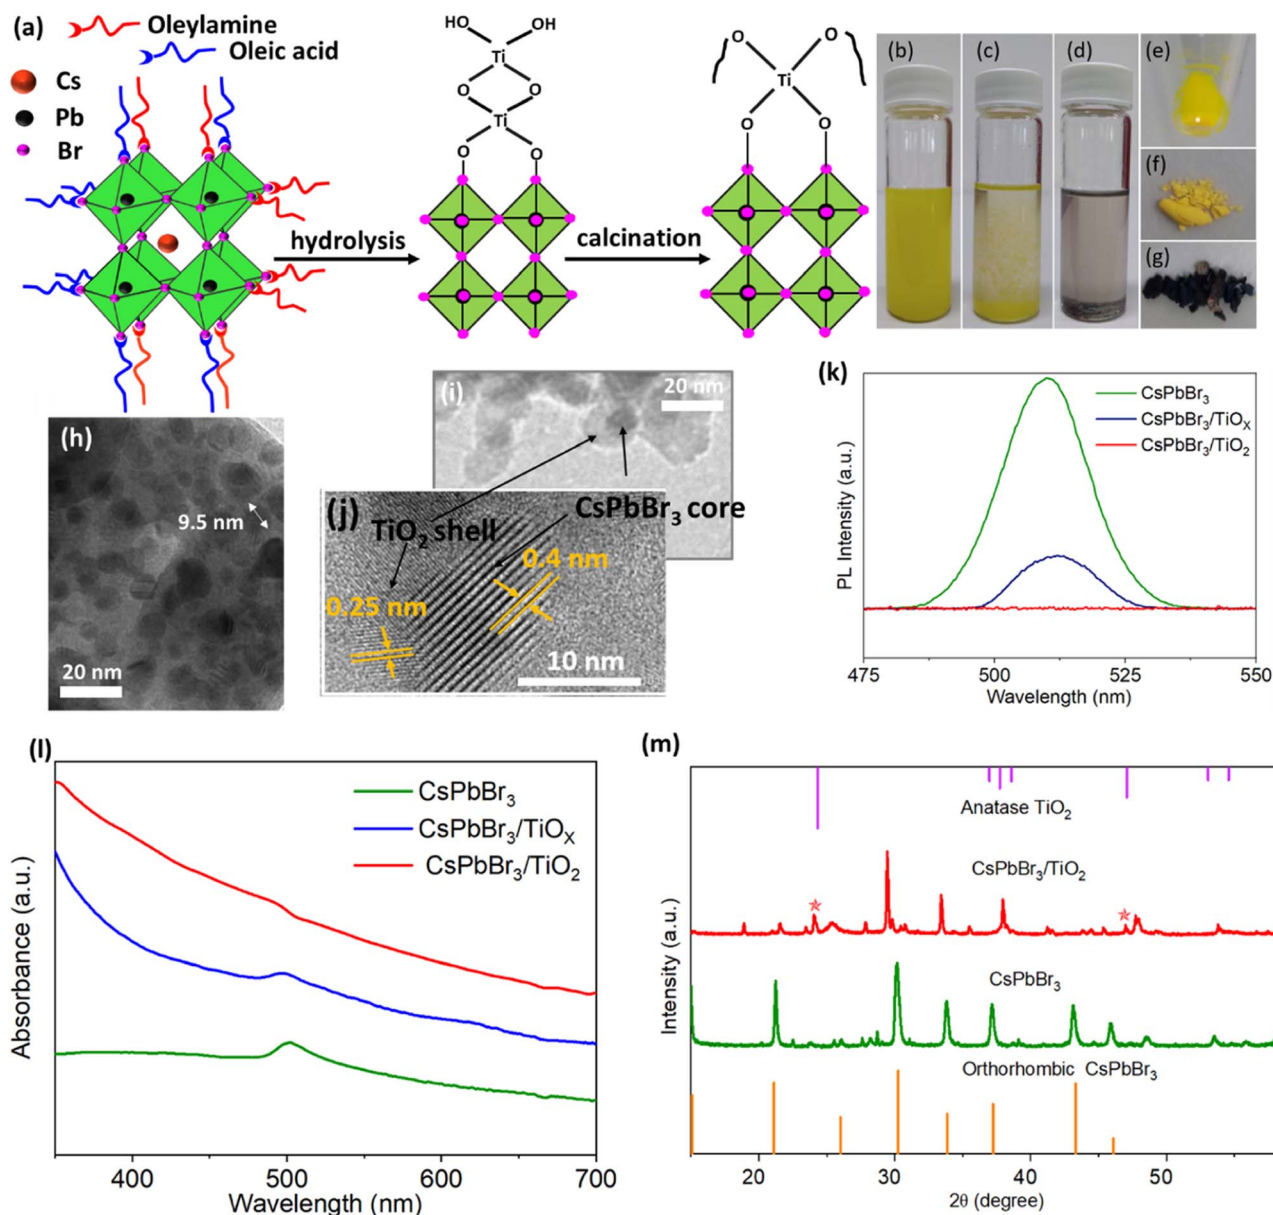


Fig. 2 (a) Schematic illustration of coating of CsPbBr₃ QDs, optical images of (b) CsPbBr₃ QDs (~1 mg mL⁻¹), (c) CsPbBr₃/TiO_x and (d) CsPbBr₃/TiO₂ in toluene, optical images of solid state (e) CsPbBr₃, (f) CsPbBr₃/TiO_x and (g) CsPbBr₃/TiO₂, TEM images of (h) CsPbBr₃ QDs (i) and (j) the CsPbBr₃/TiO₂ – core/shell structure, (k) PL intensity, (l) UV-visible absorption spectra of CsPbBr₃ QDs, CsPbBr₃/TiO_x and CsPbBr₃/TiO₂ and (m) XRD spectra of CsPbBr₃ QDs and CsPbBr₃/TiO₂.

PL intensity was varied for CsPbBr₃ QDs, CsPbBr₃/TiO_x, and CsPbBr₃/TiO₂ as shown in Fig. 2(k). The emission peak for bare QDs was 510 nm with a full width at half maximum (FWHM) of 19.7 nm. After hydrolysis, the emission intensity was reduced, and the emission peak changed to 512 nm with an FWHM of 16.4 nm. The red shift of CsPbBr₃/TiO_x is due to the agglomeration of the QDs bridged by the TiO₂ layer. PL quenching occurred after the coating of TiO₂ because the excited electrons from the conduction band of QDs under the illumination of blue laser light transfer to the layer of TiO₂, which provides a new pathway for transferring electrons.^{10,13}

UV visible absorption spectra of the CsPbBr₃ QDs, CsPbBr₃/TiO_x and CsPbBr₃/TiO₂ are shown in Fig. 2(l). One can observe a sharp absorption peak at 502 nm for CsPbBr₃ QDs while the absorption edge was blue shifted to 498 nm after the hydrolysis process. It is further blue shifted after the calcination process. Also, the absorption region < 400 nm was strong because of amorphous TiO₂ and carbon residues after TiO₂ coating.¹²

The X-ray diffraction (XRD) patterns of the CsPbBr₃ QDs and CsPbBr₃/TiO₂ are shown in Fig. 2(m). The XRD pattern confirms that the crystal structure of CsPbBr₃ exhibits an orthorhombic phase with identical peaks. The diffraction peaks at ~24.0° and

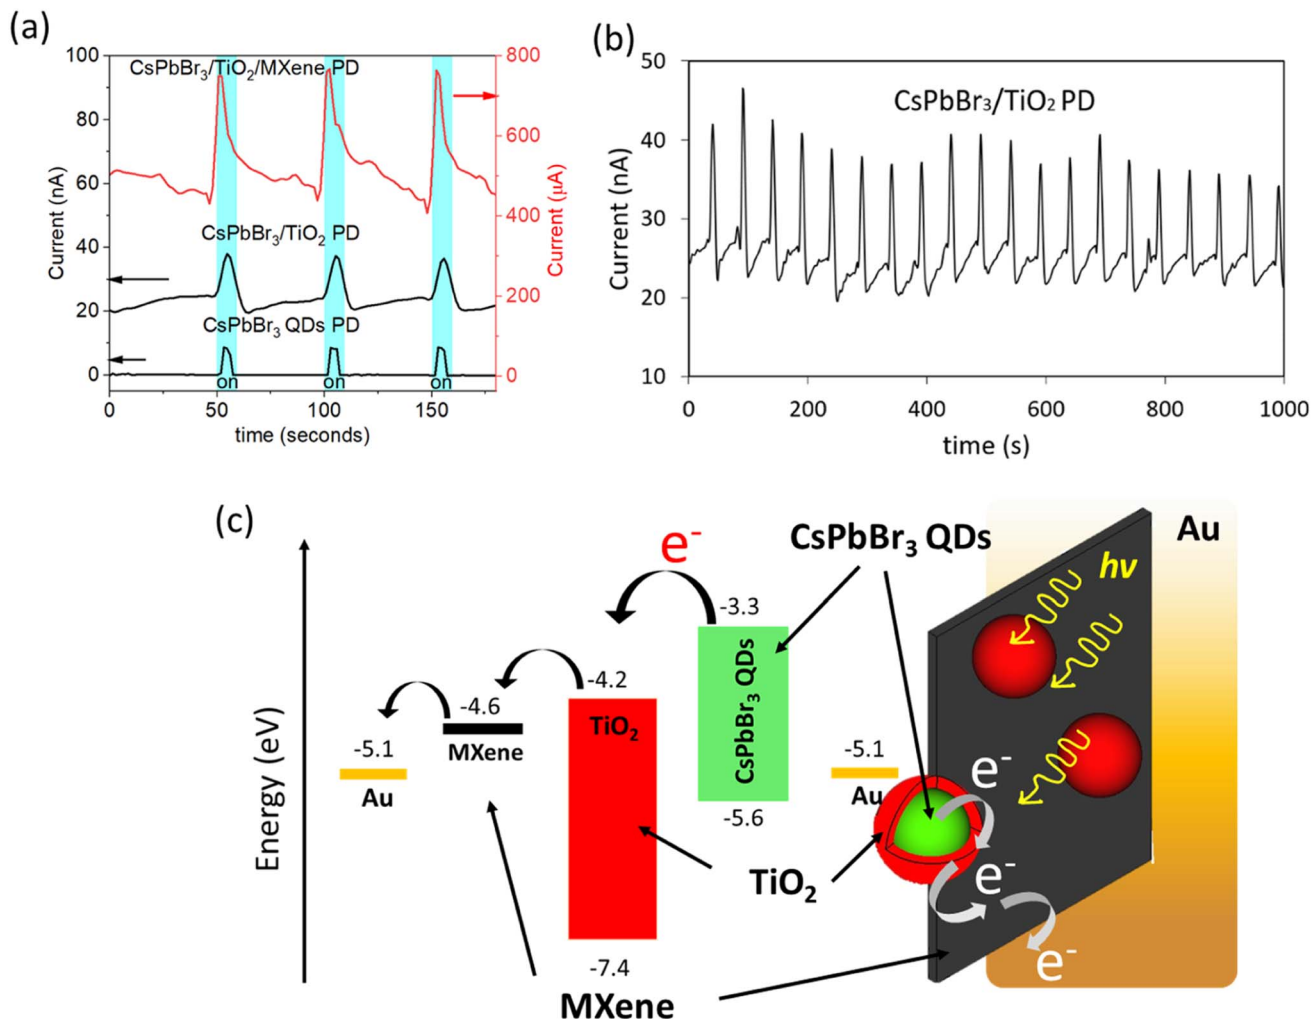


Fig. 3 (a) Photocurrent–time response measured in the dark and under the illumination of a blue laser with 5 V bias of three photodetectors, (b) photocurrent–time response of the CsPbBr₃/TiO₂ photodetector measured in the dark and under illumination of a blue laser with a 16 min alternative pulse, and (c) energy level diagram of the CsPbBr₃/TiO₂/MXene photodetector.

~46.9° correspond to the anatase phase of TiO₂, which confirms the formation of the TiO₂ layer.

3.2 Device characterization

Fig. 3(a) shows the stepwise photocurrent improvement after each modification. The device with QDs alone shows a low value of photocurrent of around 8 nA under the illumination of a blue laser ($\lambda = 450$ nm). The defects on the QD surface, long insulated ligands of OA and OAm which are used to passivate the QDs, act as barriers to the charge transport.²⁸ This results in the QD degradation due to light, heat, and also due to humidity exposure which is a huge problem for further practical applications. Therefore, the core/shell structure is believed to increase the stability of QDs while facilitating the carrier transfer as well.¹⁰ The core/shell structure increased the photocurrent by a factor of two compared to bare QD current, which shows that the core-shell structure has reduced the resistance to transportation of charges when compared to QDs. Carrier recombination loss still occurred at the interface of the QDs and TiO₂. This loss hinders significant current

improvement.¹¹ A CsPbBr₃/TiO₂/MXene PD on the other hand, shows significant photocurrent enhancement by 40 000-fold compared to photocurrent generated by QDs alone at 5 V because of the new non-radiative path generated by the addition of MXenes, and excited electrons could be transferred from the conduction band (CB) of QDs–TiO₂–MXene more efficiently. Therefore, a significant amount of charge carriers can be collected through the conductive MXene layer from the same amount of QDs. The spectral responsivity (R) is another vital parameter for PDs and it refers to the optical response ability of the device when excited by monochromatic light. This is related to the ability of the material to absorb photons. The spectral responsivity (R) can be defined as $R = J_{ph}/L_{light}$, where J_{ph} is the photocurrent and L_{light} is the incident-light intensity. The responsivity (R) of CsPbBr₃ QDs PD, CsPbBr₃/TiO₂ PD and CsPbBr₃/TiO₂/MXene PD are calculated to be 0.1, 0.2 and 3696 A W⁻¹ respectively, at 5 V bias. The external quantum efficiency (EQE) of each PD was calculated to be $2.9 \times 10^{-1}\%$, $6.1 \times 10^{-1}\%$ and $1.0 \times 10^4\%$ for CsPbBr₃ QDs PD, the CsPbBr₃/TiO₂ PD and the CsPbBr₃/TiO₂/MXene PD, respectively. 3.9×10^{13} , 6.8×10^{12}



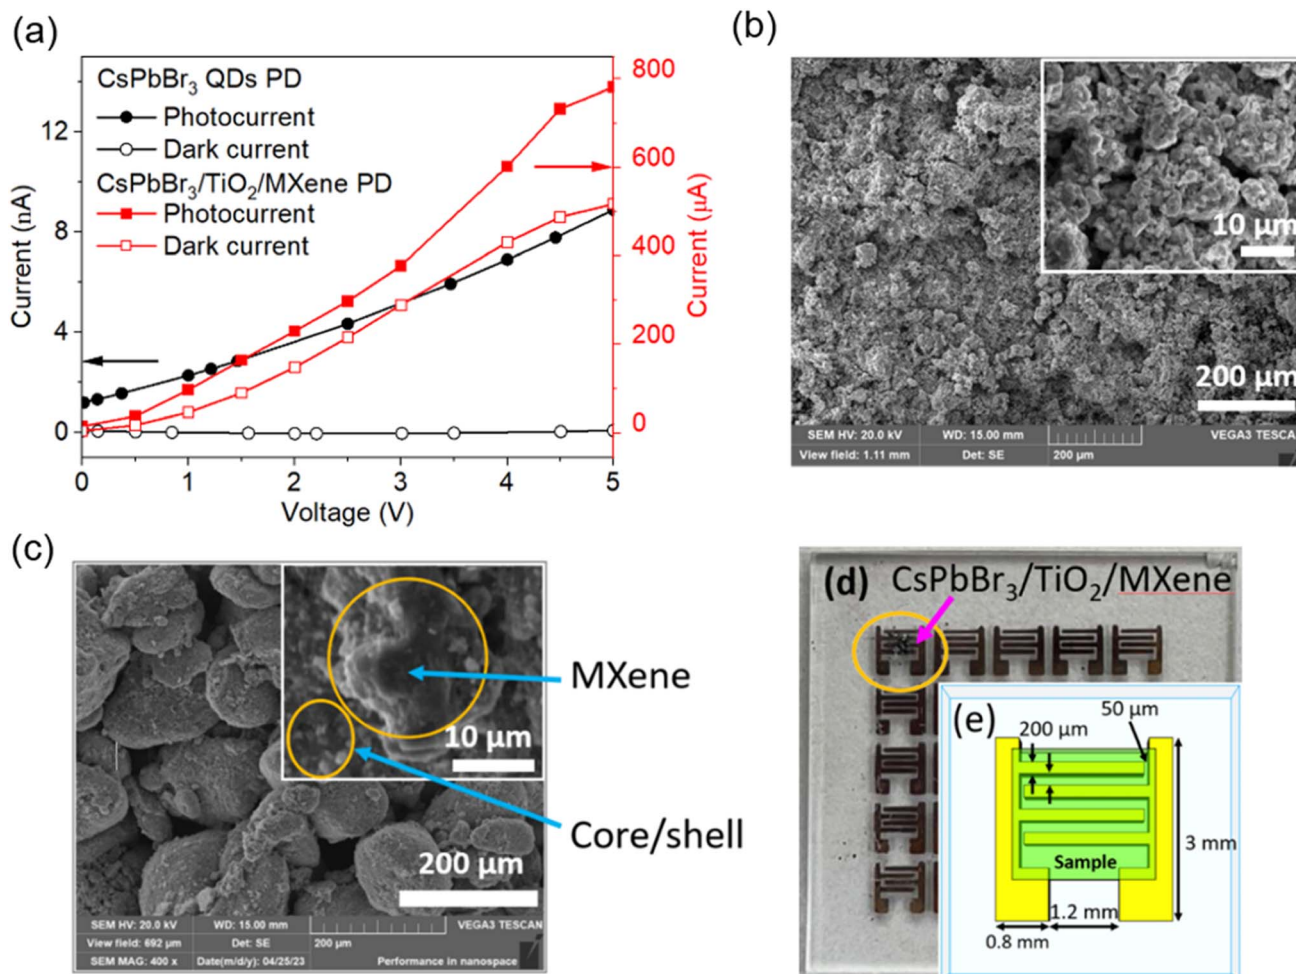


Fig. 4 (a) *I*–*V* curve of the CsPbBr₃ QD PD and CsPbBr₃/TiO₂/MXene PD in the dark and under illumination of a blue laser, SEM images of the (b) CsPbBr₃/TiO₂ PD and (c) CsPbBr₃/TiO₂/MXene PD, (d) optical image of the CsPbBr₃/TiO₂/MXene PD and (e) schematic 2D view of the measurements of Au interdigitated electrodes with the sample.

and 7.6×10^{14} jones were the detectivity of the CsPbBr₃ QDs PD, CsPbBr₃/TiO₂ PD and CsPbBr₃/TiO₂/MXene PD, respectively.^{29–31} All measurements were carried out at 81 W m^{-2} power density of the incident laser. This confirmed that utilizing the core/shell structure and introducing MXenes enhanced the photovoltaic performance of the PDs (see ESI, Table S1†). Note that a ratio $I_{\text{on}}/I_{\text{off}} = 1.7$ for the CsPbBr₃/TiO₂/MXene PD was observed at 5 V bias. The positive photocurrent spikes are evidence for the existence of accumulated photoexcited holes in interfaces within electrodes under the illumination of a laser.^{32,33} It is also found that stable photocurrent measured for the core-shell structure of QDs, can be effectively switched on and off with very good repeatability for 1000 seconds as illustrated in Fig. 3(b). Consistent switching behavior was also observed for the device after six weeks of storage in a nitrogen box (see ESI, Fig. S3†). Fig. 3(c) shows the non-radiative electron flow of the excited electrons from the CB of QDs, and the energy levels of each material used in the CsPbBr₃/TiO₂/MXene PD.

Fig. 4(a) shows the *I*–*V* response of the CsPbBr₃ QD PD and CsPbBr₃/TiO₂/MXene PD in the dark and under illumination.

There is no current observed as dark current for QDs while conductive MXenes shows μA range dark current. Higher dark current for the CsPbBr₃/TiO₂/MXene PD could be mainly due to the presence of a conductive MXene in the device. SEM images of the CsPbBr₃/TiO₂ PD and CsPbBr₃/TiO₂/MXene PD are shown in Fig. 4(b) and (c) respectively. The EDX characterization of CsPbBr₃/TiO₂ PD and CsPbBr₃/TiO₂/MXene PD can be found in the ESI (Fig. S4 and S5†). Fig. 4(d) and (e) show the optical image of the CsPbBr₃/TiO₂/MXene PD and the dimensions of the Au electrode. Prior study also observed the increase in the current density of the core/shell structure using CsPbBr₃ and CsPbBr₃/TiO₂ NCs as reference electrodes to the normal hydrogen electrode (NHE).¹⁰ This is consistent with the finding when such a core/shell structure was used to fabricate a FPD device and the performance was further enhanced by introducing the 2D materials, where the flake structure of MXenes provides conformal contact with QD. In addition, many studies have been reported on photoconductive devices based on varied configurations and material morphologies, including nanoparticles and nanosheets of CsPbBr₃ perovskites. Some of them

Table 1 Performance comparisons of perovskite PDs from previous reports based on CsPbBr₃ perovskites

Configuration	Material structure	Response time	Responsivity (R) (A W ⁻¹)	Irradiation power density	Detectivity (jones)	Ref.
Au/CsPbBr ₃ (Au NCs)/Au	Nanoparticles	1.2 ms	0.01	46.5 W m ⁻²	4.5 × 10 ⁸	34
Au/CsPbBr ₃ (mp-TiO ₂)/Au	Nanoparticles	9 s	3.5 (4 V)	NA (150 W lamp)	NA	35
Au/CsPbBr ₃ -MPA (mp-TiO ₂)/Au	Nanoparticles	4.7 s	24.5	1 W m ⁻² (λ = 405 nm)	8.9 × 10 ¹³	36
CsPbBr ₃ /PbSe	Nanoparticles	NA	7.17 (5 V)	0.25 W m ⁻² (λ = 365 nm)	9.0 × 10 ¹²	37
CsPbBr ₃	Thin film	NA	0.12	4.7 W m ⁻²	NA	38
CsPbBr ₃	Nanosheet	NA	0.09 (3 V)	(λ = 265 nm)	4.1 × 10 ¹¹	39
CsPbBr ₃ QDs PD	Nanoparticles	2.63 s	0.10 (5 V)	81 W m ⁻² (λ = 450 nm)	3.9 × 10 ¹³	This work
CsPbBr ₃ /TiO ₂ PD	Nanoparticles	3.63 s	0.20 (5 V)	81 W m ⁻² (λ = 450 nm)	6.8 × 10 ¹²	This work
CsPbBr ₃ /TiO ₂ /MXene PD	Nanoparticles	2.59 s	3696 (5 V)	81 W m ⁻² (λ = 450 nm)	7.6 × 10 ¹⁴	This work

exhibit good performances regarding responsivity, rise time, and detectivity, as shown in Table 1. The as-fabricated device of the CsPbBr₃/TiO₂/MXene PD shows the highest responsivity and detectivity.

4. Conclusion

In summary, three types of PDs were fabricated to demonstrate the performance systematically: CsPbBr₃ QD PD, CsPbBr₃ QDs/TiO₂ PD and CsPbBr₃/TiO₂/MXene PD. The device with the CsPbBr₃ QDs/TiO₂ PD appears to improve the stability and allows efficient photoinduced charge transfer through TiO₂. Consistent performance was observed upon nearly twenty minutes of exposure. The CsPbBr₃/TiO₂ PD was observed to enhance the photocurrent twice compared to a PD with pristine QDs. Ultimately, the CsPbBr₃/TiO₂/MXene PD improved the photocurrent significantly, which was 40 000 times more than that of the device with pristine QDs. This can be attributed to the effective electron transfer from QDs to MXenes upon photoirradiation. This QD decorated multilayer MXene was interconnected, which forms a conductive path to the interdigitated electrode, which sufficiently reduces the current loss. This work will lead to promising applications in integrated optoelectronic devices such as FPDs. Moreover, other conductive materials can be further introduced, such as conducting polymers, as flexible matrices for better multicomponent blending. This can address the possible issue of the current drop casting method, where a possible gap or spacing exists among multiple components.

Author contributions

C. Maduwanthi: original draft; S.-H. Hsu: draft review and funding; C.-A. Jong: funding; W. S. Mohammed: supervision.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

This work was supported by the Thailand Science Research and Innovation Fundamental Fund fiscal year 2024 and NARLabs I-Dream International Cooperation Project (13111F1201). The

authors gratefully acknowledge the support from the School of Integrated Science and Innovation (ISI), the Center of Excellence in Functional Advanced Materials Engineering (CoE FAME), the Sirindhorn International Institute of Technology (SIIT), Thammasat University and the Taiwan Semiconductor Research Institute (TSRI).

References

- 1 Y. Wang, L. Song, Y. Chen and W. Huang, Emerging New-Generation Photodetectors Based on Low-Dimensional Halide Perovskites, *ACS Photonics*, 2020, 7(1), 10–28, DOI: [10.1021/acsphotonics.9b01233](https://doi.org/10.1021/acsphotonics.9b01233).
- 2 Y. Wang, Y. Zhang, Y. Lu, *et al.*, Hybrid Graphene-Perovskite Phototransistors with Ultrahigh Responsivity and Gain, *Adv. Opt. Mater.*, 2015, 3(10), 1389–1396, DOI: [10.1002/adom.201500150](https://doi.org/10.1002/adom.201500150).
- 3 Y. Dong, Y. Gu, Y. Zou, *et al.*, Improving All-Inorganic Perovskite Photodetectors by Preferred Orientation and Plasmonic Effect, *Small*, 2016, 12(40), 5622–5632, DOI: [10.1002/sml.201602366](https://doi.org/10.1002/sml.201602366).
- 4 L. X. Wang, C. G. Tang, Z. S. Tan, *et al.*, Double-type-I charge-injection heterostructure for quantum-dot light-emitting diodes, *Mater. Horiz.*, 2022, 9(8), 2147–2159, DOI: [10.1039/d1mh00859e](https://doi.org/10.1039/d1mh00859e).
- 5 Y. Rui, Z. Jin, X. Fan, *et al.*, Defect passivation and electrical conductivity enhancement in perovskite solar cells using functionalized graphene quantum dots, *Mater. Futures*, 2022, 1(4), 045101, DOI: [10.1088/2752-5724/ac9707](https://doi.org/10.1088/2752-5724/ac9707).
- 6 H. Yang, S. Li, L. Zhang, *et al.*, Observation of high-density multi-excitons in medium-size CdSe/CdZnS/ZnS colloidal quantum dots through transient spectroscopy and their optical gain properties, *Nanoscale*, 2022, 14(14), 5369–5376, DOI: [10.1039/D2NR00761D](https://doi.org/10.1039/D2NR00761D).
- 7 B. Gidwani, V. Sahu, S. S. Shukla, *et al.*, Quantum dots: perspectives, toxicity, advances and applications, *J. Drug Delivery Sci. Technol.*, 2021, 61, 102308, DOI: [10.1016/j.jddst.2020.102308](https://doi.org/10.1016/j.jddst.2020.102308).
- 8 S. Kargozar, S. J. Hoseini, P. B. Milan, S. Hooshmand, H. W. Kim and M. Mozafari, Quantum Dots: A Review from Concept to Clinic, *Biotechnol. J.*, 2020, 15(12), 2000117, DOI: [10.1002/biot.202000117](https://doi.org/10.1002/biot.202000117).



- 9 M. Wang, W. Wang, B. Ma, *et al.*, Lead-Free Perovskite Materials for Solar Cells, *Nano-Micro Lett.*, 2021, **13**(1), 62, DOI: [10.1007/s40820-020-00578-z](https://doi.org/10.1007/s40820-020-00578-z).
- 10 Z. J. Li, E. Hofman, J. Li, *et al.*, Photoelectrochemically active and environmentally stable cspbbr3/tio2 core/shell nanocrystals, *Adv. Funct. Mater.*, 2018, **28**(1), 1704288, DOI: [10.1002/adfm.201704288](https://doi.org/10.1002/adfm.201704288).
- 11 B. Z. Zhou, M. J. Liu, Y. W. Wen, Y. Li and R. Chen, Atomic layer deposition for quantum dots based devices, *Opto-Electron. Adv.*, 2020, **3**(9), 1–14, DOI: [10.29026/oea.2020.190043](https://doi.org/10.29026/oea.2020.190043).
- 12 H. Chen, R. Li, A. Guo and Y. Xia, Highly fluorescent CsPbBr₃/TiO₂ core/shell perovskite nanocrystals with excellent stability, *SN Appl. Sci.*, 2021, **3**(6), 654, DOI: [10.1007/s42452-021-04648-8](https://doi.org/10.1007/s42452-021-04648-8).
- 13 P. Nuket, T. Kida and P. Vas-Umnuay, Influence of Annealing Temperature on Structural Properties and Stability of CsPbBr₃/TiO₂Core/Shell, in *IOP Conference Series: Materials Science and Engineering*, IOP Publishing Ltd, 2020, vol 965, DOI: [10.1088/1757-899X/965/1/012023](https://doi.org/10.1088/1757-899X/965/1/012023).
- 14 X. Zhang, X. Liu, Y. Huang, *et al.*, Review on flexible perovskite photodetector: processing and applications, *Front. Mech. Eng.*, 2023, **18**(2), 33, DOI: [10.1007/s11465-023-0749-z](https://doi.org/10.1007/s11465-023-0749-z).
- 15 L. C. T. Cao, M. H. Zhou, P. Opaprakasit, *et al.*, Facile Fabrication of Oxygen-Enriched MXene-Based Sensor and Their Ammonia Gas-Sensing Enhancement, *Adv. Mater. Interfaces*, 2023, **10**(16), 2300166, DOI: [10.1002/admi.202300166](https://doi.org/10.1002/admi.202300166).
- 16 H. Xu, A. Ren, J. Wu and Z. Wang, Recent Advances in 2D MXenes for Photodetection, *Adv. Funct. Mater.*, 2020, **30**(24), 2000907, DOI: [10.1002/adfm.202000907](https://doi.org/10.1002/adfm.202000907).
- 17 A. Pan, X. Ma, S. Huang, *et al.*, CsPbBr₃ Perovskite Nanocrystal Grown on MXene Nanosheets for Enhanced Photoelectric Detection and Photocatalytic CO₂ Reduction, *J. Phys. Chem. Lett.*, 2019, **10**(21), 6590–6597, DOI: [10.1021/acs.jpclett.9b02605](https://doi.org/10.1021/acs.jpclett.9b02605).
- 18 H. Li, Z. Li, S. Liu, *et al.*, High performance hybrid MXene nanosheet/CsPbBr₃ quantum dot photodetectors with an excellent stability, *J. Alloys Compd.*, 2022, **895**, 162570, DOI: [10.1016/j.jallcom.2021.162570](https://doi.org/10.1016/j.jallcom.2021.162570).
- 19 Y. Xie, Y. Yu, J. Gong, *et al.*, Encapsulated room-temperature synthesized CsPbX₃ perovskite quantum dots with high stability and wide color gamut for display, *Opt. Mater. Express*, 2018, **8**(11), 3494, DOI: [10.1364/ome.8.003494](https://doi.org/10.1364/ome.8.003494).
- 20 L. C. T. Cao, C. A. Jong, S. H. Hsu and S. F. Tseng, A Simple Approach to MXene Micropatterning from Molecularly Driven Assembly, *ACS Omega*, 2021, **6**(51), 35866–35875, DOI: [10.1021/acsomega.1c06662](https://doi.org/10.1021/acsomega.1c06662).
- 21 Y. Xie, Y. Yu, J. Gong, *et al.*, Encapsulated room-temperature synthesized CsPbX₃ perovskite quantum dots with high stability and wide color gamut for display, *Opt. Mater. Express*, 2018, **8**(11), 3494, DOI: [10.1364/ome.8.003494](https://doi.org/10.1364/ome.8.003494).
- 22 M. F. Leitão, M. S. Islim, L. Yin, *et al.*, Pump-power-dependence of a CsPbBr₃ -in-Cs₄PbBr₆ quantum dot color converter, *Opt. Mater. Express*, 2019, **9**(8), 3504, DOI: [10.1364/ome.9.003504](https://doi.org/10.1364/ome.9.003504).
- 23 L. Wang, H. Liu, Y. Zhang and O. F. Mohammed, Photoluminescence Origin of Zero-Dimensional Cs₄PbBr₆ Perovskite, *ACS Energy Lett.*, 2020, **5**(1), 87–99, DOI: [10.1021/acsenenergylett.9b02275](https://doi.org/10.1021/acsenenergylett.9b02275).
- 24 Q. A. Akkerman, S. Park, E. Radicchi, *et al.*, Nearly Monodisperse Insulator Cs₄PbX₆ (X = Cl, Br, I) Nanocrystals, Their Mixed Halide Compositions, and Their Transformation into CsPbX₃ Nanocrystals, *Nano Lett.*, 2017, **17**(3), 1924–1930, DOI: [10.1021/acs.nanolett.6b05262](https://doi.org/10.1021/acs.nanolett.6b05262).
- 25 M. Chen, Y. Yuan, Y. Liu, D. Cao and C. Xu, High-quality all-inorganic CsPbBr₃ single crystals prepared by a facile one-step solution growth method, *RSC Adv.*, 2022, **12**(23), 14838–14843, DOI: [10.1039/d2ra01900k](https://doi.org/10.1039/d2ra01900k).
- 26 J. Hao, G. Tai, J. Zhou, R. Wang, C. Hou and W. Guo, Crystalline Semiconductor Boron Quantum Dots, *ACS Appl. Mater. Interfaces*, 2020, **12**(15), 17669–17675, DOI: [10.1021/acsami.9b19648](https://doi.org/10.1021/acsami.9b19648).
- 27 W. Shao, G. Tai, C. Hou, Z. Wu, Z. Wu and X. Liang, Borophene-Functionalized Magnetic Nanoparticles: Synthesis and Memory Device Application, *ACS Appl. Electron. Mater.*, 2021, **3**(3), 1133–1141, DOI: [10.1021/acsaelm.0c01004](https://doi.org/10.1021/acsaelm.0c01004).
- 28 K. Chen, X. Zhang, P. A. Chen, *et al.*, Solution-Processed CsPbBr₃ Quantum Dots/Organic Semiconductor Planar Heterojunctions for High-Performance Photodetectors, *Advanced Science*, 2022, **9**(12), 2105856, DOI: [10.1002/advs.202105856](https://doi.org/10.1002/advs.202105856).
- 29 Z. Wu, G. Tai, R. Liu, *et al.*, Van der Waals Epitaxial Growth of Borophene on a Mica Substrate toward a High-Performance Photodetector, *ACS Appl. Mater. Interfaces*, 2021, **13**(27), 31808–31815, DOI: [10.1021/acsami.1c03146](https://doi.org/10.1021/acsami.1c03146).
- 30 Y. Zhang, F. Wang, X. Zhao, *et al.*, 2D Ruddlesden–Popper perovskite sensitized SnP₂S₆ ultraviolet photodetector enabling high responsivity and fast speed, *Nanoscale Horiz.*, 2023, **8**(1), 108–117, DOI: [10.1039/D2NH00466F](https://doi.org/10.1039/D2NH00466F).
- 31 G. Tai, B. Liu, C. Hou, Z. Wu and X. Liang, Ultraviolet photodetector based on p-borophene/n-ZnO heterojunction, *Nanotechnology*, 2021, **32**(50), 505606, DOI: [10.1088/1361-6528/ac27db](https://doi.org/10.1088/1361-6528/ac27db).
- 32 M. Wang, F. Ren, J. Zhou, *et al.*, N Doping to ZnO Nanorods for Photoelectrochemical Water Splitting under Visible Light: Engineered Impurity Distribution and Terraced Band Structure, *Sci. Rep.*, 2015, **5**, 12925, DOI: [10.1038/srep12925](https://doi.org/10.1038/srep12925).
- 33 A. G. Tamirat, A. A. Dubale, W. N. Su, H. M. Chen and B. J. Hwang, Sequentially surface modified hematite enables lower applied bias photoelectrochemical water splitting, *Phys. Chem. Chem. Phys.*, 2017, **19**(31), 20881–20890, DOI: [10.1039/c7cp02890c](https://doi.org/10.1039/c7cp02890c).
- 34 Y. Dong, Y. Gu, Y. Zou, *et al.*, Improving All-Inorganic Perovskite Photodetectors by Preferred Orientation and Plasmonic Effect, *Small*, 2016, **12**(40), 5622–5632, DOI: [10.1002/smll.201602366](https://doi.org/10.1002/smll.201602366).
- 35 L. Zhou, K. Yu, F. Yang, *et al.*, All-inorganic perovskite quantum dot/mesoporous TiO₂ composite-based photodetectors with enhanced performance, *Dalton Trans.*, 2017, **46**(6), 1766–1769, DOI: [10.1039/c6dt04758k](https://doi.org/10.1039/c6dt04758k).



- 36 L. Zhou, K. Yu, F. Yang, *et al.*, Insight into the effect of ligand-exchange on colloidal CsPbBr₃ perovskite quantum dot/mesoporous-TiO₂ composite-based photodetectors: much faster electron injection, *J. Mater. Chem. C*, 2017, 5(25), 6224–6233, DOI: [10.1039/C7TC01611E](https://doi.org/10.1039/C7TC01611E).
- 37 J. Hu, S. Yang, Z. Zhang, *et al.*, Solution-processed, flexible and broadband photodetector based on CsPbBr₃/PbSe quantum dot heterostructures, *J. Mater. Sci. Technol.*, 2021, 68, 216–226, DOI: [10.1016/j.jmst.2020.06.047](https://doi.org/10.1016/j.jmst.2020.06.047).
- 38 D. B. Kim, J. Han, Y. S. Jung, *et al.*, Origin of the anisotropic-strain-driven photoresponse enhancement in inorganic halide-based self-powered flexible photodetectors, *Mater. Horiz.*, 2022, 9(4), 1207–1215, DOI: [10.1039/D1MH02055B](https://doi.org/10.1039/D1MH02055B).
- 39 C. Y. Wu, Y. X. Le, L. Y. Liang, *et al.*, Non-ultrawide bandgap CsPbBr₃ nanosheet for sensitive deep ultraviolet photodetection, *J. Mater. Sci. Technol.*, 2023, 159, 251–257, DOI: [10.1016/j.jmst.2023.03.032](https://doi.org/10.1016/j.jmst.2023.03.032).

