

Showcasing research from Professor Soejima's laboratory,  
Department of Applied Chemistry, Kindai University, Osaka, Japan.

Photocatalytic hydrogen peroxide production with an external  
quantum yield of almost 500%

From the perspective of energy and environmental issues, the development of green methods for  $\text{H}_2\text{O}_2$  production is demanded. Among the candidates, photocatalytic  $\text{H}_2\text{O}_2$  production using robust inorganic materials has recently attracted much interest. However, the external quantum yield ( $\phi_{\text{ex}}$ ) of  $\text{H}_2\text{O}_2$  production by inorganic photocatalysts remains below 20% in most studies. Here we demonstrate that a nanohybrid photocatalyst consisting of antimony-doped  $\text{SnO}_2$  and  $\text{ZnO}$  can produce  $\text{H}_2\text{O}_2$  with a  $\phi_{\text{ex}}$  of ~500% from  $\text{O}_2$ -saturated ethanol aqueous solution under UV-light irradiation. The innovative results of this study pave the way for practical photocatalytic  $\text{H}_2\text{O}_2$  production.

Image reproduced by permission of Tetsuro Soejima from  
*Chem. Sci.*, 2025, **16**, 9125.

As featured in:



See Shin-ichi Naya, Hiroaki Tada,  
Tetsuro Soejima *et al.*,  
*Chem. Sci.*, 2025, **16**, 9125.

Cite this: *Chem. Sci.*, 2025, 16, 9125

All publication charges for this article have been paid for by the Royal Society of Chemistry

# Photocatalytic hydrogen peroxide production with an external quantum yield of almost 500%†

Yaozong Yan,<sup>a</sup> Shin-ichi Naya,<sup>id</sup> \*<sup>b</sup> Hisashi Sugime,<sup>id</sup> <sup>ac</sup> Hiroaki Tada<sup>id</sup> \*<sup>d</sup> and Tetsuro Soejima<sup>id</sup> \*<sup>ac</sup>

From the perspective of energy and environmental issues, the development of green methods for H<sub>2</sub>O<sub>2</sub> production is demanded as an alternative to the conventional energy-intensive anthraquinone method. Among the candidates, photocatalytic H<sub>2</sub>O<sub>2</sub> production has recently attracted much interest. To withstand the use under harsh conditions, it is desirable that the photocatalyst be composed of robust inorganic materials. However, the external quantum yield ( $\phi_{\text{ex}}$ ) of H<sub>2</sub>O<sub>2</sub> production by inorganic photocatalysts remains below 20% in most studies. Here we demonstrate that a nanohybrid photocatalyst consisting of antimony-doped SnO<sub>2</sub> and ZnO can produce H<sub>2</sub>O<sub>2</sub> with a  $\phi_{\text{ex}}$  of ~500% from O<sub>2</sub>-saturated ethanol aqueous solution under UV-light irradiation. In the photochemical reactions, the quantum yield is usually far below unity (<100%) due to the rapid recombination of photogenerated charge carriers. Breaking through this limit will pave the way for innovative photochemical reactions with the photocatalytic H<sub>2</sub>O<sub>2</sub> synthesis brought closer to practical application.

Received 24th February 2025

Accepted 2nd May 2025




DOI: 10.1039/d5sc01447f

rsc.li/chemical-science

## Introduction

Hydrogen peroxide (H<sub>2</sub>O<sub>2</sub>) is of paramount importance because it is not only a versatile clean oxidant<sup>1</sup> but also a promising fuel for fuel cells and photo-fuel cells.<sup>2,3</sup> At present, most H<sub>2</sub>O<sub>2</sub> is industrially produced by the anthraquinone auto-oxidation method involving multi-steps with large amounts of energy, hydrogen gas, and organic solvent consumed. In view of safety, low carbonization, and cost reduction, the development of green and sustainable on-site processes is imperative to produce the required amount of H<sub>2</sub>O<sub>2</sub> at the required location. To this end, research on various green processes for H<sub>2</sub>O<sub>2</sub> production is actively being conducted.<sup>4</sup> Among them, photocatalytic H<sub>2</sub>O<sub>2</sub> synthesis *via* two electron-oxygen reduction reaction (2e<sup>-</sup>-ORR, eqn (1)) utilizing sunlight as the driving force has recently attracted much attention.<sup>4–7</sup> In this case, it should be noted that the standard electrode potential ( $E^0$  vs. standard hydrogen electrode, SHE) for the reduction of H<sub>2</sub>O<sub>2</sub> to H<sub>2</sub>O (eqn (2)) is much more positive than that for 2e<sup>-</sup>-ORR,

which means that H<sub>2</sub>O<sub>2</sub> once produced easily undergoes further reduction to H<sub>2</sub>O under the photocatalytic reaction conditions.



Also, the decomposition of H<sub>2</sub>O<sub>2</sub> *via* disproportionation with a large negative Gibbs energy of reaction ( $\Delta_r G^0$ ) can spontaneously occur in the presence of a catalyst (eqn (3)). The intensive photocatalytic activity for H<sub>2</sub>O<sub>2</sub> production is commonly evaluated using the external quantum yield ( $\phi_{\text{ex}}$ ) or apparent quantum yield defined by eqn (4).

$$\phi_{\text{ex}}(\lambda) = (N_{\text{H}_2\text{O}_2}/N_{\text{photon}}) \times 2 \times 100 \quad (4)$$

where  $\lambda$  is the wavelength of incident light,  $N_{\text{H}_2\text{O}_2}$  is the number of H<sub>2</sub>O<sub>2</sub> molecules produced, and  $N_{\text{photon}}$  is the number of incident photons.

Additionally, the concentration ( $C$ ) and mole number ( $N$ ) of the obtained H<sub>2</sub>O<sub>2</sub> are important extensive indicators of the photocatalyst performance. The photocatalysts so far developed for H<sub>2</sub>O<sub>2</sub> synthesis can be broadly classified into organic polymers<sup>8–10</sup> and semiconducting metal oxides (MOs).<sup>11</sup> Recent progress in the research on the H<sub>2</sub>O<sub>2</sub> synthesis from O<sub>2</sub> using polymer-based photocatalysts is remarkable. For example, photocatalytic performances of  $\phi_{\text{ex}} = 7.6\%$  ( $\lambda = 420 \text{ nm}$ ),  $C = 5.4 \text{ mM}$  and  $N = 0.27 \text{ mmol}$  at photoirradiation time ( $t_p$ ) = 5 h were achieved in H<sub>2</sub>O<sub>2</sub> production from O<sub>2</sub> and H<sub>2</sub>O by using


<sup>a</sup>Graduate School of Science and Engineering, Kindai University, 3-4-1, Kowakae, Higashi-Osaka, Osaka 577-8502, Japan. E-mail: soejima@apch.kindai.ac.jp

<sup>b</sup>Environmental Research Laboratory, Kindai University, 3-4-1, Kowakae, Higashi-Osaka, Osaka 577-8502, Japan. E-mail: shinichi.naya@itp.kindai.ac.jp

<sup>c</sup>Department of Applied Chemistry, Faculty of Science and Engineering, Kindai University, 3-4-1, Kowakae, Higashi-Osaka, Osaka 577-8502, Japan

<sup>d</sup>Institutes of Innovation for Future Society, Nagoya University, Furo-cho, Chikusa-ku, Nagoya, 464-8603, Aichi, Japan

† Electronic supplementary information (ESI) available. See DOI: <https://doi.org/10.1039/d5sc01447f>



a resorcinol-formaldehyde resin photocatalyst.<sup>12</sup> Also, an antimony-dispersed g-C<sub>3</sub>N<sub>4</sub> photocatalyst was reported to yield H<sub>2</sub>O<sub>2</sub> from O<sub>2</sub> and H<sub>2</sub>O with  $\phi_{\text{ex}} = 17.6\%$  ( $\lambda = 420$  nm),  $C = 4.71$  mM and  $N = 0.24$  mmol at  $t_p = 5$  h.<sup>13</sup> Further, a photo-electrochemical (PEC) cell with a polyterthiophene photoanode was developed to produce 110 mM H<sub>2</sub>O<sub>2</sub> at  $t_p = 11$  h with the faradaic efficiency of  $\sim 100\%$  under illumination of simulated sunlight (one sun).<sup>14</sup> On the other hand, from the viewpoint of stability, robust MO-based photocatalysts are more favorable since the organic polymers can be degraded by reactive oxygen species generated during H<sub>2</sub>O<sub>2</sub> production.<sup>15</sup> Recently, active research has dramatically improved the activity of MO-based photocatalysts for H<sub>2</sub>O<sub>2</sub> production. For example, visible light-irradiation of Mo-doped BiVO<sub>4</sub> decorated with CoO<sub>x</sub> and Pd nanoparticles (NPs) generated H<sub>2</sub>O<sub>2</sub> from O<sub>2</sub> and H<sub>2</sub>O with a  $\phi_{\text{ex}}$  of 5.8% ( $\lambda = 420$  nm), and the  $C$  and  $N$  reached 1.2 mM and 0.017 mmol at  $t_p = 1$  h (saturated  $C$  ( $C_{\text{sat}}$ )  $\approx 1.6$  mM and saturated  $N$  ( $N_{\text{sat}}$ ) = 0.022 mmol at  $t_p \rightarrow \infty$ ), respectively, owing to the catalytic activities of CoO<sub>x</sub> for oxygen evolution reaction and Pd NPs for 2e<sup>−</sup>-ORR.<sup>16</sup> The addition of appropriate electron and proton donors can further enhance the photocatalytic performances. In the presence of ethanol, Au NP-loaded TiO<sub>2</sub> (Au/TiO<sub>2</sub>) particles immobilized on a porous hydrophobic substrate provided photocatalytic performances of  $\phi_{\text{ex}} = 17\%$  ( $\lambda = 367$  nm),  $C = 26.5$  mM and  $N = 0.040$  mmol at  $t_p = 16$  h ( $C_{\text{sat}} = 28.1$  mM and  $N_{\text{sat}} = 0.042$  mmol), which results from an increased supply of O<sub>2</sub> to the reaction sites.<sup>17</sup> Also, photocatalytic performances of  $\phi_{\text{ex}} = 7.2\%$  ( $\lambda = 365$  nm),  $C = 3.0$  mM and  $N = 0.30$  mmol at  $t_p = 1$  h were reported using a TiO<sub>2</sub>/MoS<sub>x</sub>-Au NP photocatalyst, in which MoS<sub>x</sub> tunes the electronic state of Au NPs to facilitate the O<sub>2</sub> adsorption.<sup>18</sup> Further, very high values of  $\phi_{\text{ex}} = 55\%$  ( $\lambda = 450$  nm),  $C = 38$  mM and  $N = 0.19$  mmol at  $t_p = 3$  h ( $C_{\text{sat}} = 51$  mM and  $N_{\text{sat}} = 0.26$  mmol) were recorded in the WO<sub>3</sub>-photocatalyzed H<sub>2</sub>O<sub>2</sub> synthesis by adding 2-propanol mainly due to its excellent electron and proton donating ability.<sup>19</sup> However, in all MO-photocatalyzed H<sub>2</sub>O<sub>2</sub> production reported so far, the rate of H<sub>2</sub>O<sub>2</sub> production significantly decreases with reaction time, and the amount produced saturates within a few hours due to further reduction (eqn (2)) and/or decomposition of H<sub>2</sub>O<sub>2</sub> (eqn (3)). Therefore, to further enhance the  $C$  and  $N$ , it is essential to use MOs with low affinity for H<sub>2</sub>O<sub>2</sub> as the photocatalyst materials. While most MOs are catalytically active for H<sub>2</sub>O<sub>2</sub> decomposition, we have found that SnO<sub>2</sub>, Sb-doped SnO<sub>2</sub> (ATO), and ZnO are inactive (Fig. S1†), and that ATO possesses high catalytic activity for 2e<sup>−</sup>-ORR.<sup>20</sup>

This study shows that a self-assembled nanohybrid photocatalyst consisting of ATO clusters and ZnO (ATO-CL/ZnO) produces H<sub>2</sub>O<sub>2</sub> from an O<sub>2</sub>-saturated ethanol aqueous solution with an unprecedented  $\phi_{\text{ex}}$  value of  $\sim 500\%$ , and the  $C$  and  $N$  increase with increasing light exposure time to reach 162 mM and 8.0 mmol, respectively, at  $t_p = 24$  h (eqn (5)). The basic action mechanism of the ATO-CL/ZnO photocatalyst is discussed based on electrochemical (EC) and PEC data.



The combination of the reaction in eqn (5) with the natural photosynthesis can form a carbon neutral cycle with H<sub>2</sub>O<sub>2</sub> as the key substance because ethanol can be produced from biomasses.<sup>21</sup>

## Experimental

### Materials

Zinc oxide powder (crystallite size = 41.5 nm, specific surface area = 9.5 m<sup>2</sup> g<sup>−1</sup>) was purchased from Sigma-Aldrich Co. ATO powder (Sb-doped amount = 11.6 mol%, crystallite size = 4.3 nm, specific surface area = 58.5 m<sup>2</sup> g<sup>−1</sup>, SN-100P) was kindly gifted from Ishihara Sangyo Co. TiO<sub>2</sub> powder (anatase, mean particles size = 150 nm, specific surface area = 8.1 m<sup>2</sup> g<sup>−1</sup>, A-100) was purchased from Ishihara Sangyo Co. Fluorine-doped tin(IV) oxide film-coated glass (FTO, 7  $\Omega$  per square, TEC7) and Nafion film (Nafion 117, thickness = 0.18 mm, Sigma-Aldrich Co.) were used for PEC measurements. The following reagents were used as received: 2,9-dimethyl-1,10-phenanthrolinehemihydrate (C<sub>14</sub>H<sub>12</sub>N<sub>2</sub>·0.5H<sub>2</sub>O, FUJIFILM Wako Pure Chemical Co.), ethanol (C<sub>2</sub>H<sub>5</sub>OH > 99.5%, FUJIFILM Wako Pure Chemical Co.), ethanol-d<sub>6</sub> (C<sub>2</sub>D<sub>5</sub>OD > 99%, FUJIFILM Wako Pure Chemical Co.), copper(II) sulfate pentahydrate (CuSO<sub>4</sub>·5H<sub>2</sub>O > 99.5%, FUJIFILM Wako Pure Chemical Co.), hydrogen tetrachloroaurate(III) tetrahydrate (HAuCl<sub>4</sub>·4H<sub>2</sub>O > 99%, FUJIFILM Wako Pure Chemical Co.), silver nitrate (AgNO<sub>3</sub> > 99.8%, FUJIFILM Wako Pure Chemical Co.), cobalt(II) nitrate hexahydrate (Co(NO<sub>3</sub>)<sub>2</sub>·6H<sub>2</sub>O > 98%, FUJIFILM Wako Pure Chemical Co.), and sodium hydroxide (NaOH > 97%, FUJIFILM Wako Pure Chemical Co.), phosphate buffer solution (pH 6.9, Kishida Chemical Co.), and sodium perchlorate (NaClO<sub>4</sub> > 96.0%, Kanto Chemical Co.). All aqueous solutions were prepared with distilled water.

### Characterization

The specific surface area was determined by the Brunauer–Emmett–Teller (BET) method. Adsorption–desorption isotherms of N<sub>2</sub> were measured at 77 K using a micromeritics automatic surface area and porosimetry analyzer (TriStar 3000, Shimadzu). Before the measurements, the samples were degassed in a vacuum at 423 K for 1 h. X-ray diffraction (XRD) patterns were measured using a Rigaku MiniFlexII using Cu K $\alpha$  radiation. Scanning electron microscopic (SEM) observation was carried out with Hitachi SU8230 at an applied voltage of 20–25 kV. Transmission electron microscopy (TEM) and high-resolution TEM (HR-TEM) measurements were performed using a JEOL JEM-2100F at an applied voltage of 200 kV. The diffuse reflectance spectra were measured in an ultraviolet-visible-near infrared (UV-vis-NIR) region by means of a Hitachi UH4150 UV-vis spectrophotometer equipped with an integrating sphere. To avoid the saturation, samples (30 mg) were diluted with BaSO<sub>4</sub> (270 mg). The diffuse reflectance spectra were measured using BaSO<sub>4</sub> as a reference to be transformed to the absorption spectra using the Kubelka–Munk function  $F(R_\infty) = (1 - R_\infty)^2/2R_\infty$ , where  $R_\infty$  is the reflectivity for thick enough sample. The photoluminescence (PL) spectra were collected by means of a JASCO FP-6000 spectrofluorometer with varying





excitation wavelengths at 77 K. The particle size distribution of ATO, ZnO, and the mixture, and their  $\zeta$ -potential in a 4% ethanol solution were measured using a Zetasizer Nano ZS (Malvern Instruments).

### Photocatalytic H<sub>2</sub>O<sub>2</sub> production

ZnO (50 mg) and ATO (100 mg) were dispersed into 4 vol% or 90 vol% aqueous EtOH solution (50 mL) by using ultrasonic irradiation, unless otherwise stated. This suspension was placed in the inner cell (100 mL) of a double-jacketed reaction vessel, and the temperature of the reaction solution was maintained at 298 K by circulating constant temperature water in the outer cell during light irradiation. During the reaction, O<sub>2</sub> gas bubbling was continued with a flow rate of 200 sccm. When the EtOH concentration ( $C_{\text{EtOH}}$ ) is 4 vol%, the rate of vaporization was negligibly small ( $\sim 0.04 \text{ mL h}^{-1}$ ) under the conditions. However, the evaporation rate reached  $0.6 \text{ mL h}^{-1}$  at  $C_{\text{EtOH}} = 90 \text{ vol\%}$ , so the reaction suspension was continuously replenished with 90 vol% EtOH aqueous solution at the same rate using a syringe pump (Pump 11, Harvard Apparatus). Experiments on isotope effects were performed at a tenth scale. After exposure to light for a given period of time, the particles were removed from the dispersion using a membrane filter. The H<sub>2</sub>O<sub>2</sub> concentration in the resulting solution was determined by a spectrophotometric method with Cu(II) ion and 2,9-dimethyl-1,10-phenanthroline.<sup>22</sup> We confirmed that this method allows accurate quantification of H<sub>2</sub>O<sub>2</sub> even in the presence of EtOH and oxidation products (CH<sub>3</sub>CHO and CH<sub>3</sub>COOH).

To determine the  $\phi_{\text{ex}}$ , monochromatic light was irradiated by using LED with various emission wavelength (CCS inc.). ZnO (10 mg) and ATO (10 mg) were dispersed in a 4 vol% aqueous EtOH solution (10 mL) by ultrasonic irradiation. This suspension was placed in the inner cell (100 mL) of a double-jacketed reaction vessel, and the temperature of the reaction solution was maintained at 298 K by circulating constant temperature water in the outer cell during light irradiation. During the reaction, O<sub>2</sub> gas bubbling was continued with a flow rate of 200 sccm. After irradiation for 15 min, the particles were removed from the suspension using a membrane filter, and the H<sub>2</sub>O<sub>2</sub> concentration was quantified by the spectrophotometric method with Cu(II) ion and 2,9-dimethyl-1,10-phenanthroline.<sup>22</sup> The number of incident photons ( $N_{\text{photon}}$ ) was calculated from the relation of  $N_{\text{photon}} = I/(hc/\lambda)$ , where  $I$  ( $\text{W cm}^{-2}$ ) is the light intensity,  $h$  is Planck constant,  $c$  is the speed of light,  $\lambda$  is the wavelength of incident light. From the values of  $N_{\text{H}_2\text{O}_2}$  and  $N_{\text{photon}}$ , the  $\phi_{\text{ex}}$  was calculated by eqn (4) as a function of  $I$ .

### Photodeposition of Ag and CoO<sub>x</sub>

In the Ag photodeposition, ATO-CL/ZnO particles (30 mg) were ultrasonically dispersed in 4 vol% aqueous EtOH solution (10 mL) with AgNO<sub>3</sub> (1 mM) for 10 s in a glass test tube. The resulting suspension was degassed by bubbling Ar with a stainless-steel syringe needle for 30 min with stirring. The test tube was capped with a rubber lid and set inside a double-

jacketed glass reaction vessel. The suspension was irradiated by two ultraviolet-light emitting diodes (UV-LED) ( $\lambda = 365 \text{ nm}$ ,  $I = 120 \text{ mW cm}^{-2}$ , HLV-24UV365-4WNRBTN, CCS Inc.) at 298 K for 2 h. The resulting particles were collected and washed with water by centrifugal separation.

In the CoO<sub>x</sub> photodeposition, ATO-CL/ZnO particles (30 mg) were ultrasonically dispersed in 10 mL of aqueous Co(NO<sub>3</sub>)<sub>2</sub> solution (1 mM) for 10 s in a glass test tube. The suspension was bubbled with O<sub>2</sub> gas using a stainless-steel syringe needle for 30 min with stirring. The test tube was capped with a rubber lid and set inside a double-jacketed glass reaction vessel. After the suspension was irradiated under the same irradiation conditions as the Ag photodeposition, the resulting particles were collected and washed with water by centrifugal separation.

### Electrochemical measurements

EC measurements were performed using two-component three-electrode cell consisting of ATO-CL/ZnO nanorod array (NRA) (working electrode), Ag/AgCl (reference electrode)|0.1 M NaClO<sub>4</sub> aqueous solution containing 4 vol% EtOH|Nafion|0.1 M NaClO<sub>4</sub> aqueous solution containing 4 vol% EtOH|Pt film (counter electrode) in the dark. The active area of working electrode is  $1 \text{ cm}^2$  ( $1 \text{ cm} \times 1 \text{ cm}$ ). By the reported procedure, ZnO NRA was formed on FTO.<sup>23</sup> ATO (2 mg) was dispersed into H<sub>2</sub>O (0.4 mL), and the resulting suspension was dropped onto ZnO NRA. The sample was dried at 353 K to obtain ATO-CL/ZnO NRA electrode. After bubbling by argon or O<sub>2</sub> gas for 30 min, the linear sweep voltammetry curves were measured by means of a galvanostat/potentiostat (HZ-7000, Hokuto Denko) with scan rate =  $20 \text{ mV s}^{-1}$  in the dark. The faradaic efficiency ( $\eta$ ) was calculated at irradiation time ( $t$ ) = 30 min by eqn (6).

$$\eta = 2N(t)/(\int I(t)dt/F) \quad (6)$$

where  $N(t)$  is the mole number of H<sub>2</sub>O<sub>2</sub> produced and  $I(t)$  is current at  $t$ , and  $F$  is the Faraday constant.

### Photoelectrochemical H<sub>2</sub>O<sub>2</sub> production

Two-component three-electrode cells were fabricated with a structure of ZnO NRA (working electrode), Ag/AgCl (reference electrode)|0.1 M NaClO<sub>4</sub> aqueous solution containing 4 vol% EtOH (80 mL)|Nafion|0.1 M NaClO<sub>4</sub> aqueous solution containing 4 vol% EtOH (80 mL)|ATO/FTO (counter electrode). ATO (2 mg) was dispersed into H<sub>2</sub>O (0.4 mL), and the suspension was dropped onto FTO. The active area of working electrode is  $1 \text{ cm}^2$  ( $1 \text{ cm} \times 1 \text{ cm}$ ). The sample was dried at 353 K to obtain ATO/FTO electrode. After O<sub>2</sub> bubbling each component for 30 min, the working electrode was illuminated by LED lamp ( $\lambda_{\text{ex}} = 365 \pm 20 \text{ nm}$ , intensity =  $120 \text{ mW cm}^{-2}$ ) at 298 K. The photocurrent was measured by means of a galvanostat/potentiostat (HZ-7000, Hokuto Denko) at dark rest potential. The H<sub>2</sub>O<sub>2</sub> concentration was quantified by the spectrophotometric method with Cu(II) ion and 2,9-dimethyl-1,10-phenanthroline.<sup>22</sup> The faradaic efficiency ( $\eta$ ) was also calculated by eqn (6).



## Results


### Preparation and characterization of ATO-CL/ZnO photocatalysts

Commercial particles of ATO (Sb-doped amount = 11.6 mol%, SN-100P, Ishihara Sangyo) and ZnO (Sigma-Aldrich) were used as received. The specific surface area of ATO and ZnO particles were determined to be  $58.5 \text{ m}^2 \text{ g}^{-1}$  and  $9.5 \text{ m}^2 \text{ g}^{-1}$ , respectively, by the BET method. In the XRD pattern of ATO particles, diffraction peaks are observed at  $2\theta = 26.66^\circ$ ,  $33.94^\circ$ ,  $37.98^\circ$ , and  $51.80^\circ$  assignable to the diffraction from the (110), (101), (200), and (211) planes of tetragonal  $\text{SnO}_2$  (Fig. 1a). Also, the XRD pattern of ZnO has strong diffraction peaks at  $2\theta = 31.74^\circ$ ,  $34.40^\circ$ , and  $36.24^\circ$  due to the diffraction from the (10 $\bar{1}$ 0), (0002),

and (10 $\bar{1}$ 1) planes of hexagonal ZnO. The crystallite sizes of ATO and ZnO were determined to be 4.3 nm and 41.5 nm, respectively, using Scherrer's equation from the ATO (110) and ZnO (10 $\bar{1}$ 0) diffraction line widths, respectively. TEM images show that the ZnO sample consists of faceted NPs involving short nanorods with a large variation in size (Fig. S2†), while the ATO sample forms clusters of aggregated particles smaller than 10 nm (Fig. S3†). After the ATO (100 mg) and ZnO NPs (50 mg) were dispersed in 4 vol% ethanol aqueous solution (50 mL) by ultrasonic irradiation for 1 min and stirred for 60 min, the solids were recovered by centrifugation to be washed and dried. The XRD pattern of the obtained sample is a superposition of those for ATO and ZnO. The TEM image of the hybrid sample shows that the ZnO surface is partly modified with ATO clusters (ATO-CL/ZnO, Fig. 1b) as more clearly shown by the TEM-energy dispersive X-ray spectroscopy (EDS) elemental mapping (Fig. 1c).

The size distribution of ATO (100 mg) and ZnO (50 mg) particles dispersed in 4 vol% ethanol aqueous solution (50 mL) before and after mixing was measured by dynamic light scattering (DLS) (Fig. 1d). In each suspension, ATO and ZnO particles exist as aggregates with the mean size of 188 nm and 335 nm, respectively. On mixing both the suspensions with excess ATO, the peak size of ZnO shifts to 447 nm, while a peak of non-coupled ATO particles is observed at 159 nm. Evidently, self-assembling of ATO and ZnO particles occurs only by mixing both the suspensions.  $\zeta$ -Potentials were measured in 4 vol% ethanol aqueous solution (pH 6.4) by the electrophoretic method (Fig. 1e). The  $\zeta$ -potentials of ATO and ZnO particles are  $-24.8 \text{ mV}$  and  $+20.8 \text{ mV}$ , respectively. ATO-CL/ZnO has a value of  $-18.6 \text{ mV}$ , which is intermediate between the values of ATO and ZnO. Clearly, the hybridization of the ATO and ZnO particles is caused by the electrostatic attraction between them in the near-neutral aqueous solution. The hybrid sample prepared by mixing ATO ( $x/\text{mg}$ ) and ZnO ( $y/\text{mg}$ ) in 4 vol% ethanol aqueous solution (50 mL) is designated as ATO-CL( $x$ )/ZnO( $y$ ) below.

In the HR-TEM image of ATO-CL(100)/ZnO(50) (Fig. 1f), the interplanar spacings of fringes observed in the small crystals of 0.26 nm and 0.31 nm are close to the values of the  $\text{SnO}_2$ (101) and (001) planes, respectively. Also, the  $d$ -spacing of 0.24 nm in the large particle is in agreement with the value of ZnO (10 $\bar{1}$ 1). As indicated by the yellow arrows, some voids are observed near the interface between ATO and ZnO particles. ATO-CL(100)/ZnO(50) was further heated at 673 K for 1 h in air (ht-ATO-CL(100)/ZnO(50)). TEM-EDS mapping of ht-ATO-CL(100)/ZnO(50) shows that the ZnO particle surfaces are effectively modified with ATO clusters (Fig. S4†), similar to that of ATO-CL(100)/ZnO(50) before calcination (Fig. 1b and c). Among the many particles observed, all ZnO particles were coupled to ATO clusters without independent ZnO particles. Importantly, the HR-TEM image of ht-CL(100)/ZnO(50) shows that the voids observed in the unheated sample almost disappear, and some of the ATO NPs in the cluster are tightly bonded to the ZnO surface (Fig. 1g). Obviously, the heat treatment makes the ZnO and ATO particles more firmly bonded at the interface and increases the contact area.

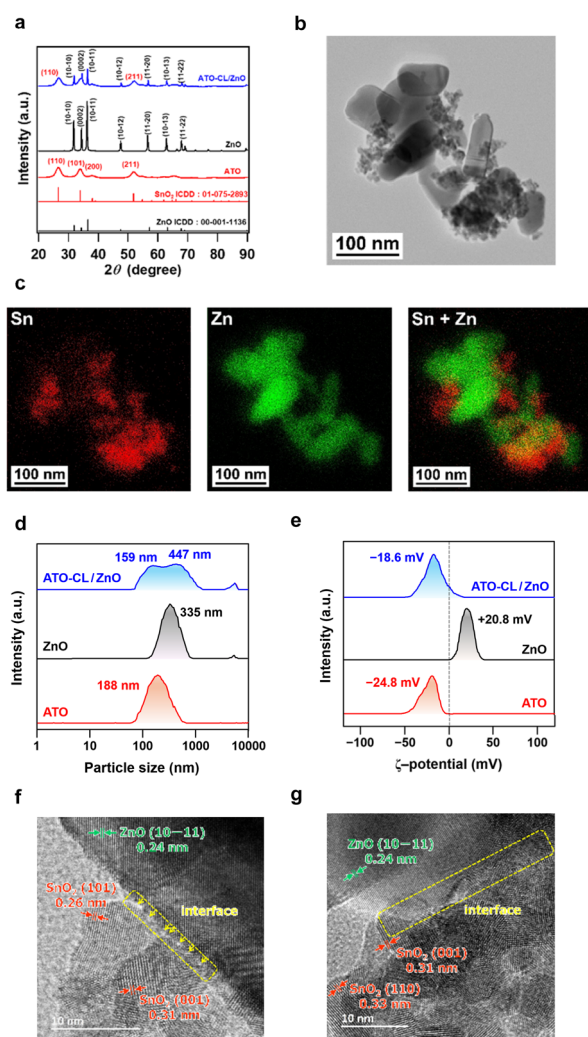

**Fig. 1** (a) XRD patterns of ATO, ZnO, and ATO-CL/ZnO. (b) TEM image of ATO-CL/ZnO. (c) EDS elemental mapping of ATO-CL/ZnO for the TEM image in (b). (d) Size distributions of ATO and ZnO NP suspensions, and their mixture in 4 vol% ethanol aq. (pH 6.4) measured by the DLS method. (e)  $\zeta$ -Potentials of ATO and ZnO NP suspensions, and their mixture in 4% ethanol aq. (pH 6.4). HR-TEM images of ATO-CL/ZnO (f) and ht-ATO-CL/ZnO (g). In each image, the interface is indicated by a dotted rectangle.

Diffuse reflectance UV-vis-NIR absorption spectra of ZnO, ATO, and ATO-CL(100)/ZnO(50) were measured. In the Kubelka-Munk-transformed absorption spectra of ZnO and ATO (Fig. S5†), the absorption due to the interband transition rises at light wavelength ( $\lambda$ )  $< 380$  nm and  $\lambda < \sim 340$  nm, respectively. ATO has also strong absorption by free electrons in the NIR region,<sup>23</sup> and the absorption tail extending from 340 nm to  $\sim 400$  nm indicates the existence of mid-gap levels due to defects. From the Tauc plots for ZnO and ATO (Fig. S6†), the allowed and inhibited direct band gaps were determined to be 3.27 eV for ZnO and 3.53 eV for ATO, respectively, which are close to the reported values of 3.26 eV<sup>24</sup> and 3.60 eV.<sup>25</sup> The absorption spectrum of ATO-CL(100)/ZnO(50) consists of the superposition of the ATO and ZnO spectra.

### Photocatalytic H<sub>2</sub>O<sub>2</sub> production

The photocatalytic activities of ATO, ZnO, and ATO-CL(100)/ZnO(50) for H<sub>2</sub>O<sub>2</sub> generation from aerated 4% ethanol solution (pH 6.4, 50 mL) were evaluated at 298 K under UV-light irradiation ( $\lambda = 365$  nm) by comparing that of the typical Au/TiO<sub>2</sub> photocatalyst (Fig. 2a and S7†).<sup>21</sup> During the reaction, O<sub>2</sub> gas bubbling was continued with a flow rate of 200 standard cubic centimetre per min (sccm), where the change in H<sub>2</sub>O<sub>2</sub> concentration accompanying the evaporation of the solvent was negligible. Au/TiO<sub>2</sub> initially shows high photocatalytic activity for H<sub>2</sub>O<sub>2</sub> production, which significantly decreases over photoirradiation time. As a result, the H<sub>2</sub>O<sub>2</sub> concentration reaches an almost constant value of  $18.1 \pm 0.7$  mM at  $t_p \geq 12$  h. While

ATO itself is inactive, ZnO produces H<sub>2</sub>O<sub>2</sub> with an almost constant rate of  $1.2 \text{ mM h}^{-1}$ , and the H<sub>2</sub>O<sub>2</sub> concentration at  $t_p = 24$  h of 28.8 mM exceeds the value of 18.8 mM in the Au/TiO<sub>2</sub> system. Strikingly, in the ATO-CL/ZnO system, the concentration of H<sub>2</sub>O<sub>2</sub> continues to increase to reach 105 mM at  $t_p = 24$  h. Also, gas chromatography analysis confirmed that acetaldehyde is produced in the gas phase as an oxidation product of ethanol. The photocatalytic activity of ATO-CL/ZnO strongly depends on the mixing ratio of ATO and ZnO with a maximum at  $x/y = 2$  (Fig. S8†).

In the ATO-CL/ZnO system, the amount of H<sub>2</sub>O<sub>2</sub> generated was small without ethanol in the reaction solution (9.1  $\mu\text{M}$ ), and then, the photocatalytic activity was assessed by increasing the ethanol concentration from 4 vol% to 90 vol% (Fig. 2b). In this case, the evaporation rate reached  $0.6 \text{ mL h}^{-1}$ , so the reaction suspension was continuously replenished with 90 vol% ethanol aqueous solution at the same rate using a syringe pump. In the ATO-CL/ZnO system, the photocatalytic activity significantly decreases (Fig. S9†). On the contrary, the photocatalytic activity of ht-CL(100)/ZnO(50) drastically increases with the H<sub>2</sub>O<sub>2</sub> concentration to reach 162 mM at  $t_p = 24$  h. These results indicate that at least partial tight bonding between ATO and ZnO is essential for ATO-CL/ZnO to exhibit high photocatalytic activity (Fig. 1f and g). In high-concentration ethanol aqueous solutions, heat treatment of a mixture of ATO and ZnO particles at 673 K is effective for this purpose, but above 773 K, the photocatalytic activity of ZnO decreases (Fig. S10†), probably due to the reduction in surface area. To check the stability of ht-CL(100)/ZnO(50), the XRD patterns of the samples collected after 24 h of reaction were measured. The XRD patterns show almost no change before and after the reaction (Fig. S11†).

Catalytic and photocatalytic activities of ATO-CL(100)/ZnO(50) and Au/TiO<sub>2</sub> for H<sub>2</sub>O<sub>2</sub> decomposition were studied in dark and under UV-light irradiation, respectively (Fig. S12†). In the Au/TiO<sub>2</sub> system, the concentration of H<sub>2</sub>O<sub>2</sub> decreases in dark due to the adsorption and the catalytic decomposition of H<sub>2</sub>O<sub>2</sub>, which is considerably accelerated by photoirradiation. On the other hand, in the ATO-CL/ZnO system, the H<sub>2</sub>O<sub>2</sub> concentration remains almost constant in dark and even under photoirradiation.

The photocatalytic activity of ATO(100)/ZnO(50) was evaluated using LEDs with varying emission wavelengths as the light source otherwise under the same conditions (Fig. 2c). The action spectrum of  $\phi_{\text{ex}}$  rises at  $\lambda = 365$  nm, well tracing the absorption spectrum of ZnO, and thus, this photocatalytic reaction is mainly driven by the band gap excitation of ZnO. In this case, the optical absorption of ZnO is hardly blocked by ATO CLs since ATO is nearly transparent to the UV region where the ZnO has strong absorption (Fig. S5†). Further, the light intensity-dependence of  $\phi_{\text{ex}}$  was examined at  $\lambda = 365$  nm (Fig. 2d). The  $\phi_{\text{ex}}$  increases with lowering light intensity, and surprisingly, reaches  $\sim 500\%$  at an incident photon flux of  $1.6 \times 10^{14} \text{ cm}^{-2} \text{ s}^{-1}$ . When the reaction was carried out in air-saturated solution, the  $\phi_{\text{ex}}$  of 109% lowers to 13% at an incident photon flux of  $1.6 \times 10^{16} \text{ cm}^{-2} \text{ s}^{-1}$ .

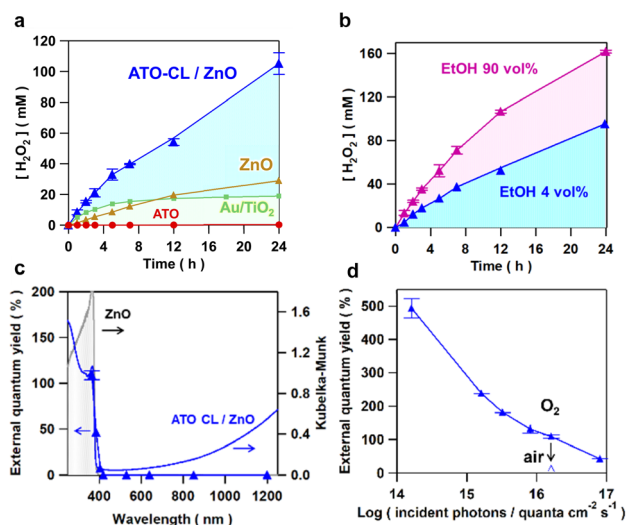


Fig. 2 (a) Time courses for H<sub>2</sub>O<sub>2</sub> generation from 4 vol% ethanol aqueous solutions (pH 6.4, 50 mL) in the ATO (100), ZnO(50), ATO-CL(100)/ZnO(50) systems, and for comparison, Au/TiO<sub>2</sub> system under UV-light irradiation ( $\lambda = 365$  nm) using two LED lamps (each light intensity =  $120 \text{ mW cm}^{-2}$ ). (b) Ethanol concentration effect on the photocatalytic activities of ht-ATO-CL(100)/ZnO(50) under the same irradiation conditions as (a). (c) Action spectrum of external quantum yield for the photocatalytic H<sub>2</sub>O<sub>2</sub> generation in the ATO-CL(100)/ZnO(10) system (pH 6.4, 50 mL). (d) Plots of external quantum yield vs. light intensity. The data in the O<sub>2</sub>-saturated and air-saturated solutions are solid triangles and open triangle, respectively.





## Discussion

To gain insight into the origin for the extremely high photocatalytic activity of ATO-CL/ZnO, the redox sites were firstly studied using the labeling and visualizing technique by photodeposition.<sup>26</sup> To specify the reduction sites, Ag NPs were photodeposited on ht-ATO-CL/ZnO from a degassed AgNO<sub>3</sub> aqueous solution containing 4% ethanol under UV irradiation ( $\lambda = 365$  nm). TEM-EDS elemental mapping for the resulting sample shows that Ag NPs are deposited on the ATO CL and close to the interface with ZnO (Fig. 3a). Also, to specify the oxidation sites, CoO<sub>x</sub> photodeposition on ht-ATO-CL/ZnO was carried out from an O<sub>2</sub>-saturated Co(NO<sub>3</sub>)<sub>2</sub> aqueous solution under the same irradiation conditions.<sup>27,28</sup> In contrast to the Ag photodeposition, CoO<sub>x</sub> species are selectively formed on the surface of ZnO (Fig. 3b). These results indicate that in the ATO-CL/ZnO system, ATO CL and ZnO act as the reduction sites and oxidation sites, respectively, through effective charge separation.

Next, photoluminescence (PL) spectra were measured under excitation by light with  $\lambda = 365$  nm at 77 K (Fig. 3c). Under these

conditions, the interband transition of ZnO and the excitation of the electrons from the mid-gap states of ATO to the conduction band (CB) are possible. In the spectrum of ZnO, broad emission bands are present around 429 nm (E1) and 525 nm (E2), which are assignable to the near band-to-band emission and the defect-level-related emission, respectively. ATO has emission at 429 nm (E3) with a shoulder around 500 nm due to the defect-level-related emission. As shown by the difference spectrum (ATO-CL/ZnO-ATO), the E2 and E1 signals of ZnO disappear with the coupling with ATO, which can be attributed to the interfacial electron transfer from the CB of ZnO to ATO in a manner similar to the ATO/TiO<sub>2</sub> system.<sup>29</sup> On the contrary, the E3 signal of ATO weakens, suggesting simultaneous occurrence of the hole transfer from the deep defect levels of ATO to the valence band (VB) of ZnO.

Further, ZnO nanorod array was formed on fluorine-doped tin oxide electrode (ZnO NRA/FTO) for EC measurements (Fig. S13†).<sup>30</sup> The dark current ( $J$ )-potential ( $E$ ) curves were measured using a three-electrode EC cell with the structure of ZnO NRA/FTO or ATO-CL/ZnO NRA/FTO (working electrode)|0.1 M NaClO<sub>4</sub> aq. containing 4 vol% ethanol (electrolyte solution, 80 mL)|Ag/AgCl (reference electrode)|Pt (auxiliary





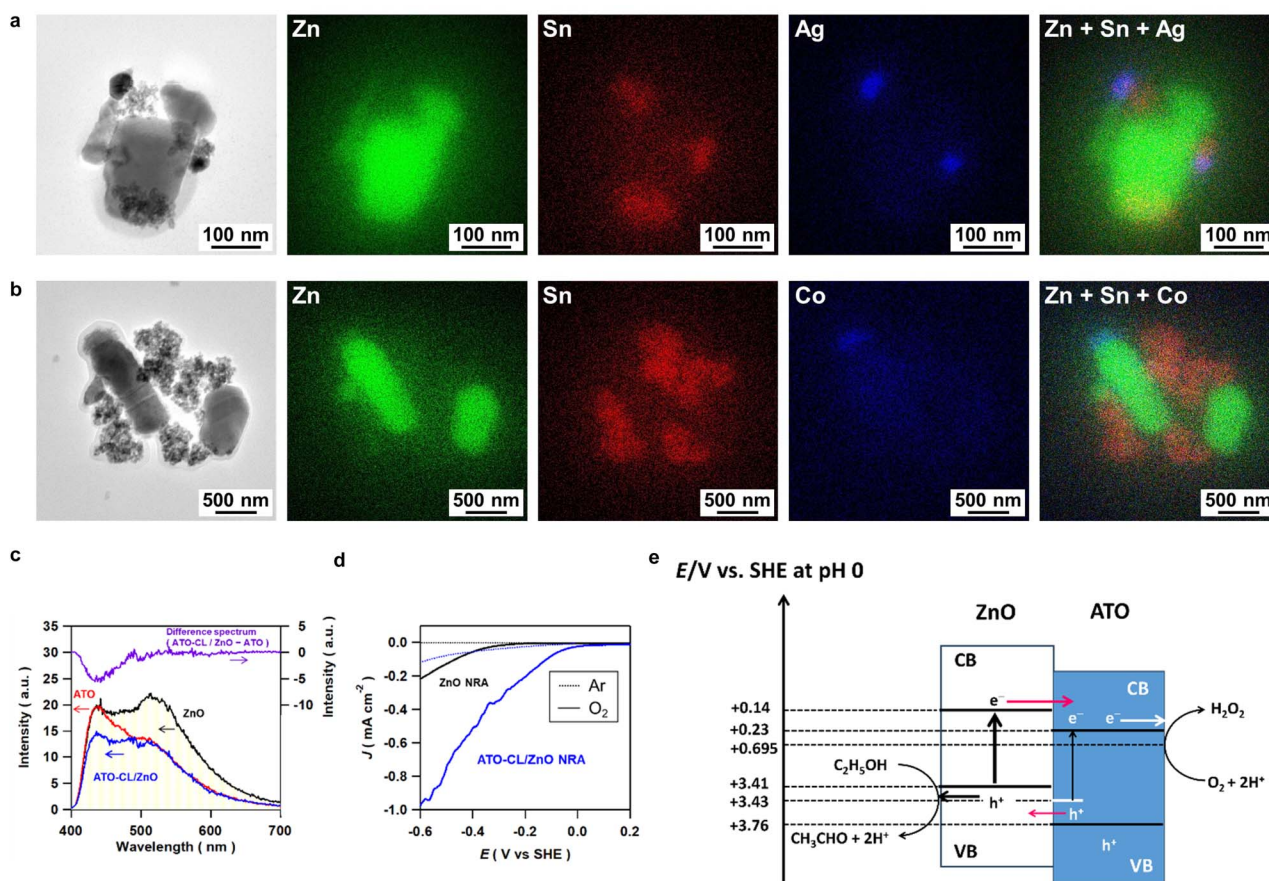


Fig. 3 (a) TEM-EDS elemental mapping of Ag-photodeposited ht-ATO-CL(20)/ZnO(10). (b) TEM-EDS elemental mapping of CoO<sub>x</sub>-photodeposited ht-ATO-CL(20)/ZnO(10). (c) PL spectra of ATO, ZnO, and ATO-CL(100)/ZnO(50) NPs on excitation by light with wavelength of 365 nm at 77 K. (d) Dark current ( $J$ )-potential ( $E$ ) curves of ZnO NRA and ATO-CL/ZnO NRA electrodes in argon gas (dotted lines) and oxygen gas (solid lines)-bubbled 0.1 M NaClO<sub>4</sub> electrolyte solution containing 4 vol% ethanol. (e) A reaction mechanism proposed for the present ATO-CL/ZnO-photocatalyzed H<sub>2</sub>O<sub>2</sub> production.

electrode) (Fig. 3d). In a degassed electrolyte solution, only a small current flows at  $-0.6 \leq E \leq 0$  V in each electrode system. On the other hand, in the  $O_2$ -saturated electrolyte solution, a cathodic current due to ORR rises at  $E = -0.3$  V in the ZnO NRA/FTO electrode system. The current is further increased significantly in the ATO-CL/ZnO NRA/FTO electrode system with the current onset potential shifted to  $\sim 0$  V.

Based on the results above, the action mechanism of ATO-CL/ZnO is discussed. The energy diagram was constructed using the flatband potentials and band gaps of ZnO (0.14 V, 3.27 eV)<sup>31</sup> and ATO (0.229 V, 3.53 eV)<sup>32</sup> (Fig. 3e). When ATO and ZnO NPs were dispersed in near neutral 4 vol% ethanol aqueous solution, the surfaces of ATO and ZnO NPs are strongly negatively and positively charged, respectively. As a result, they are coupled *in situ* through the electrostatic interaction to yield ATO-CL/ZnO nanohybrids. Upon UV-light irradiation ( $\lambda = 365$  nm) of ATO-CL/ZnO, the electrons in the VB of ZnO are promoted to the CB with simultaneous excitation of the deep defect levels in ATO to the CB (eqn (7)). As indicated by the Ag and  $CoO_x$  photodeposition and the PL spectra, the CB electrons in ZnO ( $E \approx 0.14$  V) are transferred to ATO with the lower-lying CB minimum ( $E \approx 0.48$  V), and at the same time, the holes generated in the deep defect levels in ATO ( $E \approx 3.43$  V) can be moved to the VB of ZnO ( $E \approx 3.41$  V) (eqn (8)). Consequently, effective charge separation can be achieved by the interfacial electron and hole transfer in the opposite direction. The electrons in the CB of ATO efficiently reduce  $O_2$  to  $H_2O_2$  ( $E^0(O_2/H_2O_2) = 0.695$  V) with the assistance by its electrocatalysis for  $2e^-$ -ORR (eqn (9)),<sup>20</sup> while the VB holes in ZnO oxidizes ethanol (eqn (10)).<sup>33,34</sup> In this case, even if part of the ATO cluster is in contact with ZnO, the large-surface-area ATO cluster facilitates  $2e^-$ -ORR because of the delocalization of the injected electrons throughout the cluster due to the interparticle electron transfer.<sup>35</sup> Further, the amount of  $H_2O_2$  increases almost in proportion to irradiation time owing to the low catalytic and photocatalytic activity of ATO-CL/ZnO for  $H_2O_2$  decomposition. In 90 vol% ethanol aqueous solution, the significant coupling effect can only be obtained after heat treatment of ATO-CL/ZnO because of the decrease in the amounts of the surface charges, which points out the importance of the intimate junction between ATO and ZnO for the charge separation, and further the photocatalytic activity.<sup>36</sup>



Consequently, the remarkable photocatalytic performances of ATO-CL/ZnO and ht-ATO-CL/ZnO for  $H_2O_2$  production can stem from the following features: (1) effective charge separation *via* the interfacial electron and hole transfer through the

intimate junction between the components, (2) high electric conductivity and electrocatalytic activity of ATO for  $2e^-$ -ORR, (3) low catalytic and photocatalytic activities of ATO and ZnO for  $H_2O_2$  decomposition. However, these features alone cannot explain the origin of the  $\phi_{ex}$  above 100%.

Then, to explicate the reactions on the reduction sites (ATO) and oxidation sites (ZnO) of the ATO-CL/ZnO photocatalyst, a two-compartment three-electrode PEC cell with the structure ZnO NRA/FTO (working electrode), Ag/AgCl (reference electrode)|0.1 M  $NaClO_4$  aq. containing 4 vol% ethanol (80 mL)|Nafion| $O_2$ -saturated 0.1 M  $NaClO_4$  aq. (80 mL)|ATO/FTO (auxiliary electrode) was fabricated as a model for the particulate system (Fig. 4a). Light irradiation of the ZnO NRA/FTO electrode ( $\lambda = 365$  nm) for 30 min yielded 10  $\mu M$   $H_2O_2$  in the cathode compartment and 30  $\mu M$   $H_2O_2$  in the anode compartment for which the faradaic efficiencies were calculated to be 81% and 243%, respectively. Obviously,  $H_2O_2$  is produced in the ATO-CL/ZnO-photocatalyzed reaction *via* not only  $2e^-$ -ORR on the ATO electrode (Fig. 4a, right) but also ethanol oxidation on the ZnO photoelectrode (Fig. 4b, left). Even if ethanol is oxidized on the ZnO photoelectrode with a current doubling effect,<sup>37</sup> the faradaic efficiency should remain at an upper limit of 200%.

To explain the faradaic efficiency above 200% in the photoanodic reaction, we propose the following chain reaction mechanism (Fig. 4a, left). When  $CH_3CH_2OH$  is oxidized by the holes in the VB of ZnO,  $CH_3\dot{C}HOH$  radical and  $H^+$  are generated

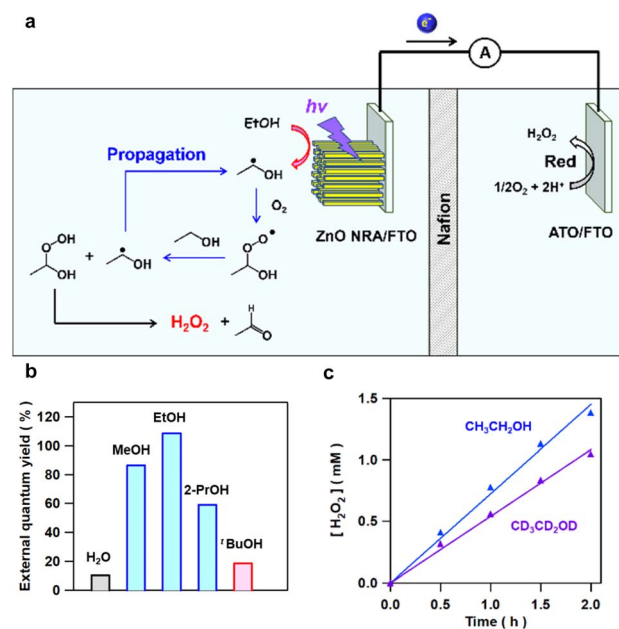




Fig. 4 (a) Photoelectrochemical cell with the structure ZnO NRA/FTO (working electrode), Ag/AgCl (reference electrode)|0.1 M  $NaClO_4$  aq. containing 4 vol% ethanol|Nafion| $O_2$ -saturated 0.1 M  $NaClO_4$  aq.|ATO/FTO (auxiliary electrode). For simplicity, the Ag/AgCl reference electrode is omitted in this figure. (b) Additive effect of various alcohols on the ATO-CL(100)/ZnO(50)-photocatalyzed  $H_2O_2$  production under UV-light irradiation ( $\lambda = 365$  nm, light intensity = 1 mW  $cm^{-2}$ , photon flux =  $1.6 \times 10^{16}$   $cm^{-2}$   $s^{-1}$ ). (c) Time courses for ATO-CL(100)/ZnO(50)-photocatalyzed  $H_2O_2$  production in the 4 vol%  $C_2H_5OH$  and  $C_2D_5OD$  aqueous solutions at 288 K.





Scheme 1 Schematic description of the action mechanism of ATO-CL/ZnO photocatalysis for the production of  $\text{H}_2\text{O}_2$  from ethanol aqueous solution.

(eqn (10)).  $\text{CH}_3\dot{\text{C}}\text{HOH}$  radical reacts with  $\text{O}_2$  to yield  $\text{CH}_3\text{CH}(\text{OH})\text{O}\dot{\text{O}}$  radical (eqn (11)). Extraction of H atom of  $\text{CH}_3\text{CH}_2\text{OH}$  by  $\text{CH}_3\text{CH}(\text{OH})\text{O}\dot{\text{O}}$  radical affords  $\text{CH}_3\text{CH}(\text{OH})\text{OOH}$  with  $\text{CH}_3\dot{\text{C}}\text{HOH}$  radical reproduced (eqn (12)).  $\text{CH}_3\text{CH}(\text{OH})\text{OOH}$  is decomposed to  $\text{H}_2\text{O}_2$  and  $\text{CH}_3\text{CHO}$  (eqn (13)).



It has recently been observed in a  $\text{TiO}_2$  photoelectrode system that a large photocurrent due to the current doubling of  $\text{C}_2\text{H}_5\text{OH}$  in a degassed electrolyte solution is halved by the presence of  $\text{O}_2$ .<sup>38</sup> This result indicates that the current doubling of  $\text{C}_2\text{H}_5\text{OH}$  is inhibited due to the rapid reaction of  $\text{CH}_3\dot{\text{C}}\text{HOH}$  with  $\text{O}_2$  in the solution (eqn (11)). For the reaction to occur according to this reaction scheme, the alcohol must have at least one H atom on the  $\alpha$ -carbon. To confirm this, the effect of adding various alcohols on the ATO-CL/ZnO-photocatalyzed  $\text{H}_2\text{O}_2$  production was investigated. As shown by the data (Fig. 4b), the external quantum efficiency decreases in the following order: primary alcohols (ethanol, methanol) > secondary alcohol (2-propanol) > tertiary alcohol (tert-butanol). In fact, the addition of butanol bearing no H atom at the  $\alpha$ -position hardly accelerates the reaction.

4-Nitrophenol was reported to be a scavenger of ethyl radical ( $\text{CH}_3\dot{\text{C}}\text{H}_2$ ).<sup>39</sup> Then, the effect of adding 4-nitrophenol on the photocatalytic activity of ATO-CL/ZnO was examined. The amount of  $\text{H}_2\text{O}_2$  produced after 15 min UV-light irradiation decreases with increasing concentration of 4-nitrophenol (Fig. S14†). Further, since the propagation process in the chain reaction involves the C–H bond cleavage, the kinetic isotope effect was investigated by measuring the rates of reaction in the  $\text{C}_2\text{H}_5\text{OH}$  and  $\text{C}_2\text{D}_5\text{OD}$  systems at 288 K. In both the systems, the reaction apparently follows the zero-order rate law at  $t_p \leq 2$  h (Fig. 4c), and the rate of  $\text{H}_2\text{O}_2$  generation in the  $\text{C}_2\text{D}_5\text{OD}$  system ( $0.52 \text{ mM h}^{-1}$ ) decreases as compared to the value in the

$\text{C}_2\text{H}_5\text{OH}$  system ( $0.69 \text{ mM h}^{-1}$ ). All these results support the chain reaction mechanism, which explains the faradaic efficiency of PEC  $\text{H}_2\text{O}_2$  production at the ZnO NRA photoanode exceeding 200% and the external quantum yield of ATO-CL/ZnO-photocatalyzed reaction reaching approximately 500%.

In the  $\text{TiO}_2$  photocatalytic reaction, the degradation of alcohols and aldehydes is known to proceed in the presence of  $\text{O}_2$  via the autooxidation involving radical chain reactions.<sup>40</sup> Also, the research group of Hashimoto and Fujishima previously studied PEC oxidation of ethanol on a Pd patterned film-coated  $\text{TiO}_2$  photoelectrode in the presence of  $\text{O}_2$ . The authors demonstrated that  $\text{H}_2\text{O}_2$  is produced via a similar radical chain reaction (eqn (10)–(13)) on the oxidation site (or  $\text{TiO}_2$  surface) but not on the reduction site (or Pd surface).<sup>41</sup> However, in the  $\text{TiO}_2$ -photocatalyzed ORR in aerated ethanol aqueous solution, the concentration of  $\text{H}_2\text{O}_2$  produced saturates only at  $\sim 0.35 \text{ mM}$ .<sup>42</sup> This is because  $\text{H}_2\text{O}_2$  is chemisorbed onto  $\text{TiO}_2$  and the resulting surface complex readily undergoes reductive photocatalytic decomposition.<sup>43</sup>

## Conclusions

In the photocatalytic  $\text{H}_2\text{O}_2$  production, increasing the quantum yield and production amount is a major challenge, while it is also important from the viewpoint of artificial photosynthesis to synthesize  $\text{H}_2\text{O}_2$  from  $\text{O}_2$  and  $\text{H}_2\text{O}$  under visible light irradiation. The key findings in this study are summarized as follows (Scheme 1). Only mixing of ZnO and ATO NPs in near-neutral solution spontaneously forms a nanohybrid consisting of ATO clusters and ZnO due to the electrostatic interaction between them (ATO-CL/ZnO). Noble metal-free ATO-CL/ZnO possesses the features of effective separation of reduction sites (ATO) and oxidation sites (ZnO) through the interfacial charge transfer between the components, high electric conductivity and electrocatalytic activity of ATO for  $2e^-$ -ORR, and very low affinity of ATO and ZnO for  $\text{H}_2\text{O}_2$ . Consequently, UV-light irradiation ( $\lambda = 365 \text{ nm}$ ) of ATO-CL/ZnO in  $\text{O}_2$ -saturated ethanol solution yields  $162 \text{ mM H}_2\text{O}_2$  ( $8.0 \text{ mmol}$ ) at  $t_p = 24 \text{ h}$ . Further, an unparalleled high external quantum yield of  $\sim 500\%$  can be achieved through  $2e^-$ -ORR by the CB electrons over ATO and the VB hole-induced radical chain reaction over ZnO. Finally, it should be emphasized that the present photocatalytic and PEC systems yield  $\text{H}_2\text{O}_2$  via both the reduction and oxidation processes, which is a great advantage over water splitting. Rational design of the entire reaction system including the photocatalyst materials can break through the quantum yield limit of unity (100%) to open up the practical on-site  $\text{H}_2\text{O}_2$  production.

## Data availability

The authors confirm that the data supporting the findings of this study are available within the article and its ESI.†

## Author contributions

Y. Y. and H. S. conducted catalyst synthesis, characterization, photocatalytic experiments, and S. N. carried out EC and PEC



experiments, and T. S. and H. T. supervised the work and data analysis.

## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

This work was financially supported by JSPS KAKENHI Grant-in-Aid for Scientific Research (C) no. 21K05236 and 23K04545, the Futaba Foundation, Nippon Sheet Glass Foundation for Materials Science and Engineering, Kato Foundation for Promotion of Science, and Izumi Science and Technology Foundation.

## Notes and references

- 1 J. M. Campos-Martin, G. Blanco-Brieva and J. L. G. Fierro, Hydrogen peroxide synthesis: an outlook beyond the anthraquinone process, *Angew. Chem., Int. Ed.*, 2006, **45**, 6962–6984.
- 2 K. Mase, M. Yoneda, Y. Yamada and S. Fukuzumi, Seawater usable for production and consumption of hydrogen peroxide as a solar fuel, *Nat. Commun.*, 2016, **7**, 11470.
- 3 H. Tada, Hydrogen peroxide photo-fuel cells, *Dalton Trans.*, 2023, **52**, 14733–14741.
- 4 H. Hou, X. Zeng and X. Zhang, Production of hydrogen peroxide by photocatalytic processes, *Angew. Chem., Int. Ed.*, 2020, **59**, 17356–17376.
- 5 N. Karamoschos and D. Tasis, Photocatalytic evolution of hydrogen peroxide: A minireview, *Energies*, 2022, **15**, 6202.
- 6 S. Lee, H.-S. Bae and W. Choi, Selective control and characteristics of water oxidation and dioxygen reduction in environmental photo(electro)catalytic systems, *Acc. Chem. Res.*, 2023, **56**, 867–877.
- 7 S. Mansingh, K. K. Das, N. Priyadarshini, D. P. Sahoo, D. Prusty, J. Sahu, U. A. Mohanty and K. Parida, Minireview elaborating S-scheme charge dynamic photocatalysts: Journey from Z to S, mechanism of charge flow, characterization proof, and H<sub>2</sub>O<sub>2</sub> evolution, *Energy Fuels*, 2023, **37**, 9873–9894.
- 8 Y. Kofuji, Y. Isobe, Y. Shiraishi, H. Sakamoto, S. Tanaka, S. Ichikawa and T. Hirai, Carbon nitride–aromatic diimide–graphene nanohybrids: Metal-free photocatalysts for solar-to-hydrogen peroxide energy conversion with 0.2% efficiency, *J. Am. Chem. Soc.*, 2016, **138**, 10019–10025.
- 9 L. Shi, L. Yang, W. Zhou, Y. Liu, L. Yin, X. Hai, H. Song and J. Ye, Photoassisted construction of holey defective g-C<sub>3</sub>N<sub>4</sub> photocatalysts for efficient visible-light-driven H<sub>2</sub>O<sub>2</sub> production, *Small*, 2018, **4**, 1703142.
- 10 Q. Tian, L. Jing, S. Ye, J. Liu, R. Chen, C. A. H. Price, F. Fan and J. Liu, Nanospacial charge modulation of monodispersed polymeric microsphere photocatalysts for exceptional hydrogen peroxide production, *Small*, 2021, **17**, 2103224.
- 11 L. Wang, J. Zhang, Y. Zhang, H. Yu, Y. Qu and J. Yu, Inorganic metal-oxide photocatalyst for H<sub>2</sub>O<sub>2</sub> production, *Small*, 2022, **18**, 2104561.
- 12 Y. Shiraishi, T. Takii, T. Hagi, S. Mori, Y. Kofuji, Y. Kitagawa, S. Tanaka, S. Ichikawa and T. Hirai, Resorcinol-formaldehyde resins as metal-free semiconductor photocatalysts for solar-to-hydrogen peroxide energy conversion, *Nat. Mater.*, 2019, **18**, 985–993.
- 13 Z. Teng, Q. Zhang, H. Yang, K. Kato, W. Yang, Y.-R. Lu, S. Liu, C. Wang, A. Yamakata, C. Su, B. Liu and T. Ohno, Atomically dispersed antimony on carbon nitride for the artificial photosynthesis of hydrogen peroxide, *Nat. Catal.*, 2021, **4**, 374–384.
- 14 W. Fan, B. Zhang, X. Wang, W. Ma, D. Li, Z. Wang, M. Dupuis, J. Shi, S. Liao and C. Li, Efficient hydrogen peroxide synthesis by metal-free polyterthiophene via photoelectrocatalytic dioxygen reduction, *Energy Environ. Sci.*, 2020, **13**, 238–245.
- 15 J. D. Xiao, Q. Han, Y. Xie, J. Yang, Q. Su, Y. Chen and H. Cao, Is C<sub>3</sub>N<sub>4</sub> chemically stable toward reactive oxygen species in sunlight-driven water treatment?, *Environ. Sci. Technol.*, 2017, **51**, 13380–13387.
- 16 T. Liu, Z. Pan, J. J. M. Vequizo, K. Kato, B. Wu, A. Yamakata, K. Katayama, B. Chen, C. Chu and K. Domen, Overall photosynthesis of H<sub>2</sub>O<sub>2</sub> by an inorganic semiconductor, *Nat. Commun.*, 2022, **13**, 1034.
- 17 Z. Liu, X. Sheng, D. Wang and X. Feng, Generation utilizing photocatalytic oxygen reduction at a triphase interface, *iScience*, 2019, **17**, 67–73.
- 18 X. Zhang, D. Gao, B. Zhu, B. Cheng, J. Yu and H. Yu, Enhancing photocatalytic H<sub>2</sub>O<sub>2</sub> production with Au co-catalysts through electronic structure modification, *Nat. Commun.*, 2024, **15**, 3212.
- 19 H. Kominami, K. Kamitani and A. Tanaka, Rapid production of 38 mM H<sub>2</sub>O<sub>2</sub> in an alcoholic suspension of a WO<sub>3</sub> photocatalyst under visible light, *Chem. Commun.*, 2024, **60**, 7017–7020.
- 20 H. Tada and S. Naya, Antimony-doped tin oxide catalysts for green and sustainable chemistry, *J. Phys. Chem. C*, 2022, **126**, 13539–13547.
- 21 H. Tada, M. Teranishi and S. Naya, Hydrogen peroxide production by inorganic photocatalysts consisting of gold nanoparticle and metal oxide towards oxygen cycle chemistry, *J. Phys. Chem. C*, 2023, **127**, 5199–5209.
- 22 K. Kosaka, H. Yamada, S. Matsui, S. Echigo and K. Shishida, Comparison among the methods for hydrogen peroxide measurements to evaluate advanced oxidation processes: application of a spectrophotometric method using copper(II) ion and 2,9-dimethyl-1,10-phenanthroline, *Environ. Sci. Technol.*, 1998, **32**, 3821–3824.
- 23 J. M. Xu, L. Li, S. Wang, H. L. Ding, Y. X. Zhang and G. H. Li, Influence of Sb doping on the structural and optical properties of tin oxide nanocrystals, *CrystEngComm*, 2013, **15**, 3296–3300.
- 24 S. Liang, X. Gou, J. Cui, Y. Luo, H. Qu, T. Zhang, Z. Yang, Q. Yang and S. Sun, Novel cone-like ZnO mesocrystals with co-exposed (10-11) and (000-1) facets and enhanced



- photocatalytic activity, *Inorg. Chem. Front.*, 2018, **5**, 2257–2267.
- 25 H. Suzuki, J. Yamauchi, S. Naya, H. Sugime and H. Tada, Noble metal-free inorganic photocatalyst consisting of antimony-doped tin oxide nanorod and titanium oxide for two-electron oxygen reduction reaction, *ChemPhysChem*, 2022, **23**, e202200029.
  - 26 H. Tada, A. Hattori, Y. Tokihisa, K. Imai, N. Tohge and S. Ito, A patterned–TiO<sub>2</sub>/SnO<sub>2</sub> bilayer type photocatalyst, *J. Phys. Chem. B*, 2000, **104**, 4585–4587.
  - 27 T. Takata, J. Jiang, Y. Sakata, M. Nakabayashi, N. Shibata, V. Nandal, K. Seki, T. Hisatomi and K. Domen, Photocatalytic water splitting with a quantum efficiency of almost unity, *Nature*, 2020, **581**, 411–414.
  - 28 M. Okazaki, Y. Suganami, N. Hirayama, H. Nakata, T. Oshikiri, T. Yokoi, H. Misawa and K. Maeda, Site-selective deposition of a cobalt cocatalyst onto a plasmonic Au/TiO<sub>2</sub> photoanode for improved water oxidation, *ACS Appl. Energy Mater.*, 2020, **3**, 5142–5146.
  - 29 Y. Park, H. Kim, R. C. Pawar, S. Kang and C. S. Lee, Photocatalytic evaluation of ATO/TiO<sub>2</sub> heterojunction films fabricated by a nanoparticle deposition system, *Mater. Chem. Phys.*, 2018, **203**, 118–124.
  - 30 L. E. Greene, M. Law, J. Goldberger, F. Kim, J. C. Johnson, Y. Zhang, R. J. Saykally and P. Yang, Low-temperature wafer-scale production of ZnO nanowire arrays, *Angew. Chem., Int. Ed.*, 2003, **42**, 3031–3034.
  - 31 J. Bandara and H. C. Weerasinghe, Enhancement of photovoltage of dye-sensitized solid-state solar cells by introducing high-band-gap oxide layers, *Sol. Energy Mater. Sol. Cells*, 2005, **88**, 341–350.
  - 32 G. Boschloo and D. Fitzmaurice, Spectroelectrochemistry of highly doped nanostructured tin dioxide electrodes, *J. Phys. Chem. B*, 1999, **103**, 3093–3098.
  - 33 O. Akhavan, Photocatalytic reduction of graphene oxides hybridized by ZnO nanoparticles in ethanol, *Carbon*, 2011, **49**, 11–18.
  - 34 R. Ghalta, A. Chauhan and R. Srivastava, Selective hydrogenation of cinnamaldehyde, furanic, and aromatic aldehydes over a Z-Scheme heterojunction photocatalyst constituted of Pd NPs supported on g-C<sub>3</sub>N<sub>4</sub>/ZnO nanocomposite, *ACS Appl. Nano Mater.*, 2024, **7**, 1462–1476.
  - 35 K. Tvrđy, P. A. Frantsuzov and P. V. Kamat, Photoinduced electron transfer from semiconductor quantum dots to metal oxide nanoparticles, *Proc. Natl. Acad. Sci. U. S. A.*, 2011, **108**, 29–34.
  - 36 H. Tada, S. Naya and M. Fujishima, Nanohybrid crystals with heteroepitaxial junctions for solar-to-chemical transformations, *J. Phys. Chem. C*, 2020, **124**, 25657–25666.
  - 37 W. P. Gomes, T. Freund and S. R. Morrison, Chemical reactions involving holes at the zinc oxide single crystal anode, *J. Electrochem. Soc.*, 1968, **115**, 818–823.
  - 38 H. Tada, T. Masuda, S. Naya, H. Sugime, S. Tanaka and M. Fujishima, Efficient photon-to-current and hydrogen conversion by decomposition of formic acid on TiO<sub>2</sub> photoanode, *J. Phys. Chem. C*, 2024, **128**, 9016–9023.
  - 39 J.-J. Yao, N.-Y. Gao, C. Li, L. Li and B. Xu, Mechanism and kinetics of parathion degradation under ultrasonic irradiation, *J. Hazard. Mater.*, 2010, **175**, 138–145.
  - 40 J. Schwitzgebel, J. G. Ekerdt, H. Gerischer and A. Heller, Role of the Oxygen Molecule and of the Photogenerated Electron in TiO<sub>2</sub>-Photocatalyzed Air Oxidation Reactions, *J. Phys. Chem.*, 1995, **99**(15), 5633–5638.
  - 41 K. Ikeda, H. Sakai, R. Baba, K. Hashimoto and A. Fujishima, Photocatalytic reactions involving radical chain reactions using microelectrodes, *J. Phys. Chem. B*, 1997, **101**, 2617–2620.
  - 42 M. Teranishi, S. Naya and H. Tada, In situ liquid phase synthesis of hydrogen peroxide from molecular oxygen using gold nanoparticle-loaded titanium(IV) dioxide photocatalyst, *J. Am. Chem. Soc.*, 2010, **132**, 7850–7851.
  - 43 X. Li, C. Chen and J. Zhao, Mechanism of photodecomposition of H<sub>2</sub>O<sub>2</sub> on TiO<sub>2</sub> surfaces under visible light irradiation, *Langmuir*, 2001, **17**, 4118–4122.

