

Cite this: *Chem. Sci.*, 2019, 10, 185

All publication charges for this article have been paid for by the Royal Society of Chemistry

Hetero-metallic active sites coupled with strongly reductive polyoxometalate for selective photocatalytic CO₂-to-CH₄ conversion in water†

Shuai-Lei Xie,^a Jiang Liu,^{*b} Long-Zhang Dong,^{id b} Shun-Li Li,^b Ya-Qian Lan^{*b} and Zhong-Min Su^{id *ac}

The photocatalytic reduction of CO₂ to value-added methane (CH₄) has been a promising strategy for sustainable energy development, but it is challenging to trigger this reaction because of its necessary eight-electron transfer process. In this work, an efficient photocatalytic CO₂-to-CH₄ reduction reaction was achieved for the first time in aqueous solution by using two crystalline heterogeneous catalysts, H{[Na₂K₄Mn₄(PO₄)₃(H₂O)₄]·[Mo₆O₁₂(OH)₃(HPO₄)₃(PO₄)₄][Mn₆(H₂O)₄]·16H₂O (NENU-605) and H{[Na₆CoMn₃(PO₄)₃(H₂O)₄]·[Mo₆O₁₂(OH)₃(HPO₄)₃(PO₄)₄][Co_{1.5}Mn_{4.5}]·21H₂O (NENU-606). Both compounds have similar host inorganic polyoxometalate (POM) structures constructed with strong reductive {P₄Mo₆^V} units, homo/hetero transition metal ions (Mn^{II}/Co^{II}Mn^{II}) and alkali metal ions (K⁺ and/or Na⁺). It is noted that the {P₄Mo₆^V} cluster including the six Mo^V atoms served as a multi-electron donor in the case of a photocatalytic reaction, while the transition metal ions functioned as catalytically active sites for adsorbing and activating CO₂ molecules. Additionally, the presence of alkali metal ions was believed to assist in the capture of more CO₂ for the photocatalytic reaction. The synergistic combination of the above-mentioned components in NENU-605 and NENU-606 effectively facilitates the accomplishment of the required eight-electron transfer process for CH₄ evolution. Furthermore, NENU-606 containing hetero-metallic active sites finally exhibited higher CH₄ generation selectivity (85.5%) than NENU-605 (76.6%).

Received 5th August 2018
Accepted 1st October 2018

DOI: 10.1039/c8sc03471k

rsc.li/chemical-science

Introduction

The massive discharge of CO₂ resulting from the combustion of limited fossil fuels is leading to global warming, which has driven people to find effective ways to alleviate this crisis.^{1–4} The photocatalytic reduction of CO₂ to valuable hydrocarbon fuels, such as methane (CH₄), provides a promising ‘one stone two birds’ approach to realize the purpose of eliminating energy shortage and environmental challenges.^{5,6} Nevertheless, the accomplishment of this catalytic reaction means that chemically inert CO₂ molecules adsorbed on the catalyst have to undergo a proton-assisted multi-electron transfer process; it is

a rather challenging task for catalyst design because of the uncontrollable multi-electron supply and complicated photocatalytic reaction mechanism.^{7,8} Moreover, the heterogeneous nature of the catalyst in principle is also indispensable in view of its practical application.^{7,9–17} So far, the studies on heterogeneous catalysts, especially those applied in the photocatalytic reduction of CO₂ to CH₄, mainly focus on nano-sized semi-conducting materials or composites^{18–21} because of their rich interfacial modification and structural stability that are beneficial for the photocatalytic CO₂ reduction reaction (CO₂RR)^{22–27} towards high activity and good photocatalytic durability. It is well-known that these inorganic nanomaterials are stable, but their indistinct active sites and even their electron donors are commonly difficult for the explanation of the photocatalytic reaction mechanism.²⁸ Also, the introduction of noble metal co-catalysts or heterojunctions sometimes would raise the cost and/or cover the surface active sites to obstruct incident light absorption, which results in reduced photo-conversion efficiency. Consequently, the construction of crystalline inorganic heterogeneous catalysts with well-defined active sites and multi-electron sources would be a better choice for obtaining multi-electron reductive hydrocarbon fuels and investigating the mechanism of the photocatalytic CO₂RR.²⁹

Polyoxometalate (POM) with inherent redox and semi-conductor features is one kind of inorganic crystalline material,

^aInstitute of Functional Material Chemistry, Department of Chemistry, National & Local United Engineering Lab for Power Battery, Northeast Normal University, Changchun 130024, P. R. China. E-mail: zmsu@nenu.edu.cn

^bSchool of Chemistry and Materials Science, Jiangsu Key Laboratory of Biofunctional Materials, Nanjing Normal University, Nanjing 210023, P. R. China. E-mail: liuj@njnu.edu.cn; yqlan@njnu.edu.cn

^cSchool of Chemistry and Environmental Engineering, The Collaborative Innovation Center of Optical Materials and Chemistry, CUST, Changchun University of Science and Technology, Changchun 130028, P. R. China

† Electronic supplementary information (ESI) available: Experimental methods and supporting figures and tables. CCDC 1855992–1855994. For ESI and crystallographic data in CIF or other electronic format see DOI: 10.1039/c8sc03471k

Herein, we report two stable POM-containing inorganic compounds, $\text{H}\{\text{[Na}_2\text{K}_4\text{Mn}_4(\text{PO}_4)_4(\text{H}_2\text{O})_4]\} \cdot \{\text{[Mo}_6\text{O}_{12}(\text{OH})_3(\text{HPO}_4)_3(\text{PO}_4)_4]\text{[Mn}_6(\text{H}_2\text{O})_4]\} \cdot 16\text{H}_2\text{O}$ (**NENU-605**) and $\text{H}\{\text{[Na}_6\text{CoMn}_3(\text{PO}_4)_4(\text{H}_2\text{O})_4]\} \cdot \{\text{[Mo}_6\text{O}_{12}(\text{OH})_3(\text{HPO}_4)_3(\text{PO}_4)_4]\text{[Co}_{1.5}\text{Mn}_{4.5}]\} \cdot 21\text{H}_2\text{O}$ (**NENU-606**), which have very similar host skeletons but different catalytically active species. It is noted that assembling $\{\text{P}_4\text{Mo}_6^{\text{V}}\}$ ($\text{[Mo}_6\text{O}_{12}(\text{OH})_3(\text{HPO}_4)_3(\text{PO}_4)_4\}^{6-}$) units with strong reducibility into the structures endows **NENU-605** and **NENU-606** with efficient heterogeneous photocatalytic CO_2 -to- CH_4 reduction ability in water. To our knowledge, this is the first report of $\{\text{P}_4\text{Mo}_6^{\text{V}}\}$ -based crystalline inorganic materials applied in the photocatalytic CO_2RR . Photocatalytic analysis revealed that the synergistic combination of strong reductive $\{\text{P}_4\text{Mo}_6^{\text{V}}\}$ units (donating electrons) and the first-row transition metal active centres ($\text{Mn}^{\text{II}}/\text{Co}^{\text{II}}\text{Mn}^{\text{II}}$) in **NENU-605** and **NENU-606** effectively boosts the necessary eight-electron reduction process for CH_4 evolution. Furthermore, the hetero-metallic active sites of **NENU-606** finally exhibited a higher CH_4 generation selectivity (85.5%) in the photocatalytic CO_2RR than those of **NENU-605** (76.6%). Besides, the coordination effect of alkali metal ions can also assist the accomplishment of the photocatalytic reaction by influencing the CO_2 adsorption ability of the title compounds. At the same time, the crystalline and heterogeneous nature of these stable inorganic POM-included compounds also provides some insight into the photocatalytic CO_2RR mechanism.

and have very similar pure inorganic matrices composed of three kinds of independent $\text{Mn}^{\text{II}}/\text{Co}^{\text{II}}\text{-Mn}^{\text{II}}$ ions, $\text{Na}^+\text{-K}^+/\text{Na}^+$ ions, $\{\text{P}_4\text{Mo}_6^{\text{V}}\}$ polyanions, phosphate anions and water molecules (Fig. S2[†]). The overall three-dimensional (3D) architecture of these two compounds is assembled with nesting subunits by using PO_4^{3-} and O^{2-} bridges. Such a nested substructure in **NENU-605** can be described as a three-shell assembly where the PO_4^{3-} group is the innermost shell (Fig. 1a). Four $\mu_2\text{-O}$ atoms of PO_4^{3-} connect with four six-coordinated Mn1 and four K1 atoms, and these Mn1 and K1 atoms establish two types of metal-based tetrahedrons respectively. The interpenetrating coupling of two tetrahedra forms a twisted hexahedron whose diagonal-linked vertexes are occupied by Mn1 or K1 atoms. Meanwhile, the top and bottom surfaces of this hexahedron are capped by two Na atoms to build the shuttle-shaped second shell (Fig. 1b). Through the 16PO_4^{3-} and 8O^{2-} groups, the second shell further communicates with the outer four Mn2 atoms and four $\{\text{Mo}_6^{\text{V}}\}$ rings. Each Mn2 atom is coordinated by five O atoms from four PO_4^{3-} anions and one O atom from the coordinated water molecule (Fig. S3[†]) and is surrounded by four $\{\text{Mo}_6^{\text{V}}\}$ rings made of six edge-sharing $\{\text{Mo}^{\text{VO}}_6\}$ octahedrons. It is noted that every $\{\text{Mo}_6^{\text{V}}\}$ ring supported by four PO_4^{3-} anions constitutes a strong reductive component, $\text{P}_4\text{Mo}_6^{\text{V}}$,^{45–49} which includes six Mo^{V} atoms (Fig. S4[†]). Interestingly, these Mn2 atoms and $\{\text{Mo}_6^{\text{V}}\}$ rings can construct peripherally larger distorted hexahedrons in the same interpenetrating way as the second shell; the diagonal-linked vertexes are occupied by Mn2 atoms or $\{\text{Mo}_6^{\text{V}}\}$ rings that can be treated as the third shell (Fig. 1c). In such a way, a three-shell nested substructure is formed (Fig. 1d). To better further understand the evolution of this nested subunit, it has been simplified as a distorted hexahedral entity whose eight vertexes are taken up by Mn2 atoms and $\{\text{Mo}_6^{\text{V}}\}$ rings, as shown in Fig. 2a and b. These Mn2 atoms and $\{\text{Mo}_6^{\text{V}}\}$ rings serve as nodes to come into contact with the eight adjacent subunits in Mn2-to-Mn2 and $\{\text{Mo}_6^{\text{V}}\}\text{-Mn3-}\{\text{Mo}_6^{\text{V}}\}$ modes (Fig. 2c), which finally gives rise to the 3D inorganic structure of **NENU-605** (Fig. 2d). The linkage of Mn2-to-

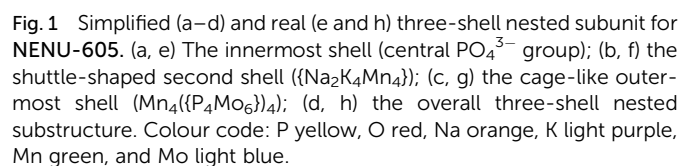




Fig. 2 Graphical growth of the 3D architecture of **NENU-605**: (a) simplified three-shell nested substructure; (b) further simplified nested substructure as a distorted hexahedral entity (Mn2, green; {Mo₆V} ring, light blue); (c) nested substructure with an 8-connected node in contact with the eight adjacent subunits (Mn2/Mn3, pink; {Mo₆V} ring, dashed light blue); (d) real 3D inorganic structure of **NENU-605**.

Mn2 is achieved by two μ_2 -O atoms from two PO_4^{3-} , while every six-coordinated Mn3 atom is shared by two {Mo₆V} rings from two neighboring subunits (Fig. S5†). For **NENU-606**, the coordination environment of the Mn2 atom is crooked tetragonal pyramid structure consisting of five O atoms from four PO_4^{3-} groups (Fig. S6†); moreover the K1 atoms are fully replaced by Na atoms (Fig. S7†). The most important difference between these two compounds is that the original Mn atom sites in the lattice of **NENU-605** are partially substituted by Co atoms, and the doping ratio (1 : 3) of Co/Mn in **NENU-606** is determined by an Inductively Coupled Plasma Atomic Emission Spectrometer (ICP-AES). Besides, if the nested substructure and the Mn2/Mn3 atoms are regarded as 8-connected nodes and linkers, respectively, then the skeletons of **NENU-605** and **NENU-606** feature a unimodal topology with the Schläfli symbol of $4^{24} \cdot 6^4$ (Fig. S8†).

The phase purity and thermal stability of **NENU-605** and **NENU-606** were demonstrated using well-matched powder X-ray diffraction (PXRD) patterns and thermogravimetric analysis, respectively (Fig. S9 and S10†). As shown in Fig. S9a and b,† these two compounds can also remain stable when being soaked in aqueous solutions at different pH values for several days, which indicated that their structures have strong acid and alkali resistance.⁵⁰ Besides, in order to confirm the heterogeneous catalytic nature, the structural stability of the title compounds was tested again under the conventional conditions of the photocatalytic CO₂RR. It is obvious that the PXRD patterns of all the treated crystals remain intact, indicating that no phase transition or structural collapse occurred. A broad UV-vis absorption range of 200–600 nm for **NENU-605** and **NENU-606** revealed that they indeed have better light-harvesting ability than a single POM cluster, whose absorption mainly focuses on the ultraviolet region (200–400 nm).^{51–53} Based on this, the band gaps of 3.20 (**NENU-605**) and 2.57 eV (**NENU-606**) were evaluated by the Kubelka–Munk (KM) method (Fig. S11†), unveiling the potential for these two compounds to be used as semi-conducting photocatalysts. At the same time, Mott–Schottky measurements at frequencies of 1000, 1500, and 2000 Hz were used to determine the LUMO positions of **NENU-605** and **NENU-606** such that the occurrence of the photocatalytic CO₂RR and relevant reductive products can be simply inferred (Fig. S12 and S13†). As we can see, the LUMO locations of compounds are more negative than the reduction potentials required for producing CO (−0.53 V vs. NHE) and CH₄ (−0.24 V vs. NHE),

indicating that the electrons can be transferred to the CO₂ molecule for further reduction.

Taking the above features of **NENU-605** and **NENU-606** into consideration, the photocatalytic CO₂RR was conducted under a pure CO₂ (1.0 atm, 293 K) atmosphere in an aqueous solution with triethanolamine (TEOA) as a sacrificial agent (TEOA/H₂O = 2 : 28 mL, pH \approx 10.5). In addition, [Ru(bpy)₃]Cl₂·6H₂O (0.01 mmol) as an auxiliary photosensitizer (PS) was added into the reaction system for increased visible-light absorption.⁵⁴ Because of the matched LUMO positions between the PS and catalysts (Fig. S14 and S15†), photo-generated electrons were allowed to migrate from the PS to the catalysts. During the whole photo-reduction process, gaseous CH₄ and CO were the main reaction products detected by gas chromatography, while trace amounts of HCOOH were produced in the aqueous solution as detected by ion chromatography. Moreover, no competitive H₂ was produced during the whole reaction (Fig. S16†). With the increasing irradiation time, the yields of CO and CH₄ increase simultaneously at different reaction rates (Fig. 3a and b); the amount of CH₄ for **NENU-605** reached up to 170 nmol (*i.e.*, 894.7 nmol g^{−1} h^{−1}) after 19 h. In contrast, the maximum production of CH₄ achieved for **NENU-606** was 402 nmol (*i.e.*, 1747.8 nmol g^{−1} h^{−1}) after 23 h (Fig. 3c). Moreover, they finally exhibit a very high selectivity (CH₄ over CO) of 76.6% (**NENU-605**) and 85.5% (**NENU-606**) (Fig. 3c). It is significant that this is the first report of heterogeneous POM-based catalysts applied in the photocatalytic CO₂RR that exhibited such a high selectivity towards CH₄, although the corresponding CH₄ outputs are still very low and need to be greatly improved. The CO amounts determined after the reaction were 267.0 nmol g^{−1} h^{−1} (**NENU-605**) and 295.7 nmol g^{−1} h^{−1} (**NENU-606**), and the relevant parameters including the TONs and TOFs of these

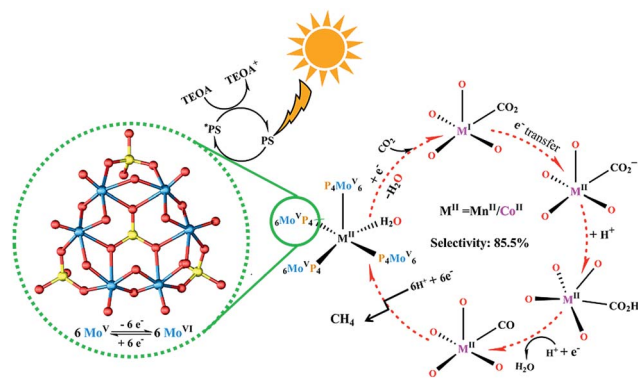


Fig. 3 Amounts of CH₄ and CO produced as a function of the time of visible-light irradiation using (a) **NENU-605** and (b) **NENU-606**; (c) total product yield and the selectivity of gaseous products in the photocatalytic CO₂RR; (d) the mass spectra of ¹³CH₄ recorded under a ¹³CO₂ atmosphere. The reaction with the catalyst (10 mg) in the H₂O/TEOA (14 : 1 v/v, 30 mL) solution irradiated using a Xe lamp filtered to produce light in the range of 420–800 nm.



To disclose the origin and difference of the photocatalytic performances of **NEU-605** and **NEU-606** in the CO₂RR, the role of the {Mn[Mo₆O₁₂(OH)₃(HPO₄)₃(PO₄)₂]} (abbr.{Mn(P₄-Mo₆)₂}) cluster (**NEU-607**) (Fig. S24-26†) was mainly considered in our system. **NEU-607** is a dimer, with one {Mn^{II}} atom sandwiched between two {P₄Mo₆} units, displaying a similar connection mode to that of **NEU-605** and **NEU-606**. When

Based on the analysis of related experimental results, a speculative reaction mechanism with respect to the photocatalytic CO₂-to-CH₄ conversion using these two crystalline POM-containing compounds, as well as possible photo-generated electron transport pathways, was proposed (Fig. 4). First, the photosensitizer in the system absorbs sunlight to generate photo-excited electrons from the HOMO and then transports them to the catalyst through the matched LUMO positions; TEOA as the sacrificial reagent consumes the electron holes produced in the valence band. Second, strongly reductive {P₄Mo₆^V} units enrich and offer electrons to the active metal centre under the stimulation of the photo-induced redox reaction. Third, the adsorbed CO₂ molecule obtains electrons from the active metal sites, with the assistance of H₂O as a proton donor, eventually undergoing the multi-electron transfer process of CO₂-to-CH₄ reduction. In addition, because the low



This journal is © The Royal Society of Chemistry 2019

local concentration of CO₂ around the typical catalysts can make the reaction suffer from slow kinetics,^{56,57} the coordination of alkali metal cations in **NENU-605** and **NENU-606** architectures is helpful to effectively physically adsorb CO₂ molecules through non-covalent interactions,^{58,59} which could lower the overpotential and Gibbs free energy ΔG of the chemical reduction of CO₂.^{60–62}

Conclusions

In summary, this is the first report of inorganic POM-containing crystalline materials as heterogeneous catalysts applied in the photocatalytic CO₂RR, and significant CO₂-to-CH₄ conversion in the aqueous phase is realized. Both **NENU-605** and **NENU-606** have almost identical 3D host structures composed of three-shell nested substructures, which were further composed of {P₄Mo₆} clusters, first-row transition metals and alkali metals. Because of the strong reducibility and electron-enrichment of the {P₄Mo₆} unit, sufficient electrons can be transported to active metal sites under the effect of the photo-stimulated redox reaction for the activation and reduction of CO₂ molecules. In virtue of the synergistic coupling of structural components, these compounds finally exhibit high photocatalytic CH₄ selectivity (76.6%, **NENU-605**; 85.5%, **NENU-606**). Especially for **NENU-606** with hetero-metallic active sites, the interaction between Mn^{II} and Co^{II} ions is found to be more efficient for the photocatalytic CO₂RR than that between the homo-metallic Mn^{II} ions in **NENU-605**. Notably, the introduction of the {P₄Mo₆} building block not only endows **NENU-605** and **NENU-606** with favorable structural rigidity, but also, indeed, facilitates the accomplishment of the eight-electron transfer process of CH₄ formation by delivering sufficient electrons. We anticipate that such a feasible strategy, embedding strongly reductive components into the visible-light sensitized catalyst architecture, could inspire more enthusiasm to construct stable inorganic networks for the effective reduction of CO₂ to other high-valued hydrocarbons and further enhance their photocatalytic activity.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

This work was financially supported by NSFC (No. 21622104, 21471080, 21701085 and SBK2017040708), the NSF of Jiangsu Province of China (No. BK20171032), the Natural Science Research of Jiangsu Higher Education Institutions of China (No. 17KJB150025), Priority Academic Program Development of Jiangsu Higher Education Institutions and the Foundation of Jiangsu Collaborative Innovation Center of Biomedical Functional Materials.

Notes and references

- 1 C. Steinlechner and H. Junge, *Angew. Chem., Int. Ed.*, 2018, **57**, 44–45.
- 2 T. Sakakura, J.-C. Choi and H. Yasuda, *Chem. Rev.*, 2007, **107**, 2365–2387.
- 3 T. Inoue, A. Fujishima, S. Konishi and K. Honda, *Nature*, 1979, **277**, 637–638.
- 4 A. Rubino, *Nat. Energy*, 2018, **3**, 255–256.
- 5 X. Li, J. Wen, J. Low, Y. Fang and J. Yu, *Sci. China Mater.*, 2014, **57**, 70–100.
- 6 H. Rao, L. C. Schmidt, J. Bonin and M. Robert, *Nature*, 2017, **548**, 74–77.
- 7 X. Liu, S. Inagaki and J. Gong, *Angew. Chem., Int. Ed.*, 2016, **55**, 14924–14950.
- 8 X. Chang, T. Wang and J. Gong, *Energy Environ. Sci.*, 2016, **9**, 2177–2196.
- 9 K. Li, B. Peng and T. Peng, *ACS Catal.*, 2016, **6**, 7485–7527.
- 10 L. Zeng, X. Guo, C. He and C. Duan, *ACS Catal.*, 2016, **6**, 7935–7947.
- 11 Y. Fu, D. Sun, Y. Chen, R. Huang, Z. Ding, X. Fu and Z. Li, *Angew. Chem., Int. Ed.*, 2012, **51**, 3364–3367.
- 12 S. Wang, W. Yao, J. Lin, Z. Ding and X. Wang, *Angew. Chem.*, 2014, **126**, 1052–1056.
- 13 H. Zhang, J. Wei, J. Dong, G. Liu, L. Shi, P. An, G. Zhao, J. Kong, X. Wang, X. Meng, J. Zhang and J. Ye, *Angew. Chem.*, 2016, **128**, 14522–14526.
- 14 C. Wang, Z. Xie, K. E. deKrafft and W. Lin, *J. Am. Chem. Soc.*, 2011, **133**, 13445–13454.
- 15 Y. Wang, N.-Y. Huang, J.-Q. Shen, P.-Q. Liao, X.-M. Chen and J.-P. Zhang, *J. Am. Chem. Soc.*, 2018, **140**, 38–41.
- 16 H.-Q. Xu, J. Hu, D. Wang, Z. Li, Q. Zhang, Y. Luo, S.-H. Yu and H.-L. Jiang, *J. Am. Chem. Soc.*, 2015, **137**, 13440–13443.
- 17 D. Wang, R. Huang, W. Liu, D. Sun and Z. Li, *ACS Catal.*, 2014, **4**, 4254–4260.
- 18 W. Min, C. Lingjing, L. Tai-Chu and R. Marc, *Angew. Chem., Int. Ed.*, 2018, **57**, 7769–7773.
- 19 R. Kuriki, M. Yamamoto, K. Higuchi, Y. Yamamoto, M. Akatsuka, D. Lu, S. Yagi, T. Yoshida, O. Ishitani and K. Maeda, *Angew. Chem.*, 2017, **129**, 4945–4949.
- 20 R. Kuriki, H. Matsunaga, T. Nakashima, K. Wada, A. Yamakata, O. Ishitani and K. Maeda, *J. Am. Chem. Soc.*, 2016, **138**, 5159–5170.
- 21 W. Tu, Y. Zhou and Z. Zou, *Adv. Mater.*, 2014, **26**, 4607–4626.
- 22 S. N. Habisreutinger, L. Schmidt-Mende and J. K. Stolarczyk, *Angew. Chem., Int. Ed.*, 2013, **52**, 7372–7408.
- 23 Y. Fang and X. Wang, *Chem. Commun.*, 2018, **54**, 5674–5687.
- 24 G. Chao, M. Qiangqiang, Z. Kun, Y. Huajie, W. Dawei, G. Jun, Z. Shenlong, C. Lin, H. Meng, L. Qunxiang, Z. Huijun, H. Xingjiu, G. Yan and T. Zhiyong, *Adv. Mater.*, 2016, **28**, 6485–6490.
- 25 R. Long, Y. Li, Y. Liu, S. Chen, X. Zheng, C. Gao, C. He, N. Chen, Z. Qi, L. Song, J. Jiang, J. Zhu and Y. Xiong, *J. Am. Chem. Soc.*, 2017, **139**, 4486–4492.
- 26 C. Gao, S. Chen, Y. Wang, J. Wang, X. Zheng, J. Zhu, L. Song, W. Zhang and Y. Xiong, *Adv. Mater.*, 2018, **30**, 1704624–1704632.
- 27 S. Yongfu, W. Ju, L. Xiaodong, S. Wen, L. Peiquan, J. Xingchen, G. Shan, L. Liang, X. Jiaqi, Y. Wensheng, W. Chengming and X. Yi, *Angew. Chem.*, 2018, **130**, 8855–8859.

- 28 S. Wang, B. Y. Guan, Y. Lu and X. W. D. Lou, *J. Am. Chem. Soc.*, 2017, **139**, 17305–17308.
- 29 R. Kuriki, T. Ichibha, K. Hongo, D. Lu, R. Maezono, H. Kageyama, O. Ishitani, K. Oka and K. Maeda, *J. Am. Chem. Soc.*, 2018, **140**, 6648–6655.
- 30 J. Etteedgui, Y. Diskin-Posner, L. Weiner and R. Neumann, *J. Am. Chem. Soc.*, 2011, **133**, 188–190.
- 31 J. Dong, J. Hu, Y. Chi, Z. Lin, B. Zou, S. Yang, C. L. Hill and C. Hu, *Angew. Chem.*, 2017, **129**, 4544–4548.
- 32 S. Mukhopadhyay, J. Debgupta, C. Singh, A. Kar and S. K. Das, *Angew. Chem.*, 2018, **130**, 1936–1941.
- 33 A. Proust, B. Matt, R. Villanneau, G. Guillemot, P. Gouzerh and G. Izzet, *Chem. Soc. Rev.*, 2012, **41**, 7605–7622.
- 34 P. Yang and U. Kortz, *Acc. Chem. Res.*, 2018, **51**, 1599–1608.
- 35 M. Zhao, X.-W. Zhang and C.-D. Wu, *ACS Catal.*, 2017, **7**, 6573–6580.
- 36 L.-X. Cai, S.-C. Li, D.-N. Yan, L.-P. Zhou, F. Guo and Q.-F. Sun, *J. Am. Chem. Soc.*, 2018, **140**, 4869–4876.
- 37 W. Guo, H. Lv, Z. Chen, K. P. Sullivan, S. M. Lauinger, Y. Chi, J. M. Sumliner, T. Lian and C. L. Hill, *J. Mater. Chem. A*, 2016, **4**, 5952–5957.
- 38 T. Ishizuka, S. Ohkawa, H. Ochiai, M. Hashimoto, K. Ohkubo, H. Kotani, M. Sadakane, S. Fukuzumi and T. Kojima, *Green Chem.*, 2018, **20**, 1975–1980.
- 39 B. B. Sarma, I. Efremenko and R. Neumann, *J. Am. Chem. Soc.*, 2015, **137**, 5916–5922.
- 40 H. Shi, Y. Yu, Y. Zhang, X. Feng, X. Zhao, H. Tan, S. U. Khan, Y. Li and E. Wang, *Appl. Catal., B*, 2018, **221**, 280–289.
- 41 S. Li, S. Liu, S. Liu, Y. Liu, Q. Tang, Z. Shi, S. Ouyang and J. Ye, *J. Am. Chem. Soc.*, 2012, **134**, 19716–19721.
- 42 M. Natali, I. Bazzan, S. Goberna-Ferrón, R. Al-Oweini, M. Ibrahim, B. Bassil, H. Dau, F. Scandola, J. Galán-Mascarós and U. Kortz, *Green Chem.*, 2017, **19**, 2416–2426.
- 43 A. Rubinstein, P. Jiménez-Lozano, J. J. Carbó, J. M. Poblet and R. Neumann, *J. Am. Chem. Soc.*, 2014, **136**, 10941–10948.
- 44 K. Suzuki, F. Tang, Y. Kikukawa, K. Yamaguchi and N. Mizuno, *Angew. Chem., Int. Ed.*, 2014, **53**, 5356–5360.
- 45 Y. Dong, Z. Dong, Z. Zhang, Y. Liu, W. Cheng, H. Miao, X. He and Y. Xu, *ACS Appl. Mater. Interfaces*, 2017, **9**, 22088–22092.
- 46 D.-Y. Du, J.-S. Qin, Y.-G. Li, S.-L. Li, Y.-Q. Lan, X.-L. Wang, K.-Z. Shao, Z.-M. Su and E.-B. Wang, *Chem. Commun.*, 2011, **47**, 2832–2834.
- 47 K. Gong, W. Wang, J. Yan and Z. Han, *J. Mater. Chem. A*, 2015, **3**, 6019–6027.
- 48 Z. Han, X. Xin, R. Zheng and H. Yu, *Dalton Trans.*, 2018, **47**, 3356–3365.
- 49 D.-Y. Du, J.-S. Qin, T.-T. Wang, S.-L. Li, Z.-M. Su, K.-Z. Shao, Y.-Q. Lan, X.-L. Wang and E.-B. Wang, *Chem. Sci.*, 2012, **3**, 705–710.
- 50 E.-X. Chen, M. Qiu, Y.-F. Zhang, Y.-S. Zhu, L.-Y. Liu, Y.-Y. Sun, X. Bu, J. Zhang and Q. Lin, *Adv. Mater.*, 2018, **30**, 1704388–1704395.
- 51 E. Haviv, L. J. W. Shimon and R. Neumann, *Chem.-Eur. J.*, 2017, **23**, 92–95.
- 52 C. Li, K. Suzuki, N. Mizuno and K. Yamaguchi, *Chem. Commun.*, 2018, **54**, 7127–7130.
- 53 J. J. Walsh, A. M. Bond, R. J. Forster and T. E. Keyes, *Coord. Chem. Rev.*, 2016, **306**, 217–234.
- 54 T. Ouyang, H.-H. Huang, J.-W. Wang, D.-C. Zhong and T.-B. Lu, *Angew. Chem., Int. Ed.*, 2017, **56**, 738–743.
- 55 J. Zhao, Q. Wang, C. Sun, T. Zheng, L. Yan, M. Li, K. Shao, X. Wang and Z. Su, *J. Mater. Chem. A*, 2017, **5**, 12498–12505.
- 56 S. Back, M. S. Yeom and Y. Jung, *ACS Catal.*, 2015, **5**, 5089–5096.
- 57 Q. Lu, J. Rosen, Y. Zhou, G. S. Hutchings, Y. C. Kimmel, J. G. Chen and F. Jiao, *Nat. Commun.*, 2014, **5**, 3242–3247.
- 58 Y. Chen, C. W. Li and M. W. Kanan, *J. Am. Chem. Soc.*, 2012, **134**, 19969–19972.
- 59 A. S. Varela, M. Kroschel, T. Reier and P. Strasser, *Catal. Today*, 2016, **260**, 8–13.
- 60 M. Liu, Y. Pang, B. Zhang, P. De Luna, O. Voznyy, J. Xu, X. Zheng, C. T. Dinh, F. Fan, C. Cao, F. P. de Arquer, T. S. Safaei, A. Mepham, A. Klinkova, E. Kumacheva, T. Filleter, D. Sinton, S. O. Kelley and E. H. Sargent, *Nature*, 2016, **537**, 382–386.
- 61 J. Resasco, L. D. Chen, E. Clark, C. Tsai, C. Hahn, T. F. Jaramillo, K. Chan and A. T. Bell, *J. Am. Chem. Soc.*, 2017, **139**, 11277–11287.
- 62 M. R. Singh, Y. Kwon, Y. Lum, J. W. Ager III and A. T. Bell, *J. Am. Chem. Soc.*, 2016, **138**, 13006–13012.

