

Cite this: *Mater. Adv.*, 2023,
4, 5314Ultra-small platinum-based coordination
nanoparticles for radiotherapy†‡Riya George,^a Lucile Fétiveau,^a Erika Porcel,^b Farah Savina,^b
Charles Bosson Bapaume,^b Diana Dragoe,^a François Brisset,^a Hynd Remita,^c
Sandrine Lacombe^b and Laure Catala^a

Radiation therapy is an effective and localised method for cancer treatment and its efficacy is considerably improved by using radioenhancing agents. Nanoparticles containing high atomic number (Z) elements have emerged as an appealing class of enhancers. This work reports the first example of radioenhancers based on ultrasmall platinum (Pt)-polycyanometallate nanoparticles. Importantly, both novel nano-enhancers (Pt[Pt(CN)₄] and Pt[Fe(CN)₆]) are prepared in fairly large quantities using a water-based, surfactant-free, green route. The post-coating of the inorganic cores by different biocompatible polymers is straightforward and allows probing of the influence of the coating on the radiotherapeutic efficiency of the nanosystems. The structural/chemical integrity is maintained after high doses of γ -radiation and high colloidal stability is obtained in biological media. At 250 μ M total metal concentration, these nanoparticles are non-toxic to cells, but when coupled with γ -radiation, they amplify apoptosis of HeLa cells by 20% at 4.5 Gray, which rises to 60% at larger doses. Furthermore, irradiation studies conducted on a model DNA probe evidence that the amount of lethal Double Strand Breaks (DSB) is significantly enhanced in the presence of these novel Pt-based radioenhancers. The radiotherapeutic efficiency of these versatile coordination nanoparticles obtained using a cheap, fast and green process opens interesting possibilities in the field of nanomedicine.

Received 8th August 2023,
Accepted 5th October 2023

DOI: 10.1039/d3ma00516j

rsc.li/materials-advances

Introduction

Even in the 21st century, cancer remains one of the biggest healthcare challenges with 19.3 million new cases detected in 2020, resulting in 10 million deaths all across the globe.¹ There is widespread ongoing research to develop targeted, safe, and patient-specific treatment methods. Radiation therapy is applied to more than 50% of cancer patients to eliminate cancerous tissues in a localised way while minimizing the chances of recurrence in the affected area. A major advantage of radiotherapy is that tumours located deep within the body could also be targeted using high energy X-rays, γ -rays or ion beams as their penetration depth is greater than 10 cm.² However, a high dose of these ionizing radiations can damage the healthy tissues and organs adjacent to the tumour, and cause adverse side-effects like severe fatigue, radiodermatitis and in some cases, even second

cancers due to mutations generated during the process.³ Therefore, several radio-enhancers have been developed over the past two decades to maximize cancer cell killing while working within a safe range of therapeutic doses of radiation. These agents need to be stable, non-toxic to normal tissues and fairly resistant to metabolic breakdown.⁴

Irradiating cells internalized with high-Z elements generate a cascade of secondary electrons.⁵ These electrons are brought about by the ionization of heavy metal atoms, which induce a significant increase in the amount of reactive oxygen species (ROS) produced upon water radiolysis. When these radicals are produced in close proximity to the cancer cells, their proliferation is stalled, causing apoptosis and subsequent elimination. In 2004, J. F. Hainfield *et al.* provided the first proof that gold nanoparticles (NPs) significantly improved the *in vivo* efficacy of radiation therapy. They demonstrated that the ultra-small size of these particles proves beneficial for bio-distribution and relatively high concentrations of the heavy metal could be incorporated without toxicity.⁶ The potential of metallic NPs in enhancing the biological efficiency of radiation was realised, and this resulted in an exponential increase in the development of varied particles that can improve the performance of conventional radiation therapy. Additionally, nanoparticles provide a relatively large surface area and are flexible towards size, shape, and charge modifications, which proves to be

^a Université Paris-Saclay, CNRS, Institut de chimie moléculaire et des matériaux d'Orsay, 91405, Orsay, France. E-mail: laure.catala@universite-paris-saclay.fr, riya.george@universite-paris-saclay.fr

^b Université Paris-Saclay, CNRS, Institut des Sciences Moléculaires d'Orsay, 91405, Orsay, France. E-mail: erika.porcel@universite-paris-saclay.fr

^c Université Paris-Saclay, CNRS, Institut de Chimie Physique, 91405, Orsay, France

† In tribute to Dr Géraldine Carrot.

‡ Electronic supplementary information (ESI) available. See DOI: <https://doi.org/10.1039/d3ma00516j>

advantageous for drug encapsulation and delivery to target sites.⁷ Few of the NPs developed for radiotherapy like gold (CYT-6091 CyImmune),⁸ gadolinium-based (AGuIX, NHTheraguix)⁹ and hafnium oxide-based nanoparticles (NBTXR3, Nanobiotix)¹⁰ have reached the clinical trial phase. Besides, precious-metal-based radio-enhancers, rare-earth element-based, semiconductor, and even non-metallic NPs have been explored over the past years.^{11–15}

However, most synthesis methods require multiple steps, organic solvents, reducing agents or surfactants for controlling the nanoparticles' growth. Subsequent functionalization and additional steps of purification are often required to make them water-soluble and biocompatible.¹⁶ Such complications could be avoided by using a radiolytic method for synthesis and as Leza *et al.* showed, monodisperse Pt NPs were prepared in a one-pot manner using γ -radiation. These particles efficiently enhance the effect of both proton and medical carbon beams on cancer cells.^{17,18} However, the scarce availability of ionizing sources (cobalt-60 radiation, accelerated electrons) to perform the synthesis of these nanoparticles reduces their development. It is therefore important to propose green, one-pot synthetic procedures for the generation of novel radio-enhancing agents.

With this aim in mind, new microporous coordination nanoparticles related to Prussian Blue (PB) and polycyanometallate networks have been explored for improving radiation therapy. PB is a famous pigment and the oldest microporous coordination polymer. It is an FDA-approved compound known as Radiogardase[®] and is used for radioisotope decontamination.¹⁹ Nanoparticles of PB and related polycyanometallate coordination networks with different compositions have been studied for their magnetic and optical properties, applications in catalysis, batteries as well as electrochromic devices.^{20,21} Besides, many new and exciting biomedical applications of PB-based nanostructures have been discovered and their applicability in photo-thermal therapy (PTT), chemotherapeutic drug delivery and multimodal imaging (MRI, PET, PAI) has been demonstrated over the past decade.²² The synthesis of such coordination NPs using a fast and green surfactant-free, water-based method while maintaining a sub-10 nm size has been reported.^{23–26} These nanoparticles gather more advantages: (i) a high proportion of metal atoms are at the surface (50% for 4 nm NPs) of the particle due to its porous nature; (ii) the combination of different metals in precise proportions is possible; (iii) their post-coating by polymers/molecules without affecting the core size and shape is straightforward and allows evaluation of the coating's impact; (iv) the presence of zeolitic water in the PB FCC structure may participate in radioenhancement.

Indeed, it was recently demonstrated that the microporosity of a nanostructure could amplify the production of ROS and facilitate their diffusion after irradiation. Li *et al.* showed for the first time that the porous structure of 200 nm MIL-100 iron (Fe) nanoMOFs not only serves as cargo to release drug molecules but also participates as efficient radiation enhancers due to the presence of well-dispersed Fe centres.²⁷ Unlike nanoMOFs, PB and related polycyanometallate nanoparticles are stable even in diluted conditions and do not degrade. It was hypothesised that, since such polycyanometallate-based NPs are also intrinsically

porous, irradiation in the presence of water could increase the production of reactive radicals. In 2020, Ren *et al.* reported 200 nm hollow mesoporous PB NPs doped with radio-sensitizing bismuth nanodots for achieving combined photo-thermal and radiation therapy.²⁸ Still, the application of ultra-small polycyanometallate coordination compounds for radiation therapy remains a widely unexplored field. Therefore, a new family of radioenhancers made up of porous Pt-containing coordination networks is proposed in this work. Two novel Pt-based nanostructures of $\text{Pt}[\text{Fe}(\text{CN})_6]$ and $\text{Pt}[\text{Pt}(\text{CN})_4]$ are reported in this study. The use of DNA plasmid as a model system to understand the molecular scale mechanisms occurring in the presence of our NPs and radiation is also discussed. The effect of radiation beams on HeLa cells in the presence of these coordination nanosystems is examined.

Experimental section

Materials

Potassium ferrocyanide ($\text{K}_4[\text{Fe}(\text{CN})_6] \cdot 3\text{H}_2\text{O}$), potassium tetrachloroplatinate ($\text{K}_2[\text{PtCl}_4]$), potassium tetracyanoplatinate ($\text{K}_2[\text{Pt}(\text{CN})_4] \cdot 3\text{H}_2\text{O}$), and dextran were purchased from Aldrich. Polyvinylpyrrolidone (PVP) (Thermofischer, average MW 3500), Agarose D5 (Type D-5-DNA Grade from EUROMEDEX), Tris-Acetate-EDTA (TAE, 50x), Tris EDTA (TE)(1x), DNA (pBR322, $0.5 \mu\text{g} \mu\text{L}^{-1}$, from molecular biology), 6xDNA loading dye (#R0611, molecular biology), Ethidium Bromide (EB, ref: EU0070, 10 mg mL^{-1} , molecular biology Grade, from EUROMEDEX).

Preparation of nanoparticles

The conditions for the most optimized sample are reported. For obtaining PtFe NPs, $\text{K}_4[\text{Fe}(\text{CN})_6] \cdot 3\text{H}_2\text{O}$ (10 mM) and $\text{K}_2[\text{PtCl}_4]$ (10 mM) solutions were prepared in distilled water and heated to reach the temperature of 55°C . $\text{K}_2[\text{PtCl}_4]$ solution was added in one go into the $\text{K}_4[\text{Fe}(\text{CN})_6] \cdot 3\text{H}_2\text{O}$ solution under vigorous stirring. The mixture turned yellow in colour and the reaction was run for 1 h while maintaining the temperature. The solution was cooled down to room temperature and turned dark green in colour.

In the case of PtPt NPs, the precursor solutions $\text{K}_2[\text{Pt}(\text{CN})_4] \cdot 3\text{H}_2\text{O}$ (10 mM) and $\text{K}_2[\text{PtCl}_4]$ (10 mM) were prepared in water, and heated until the activation temperature of 85°C was reached. $\text{K}_2[\text{PtCl}_4]$ was quickly added to the metal cyanide solution under constant stirring. The initial colour of the solution mixture was light brown, but as the reaction progressed (1 h, 85°C) it became a colourless solution. The reaction was stopped after 1 h and the solution was brought to room temperature.

Polymer coating

PVP solution (150 mM) was prepared in water and added to preformed NP solution under constant stirring, maintaining a ratio of 30 (PVP monomer to metal). After 30 minutes, the solution was ultra-filtered and washed twice with distilled water to remove excess reactants. This solution was utilised for



characterization and biological tests. A similar process was followed for coating the NPs with dextran (125 mM).

Powders of NPs were obtained by the addition of acetone (1 : 1 with respect to the colloidal solution of PtFe and acetone/methanol for PtPt), followed by centrifugation at 2 °C until a pellet was formed. They were dried under a vacuum for several hours.

Physicochemical characterization

The hydrodynamic diameter and zeta potential of each prepared sample were determined using Zetasizer NanoZS (Malvern Instruments, UK) equipped with backscattering mode. Multiple batches of the sample were analyzed with standard disposable polystyrene and DTS 1070 cuvettes, and the mean values are reported with corresponding standard deviation. A transmission electron microscope (TEM JEOL 1400, Japan) operating at an accelerating voltage of 120 kV, was used to observe the size and dispersity of the sample. Formvar-coated copper grids were glow-discharged before placing a few drops of PtFe and PtPt NP solution. The characteristic chemical bonds making up the structure of the nanoparticles were verified using an FT-IR spectrophotometer (PerkinElmer Spectrum 100) by preparing KBr pellets. UV-Visible absorption spectra (Cary Win UV), energy dispersive spectra (EDS SAMx) and X-ray photoelectron spectra (ThermoFisher Scientific K-Alpha) were also used for the characterization of the NPs.

Irradiation studies

Cobalt-60 gamma source (1.25 MeV) at the Institute of Physical Chemistry (ICP), University Paris-Saclay was used as the radiation source for the experiments. PtFe and PtPt NP solutions synthesised with PVP and dextran coating along with their precursors: $K_4[Fe(CN)_6]$, $K_4[Fe(CN)_6] + PVP$, $K_4[Fe(CN)_6] + dextran$, $K_2[Pt(CN)_4] \cdot 3H_2O$ and $K_2[Pt(CN)_4] \cdot 3H_2O + PVP$ were analysed before and after irradiation to evaluate changes occurring in presence of high energy beams. Each sample was degassed with N_2O and irradiated for an hour at a 4 kGy h^{-1} dose rate.

Radio-sensitizing effect on DNA: sample preparation and analysis

The plasmid pBR322 (Fisher Scientific in 10 mM Tris-HCl, 1 mM EDTA) was used as a probe to represent biomolecules, in order to understand the radio-enhancing effect of prepared nanoparticles. It consists of circular double-stranded DNA of 4361 base pairs (2.83×10^6 Da) with 95% in native supercoiled (S) conformation and approximately 5% in the relaxed (R) conformation. R arises as a result of single-strand breaks (SSB) in DNA while double-strand breaks (DSB) are caused by two breaks in two strands separated by less than 10 base pairs. DSB leads to linear (L) conformation in the plasmid and this form is absent in the native product.

Each sample was prepared by using 10 μ g of DNA (10 μ L) in 123 μ L Tris-EDTA buffer solution. The plasmid was incubated with each nanoparticle solution (24 μ L) for one hour to ensure binding. The stock solution was diluted to attain a total metal (Fe + Pt/Pt) concentration of 5.3×10^{-6} mol L^{-1} and the final volume was adjusted to 180 μ L using Milli-Q water (18.2 M Ω cm at 25 °C). A control sample was prepared simultaneously containing the plasmid with 24 μ L of water to present the

effect of radiation in the absence of radio-enhancers. Each sample was split into 6 aliquots (18 μ L each) and exposed to γ -radiation with the applied dose ranging between 0–158 Gy.

The damaging effect of irradiation was quantified by analysis of linear, relaxed and supercoiled conformation in the sample using agarose gel electrophoresis. 14 well (1% agarose) gels were prepared in Tris-Acetate-EDTA (TAE) buffer and 9 μ L of each irradiated plasmid solution was loaded in the wells together with a blue dye. Due to the difference in volume, the three forms migrated different distances by electrophoresis (80 V, 3 h, 4 °C). The gel was stained using ethidium bromide (EB) solution, washed twice, studied under a UV transilluminator ($\lambda = 302$ nm) and recorded by a CCD camera. The images were examined to calculate amounts of L, S and R conformations present in each irradiated sample. Since S binds 1.47 times less to EB than R and L, normalization was done and respective fractions of R (R'), S (S') and L (L') were calculated.

$$\text{Total} = 1.47 \times S + R + L$$

$$R' = R/\text{total}$$

$$S' = 1.47 \times S/\text{total}$$

$$L' = L/\text{total}$$

The yield of nanosized damages (SSB and DSB) per plasmid was determined using the established formulae based on Poisson law statistics.²⁹

$$\text{DSB per plasmid} = L'/(1 - L') \quad (1)$$

Cell viability studies

HeLa and primary dermal fibroblast cells purchased commercially from the American Type Culture Collection (CCL-2TM, LGC Standards S.a.r.l. – France Office), were cultivated in Dulbecco's Modified Eagle Medium (DMEM) (Life Technologies) enriched with 4.5 g L^{-1} glucose and supplemented with 10% heat-inactivated Fetal Bovine Serum (FBS), 1% antibiotics (100 U mL^{-1} penicillin and 100 μ g mL^{-1} streptomycin) and 1% non-essential amino acids (all supplements from PAA Laboratories) and cultured at 37 °C in 5% CO_2 atmosphere.

The toxicity of PtFe and PtPt nanoparticles was evaluated in both systems: healthy primary Fibroblast cells and cervical cancer-derived HeLa cells, using a colony formation assay. The cells were incubated with nanoparticle solutions containing total metal concentrations in the range of 0.1 – 1.0×10^{-3} mol L^{-1} for 6 hours. The colonies formed were fixed and stained using 0.5% methylene blue 50% (v/v) methanol solution and counted manually. The control sample containing cells incubated with the same amount of water was used to determine the toxicity of NPs at each concentration. Each data point was triplicated to incorporate a margin of experimental error.


Uptake quantification

HeLa cells (2×10^5) were incubated with PtFe and PtPt nanoparticles for 6 h at a total metal concentration of 2.5×10^{-4} mol L^{-1} .



TEM micrographs reveal homogenous PtFe and PtPt nanoparticles. The size distribution histograms (Fig. 1) calculated by averaging the sizes of 200 NPs reveal that PtFe particles have a core average diameter of 5.2 ± 1.0 nm and PtPt is much smaller at 1.2 ± 0.4 nm. Due to the intense absorption of the green-coloured PtFe colloidal solution in the laser absorption region, the hydrodynamic diameter obtained was not reliable. DLS measurements indicated that the hydrodynamic diameter of synthesized PtPt NPs was 9.9 ± 3.9 nm which appeared to increase by ~ 3 nm in three days. However, the addition of PVP after the synthesis, stops the growth and the sub-10 nm size is maintained (ESI,† Fig. S1). The zeta potential of PVP-coated PtFe and PtPt in water was around -23 ± 5 mV and -27 ± 6 mV respectively (ESI,† Fig. S2). The presence of polycyanometallate complex at the surface of the NPs explains the negative charge and their long-term stability in the colloidal solution. The strong electrostatic repulsions prevent aggregation of the particles and

The synthesis of (Pt[Fe(CN)₆] and Pt[Pt(CN)₄]) self-standing nanoparticles is described in the experimental section.



In order to evaluate the viability of the NPs as radio-enhancing agents, their stability under irradiation was investigated. Both the solutions with NPs and the controls (precursors), in the presence of PVP and dextran polymers were exposed to a gamma-radiation dose of 4 kGy. Upon irradiation, reactive oxygen species (ROS) are generated in solution. The ROS play a crucial role in enhancing the effect of radiation in living cells. They are capable of oxidising Fe^{II} to Fe^{III} and it is substantiated by the appearance of a new band around 425 nm after irradiation of ferrocyanide control solution due to the LMCT band of ferricyanide moiety (ESI,† Fig. S11). However, in the presence of dextran polymer, this evolution was not observed indicating no oxidation had taken place. This evidenced that dextran is capable of scavenging the ROS formed and therefore is not appropriate for coating nanoparticles developed for radiation therapy. Since PtFe and PtPt nanoparticles could easily be post-coated, the synthesis was optimised to

The number of lethal, nanometric DSBs generated as a function of radiation dose (0–160 Gy) is presented in Fig. 4. As expected, the number of nanosize breaks rises with an increase in the dose of radiation applied to the samples. But, in the presence of PtFe and PtPt NPs, the amount of damage is significantly enlarged and the sensitizer enhancing ratio (SER) was used to quantify the efficiency of the NPs. It was calculated using the following equation:

$$\text{SER} = \text{DSB}_{\text{NP}}/\text{DSB}_{\text{control}} \quad (2)$$

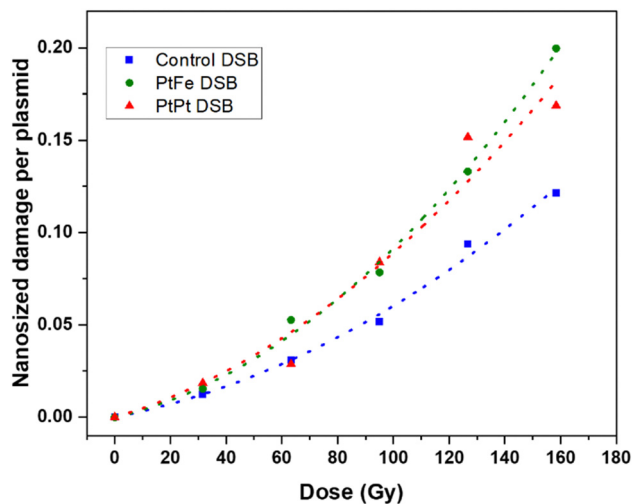


Fig. 4 Nanometric damages induced by gamma radiation on plasmid nanoprobe without NPs (blue) and in the presence of PtFe (green) and PtPt (red) NPs and their respective fitted curves.

where DSB_{NP} and $DSB_{control}$ correspond to the number of nanosize damages per plasmid induced by a certain radiation dose when NPs are present and absent in the solution respectively.

Table 1 Sensitizer enhancer ratio (SER) of PtFe and PtPt NPs at different radiation doses

Dose (Gy)	SER FePt	SER PtPt
30	1.34	1.49
65	1.44	1.48
95	1.51	1.48
125	1.55	1.47
160	1.59	1.46

It is interesting to see that with PtPt, irrespective of the dose supplied, an almost constant enhancement in double-strand breaks in the range of 46–49% was obtained (Table 1). On the other hand, PtFe NPs produce a comparatively smaller effect at low doses (SER 1.34 at 30 Gy) and sequentially intensifies the breaks to the model DNA with increasing dose of radiation (1.59 at 160 Gy). The aim of adding radio-enhancers is to maximize the amount of damage to the cancerous cells, instigate quick apoptosis and minimize the possibility of regeneration while applying a therapeutic dose of radiation. Therefore, even an amplification of 30% in DSBs, in the presence of these porous coordination nanoparticles is very significant. It is important to note that the plasmid used for the experiment is a representative model for different organelles present in the cell and not specifically for DNA in the nucleus. As shown by several groups most NPs do not penetrate or enter the cell nucleus, but complex damage to cytoplasmic organelles also proves detrimental to the cell.^{31,32} Here, we have demonstrated that at a minimal concentration of 5.3×10^{-6} mol L⁻¹, both nanoparticles amplified the effect of radiation, indicating clearly that they could act as radiation-enhancing agents. However, in contrast to cells, once the strand breaks occur after irradiation, no repair mechanisms happen within the plasmid. Therefore as a next step, the effect of NP and radiation on living cells needed to be understood.

Cytotoxicity, uptake and radiation effects of nanoparticles in cells

The primary fibroblasts are used as a model of healthy cells with normal metabolism, while HeLa cells provide an indication of the effect of NPs towards cancerous cells. The effect of a range of different metal concentrations ($[M]$) in PtFe and PtPt NPs was tested in both cell lines with an incubation time of 6 h (Fig. 5). The columns represent average survival fractions with

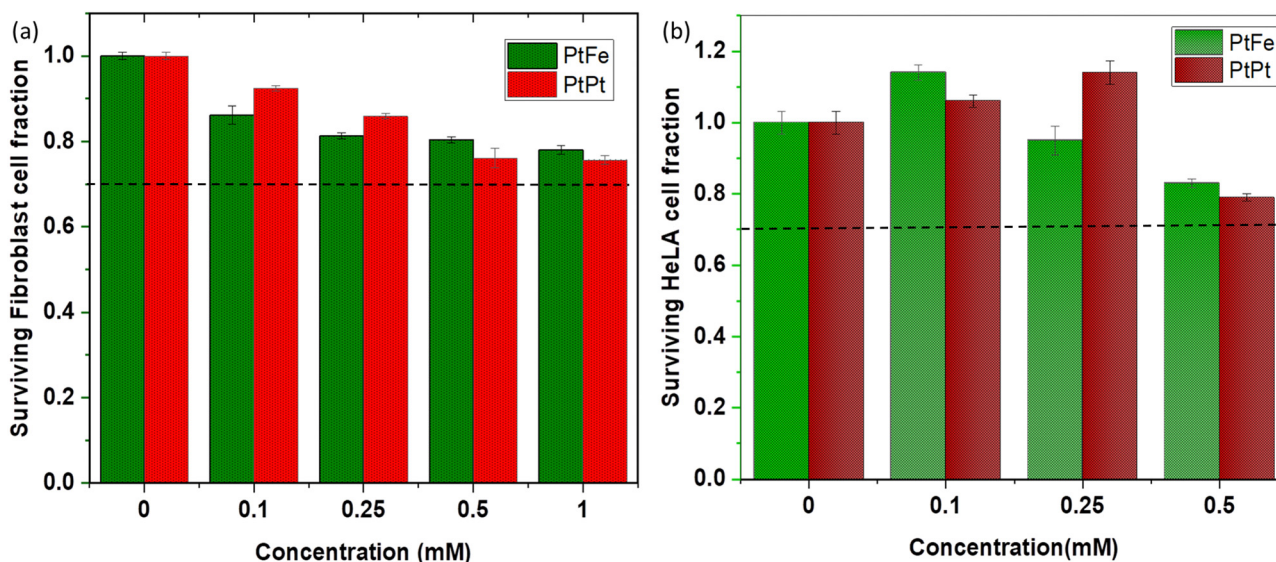


Fig. 5 *In vitro* toxicity results of PtFe and PtPt NPs evaluated by a clonogenic assay using (a) fibroblast cells and (b) HeLa cells after 6 h incubation. The total metal concentration: [Pt + Fe]/[Pt], was considered for the experiment and it lies in the range of $0-1 \times 10^{-3}$ M. The black dotted line corresponds to the safety limit according to ISO-10 933.

respective average deviation values. According to the international standard for biological evaluation of medical devices, a sample is considered non-cytotoxic when even the highest concentration provides 70% cell survival.³³ The fibroblast cell viability is close to 80% at the highest metal concentration ($[M]$) of 1×10^{-3} M for both nanoparticles indicating their safety for medical applications, towards healthy cells. HeLa cells appear more sensitive to the presence of nanoparticles as they reach the same limit at 5.0×10^{-4} M concentration. Therefore, a lower and safer total metal concentration of 2.5×10^{-4} mol L⁻¹ was chosen for further experiments with HeLa cells, as the cancer cell-killing effect rising specifically from radiation enhancement needed to be quantified.

ICP-OES analysis of HeLa (*ca.* 1.3×10^6) cells incubated with PtFe NPs for 6 h showed that a total of 73 ng of Pt was internalized. Therefore, 0.28 fmol of this high-Z element was taken up by one cell. In the case of PtPt NPs, 182 ng of platinum was detected in *ca.* 1.8×10^6 HeLa cells, meaning the amount of Pt internalized was approximately 0.52 fmol per cell. The impact of these particles in cell killing was studied using γ -rays from a Cesium-137 source (0.63 MeV). The cancer cells incubated with NPs were irradiated for different time intervals at a dose rate of 0.75 Gy min⁻¹. The colonies formed at the end of the standard 14 day incubation period helped determine the survival fraction (SF) at each dose.

The colony count data were fitted using a linear-quadratic model (LQM) (SF vs. dose) using eqn (3):

$$SF(D) = e^{-(\alpha D + \beta D^2)} \quad (3)$$

D corresponds to the dose supplied, while the parameters α and β describe the cell's radiosensitivity. α represents the induction of directly lethal damages whereas β term corresponds to additive sub-lethal lesions leading to cell death. The α/β provides the dose (Gy) at which 50% of the damages caused to the cells are due to the directly lethal effect of radiation while the rest are a result of additive damages triggering a lethal consequence.

The percentage of surviving cells sequentially decreased with increasing the radiation dose but as presented in Fig. 6, this decline is significantly amplified in the presence of PtFe and PtPt NPs. This result proves the radioenhancing property of these novel polycyanometallate-based NPs. The effectiveness of NPs as radioenhancers was quantified using Dose Enhancement Factor (DEF) which gives a measure of the efficiency of *in vitro* cell killing at a given dose point (D). It was calculated using the following equation:

$$DEF = SF_{\text{control,fit}}/SF_{\text{NP,fit}} \quad (4)$$

SF_{control} and SF_{cyanosol} correspond to the survival fractions of the dose of radiation. Until a radiation dose of 4.5 Gy, both NPs behave similarly and a DEF of ~ 1.25 was obtained. As the dose supplied to the sample increased, high DEF values up to 1.92 for PtPt and 2.45 for PtFe were observed. This corresponds to a 48% and 59% rise in the cancer cell-killing rate in the presence of 2.5×10^{-4} mol L⁻¹ PtFe and PtPt NPs. As reported in Table 2, the α in all three cases are quite similar, indicating that the number of directly lethal damages produced as an effect of

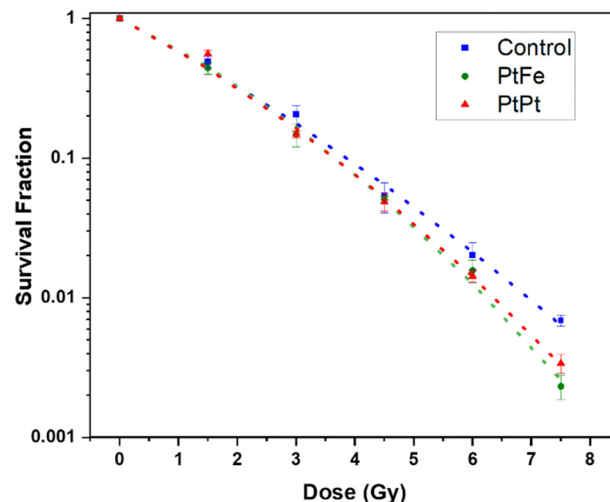


Fig. 6 Survival fraction of HeLa cells after Cs-137 irradiation without NPs (blue), in the presence of 2.5×10^{-4} M PtFe (green) and PtPt (red) NPs fit using LQM (dotted lines) as a function of dose.

Table 2 Values of α and β obtained from the fitting curve for NPs and control experiment in HeLa cells in the presence of radiation

Sample	α (Gy ⁻¹)	β (Gy ⁻²)	α/β (Gy)
Control	0.515 ± 0.050	0.021 ± 0.007	24.30 ± 9.44
PtFe	0.464 ± 0.050	0.044 ± 0.008	10.57 ± 2.21
PtPt	0.500 ± 0.049	0.034 ± 0.007	14.38 ± 3.56

radiation does not change much in the presence of these NPs. However, the β value shifts from 2.1×10^{-2} Gy⁻² in the control (no NPs) experiment to 3.4×10^{-2} Gy⁻² for PtPt. In the case of PtFe NPs, the β is more than double that of the control, at 4.4×10^{-2} Gy⁻². This significant increase in β value indicates that the radioenhancing mechanisms of such polycyanometallate NPs are unique as they first produce a high amount of sub-lethal damages, which then add up and lead to cancer cell death.

Compared to the control, the presence of Pt increases the number of radicals formed in the solution. It is possible that, due to the microporosity of the NP, the generated ROS quickly disperses through the biological system causing a markedly high amount of sub-lethal damages that is transformed into a final lethal effect in the cell. It has to be noted that as seen with plasmid experiments earlier, despite the presence of a lower amount of high-Z element in PtFe NP, they produce similar and sometimes even better amplification of radiation damage when compared to PtPt NPs.

This could be due to two reasons. The γ -radiation interacts with Fe atoms as well and following a combination of various phenomena (activation, de-excitation and emission of electrons) also leads to the production of radicals that help with cell killing.²⁷ Secondly, as compared to the 2D sheets that form PtPt NP, the PtFe nanostructure is a Prussian Blue-like structure full of defects and vacancies that can be occupied by water molecules. Therefore, more reactive radicals are formed within and around PtFe NP and they have higher freedom of mobility to



undergo faster diffusion throughout the cell media. This is a further indication that the microporosity of nanostructures used in radiation therapy heavily affects the final results. It can be concluded from the data that even at low concentrations, both the nanoparticles cause the death of targeted cells and positively improve the lethality of γ -radiation. As the results from the clonogenic assay and plasmid experiments are in agreement, it can be said that the complex damages occurring to the biomolecules after gamma radiation are the root cause of the amplification of cancer cell death.

Conclusions

The present study reported a green, cheap and fast synthetic procedure of two novel Pt-containing polycyanometallate-based nanostructures. A complete characterization revealed that these ultra-small, negatively charged, coordination nanoparticles are stable in water, buffer as well as physiological media like FBS and ALF. These PtFe and PtPt NPs are easily post-coated with polymers depending on the targeted applications and they remained intact upon irradiation, which suggested their applicability as radioenhancers. A marked increase in lethal double-strand breaks on plasmids is observed in the presence of these newly synthesised NPs. Plasmid DNA was chosen as a nanoprobe to quantify complex molecular damage and the efficiency of NPs to amplify this damage when combined with radiation. This complex damage can occur in any biomolecule of the cytoplasm, in the vicinity of the NP. The *in vitro* tests revealed that they were non-toxic to primary fibroblast and HeLa cells in a good range of concentrations. However, irradiation of the cells containing the NPs with an ionizing beam induces strong cytotoxicity, with the amplification factor rising close to 60%. Therefore, our cyanide-bridged PtFe and PtPt NPs may serve as effective agents that amplify the damage to cancer cells at therapeutic doses. Interestingly, the PtFe shows an improved radioenhancing effect compared to its PtPt counterpart and it could be due to its more porous, 3D Prussian Blue-like structure. The role of zeolitic water as well as porosity will be further investigated. We envisage imparting MRI contrast properties by coordination of paramagnetic ions (Mn(II), Fe(III)) at the surface (as shown by some of us on PB) for image-guided treatments.

Author contributions

RG: investigation, conceptualization, methodology, data curation, validation, writing – original draft and editing. LF: methodology, investigation. EP: methodology, *in vitro* experiments, resources, supervision, writing – review and editing. FS and CB: *in vitro* experiments. FB: high-resolution TEM and EDS. DD: XPS measurements. HR and SL: funding acquisition, project administration, resources, writing – review and editing. LC: conceptualization, methodology, funding acquisition, project administration, resources, supervision, writing – draft, review and editing.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

We acknowledge the DIM RESPORE, NanoTherad and INan-oTheRad, Paris Saclay University and CNRS for their financial support. The present work has benefited from Imagerie-Gif core facility supported by l'Agence Nationale de la Recherche (ANR-11-EQPX-0029/Morphoscope, ANR-10-INBS-04/France-BioImaging; ANR-11-IDEX-0003-02/Saclay Plant Sciences).

Notes and references

- 1 H. Sung, J. Ferlay, R. L. Siegel, M. Laversanne, I. Soerjomataram, A. Jemal and F. Bray, *CA Cancer J. Clin.*, 2021, **71**(3), 209–249.
- 2 M. Chalmers, *Phys. World*, 2003, **16**(8), 32.
- 3 C. B. Dracham, A. Shankar and R. Madan, *Radiat Oncol J.*, 2018, **36**(2), 85–94.
- 4 G. E. Adams, *Br. Med. Bull.*, 1973, **29**(1), 48–53.
- 5 K. Kobayashi, N. Usami, E. Porcel, S. Lacombe and C. Le Sech, *Mutat. Res.*, 2010, **704**(1–3), 123–131.
- 6 J. F. Hainfeld, D. N. Slatkin and H. M. Smilowitz, *Phys. Med. Biol.*, 2004, **49**(18), N309–N315.
- 7 A. Z. Wilczewska, K. Niemirowicz, K. H. Markiewicz and H. Car, *Pharmacol Rep.*, 2012, **64**(5), 1020–1037.
- 8 S. K. Libutti, G. F. Paciotti, A. A. Byrnes, H. R. Alexander Jr, W. E. Gannon, M. Walker, G. D. Seidel, N. Yuldasheva and L. Tamarkin, *Clin. Cancer Res.*, 2010, **16**(24), 6139–6149.
- 9 C. Verry, S. Dufort, J. Villa, M. Gavard, C. Iriart, S. Grand, J. Charles, B. Chovelon, J. L. Cracowski, J. L. Quesada, C. Mendoza, L. Sancey, A. Lehmann, F. Jover, J. Y. Giraud, F. Lux, Y. Crémillieux, S. McMahon, P. J. Pauwels, D. Cagney, R. Berbeco, A. Aizer, E. Deutsch, M. Loeffler, G. Le Duc, O. Tillement and J. Balosso, *Radiother. Oncol.*, 2021, **160**, 159–165.
- 10 S. Bonvalot, P. L. Rutkowski, J. Thariat, S. Carrère, A. Ducassou, M. P. Sunyach, P. Agoston, A. Hong, A. Mervoyer, M. Rastrelli, V. Moreno, R. K. Li, B. Tiangco, A. C. Herraiez, A. Gronchi, L. Mangel, T. Sy-Ortin, P. Hohenberger, T. de Baère, A. Le Cesne, S. Helfre, E. Saada-Bouazid, A. Borkowska, R. Anghel, A. Co, M. Gebhart, G. Kantor, A. Montero, H. H. Loong, R. Vergès, L. Lapeire, S. Dema, G. Kacso, L. Austen, L. Moureau-Zabotto, V. Servois, E. Wardelmann, P. Terrier, A. J. Lazar, J. V. M. G. Bovée, C. Le Péchoux and Z. Papai, *Lancet Oncol.*, 2019, **20**(8), 1148–1159.
- 11 R. Crapanzano, V. Secchi and I. Villa, *Appl. Sci.*, 2021, **11**(15), 7073.
- 12 Y. Li, K. H. Yun, H. Lee, S. H. Goh, Y. G. Suh and Y. Choi, *Biomaterials*, 2019, **197**, 12–19.
- 13 A. Mignot, C. Truillet, F. Lux, L. Sancey, C. Louis, F. Denat, F. Boschetti, L. Bocher, A. Gloter, O. Stéphane, R. Antoine, P. Dugourd, D. Luneau, G. Novitchi, L. C. Figueiredo, P. C. de Moraes, L. Bonneviot, B. Albela, F. Ribot, L. Van Lokeren, I. Déchamps-Olivier, F. Chuburu, G. Lemerrier,



- C. Villiers, P. N. Marche, G. Le Duc, S. Roux, O. Tillement and P. Perriat, *Chemistry*, 2013, **19**(19), 6122–6136.
- 14 E. Gharibshahi, E. Saion, A. Ashraf and L. Gharibshahi, *Appl. Radiat. Isot.*, 2017, **130**, 211–217.
 - 15 Y. Zhang, X. Han, Y. Liu, S. Wang, X. Han and C. Cheng, *Mater. Adv.*, 2022, **3**, 3709–3725.
 - 16 Z. Bao, M. He, H. Quan, D. Jiang, Y. Zheng, W. Qin, Y. Zhou, F. Ren, M. Guo and C. Jiang, *RSC Adv.*, 2016, **6**, 35124–35134.
 - 17 X. Yang, D. Salado-Leza, E. Porcel, C. R. González-Vargas, F. Savina, D. Dragoe, H. Remita and S. Lacombe, *Int. J. Mol. Sci.*, 2020, **21**(5), 1619.
 - 18 D. Salado-Leza, E. Porcel, X. Yang, L. Štefančíková, M. Bolsa-Ferruz, F. Savina, D. Dragoe, J. L. Guerquin-Kern, T. D. Wu, R. Hirayama, H. Remita and S. Lacombe, *Nanotechnol., Sci. Appl.*, 2020, **13**, 61–76.
 - 19 Center for Drug Evaluation and Research. Approval Letter for Radiogardase (insoluble Prussian Blue), 2003, 21–626.
 - 20 Z. Y. Liu, G. T. Fu, L. Zhang, X. Y. Yang, Z. Q. Liu, D. M. Sun, L. Xu and Y. W. Tang, *Sci. Rep.*, 2016, **6**, 32402.
 - 21 S. Y. Lin, Y. Q. Yao, L. Zhang, J. J. Feng and A. J. Wang, *Mater. Today Energy*, 2021, **20**, 100701.
 - 22 Z. Qin, Y. Li and N. Gu, *Adv. Healthcare Mater.*, 2018, **7**(20), 1800347.
 - 23 G. Paul, Y. Prado, N. Dia, E. Rivière, S. Laurent, M. Roch, L. V. Elst, R. N. Muller, L. Sancey, P. Perriat P, O. Tillement, T. Mallah and L. Catala, *Chem. Commun.*, 2014, **50**(51), 6740–6743.
 - 24 L. Catala and T. Mallah, *Coord. Chem. Rev.*, 2017, **346**, 32–61.
 - 25 G. Fornasieri, M. Aouadi, E. Delahaye, P. Beaunier, D. Durand, E. Rivière, P.-A. Albouy, F. Brisset and A. Bleuzen, *Materials*, 2012, **5**, 385–403.
 - 26 L. Fétiveau, G. Paul, A. Nicolas-Boluda, J. Volatron, R. George, S. Laurent, R. Muller, L. Sancey, P. Mejanelle, A. Gloter, F. Gazeau and L. Catala, *Chem. Comm.*, 2019, **55**, 14844–14847.
 - 27 X. Li, E. Porcel, M. Menendez-Miranda, J. Qiu, X. Yang, C. Serre, A. Pastor, D. Desmaële, S. Lacombe and R. Gref, *ChemMedChem*, 2020, **15**(3), 274–283.
 - 28 C. Ren, Y. Cheng, W. Li, P. Liu, L. Yang, Q. Lu, M. Xu, F. Tan, J. Li and N. Li, *Biomater. Sci.*, 2020, **8**, 1981–1995.
 - 29 M. Spothem-Maurizot, M. Charlier and R. Sabattier, *Int. J. Radiat. Biol.*, 1990, **57**(2), 301–313.
 - 30 C. M. Burgess, N. Yao and A. B. Bocarsly, *J. Mater. Chem.*, 2009, **19**, 8846–8855.
 - 31 L. Štefančíková, S. Lacombe, D. Salado, E. Porcel, E. Pagáčová, O. Tillement, F. Lux, D. Depeš and M. Falk, *J. Nanobiotechnol.*, 2016, **14**, 63.
 - 32 E. Pagáčová, L. Štefančíková, F. Schmidt-Kaler, G. Hildenbrand, T. Vičar, D. Depeš, J.-H. Lee, F. Bestvater, S. Lacombe, E. Porcel, S. Roux, F. Wenz, O. Kopečná, I. Falková, M. Hausmann and M. Falk, *Int. J. Mol. Sci.*, 2019, **20**(3), 588.
 - 33 Biological evaluation of medical devices-ISO-10993-5-2009.

