



Cite this: *EES Catal.*, 2023,
1, 934

Advances and challenges in scalable carbon dioxide electrolysis

Ji Wei Sun,^a Huai Qin Fu,^b Peng Fei Liu,^{id a} Aiping Chen,^a Porun Liu,^{id b}
Hua Gui Yang^{id *a} and Huijun Zhao^{id *b}

The electrochemical CO₂ reduction reaction (CO₂RR) is an effective way of utilizing carbon and can be economically profitable by converting captured CO₂ into valuable products. In the last decade, significant research efforts have been dedicated to CO₂RR technology and significant breakthroughs in materials design, mechanistic understanding and device applications have been made. Although laboratory-level CO₂RR performance has shown its potential prospects, scalable CO₂ electrolysis is still far from market ready. The keys for industrialization are to cut running costs, increase the CO₂ conversion rate and obtain high industrial value reaction products. Here, we start by systematically introducing the current research progress made in CO₂ electrolyzer development in terms of the device structure and reaction environments. Then, the current problems in the scale-up process and corresponding solutions are summarized. Some improvement strategies and development directions are proposed, for example, cathodic salting, the use of ion exchange membranes and flow channel design. This perspective illustrates the importance of practical electrolyzers, which will guide the design of scalable CO₂ electrolyzers and accelerate the commercialization process of CO₂RR technology.

Received 7th July 2023,
Accepted 30th August 2023

DOI: 10.1039/d3ey00159h

rsc.li/eescatalysis

Broader context

The carbon dioxide reduction reaction (CO₂RR) is an important form of carbon utilization that has received widespread attention because of its simplicity of operation, product selectivity, and use of renewable electricity. Currently, significant breakthroughs have been achieved in materials design, mechanistic understanding and device applications. However, little attention has been paid to scalable electrocatalytic CO₂ reduction. As an important bridge for the transition from laboratory level to industrialization, scalable CO₂ electrolysis is crucial in improving CO₂ conversion ability and realizing long-term, large-scale generation of chemicals and fuels. Therefore, in this perspective, we introduce scalable electrolyzer design in terms of electrolyzer types and reaction environment factors, and highlight problems and corresponding solutions in the scale-up of these cells. Finally, strategies are proposed for the development of scalable electrolyzers in terms of cathodic salting, the use of ion exchange membranes and flow channel design.

^a Key Laboratory for Ultrafine Materials of Ministry of Education, Shanghai Engineering Research Center of Hierarchical Nanomaterials, School of Materials Science and Engineering, East China University of Science and Technology, Shanghai 200237, China. E-mail: hgyang@ecust.edu.cn

^b Centre for Catalysis and Clean Energy, Gold Coast Campus, Griffith University, Gold Coast, QLD 4222, Australia. E-mail: h.zhao@griffith.edu.au



Ji Wei Sun

Ji Wei Sun received his BSc degree from the Shandong University of Science and Technology in 2019. He is currently a PhD candidate under the supervision of Prof. Hua Gui Yang in the school of materials science and engineering at the East China University of Science and Technology. His current research interests are focused on the design of membrane electrode assemblies and the fabrication of advanced catalysts for carbon dioxide electrolysis.



Hua Gui Yang

Hua Gui Yang received his PhD from the National University of Singapore in 2005. He joined the University of Queensland in 2007 as a Postdoctoral Research Fellow. After finishing his postdoctoral training, he came back to China and took a professorship at the East China University of Science and Technology at the end of 2008. His main research interests are focused on the rational design and fabrication of functional materials for solar fuels.



1. Introduction

The massive burning of fossil fuels has resulted in a dramatic increase in global atmospheric CO₂ concentration, increasing from 317 ppm in 1960 to 420 ppm in 2023. This change has led to a series of problems, such as global climate change, ocean acidification, deterioration of human health and an energy crisis.^{1–3} Therefore, reducing atmospheric CO₂ concentration has become one of the most urgent problems for humankind. Carbon capture, utilization and storage (CCUS) is considered to be a key technological alternative for global decarbonization.^{4–7} Studies from some researchers have suggested that CCUS may reduce carbon emissions by as much as 32% by 2050.⁸ However, the development of CCUS is blocked, mainly due to the cost of carbon capture and storage (CCS) processes. These processes involve the capture of CO₂ gas from industries such as thermal power, cement and steel, followed by transportation of supercritical CO₂ to selected underground strata through pipelines or storage tanks for permanent sequestration.^{9–11} The capital investment required for a typical centralized CCS facility is \$1 billion, but sequestering CO₂ in the ground usually needs additional investment in transportation pipelines and infrastructure.^{12,13} On the contrary, carbon utilization, the key process of CCUS, can be economically profitable by converting captured CO₂ into economically valuable raw materials.^{14–16}

An efficient way to utilize carbon, electrochemical CO₂ reduction reactions (CO₂RR) have received much attention in the past decade (Fig. 1). The main reasons for this can be outlined as follows:^{17,18} (1) renewable electricity can be used as the source of energy for the reaction; (2) the reaction can be performed at room temperature and atmospheric pressure; (3) the reduction products are economically valuable and their selectivity depends on the catalyst design; and (4) the reaction system is simple and shows prospects for use in large-scale applications. The CO₂RR involves complex mechanisms due to multiple proton-coupled electron transfer processes, high

overpotentials and low selectivity for a single product. Nevertheless, great breakthroughs have been achieved on fundamental catalyst design and mechanism understanding, which have significantly improved the reaction rate, product selectivity, carbon utilization efficiency and stability.^{19,20} For example, Qiao *et al.*²¹ achieved the conversion of CO₂ to multiple carbon products at ampere-level current densities on copper-based catalysts modulated by a series of heteroatoms (*e.g.* N, P, S, O). At a current density (*J*) of -1.1 A cm^{-2} , the Faraday efficiency (FE) for C₂₊ products reached 73.7%, indicating high product selectivity can be achieved at high current densities. Gewirth *et al.*²² prepared Cu-polyamine hybrid catalysts *via* a co-plating method to drive CO₂-to-C₂H₄ conversion. The FE of C₂H₄ was $87\% \pm 3\%$ at $-0.47 \text{ V (vs. RHE)}$, the highest value reported so far, and the full cell energy efficiency reached $50\% \pm 2\%$. Sargent *et al.*²³ achieved a single CO₂ utilization of up to 77% in a strongly acidic electrolyte by modifying ionic polymers on the surface of copper electrodes, the highest conversion available for generating multi-carbon products. Masel *et al.*²⁴ achieved 1000 h of operation at a *J* of 200 mA cm^{-2} in a membrane electrode (one of the best CO₂RR stabilities) by functionalizing an anion exchange membrane with imidazole-based ionic liquids, using Ag as a catalyst.

The above-mentioned reports indicate that catalyst-related laboratory-scale CO₂ electrocatalytic reduction is becoming increasingly mature. However, the current electrolyzer devices that can be initially scaled up and have prospects for industrial application suffer from a number of problems, such as low current, low energy efficiency, and poor stability. These devices are far from the standard required at the industrial level and are still in the initial stage. In this regard, this perspective illustrates the importance of scalable electrolyzers through techno-economic accounting (TEA), and introduces some existing electrolyzers that are expected to be industrialized. These electrolyzers are classified by electrolyzer type and reaction environment factors (Fig. 1), for example, large-area electrolyzers, electrostacks, and high-pressure heated electrolyzers, *etc.* The problems in the scale-up process and some corresponding solutions are also summarized. Finally, strategies in terms of device structure, flow channel design and ion exchange membranes for the development of scalable electrolyzers are proposed.

2. Types and importance of scalable CO₂ electrolyzers

2.1 CO₂ electrolyzers

A CO₂ electrolyzer is a device that converts CO₂ into specific products driven by electricity. It is mainly composed of an electrolyzer, a catalytic electrode, ion exchange membrane and electrolyte. CO₂ is reduced to high value-added chemical raw materials at the cathode, and oxygen is generated at the anode *via* the oxygen evolution reaction (OER).²⁵ At present, there are three types of electrochemical cells for the CO₂RR: the H-type cell, flow cell and membrane electrode assembly (MEA). Due to



Huijun Zhao

Prof. Huijun Zhao is the director of the Centre for Catalysis and Clean Energy, Griffith University, Fellow of the Australian Academy of Science (FAA), Fellow of the Australian Academy of Technological Sciences (FTSE), Fellow of Royal Society of Chemistry (FRSC), Fellow of the Royal Australian Chemical Institute (FRACI), and the winner of the 2016 R. H. Stokes Medal. He has extensive and valuable experience in diversified research

fields including applied electrochemistry, analytical chemistry, photocatalysis, surface chemistry, energy storage materials and nanomaterials.



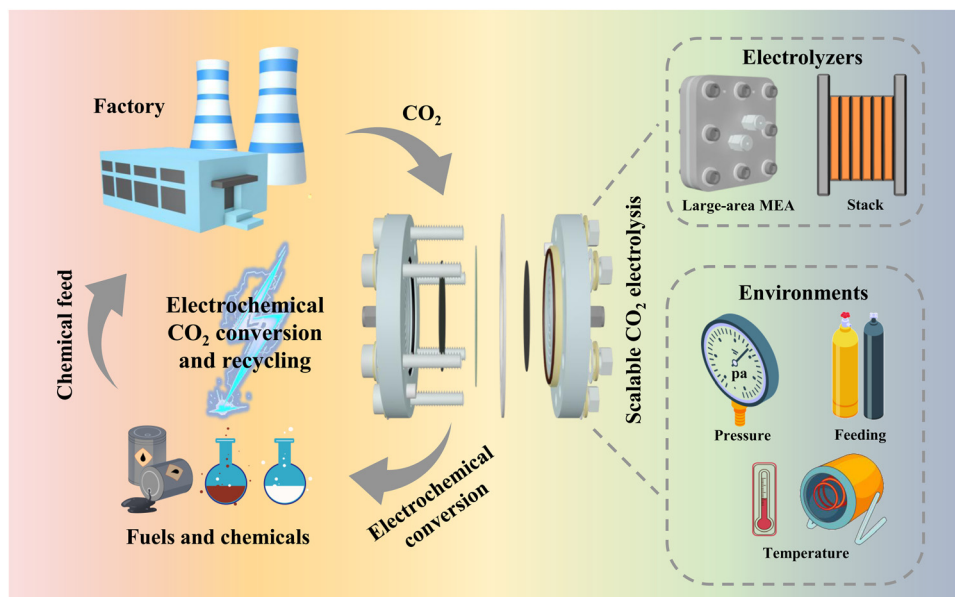


Fig. 1 Schematic diagram of the use of the CO₂RR for carbon recycling and the design of electrolyzer strategies and environments to realize scalable CO₂ electrolysis.

the differences in the electrolyzer structure and the CO₂ mass transfer mode, the electrolyzers have a great impact on the current density, selectivity and stability of the catalytic reaction.²⁶ Therefore, an in-depth exploration of the structural characteristics of different CO₂ electrolyzers is of paramount significance to the development of scalable CO₂ electrolyzers.

The H-type cell is divided into cathode and anode reaction chambers by an ion exchange membrane. In the CO₂RR process, CO₂ is introduced into the electrolyte of the cathode chamber containing the working electrode. When the CO₂ concentration in the electrolyte reaches saturation, it is transferred to the catalyst surface by diffusion, and thus the reduction reaction occurs.^{27–29} The H-type cell has become a basic tool for evaluating the performance of CO₂RR electrocatalytic materials at laboratory scale due to its simple structure and easy assembly. However, H-type cells have many serious problems in scalable applications. For example, the CO₂ has to be dissolved in the electrolyte before being transferred to the catalyst surface, but CO₂ has a low solubility (~ 33 mM at 25 °C) and diffusion rate (diffusion coefficient of $0.00194 \text{ mm}^2 \text{ s}^{-1}$ at 25 °C) in water, leading to difficulties in CO₂ transfer to the catalyst surface. In particular, a significant decrease in selectivity occurs at high current densities because the supply of CO₂ does not cover demand.^{30–32} In addition, the catalyst is easily dislodged when immersed in the electrolyte, and stability tests cannot be run for a long time, often only a dozen hours.^{33,34} Therefore, H-type cells are only suitable for laboratory-scale research and cannot be scaled up for industrial applications.

Aimed at solving the problem of difficult CO₂ mass transfer in the H-type cell, a flow cell with a three-phase interface has been developed to greatly improve CO₂ mass transfer efficiency. Unlike the H-type cell, in the cathode chamber of the flow cell, a hydrophobic gas diffusion layer (GDL) separates the electrolyte

and CO₂ gas, forming a gas–liquid–solid mass transfer interface, allowing CO₂ gas to pass through the GDL and reach the catalyst surface directly, thus eliminating the CO₂ mass transport limitation.^{35–37} Therefore, this design of flow cell greatly improves the reaction rate of the CO₂RR, and can reach several hundred milliamperes per square centimeter for industrial applications. However, the flow cell still has some significant problems in the scale-up process. On the one hand, the electrolyte layer between the cathode and the ion exchange membrane increases the ohmic resistance and reduces the energy efficiency of the electrolyzer, making it impossible to use a mild neutral electrolyte. If a strong alkaline electrolyte is used, it will aggravate the corrosion of the device, CO₂ loss and salt precipitation; on the other hand, since the layer of catalyst coated on the GDL is in direct contact with the electrolyte, the GDL will be broken down over long operating time, flooding the electrodes with electrolyte and leading to a serious decrease in selectivity. Therefore, based on the above problems, it is difficult for the flow cell to be scaled up at present.

To solve the problems in a flow cell, new scalable electrolyzers must be developed to meet industrialization requirements. In recent years, MEA-type electrolyzers have been applied to CO₂RR research inspired by fuel cells and water electrolyzers. Unlike in a flow cell, there is no electrolyte layer between the GDL and ion exchange membrane in MEA, instead they are directly pressed together, almost eliminating the gap between the cathode catalyst, ion exchange membrane and anode catalyst.^{38–40} This zero-gap structure not only makes the ohmic impedance of the electrolyzer lower, but also effectively avoids the problem of GDL flooding. This structure allows for more stable and efficient CO₂ conversion in the MEA device.

According to recent reports on the catalytic performance of the three CO₂RR electrolyzers,^{41–43} MEA electrolyzers are



significantly better than H-type cells and flow cells in terms of selectivity, current density and stability. In summary, MEA is currently the most promising CO₂RR device for achieving industrial scale-up.

2.2 TEA analysis of scalable electrolyzers

Preliminary techno-economic studies have shown that CO₂ electrolysis is economically viable, but the cost of electricity and the efficiency of the electrolyzer are the main economic barriers to industrial development. Fortunately, recent studies on renewable power generation have shown that the cost of photovoltaic power is on a significant downward trend, with prices as low as \$0.03 per kW h in the near future.⁴⁴ Therefore, the further development of electrolyzers is particularly important at present.

Currently, MEA-based large-area electrolyzers and multi-reactor stacks have been used for scalable CO₂RR electrolyzers. In a report by Jiao *et al.*,¹² a TEA analysis of CO₂ industrial electrolysis was carried out using an electrostack and single chamber electrolyzer (SC electrolyzer), respectively. Only the reduction by the electrolyzer itself and maintenance cost related to the use of the stack is considered here, and the value-added cost outside the device is not taken into account (the difference between the two would be further increased if the difference in value-added cost is considered). The cost of CO₂-to-CO electrolysis was calculated to be \$0.37 per kg (Fig. 2a) instead of \$0.41 per kg when a three-chamber stack is used instead of a single-chamber MEA. If this cost is used to simulate the profitability of a plant with a CO production capacity of 50 000 kg per day over a 10 year period, the plant with a single-chamber MEA would still lose about \$3 000 000 after 10 years of operation (Fig. 2b), while the plant with a three-chamber stack would make a profit of about \$5 600 000 (Fig. 2c). Based on the above analysis, research on scalable electrolyzers is crucial to reduce the cost of industrial application and to advance the industrialization of CO₂ electrolysis.

3. Current applications and challenges of scalable CO₂ electrolysis

Initial progress on scalable electrolyzers has been made at the laboratory level. We introduce here the scalable CO₂ electrolyzers reported in recent years, summarize the advantages and problems of different electrolyzers, and finally provide an outlook on the future development of scalable electrolyzers.

3.1 Large-area CO₂RR electrolyzer

In order to undertake CO₂ electrolysis at industrial reaction rates and increase the CO₂ conversion rate, a series of attempts have been made to achieve the industrial feasibility of large-area CO₂ electrolyzers based on MEA electrolyzers. A large-area CO₂ electrolyzer represents a parallel scaling up (enlargement of device volume and reaction area without structural change) of the reaction area compared to the laboratory-grade MEA, so

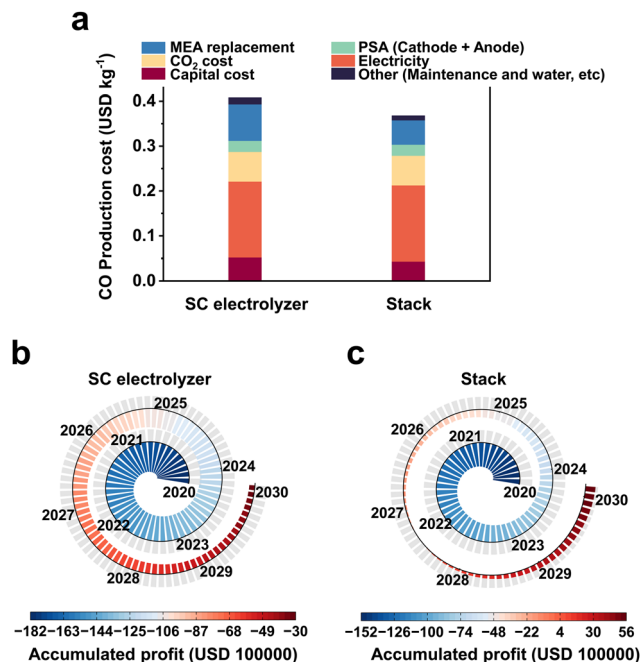


Fig. 2 TEA of the production of CO using an SC electrolyzer and stack. (a) Cost of CO production using SC electrolyzer and stack. Simulation of the profitability of a plant with a CO production capacity of 50 000 kg day⁻¹ over a 10 year period using (b) an SC electrolyzer or (c) a stack. The TEA results indicate that the use of more scalable electrolyzers will reduce the cost of CO₂ electrolysis.

it is relatively simple and easy to operate in terms of assembly and operation. Our group⁴⁵ prepared a Co single-atom catalyst using a microwave method and performed CO₂ electrolysis utilizing an electrolyzer with an effective reaction area of 100 cm² (Fig. 3a–c). The selectivities of CO in this electrolyzer are over 85% in the current range of 1–10 A (Fig. 3d). In particular, at a current of 10 A and a CO₂ flow rate of 150 mL min⁻¹, the single-pass conversion efficiency (SPC) of CO₂ was still as high as 40.4% (Fig. 3e), and it took only 6.2 h to generate 1 mole of CO (Fig. 3f). Wang *et al.*⁴⁶ compared the CO₂ reduction performance of electrolyzers with an active area of 4 cm² and 100 cm² under a neutral electrolyte. As shown in Fig. 3g and h, the current density of the small-area device is significantly higher than that of the large-area device at the same potential (*e.g.*, at a full-cell voltage of 2.7 V, the current density of the 4 cm² electrolyzer is about 130 mA cm⁻², while that of the 100 cm² electrolyzer is about 60 mA cm⁻²). This indicates that the impedance of the device itself or the electrochemical impedance of the electrolysis process increases accordingly when the electrolyzer is enlarged, leading to a drop in the current density and a decrease in the energy efficiency (EE) of the reaction. Fortunately, the decrease in current density does not affect the product selectivity, and the Faraday efficiency of CO remains close to 100% (Fig. 3i). Similar results were found in the research by Janáky *et al.*⁴⁷ An 8 cm² electrolyzer has a CO current density close to 600 mA cm⁻² at a full cell potential of 3.2 V, while the CO current density of a 100 cm² electrolyzer is only ~350 mA cm⁻² (Fig. 3j–l).



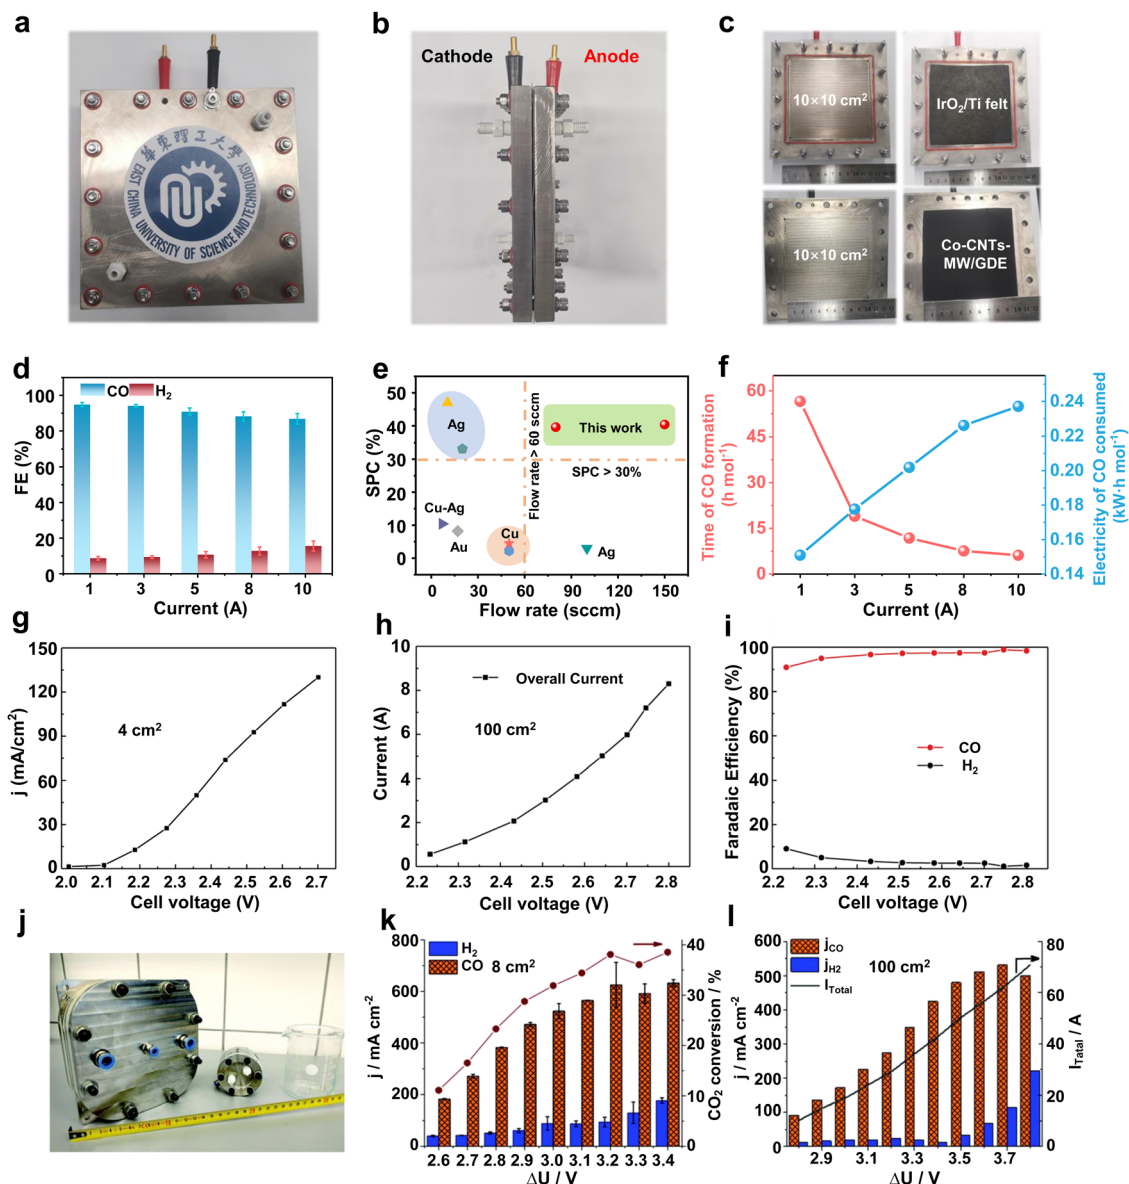


Fig. 3 Large-area MEA electrolyzer CO₂RR performance. (a) Front view, (b) side view and (c) runner view photograph of a home-made 100 cm² MEA. (d) CO and H₂ selectivity in a current range from 1 to 10 A. (e) Single-pass conversion of Co-CNTs-MW catalyst compared with various CO₂RR electrocatalysts. (f) Time of CO formation and electricity of CO consumed in a 100 cm² MEA. Reproduced with permission from ref. 45 copyright 2023, Springer Nature. Current density of a (g) 4 cm² and (h) 100 cm² MEA under different voltages. (i) Selectivity of CO and H₂ in a 100 cm² electrolyzer at different voltages. Reproduced with permission from ref. 46 copyright 2019, Elsevier Publishing Group. (j) Digital photo of 8 cm² and 100 cm² electrolyzers. CO₂RR performance of (k) 8 cm² and (l) 100 cm² electrolyzers at different potentials. Reproduced with permission from ref. 47 copyright 2020, RSC Publishing. A large-area MEA electrolyzer can increase the CO₂ electrolysis current while ensuring high product selectivity.

The above findings indicate that large-area CO₂ electrolyzers have important implications for improving CO₂ conversion rates and achieving further industrial-grade CO₂ electrolysis. However, there are still some problems related to large-area CO₂ electrolyzers. For example, the ohmic resistance of the large-area electrolyzer itself increases, resulting in lower current densities and EE. Moreover, the operational stability gradually decreases due to the precipitation of carbonate blocking the active site and catalyst shedding, *etc.* Therefore, the future development of large-area electrolyzers should be devoted to both reducing resistance and improving stability.

For the reduction of resistance, gold plating on the electrolyzer surface can be attempted.⁴⁸ For the problem of carbonate precipitation blocking the active site, this is a difficulty common to MEA-type electrolytic cells at present. We will summarize a detailed solution in the subsequent part of the perspective.

3.2 CO₂ electrostacks

Although large-area electrolyzers can bring higher CO₂ conversion rates, they are still not compatible with industrial requirements in terms of device cost and space occupation. As an integrated electrolyzer, an electrostack allows for simultaneous



CO₂ conversion in multiple chambers, resulting in sufficient CO₂ conversion while reducing device material costs. As shown in Fig. 4a and b, electrostacks commonly encompass two or more electrolytic chambers. Notably, each pair of these chambers is linked by means of a bipolar plate (BPP), wherein one facet of the BPP serves as the anode electrolytic chamber while the opposite facet functions as the cathode electrolytic chamber.⁴⁹ From the perspective of current, the electrolytic chambers are connected in series with each other, so that the same current flows through each electrode. For the flow of CO₂ gas between the electrolyzer layers, there are two types of connections: parallel and series. A parallel connection (Fig. 4a) means that the gas flows evenly through each cathode chamber, and the gas concentrations in the feed and discharge of each chamber are basically the same. A series connection (Fig. 4b) means that the CO₂ enters the first cathode chamber, then the reaction products and the remaining CO₂ enters the second cathode chamber, and so on, until it flows through the last cathode chamber and finally out of the cell, and thus this flow method can obtain a very high CO₂ conversion rate.

In recent years, CO₂ electrolyzers based on electrostacks have gradually become a hot research topic. Janáky *et al.*⁴⁹ built a 61 cm² three-chamber stack with gas flowing in series. In terms of current density, the three-cell stack and single-cell electrolyzer are basically consistent (Fig. 4c). However, under different CO₂ feed flow rates, the three-chamber stack shows a significantly better CO₂ conversion rate than the single-chamber electrolyzer (Fig. 4d), indicating that more reaction chambers and the total length of the flow paths facilitated the full utilization of CO₂. Hyung-Suk Oh *et al.*⁵⁰ designed a three-chambered electrostack with an area of 10 cm². To reduce the voltage, the stack used iron-doped cobalt foam as the OER electrode and a KOH-incorporated Cu nanoparticle electrocatalyst deposited on the GDL as the cathode for the CO₂RR. When the stack was operated at a current of 6 A, the voltage was maintained at about 7 V. This indicates that the voltage of each zero-gap electrolyzer was about 2.3–2.4 V, which is basically consistent with the electrolysis voltage of a single-chamber electrolyzer (Fig. 4e). In addition, the product selectivity of the three-chamber stack was also not attenuated compared to

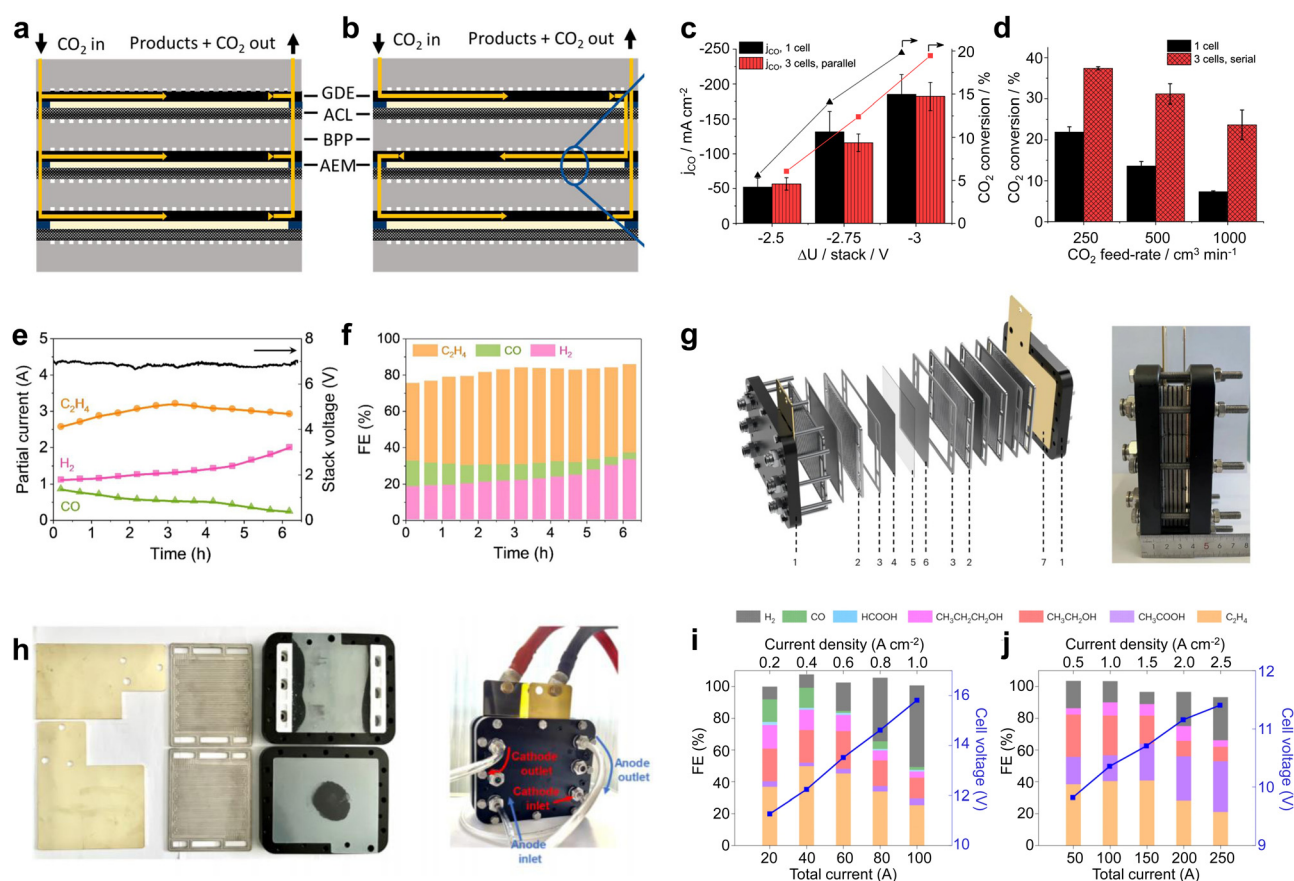


Fig. 4 Material flow patterns and CO₂RR performance in electrostacks. Circulation of CO₂ in the stack: (a) parallel and (b) series circulation. (c) Current density and (d) CO₂ conversion for a single-chamber electrolyzer and a three-chamber stack with an area of 61 cm². Reproduced with permission from ref. 49 copyright 2019, American Chemical Society. (e) Potential and (f) product selectivity distribution of a three-compartment stack with an area of 10 cm² at 6 A. Reproduced with permission from ref. 50 copyright 2021, Elsevier Publishing Group. (g) Structure schematic and digital photo of 4 × 100 cm² electrostack. (h) Digital photos of the internal runners of the stack and during testing. (i) FE and cell voltage as a function of applied current density measured in (i) 0.1 M KOH under a pure CO₂ feed and (j) 1 M KOH under a pure CO feed. Reproduced with permission from ref. 51 copyright 2023, Springer Nature. The stack can realize simultaneous CO₂ electrolysis in multiple electrolytic chambers, further improving the CO₂ conversion capacity.



that of the single-chamber electrolyzer (Fig. 4f). In a 6 hour stability test, the C_2H_4 selectivity was maintained at $\sim 45\%$ with a current of ~ 3 A, consuming 2.8 L of CO_2 and producing 1.4 L of C_2H_4 . Some breakthroughs have also been made in conducting high-current CO_2 electrolysis in an electrostack. Bao *et al.*⁵¹ designed a four-chamber electrolytic stack with an area of 100 cm^2 (Fig. 4g). This electrolyzer was designed to provide a parallel and uniform flow of gas through each chamber (Fig. 4h), and CO_2/CO co-electrolysis was achieved using CuO nanosheet catalysts at a current of more than 100 A. The stack achieved the highest C_2H_4 production rate of 457.5 mL min^{-1} at 150 A and a CH_3COOH production rate of 2.97 g min^{-1} at 250 A (Fig. 4i and j). The product generation rates here reached the level required for industrial application, indicating that a stack holds great promise for industrial production.

Some advances have also been made in new and industrial pilot power stacks. Kang *et al.*³⁹ reported that an electrostack unit for CO_2 electrolysis (Fig. 5a) to produce syngas has been pilot tested at Yitai Chemical's coal-to-oil plant in Ordos, Inner Mongolia, with a single electrolyzer voltage of only 2.8 V and an annual CO_2 throughput of 30 tons per year and stability of 2000 h. Takeda *et al.*⁵² at Toyota reported a large-volume photovoltaic power electrolyzer for converting CO_2 to formate. The electrolyzer contains five stacked electrodes and six single-crystal Si photovoltaic cells ($\sim 1000\text{ cm}^2$) connected in series (Fig. 5b and c), which were electrolyzed by immersing the electrodes in water bubbled with CO_2 . The photovoltaic part of the device is well-matched to the electrocatalytic cell to produce a reaction current of 6.30 A. The overall solar-formate conversion efficiency reached 7.2% and the formate

production rate reached 93.5 mmol h^{-1} . In addition, Chen *et al.*⁵³ designed a 100 cm^2 stack with four electrolytic chambers (Fig. 5d and e). Unlike previous reports, the cathode chamber of this stack was fed with a CO_2 -saturated electrolyte. This electrolyte flows into the cathode by forced convection, and due to the reduction of pressure at the cathode, CO_2 gas precipitates *in situ* on the catalyst surface, causing the CO_2RR to occur (Fig. 5f). This design not only improves the conduction rate of CO_2 and protons, but also takes away the generated carbonate in time and avoids the blockage of the reaction site.

To further illustrate the significance of scalable electrolyzers, we compared the CO product generation performance of several different electrolyzers. As shown in Table 1, when electrolysis is performed using a large area stack, it is capable of generating ~ 80 L of CO per hour, far exceeding that of a laboratory-scale small area MEA.

3.3 High-pressure and heated CO_2RR electrolyzers

In addition to large-area electrolyzers and electrostacks which can increase the CO_2 conversion rate, some changes to the reaction environmental factors of the scaled-up electrolyzer can lead to further performance improvements, such as high-pressure and heated CO_2 electrolyzers.

In atmospheric electrolyzer tests, the pressure of the cathode CO_2 gas is about one atmosphere. For high-pressure electrolyzers, the cathode CO_2 pressure typically reaches several to even dozens of atmospheres. This heightened pressure effectively enhances the concentration of CO_2 at the catalyst surface, thereby facilitating the process of CO_2 mass transfer. Consequently, this augmentation contributes to elevated current

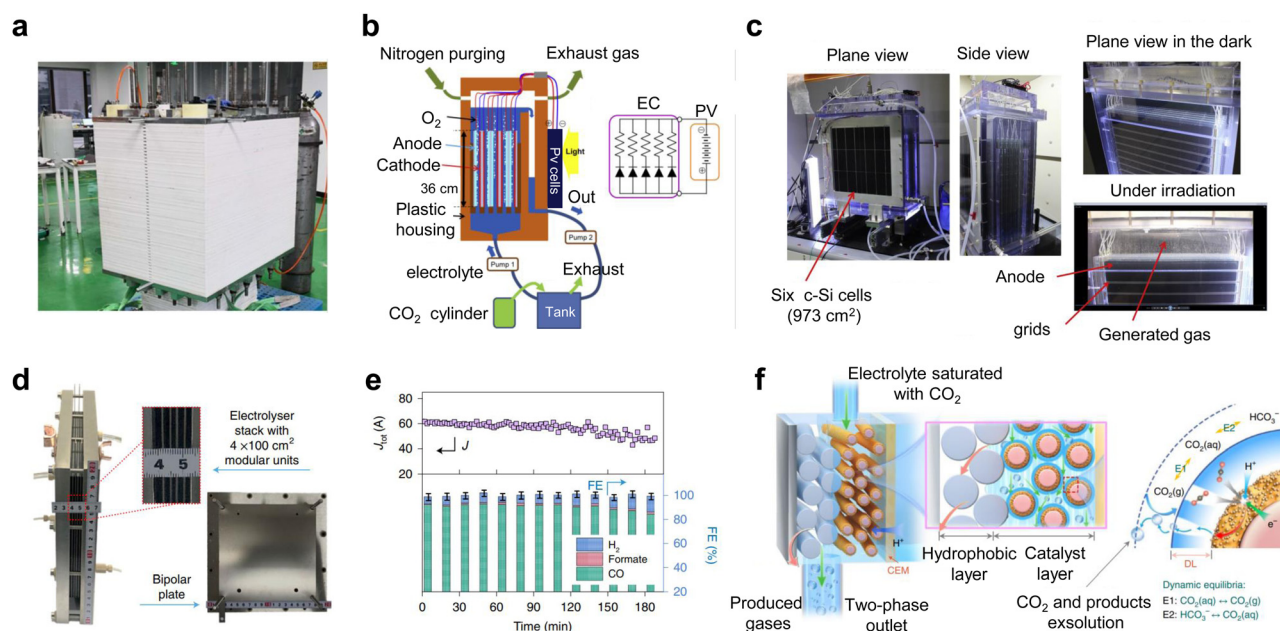


Fig. 5 Subtly designed industrial pilot power stacks. (a) CO_2 electrostack medium-scale test device. Reproduced with permission from ref. 39 copyright 2022, American Chemical Society. (b) Schematic and (c) digital photos of a large-volume photovoltaic power electrolysis cell converting CO_2 to formate. Reproduced with permission from ref. 52 copyright 2021, Elsevier Publishing Group. (d) Digital photo and (e) CO_2RR performance of a 100 cm^2 stack with four electrolytic chambers. (f) Schematic diagram of gas precipitation *in situ* on the catalyst surface when CO_2 -saturated electrolyte is forced through the cathode. Reproduced with permission from ref. 53 copyright 2022, Springer Nature.



Table 1 Performance comparison of CO₂-to-CO conversion in different electrolyzers

Electrolyzer	Catalysts	Area (cm ⁻²)	FE _{CO} (%)	<i>I</i> (A)	CO generation rate (L h ⁻¹)	Ref.
MEA	Ni-N-C	4.0	~90.0	~0.6	0.2	54
	Ag	5.0	~96.0	1.0	0.4	24
	Au/C	3.2	85.0	1.6	0.6	43
Large-area MEA	Co-CNTs-MW	100.0	86.8	10.0	3.6	45
	Ni-N-C-QAPPT	100.0	~85.0	80.0	28.4	55
	Ni-NC	100.0	99.0	8.3	3.4	46
Electrostack	Ag	100.0	~80.0	~85.0	28.4	56
	Ag	100.0 × 3	~75.0	~80.0	75.2	40
	Ag	100.0 × 4	~85.0	59.0	83.8	53
	Ag	61.0 × 3	75.0	~14.2	13.4	49

densities and heightened selectivity, ultimately yielding decreased energy consumption and mitigated costs. Sinton *et al.*⁵⁷ performed CO₂ tests at 10–50 bar, under which both the current density and CO selectivity of the catalyst increased *via* increasing pressure (Fig. 6a–c). Sinton *et al.*⁵⁸ achieved CO₂ reduction supplied by flue gas under high pressure. This method improved the reactivity of CO₂ reduction by constructing a hydrophilic layer on the catalyst surface, increasing the solubility of CO₂ at high pressure, and preventing O₂ from reaching the reaction site (Fig. 6d–f).

For heated electrolyzers, the temperature is often in the tens of degrees. A proper temperature increase can reduce the impedance of the electrolyzer (Fig. 7a) and increase the conduction rate of the ions in the electrolyte (Fig. 7b), thus increasing the current density (Fig. 7c). However, when the temperature rises to a certain level, the activity of H₂ gradually increases (Fig. 7d) and may also cause structural damage of the ion exchange membrane, thus resulting in a decrease in CO₂ reduction performance.^{43,47}

While high-pressure and heated electrolyzers can further improve the CO₂ reduction performance of amplifiable electrolyzers, this often requires the support of a more expensive pressurized or heated infrastructure. Therefore, to successfully use high-pressure and heating units for industrial-scale CO₂ reduction, it is necessary to design the unit structure properly and reduce the additional costs associated with the infrastructure.

3.4 Cathode gas feeding

The use of CO₂ + CO/O₂ co-feed gas or flue gas in scalable CO₂ electrolysis processes has also received much attention recently. This is because a reasonable adjustment of the cathode atmosphere composition will be beneficial to improve the selectivity of specific products and reduce the feed cost.

Strasser *et al.*⁵⁹ reported a mechanistic investigation of a CO₂RR based on a CO₂/CO co-feed over copper. When the ratio of CO₂ to CO was 1:1, the yield of C₂H₄ was unexpectedly increased by nearly 50%. Lu *et al.*⁶⁰ reported co-electrolysis of CO₂ and low concentration O₂. A small amount of oxygen reduction reaction is used to supplement hydroxyl groups on the catalyst surface, improving the selectivity of oxygen and hydrocarbon substances in the product. In addition, the use of

flue gas as a source of CO₂ for electrolysis can greatly reduce the feed cost. The main components of flue gas are N₂, CO₂ and O₂. N₂, due to its chemical inertness, only acts as a diluting agent for CO₂. Won *et al.*⁶¹ demonstrated that the selectivity of the CO₂RR was almost constant when the N₂ content was increased, but the current density decreases when the ratio of CO₂ and N₂ is modulated. Unfortunately, O₂ can severely inhibit CO₂ electrolysis in MEA electrolyzers due to its high reduction potential.⁶² Takeda *et al.*⁶³ reported that the selectivity of the CO₂RR decreases to 20% with only 1% O₂ present in the CO₂ gas. Wang *et al.*⁶⁴ achieved nearly 100% selectivity of formic acid in the presence of 5% O₂ by spraying an amine-based polymer film on the reverse side of the GDE that selectively permeates CO₂. Although this physical filtration method can achieve better performance, if the catalyst can be directly used to capture and transform CO₂ in flue gas, the cost and GDE preparation will be further optimized. In summary, the rational use and design of the source and composition of the cathode feed is important for scalable CO₂ electrolysis to reduce costs and improve product selectivity.

4. Further design of scalable electrolyzers

Based on the above electrolyzer research, further design and improvement of the scalable electrolyzer structure will facilitate the process of industrial application. Here, we summarize solutions to the carbonate precipitation problem, the use of ion exchange membranes and the design of flow channels, *etc.*, hoping to provide reference values for industrial CO₂ electrolyzers.

4.1 Solutions for carbonate precipitation

Clogging of the active site by carbonate precipitation, a common problem in MEA-type electrolyzers, is a serious obstacle to the long-term operation of CO₂ electrolysis.

Currently, there are several typical solutions to this problem. One is to periodically clean the gas diffusion electrode (GDE) of the cathode gas chamber to flush out the carbonate produced. For example, Sargent *et al.*⁶⁵ achieved CH₄ production at 190 mA cm⁻² for up to 100 h by periodically cleaning the cathode GDE with deionized water (Fig. 8a). The second method is to transfer the carbonate to the anode by electromigration at low potential under an alternating electric field. This method reduces the reaction rate to near 0 mA cm⁻² at low potentials, eliminating hydroxide formation, while maintaining sufficient negative polarization at the cathode to transport carbonate ions to the anode under electromigration. Using this method, Sinton *et al.*⁶⁶ ensured that the selectivity of the C₂ product remained close to 80% after up to 236 h of electrolysis (Fig. 8b). However, this method entails additional energy losses and increased time costs. Some recent progress in CO₂ electrolysis using proton exchange membranes under strongly acidic electrolytes was reported to avoid carbonate precipitation. This method allows the generated carbonate to regenerate CO₂ with



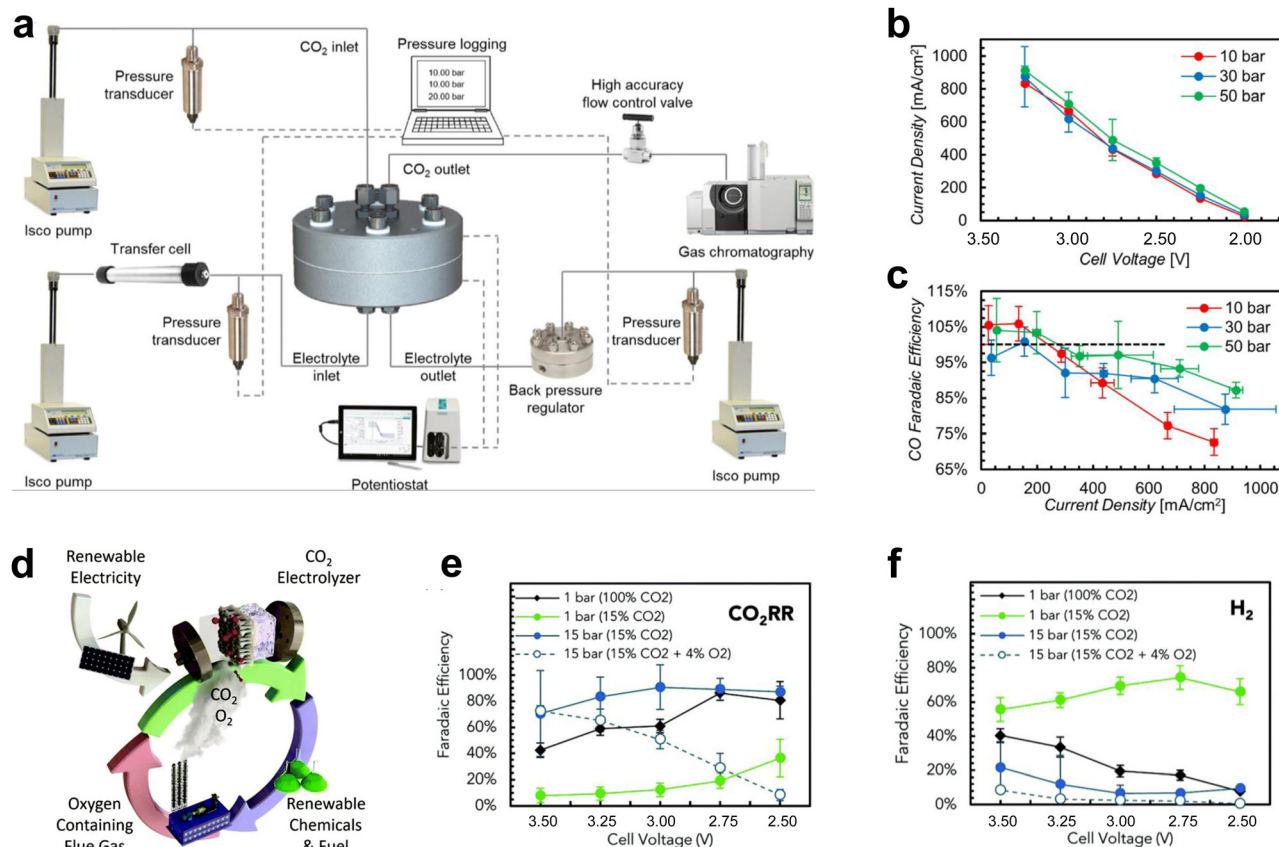


Fig. 6 Effect of pressure on CO₂ electrolyzers. (a) Schematic diagram of the structure of the high-pressure test system. (b) Product current density and (c) selectivity at different pressures. Reproduced with permission from ref. 57 copyright 2020, Elsevier Publishing Group. (d) Schematic diagram of CO₂ reduction of flue gas under high pressure. Selectivity of (e) CO₂RR and (f) HER under high pressure. Proper pressure facilitates CO₂ mass transfer and improves the current density and selectivity of the products. Reproduced with permission from ref. 58 copyright 2020, RSC Publishing.

H⁺ in solution (Fig. 8c),⁶⁷ effectively avoiding blockage of the reactive site. However, the elevated H₂ selectivity caused by the strong acidity makes electrolysis impossible to run for a long time, which is still challenging for industrialization. The use of salt-free electrolyte solutions can fundamentally solve the salt precipitation problem, but the lack of metal cations can make CO₂ activation difficult, leading to large-scale hydrogen evolution reactions (HERs). Excitingly, Zhuang *et al.*⁶⁸ achieved high-performance CO₂ electrolysis in pure water (Fig. 8d) by using porous copper modified with a quaternary polyether ether ketone (QAPEEK) containing carbonyl groups (Fig. 8e) to activate CO₂ in a salt-free environment. A total current density of 1000 mA cm⁻² was achieved at a cell voltage of 3.73 V (Fig. 8f). CO₂ electrolysis using bipolar membranes can also alleviate carbonate production to some extent.^{69,70} In addition, direct electrolysis of CO₂ absorbed in amine solutions using the reaction swing absorption technique can also be a good way to slow down carbonate precipitation.^{71,72} This is because the amine solution flowing through the cathode side can carry away the carbonate produced in time. In conclusion, one way to solve the carbonate precipitation problem is to clean or convert the generated carbonate in time, and the other is to avoid the use of salt-containing electrolytes.

4.2 Ion exchange membrane

As an important component of MEA electrolyzers, the ion exchange membrane plays a vital role in controlling ion transport, regulating pH, and avoiding crossover of cathode and anode products. There are three main types of ion exchange membranes used for the CO₂RR depending on the ion transfer: anion exchange membranes (AEM), cation exchange membranes (CEM) and bipolar membranes (BPM).

Firstly, AEMs (Fig. 9a) can transfer anions (such as OH⁻, CO₃²⁻, etc.) produced by the cathode to the anode, avoiding the transmembrane transfer of H⁺ produced by the anode, thus inhibiting the HER reaction and improving the CO₂ reduction selectivity. However, since the CO₃²⁻ produced at the cathode will transport across the membrane to the anode to produce CO₂ with H⁺, AEMs will lead to a large amount of carbon loss, and the theoretical CO₂ utilization rate will not exceed 50%.⁷³ CEMs (Fig. 9b) can transfer H⁺ from the anode to cathode, and then generate CO₂ with CO₃²⁻ produced at the cathode, so that the CO₂ can be reused and carbon loss can be avoided. However, due to the transfer of H⁺ to the cathode, this tends to cause serious HER side reactions. Finally, BPMs (Fig. 9c) consist of a CEM and an AEM with an H₂O layer between the two membranes, providing H⁺ and OH⁻ to the cathode and



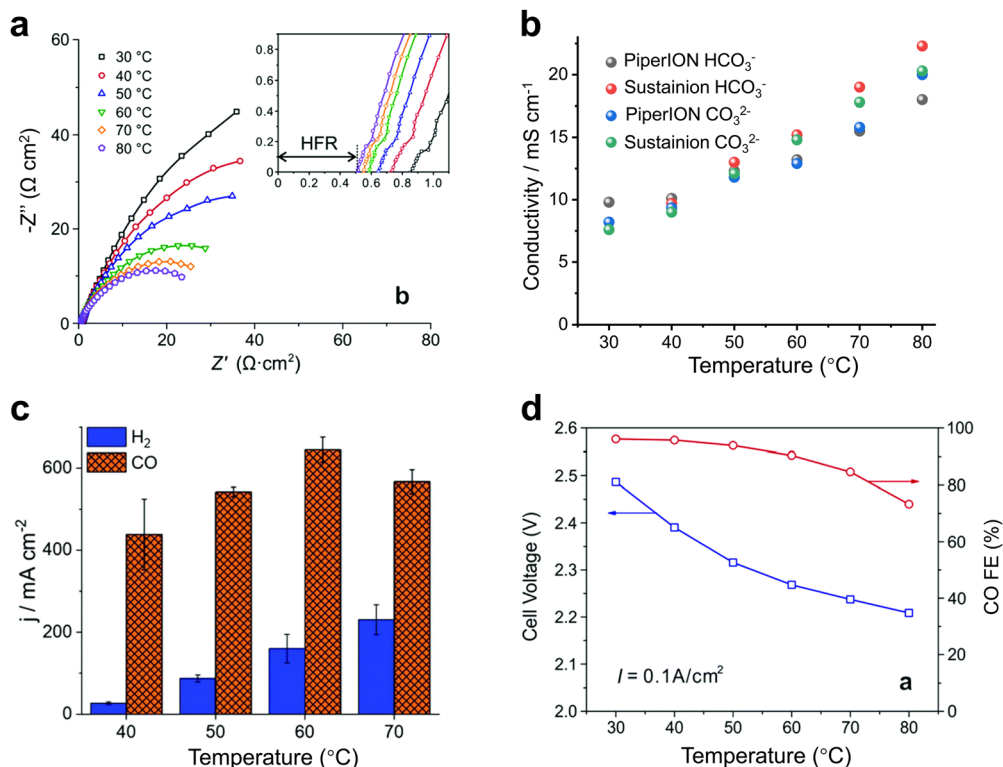


Fig. 7 Effect of heating on CO₂ electrolyzers. Effects of temperature on (a) the impedance, (b) ionic conductivity, (c) current density and (d) product selectivity of the electrolyzer. Proper temperature facilitates ion transport, reduces impedance, and increases current density. (a) and (d) Reproduced with permission from ref. 43, 47 copyright 2019, RSC Publishing. (b) and (c) Reproduced with permission from ref. 47 copyright 2020, RSC Publishing.

anode through the water dissociation catalyst. BPM can avoid the carbon loss from the cathode while avoiding the HER caused by high H⁺ at the cathode.⁷⁴ Unfortunately, there are some problems with the BPM, such as high cost, poor durability, *etc.* and the membrane will crack from the middle during long duration use.

Therefore, subtle modifications of ion exchange membranes are also necessary if scalable electrolyzers are to meet the requirements of industrialization. In this regard, problems such as carbon loss in AEM, severe cathode HERs in the CEM and poor durability of the BPM, still remain big challenges. To solve these problems, Sinton *et al.*⁷⁵ designed a micro-channel solid electrolyte to enable the capture and recovery of CO₃²⁻ before it reaches the anode and reduce CO₂ loss to ~3% whilst using an AEM. Ma *et al.*⁷⁶ constructed a hydrophobic environment by depositing a porous carbon layer on Fe nanoparticles to inhibit the penetration of water in a strongly acidic electrolyte whilst using a CEM, achieving a CO selectivity close to 90%.

In addition, some physicochemical properties of ion exchange membranes (IEMs) can have a dramatic impact on the performance of the electrolyzer. For example, IEMs with lower impedance have higher ionic conductivity and give the electrolyzers a higher circuit density (Fig. 9d and e).⁵⁶ Meanwhile, IEMs are made more durable by characteristic functional group modifications. Masel *et al.*⁷⁷ achieved 3000 hours of operation at a current density of 200 mA cm^{-2} by functionalizing an AEM with

imidazole-based ionic liquid using Ag as the catalyst (Fig. 9f). Therefore, it is crucial to design IEMs with higher ionic conductivity and more durability. Overall, the improvement and design based on ion-exchange membranes is an important strategy to accelerate the industrialization of scalable CO₂ electrolyzers.

4.3 Flow channel design

The flow plate is a critical component that ensures proper water/CO₂ management and stabilizes the system reaction state parameters. The structural parameters of the electrolyzer flow channel have an impact on the local pressure, flow rate, and uniformity of distribution of the fluid. The state of these fluids is closely related to the current density and stability of CO₂ reduction. Therefore, it is possible to improve the flow state of the fluid by adjusting the distribution structure, depth, and width of the flow channel, thus improving the performance of the CO₂ electrolyzer.

To date, little research has been done in the field of electrochemical CO₂ reduction for the simulation and design of flow channels, drawing mainly from studies in fuel cells and redox flow batteries. Flow field designs typically include parallel, serpentine and interdigitated flow fields.⁷⁸ Appropriate designs, such as spiral, circular, and mesh flow fields, would optimize the geometric structure of the original flow field to improve distribution uniformity and enhance mass transfer.^{79,80} Additionally, biomimetic structures like the lung-inspired flow field, which is inspired by the fractal geometry of the lungs, has emerged to



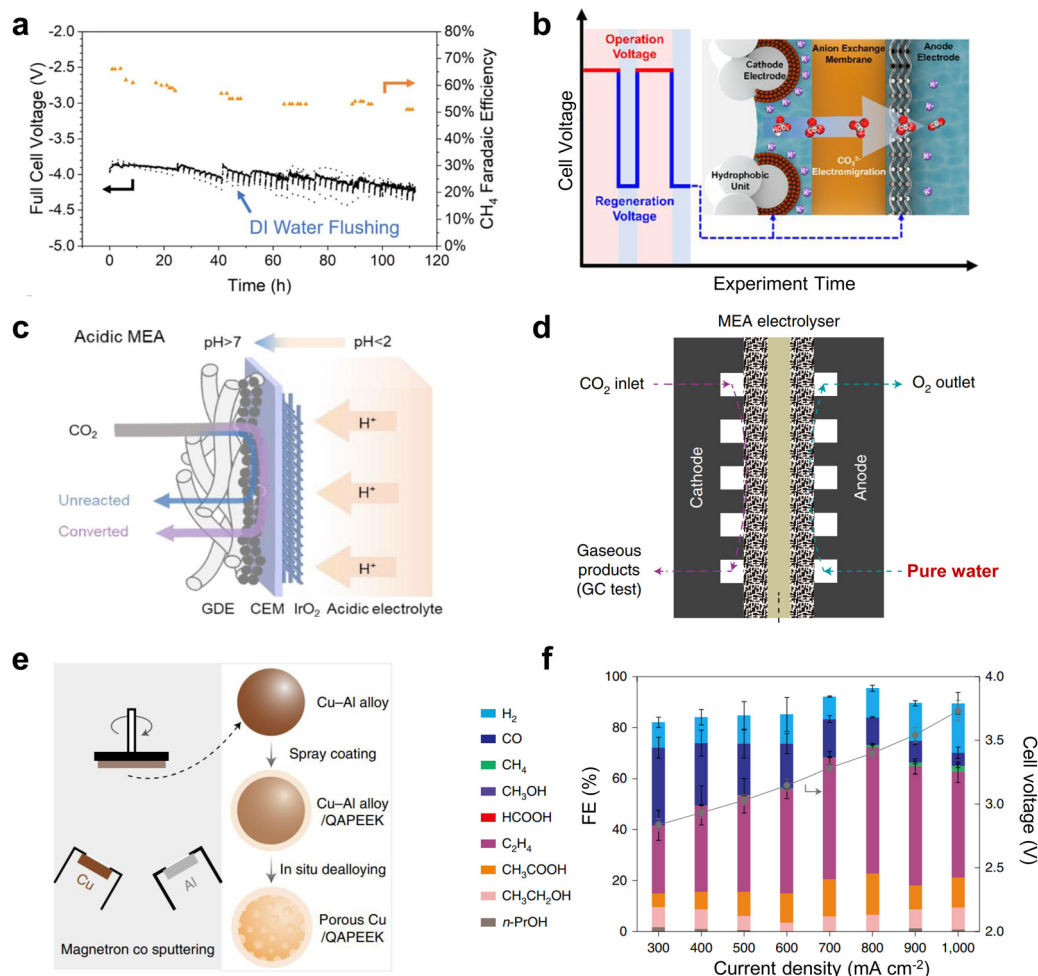


Fig. 8 Solutions to the cathodic carbonate precipitation problem. (a) Regular flushing of the GDE to achieve stability for up to 100 h. Reproduced with permission from ref. 65 copyright 2021, Springer Nature. (b) Under an alternating electric field, the carbonate is transferred to the anode by electromigration at low potential. Reproduced with permission from ref. 66 copyright 2021, American Chemical Society. (c) Carbonate regeneration processes in acidic electrolytes. Reproduced with permission from ref. 67 copyright 2022, American Chemical Society. (d) Structural illustration of the MEA with pure water. (e) Schematic illustration of the preparation process of the porous Cu-QAPEEK GDE. (f) Product selectivity and cell voltage at different current densities. Reproduced with permission from ref. 68 copyright 2022, Springer Nature.

overcome the issue of uniform reactant distribution.⁸¹ Typical CO₂ electrolyzer flow fields are now mainly serpentine and spiral flow paths. Yan *et al.*⁸² reported that the mass fraction distribution of gas was positively correlated with the current density. In the serpentine flow channel (Fig. 10a), the turns have more resistance, leading to a greater local concentration of CO₂ than in the linear flow channel. In the electrocatalytic process, this aspect of mass transfer will be easier, which will lead to inhomogeneous current density and thus instability of the reaction (local salt precipitation, GDL local decomposition damage, *etc.*). In the spiral flow channel (Fig. 10b), there is almost no turnaround, avoiding such problems. The use of a spiral flow channel results in a flow channel with a long total length, increasing the CO₂ residence time and the CO₂ single conversion rate.^{83,84} However, at lower CO₂ flow rates, this also increases the difference in CO₂ concentration between the inlet and outlet, resulting in uneven current density distribution and additional energy loss. Computational fluid dynamics simulation is an essential tool to assist in

the rational design of flow channel structures and understand the impact of geometric parameters on electrolysis performance. Berlinguette *et al.* developed a 3D flow plate model for CO₂ reduction (Fig. 10c), and found that increasing the CO₂ humidity at the inlet can make water distribution more uniform.⁸⁵ In general, ensuring the uniformity of CO₂ gas transport, reducing the pressure drop, and increasing the CO₂ conversion rate are the keys to the design of flow paths in the current dischargeable large CO₂ electrolyzer.

4.4 Reduced product separation costs

The cost of product separation is also an important part of large-scale CO₂ electrolysis costs. Currently, there have been advances in research to effectively reduce the cost of CO₂RR products through the design of electrolyzers. Next, we discuss the impact of electrolysis parameters on separation costs.

For the current separation of the products of CO₂ electrolysis, there are two aspects to consider: the separation of the



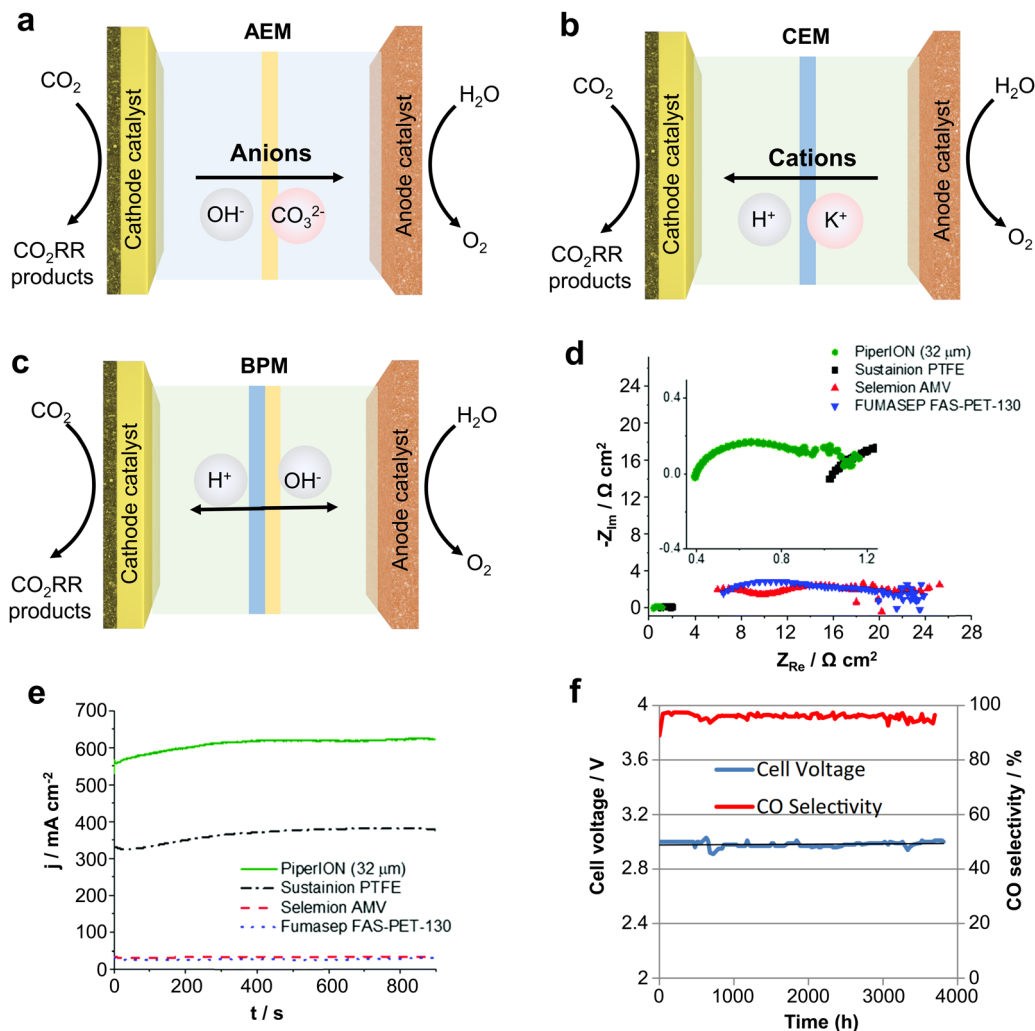


Fig. 9 Types of IEMs and their effects on CO₂ electrolysis performance. Different types of ion exchange membranes: (a) AEM, (b) CEM and (c) BPM. (d) Impedance and (e) current density of different AEMs at the same voltage. (f) Imidazolium-based ion-functionalized AEM achieves over 3000 hours of CO₂ electrolysis. Rational design of ion exchange membranes can improve the ion conduction speed, current density and stability. (d) and (e) Reproduced with permission from ref. 56 copyright 2020, RSC Publishing. (f) Reproduced with permission from ref. 77 copyright 2018, ECS Publishing.

products in the gas phase and in the liquid phase. For the separation of gas-phase products, industry currently uses, in the main, pressure swing adsorption (PSA) technology. The principle is to use a molecular sieve based on the gas molecule adsorption performance differences of different gas molecules and separate the gas mixture.⁸⁶ The cost of separation is closely related to factors such as the type and content of the gas. Jiao *et al.*⁸⁷ reported that the cost of separating the gas product (a mixture of CO₂ and CO) using PSA technology is about 23% of the total operating cost at 10% CO₂ single-pass conversion efficiency in the CO₂RR to CO process. In contrast, increasing the CO₂ single-pass conversion efficiency to 50% reduces the separation cost by 78% (6% of the total cost). Therefore, the key to reducing the cost of gas product separation is therefore to increase the CO₂ single-pass conversion efficiency, *i.e.*, to increase the concentration of the product in the effluent gas.

For the separation of liquid phase products, distillation is often used in industry to separate substances by utilizing their

different boiling points, but this process is extremely energy intensive.⁸⁸ Recently Wang *et al.*⁷⁰ have separated relatively pure products such as HCOOH by using solid electrolyte membrane electrodes, which is an inexpensive method to separate the products *in situ*, and is expected to be used in later developments.

5. Summary and outlook

Electrochemical CO₂ conversion is a promising approach to carbon utilization and has great potential to reduce the atmospheric CO₂ concentration and realize economic benefits by obtaining value-added commodities. The development of large-scale CO₂ electrolyzers with excellent performance is the key to achieving industrial-scale conversion of CO₂. This perspective mainly outlines several typical electrolyzers for CO₂ electrochemical conversion and highlights the most promising role of



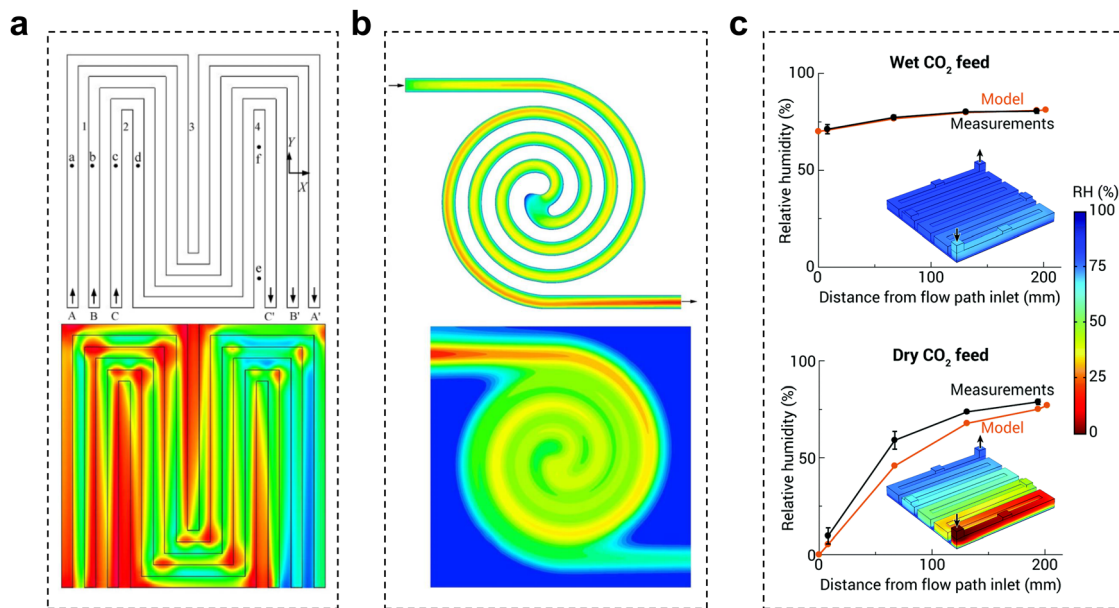


Fig. 10 Effect of the flow channel on CO₂ electrolysis. Schematic diagram of the gas mass distribution in (a) a serpentine flow channel and (b) a spiral flow channel, red to blue indicates a change from a high mass concentration to a low mass concentration. (c) Comparison of relative humidity (RH) in the cathode flow field obtained with the analytical electrolyzer and model for wet and dry CO₂ feeds. (a) Reproduced with permission from ref. 82 copyright 2007, Elsevier Publishing Group. (b) Reproduced with permission from ref. 83 copyright 2017, Wiley. (c) Reproduced with permission from ref. 85 copyright 2020, RSC Publishing.

MEA-type electrolyzers for industrial applications. Currently, numerous researchers have undertaken investigations on large-area electrolyzers, power stacks, and high-pressure/heated electrolyzers as part of the initial exploratory efforts towards scalable CO₂ electrolysis. These amplifiable devices have shown outstanding performance in increasing CO₂ conversion rates and reducing costs. However, there are still some issues that cannot be ignored, such as how to avoid severe salt precipitation, excessive energy consumption, short durability, and the high base unit cost.

To achieve industrialization of CO₂RR technologies, the design of scalable electrolyzers needs to be optimized in terms of device structure, flow channels and ion exchange membranes. The following is a summary of these aspects.

(1) Multi-field coupling of temperature, pressure, flow field and atmosphere. Optimizing the temperature can decrease the impedance of the electrolyzers and enhance the ion conduction rate in the electrolyte, leading to an increased reaction current density. Applying pressure can elevate the local CO₂ concentration on the catalyst surface, which is conducive to the CO₂ mass transfer process, and ultimately, increases the current density and selectivity. The flow field parameters are closely related to the local pressure, flow rate and atmosphere homogeneity of the fluid, which will affect the current density and stability of the CO₂RR. Adjusting the composition of the cathode atmosphere (CO₂ + CO/O₂ co-feed or flue gas) can enhance the selectivity of specific products and reduce the feed cost. Taking these operational parameters together and optimizing the factors required for CO₂ electrolysis should be comprehensively explored to maximize the CO₂RR performance.

(2) Robust IEMs for optimal MEA configurations. IEMs with high ionic conductivity which prevent the crossover of cathode and anode products can achieve long-term stability, high energy efficiency, and high yields. In particular, targeted functional group modifications of IEMs have been shown to enhance their ionic conductivity, resulting in elevated current densities during the reaction. Furthermore, IEMs possessing superior mechanical strength promote prolonged operation in scalable electrolyzers, thus reducing reaction expenses.

(3) Avoiding salt precipitation around the cathode. To maintain the stability of the CO₂RR electrolyzer, it is necessary to carry away or convert the carbonate produced, by changing the inflow of CO₂ gas to the cathode (*e.g.*, forced passage of a CO₂ saturated electrolyte) or by using CEM electrolysis in an acidic electrolyte. Pure water-fed CO₂ electrolysis also effectively avoids the formation of carbonates while yielding a pure liquid phase product.

(4) Non-precious CO₂RR and OER electrocatalysts. In a full-cell system, the CO₂RR cathode material assumes a pivotal function in enhancing product selectivity and ensuring sustained reaction stability over time. Large-scale fabrication of non-precious, highly selective CO₂RR electrocatalysts is still challenging. In addition, OER anode materials in the MEA system also play an important role in reducing the voltage and reducing the total energy input, which should ensure that the anode material does not poison the cathode catalyst through the IEM. However, Ir-based anode materials with high loadings currently still dominant the MEA configurations.

In summary, we believe that with continued research and development of scalable CO₂ electrolyzers, CO₂ electrolysis technology will be effectively implemented in industrial production in the near future.



Conflicts of interest

There are no conflicts to declare.

Acknowledgements

This work was financially supported by the Australian Research Council Discovery Project (DP200100965) and the Science and Technology Commission of Shanghai Municipality (21DZ1207101, 22ZR1416400).

References

- 1 D. Wakerley, S. Lamaison, J. Wicks, A. Clemens, J. Feaster, D. Corral, S. A. Jaffer, A. Sarkar, M. Fontecave, E. B. Duoss, S. Baker, E. H. Sargent, T. F. Jaramillo and C. Hahn, *Nat. Energy*, 2022, **7**, 130–143.
- 2 S. Jin, Z. Hao, K. Zhang, Z. Yan and J. Chen, *Angew. Chem., Int. Ed.*, 2021, **60**, 20627–20648.
- 3 A. Rode, T. Carleton, M. Delgado, M. Greenstone, T. Houser, S. Hsiang, A. Hultgren, A. Jina, R. E. Kopp, K. E. McCusker, I. Nath, J. Rising and J. Yuan, *Nature*, 2021, **598**, 308–314.
- 4 Y. Yan, T. N. Borhani, S. G. Subraveti, K. N. Pai, V. Prasad, A. Rajendran, P. Nkulikiyinka, J. O. Asibor, Z. Zhang, D. Shao, L. Wang, W. Zhang, Y. Yan, W. Ampomah, J. You, M. Wang, E. J. Anthony, V. Manovic and P. T. Clough, *Energy Environ. Sci.*, 2021, **14**, 6122–6157.
- 5 R. Meys, A. Kätelhön, M. Bachmann, B. Winter, C. Zibunas, S. Suh and A. Bardow, *Science*, 2021, **374**, 71–76.
- 6 P.-F. Sui, M. Gao, M. Zhu, C. Xu, Y.-C. Wang, S. Liu and J.-L. Luo, *EES Catal.*, 2023, **1**, 290–300.
- 7 Q. Zhou, X. Tang, S. Qiu, L. Wang, L. Hao and Y. Yu, *Mater. Today Phys.*, 2023, **33**, 101050.
- 8 K. Jiang and P. Ashworth, *Renewable Sustainable Energy Rev.*, 2021, **138**, 110521.
- 9 J. Mertens, C. Breyer, K. Arning, A. Bardow, R. Belmans, A. Dibenedetto, S. Erkman, J. Griepkoven, G. Léonard, S. Nizou, D. Pant, A. S. Reis-Machado, P. Styring, J. Vente, M. Webber and C. J. Sapart, *Joule*, 2023, **7**, 442–449.
- 10 L. Sun and W. Chen, *J. Cleaner Prod.*, 2022, **333**, 130027.
- 11 J. G. Vitillo, *Chem. Rev.*, 2017, **117**, 9521–9523.
- 12 H. Shin, K. U. Hansen and F. Jiao, *Nat. Sustain.*, 2021, **4**, 911–919.
- 13 W. Gao, S. Liang, R. Wang, Q. Jiang, Y. Zhang, Q. Zheng, B. Xie, C. Y. Toe, X. Zhu, J. Wang, L. Huang, Y. Gao, Z. Wang, C. Jo, Q. Wang, L. Wang, Y. Liu, B. Louis, J. Scott, A.-C. Roger, R. Amal, H. He and S.-E. Park, *Chem. Soc. Rev.*, 2020, **49**, 8584–8686.
- 14 S. M. Jordaán and C. Wang, *Nat. Catal.*, 2021, **4**, 915–920.
- 15 S. Sarkar, J. Raj, D. Bagchi, A. Cherevotan, C. P. Vinod and S. C. Peter, *EES Catal.*, 2023, **1**, 162–170.
- 16 W. Zhang, C. Huang, Q. Xiao, L. Yu, L. Shuai, P. An, J. Zhang, M. Qiu, Z. Ren and Y. Yu, *J. Am. Chem. Soc.*, 2020, **142**, 11417–11427.
- 17 F.-Y. Gao, R.-C. Bao, M.-R. Gao and S.-H. Yu, *J. Mater. Chem. A*, 2020, **8**, 15458–15478.
- 18 W. Zhang, C. Huang, J. Zhu, Q. Zhou, R. Yu, Y. Wang, P. An, J. Zhang, M. Qiu, L. Zhou, L. Mai, Z. Yi and Y. Yu, *Angew. Chem., Int. Ed.*, 2022, **61**, e202112116.
- 19 W. Ma, X. He, W. Wang, S. Xie, Q. Zhang and Y. Wang, *Chem. Soc. Rev.*, 2021, **50**, 12897–12914.
- 20 C. Chen, J. F. Khosrowabadi Kotyk and S. W. Sheehan, *Chem*, 2018, **4**, 2571–2586.
- 21 M. Zheng, P. Wang, X. Zhi, K. Yang, Y. Jiao, J. Duan, Y. Zheng and S.-Z. Qiao, *J. Am. Chem. Soc.*, 2022, **144**, 14936–14944.
- 22 X. Chen, J. Chen, N. M. Alghoraibi, D. A. Henckel, R. Zhang, U. O. Nwabara, K. E. Madsen, P. J. A. Kenis, S. C. Zimmerman and A. A. Gewirth, *Nat. Catal.*, 2021, **4**, 20–27.
- 23 J. E. Huang, F. Li, A. Ozden, A. Sedighian Rasouli, F. P. García de Arquer, S. Liu, S. Zhang, M. Luo, X. Wang, Y. Lum, Y. Xu, K. Bertens, R. K. Miao, C.-T. Dinh, D. Sinton and E. H. Sargent, *Science*, 2021, **372**, 1074–1078.
- 24 R. B. Kutz, Q. Chen, H. Yang, S. D. Sajjad, Z. Liu and I. R. Masel, *Energy Technol.*, 2017, **5**, 929–936.
- 25 B. Pan, Y. Wang and Y. Li, *Chem. Catal.*, 2022, **2**, 1267–1276.
- 26 E. W. Lees, B. A. W. Mowbray, F. G. L. Parlane and C. P. Berlinguette, *Nat. Rev. Mater.*, 2022, **7**, 55–64.
- 27 H. Yang, L. Shang, Q. Zhang, R. Shi, G. I. N. Waterhouse, L. Gu and T. Zhang, *Nat. Commun.*, 2019, **10**, 4585.
- 28 W. Ni, Z. Liu, Y. Zhang, C. Ma, H. Deng, S. Zhang and S. Wang, *Adv. Mater.*, 2021, **33**, 2003238.
- 29 H. Q. Fu, J. Liu, N. M. Bedford, Y. Wang, J. W. Sun, Y. Zou, M. Dong, J. Wright, H. Diao, P. Liu, H. G. Yang and H. Zhao, *Adv. Mater.*, 2022, **34**, 2202854.
- 30 J. Y. Zhao, Y. Liu, W. Li, C. F. Wen, H. Q. Fu, H. Y. Yuan, P. F. Liu and H. G. Yang, *Chem. Catal.*, 2023, **3**, 100471.
- 31 C. Liu, Y. Wu, K. Sun, J. Fang, A. Huang, Y. Pan, W.-C. Cheong, Z. Zhuang, Z. Zhuang, Q. Yuan, H. L. Xin, C. Zhang, J. Zhang, H. Xiao, C. Chen and Y. Li, *Chem*, 2021, **7**, 1297–1307.
- 32 H. Q. Fu, J. Liu, N. M. Bedford, Y. Wang, J. Wright, P. F. Liu, C. F. Wen, L. Wang, H. Yin, D. Qi, P. Liu, H. G. Yang and H. Zhao, *Nano-Micro Lett.*, 2022, **14**, 121.
- 33 D. Yao, C. Tang, X. Zhi, B. Johannessen, A. Slattery, S. Chern and S.-Z. Qiao, *Adv. Mater.*, 2023, **35**, 2209386.
- 34 D. Yao, C. Tang, A. Vasileff, X. Zhi, Y. Jiao and S. Z. Qiao, *Angew. Chem., Int. Ed.*, 2021, **60**, 18178–18184.
- 35 S. Ren, D. Joulié, D. Salvatore, K. Torbensen, M. Wang, M. Robert and C. P. Berlinguette, *Science*, 2019, **365**, 367–369.
- 36 A. Inoue, T. Harada, S. Nakanishi and K. Kamiya, *EES Catal.*, 2023, **1**, 9–16.
- 37 X. Zhang, Y. Wang, M. Gu, M. Wang, Z. Zhang, W. Pan, Z. Jiang, H. Zheng, M. Lucero, H. Wang, G. E. Sterbinsky, Q. Ma, Y.-G. Wang, Z. Feng, J. Li, H. Dai and Y. Liang, *Nat. Energy*, 2020, **5**, 684–692.
- 38 L. Ge, H. Rabiee, M. Li, S. Subramanian, Y. Zheng, J. H. Lee, T. Burdyny and H. Wang, *Chem*, 2022, **8**, 663–692.
- 39 Y. Cheng, P. Hou, X. Wang and P. Kang, *Acc. Chem. Res.*, 2022, **55**, 231–240.
- 40 B. Endrődi, A. Samu, E. Kecsenovity, T. Halmágyi, D. Sebők and C. Janáky, *Nat. Energy*, 2021, **6**, 439–448.



- 41 J. Gao, H. Zhang, X. Guo, J. Luo, S. M. Zakeeruddin, D. Ren and M. Grätzel, *J. Am. Chem. Soc.*, 2019, **141**, 18704–18714.
- 42 M. Zhong, K. Tran, Y. Min, C. Wang, Z. Wang, C.-T. Dinh, P. De Luna, Z. Yu, A. S. Rasouli, P. Brodersen, S. Sun, O. Voznyy, C.-S. Tan, M. Askerka, F. Che, M. Liu, A. Seifitokaldani, Y. Pang, S.-C. Lo, A. Ip, Z. Ulissi and E. H. Sargent, *Nature*, 2020, **581**, 178–183.
- 43 Z. Yin, H. Peng, X. Wei, H. Zhou, J. Gong, M. Huai, L. Xiao, G. Wang, J. Lu and L. Zhuang, *Energy Environ. Sci.*, 2019, **12**, 2455–2462.
- 44 N. M. Haegel, R. Margolis, T. Buonassisi, D. Feldman, A. Froitzheim, R. Garabedian, M. Green, S. Glunz, H.-M. Henning, B. Holder, I. Kaizuka, B. Kroposki, K. Matsubara, S. Niki, K. Sakurai, R. A. Schindler, W. Tumas, E. R. Weber, G. Wilson, M. Woodhouse and S. Kurtz, *Science*, 2017, **356**, 141–143.
- 45 J. Wei Sun, X. Wu, P. Fei Liu, J. Chen, Y. Liu, Z. Xin Lou, J. Yue Zhao, H. Yang Yuan, A. Chen, X. Lu Wang, M. Zhu, S. Dai and H. Gui Yang, *Nat. Commun.*, 2023, **14**, 1599.
- 46 T. Zheng, K. Jiang, N. Ta, Y. Hu, J. Zeng, J. Liu and H. Wang, *Joule*, 2019, **3**, 265–278.
- 47 B. Endrodi, E. Kecsenvity, A. A. Samu, T. Halmágyi, S. Rojas-Carbonell, L. Wang, Y. Yan and C. Janáky, *Energy Environ. Sci.*, 2020, **13**, 4098–4105.
- 48 B. Wu, B. Tan, G. Tan, M. Zeng, J. Luo, G. Hu, J. Luo, Z. Hao, S. Lai and B. Liu, *RSC Adv.*, 2021, **11**, 39153–39168.
- 49 B. Endrődi, E. Kecsenvity, A. Samu, F. Darvas, R. V. Jones, V. Török, A. Danyi and C. Janáky, *ACS Energy Lett.*, 2019, **4**, 1770–1777.
- 50 W. H. Lee, C. Lim, S. Y. Lee, K. H. Chae, C. H. Choi, U. Lee, B. K. Min, Y. J. Hwang and H.-S. Oh, *Nano Energy*, 2021, **84**, 105859.
- 51 P. Wei, D. Gao, T. Liu, H. Li, J. Sang, C. Wang, R. Cai, G. Wang and X. Bao, *Nat. Nanotechnol.*, 2023, **18**, 299–306.
- 52 N. Kato, S. Mizuno, M. Shiozawa, N. Nojiri, Y. Kawai, K. Fukumoto, T. Morikawa and Y. Takeda, *Joule*, 2021, **5**, 687–705.
- 53 G. Wen, B. Ren, X. Wang, D. Luo, H. Dou, Y. Zheng, R. Gao, J. Gostick, A. Yu and Z. Chen, *Nat. Energy*, 2022, **7**, 978–988.
- 54 C. Xia, Y. Qiu, Y. Xia, P. Zhu, G. King, X. Zhang, Z. Wu, J. Y. Kim, D. A. Cullen, D. Zheng, P. Li, M. Shakouri, E. Heredia, P. Cui, H. N. Alshareef, Y. Hu and H. Wang, *Nat. Chem.*, 2021, **13**, 887–894.
- 55 P. Wei, H. Li, R. Li, Y. Wang, T. Liu, R. Cai, D. Gao, G. Wang and X. Bao, *Small*, 2023, 2300856.
- 56 B. Endrődi, E. Kecsenvity, A. Samu, T. Halmágyi, S. Rojas-Carbonell, L. Wang, Y. Yan and C. Janáky, *Energy Environ. Sci.*, 2020, **13**, 4098–4105.
- 57 J. P. Edwards, Y. Xu, C. M. Gabardo, C.-T. Dinh, J. Li, Z. Qi, A. Ozden, E. H. Sargent and D. Sinton, *Appl. Energy*, 2020, **261**, 114305.
- 58 Y. Xu, J. P. Edwards, J. Zhong, C. P. O'Brien, C. M. Gabardo, C. McCallum, J. Li, C.-T. Dinh, E. H. Sargent and D. Sinton, *Energy Environ. Sci.*, 2020, **13**, 554–561.
- 59 X. Wang, J. F. de Araújo, W. Ju, A. Bagger, H. Schmies, S. Köhl, J. Rossmeisl and P. Strasser, *Nat. Nanotechnol.*, 2019, **14**, 1063–1070.
- 60 M. He, C. Li, H. Zhang, X. Chang, J. G. Chen, W. A. Goddard, M.-J. Cheng, B. Xu and Q. Lu, *Nat. Commun.*, 2020, **11**, 3844.
- 61 D. Kim, W. Choi, H. W. Lee, S. Y. Lee, Y. Choi, D. K. Lee, W. Kim, J. Na, U. Lee, Y. J. Hwang and D. H. Won, *ACS Energy Lett.*, 2021, **6**, 3488–3495.
- 62 X. Lu, Z. Jiang, X. Yuan, Y. Wu, R. Malpass-Evans, Y. Zhong, Y. Liang, N. B. McKeown and H. Wang, *Sci. Bull.*, 2019, **64**, 1890–1895.
- 63 Y. Takeda, S. Mizuno, R. Iwata, T. Morikawa and N. Kato, *J. CO₂ Util.*, 2023, **71**, 102472.
- 64 P. Li, X. Lu, Z. Wu, Y. Wu, R. Malpass-Evans, N. B. McKeown, X. Sun and H. Wang, *Angew. Chem., Int. Ed.*, 2020, **59**, 10918–10923.
- 65 Y. Xu, F. Li, A. Xu, J. P. Edwards, S.-F. Hung, C. M. Gabardo, C. P. O'Brien, S. Liu, X. Wang, Y. Li, J. Wicks, R. K. Miao, Y. Liu, J. Li, J. E. Huang, J. Abed, Y. Wang, E. H. Sargent and D. Sinton, *Nat. Commun.*, 2021, **12**, 2932.
- 66 Y. Xu, J. P. Edwards, S. Liu, R. K. Miao, J. E. Huang, C. M. Gabardo, C. P. O'Brien, J. Li, E. H. Sargent and D. Sinton, *ACS Energy Lett.*, 2021, **6**, 809–815.
- 67 B. Pan, J. Fan, J. Zhang, Y. Luo, C. Shen, C. Wang, Y. Wang and Y. Li, *ACS Energy Lett.*, 2022, **7**, 4224–4231.
- 68 W. Li, Z. Yin, Z. Gao, G. Wang, Z. Li, F. Wei, X. Wei, H. Peng, X. Hu, L. Xiao, J. Lu and L. Zhuang, *Nat. Energy*, 2022, **7**, 835–843.
- 69 T. Li, E. W. Lees, M. Goldman, D. A. Salvatore, D. M. Weekes and C. P. Berlinguette, *Joule*, 2019, **3**, 1487–1497.
- 70 C. Xia, P. Zhu, Q. Jiang, Y. Pan, W. Liang, E. Stavitski, H. N. Alshareef and H. Wang, *Nat. Energy*, 2019, **4**, 776–785.
- 71 K. M. G. Langie, K. Tak, C. Kim, H. W. Lee, K. Park, D. Kim, W. Jung, C. W. Lee, H.-S. Oh, D. K. Lee, J. H. Koh, B. K. Min, D. H. Won and U. Lee, *Nat. Commun.*, 2022, **13**, 7482.
- 72 G. Lee, Y. C. Li, J.-Y. Kim, T. Peng, D.-H. Nam, A. Sedighian Rasouli, F. Li, M. Luo, A. H. Ip, Y.-C. Joo and E. H. Sargent, *Nat. Energy*, 2021, **6**, 46–53.
- 73 J. Y. T. Kim, P. Zhu, F.-Y. Chen, Z.-Y. Wu, D. A. Cullen and H. Wang, *Nat. Catal.*, 2022, **5**, 288–299.
- 74 K. Xie, R. K. Miao, A. Ozden, S. Liu, Z. Chen, C.-T. Dinh, J. E. Huang, Q. Xu, C. M. Gabardo, G. Lee, J. P. Edwards, C. P. O'Brien, S. W. Boettcher, D. Sinton and E. H. Sargent, *Nat. Commun.*, 2022, **13**, 3609.
- 75 Y. Xu, R. K. Miao, J. P. Edwards, S. Liu, C. P. O'Brien, C. M. Gabardo, M. Fan, J. E. Huang, A. Robb, E. H. Sargent and D. Sinton, *Joule*, 2022, **6**, 1333–1343.
- 76 Q. Fan, G. Bao, X. Chen, Y. Meng, S. Zhang and X. Ma, *ACS Catal.*, 2022, **12**, 7517–7523.
- 77 Z. Liu, H. Yang, R. Kutz and R. I. Masel, *J. Electrochem. Soc.*, 2018, **165**, J3371.
- 78 A. Kazim, H. T. Liu and P. Forges, *J. Appl. Electrochem.*, 1999, **29**, 1409–1416.



- 79 Y. Vazifeshenas, K. Sedighi and M. Shakeri, *Int. J. Hydrogen Energy*, 2015, **40**, 15032–15039.
- 80 S. Rau, S. Vierrath, J. Ohlmann, A. Fallisch, D. Lackner, F. Dimroth and T. Smolinka, *Energy Technol.*, 2014, **2**, 43–53.
- 81 P. Trogadas, J. I. S. Cho, T. P. Neville, J. Marquis, B. Wu, D. J. L. Brett and M. O. Coppens, *Energy Environ. Sci.*, 2018, **11**, 136–143.
- 82 X.-D. Wang, Y.-Y. Duan and W.-M. Yan, *J. Power Sources*, 2007, **173**, 210–221.
- 83 B. Ibrahimoglu, M. Z. Yilmazoglu and S. Celenk, *Fuel Cells*, 2017, **17**, 786–793.
- 84 R. Kas, A. G. Star, K. Yang, T. Van Cleve, K. C. Neyerlin and W. A. Smith, *ACS Sustainable Chem. Eng.*, 2021, **9**, 1286–1296.
- 85 D. G. Wheeler, B. A. W. Mowbray, A. Reyes, F. Habibzadeh, J. He and C. P. Berlinguette, *Energy Environ. Sci.*, 2020, **13**, 5126–5134.
- 86 P. Hao, Y. Shi, S. Li and N. Cai, *Adsorption*, 2020, **26**, 1093–1100.
- 87 E. Jeng and F. Jiao, *React. Chem. Eng.*, 2020, **5**, 1768–1775.
- 88 L. Tang, *Nat. Methods*, 2019, **16**, 18.

