



Cite this: DOI: 10.1039/d5lp00104h

Chitin nanowhiskers: a review of manufacturing, processing, and the influence of content on composite reinforcement and property enhancement†

Reshma Panackal Shibu,^{‡a} Mona Jafari,^{‡a} Sophia L. Sagala ^{‡a} and Julia L. Shamshina ^{‡a,b}

This review critically examines the potential of chitin nanowhiskers (ChNWs) as high-performance reinforcement materials for the plastics industry, with a specific emphasis on their impact on composite properties. It provides a structured overview of established ChNW preparation techniques—acid hydrolysis, oxidation, mechanical disintegration, and green solvent processing—and discusses advanced fabrication strategies for producing ChNW-reinforced composites of both natural (e.g., cellulose, chitosan, starch, hyaluronan) and synthetic (e.g., polyvinyl alcohol, poly(α -cyanoacrylate), polyaniline, polyethylene terephthalate, polypropylene) types. Key performance enhancements include increased mechanical strength, tensile strength, Young's modulus, thermal stability, and water resistance. These enhancements make ChNW-based composites suitable for real-world applications in aerospace, biomedical devices, packaging, and construction. Unlike previous reviews that emphasize only processing methods, this work identifies and highlights structure–property relationships as a central theme, bridging nanoscale morphology with macroscopic functionality.

Received 9th April 2025,
Accepted 19th June 2025

DOI: 10.1039/d5lp00104h

rsc.li/rscappliedpolym

1. Introduction

1.1. Overview of chitin and its potential as a reinforcement material

The field of nanotechnology has witnessed significant growth, with increasing focus on nanocomposites due to their improved mechanical strength, electrical conductivity, and

^aFiber and Biopolymer Research Institute, Department of Plant and Soil Science, Texas Tech University, TX 79409, USA. E-mail: jshamshi@ttu.edu

^bDepartment of Chemistry and Biochemistry, Texas Tech University, TX 79403, USA

†Electronic supplementary information (ESI) available. See DOI: <https://doi.org/10.1039/d5lp00104h>

‡These authors contributed equally.



Reshma Panackal Shibu

Reshma Panackal Shibu is a Ph.D. student and Graduate Research Assistant at Texas Tech University in Dr Shamshina's research group. She specializes in the processing, isolation, and application of biopolymers—primarily nanochitin—for advanced material synthesis. Her current research aims to create high-performance materials by harnessing the unique properties of nanochitin.



Sophia L. Sagala

Dr Sophia L. Sagala is a Postdoctoral Research Associate (PDRA) at the Fiber and Biopolymer Research Institute, Texas Tech University. She earned her Ph.D. in Chemistry in 2024, with a specialization in the synthesis, physicochemical properties, and dynamics of ionic liquids for diverse applications. Currently, she is conducting postdoctoral research in Dr Julia Shamshina's group, where her work focuses on the development of advanced biopolymer-based materials enabled by ionic liquid technologies.



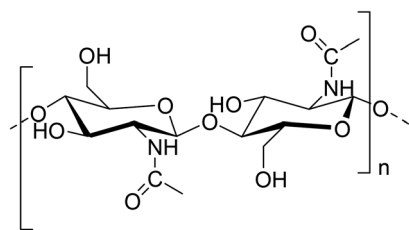


Fig. 1 Chitin structure.

thermal stability. A substantial portion of research centers on polysaccharide nanomaterials derived from renewable semicrystalline biopolymers, such as chitin, valued for their high strength, large surface area, abundance, and renewability. Chitin is a linear polysaccharide found in the exoskeletons of crustaceans, and the protective tissues of invertebrates such as insects. As a waste product, rather than a nonrenewable commodity based on fossil fuels, chitin is expected to have a low environmental impact.² Structurally, chitin is similar to cellulose, but features an acetamide group on the C-2 carbon atom replacing the hydroxyl group found in cellulose (Fig. 1).³

Chitin exists in nanosized microfibril form within the structural scaffold of crustaceans, insects, or fungi.^{4,5} Among these, crustaceans represent the largest source of chitin, with global aquaculture production of crustaceans exceeding 11.88 million metric tons (MT) per annum in 2021.⁶ Studies on the lobster cuticle (*Homarus americanus*) have demonstrated that the crustacean shells exhibit a highly organized hierarchical structure⁷ primarily composed of chitin, proteins, calcium carbonate, and smaller quantities of lipids and astaxanthin. Sugar monomers of *N*-glucosamine form the chitin chains which assemble into semicrystalline structures featuring alternating amorphous and nanocrystalline domains stabilized by hydrogen

bonds and van der Waals forces.^{8–10} These nanocrystalline units typically have diameters of $\sim 2\text{--}5\text{ nm}$.¹¹ The semicrystalline structures form chitin nanofibrils, which are further bundled into microfibrils with diameters of $\sim 20\text{--}100\text{ nm}$, oriented along the longitudinal axis. The microfibrils are encased in a sheath of proteins and assembled into elongated fibrils. The chitin–protein fibrils are organized into planar layers that stack to create a Bouligand structure, a higher-order 3D helicoidal arrangement that enables the exoskeleton to resist fractures.¹² To achieve this helicoidal structure, adjacent planar layers of chitin–protein fibrils rotate at a constant angle, completing a full 180° rotation. This Bouligand structure is also mineralized allowing it to withstand high-velocity impacts. The anisotropy ratio of the elastic modulus varies throughout the structure, decreasing progressively from 4.25 for single-crystalline chitin to 1.75 for mineralized chitin–protein nanofibrils and 1.4 in the fully developed helicoidal Bouligand structure.¹¹

To utilize chitin in nanoform from mineralized chitin–protein nanofibrils for the development of promising biomaterials, the amorphous domains must first be removed. This process, detailed in the next section, can be achieved through methods such as mechanical shearing, high-pressure homogenization, chemical or enzymatic hydrolysis, or oxidation. Once the amorphous domains are eliminated, the remaining crystalline domains can be isolated on a nanoscale. These nanosized crystalline particles can be categorized as chitin nanocrystals (ChNCs), nanowhiskers (ChNWs), or nanofibers (ChNFs), collectively referred to as nanofillers, which differ in size and morphology. ChNCs or ChNWs are rod-like, whisker-shaped particles with a crystalline structure. Their dimensions typically range from $50\text{--}500\text{ nm}$ in length and $5\text{--}20\text{ nm}$ in width, depending on the source biomass.^{13–15} ChNFs exist as long, flexible fiber networks with a fibril diameter of $2\text{--}5\text{ nm}$ and lengths extending from several hundred nanometers to several microns, making them significantly larger than ChNWs.^{14,16,17} The distinct size and shape of these nanofillers contribute to their versatility and applicability in advanced biomaterial systems.

These nanosized crystalline particles have emerged as novel nanomaterials offering unique size-dependent properties.¹⁸ Particle size influences key characteristics such as diffusivity,^{19,20} viscosity, chirality, phase transitions from isotropic to anisotropic states, immunogenicity,²¹ nanocomposite transparency,³ and light transmission,²² all of which are important for material manufacturing. These nanomaterials are lightweight, with an average density of 1.45 g m^{-3} ,^{3,19} and feature a high aspect ratio ranging from $20\text{--}100$.^{19,23–25} They also exhibit exceptional mechanical properties, including an elastic modulus of $\sim 120\text{--}150\text{ GPa}$, a transverse modulus of $\sim 15\text{ GPa}$,²⁶ Young's modulus of $\sim 40\text{ GPa}$,²⁷ and tensile strength of $\sim 170\text{ MPa}$.^{16,28} From a materials engineering perspective, chitin nanofillers are particularly appealing as renewable and sustainable materials, suitable for a diverse range of applications. These include adhesives²⁹ and coatings,^{30,31} rheology³² and barrier property modifiers,^{33,34} food/cosmetic



Julia L. Shamshina

Dr Julia L. Shamshina is an Assistant Professor at the Fiber and Biopolymer Research Institute, Texas Tech University, where she leads research on the development of advanced functional materials from biopolymers and biomass. She earned her Ph.D. in Chemistry with a focus on organic synthesis, and later completed postdoctoral training at The University of Alabama, specializing in ionic liquids. Before returning to academia in 2021, Dr Shamshina spent nearly eight years in industry, where she led the development of patentable technologies involving chitin polymer. Her current research spans both the fundamental science and industrial applications of sustainable biopolymer processing.

Before returning to academia in 2021, Dr Shamshina spent nearly eight years in industry, where she led the development of patentable technologies involving chitin polymer. Her current research spans both the fundamental science and industrial applications of sustainable biopolymer processing.



additives,³⁵ iridescent sensors,³⁶ liquid crystals (LC),³⁷ polymer reinforcements, cement³⁸ and concrete strength and durability enhancements,³⁹ and more. Furthermore, chemical modifications such as oxidation, esterification, and grafting have expanded the potential of nanochitin-based products endowing them with fascinating new properties.^{2,40} Due to their high longitudinal and transverse modulus, these particles are particularly valuable as reinforcing materials in thermoplastic and thermoset plastics.⁴¹ The incorporation of nanochitin particles into various plastics enables the production of advanced materials with superior properties. These enhanced plastics find applications across various industries, from aerospace to medical devices.

The currently used industrial fillers – fiberglass,⁴² carbon nanotubes,⁴³ graphene nanoplatelets,⁴⁴ nanoclays,^{45,46} and mineral fillers,^{23,47,48} – are plagued by several significant issues, including: (1) heterogeneity and lack of proper bonding with polymers of organic origin;^{24,49–52} (2) high density, which increases the weight of the composites,¹³ impacting applications requiring lightweight materials; (3) high abrasiveness, which causes wear and tear on processing equipment, shortening device lifespan;^{53,54} (4) high hardness, which complicates polishing and coating processes;^{55,56} (5) reduced toughness and ductility which leads to brittleness in composites;¹³ (6) high cost which limits widespread adoption in cost-sensitive applications;^{25,51} and (7) non-compostability which restricts use to non-biodegradable plastics, contributing to environmental concerns.^{24,49,52,57}

More specific problems with “traditional” filler materials are as follows. Fiberglass fiber-reinforced polymer composites (so-called GFRP composites) common in electronics, aerospace, and automotive industries⁵⁸ suffer from poor rigidity, low fatigue resistance, and weak strength perpendicular to fiber alignment (as low as 5%).⁵⁹ Manufacturing and testing are complex and specialized, and the material's density adds weight.⁶⁰ Carbon nanotube (CNT)-based nanomaterials and graphene nanoplatelets exhibit remarkable mechanical, electrical, and electron transport properties expanding their applications in areas ranging from energy harvesting to electronic skin to reinforced plastics.^{61,62} However, their high costs limit their usage. Clay and mineral filler materials (*e.g.*, silica, talc, mica, kaolin) are widely used in the plastics industry, *e.g.*, for automotive parts, multilayer films, high-barrier bottles and containers, packaging applications, furniture, and household appliances, due to their excellent mechanical properties (tensile, stress, and elongation), high thermal stability, reduction of gas and liquid permeability, improvement of dynamic mechanical performance, and flame retardancy.⁶³ However, their use is necessitated by thermoplastics' inherent limitations, including shrinkage during molding, stiffness, and they contribute to weight and brittleness.

Optimizing the benefits of fillers while minimizing their drawbacks is an essential industrial goal that significantly influences product properties, including cost, processing efficiency, shrinkage, stiffness, heat resistance, flammability, appearance, aging, and toughness.⁶⁴ Chitin nanofillers offer a

sustainable solution as they are organic, bind effectively with organic polymers, and exhibit low density, hardness, and abrasiveness, all while enhancing material stability. Due to their nanoscale dimensions and exceptionally high surface-to-volume ratios, they provide a significantly larger interface area between the matrix and filler. The addition of a small amount of ChNWs, typically 0.1–0.5 wt%, leads to marked improvements in composite properties.²

This review focuses on the potential of ChNWs as reinforcement materials for the plastic industry, emphasizing their role in improving composite properties. It will cover the methods for manufacturing ChNWs (summarized briefly due to extensive existing literature), technologies for preparing biocompatible and biodegradable chitin nanofiller composites, and factors affecting property enhancements, such as the amount and dispersion of chitin, matrix–filler interactions, and processing methods (*e.g.*, *in situ* polymerization, casting, nonaqueous solvent dispersion, and post-solution blending). Critical processing conditions, including reaction time and temperature, will also be analyzed, along with an evaluation of various plastics reinforced with nanostructured chitin and the impact of ChNWs on mechanical, thermal, and optical properties. This review excludes the use of biopolymers other than chitin (*e.g.*, chitosan, cellulose) and reinforced plastics that are mentioned in the literature but lack supporting characterization data. The novelty of this review lies in its focused analysis of structure–property relationships of nanochitin in polymer matrices—a crucial aspect largely overlooked in the current literature. Unlike previous reviews that emphasize only processing methods, this work identifies and highlights structure–property relationships as a central theme, bridging nanoscale morphology with macroscopic functionality.

Despite the extensive literature on ChNW extraction and processing, few reviews address how the intrinsic structure and surface chemistry of nanochitin directly influence composite performance. This review fills that gap by analyzing structure–property relationships, thereby offering a deeper understanding of how nanochitin's nanoscale characteristics affect dispersion, interfacial bonding, and bulk mechanical properties.

The incorporation of nanochitin into synthetic and natural polymers has yielded reinforced plastics with significant enhancements in tensile strength, thermal stability, and water vapor barrier properties—critical for applications in biomedical devices, sustainable packaging, and lightweight construction materials. These real-world applications underscore the value of ChNWs as multifunctional, sustainable additives capable of replacing mineral and petroleum-derived fillers in high-performance plastic systems.

1.2. Summary of preparation methods for nanochitin

The preparation of ChNWs primarily relies on hydrolysis, a method first developed in 1959⁶⁵ and extensively utilized since (Table 1). This process involves treating chitin polymer with hydrochloric acid (HCl) which removes disordered regions of chitin, leaving acid-resistant crystallized sections (Table 1).^{10,66–68}



Table 1 The preparation of nanochitin via acidic hydrolysis and stem explosion

Chitin source	Extraction method	Structural parameters of nanowhiskers			Ref.
		Length (nm)	Width (nm)	Aspect ratio (L/d)	
Hydrochloric acid hydrolysis					
Chitin powder ^a	Purification through the removal of residual proteins with 5% NaOH, followed by hydrolysis with 3 N HCl	200–400	10–25	8–40	40
Chitin flakes	Chitin flakes hydrolyzed with concentrated HCl ^b	ND	13.5	ND	75
Chitin	Hydrolysis with 3 N HCl	200–600	20–60	3.3–30	76
Crab α-chitin	Hydrolysis with 3 M HCl	ND	ND	ND	77
Shrimp α-chitin	Hydrolysis with 3 N HCl	206 ± 72	18 ± 5	5.8–21.4	78
Crab α-chitin	Hydrolysis with 3 N HCl	114 ± 28	15 ± 2	5.05–10.9	79
Chitin (practical grade)	Purification through the removal of residual proteins with 5% KOH, bleaching with NaClO ₂ . Then hydrolysis with 3 N HCl	ND	ND	ND	80
Chitin	Hydrolysis with 3 N HCl	100–900	20	5–45	81
Shrimp α-chitin	Hydrolysis with 3 N HCl	383	33.0	11.6	82
Chitin	Hydrolysis with 3 N HCl	20	40	0.5	83
Crab α-chitin	Purification through the removal of residual proteins with 3% KOH and bleaching with 1.7% NaClO ₂ . Then hydrolysis with 3 N HCl	100–350 (214 ± 49)	5–30 (16 ± 5.2)	13 (15 ± 5.4)	84
Chitin	Purification through the removal of residual proteins with 5% KOH. Hydrolysis with 3 N HCl	200–400	10–25	8–40	85
Squid pen β-chitin	Hydrolysis with 3 N HCl	30–250	4–22	1.36–62.5	86
Crab α-chitin	Extraction of α-chitin from the speckled swimming crabs: deproteinization with 5% NaOH, a demineralization with 7% HCl solution. Then hydrolysis with 3 M HCl	410	19	21.6	87
Shrimp α-chitin	Hydrolysis with 3 N HCl	180.9 ± 86.0	30.8 ± 9.0	2.4–12.2	88
Shrimp shells	Extraction of α-chitin from shrimp shells: demineralization with 2 N oxalic acid, bleaching with 15% H ₂ O ₂ , and deproteinization with 10% NaOH. Then hydrolysis with 3 N HCl	400	25–32	12–16	89
Chitin powder	Hydrolysis with 3 N HCl	100–200	10–40	2.5–20	90
Crab α-chitin	Hydrolysis with 3 N HCl	253 ± 100	23 ± 5	11 ± 3	1
Chitin	2× hydrolysis with 3 N HCl	209.63 ± 23.13	17.50 ± 3.75	12	91
Crab α-chitin	2× hydrolysis with 3 N HCl	590 ± 180	58 ± 14	10	92
Lobster shells	Extraction of α-chitin from lobster wastes: deproteinization with 2 M NaOH followed by demineralization with 2 N HCl and depigmentation with acetone and ethanol. Then hydrolysis with 3 N HCl	300	60	5	20
Crab α-chitin	Hydrolysis with 3 N HCl	100–200	6–8	12.5–33	24
Chitin from crab shells ^a	Purification through the removal of residual proteins with 5% KOH, bleaching with NaClO ₂ . Then hydrolysis with 3 N HCl	100–600 (~240)	4–40 (~15)	~16	25 and 51
α-Chitin flakes prepared from crab shells	Hydrolysis with 3 N HCl	114–320	8–17	6.5–40	93
α-Chitin from shells of <i>Penaeus merguensis</i> shrimps	Hydrolysis with 3 N HCl	231–969 (~549)	12–65 (~31)	~17.7	49
Chitin (practical grade)	Hydrolysis with 3 N HCl	100–500	10–50	15	94
Shells of <i>Penaeus merguensis</i> shrimps	Extraction of α-chitin from <i>Penaeus merguensis</i> shrimp: deproteinization with NaOH followed by demineralization with HCl. Then hydrolysis with 3 N HCl	200–1000	~50	4–20	13
Chitin powder from shrimp shells	Purification through the removal of residual proteins with 1 N NaOH and bleaching with NaClO ₂ . Then hydrolysis with 3 N HCl	150–800 (~417)	5–70 (~33)	17	95
Chitin powder	Hydrolysis with 3 N HCl	156–426 (~226)	16–47 (~27)	~8.3	96
<i>Riftia</i> tubes	Extraction of β-chitin from <i>Riftia</i> tubes: deproteinization with 5% KOH followed by bleaching with NaClO ₂ (no demineralization required). Then hydrolysis with 3 N HCl	200–500	15	13–33	41
α-Chitin from crab	Purification through the removal of residual proteins with 5% KOH and bleaching with NaClO ₂ . Then hydrolysis with 4 M HCl	>500 (~2200 μm)	18	120	97
Lobster wastes powder	Extraction of α-chitin from the yellow lobster wastes: deproteinization with 2 M NaOH, a demineralization with 2 M HCl solution. Then hydrolysis with 3 N HCl	200–500	5–20	15–20	68
Chitin powder from crab shells	Hydrolysis with 3 M HCl	300	60	5	98
Fresh speckled swimming crabs	Extraction of α-chitin from the speckled swimming crabs: deproteinization with 5% NaOH, a demineralization with 7% HCl solution. Then hydrolysis with 3 M HCl	150–260	8–40	~8.8	86
Coarse flakes of α-chitin from shrimp shells	Purification through the removal of residual proteins with 5% KOH and bleaching with NaClO ₂ . Then hydrolysis with 3 M HCl	100–700	3–25	25.6	99
		229–258	9–10	23–29	100



Table 1 (Contd.)

Chitin source	Extraction method	Structural parameters of nanowhiskers			Ref.
		Length (nm)	Width (nm)	Aspect ratio (L/d)	
Dried shrimp flakes (shells)	Extraction of α -chitin from dried shrimp flakes: demineralization with 0.25 M HCl, deproteinization with 1 M NaOH, and chlorine bleaching. Then hydrolysis with 3 M HCl	262 $\pm$ 122	8.7 $\pm$ 3.8	~30	101
Shrimp chitin powder	3 $\times$ hydrolysis with 3 M HCl	50–150	30–50	1–5	102
Native crab shell powder	Extraction of α -chitin from native crab shell powder: demineralization with 3 N HCl, deproteinization with 5% KOH, and bleaching with NaClO ₂ and C ₃ H ₃ NaO ₂ . Then hydrolysis with 3 M HCl	100–500	5–10	10–100	103
Sulfuric acid hydrolysis					
Fresh lobster (<i>Homarus americanus</i>)	Extraction of α -chitin from lobster (<i>Homarus americanus</i>): demineralization with 2 M HCl, depigmentation in ethanol, deproteinization with NaOH ^a . Then hydrolysis with 64 wt% H ₂ SO ₄	>500	10–40	12.5–50	72
Chitin powder	Hydrolysis with 15–40 wt% H ₂ SO ₄	446	~43	~10	104
Shrimp shell-derived α -chitin	Hydrolysis with H ₂ SO ₄	162 $\pm$ 56	22 $\pm$ 8	7.4	105
Bleached shrimp shell flakes	Extraction of α -chitin from bleached shrimp shell flakes: deproteinization with 5% KOH, bleaching with NaClO ₂ . ^c Then hydrolysis with H ₂ SO ₄ ^b	20–100	ND	ND	15
Chitin powder from shrimp shells	Hydrolysis with H ₂ SO ₄	150–250	15	10–16.67	106
Steam explosion technique					
Shrimp shell flakes	40 g of raw chitin flakes were treated with 3 N NaOH for deproteinization followed by demineralization with 2 N HCl	100–400	ND	ND	73
Chitin from prawn shell	Prawn shells waste was treated with 3 N NaOH, after that chitin was taken from the autoclave and washed with water, the suspension was then treated with 2 N HCl, treated with DI water to neutral Ph	100–400	10–50	2–40	74

^a While the manuscript claims to use chitin powder, the additional deproteinization was employed; ^b no concentration was provided in the manuscript; ^c demineralization step is erroneously claimed to be achieved with KOH treatment; ND = not determined.

Boco Technology, Inc. (Toronto, Canada) has commercialized the preparation of chitin nanowhisker-based polymer composites using hydrogen chloride (HCl) as a hydrolyzing agent and holds the exclusive patents for the preparation and use of ChNWs as a reinforcing material in plastics.^{69,70} In addition to HCl, sulfuric acid, H₂SO₄, has also been employed for hydrolysis of chitin and ChNWs synthesis (Table 1).^{71,72} An alternative to using harsh chemicals such as strong acids and alkalis is a pressure-assisted technique called steam explosion that utilizes high-pressure steam under neutral conditions accompanied by rapid decompression to precisely break down the chitin structure, fragmenting it into individualized nanowhiskers (Table 1).^{73,74}

Beyond acid hydrolysis, alternative methods for ChNW preparation include oxidation mediated by 2,2,6,6-tetramethylpiperidine-1-oxyl radical (TEMPO),^{107–109} periodate-anions,^{110–112} and ammonium persulfate (APS)¹¹³ (Table 2). In these processes, the amorphous regions of chitin are oxidized, releasing ChNWs. For instance, in TEMPO/NaBr/NaClO oxidation, the primary hydroxyl groups of chitin are selectively converted to carboxyl groups. Sodium hypochlorite (NaClO) acts as the primary oxidant, oxidizing the TEMPO radical to its *N*-oxoammonium form (TEMPO⁺). This cation reacts with dissociated primary hydroxy groups forming a covalent bond producing an intermediate structure. Subsequent cleavage of this covalent bond generates aldehyde groups and *N*-hydroxy-TEMPO molecules. Further hydration of aldehydes and dissociation of hydroxy groups under alkaline conditions result in additional covalent bond formation with TEMPO⁺, ultimately yielding carboxyl groups and *N*-hydroxy-TEMPO.¹¹⁴

Deep eutectic solvents (DESs), composed of hydrogen bond acceptors (HBAs) and hydrogen bond donors (HBDs) linked by intermolecular hydrogen bonding, have also been used for the formation of ChNWs from raw materials. The acidic HBDs facilitate demineralization while strongly electronegative HBAs enable deproteinization. DESs dissolve chitin by forming new hydrogen bonds with chitin molecules, disrupting their intra- and inter-molecular hydrogen bonds. During this process, the surface chemistry of chitin is simultaneously modified, producing acylated or deacetylated chitin derivatives. Subsequent mechanical disintegration results in ChNCs and ChNFs with distinctive yields, morphologies, and surface chemistries.¹²² Additionally, ChNWs can be formed by dissolving commercially available chitin powder in 1-allyl-3-methylimidazolium bromide ([Amim]Br) ionic liquid, followed by the mechanical breaking of the formed gelated polymeric chains.^{108,123} The dimensional characteristics of ChNWs extracted through various DES- and IL-type of treatments from diverse sources are summarized in Table 3.

Mechanical disintegration, as the term suggests, involves applying physical forces such as ultrasonication,¹²⁵ grinding,¹²⁶ high-pressure homogenization,¹²⁶ or magnetic stirring¹²⁷ under controlled conditions to break down chitin fibrils into individual nanoscale fibrils or whiskers (Table 4). It is typically part of a multistep process, preceded by deproteinization, demineralization, and depigmentation, which serve to



Table 2 The preparation of nanochitin *via* oxidation

		Structural parameters of nanowhiskers			
Chitin source	Extraction method	Length (nm)	Width (nm)	Aspect ratio (L/d)	Ref.
2,2,6,6-Tetramethylpiperidine-1-oxy-radical (TEMPO)-mediated oxidation					
Chitin powder from crab shell	TEMPO-mediated oxidation	50–500	8	6–62	107
Chitin powder from crab shell	TEMPO-mediated oxidation	242 ± 75	12.67 ± 3.43	~18	115
Chitin	TEMPO-mediated oxidation	200–400	10–15	13–40	116
Chitin	TEMPO-mediated oxidation	347.63 ± 113	5 ± 1.9	~70	117
α-Chitin powder	Purification through the removal of residual proteins with 1 M NaOH and 1 M HCl, respectively, followed by bleaching with NaClO ₂ and NaClO. Subsequent partial deacetylation (%DA 77.2%) with 30% NaOH. Then TEMPO-mediated oxidation	~544	~10	~54	118
Chitin particles from crab shells	O ₂ /laccase/TEMPO oxidation	480 ± 200	24 ± 17	11–20	119
Chitin	TEMPO oxidation followed by high-pressure homogenization	100–500	ND	ND	120
Chitin powder	Purification through the removal of residual proteins with 5% NaOH, residual minerals with 5% HCl, and bleaching with 0.3% NaClO. TEMPO oxidation followed	100–500	~5–10	10–100	121
Ammonium persulfate (APS)-mediated oxidation					
Chitin from crab shell	APS-mediated oxidation	400–500	15	26–33	113
Periodate-anions mediated oxidation					
Chitin from shrimp shells	Periodate oxidation	250–400	10–30	8–40	110
Chitin from crab shells	Periodate oxidation	227 ± 76	11.7 ± 5	~19.5	111
Chitin from shrimp shells	Periodate oxidation	241.8 ± 80	12.2 ± 5	~21	111

Table 3 IL- and DES-related methods for the preparation of nanochitin

		Structural parameters of nanowhiskers			
Chitin source	Extraction method	Length (nm)	Width (nm)	Aspect ratio (L/d)	Ref.
Deep eutectic solvents (DESS)					
Chitin from shrimp shells	Pretreatment with deep eutectic solvent (DESS) ([HBet]Cl/FeCl ₃ ·6H ₂ O), ^a followed by ultrasonication	201–268	10	20–27	124
Ionic liquids					
Chitin powder from crab shells	Dissolution in [Amim]Br, gelation, regeneration with methanol, and subsequent ultrasonication	Several hundred	20–60	ND	123
Crustacean biomass	No prior chitin isolation. Hydrolysis with 1-butyl-3-methylimidazolium hydrogen sulfate, and subsequent ultrasonication	400–600	5	80–120	14
Chitin	Hydrolysis with 1-butyl-3-methylimidazolium hydrogen sulfate, and subsequent ultrasonication	200	20	10	14

^a Betaine hydrochloride/ferric chloride hexahydrate DES; ND = not determined.

weaken the H-bonding between fibrils.^{126,128} It also promotes protonation of amino groups on the fibril surface under acidic conditions, enhancing electrostatic repulsion and facilitating fibril individualization. The nanofibrils isolated through this approach retain their native properties without significant chemical modification, thus preserving their structural integrity. The goal of gentle mechanical processing is crucial to avoid structural degradation while still allowing for efficient isolation. Furthermore, this method can yield nanofibrils with high aspect ratios, making them structurally intact and effective as reinforcing agents in composite materials.

The preparation of partially deacetylated chitin nanowhiskers (ChNWs) involves the removal of residual proteins and minerals through a series of sequential chemical pretreatments, including deproteinization and demineralization, followed by an additional treatment with concentrated NaOH or KOH solutions (commonly 10–50 wt%)^{121,127,129–131} (Table 5). This final alkaline treatment selectively removes a controlled fraction of acetyl groups at the C₂ position, introducing protonated amino groups that enhance the surface charge of the chitin fibrils. The degree of deacetylation plays a critical role in tailoring the functional properties of ChNWs, including improved dispersibility



Table 4 The preparation of nanochitin *via* mechanical disintegration

Chitin source	Extraction method	Structural parameters of nanowhiskers			Ref.
		Length (nm)	Width (nm)	Aspect ratio (L/d)	
Mechanical disintegration					
Chitin powder from crab shell	Partial deacetylation (%DA 70–77%) with 33% NaOH. Then mechanical disintegration <i>via</i> a magnetic stirring at 1200 rpm for 5 days, and ultrasonication for 1 min	250 ± 140	6.2 ± 1.1	18–40	127
Speckled swimming crab shells	Extraction of α-chitin from swimming crab shells: deproteinization with 5% NaOH, demineralization with 7% HCl, depigmentation in ethanol. Then mechanical disintegration <i>via</i> wet grinding and high-pressure homogenization	500–1000	10–80	6–100	126
α-Chitin from crab shell	Mechanical disintegration <i>via</i> ultrasonic homogenization	ND	ND	ND	125
Crab tendon (<i>Chionoecetes opilio</i>)	Extraction of β-chitin from crab tendon (<i>Chionoecetes opilio</i>): deproteinization with 0.5 M NaOH, demineralization with 0.5 M HCl. Then mechanical disintegration <i>via</i> ultrasonic homogenization	ND	ND	ND	125
Tubeworm (<i>Lamellibrachia satsuma</i>)	Extraction of β-chitin from tubeworm (<i>Lamellibrachia satsuma</i>): deproteinization with 0.5 M NaOH, demineralization with 0.5 M HCl. Then mechanical disintegration <i>via</i> ultrasonic homogenization	ND	ND	ND	125
Squid pen	Extraction of β-chitin from squid pen: deproteinization with 0.5 M NaOH, demineralization with 0.5 M HCl. Then mechanical disintegration <i>via</i> ultrasonic homogenization at pH 3–4	A few microns	3–4	>250	125
Lobster shells (<i>Homarus americanus</i>)	Extraction of α-chitin from lobster (<i>Homarus americanus</i>): demineralization with 2 M HCl, depigmentation in ethanol, deproteinization with 8–20% NaOH. Then mechanical disintegration <i>via</i> blending and micro-fluidization	200–2000	4–5.6	36–500	128

in aqueous media, increased surface reactivity, tunable morphology, enhanced swelling and antimicrobial activity, as well as the mechanical and crystalline properties, which could ensure compatibility with various polymer matrices.

1.3. Reinforced plastics with chitin

ChNWs are highly crystalline, rigid, whisker-like particles with exceptional mechanical properties.^{40,135} They are non-toxic and exhibit liquid crystalline behavior, making them ideal candidates for the preparation and reinforcement of nanocomposites with unique properties across different polymer matrices.^{82,94,135,136} A list of polymers used as a matrix reinforced with ChNWs can be found in Table 6, which provides a concise summary. Detailed explanations and discussions are presented in the subsequent sections. These polymers include various fossil fuel-based polymers, such as poly(vinyl) alcohol (PVA) and polypropylene (PP); thermoset polymers, such as epoxy resin and bio-based polyurethane; rubber, such as natural rubber (NR), styrene–butadiene rubber latex (SBR), carboxylated styrene butadiene rubber latex (XSBR), and nitrile butadiene rubber (NBR); biodegradable polyesters, such as polycaprolactone (PCL) and polylactic acid (PLA); and natural polymers, such as corn starch, gelatin, potato starch, and chitosan.^{14,18,40,108,137–139}

2. Preparation methods for chitin-reinforced plastics

The methods to prepare polymer nanocomposites reinforced with nanostructured chitin can be broadly categorized into *ex*

situ processing and *in situ* polymerization (Fig. 2). In *ex situ* preparation, nanomaterials are dispersed into a pre-existing polymer matrix, either in solid form or in solution, to create the composite. This method is particularly suited for large-scale applications. However, a significant challenge is achieving a uniform dispersion of nanomaterials within the polymer matrix, along with maintaining long-term stability against aggregation. Sonication is commonly employed to enhance the dispersion of nanomaterials in polymer solutions.

In contrast, *in situ* preparation involves synthesizing the polymer matrix in the presence of nanomaterials, allowing nanoparticles to be trapped within the polymer as it forms. This approach prevents particle agglomeration and ensures a uniform spatial distribution of nanoparticles within the polymer matrix. Additionally, *in situ* polymerization is a simple and effective method for producing nanocomposites with improved dispersion stability.

2.1. Casting

Casting is an *ex situ* method for preparing nanocomposites, where a suspension containing base polymer(s) and fillers—such as chitin nanowhiskers (ChNWs) or chitin nanofibers (ChNFs)—is poured into molds. These molds are typically made from or coated with materials such as polytetrafluoroethylene (PTFE),^{13,25,29,41,51,73,74,83,93,147} polyethylene (PE),^{40,80} or silicone rubber;³ Petri dishes are also used.^{81,148} After casting, the solvent is removed through evaporation (referred to in this review as casting-evaporation), freeze-drying, or hot pressing under controlled conditions (temperature, pressure, relative humidity) tailored to the specific properties of the polymers.



Table 5 The preparation of nanochitin from partially deacetylated chitin

		Structural parameters of nanowhiskers			
Chitin source	Extraction method	Length (nm)	Width (nm)	Aspect ratio (L/d)	Ref.
Nanowhiskers from partially deacetylated chitin (DA > 0.50)					
α -Chitin (source not shown)	Purification through the removal of residual proteins with 5% KOH, and bleaching with 0.17 wt% NaClO ₂ followed by hydrolysis with 3 N HCl to obtain ChNWs. CNWs then partially deacetylated to %DA = 60% ^a	100–500	6–15	6.7–83.3	132
Chitin flakes	Flakes were deacetylated with 40 wt% NaOH (%DA = 62% ^a) and homogenized under high pressure	120 ± 46	6.2 ± 1.5	9.6–35.3	129
Crab shells	Shells were deproteinized with 5 wt% KOH and demineralized with 7 wt% HCl. The purified chitin was deacetylated with 40 wt% NaOH (%DA = 76% ^a) and homogenized under high-pressure	114	3.4	33.5	130
Crab shells	Shells were deproteinized with 5 wt% and demineralized with 7 wt% HCl. The purified chitin was deacetylated with 30 wt% NaOH (%DA = 85% ^a) and homogenized under high pressure	230	3.8	60.5	130
Chitin powder	Purification through the removal of residual proteins with 5% NaOH, residual minerals with 5% HCl, and bleaching with 0.3% NaClO. The powder was suspended in 36% NaOH solution, and 0.15 wt% NaBH ₄ was added. Then the partially deacetylated chitin (%DA = 66% ^a) was washed to pH 7 and homogenized under high pressure	100–500	~5–10	10–100	121
Crab shells (<i>Portunus trituberculatus</i>)	Extraction of α -chitin from the speckled swimming crabs: deproteinization with 1 M NaOH, a demineralization with 1 M HCl solution, and bleaching with NaClO ₂ . Partial deacetylation in 33% NaOH (%DA = 72% ^a), then mechanical disintegration	ND	ND	ND	131
α -Chitin	Partial deacetylation in 33% NaOH (DA 0.60–0.90), then mechanical disintegration	250 ± 140	6.2 ± 1.1	15.1–76.5	127
Crab and shrimp shells	Extraction of α -chitin from the speckled swimming crabs: deproteinization with 1 M NaOH, a demineralization with 1 M HCl solution, and bleaching with 0.3% v/w NaClO ₂ . The powder was suspended in 33% NaOH solution, and NaBH ₄ was added. Then the partially deacetylated (DA not shown) chitin was washed to pH > 4 and homogenized under high pressure	800	10–50	16–80	133
α -Chitin nanocrystals from yellow lobster	α -Chitin nanocrystals from yellow lobster was extracted using microwave-assisted extraction (MAE) technique with optimal isolation condition of 1 M HCl, 10 min, and 124.75 W	314.74 ± 62.50	41.16 ± 10.92	7	134
α -Chitin nanocrystals from shrimp	α -Chitin nanocrystals from shrimp was extracted using MAE technique with optimal isolation condition of 1 M HCl, 14.34 min, and 50.21 W	386.12 ± 47.49	42.16 ± 4.62	9	134

^a In chitin, the acetylated units prevail (the degree of acetylation (%DA) is >50%), while in chitosan the deacetylated units prevail (%DA is <50%). Therefore, this material is classified as chitin by definition; ND = not determined.

In casting-evaporation method (Fig. 3), ChNWs or CNFs and the base polymer are suspended or dissolved either in the same solvent, or two miscible solvents and mixed (Table 7, entries 1–27). The resulting mixture is then cast into films, and the solvent is evaporated. Water,^{40,48,49,88,146} alcohols,³ or weak organic acids (e.g., formic acid^{149,150}) are typically used as solvents for hydrophilic polymers such as PVA, rubber latex, carboxylated styrene butadiene, polycarbonate, biopolymers – starch and hyaluronic acid, while organic solvents (e.g., toluene,¹⁴⁷ 1-methylpyrrolidinone,⁷⁶ methylene chloride⁹³) are employed for hydrophobic polymers such as polysulfone, acrylics, polylactic acid, epoxy-polymers, polyethylene, polystyrene, and polyvinyl chloride.

The solvents are often evaporated at room temperature, elevated temperatures, under vacuum, through incubation, or using a combination of these methods. For instance, various


studies by different authors on the reinforcement of PVA have reported solvent removal being conducted at room temperature, elevated temperatures, or under vacuum. The specific conditions varied depending on factors such as the solution stability and uniformity of dispersion,^{78,137} the use of additional reagents (e.g. NaOH, NaCl),^{40,80} or the types of solvents employed.^{40,49,80,83,149,150} In the casting-evaporation process, this treatment provides sufficient time for ChNWs to form a percolated network through hydrogen bonding interaction, resulting in composites with enhanced mechanical properties.

Lyophilization, or freeze-drying (Table 7, entries 28–31), is another technique used for the solvent removal to obtain solid nanocomposite films. This process involves freezing the material, followed by sublimation under reduced pressure,¹⁵¹ creating a porous network within the matrix while preserving



Table 6 Reinforced plastics with nanochitin

Polymer name	Abbreviation (if any)	Polymer type	Ref.
Acrylonitrile-butadiene rubber	NBR	Synthetic rubber/elastomer	18
Bio-based polyurethane	Bio-PUR	Renewable thermoset	139
Carboxymethyl chitosan	CMCS	Derivative of natural polysaccharide	106
Cellulose	—	Natural polysaccharide	121
(Microcrystalline) cellulose	MCC powder	Natural biopolymer, biodegradable	79
Cellulose acetate	CA	Derivative of natural polysaccharide	140
Cellulose acetate	CA	Derivative of natural polysaccharide	141
Cellulose acetate	CA	Derivative of natural polysaccharide	142
Chitosan	Cs	Natural polysaccharide	24
Corn starch	—	Natural polysaccharide	20
Epoxy resin	—	Thermoset	23
Epoxy resin	EPON828	Biodegradable synthetic resin	23
Gelatin	—	Protein	143
Gelatin	Gel	Protein	120
Gelatin	—	Protein	78
Hyaluronan	HA	Natural polysaccharide	88
Methacrylate polymer	MA	Non-biodegradable synthetic polymer	77
Natural rubber	NR	Natural occurring rubber/elastomer	25
Poly(butylene adipate-co-furanoate)	PBAF	Synthetic polyester, biodegradable	105
Poly(ethylene terephthalate)	PET	Synthetic polyester, non-biodegradable	129
Poly(ethylene terephthalate)	PET	Synthetic polyester, non-biodegradable	130
Poly(ethylene terephthalate)	PET	Synthetic polyester, non-biodegradable	89
Poly(vinyl alcohol)	PVA	Synthetic polymer, biodegradable	80
Poly(vinyl alcohol)	PVA	Synthetic polymer, biodegradable	40
Poly(vinyl alcohol)	PVA	Synthetic polymer, biodegradable	133
Poly(vinyl alcohol)	PVA/PVOH	Synthetic polymer, biodegradable	144
Poly(vinyl alcohol)/modified boron nitride	PVA	Synthetic polymer, biodegradable, inorganic	81
Poly(vinyl alcohol)/montmorillonite	PVA	Synthetic polymer, biodegradable, clay mineral	83
Poly(3-hydroxybutyrate-co-3-hydroxyvalerate)	PHBV	Natural polymer, microbially produced, biodegradable	91
Poly(ϵ -caprolactone)	PCL	Synthetic polyester, biodegradable	145
Polyaniline	PANI	Synthetic polymer, non-biodegradable	87
Polycarbonate	PC	Synthetic polyester, non-biodegradable	76
Polyethylene glycol di-methacrylate	PEGDA	Synthetic polyester, non-biodegradable	90
Poly(lactic acid)	PLA	Synthetic polyester, biodegradable	91
Polypropylene	PP	Synthetic polymer, non-biodegradable	19
Polypropylene	PP	Synthetic polymer, non-biodegradable	82
Potato starch	—	Natural polysaccharide	48
Silk	—	Sericin and fibroin proteins	131
Sodium alginate	SA	Natural polysaccharide	75
Sodium alginate	ALG	Natural polysaccharide	132
Soy protein isolate	SPI	Natural biopolymer, biodegradable	73
Soy protein isolate	SPI	Protein	74
Styrene-butadiene rubber/carboxylated styrene butadiene rubber latex (XSBR latex)	SBR/XSBR	Synthetic rubber/elastomer, non-biodegradable	146

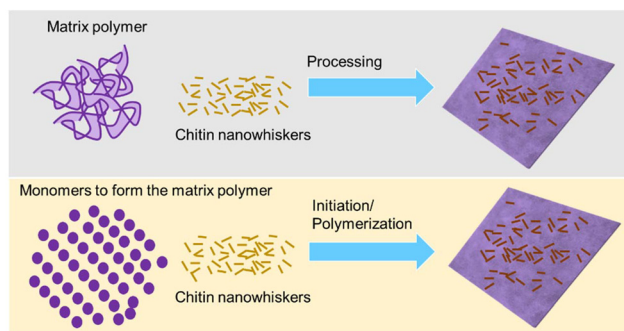Ex-situ polymerization**In-situ polymerization****Fig. 2** Schematics of *ex situ* and *in situ* polymerization.

the material's structure. Freeze-drying begins with the formation of ice crystals, which is achieved through different freezing methods. Slow freezing occurs at approximately $-20\text{ }^{\circ}\text{C}$, while fast freezing uses dry ice and organic solvents at $-78\text{ }^{\circ}\text{C}$. Ultra-fast freezing is typically done with liquid nitrogen at around $-196\text{ }^{\circ}\text{C}$.¹⁵² The size and structure of the ice crystals formed during freezing significantly influence the pore size and morphology of the composite matrix. Fast freezing generally results in smaller ice crystals, which cause minimal disruption to the material's original morphology. In contrast, slow freezing forms larger ice crystals that can penetrate the structure, potentially creating fractures or cavities, which may compromise the material's integrity. For example, under freezing conditions of $-40\text{ }^{\circ}\text{C}$ followed by lyophilization, alginate dressings with ChNWs (Table 7, entry 28) exhibited a



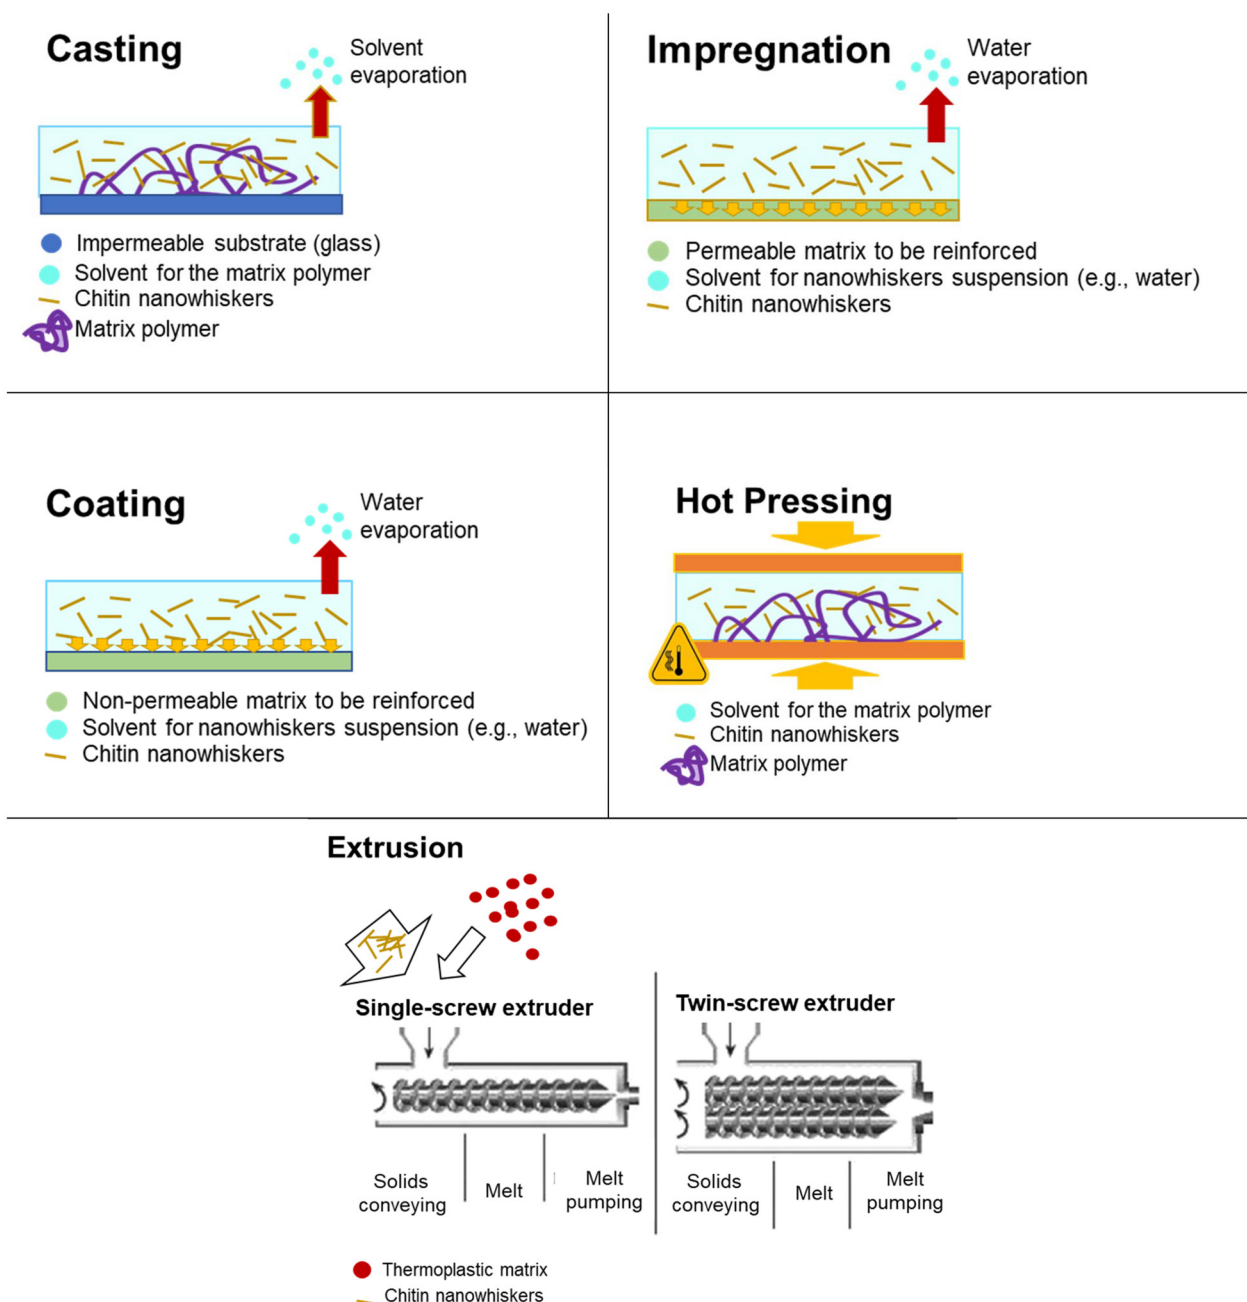


Fig. 3 Schematics of commonly used fabrication methods.

soft, porous morphology, and reduced surface roughness ($9.17 \pm 4.06 \mu\text{m}$).⁷⁵ In another study, sodium alginate (ALG)-ChNW hydrogels formed under slow freezing (-20°C) followed by lyophilization (Table 7, entry 29) developed a honeycomb structure.¹³² A directional freeze-drying which involves freezing the material in a controlled direction, often achieved by applying a temperature gradient during freezing, is also used. This method promotes the formation of aligned ice crystals, which, upon sublimation during lyophilization, result in a structured matrix with oriented channels. Thus, a directional freeze-casting method using fast freezing with liquid nitrogen

(-196°C) followed by lyophilization (Table 7, entry 30) produced structured ChNW/PVA biofoams with an oriented and continuous channel architecture.¹⁵³

2.2. Hot pressing

The hot-pressing technique is another widely used for drying chitin nanoparticle-polymer suspensions or solutions. This process involves placing the material into a mold, typically made of high heat- and pressure-resistance materials, and subjecting it to elevated temperatures and pressures simultaneously. The technique shapes and reinforces the polymer






Table 7 Preparation methods of polymer nanocomposites reinforced with nanostructured chitin

Polymers	Method	Ratio of components in final composite, g g ⁻¹	Protocol	Notes	Ref.
Casting					
<i>Casting followed by solvent evaporation</i>					
1 PVA ($M_n = 75\ 000$ Da)/ α -ChNWs	Casting	ChNWs/PVA = 2.55/97.45 ChNWs/PVA = 5.11/94.89 ChNWs/PVA = 7.66/92.34 ChNWs/PVA = 10.11/89.89 ChNWs/PVA = 12.76/87.24 ChNWs/PVA = 15.17/84.83 ChNWs/PVA = 17.74/82.26 ChNWs/PVA = 25.38/74.62 ChNPs/potato starch = 1/99 ChNPs/potato starch = 2/98 ChNPs/potato starch = 3/97 ChNPs/potato starch = 4/96 ChNPs/potato starch = 5/95 ChNWs/XSBR latex = 4.1/95.9 ChNWs/XSBR latex = 6.6/93.4 ChNWs/XSBR latex = 9.0/91.0 ChNCs/unvulc. NR = 1.0/99.0 ChNCs/unvulc. NR = 2.4/97.6 ChNCs/unvulc. NR = 4.8/95.2 ChNCs/unvulc. NR = 7.0/93.0 ChNCs/unvulc. NR = 9.0/91.0	The suspension of ChNWs in water was mixed with PVA _{aq} solution, then the resulting suspension was cast into film	Solvent removal by evaporation at room temperature	49
2 Potato starch powder/chitin nanoparticles (ChNPs)	Casting		ChNPs were dispersed in a solution of distilled water and glycerol plasticizer and ultrasonicated before adding starch. The mixture was heated at 90 °C to plasticize the starch, and then cast into a dish Chitin and latex were suspended in water, mixed at certain volume ratio, and cast	Dried in an air-circulating oven at 50 °C (~6 h)	48
3 XSBR latex/ChNWs	Casting		ChNCs were added into water, and then ultrasonicated. Meanwhile, NR latex was diluted using water. Afterward, ChNCs dispersions were added to the uniform NR latex with stirring, to obtain a homogeneous mixture. The NR/ChNCs composite films were cast in a square PTFE mold	Solvent (water) removal by evaporation, in 40 °C oven	146
4 Unvulcanized natural rubber latex (unvulc. NR)/ChNCs	Casting			Solvent removal by oven drying at 60 °C for 16 h	13
5 XSBR latex/ChNWs	Casting	ChNWs/XSBR = 1/99 ChNWs/XSBR = 2/98 ChNWs/XSBR = 3/97 ChNWs/XSBR = 4/96 ChNWs/XSBR = 5/95 ChNWs/SPI = 6/94 ChNWs/SPI/MgO = 6/93/1 ChNWs/SPI/MgO = 6/89/5	The dispersion of chitin nanowhiskers was mixed with XSBR latex with the addition of distilled water and the mixture was cast on a PTFE mold	Solvent removal by evaporation in an oven at 40 °C for 12 h and then at 60 °C under vacuum for 2 h	41
6 SPI/magnesium oxide (MgO)/ChNWs	Casting		The solution of SPI in distilled water and glycerol was mixed with required amounts of chitin nanowhiskers and MgO followed by casting the mixture on a Teflon-coated pan	Solvent removal by drying in a vacuum oven overnight and storage in a desiccator at 50% RH	73
7 Gel/dialdehyde microfibrillated cellulose (DAMFC)/ChNWs	Casting	DAMFC/gel/ChNWs = 14.90/84.30/0.80 DAMFC/gel/ChNWs = 14.74/83.55/1.71 DAMFC/gel/ChNWs = 14.62/82.82/2.56 DAMFC/gel/ChNWs = 14.36/81.36/4.28 DAMFC/gel/ChNWs = 13.71/77.66/8.63 ChNWs/gel = 1/100 ChNWs/gel = 2/98 ChNWs/gel = 4/96	The aqueous solution of gel was mixed with the aqueous suspensions of DAMFC and chitin nanowhiskers and the mixture was cast to form hydrogels	Incubating for 48 h, at 25 °C	120
8 Gel/ChNWs	Casting		The aqueous solution containing gelatin, glucose cross-linker, and glycerol plasticizer was mixed with the suspension of chitin nanowhiskers in deionized water and the mixture was cast	Solvent removal by evaporation in air-circulating fume hood at 20 °C and 56% RH for 24 h	106

Table 7 (Contd.)

Polymers	Method	Ratio of components in final composite, g g ⁻¹	Protocol	Notes	Ref.
9 Soy Protein Isolate (SPI)/ChNWs	Casting	ChNWs/SPI = 61.54/38.46 ChNWs/SPI/CTE = 38.10/23.81/38.10	The aqueous dispersion of SPI was mixed with glycerol, <i>Clitoria ternatea</i> flower extract (CTE extract), suspension of chitin nanowhiskers in water and the mixture was cast on Teflon plate	Solvent removal by evaporation in an air oven at 55 °C	74
10 Montmorillonite (MMT)/PVA/ChNWs	Casting	MMT/ChNWs = 50/50 PVA/ChNWs = 50/50 ChNWs/MMT/PVA = 33.33/33.33/33.33	The dispersions of PVA in distilled water and MMT in deionized water were mixed with chitin nanowhiskers were dispersed in deionized water and were cast on Teflon plate	Solvent removal by evaporation in air at room temperature	83
11 Polyaniline (PANI)/ZnO nanoparticles (ZnO NPs)/β-chitin ChNWs	Casting	β ChNWs/ZnO = 97.09/2.91 β ChNWs/PANI = 99.01/0.99 β ChNWs/ZnO/PANI = 96.15/2.88/0.96	The suspension of chitin nanowhiskers in distilled water was mixed with aqueous glycerol suspension of: 1. ZnO NPs; 2. PANI; 3. ZnO NPs + PANI and the suspensions were cast	Solvent removal by drying in an oven at 40 °C for 18 h and conditioning at 25 °C for at least 24 h	87
12 Carboxymethyl chitosan (CMCS) cross-linked with dextran dialdehyde (DDA)/ChNWs/	Casting	ChNWs/CMCS = 0.5/99.5 ChNWs/CMCS = 1.0/99.0	The dispersion of ChNWs in deionized water was mixed with CMCS and hydrogels were prepared by coextruding DDA solution and CMCS solution	Gelation time was monitored by a vial inversion test at 37 °C	106
13 Hyaluronic Acid (HA)/partially deacetylated chitin nanowhiskers (ChNWs, DA 73%)	Casting	ChNWs/HA = 50.00/50.00 ChNWs/HA = 90.91/9.09 ChNWs/HA = 93.75/6.25 ChNWs/HA = 97.22/2.78 ChNWs/HA = 98.04/1.96 ChNWs/PVA = 1.0/99.0 ChNWs/PVA = 1.5/98.5 ChNWs/PVA = 2.0/98.0 ChNWs/PVA = 2.5/97.5 ChNWs/PVA = 3.0/97.0	The solution of HA in deionized water was mixed with partially deacetylated ChNWs and were cast	Solvent removal by drying in an oven at 125 °C for 10 min	88
14 PVA/ChNWs	Casting		The suspension of chitin nanowhiskers was mixed with PVA aqueous solution and NaCl and the mixture was cast on a polyethylene plate. The film was then soaked in NaOH to reconstruct the hydrogen bonds	Dried under vacuum	80
15 PVA/ionic shielded chitin nanowhiskers (IsChNWs)	Casting	IsChNWs/PVA = 80/20 IsChNWs/PVA = 70/30 IsChNWs/PVA = 60/40 IsChNWs/PVA = 50/50	The dispersion of chitin nanowhiskers in HCl was mixed with aqueous solution of PVA. NaCl aqueous was then added in the mixture as an ion-shielding agent, centrifuged and cast into a film on a polyethylene (PE) plate	Solvent removal by drying at room temperature	40
16 PVA (DP = 2500) and β-ChNWs	Casting	β-ChNWs/PVA = 90/10 β-ChNWs/PVA = 80/20 β-ChNWs/PVA = 70/30 β-ChNWs/PVA = 60/40 β-ChNWs/PVA = 50/50 ^a β-ChNWs/PVA = 40/60 β-ChNWs/PVA = 30/70	β-Chitin ^a was dissolved in formic acid and mixed with PVA-formic acid solution, at room temperature, then the resulting solution was cast into film	Solvent removal by drying in an oven at 40 °C for 24 h	149






Table 7 (Contd.)

Polymers	Method	Ratio of components in final composite, g g ⁻¹	Protocol	Notes	Ref.
17 PVA/ChNWs	Casting	β-ChNWs/PVA = 80/20 β-ChNWs/PVA = 60/40 β-ChNWs/PVA = 50/50 β-ChNWs/PVA = 40/60 β-ChNWs/PVA = 20/80 ChNWs/CS = 2.97/97.03 ChNWs/CS = 5.77/94.23 ChNWs/CS = 10.90/89.10 ChNWs/CS = 13.3/86.70	β-Chitin ^b was dissolved in formic acid and mixed with PVA-formic acid solution, at room temperature, then the resulting solution was cast into film Chitosan solution in acetic acid was mixed with ChNWs aqueous suspension. To each of these suspensions, isocyanate cross-linker HDS was added and mixed. The mixtures were transferred to a mold, and gelation was allowed to occur by standing at 60 °C for 48 h. The resulting chitosan/chitin nanowhisker gels were washed in water	Solvent removal by drying in a drying oven at 60 °C for 12 h	150
18 Chitosan (CS)/ChNWs	Casting			Obtained as gels, not dried	24
19 Sorbitol polyglycidyl ether (SPE)/ChNWs/CS	Casting	ChNFs/SPE/CS = 3/66.3/30.7 ChNFs/SPE/CS = 5/64.9/30.1 ChNFs/SPE/CS = 10/61.5/28.5 (footnote: calculated w/o inclusion of hardener)	The slurry of ChNFs in aqueous acetic acid was mixed with SPE and an aqueous acetic acid solution of CS, then the resulting solution was poured into Petri dish	Dried at 80 °C for 12 h followed by post-curing at 120 °C for 6 h	148
20 NR latex/ChNWs grafted with alkenyl succinic anhydride (ASA), phenyl isocyanate (PI), and isopropenyl-α,α'-dimethylbenzyl isocyanate (TMI)	Casting	ChNWs-ASA/NR = 90/10 ChNWs-PI/NR = 90/10 ChNWs-TMI/NR = 90/10	The ChNWs grafted with alkenyl succinic anhydride (ASA) and phenyl isocyanate (PI) isopropenyl-α,α'-dimethylbenzyl isocyanate (TMI) and lyophilized NR latex (neat and treated with) were separately dispersed in toluene. The two dispersions were then mixed, after which toluene was removed in a rotavapor. The thick slurry was then cast in a Teflon mold Ac-ChNCs and PLA were added to CH ₂ Cl ₂ , and then stirred to produce a mixture which was conditioned overnight to eliminate bubbles before being cast into a Teflon mold	Drying in an oven at 60 °C for several days	147
21 PLA/acylated chitin nanocrystals (Ac-ChNCs)	Casting	Ac-ChNCs/PLA = 1/99 Ac-ChNCs/PLA = 2/98 Ac-ChNCs/PLA = 4/96 Ac-ChNCs/PLA = 6/94 Ac-ChNCs/PLA = 8/92 Ac-ChNCs/PLA = 10/90		Solvent removal by evaporation at ambient temperature for 24 h	93
22 Recycled polycarbonate (rPC, MW 45 000)/polysulfone (PSf, MW 75 000–81 000)/ChNWs	Casting	ChNWs/rPC/PSf = 2/49/49 ChNWs/rPC/PSf = 4/48/48 ChNWs/rPC/PSf = 6/47/47 ChNWs/rPC/PSf = 8/46/46 ChNWs/rPC/PSf = 10/45/45	PSf was added to a solution of rPC in 1-methyl-2-pyrrolidinone solvent (NMP). Pluronic F127 porogen and ChNWs followed by casting the mixture on a glass plate using casting knife. The fabricated membrane was then washed with water, to remove NMP	Solvent removal by washing with water at 70 °C for 1 h, and then at room temperature for 24 h. Not dried	76

Table 7 (Contd.)

Polymers	Method	Ratio of components in final composite, g g ⁻¹	Protocol	Notes	Ref.
23 Modified boron nitride modified with silane (BNSi)/ChNWs	Compounding	ChNWs/BNSi = 16.7/83.3	Pre-made BNSi and ChNWs were mixed in ethanol at room temperature with magnetic stirring for 5 h. The hybrid material was collected, cast in Petri dishes, and dried	Dried at room temperature	81
24 BNSi/ChNWs/PVA	Compounding followed by casting	ChNWs/BNSi/PVA = 0.79/3.97/95.24 ChNWs/BNSi/PVA = 2.17/10.87/86.96 ChNWs/BNSi/PVA = 3.33/16.67/80.00 ChNWs/BNSi/PVA = 4.35/21.74/73.91	Pre-made BNSi and ChNWs were mixed in ethanol at room temperature with magnetic stirring for 5 h. The hybrid material was collected. PVA was dissolved in deionized water, then hybrid materials were mixed into the PVA solution. After mixing evenly, mixtures were poured cast in Petri dishes, and dried	Dried in ventilate oven at 60 °C for 24 h	81
25 Modified boron nitride modified with polyvinylpyrrolidone (BNPVP)/ChNWs	Compounding followed by casting	ChNWs/BNPVP = 16.7/83.3	Pre-made BNPVP and ChNWs were mixed in ethanol at room temperature with magnetic stirring for 5 h. The hybrid material was collected, cast in Petri dishes, and dried	Dried at room temperature	81
26 BNPVP/ChNWs/PVA	Compounding followed by casting	ChNWs/BNPVP/PVA = 0.79/3.97/95.24 ChNWs/BNPVP/PVA = 2.17/10.87/86.96 ChNWs/BNPVP/PVA = 3.33/16.67/80.00 ChNWs/BNPVP/PVA = 4.35/21.74/73.91	Pre-made BNPVP and ChNWs were mixed in ethanol at room temperature with magnetic stirring for 5 h. The hybrid material was collected and dried	Dried in ventilate oven at 60 °C for 24 h	81
27 Epoxy resin bisphenol A diglycidyl ether (DGEBA)/ChNWs	Slurry compounding followed by casting	ChNWs/DGEBA = 0.25/99.75 ChNWs/DGEBA = 0.50/99.50 ChNWs/DGEBA = 0.75/99.25	The suspension of chitin nanowhiskers was mixed with the solution of DGEBA in ethanol through slurry compounding followed by the addition of triethylenetetramine (TETA) curing agent, and the mixture was cast on silicone rubber molds	Post curing at 100 °C for 24 hours	3
28 ALG/α-ChNWs	n Casting	ChNWs/ALG = 33.3/66.7	The ChNWs suspension in deionized water was mixed with sodium alginate and glycerol and were cast	Solvent removal by overnight freezing at -40 °C and lyophilization at 0.11 mbar for 8 h	75
29 ALG/partially deacetylated α-ChNWs (DDA 0.40 ± 0.03)	Casting	ChNWs/ALG = 2.5/97.5 ChNWs/ALG = 7.5/92.5 ChNWs/ALG = 14.5/85.5	The partially deacetylated ChNWs aqueous suspension was mixed with concentrated solutions of ALG and were cast. To isolate the ALG-ChNW microgels, the ALG-ChNW hydrogel was diluted with water, centrifuged, washed with water, and freeze-dried	Solvent removal by drying by refrigerator at 4 °C for 2 days, and freeze-dried	132



Table 7 (Contd.)

Polymers	Method	Ratio of components in final composite, g g ⁻¹	Protocol	Notes	Ref.
30 PVA/ChNWs	Casting	ChNWs/PVA = 25/75 ChNWs/PVA = 40/60 ChNWs/PVA = 50/50	The chitin nanowhisker suspension was mixed with PVA solution and added with water to reach the final volume of 100 mL. The mixture was gently stirred at room temperature for 4 h, then transferred into a glass vial, and frozen by two methods	Two methods of solvent removal: 1. Plunging in liquids N ₂ for 5 min (−196 °C) 2. Directional freezing in which only the bottom vial containing samples was in contact with liquid N ₂ , followed by freeze-dried for 24 h	153
31 PVA/partially deacetylated α-ChNWs	Casting	ChNWs/PVA = 20/80 ChNWs/PVA = 30/70 ChNWs/PVA = 40/60 ChNWs/PVA = 50/50 ChNWs/PVA = 60/40	The partially deacetylated ChNWs suspension in deionized water and acetic acid was mixed with the suspension of PVA in deionized water followed by adding glutaraldehyde as the cross linker and finally the well mixed suspensions were molded	Solvent removal by freezing at −20 °C for about 24 h, followed by thawing for 12 h for three continuous cycles (repeating freeze–thawing cycle)	133
<i>Casting followed by hot pressing</i>					
32 Poly-(ε-caprolactone) (PCL)/ChNWs	Casting	ChNWs/PCL = 0.5/99.5 ChNWs/PCL = 1.0/99.0 ChNWs/PCL = 2.5/97.5 ChNWs/PCL = 5.0/95.0 ChNWs/PCL = 10.0/90.0	The colloidal microcrystalline dispersion of chitin nanowhiskers in water was mixed with the suspension of PCL and were molded	Freeze drying and hot pressing at 21 bar (2.1 MPa) and 100 °C	97
33 NR latex/ChNWs	Casting	ChNWs/NR = 2/98 ChNWs/NR = 5/95 ChNWs/NR = 10/90 ChNWs/NR = 15/85 ChNWs/NR = 20/80	The aqueous suspensions of chitin whiskers and NR latex were mixed and cast in a Teflon mold	Solvent removal by either one: 1. evaporation (unvulcanized NR) at 40 °C for 10–15 days; 2. hot pressing (pre-vulcanized NR) at 138 bar (13.8 MPa) for 2 min at 100 °C; and 3. (pre-vulcanized NR) freeze drying	25 and 51
34 SPI plastics/ChNWs	Casting	ChNWs/SPI = 5/95 ChNWs/SPI = 10/90 ChNWs/SPI = 15/85 ChNWs/SPI = 20/80 ChNWs/SPI = 25/75 ChNWs/SPI = 30/70 ChNP/PLA = 0.5/99.5 ChNP/PLA = 1/99 ChNP/PLA = 2/98 ChNP/PLA = 3/97	The homogenous dispersions of SPI and various content of ChNWs were freeze-dried and 30% glycerol was added. The resulting mixture were hot pressed, and slowly cooled to room temperature Nano-chitin was mixed with PLA containing 20 wt% glycerol triacetate and the resulting mixture was hot-pressed into films The self-bonded composite films were obtained by mixing cellulose nanofibers and chitin nanocrystals at 15 000 rpm, 10 min to ensure well-dispersed slurry. The wet mats were dried at 50 °C and molded	Hot pressing at 20 MPa, for 10 min at 140 °C	155
35 Polylactic acid (PLA)/chitin nanoparticle (ChNP)		ChNP/PLA = 0.5/99.5 ChNP/PLA = 1/99 ChNP/PLA = 2/98 ChNP/PLA = 3/97		Hot pressing at 15 kPa and 190 °C	156
36 Cellulose nanofibers/ChNC		ChNC/cellulose = 1/99 ChNC/cellulose = 2.5/97.5 ChNC/cellulose = 5/95 ChNC/cellulose = 7.5/92.5 ChNC/cellulose = 9/91 ChNC/cellulose = 10/90		Water removal by vacuum filtration. Hot pressing at 18 MPa, for 15 min, at 110 °C	154
<i>Casting followed by the combination of freeze-drying and hot pressing</i>					
37 Unvulc. NR/ChNWs	Casting	ChNWs/unvulc. NR = 5/95 ChNWs/unvulc. NR = 10/90 ChNWs/unvulc. NR = 15/85 ChNWs/unvulc. NR = 20/80	The aqueous suspension of ChWs and unvulc. NR were mixed, stirred and then cast to obtain solid composite films	Freeze-drying and subsequent hot pressing	51



Table 7 (Contd.)

Polymers	Method	Ratio of components in final composite, g g ⁻¹	Protocol	Notes	Ref.
38 PCL/ChNWs	Casting	ChNWs/PCL = 0.5/99.5 ChNWs/PCL = 1/99 ChNWs/PCL = 1.5/98.5 ChNWs/PCL = 5/95 ChNWs/PCL = 10/90	The colloidal chitin dispersion was mixed with the suspension of latex and cast to obtain composite films	Freeze-drying and hot pressing at 21 bar, 100 °C	97
39 PVA/α-ChNWs	Casting	ChNWs/PVA = 0.74/99.26 ChNWs/PVA = 1.48/98.52 ChNWs/PVA = 2.96/97.34 ChNWs/PVA = 7.40/92.60 ChNWs/PVA = 14.8/85.20 ChNWs/PVA = 22.2/77.80 ChNWs/PVA = 29.6/70.40	The dispersion of ChNWs in HCl were mixed with a solution of PVA in distilled water and were cast onto a plastic mold. After solvent removal, ChNWs-reinforced PVA films were heat treated in an autoclave at 110 °C for 5 min	Solvent removal by drying at 40 °C for 24 h	95
40 Epoxy resin bisphenol A diglycidyl ether (DGEBA)/ChNWs	Casting	ChNWs/DGEBA = 0.8/98.2 ChNWs/DGEBA = 1.0/99.0 ChNWs/DGEBA = 1.5/98.5 ChNWs/DGEBA = 2.0/98.0 ChNWs/DGEBA = 3.0/97.0	The CNWs ethanol suspension was mixed with DGEBA epoxy, ethanol was evaporated, and small amount of [C ₂ mim][OAc] IL was added as a dispersion aid/plasticizer. Then the solution was degassed in a vacuum chamber and cast in customized two-part rectangular glass molds to a sheet	Dried in an oven at 100 °C for 24 h to complete the cure	22
41 PVA (DP 4300)/ChNWs	Gel casting	ChNWs/PVA = 76.92/23.08 ChNWs/PVA = 83.33/16.66 ChNWs/PVA = 90.91/9.09 ChNWs/PVA = 95.24/4.76 ChNWs/PVA = 99.01/0.99	The dispersion of chitin in [Amim]Br ionic liquid (IL) was heated at 100 °C for 48 hours to dissolve chitin and form a gel. A solution of PVA in hot water was then mixed to the gel. The resulting mixture was then soaked in methanol was added to the mixture, followed by sonication, filtration and finally Soxhlet extraction with methanol	Dried under reduced pressure at 60 °C for 12 h	123
42 SPE epoxy/ChNFs/chitosan (CS)	Compression molding then curing	ChNFs/SPE/CS = 3/78.7/18.3 ChNFs/SPE/CS = 5/77.1/17.9 ChNFs/SPE/CS = 10/73.1/16.9 (footnote: calculated without inclusion of hardener)	The slurry of SPE and CNFs in aqueous acetic acid were mixed with a solution of CS in acetic acid, poured on a Petri dish made of stainless steel, and stirred using a spatula on a hot plate of 100–140 °C while distilling most of the solvent. Polyamidoamine- (PAA- or PEA-) hardeners were added to the reaction mixture, and stirred at 100 °C for 15 min. The mixture was compression-molded at 6 MPa for 6 h to form a cured biocomposite	The mixture was dried at 80 °C for 12 h and then post-cured at 120 °C for 6 h in an electric oven	148





Table 7 (Contd.)

Polymers	Method	Ratio of components in final composite, g g ⁻¹	Protocol	Notes	Ref.
43 SPE epoxy resin/ChNFs/lysine (Lys)	Compression molding/casting	ChNFs/SPE/Lys = 3.00/82.94/14.07 ChNFs/SPE/Lys = 5.00/81.23/13.78 ChNFs/SPE/Lys = 10.00/76.95/13.05	The dispersion of ChNFs in aqueous acetic acid were mixed with a solution of SPE and lysine (acting as a curing agent) in ethanol and aqueous acetic acid. The suspension was poured on a Petri dish and stirred using a spatula on a hot plate of 100–110 °C while distilling most of the solvent. The mixture was compression-molded at 3 MPa for 3 h to form SPE/Lys/ChNFs	Cured at 60 °C for 24 h and subsequently at 140 °C for 6 h in a vacuum oven	161
44 SPE epoxy resin/ChNFs/arginine (Arg)	Compression molding/casting	ChNFs/SPE/Arg = 3.00/84.79/12.21 ChNFs/SPE/Arg = 5.00/83.05/11.95 ChNFs/SPE/Arg = 10.00/78.68/11.32	The dispersion of ChNFs in aqueous acetic acid were mixed with a solution of SPE and arginine (acting as a curing agent) in ethanol and aqueous acetic acid. The suspension was poured on a Petri dish and stirred using a spatula on a hot plate of 100–110 °C while distilling most of the solvent. The mixture was compression-molded at 3 MPa for 3 h to form SPE/Arg/ChNFs.	Cured at 60 °C for 24 h and subsequently at 140 °C for 6 h in a vacuum oven	161
45 SPE epoxy resin/ChNFs/cysteine (Cys)	Compression molding/casting	ChNFs/SPE/Cys = 3.00/84.79/12.21 ChNFs/SPE/Cys = 5.00/83.05/11.95 ChNFs/SPE/Cys = 10.00/78.68/11.32	The dispersion of ChNFs in aqueous acetic acid were mixed with a solution of SPE and cysteine (acting as a curing agent) in ethanol and aqueous acetic acid. The suspension was poured on a Petri dish and stirred using a spatula on a hot plate of 100–110 °C while distilling most of the solvent. The mixture was compression-molded at 3 MPa for 3 h to form SPE/Cys/ChNFs	Cured at 60 °C for 24 h and subsequently at 140 °C for 6 h in a vacuum oven	161
Compounding					
46 Acrylonitrile butadiene rubber (NBR)/ChNWs	Masterbatch preparation followed by compounding	ChNWs/NBR = 3.84/96.16 ChNWs/NBR = 7.41/92.59 ChNWs/NBR = 10.71/89.29	The ChNWs were dispersed in NBR latex and were coagulated using CaCl ₂ solution to obtain sheets. The masterbatch was then compounded with solid NBR and other vulcanizing agents to obtain NBR/ChNWs composites	Solvent removal by drying in vacuum at 70 °C for 48 h and conditioning for 24 h	18
47 Eucalyptus pulp/partially deacetylated chitin nanowhiskers (DeChNWs)/TEMPO-oxidized chitin nanowhiskers (TOChNWs)	Compounding	ChNWs/dry pulp = 0.2/99.8 ChNWs/dry pulp = 0.4/99.6 ChNWs/dry pulp = 0.6/99.4 ChNWs/dry pulp = 0.8/99.2 ChNWs/dry pulp = 1.0/99.0 ChNWs/dry pulp = 2.0/98.0 ChNWs/dry pulp = 5.0/95.0	The bleached eucalyptus pulp soaked in water was dispersed with a standard pulp defibrilizer and chitin nanowhiskers were added. The mixture was compounded and made into handsheets by drying	Equilibrating at 23 °C and 50% RH for at least 24 h	121

Table 7 (Contd.)

Polymers	Method	Ratio of components in final composite, g g ⁻¹	Protocol	Notes	Ref.
48 Epoxy resin bisphenol A diglycidyl ether (DGEBA)/ChNWs	Slurry compounding then curing	ChNWs/DGEBA = 0.5/99.5 ChNWs/DGEBA = 1.0/99.0 ChNWs/DGEBA = 2.5/97.5	Suspension of ChNWs in ethanol was added into DGEBA and the mixture was heated at 60 °C. Then amine hardener was added into the ChNWs/DGEBA mixture and homogenized. The mixture was degassed under vacuum at 80 °C for 1 h and cured	Cured at 100 °C for 2 h and at 200 °C for 5 h	27
Melt extrusion					
49 Polypropylene (PP)/ChNWs	Twin screw micro compounding	ChNWs/PP = 1/99 ChNWs/PP = 2/98 ChNWs/PP = 5/95 ChNWs/PP = 10/90	The chitin nanowhiskers was added into the mixture of PP and maleated PP (MAPP) and compounded using co-rotating twin screw micro compounding followed by compression molding to obtain composite films	Compression molding at 180 °C and 1000 psi	19
50 PLA/polyhydroxybutyrate-co-valerate (PHBV)/ChNWs	Twin screw micro compounding	ChNWs/PLA = 0.5/99.5 ChNWs/PLA = 1.0/99.0 ChNWs /PLA = 2.0/98.0 ChNWs /PLA = 5.0/95.0	The dispersions of ChNWs in <i>N,N</i> -dimethyl acetamide (DMAc) solution and oven-dried PLA were blended in co-rotating twin screw micro compounding and molded into a dog-bone shaped tensile specimen	Sealing in high pressure chambers at 4.14 MPa for 48 h followed by soaking at 95 °C for 10 s	91
51 ChNWs/PLA/PHBV	Twin screw micro compounding	ChNWs/PLA/PHBV = 0.5/84.6/14.9 ChNWs/PLA/PHBV = 1.0/84.5/14.8 ChNWs/PLA/PHBV = 2.0/84.4/14.7 ChNWs/PLA/PHBV = 5.0/80.7/14.3	The dispersions of ChNWs in <i>N,N</i> -dimethyl acetamide (DMAc) solution and oven-dried PLA and PHBV pellets were blended in co-rotating twin screw micro compounding at 180 °C with the screw speed of 200 rpm for 10 min, and shaped into a dog-bone shaped tensile specimen	Compositions were air cooled, cut into pellet-sized pieces, and oven dried at 45 °C for 24 h	91
52 PLA/α-ChNWs	Melt blending/batch-foaming	ChNWs/PLA = 2/98 ChNWs/PLA = 5/95 ChNWs/PLA = 1/99	PLA was compounded with chitin nanocomposite using benchtop twin screw compounding to yield compatibilized chitin nanocomposite. Then the foams of PLA–chitin composites were prepared by two-step batch foaming technique using CO ₂	Heated in hot water at 95 °C for a period of 20 s and then quenched in cold water	92
53 PLA grafted with maleic anhydride (PLA-(grafted)-MA)/α-ChNWs	Melt blending/batch-foaming	ChNWs/(PLA-(grafted)-MA) = 2/98 ChNWs/(PLA-(grafted)-MA) = 5/95 ChNWs/(PLA-(grafted)-MA) = 1/99	PLA-(grafted)-MA with peroxide-based free radical initiator were compounded with chitin nanocomposite and PLA using benchtop twin screw compounding to yield compatibilized chitin nanocomposite. Then the foams of PLA–chitin composites were prepared by two-step batch foaming technique using CO ₂	Heated in hot water at 95 °C for a period of 20 s and then quenched in cold water	92




Table 7 (Contd.)

Polymers	Method	Ratio of components in final composite, g g ⁻¹	Protocol	Notes	Ref.
54 PLA (M_w , 170 000)/chitin nanofibrils (ChNFs)/polyethylene glycol (PEG, M_w 400, and 8000)	Extrusion	PEG ₄₀₀ /ChNFs/PLA = 10/2/88 PEG ₈₀₀₀ /ChNFs/PLA = 10/2/88 PEG ₄₀₀ /ChNFs/PLA = 1/2/97 PEG ₄₀₀ /ChNFs/PLA = 5/2/93 PEG ₄₀₀ /ChNFs/PLA = 10/5/85 PEG ₄₀₀ /ChNFs/PLA = 10/12/78	The dispersions of chitin nanofibrils (ChNFs) in water were mixed with poly(ethylene glycol) (PEG) and dried by water evaporation to prepare a solid pre-composite. The pre-composite is then added to PLA in the injection molding extruder to obtain transparent nanocomposites. The dispersions of ChNFs or ChNFs in distilled water with glycerol plasticizer were mixed with starch using micro compounder, then molded using an injection molding. The ChNFs (pre-treated in water, polyethylene glycol (PEG), or polyethylene oxide (PEO) followed by freeze-drying), were mixed with PLA powder followed by blending, compounding, and ultimately extrusion.	Injection molding at 180 °C, 650 bars holding time of 15 s, mold temperature of 35 °C	165
55 Corn starch granules(α -ChNFs/ α -ChNCs	Melt-mixing in micro compounder, then injection molding	ChNFs or ChNCs/corn starch = 5/95 ChNFs or ChNCs s/corn starch = 10/90 ChNFs or ChNCs/corn starch = 15/85 ChNFs or ChNCs/corn starch = 20/80		Conditioning at 50% relative humidity (RH) at 25 °C for 7 days	20
56 PLA(α -ChNFs	Extrusion with Minilab (small twin-screw extruder)	ChNFs/PLA = 10/90 ChNFs/PLA = 20/80 ChNFs/PLA = 30/70 ChNFs PLA = 40/60 ChNFs/PLA/PEG or PEO = 10/80/10 ChNFs/PLA/PEG or PEO = 20/70/10 ChNFs/PLA/PEG or PEO = 30/60/10 ChNFs/PLA/PEGorPEO = 40/50/10		Not conducted	26
In situ polymerization					
57 Poly(butylene adipate-co-furanoate) (PBAF) made <i>in situ</i> from adipic acid (AA) and dimethyl 2,5-furandicarboxylate (DMFD)/sulfated α -chitin nanowhiskers (S-ChNFs)	<i>In situ</i> polymerization, then hot-pressing	S-ChNFs/(AA + DMFD) = 0.1/99.9 S-ChNFs/(AA + DMFD) = 0.3/99.7 S-ChNFs/(AA + DMFD) = 0.7/99.3 S-ChNFs/(AA + DMFD) = 1.0/99.0	Respective amount of S-ChNW in butanediol were added to a liquid mixture of AA and DMFD monomers, and titanium(IV) butoxide (TBT, 97%) catalyst by heating at 180 °C for 2 h for transesterification, then increased to 210 °C for 2 h, and to 240 °C for complete polymerization, finally polycondensation for <i>in situ</i> formation of PBAF.	Films were prepared by pressing the <i>in situ</i> composites at 150 °C at 10 Pa for 5 min and then quenching in cold water	105
58 Polyethylene glycol dimethacrylate (PEGDA, M_n = 6000 Da)/CS (M_w = 100 000 Da)/ChNFs	<i>In situ</i> free radical polymerization using UV light (365 nm, 50 mW cm ⁻²)	PEGDA/CS = 88.24/11.76 PEGDA/CS/ChNFs = 68.18/9.09/22.73	<i>In situ</i> free radical polymerization of PEGDA/chitosan/ChNFs aqueous suspension initiated by UV light	Not conducted	90
59 Poly(butylene adipate-co-terephthalate) (PBAT) made <i>in situ</i> from adipic acid (AA) and dimethylterephthalate/sulfated α -chitin nanowhiskers (S-ChNFs)	<i>In situ</i> polymerization, then hot-pressing	S-ChNFs/(AA + DMT) = 0.1/99.9 S-ChNFs/(AA + DMT) = 0.3/99.7 S-ChNFs/(AA + DMT) = 0.7/99.3 S-ChNFs/(AA + DMT) = 1.0/99.0	Respective amounts of S-ChNW in butanediol were added to a mixture of AA and DMT monomers, and titanium(IV) butoxide (TBT, 97%) catalyst by heating at 180 °C for 2 h for transesterification, then increased to 210 °C for 2 h, and to 240 °C for complete polymerization, finally polycondensation for <i>in situ</i> formation of PBAT	Films were prepared by pressing the <i>in situ</i> composites at 150 °C at 10 Pa for 5 min and then quenching in cold water	105



Table 7 (Contd.)

Polymers	Method	Ratio of components in final composite, g g ⁻¹	Protocol	Notes	Ref.
60 PANI-grafted (g)/chitin nanocrystals (ChNCs)	<i>In situ</i> oxidative polymerization	ChNC/PANI = 14.3/85.7 ChNC/PANI = 50/50	PANI-g-ChNCs were prepared <i>via in situ</i> oxidative polymerization of aniline monomers with ammonium persulfate serving as the oxidant and HCl as an acid dopant for PANI. The ChNC suspension was sonicated for 30 s in acidic HCl solution, after which the corresponding amount of aniline was added. The suspension was centrifuged, washed several times with 0.5 M HCl to remove byproducts and remaining agents, and the pH was adjusted to 3. For the preparation of PANI-g-ChNC/latex nanocomposites the desired amounts of PANI-g-ChNCs suspension were sonicated for 20 s then added to 1.5 g of latex under stirring, and cast into Teflon mold	Dried at room temperature for 24 h	29
3D printing					
61 Methacrylate (MA)/ α -chitin photocurable nanowhiskers (pChNWs, DDA ~6.4%, M_w ~150 kDa)	Stereolithography (SLA) printing <i>via</i> radical photopolymerization	pChNWs/MA = 0.2/99.8 pChNWs/MA = 0.5/99.5 pChNWs/MA = 1.0/99.0	The ChNWs of varying amounts were mixed with the MA resin and underwent SLA printing <i>via</i> radical photopolymerization to form 3D-printed nanocomposites	Solvent was removed by drying in vacuum oven at 60 °C for 15 min	81
62 MA resin/ChNWs	Modified slurry compounding	ChNWs/MA = 0.5/99.5 ChNWs/MA = 1.0/99.0 ChNWs/MA = 1.5/98.5	The dispersions of ChNWs in ethanol was mixed with MA-ethanol solution and the nanocomposite resin obtained were 3D printed	The solvent was removed by drying in vacuum at 60 °C	1
Gel spinning and electrospinning					
63 PVA/ α -ChNWs	Gel spinning	ChNWs/PVA = 3/97 ChNWs/PVA = 5/95 ChNWs/PVA = 10/90 ChNWs/PVA = 15/85 ChNWs/PVA = 20/80 ChNWs/PVA = 30/70	The dispersion of ChNWs and water was mixed with a solution of PVA in distilled water in the rotary mixer and fibers were fabricated using a laboratory-scale gel-spinning apparatus	Cooling in a methanol bath for 24 h followed by solvent removal by evaporation for 48 h	94
64 PVA (M_w = 78 000)/ α -ChNWs	Electrospinning	ChNWs/PVA = 2.5/97.5 ChNWs/PVA = 5.0/95.0 ChNWs/PVA = 7.5/92.5	The dispersions of ChNWs was mixed with a solution of PVA in distilled water and electrospun using a single-needle electrospinning to form nanofibrous membranes	Solvent removal by drying at 155 °C for 15 min	96
65 Cellulose acetate (CA M_n $\approx$ 30 000 Da)/ChNWs	Electrospinning	ChNWs/CA = 0.5/99.5 ChNWs/CA = 2.5/97.5	The solution of CA in acetone and DMAc was mixed with ChNWs and electrospun using a single-needle electrospinning to form nanofiber mats	Solvent removal by vacuum drying at ~25 °C and conditioned at ~53% RH	142





Table 7 (Contd.)

Polymers	Method	Ratio of components in final composite, g ⁻¹	Protocol	Notes	Ref.
66 PVA ($M_w = 75\,000$ Da)/ α -ChNWs	Electro-spinning	ChNWs/PVA = 2.55/97.45 ChNWs/PVA = 5.11/94.89 ChNWs/PVA = 7.66/92.34 ChNWs/PVA = 10.11/89.89 ChNWs/PVA = 12.76/87.24 ChNWs/PVA = 15.17/84.83 ChNWs/PVA = 17.74/82.26 ChNWs/PVA = 25.38/74.62	The suspension of ChNWs in water was mixed with PVA _{aq} solution, then the resulting suspension was electrospun	Solvent removal by evaporation at room temperature for 3 days	49
Coating					
67 Polyethylene terephthalate (PET)/ChNWs/cellulose nanocrystals (CNCs)	Spray-coating	ChNWs/CNCs = 50/50 coated in sequence on PET film	Two separate dispersions of ChNWs and CNCs in water were spray-coated on PET film in sequence, to form a bilayer-coated PET film	Solvent removal by drying at room temperature for 24 h	129
68 Cellulose acetate (CA)/ α -ChNWs/CNCs	Spray-coating	ChNWs/CNCs = 50/50 coated in sequence on CA film	Two separate dispersions of ChNWs and CNCs in water were coated on the CA substrate to form a bilayer-coated CA film	Solvent removal by drying at room temperature for 96 h	140
69 CA/ChNWs/cellulose nanocrystals (CNCs)	Spray coating followed by thermal treatment	ChNWs/CNC = 50/50 coated in sequence on CA film	Two separate dispersions of ChNWs and CNCs in water were spray-coated on CA-film, to form a bilayer-coated CA film	Solvent removal by drying at room temperature for 24 h and conditioned at ~53% RH	141
70 α -ChNWs/CS/PET	Blade-coating	ChNWs/CS = 66.66/33.33 and ChNWs/CS = 50.0/50.0 and ChNWs/CS = 33.33/66.66 spread over PET substrate	The dispersion of ChNWs and CS (mixed together) in water was spread over PET substrate	Solvent removal by drying at 60 °C for 30 min	130
71 α -ChNWs/PET	Blade-coating	ChNWs spread over PET substrate	The dispersion of ChNWs in water was spread over PET substrate	Solvent removal by drying at 60 °C for 30 min	130
72 α -Short chitin nanowhiskers (SChNWs 114 nm) or α -long chitin nanowhiskers (LChNWs, 230 nm)/chitosan (CS)/polyethylene terephthalate (PET)	Blade-coating	SChNWs/CS = 66.66/33.33 and SChNWs/CS = 50.0/50.0 and SChNWs/CS = 33.33/66.66 LChNWs/CS = 66.67/33.33 LChNWs/CS = 50/50	The dispersion of (ChNWs + CS) mixed together spread over PET substrate pre-coated with CNC in layer-by-layer (LBL) fashion	Solvent removal by drying at 60 °C for 30 min	130
73 PP/ α -ChNWs/TEMPO cellulose nanofibers (TCNFs)	Layer-by-Layer (LBL) coating	LChNWs/CS = 33.3366.67 spread over PET substrate pre-coated with CNC ChNWs and TCNFs coated in sequence on PP film, ratio not shown	The ultraviolet/ozone treated PP substrates were alternately immersed into two separate dispersions: ChNWs and TCNF in water forming bi-layered coated films	Solvent removal by drying at 80 °C for 24 h	82
74 PET/ α -ChNWs/cellulose nanofibers (CNFs)	Layer-by-Layer (LBL) coating	ChNWs and CNFs coated in sequence on PET film, ratio not shown	The dispersion of ChNWs in aqueous acetic acid and CNFs in water were sprayed on the upper surface of the PET substrate in a zigzag pattern completing a single bilayer structure	Solvent removal by hot-pressing at 80 °C at 32 MPa for 10 min	89
Impregnation					
75 PVA (99% hydrolyzed)/ChNFs	Impregnation	ChNFs/PVA = 60/40	ChNFs dispersed in water were vacuum filtered to make a wet sheet. After drying, ChNFs pre-made film was impregnated into the pre-prepared PVA _{aq} solution for 12 h as a sandwich-like structure	Solvent removal by drying in an oven at 55 °C for 12 h	16

Table 7 (Contd.)

Polymers	Method	Ratio of components in final composite, g g ⁻¹	Protocol	Notes	Ref.
76 Gelatin (gel)/ChNFs	Immersion	ChNFs/gel = 73.0/27.0 ChNFs/gel = 62.5/37.5 ChNFs/gel = 50.2/49.8	ChNF suspensions were vacuum filtered to prepare a wet film. The gelatin powder was dissolved in distilled water at different concentrations. Afterwards the wet gelatin films were immersed into gelatin solutions and kept at 60 °C for 12 h, respectively	The ChNF/gelatin films were dried at room temperature for 2 days	143
77 PVA ($M_w = 26\,000$ Da)/ α -ChNWs	Solution impregnation	Sandwich-like structure, ratio not shown	ChNWs aqueous suspension was cast, dried and ChNWs film was obtained. After that, ChNWs pre-made film was impregnated in the pre-prepared PVA _{aq} solution for 12 h as a sandwich-like structure	Solvent removal by evaporation at room temperature overnight, followed by drying at 40 °C for 12 h	52
78 Microcrystalline cellulose (MCC, $M_w = 1 \times 10^5$)/ α -ChNWs	Impregnation	ChNWs/MCC = 1.0/99.0 ChNWs/MCC = 2.5/97.5 ChNWs/MCC = 5.0/95.0 ChNWs/MCC = 10.0/90.0	The dispersion of ChNWs was introduced into cellulose solutions in phosphoric acid at the stage of cellulose regeneration	The obtained material was a gel, that was freeze-dried and vacuum dried for the characterization	79

^a ChNWs are the essential component rather than a reinforcement filler. ^b Chitin is not usually soluble in acids, so it was likely a misleading title, and the paper might have used chitosan.

composites into a more compact and structurally sound form. In general polymer applications, heat is often provided by induction or resistance heating, with temperatures reaching up to 2400 °C and pressures up to 50 MPa. However, for chitin nanocomposite fabrication, much lower temperatures and pressures are employed, to prevent chitin nanomaterials from degradation.¹⁵⁴ Examples include 100 °C and 2.1–13.8 MPa (Table 7, entries 32–33),^{25,51,97} 140 °C and 20 MPa (Table 7, entry 34),¹⁵⁵ 190 °C and 15 kPa (Table 7, entry 35),¹⁵⁶ and 110 °C and 18 MPa (Table 7, entry 36).¹⁵⁴ This technique improves mechanical performance by densification of materials and eliminating porosity. The combination of high temperature and pressure compacts the material, reducing voids and improving interfacial bonding between components in the ChNWs composites.

The combination of two drying techniques can also be applied in the fabrication of ChNW-reinforced composites. For instance, freeze-drying is often combined with hot pressing to produce ChNW-reinforced NR composite films (Table 7, entry 37).⁵¹ However, the obtained composite films were up to 20 times mechanically weaker than those prepared by casting-evaporation (10.2 vs. 229 MPa, respectively). This disparity is likely due to the insufficient formation of a robust 3-D rigid network through hydrogen bond interaction as a result of fast solvent removal process as opposed to relatively slow solvent removal in casting-evaporation. The same freeze-drying/hot pressing combination in the case of ChNW/poly-(caprolactone) composites⁹⁷ (Table 7, entry 38) also produced materials with great mechanical attributes.^{51,97}

Autoclave heat treatment has been reported as another solvent removal method to prepare ChNW-reinforced PVA composite films (Table 7, entry 39).⁹⁵ This treatment reduces the water affinity of the ChNW-reinforced composites. Here, heat treatment has been shown to improve the mechanical properties and dimensional stability of PVA-based materials. While the mechanical properties of heat-treated ChNW/PVA composites were not explicitly reported, it can be presumed that they exhibit similar improvements due to the enhanced structural integrity imparted by heat treatment.⁹⁵

2.3. Methods that utilize ionic liquids

The use of ionic liquids (ILs) has also been explored as processing aids in chitin nanocomposite fabrication. For example ILs such as [Amim]Br,¹²³ and [C₂mim][OAc]²³ (Table 7, entries 40 and 41) have demonstrated utility in various roles. Thus, [C₂mim][OAc] has been employed as both a dispersion aid and a plasticizer, effectively disrupting the hydrogen bonds in chitin (Table 7, entry 40). This disruption facilitates a more uniform ChNW distribution in the epoxy-polymer matrix.²³ In another example [Amim]Br,¹²³ was used not merely as a dispersant but as a solvent for the dissolution of ChNWs (Table 7, entry 41). This approach differs from traditional ChNWs dispersion, allowing for improved homogeneity of ChNWs within the matrix. Specifically, the use of ILs such as [Amim]Br enables a more uniform distribution of ChNWs within the PVA matrix, contributing to enhanced material properties.



2.4. Compression molding and curing

Compression molding and curing are integral processes in the fabrication of ChNWs-reinforced composite materials. Compression molding is a widely used manufacturing process where a preheated polymer or composite is placed into a preheated mold cavity (120–200 °C) using a two-segment mold system. Preheating ensures that the thermoplastic polymer melts uniformly, preventing inconsistent flow.¹⁵⁷ The mold is then tightly closed with a plug and subjected to high pressure ensuring the resin remains in contact with the entire mold surface and conforms to its shape. One segment of the compression molder (lower plate) is static, while the other (upper plate) is movable.¹⁵⁸ The vacuum generated by the compression lower plate increases pressure on the material, creating uniform Preheating ensures thermoplastic polymer melts pressure and temperature across the mold cavity. This uniformity allows the material to flow, take the shape of the cavity, and undergo chemical or physical changes necessary for achieving the desired properties.¹⁵⁹ Biocomposites composed of sorbitol polyglycidyl ether (SPE) as a bio-based epoxy resin and ChNFs were reportedly reinforced by this method (Table 7, entries 42–45). Additionally, this epoxy-based composites often require curing after the applied compression molding to achieve the final hardened state and optimal properties.

Curing, in the context of ChNW-reinforced polymer processing combined with compression molding, refers to the process of hardening or setting the material by applying heat and/or pressure on the molds, inducing crosslinking of the polymer chains. It can occur during the compression molding process or as a separate step, particularly with thermosetting polymers, such as epoxy resins which form permanent bonds by strong cross-linking (Table 7, entries 43–45).^{160,161} This method is frequently favored for nanofiber-based composites (specifically chitin nanofiber biocomposites), where the ChNFs are dispersed in solvents, often organic acids such as acetic acid,^{148,161} formic acid,^{149,150} etc., and then combined with polymer solutions to form a paste-like mixture. The paste is then molded and can be used 'as is' or treated with a cross-linking curing agent, such as amino acids or chitosan.^{148,161} After molding, curing is typically completed by drying in oven with or without vacuum. Examples include temperatures of 120–140 °C during 6 h treatment (Table 7, entries 42–45). Compared to injection molding, compression molding takes longer in the shaping process and may have less consistent results, but it is cost-effective for producing fabrics, fiber mats, strands, and tapes.

2.5. Compounding and extrusion

Compounding refers to the process of integrating reinforcement additives (ChNWs or ChNFs) into a polymer matrix to achieve specific material properties. This process is distinct from simple blending or mixing, as it typically requires the melting of the matrix polymer to ensure uniform dispersion and effective integration of the additives. Specifically, in this

process, materials are mixed in certain ratios, the mixture is melted and homogenized in a compounding machine, and the compounded material is cooled and pelletized for further use. It is possible to be processed and performed using extruders, high-shear mixers, or pelletizers (Table 7, entries 46–48).

Before the advent of continuous mixing using extruders, blends were commonly prepared using batch mixing. This was typically conducted in open mills equipped with two-roll systems featuring contra-rotating cylindrical rolls. The base polymers and fillers were repeatedly passed between these rolls to ensure consistent and uniform dispersion of the fillers throughout the matrix and to prevent particle aggregation.¹⁶² Batch mixing using roll mills is particularly suited for elastomers (rubbers) due to their high elasticity and resistance to mechanical stress. Both thermoplastics, such as PP and PLA, and thermosetting polymers (such as epoxy resin) can be processed using this method, because of their chemical and thermal stability. For instance, the preparation of NBR/ChNW composites utilized a two-roll mill,¹⁸ starting with the formulation of a mixture of polymers and ChNWs, which was then compounded with vulcanizing agents (Table 7, entry 46). In a separate study involving ChNWs/epoxy nanocomposites, a solvent-mediated slurry compounding was employed to create a homogeneous dispersion of chitin nanofillers and hardeners within the epoxy matrix²⁷ (Table 7, entry 48). The solvent-mediated approach demonstrated advantages in cost efficiency, time savings, reduced solvent consumption, and improved sustainability. Additionally compounding has been applied to the preparation of nanocomposite ChNWs/dry pulp paper handsheets. This process involves the formation of a homogeneous pulp suspension prior to the application of the standard handsheet formation method¹²¹ (Table 7, entry 47).

Extrusion offers a *continuous* mixing process for composite fabrication. In this method, the ChNWs–polymer blends pass through extruders where they are uniformly blended, devolatilized, and then transferred to the molds *via* injection or compression molding¹⁶³ (Table 7, entries 49–56). The screw speed can be adjusted for either more intense or moderate mixing, depending on the final material. Two common types of extruders are Single-Screw Extruders (SSE) and Twin-Screw Extruders (TSE). SSEs feature simple designs, low operational costs, and high reliability for small to moderate-scale production. However, their mixing capabilities are limited, often requiring additional devices or screw designs for improved efficiency. The fixed screw design may lead to prolonged residence times, causing inconsistent processing and potential material degradation.¹⁶⁴

Conversely, TSEs feature two intermeshing screws that can be customized for better mixing, melting, and conveying. This makes the twin-screw compounder a preferred choice, particularly for its ability to efficiently blend the polymer dispersions prior to molding. Its compatibility with thermoplastic polymers has led to multiple studies exploring the blending of ChNWs with polymers such as PP,¹⁹ PLA,^{26,91,92,165} and PHBV.⁹¹ In this process, the thermoplastics fed into the extruders are melted by heat generated from both the rotating



screws and external heaters. The melted samples are then mixed both dispersively and distributively by the action of the screws, ensuring uniform distribution of the components throughout the blend.¹⁶⁴ The molten mixtures are then directed toward the die, where they are shaped into desired forms such as pellets, films, discs, or hand sheets. Typical operating parameters for a micro-compounder include temperatures of 150–200 °C, screw speeds of 200 rpm, and processing time 1–10 minutes. Extruded materials are often pelletized for further processing or molded into different shapes. Depending on the target material, they may also undergo batch foaming techniques to produce foams (Table 7, entries 52–53). After molding or extrusion, materials are stabilized under specific conditions such as vacuum, hot/cold water, high pressure, or oven-drying. These treatments ensure the final properties of the materials are preserved and optimized for their intended applications.

2.6. *In situ* polymerization

In situ polymerization involves the polymerization of monomers directly in the presence of a reinforcing material such as nanochitin. During *in situ* polymerization, ChNWs or ChNFs are dispersed in a liquid monomer or a liquid mixture of monomers, leading to the formation of a polymer matrix that encapsulates nanochitin particles (Table 7, entries 57–60).^{29,90,105} Polymerization process can be initiated by heat (Table 7, entry 57),¹⁰⁵ radical initiator or UV-light (Table 7, entry 58),⁹⁰ a catalyst (Table 7, entry 59),¹⁰⁵ or an oxidizing agent (Table 7, entry 60).²⁹ Here, the nanochitin acts as a template through the surface amino groups of its nanocrystals,²⁹ and serves as a reinforcement phase,^{90,105} providing composite materials with remarkable strength and durability. When used as a structural skeleton, nanochitin provides a hierarchical framework that guides the formation and alignment of the polymer matrix around it, during the *in situ* polymerization process. For instance, the PANI-grafted chitin nanocrystals were synthesized by polymerizing the aniline monomer onto ChNCs in an acidic HCl solution.²⁹ the process began with the protonation of amino groups on the ChNC followed by their oxidation by ammonium persulfate into the ammonium cation. Polymerization was then initiated by the addition of the aniline cation radicals, leading to chain propagation driven by interactions between the growing oligomer radical cations and aniline radical cations. This continued until the aniline was fully consumed, resulting in the formation of PANI-grafted ChNC polymers.²⁹ *In situ* polymerization incorporates nanofillers directly into the polymer matrix at the monomeric stage, achieving superior dispersion compared to *ex situ* methods.

2.7. 3D-printing

3D printing, or additive manufacturing, is a process used to create three-dimensional objects. This technology facilitates the development of printable inks or filaments by mixing ChNWs with polymers. This integration can be achieved with various printing methods such as fused deposition modeling

(FDM),¹⁶⁶ stereolithography (SLA, see Table 7, entries 61 and 62),^{1,77} and inkjet printing. SLA is particularly favored for the fabrication of ChNWs-reinforced composites due to its precision, speed, and ability to create highly customized and complex structures.⁷⁷ For instance, SLA 3D printing with photocurable methacrylate-based resin reinforced with 0.5 wt% ChNWs improved the tensile strength and stiffness of material up to 78 and 71%, respectively without compromising the toughness and ductility⁷⁷ (Table 7, entry 61). This method enables the creation of complex, customized shapes and structures that are difficult to achieve with traditional manufacturing methods such as molding or extrusion. Additionally, 3D printing can produce multi-functional features such as regions with varying stiffness or porosity tailored to particular uses.

2.8. Gel spinning and electrospinning

Gel spinning⁹⁴ and electrospinning,^{49,96,142} are often combined with solution mixing to produce nanocomposite fibers or nanofibrous mats and enhance the alignment of nanochitin within the polymer matrix. Due to polymer chain alignment, both processes result in fibers with superior strength compared to those made using other techniques. In these processes, a uniform polymer–nanochitin suspension is first prepared *via* adding ChNWs to a polymeric solution and the resulting mixture is then subjected to conditions that promote gelation, forming a semi-solid gel. The gel is extruded through a spinneret to form continuous fibers which are then solidified by drying in air or coagulation in a liquid bath, such as methanol or water, to remove the solvent. Examples include mixing the dispersion of ChNWs and water with an aqueous solution of PVA fabricating fibers using a laboratory-scale gel-spinning apparatus (Table 7, entry 63).¹⁶⁷ Post-treatment processes, such as stretching or drawing, are often applied to further align the polymer chains and enhance mechanical properties, while additional treatments like heat-setting or annealing stabilize the fibers. Since the jets are only stretched to a limited extent, the resulting fibers typically have diameters ranging from 10 to 100 μm.¹⁶⁷ A combination of solution mixing and gel spinning leverages the benefits of both methods, yielding nanocomposite fibers with smooth surfaces, uniform diameters, and enhanced mechanical properties.⁹⁴ Despite its advantages, including the ability to produce ultra-strong, lightweight fibers, gel spinning requires precise control of processing conditions and may involve the use of hazardous solvents, making it more complex and expensive than other spinning methods.

Unlike conventional fiber spinning techniques (wet spinning, dry spinning, melt spinning, gel spinning), electrostatic spinning (or electrospinning) is capable of fabricating ultrafine fibers with diameters in the nm to sub-μm range.¹⁶⁸ In this process, a high-voltage electrostatic field stretches a polymer suspension containing ChNWs into fine fibers, which are collected on a grounded screen (Table 7, entries 64–66).¹⁶⁸ The polymer solution is ejected from a single-needle syringe or a multi-needle spinneret, with the applied voltage (typically 14–21 kV)^{49,96,142} controlling the alignment of the nanochitin



within the fibers. As fibers form, solvent evaporation leads to the production of solid nanocomposite fibers or mats. ChNWs-reinforced electrospun fibers have been successfully created using water soluble polymers, such as PVA or CA, with solvent evaporation occurring under various conditions such as at room temperature,⁴⁹ under vacuum drying, or at elevated temperatures,⁹⁶ with or without additional conditioning¹⁴² (Table 7, entries 64–66). This technique consistently produces fibers in the nanometer range, offering significant potential for advanced nanocomposite applications, with ChNWs assisting in reducing fiber diameter. Thus, in the fabrication of electrospun CA–ChNWs composites, the addition of as little as 0.5 wt% ChNWs reduced the fiber diameters more than twice (223 ± 76 nm for the CA–ChNWs nanofibers vs. 563 ± 222 nm for the CA nanofibers).¹⁴² This reduction was attributed to the increased electrical conductivity of the ChNW-containing solution, which accelerated and stretched the polymer jet during electrospinning. Electrospinning is a highly adaptable method for creating ChNW–polymer forms such as mats, membranes, or individual fibers tailored to specific applications.

2.9. Coating methods

Another commonly used method for fabricating reinforced nanochitin composites is coating. This method involves applying a thin layer of nanochitin (or a nanochitin-containing mixture) onto a substrate surface, typically through methods such as spraying,^{129,140,141} blade-coating,¹³⁰ or layer-by-layer (LbL) assembly.^{82,89} (Table 7, entries 67–74). In this process, nanochitin is dispersed in a solvent and applied to a surface of polymeric material, where it subsequently dried or cured to form a thin film. Coating primarily modifies the surface of composites, with the addition of nanochitin concentrated in thin surface layers, typically on the micrometer scale, to improve attributes such as water resistance and barrier performance.

For oxygen barrier coatings in the manufacture of biomaterials, nanochitin is often combined with nanocellulose to form bilayers or multiple-layer films (Table 7, entries 73 and 74).^{82,89} This technique utilizes surface-modified, oppositely charged cellulose nanofibers (CNFs) and chitin nanowhiskers (ChNWs) to create a stable polymer coating through sequential layer-by-layer (LbL) assembly driven by electrostatic interactions. First, surface modifications were applied to both cellulose nanofibers (CNFs) and ChNWs to enhance their compatibility and functionality. TEMPO-mediated oxidation was applied to CNFs, introducing carboxylate groups and producing negatively charged CNFs. In turn, ChNWs underwent deacetylation to expose amino groups, resulting in positively charged ChNWs. These modified nanomaterials were subsequently coated onto the polymer surface using a layer-by-layer (LbL) assembly technique. This process involved the sequential deposition of the oppositely charged CNFs and ChNWs, driven by strong electrostatic interactions, to create a stable and uniform coating. Hydrogen bonding and electrostatic interactions between chitin and cellulose nanomaterials promotes densification at the interface, improving barrier properties.

Since this method focuses on surface enhancement and does not significantly reinforce the bulk material, it is particularly well-suited for improving surface properties such as biocompatibility, and barrier performance particularly in food packaging applications.

2.10. Impregnation techniques

In the fabrication of nanochitin reinforced composites, impregnation refers to the process of incorporating nanochitin into polymeric matrix. The impregnation process typically begins with the preparation of a stable suspension of nanochitin in a liquid medium, often water or an organic solvent. This suspension is then processed into a pre-made film of nanochitin using methods like vacuum filtration or casting. The resulting film serves as a scaffold that will later interact with the polymeric matrix. To achieve impregnation, the nanochitin film is usually immersed in a solution of a second polymer, allowing the polymer molecules to infiltrate the porous structure of the nanochitin film and form a cohesive composite upon solidification. Reduced air pressure or applied force can be utilized to enhance the polymer's penetration into the nanochitin framework. These techniques improve the polymer's ability to uniformly infiltrate and fill the nanochitin's internal network, ensuring thorough embedding of the polymer and maximizing the interfacial bonding between the nanochitin and the polymer matrix. Ultimately, the choice of impregnation method depends on the desired composite properties, the compatibility between the polymer and nanochitin, and the manufacturing setup. Immersion-based impregnation remains the most commonly used approach due to its simplicity and effectiveness in producing uniform composites^{16,52,143} (Table 7, entries 75–77). Following impregnation, the composite is dried (at room temperature,¹⁴³ or elevated temperatures^{16,52}) to solidify the material. This method emphasizes using nanochitin films as scaffolds for polymer infiltration and is suitable for a wide variety of polymers and matrices.

Contrarily it is possible to directly integrate chitin nanowhiskers into a polymeric gel. Thus, in another study,⁷⁹ the impregnation of ChNWs into cellulose cryogels was achieved by dispersing ChNWs into the cellulose matrix during the regeneration of cellulose from a phosphoric acid solution (Table 7, entry 78), followed by freeze-drying. In this process, ChNWs served a dual role as both nanofillers and natural crosslinking agents, which significantly contributed to the formation of denser structures with reduced shrinkage and smaller composite cryogel volumes. This tighter packing resulted in a more robust cryogel structure, with the incorporation of ChNWs leading to a threefold increase in the strength of the cellulose cryogels.⁷⁹ This impregnation method is relatively simple, and applicable to a wide range of matrices, including porous, fibrous, or layered materials. Its versatility makes it effective for reinforcing bulk materials by infusing nanochitin into a matrix. However, challenges such as achieving uniform dispersion and ensuring solvent compatibility



may limit its scalability and effectiveness in certain applications.

Fig. 4 presents examples of surface micrographs illustrating how different processing methods affect the performance of ChNW-based composites. As previously discussed, the casting-evaporation method generally yields composites with superior mechanical properties compared to hot pressing (thermal processing) as demonstrated in the rubber/ChNW system²⁵ (Fig. 4a1 and a2) because solvent evaporation occurs gradually, allowing sufficient time for the nanofiller to form percolation network. In contrast, the shear stress during hot pressing tends to cause ChNW agglomeration. In the case of

the PVA reinforcement with nanochitin, the casting method¹²³ and gel spinning¹³⁶ produced films and fibers with low and high molecular orientation, respectively (Fig. 4b1 and b2). Electrospinning, however, is employed to fabricate highly porous nanofibers with improved mechanical and functional properties⁴⁹ (Fig. 4b3). From a thermodynamic perspective, *in situ* polymerization incorporates nanochitin into the polymer matrix from the monomeric stage, achieving better dispersion than *ex situ* mixing. This approach has been widely used to develop various hybrid and green biocomposites such as the nylon/ChNW system¹⁶⁹ shown in Fig. 4c.


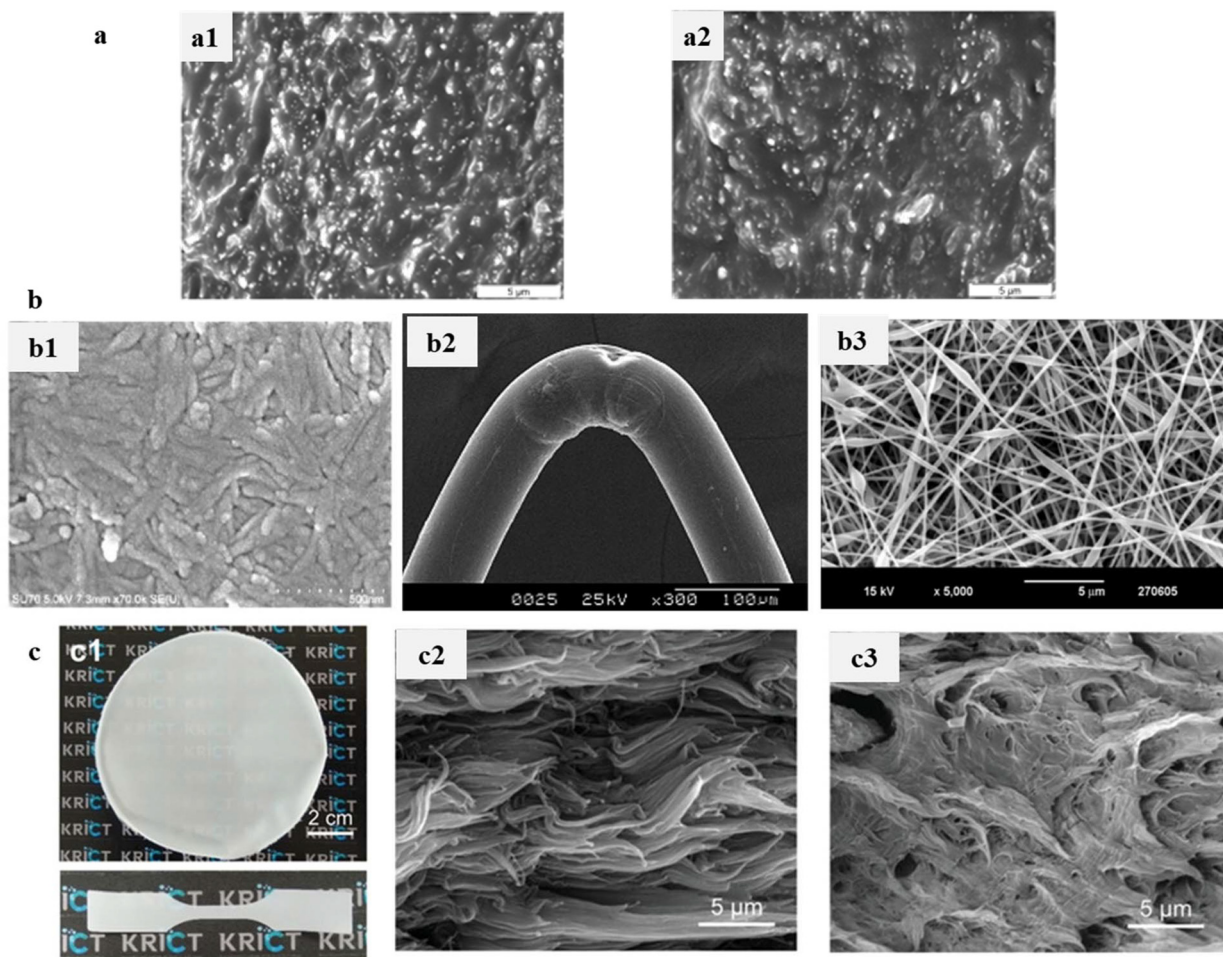


Fig. 4 Nanochitin as reinforcing fillers in various polymer systems. (a) Cryofractured surfaces of natural rubber/ChNW composites at 20 wt% ChNW load. (a1) Prepared by casting-evaporation method. SEM micrographs are obtained under 7 kV, scalebar – 5 μm , magnification not provided. Reproduced with permission.²⁵ (a2) Prepared by hot pressing method. SEM micrographs were obtained under 7 kV, scalebar – 5 μm , magnification not provided. Reproduced with permission.²⁵ (b) PVA/ChNW composites fabricated by different methods. (b1) Fabricated by casting, at 76.92 wt% nanowhiskers load. SEM micrographs are obtained under 5 kV, scalebar – 500 nm, magnification 70 000 $\times$. Adapted with permission.¹²³ (b2) Fabricated by gel spinning at 5 wt% nanowhiskers load. SEM micrographs are obtained under 25 kV, scalebar – 100 μm , magnification 300 $\times$. Reproduced with permission.¹³⁶ (b3) Fabricated by electrospinning at 5.11 wt% nanowhiskers load. SEM micrographs are obtained under 15 kV, scalebar – 5 μm , magnification 5000 $\times$. Reproduced with permission.⁴⁹ (c) Composites of nylon 6,6/ChNW at 0.4 wt% nanowhiskers load. (c1) Pictures of cast film (top) and dumbbell-shaped film specimens (bottom). Reproduced with permission.¹⁶⁹ (c2) Tensile-fractured surface of *in situ* polymerized film. SEM micrographs are obtained under 15 mA current, scalebar – 5 μm , magnification not provided. Reproduced with permission.¹⁶⁹ (c3) SEM image of *ex situ* blended film. SEM micrographs are obtained under 15 mA current, scalebar – 5 μm , magnification not provided. Reproduced with permission.¹⁶⁹



3. Reinforcing mechanism of chitin in nanocomposites

The strength of polymer composites depends on multiple factors, including the inherent properties of the polymer, the characteristics of the reinforcement agent, the compatibility and interaction between the two, and the dispersion of the reinforcement filler within the polymer matrix. Among these, the dispersion of the reinforcement filler and the interfacial interactions between the reinforcement and the polymer are critical for determining composite strength. Enhancing these interactions often involves functionalizing the surface of nanoparticles with suitable groups. Additionally, the spatial arrangement of fillers and their mutual interactions—both among themselves and with the polymer matrix—are key considerations for a comprehensive understanding of composite material performance.¹⁷⁰

The reinforcement of nanocomposites with ChNWs could be explained by several interconnected mechanisms such as mechanical reinforcement (load transfer and stress distribution),¹⁴⁴ and interfacial interaction and bonding.^{2,170} As a high-strength material, nanochitin acts as a load-bearing element when incorporated into a polymer matrix. Its large surface area facilitates efficient mechanical load transfer from the matrix to the nanofiller,¹⁴⁴ significantly enhancing the tensile strength, stiffness, and modulus of the composites. Additionally, the high aspect ratio and alignment of ChNFs within the matrix contribute to uniform stress distribution improving mechanical performance under tensile, bending, and impact forces.^{77,97}

Interfacial interaction and bonding in the ChNW-reinforced composites are primarily governed by long-range electrostatic interactions and hydrogen bonding.^{2,25,97,170} Here the amine and acetamide groups on the chitin surface, influenced by its degree of acetylation (%DA), play a crucial role. Below a pH of 6, positively charged ammonium ions promote long-range electrostatic interactions that dominate over short-range hydrogen bonding. At a pH above 6, the hydroxyl, ether, acetyl, and amine groups form an intricate network of hydrogen bonds within the crystal structure and at the interface. The number and distribution of amine groups, affected by processing conditions and source material, impacts the surface charge characteristics. Moreover, the less polar ether and acetyl

groups may contribute to material amphiphilicity, leading to varying charge fractions within chitin samples.²

Strong hydrogen bonding between chitin and polymer matrix, combined with the large surface area of ChNWs, facilitates the formation of a rigid network of fillers within the host matrix, often referred to as a “percolation network” (Fig. 5). This network significantly enhances the mechanical properties of the chitin-based polymer composites. Factors influencing the formation of this network include interparticle interactions, particles’ orientation, aspect ratio, concentration, as well as the interfacial phenomena arising from the combination of the high surface area and responsive surface of the chitin.^{97,170}

The presence of amine/amide groups further facilitates modification compared to cellulose, offering a variety of functionalization routes. Amine groups, in particular, offer increased reactivity and are often used for surface modifications such as hydrophobic group attachment to reduce hydrophilicity¹⁴⁴ or to improve its compatibility with different surfaces.² Surface modification method is essential for enhancing the compatibility and interaction at the interface between nanoparticles and the polymer matrix. However, such modification may also reduce hydrogen bonding interaction, which in turn can affect the formation of a rigid percolation network.¹⁷⁰

4. Change in properties of chitin-reinforced plastics

4.1. Reinforcement of biopolymers with nanochitin

Biopolymers are macromolecules derived from natural sources such as plants, animals, or microorganisms. These polymers are biodegradable, environmentally friendly, and attractive for various applications. Common natural polymers include polysaccharides (*e.g.*, chitosan, cellulose, alginate, starch, and hyaluronic acid), proteins (*e.g.*, gelatin, collagen, silk), and bacterial polyesters (*e.g.*, polyhydroxyalkanoates). Their biocompatibility, biodegradability, and renewability make them suitable for applications in drug delivery, tissue engineering, stem cell morphogenesis, wound healing, regenerative medicine, food packaging, *etc.*¹⁷¹ Despite their advantages, natural polymers face limitations such as poor mechanical strength, moisture sensitivity, and processing challenges. For example, cell-

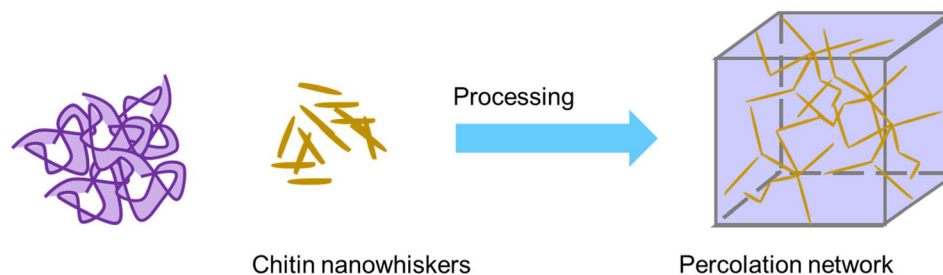


Fig. 5 Formation of a percolation network.



ulose is strong but brittle while starch and gelatin are highly moisture-sensitive, which compromises their stability in humid environments. Additionally, complex processing techniques are often required to improve their mechanical properties or enable large-scale production.¹⁷² Reinforcing these polymers with nanochitin has been extensively studied to improve their properties addressing these limitations and expanding their potential applications.

Recent studies have extensively investigated the reinforcement of natural polymers with chitin nanomaterials demonstrating significant improvements in their mechanical, thermal, and functional (*i.e.*, water-vapor transmission) properties (summarized in Table 8). These enhancements arise from the unique structural and interactive characteristics of ChNWs and ChNFs, which integrate effectively into polymer matrices, addressing inherent limitations like weak mechanical strength and high moisture sensitivity.

4.1.1. Chitosan and carboxymethyl chitosan. Thus, incorporating rod-like ChNWs into chitosan hydrogels through crosslinking with the blocked isocyanate agents resulted in remarkable increases in Young's modulus (66.8-fold) and stress at break (41.5-fold) on increasing ChNW content from 0 to 13.3%. Swelling ratio was significantly reduced, from 357.0 to 33.0 enhancing durability and flexibility of the material (Table 8, entry 1).²⁴ The authors noted that while the improved mechanical properties demonstrated effective reinforcement by the ChNWs, the role of cross-link density also in influencing these properties warrants further investigation.²⁴ Similarly, ChNWs increased the tensile strength of chitosan films by up to 137%, while tannic acid crosslinking reduced moisture content and water solubility, suggesting that the mechanical properties and water resistance of chitosan film can be controlled by adding ChNWs and using tannic acid as a crosslinking agent (Table 8, entry 2).¹⁷³

Another study demonstrated that the addition of up to 1.0 wt% ChNWs into carboxymethyl chitosan (CMCS) cross-linked with dextran dialdehyde (DDA) (Table 8, entry 3) increased compressive stress (up to 1.87 times) and Young's modulus (up to 1.56 times) while preserving the swelling ratio.¹⁰⁶ The improvements are likely attributed to ChNWs ability to strengthen interactions among the polymer coils across different layers, significantly restricting segment movement under applied stretching force.¹⁷⁴ These mechanisms also help explain the enhanced mechanical performance observed in ChNWs-incorporated CMCS/DDA hydrogels.¹⁰⁶

4.1.2. Alginate. Chitin nanomaterials have demonstrated significant reinforcement effects in alginate-based hydrogels and films (Table 8, entries 4–7). ChNWs enhanced tensile strength while reducing elongation at break, attributed to strong electrostatic interactions and molecular entanglements with alginate chains (Table 8, entry 4). Enhanced rheological properties, yield stress, and drug release control were observed, making these composites suitable for biomedical applications. This reduction in elongation was attributed to the formation of polyelectrolyte complexes (PEC) between the positively charged ammonium groups on the slightly deacety-

lated chitin backbone (%DA was not reported) and the negatively charged alginate chains, complemented by molecular entanglements and hydrogen bonding.⁷⁵ These interactions contribute to stiffer composites with enhanced tensile strength.⁷⁵

Similar findings were reported in another study, where alginate hydrogels reinforced with ChNWs showed improved tensile properties and reduced elongation at break (Table 8, entry 5).¹³² Additionally, the incorporation of ChNWs into the hydrogels increased yield stress, enhanced viscosity, modulated rheological properties, and prolonged drug release.¹³² A recent study by Santos *et al.*¹⁷⁵ highlighted surface functionalization of ChNCs can improve pectin-alginate films. Two types of surface-functionalized ChNCs – acid hydrolyzed ChNCs (AH-ChNCs) and carboxylated ChNCs (OX-ChNCs) – were studied to reinforce an edible pectin alginate film. The results showed that despite AH-ChNCs having lower rheological characteristics than OX-ChNCs, the films reinforced with AH-ChNCs exhibited higher tensile properties (Table 8, entry 6). This underscores the crucial role of amines in effectively strengthening the films.¹⁷⁵

Huang *et al.*¹⁷⁶ successfully fabricated alginate-based nanocomposite hydrogels reinforced with chitin whiskers utilizing the pH-induced charge shifting behavior of ChNWs. The addition of chitin whiskers to the hydrogels not only greatly improved the mechanical properties, but also inhibited swelling (Table 8, entry 7), attributed to the strong electrostatic interaction between ChNWs and alginate. Furthermore, the introduction of ChNWs significantly promoted osteoblast cell adhesion and proliferation, making the resulting materials suitable candidates for bone tissue engineering.¹⁷⁶

4.1.3. Cellulose and its derivatives. In the fabrication of paper handsheets, two types of ChNWs with opposite surface chargers – positive and negative – were used to reinforce bleached eucalyptus pulp cellulose paper (Table 8, entry 8). The positively charged ChNWs (DeChNWs) were prepared by partial deacetylation of chitin (%DA = 62.5) followed by protonation, while the negatively charged ChNWs (TOChNWs) were prepared by TEMPO-oxidation.¹²¹ The results demonstrated that among all composites containing from 0.2 to 5 wt% DeChNWs, composites containing 0.8 wt% DeChNWs exhibited the highest tensile index (24.2 N m g⁻¹), a 1.3-fold increase compared to unreinforced pulp (Table 8, entry 8). The value represents a maximum threshold for DeChNWs' loading, as both lower and higher concentrations decreased the tensile index. TOChNWs reinforced composites achieved a maximum tensile index of 19.59 N m g⁻¹ at 1 wt% nanowhisker loading. Overall, DeChNWs consistently produced composites with higher tensile indices than TOChNWs at equivalent loadings.

Reinforcement with DeChNWs and TOChNWs also enhanced the tear index of paper handsheets, again with DeChNWs being more effective. The maximum tear index for DeChNWs (3.7 mN m² g⁻¹) was observed at a 2 wt% loading, while TOChNWs achieved a peak tear index of 2.4 mN m² g⁻¹ at 0.8–1 wt%. Similar to the tensile index, the tear index reaches a threshold value of 3.7 mN m² g⁻¹ at a 2 wt%





Table 8 Reinforcement of natural polymers with nanochitin

No.	Polymers	Affected properties	Composition	Value	Ref.
Chitosan					
1	Chitosan (CS)/cross-linked with isocyanate hexamethylene-1,6-di-(aminocarboxysulfonate) (HDS)/ChNWs	Young's modulus, MPa	CS ChNWs/CS = 2.97/97.03 ChNWs/CS = 5.77/94.23 ChNWs/CS = 10.90/89.10 ChNWs/CS = 13.30/86.70 CS ChNWs/CS = 2.97/97.03 ChNWs/CS = 5.77/94.23 ChNWs/CS = 10.90/89.10 ChNWs/CS = 13.30/86.70 CS ChNWs/CS = 2.97/97.03 ChNWs/CS = 5.77/94.23 ChNWs/CS = 10.90/89.10 ChNWs/CS = 13.30/86.70 CS TA ^b /CS = 20/100 TA/CS = 40/100 ChNWs/CS = 10/90 ChNWs/CS = 20/80 ChNWs/CS = 30/70 ChNWs/TA/CS = 10/20/90 ChNWs/TA/CS = 20/20/80 ChNWs/TA/CS = 30/20/70 ChNWs/TA/CS = 10/40/90 ChNWs/TA/CS = 20/40/80 ChNWs/TA/CS = 30/40/70 CS TA ^b /CS = 20/100 TA/CS = 40/100 ChNWs/CS = 10/90 ChNWs/CS = 20/80 ChNWs/CS = 30/70 ChNWs/TA/CS = 10/20/90 ChNWs/TA/CS = 20/20/80 ChNWs/TA/CS = 30/20/70 ChNWs/TA/CS = 10/40/90 ChNWs/TA/CS = 20/40/80 ChNWs/TA/CS = 30/40/70 CS TA ^b /CS = 20/100 TA/CS = 40/100 ChNWs/CS = 10/90 ChNWs/CS = 20/80 ChNWs/CS = 30/70 ChNWs/TA/CS = 10/20/90 ChNWs/TA/CS = 20/20/80 ChNWs/TA/CS = 30/20/70 ChNWs/TA/CS = 10/40/90 ChNWs/TA/CS = 20/40/80 ChNWs/TA/CS = 30/40/70	2.5 17.8 59.1 130 169 3.2 17.7 42.9 117 135 357 211 53.3 40.7 33 22.02 39.75 41.88 42 49.9 52.23 37.8 38.5 48.9 34.5 34.8 48.9 50.3 40 33 26.8 23.5 21.3 25 23.2 24.8 23 21.5 22.5 555 340 320 530 415 400 330 275 273 275 270 260	24
		Stress at break, kPa			
		Swelling ratio, Q			
2	CS/cross-linked with tannic acid (TA)/ChNWs	Tensile strength ^a , MPa			173
		Elongation at break ^a , %			
		Moisture content ^d , %			



Table 8 (Contd.)

No.	Polymers	Affected properties	Composition	Value	Ref.
3	Carboxymethyl chitosan (CMCS) Carboxymethyl chitosan (CMCS) cross-linked with dextran dialdehyde (DDA)/ChNWs	Water solubility ^d , %	CS	21.8	106
			TA ^b /CS = 20/100	15.5	
			TA/CS = 40/100	13.2	
			ChNWs/CS = 10/90	18.8	
			ChNWs/CS = 20/80	16.7	
			ChNWs/CS = 30/70	13.5	
			ChNWs/TA/CS = 10/20/90	14.2	
			ChNWs/TA/CS = 20/20/80	13.4	
			ChNWs/TA/CS = 30/20/70	12.6	
			ChNWs/TA/CS = 10/40/90	12.2	
			ChNWs/TA/CS = 20/40/80	9.2	
			ChNWs/TA/CS = 30/40/70	8.4	
			CMCS/DDA	43.2 ± 4.6	
4	Alginate Sodium alginate (ALG)/α-ChNWs	Young's modulus, kPa	ChNWs/CMCS = 0.5/99.5	47.2 ± 5.6	75
			ChNWs/CMCS = 1.0/99.0	67.0 ± 6.2	
		Swelling ratio at 36 h, %	CMCS/DDA	52.62 ± 8.59	
			ChNWs/CMCS = 0.5/99.5	61.62 ± 6.10	
			ChNWs/CMCS = 1.0/99.0	64.20 ± 4.93	
		Bonding strength, kPa	CMCS/DDA	21.93	
			ChNWs/CMCS = 0.5/99.5	25.2	
			ChNWs/CMCS = 1.0/99.0	33.21	
		Tensile strength, N mm ⁻²	ALG	0.0256 ± 0.0031	
			ChNWs/ALG = 33.3/66.7	0.0618 ± 0.0054	
			ALG	51.52 ± 2.61	
		Elongation, %	ChNWs/ALG = 33.3/66.7	37.67 ± 2.31	
			ALG	1120	
5	ALG/partially deacetylated α-chitin nanowhiskers (ChNWs, DDA 0.40 ± 0.03)	Yield stress, Pa	ChNWs/ALG = 2.5/97.5	1560	132
			ChNWs/ALG = 7.5/92.5	18000–44 000	
			ChNWs/ALG = 14.5/85.5	17 000	
		Tensile strength, MPa	Pectin-ALG	25.9 ± 1.4	
			AH-ChNCs/pectin-ALG = 20/80	33.5 ± 1.7	
			OX-ChNCs/pectin-ALG = 20/80	23 ± 1	
		Elongation at break, mm	Pectin-ALG	2.1 ± 0.7	
			AH-ChNCs/pectin-ALG = 20/80	2.6 ± 0.5	
			OX-ChNCs/pectin-ALG = 20/80	1.4 ± 0.3	
		Young's modulus, MPa	Pectin-ALG	1132 ± 49	
			AH-ChNCs/pectin-ALG = 20/80	1810 ± 341	
			OX-ChNCs/pectin-ALG = 20/80	1458 ± 90	
7	ALG/ChNWs	Compressive modulus, MPa	ALG	5.08	176
			ChNWs/ALG = 0.5/99.5	9.56	
			ChNWs/ALG = 1/99	12.12	
		Compressive strength, MPa	ChNWs/ALG = 2/98	13.72	
			ChNWs/ALG = 2.5/97.5	13.81	
			ALG	1.39	
			ChNWs/ALG = 0.5/99.5	2.01	
			ChNWs/ALG = 1/99	2.52	
			ChNWs/ALG = 2/98	3.18	
			ChNWs/ALG = 2.5/97.5	1.97	
			ChNWs/ALG = 0.5/99.5	2.01	
			ChNWs/ALG = 1/99	2.52	
			ChNWs/ALG = 2/98	3.18	



Table 8 (Contd.)

No.	Polymers	Affected properties	Composition	Value	Ref.
8	Eucalyptus pulp Eucalyptus pulp/partially deacetylated chitin nanowhiskers (DeChNWs)/TEMPO-oxidized chitin nanowhiskers (TOChNWs)	Strain, %	ALG	76.05	121
			ChNWs/ALG = 0.5/99.5	78.57	
			ChNWs/ALG = 1/99	78.78	
			ChNWs/ALG = 2/98	78.15	
			ChNWs/ALG = 2.5/97.5	74.8	
		Swelling ratio, g ⁻¹	ALG	34.6	
			ChNWs/ALG = 0.5/99.5	24.6	
			ChNWs/ALG = 1/99	20.7	
			ChNWs/ALG = 2/98	17	
			ChNWs/ALG = 2.5/97.5	14	
		Tensile index, N m g ⁻¹	Dry pulp (paper)	18.4	
			DeChNWs/dry pulp = 0.2/99.8	19	
			DeChNWs/dry pulp = 0.4/99.6	21	
			DeChNWs/dry pulp = 0.6/99.4	22.5	
			DeChNWs/dry pulp = 0.8/99.2	24.2	
9	Microcrystalline cellulose (MCC) Microcrystalline cellulose (MCC, M _w 1 × 10 ⁵)/α-ChNWs	Tensile index, N m g ⁻¹	DeChNWs/dry pulp = 1.0/99.0	23	79
			DeChNWs/dry pulp = 2.0/98.0	22.5	
			DeChNWs/dry pulp = 5.0/95.0	22	
			Dry pulp (paper)	17.5	
			TOChNWs/dry pulp = 0.2/99.8	18	
		Tear index, mN m ² g ⁻¹	TOChNWs/dry pulp = 0.4/99.6	19.5	
			TOChNWs/dry pulp = 0.6/99.4	19.52	
			TOChNWs/dry pulp = 0.8/99.2	20	
			TOChNWs/dry pulp = 1.0/99.0	20.5	
			TOChNWs/dry pulp = 2.0/98.0	21	
		Compressive modulus, kPa (w.r.t freezing days)	TOChNWs/dry pulp = 5.0/95.0	18	
			Dry pulp (paper)	2.4	
			DeChNWs/dry pulp = 0.2/99.8	2.6	
			DeChNWs/dry pulp = 0.4/99.6	3	
			DeChNWs/dry pulp = 0.6/99.4	3.1	
9	Microcrystalline cellulose (MCC) Microcrystalline cellulose (MCC, M _w 1 × 10 ⁵)/α-ChNWs	Tear index, mN m ² g ⁻¹	DeChNWs/dry pulp = 0.8/99.2	3.5	79
			DeChNWs/dry pulp = 1.0/99.0	3.6	
			DeChNWs/dry pulp = 2.0/98.0	3.7	
			DeChNWs/dry pulp = 5.0/95.0	3.4	
			Dry pulp (paper)	2	
		Compressive modulus, kPa (w.r.t freezing days)	TOChNWs/dry pulp = 0.2/99.8	2.2	
			TOChNWs/dry pulp = 0.4/99.6	2.2	
			TOChNWs/dry pulp = 0.6/99.4	2.4	
			TOChNWs/dry pulp = 0.8/99.2	2.4	
			TOChNWs/dry pulp = 1.0/99.0	2.3	
		Compressive modulus, kPa (w.r.t freezing days)	TOChNWs/dry pulp = 2.0/98.0	2.1	
			TOChNWs/dry pulp = 5.0/95.0	2.4	
			MCC (3 days)	1231 ± 132	
			ChNWs/MCC = 1.0/99.0 (3 days)	1238	
			ChNWs/MCC = 2.5/97.5 (3 days)	1570	
9	Microcrystalline cellulose (MCC) Microcrystalline cellulose (MCC, M _w 1 × 10 ⁵)/α-ChNWs	Compressive modulus, kPa (w.r.t freezing days)	ChNWs/MCC = 5.0/95.0 (3 days)	273	79
			ChNWs/MCC = 10.0/90.0 (3 days)	383 ± 150	
			ChNWs/MCC = 1.0/99.0 (10 days)	3120 ± 120	
			ChNWs/MCC = 2.5/97.5 (10 days)	3050 ± 160	



Table 8 (Contd.)

No.	Polymers	Affected properties	Composition	Value	Ref.
10	Cellulose acetate (CA)/ChNCs	Young's modulus ^a , MPa	CA	183	178
			ChNCs/CA = 0.5/99.5	219	
			ChNCs/CA = 1.0/99.0	220	
			ChNCs/CA = 2.0/98.0	255	
		Tensile strength ^a , MPa	CA	2.95	
			ChNCs/CA = 0.5/99.5	2.41	
			ChNCs/CA = 1.0/99.0	2.5	
			ChNCs/CA = 2.0/98.0	2.99	
		Elongation at break ^a , %	CA	1.95	
			ChNCs/CA = 0.5/99.5	1.53	
			ChNCs/CA = 1.0/99.0	1.63	
			ChNCs/CA = 2.0/98.0	1.78	
		Contact angle measurements ^a , O	CA	48	
			ChNCs/CA = 0.5/99.5	45.4	
11	Cellulose acetate (CA)/α-ChNWs/cellulose nanocrystals (CNCs)	Anti-fungal activities, expressed as fungal growth inhibition (FGI) ^a , %	ChNCs/CA = 1.0/99.0	43.9	140
			ChNCs/CA = 2.0/98.0	44.3	
			CA	7.5	
			ChNCs/CA = 0.5/99.5	33.5	
		Optical transmittance (at 400 nm) ^a , %	ChNCs/CA = 1.0/99.0	15	
			ChNCs/CA = 2.0/98.0	35.2	
			CA	20.6	
			ChNCs/CA = 0.5/99.5	16.1	
		Ultimate tensile strength, MPa	ChNCs/CA = 1.0/99.0	13.9	
			ChNCs/CA = 2.0/98.0	12.8	
			ChNWs/CNCs = 50/50 coated in sequence on CA film		
			CA	36.0 ± 0.9	
			ChNWs suspension ^c	33.3 ± 1.2	
			(%DA = 88.8 ± 1.4)		
			ChNWs suspension	31.9 ± 0.9	
			(%DA = 88.8 ± 3.1)		
			ChNWs suspension	32.3 ± 1.4	
			(%DA = 93.1 ± 0.8)		
			ChNWs suspension	33.6 ± 1.1	
			(%DA = 93.7 ± 1.9)		
			ChNWs suspension	31.1 ± 0.9	
			(%DA = 85.7 ± 1.5)		
			ChNWs suspension	30.6 ± 1.8	
			(%DA = 93.4 ± 1.0)		
			ChNWs suspension	30.9 ± 1.7	
			(%DA = 86.5 ± 1.1)		
			ChNWs suspension	31.9 ± 1.0	
			(%DA = 89.0 ± 0.8)		
			ChNWs suspension	33.5 ± 1.0	
			(%DA = 84.1 ± 1.7)		
			ChNWs suspension	33.3 ± 1.2	
			(%DA = 75.1 ± 1.5)		
			ChNWs suspension	32.5 ± 0.9	
			(%DA = 6.8 ± 2.8)		



Table 8 (Contd.)

No.	Polymers	Affected properties	Composition	Value	Ref.
		Failure strain, %	CA		
			ChNWs suspension ^c	22.7 ± 2.7	
			(%DA = 88.8 ± 1.4)	21.6 ± 1.1	
			ChNWs suspension		
			(%DA = 88.8 ± 3.1)	19.0 ± 2.7	
			ChNWs suspension		
			(%DA = 93.1 ± 0.8)	20.5 ± 1.4	
			ChNWs suspension		
			(%DA = 93.7 ± 1.9)	23.6 ± 1.8	
			ChNWs suspension		
			(%DA = 85.7 ± 1.5)	22.7 ± 1.4	
			ChNWs suspension		
			(%DA = 93.4 ± 1.0)	22.1 ± 3.4	
			ChNWs suspension		
			(%DA = 86.5 ± 1.1)	23.4 ± 3.8	
			ChNWs suspension		
			(%DA = 89.0 ± 0.8)	21.6 ± 1.0	
			ChNWs suspension		
			(%DA = 84.1 ± 1.7)	23.5 ± 2.6	
			ChNWs suspension		
			(%DA = 75.1 ± 1.5)	22.1 ± 1.5	
			ChNWs suspension		
			(%DA = 6.8 ± 2.8)	20.9 ± 1.5	
		Water vapor transmission rate, g mm m ⁻² day ⁻¹ kPa ⁻¹	CA		
			ChNWs suspension ^c	12.5	
			(%DA = 88.8 ± 1.4)	10.2	
			ChNWs suspension		
			(%DA = 88.8 ± 3.1)	10.5	
			ChNWs suspension		
			(%DA = 93.1 ± 0.8)	10	
			ChNWs suspension		
			(%DA = 93.7 ± 1.9)	10	
			ChNWs suspension		
			(%DA = 85.7 ± 1.5)	10.1	
			ChNWs suspension		
			(%DA = 93.4 ± 1.0)	10	
			ChNWs suspension		
			(%DA = 86.5 ± 1.1)	10.1	
			ChNWs suspension		
			(%DA = 89.0 ± 0.8)	9	
			ChNWs suspension		
			(%DA = 84.1 ± 1.7)	8	
			ChNWs suspension		
			(%DA = 75.1 ± 1.5)	9.8	
			ChNWs suspension		
			(%DA = 6.8 ± 2.8)	9	
		Oxygen permeability, cm ³ μm m ⁻² day ⁻¹ kPa ⁻¹	CA		
			ChNWs suspension ^c	1553	
			(%DA = 88.8 ± 1.4)	132	
			ChNWs suspension		
			(%DA = 88.8 ± 3.1)	90	



Table 8 (Contd.)

No.	Polymers	Affected properties	Composition	Value	Ref.
12	Cellulose acetate (CA)/ChNWs/cellulose nanocrystals (CNCs)	Oxygen permeability, $\mu\text{m m}^{-2} \text{ day}^{-1} \text{ kPa}^{-1}$ (with different T_{spray} at a controlled T_{thermal} of 40 °C)	ChNWs suspension (%DA = 93.1 ± 0.8)	41	141
			ChNWs suspension (%DA = 93.7 ± 1.9)	70	
			ChNWs suspension (%DA = 85.7 ± 1.5)	50	
			ChNWs suspension (%DA = 93.4 ± 1.0)	45	
			ChNWs suspension (%DA = 86.5 ± 1.1)	75	
			ChNWs suspension (%DA = 89.0 ± 0.8)	50	
			ChNWs suspension (%DA = 84.1 ± 1.7)	45	
			ChNWs suspension (%DA = 75.1 ± 1.5)	30	
			ChNWs suspension (%DA = 76.8 ± 2.8)	16.7	
			ChNWs/CNC = 50/50 coated in sequence on CA film		
			CA	535	
			40 °C ^f	44.4	
		Oxygen permeability, $\mu\text{m m}^{-2} \text{ day}^{-1} \text{ kPa}^{-1}$ (with different T_{thermal} at a controlled T_{spray} of 80 °C)	60 °C	27.9	
			80 °C	28.6	
			100 °C	23.3	
			CA	535	
			40 °C	28.6	
			60 °C	22.1	
			80 °C	24.1	
			100 °C	20.1	
			120 °C	15.9	
			140 °C	11.5	
			T_n ^g	20.2	
			CA	8.3	
		Water vapor transmission rate, $\text{g mm m}^{-2} \text{ day}^{-1}$ (with different T_{spray} at a controlled T_{thermal} of 40 °C)	40 °C	7.5	
			60 °C	7.7	
			80 °C	7.7	
			100 °C	7.8	
			CA	8.3	
			40 °C	7.7	
			60 °C	7.6	
			80 °C	7.4	
			100 °C	7.4	
			120 °C	7.3	
			140 °C	6.6	
			T_n	6.8	
		Breaking force, N	CA	38.5 ± 0.8	
			$T_{\text{spray}}/40 T_{\text{thermal}}/40$ ^f	47.8 ± 2.0	
			$T_{\text{spray}}/60 T_{\text{thermal}}/40$	45.6 ± 2.5	
			$T_{\text{spray}}/80 T_{\text{thermal}}/40$	47.6 ± 3.4	
			$T_{\text{spray}}/100 T_{\text{thermal}}/40$	46.1 ± 4.3	
			$T_{\text{spray}}/80 T_n$	47.7 ± 2.3	
			$T_{\text{spray}}/80 T_{\text{thermal}}/60$	41.6 ± 2.3	



Table 8 (Contd.)

No.	Polymers	Affected properties	Composition	Value	Ref.
	Modulus, GPa		$T_{\text{spray}}80 T_{\text{thermal}}80$	44.0 ± 1.3	
			$T_{\text{spray}}80 T_{\text{thermal}}100$	45.2 ± 1.3	
			$T_{\text{spray}}80 T_{\text{thermal}}120$	47.9 ± 1.6	
			$T_{\text{spray}}80 T_{\text{thermal}}140$	45.9 ± 2.1	
			CA	2.39 ± 0.25	
			$T_{\text{spray}}40 T_{\text{thermal}}40$	2.44 ± 0.26	
			$T_{\text{spray}}60 T_{\text{thermal}}40$	2.58 ± 0.13	
			$T_{\text{spray}}80 T_{\text{thermal}}40$	2.62 ± 0.22	
			$T_{\text{spray}}100 T_{\text{thermal}}40$	2.45 ± 0.12	
			$T_{\text{spray}}80 T_n$	2.87 ± 0.10	
			$T_{\text{spray}}80 T_{\text{thermal}}60$	2.81 ± 0.05	
			$T_{\text{spray}}80 T_{\text{thermal}}80$	2.82 ± 0.09	
			$T_{\text{spray}}80 T_{\text{thermal}}100$	2.78 ± 0.07	
			$T_{\text{spray}}80 T_{\text{thermal}}120$	2.71 ± 0.14	
			$T_{\text{spray}}80 T_{\text{thermal}}140$	2.73 ± 0.22	
	Yield stress, MPa		CA	42.9 ± 5.9	
			$T_{\text{spray}}40 T_{\text{thermal}}40$	49.2 ± 3.9	
			$T_{\text{spray}}60 T_{\text{thermal}}40$	47.8 ± 1.7	
			$T_{\text{spray}}80 T_{\text{thermal}}40$	49.9 ± 4.3	
			$T_{\text{spray}}100 T_{\text{thermal}}40$	50.5 ± 1.5	
			$T_{\text{spray}}80 T_n$	57.2 ± 5.0	
			$T_{\text{spray}}80 T_{\text{thermal}}60$	53.3 ± 1.4	
			$T_{\text{spray}}80 T_{\text{thermal}}80$	53.8 ± 2.0	
			$T_{\text{spray}}80 T_{\text{thermal}}100$	53.6 ± 2.4	
			$T_{\text{spray}}80 T_{\text{thermal}}120$	53.2 ± 2.2	
			$T_{\text{spray}}80 T_{\text{thermal}}140$	52.3 ± 7.4	
			CA	3.3 ± 1.0	
			$T_{\text{spray}}40 T_{\text{thermal}}40$	8.9 ± 6.1	
			$T_{\text{spray}}60 T_{\text{thermal}}40$	8.7 ± 6.1	
			$T_{\text{spray}}80 T_{\text{thermal}}40$	5.5 ± 3.3	
			$T_{\text{spray}}100 T_{\text{thermal}}40$	14.5 ± 5.3	
	Strain at break, %		$T_{\text{spray}}80 T_n$	3.4 ± 0.9	
			$T_{\text{spray}}80 T_{\text{thermal}}60$	3.5 ± 0.4	
			$T_{\text{spray}}80 T_{\text{thermal}}80$	10.4 ± 6.4	
			$T_{\text{spray}}80 T_{\text{thermal}}100$	6.6 ± 3.0	
			$T_{\text{spray}}80 T_{\text{thermal}}120$	3.9 ± 0.4	
			$T_{\text{spray}}80 T_{\text{thermal}}140$	11.3 ± 7.9	
			CA	90	
			40 °C	75	
			60 °C	78	
			80 °C	80	
			100 °C	81	
			CA	90	
			40 °C	81	
			60 °C	85	
			80 °C	86	
			100 °C	84	
	Transmittance, % (with different T_{spray} at a controlled T_{thermal} of 40 °C)		120 °C	82	
			140 °C	80	
	Transmittance, % (with different T_{thermal} at a controlled T_{spray} of 80 °C)		40 °C	75	
			60 °C	78	
			80 °C	80	
			100 °C	81	
			CA	90	
			40 °C	81	
			60 °C	85	
			80 °C	86	



Table 8 (Contd.)

No.	Polymers	Affected properties	Composition	Value	Ref.
13	Potato starch powder/chitin nanoparticles (ChNPs)	Haze, % (with different T_{spray} at a controlled T_{thermal} of 40 °C)	CA	0.5	48
			40 °C	13	
			60 °C	8	
			80 °C	5	
			100 °C	2	
		Haze, % (with different T_{thermal} at a controlled T_{spray} of 80 °C)	CA	0.5	
			40 °C	8	
			60 °C	2	
			80 °C	4	
			100 °C	1	
		Tensile strength, MPa	120 °C	0.9	
			140 °C	4	
			Potato starch	2.84	
14	Corn starch granules/ α -ChNFs/ α -chitin nanocrystals (ChNCs)	Elongation at break, %	ChNPs/potato starch = 1/99	3.5	20
			ChNPs/potato starch = 2/98	5.2	
			ChNPs/potato starch = 3/97	6.25	
			ChNPs/potato starch = 4/96	7.25	
			ChNPs/potato starch = 5/95	7.79	
		Water vapor permeability, $\text{g m}^{-1} \text{s}^{-1} \text{Pa}^{-1}$	Potato starch	59.3	
			ChNPs/potato starch = 1/99	45	
			ChNPs/potato starch = 2/98	34.25	
			ChNPs/potato starch = 3/97	26	
			ChNPs/potato starch = 4/96	22	
		Young's modulus, MPa	ChNPs/potato starch = 5/95	19.3	
			Potato starch	5.62×10^{-10}	
			ChNPs/potato starch = 1/99	4.45×10^{-10}	
			ChNPs/potato starch = 2/98	4.15×10^{-10}	
			ChNPs/potato starch = 3/97	3.45×10^{-10}	
15	Corn starch	Tensile strength, MPa	ChNPs/potato starch = 4/96	3.42×10^{-10}	20
			ChNPs/potato starch = 5/95	3.41×10^{-10}	
			Corn starch	80	
			ChNCs/corn starch = 5/95	222	
			ChNCs/corn starch = 10/90	280	
		Young's modulus, MPa	ChNCs/corn starch = 15/85	367	
			ChNCs/corn starch = 20/80	390	
			ChNFs/corn starch = 5/95	330	
			ChNFs/corn starch = 10/90	390	
			ChNFs/corn starch = 15/85	410	
		Tensile strength, MPa	ChNFs/corn starch = 20/80	520	
			Corn starch	4.5	
			ChNCs/corn starch = 5/95	7.1	
			ChNCs/corn starch = 10/90	7.5	
			ChNCs/corn starch = 15/85	9	
			ChNCs/corn starch = 20/80	10.8	
			ChNFs/corn starch = 5/95	9.9	
			ChNFs/corn starch = 10/90	12	
			ChNFs/corn starch = 15/85	12	
			ChNFs/corn starch = 20/80	15	

Table 8 (Contd.)

No.	Polymers	Affected properties	Composition	Value	Ref.
15	Gelatin Gel/ChNWs	Elongation at break, %	Corn starch	87	78
			ChNCs/corn starch = 5/95	38	
			ChNCs/corn starch = 10/90	26.5	
		Ultimate tensile strength, MPa	ChNCs/corn starch = 15/85	17	
			ChNCs/corn starch = 20/80	15	
			ChNFs/corn starch = 5/95	26	
		Elongation at break, %	ChNFs/corn starch = 10/90	19	
			ChNFs/corn starch = 15/85	11	
			ChNFs/corn starch = 20/80	9	
		Young's modulus, MPa	Gelatin	2455 ± 74	
			ChNWs/gel = 1/99	2435 ± 50	
			ChNWs/gel = 2/98	2496 ± 56	
		Transparency	ChNWs/gel = 4/96	2921 ± 76	
			Gelatin	71.0 ± 1.8	
			ChNWs/gel = 1/99	69.5 ± 2.0	
16	Gel/ChNFs	Elongation at break, %	ChNWs/gel = 2/98	68.9 ± 3.3	143
			ChNWs/gel = 4/96	77.4 ± 3.1	
			Gelatin	7.7 ± 0.5	
		Absorbance (289 nm)	ChNWs/gel = 1/99	7.8 ± 0.6	
			ChNWs/gel = 2/98	9.1 ± 1.2	
			ChNWs/gel = 4/96	6.8 ± 1.1	
		Solubility	Gelatin	1.39 ± 0.07	
			ChNWs/gel = 1/99	1.77 ± 0.14	
			ChNWs/gel = 2/98	1.90 ± 0.23	
		Stress, MPa	ChNWs/gel = 4/96	2.03 ± 0.08	
			Gelatin	0.42 ± 0.01	
			ChNWs/gel = 1/99	0.45 ± 0.03	
		Strain, %	ChNWs/gel = 2/98	0.44 ± 0.03	
			ChNWs/gel = 4/96	0.41 ± 0.03	
			Gelatin	13.1 ± 1.2	
		Young's modulus, MPa	ChNWs/gel = 1/99	12.0 ± 0.3	
			ChNWs/gel = 2/98	11.0 ± 0.3	
			ChNWs/gel = 4/96	10.2 ± 0.2	
		Transmittance, %	Gelatin	87.2 ± 3.2	
			ChNFs	65.8 ± 5.3	
			ChNFs/gel = 73.0/27.0	74.0 ± 3.1	
		Young's modulus, MPa	ChNFs/gel = 62.5/37.5	84.7 ± 4.5	
			ChNFs/gel = 50.2/49.8	101.0 ± 5.3	
			Gelatin	8.0 ± 0.4	
		Strain, %	ChNFs	1.4 ± 0.1	
			ChNFs/gel = 73.0/27.0	1.4 ± 0.2	
			ChNFs/gel = 62.5/37.5	1.8 ± 0.1	
		Transmittance, %	ChNFs/gel = 50.2/49.8	3.1 ± 0.2	
			Gelatin	2576 ± 264	
			ChNFs	6705 ± 342	
		Young's modulus, MPa	ChNFs/gel = 73.0/27.0	7039 ± 277	
			ChNFs/gel = 62.5/37.5	6372 ± 313	
			ChNFs/gel = 50.2/49.8	5192 ± 194	
		Transmittance, %	Gelatin	90.6	
			ChNFs	65	





Table 8 (Contd.)

No.	Polymers	Affected properties	Composition	Value	Ref.
17	Gel/surface-deacetylated ChNFs (S-ChNFs, DA = 63 ± 2%)	Stress, MPa	ChNFs/gel = 73.0/27.0	86.9	181
			ChNFs/gel = 62.5/37.5	87.6	
			ChNFs/gel = 50.2/49.8	88.7	
			Gelatin	89.2 ± 2.83	
			S-ChNFs	100.4 ± 5.26	
			S-ChNFs/gel = 45.5/54.5	126.3 ± 3.07	
			S-ChNFs/gel = 62.5/37.5	119.4 ± 3.54	
			S-ChNFs/gel = 22.1/77.9	103.2 ± 4.72	
			Gelatin	8.07 ± 0.33	
			S-ChNFs	2.87 ± 0.19	
			S-ChNFs/gel = 45.5/54.5	3.67 ± 0.23	
			S-ChNFs/gel = 62.5/37.5	6.96 ± 0.27	
			S-ChNFs/gel = 22.1/77.9	7.58 ± 0.34	
			Gelatin	2598 ± 214	
			S-ChNFs	7075 ± 297	
			S-ChNFs/gel = 45.5/54.5	6356 ± 261	
18	Gel/dialdehyde microfibrillated cellulose (DAMFC)/ChNWs	Young's modulus, MPa	S-ChNFs/gel = 62.5/37.5	5569 ± 413	120
			S-ChNFs/gel = 22.1/77.9	4627 ± 306	
			Gelatin	0.522	
			DAMFC/gel = 15.0/85.0	1.949	
			DAMFC/gel/ChNWs = 14.90/84.30/0.80	2.419	
			DAMFC/gel/ChNWs = 14.74/83.55/1.71	2.753	
			DAMFC/gel/ChNWs = 14.62/82.82/2.56	2.729	
			DAMFC/gel/ChNWs = 14.36/81.36/4.28	1.944	
			DAMFC/gel/ChNWs = 13.71/77.66/8.63	1.504	
			Gelatin	0.522	
19	Silk nanowhiskers (SNWs)/partially deacetylated α-chitin nanofibers (DeChNFs)	Tensile strength, MPa	DeChNFs	102.00 ± 1.09	131
			DeChNFs/SNWs = 98/2	184.05 ± 13.86	
			DeChNFs/SNWs = 95/5	171.25 ± 16.16	
			DeChNFs/SNWs = 90/10	156.97 ± 9.09	
			DeChNFs/SNWs = 50/50	66.38 ± 8.77	
		Elongation at break, %	DeChNFs	9.06 ± 2.80	
			DeChNFs/SNWs = 98/2	6.35 ± 0.76	
			DeChNFs/SNWs = 95/5	6.00 ± 0.84	
			DeChNFs/SNWs = 90/10	4.93 ± 0.59	
			DeChNFs/SNWs = 50/50	4.74 ± 2.06	
		Young's modulus, MPa	DeChNFs	3802.912 ± 563.04	
			DeChNFs/SNWs = 98/2	7987.962 ± 403.88	
			DeChNFs/SNWs = 95/5	6448.212 ± 1121.18	
			DeChNFs/SNWs = 90/10	6422.663 ± 1023.48	
			DeChNFs/SNWs = 50/50	2381.890 ± 450.36	
20	Soy protein isolate (SPI) SPI/ChNWs/ <i>Clitoria ternatea</i> flower extract (CTE)	Tensile strength, MPa	SPI	4.67 ± 0.79	74
			SPI/CTE = 61.54/38.46	3.61 ± 0.92	
			ChNWs/SPI = 61.54/38.46	15.45 ± 0.95	
		Elongation at break, %	ChNWs/SPI/CTE = 38.10/23.81/38.10	13.25 ± 0.47	
			SPI	59.02 ± 1.12	
			SPI/CTE = 61.54/38.46	90.1 ± 5.52	
			ChNWs/SPI = 61.54/38.46	7.05 ± 1.75	
			ChNWs/SPI/CTE = 38.10/23.81/38.10	38.46 ± 3.2	



Table 8 (Contd.)

No.	Polymers	Affected properties	Composition	Value	Ref.
21	SPI/MgO/ChNWs	Antibacterial activity against Gram-positive <i>Bacillus subtilis</i> (inhibition zones, mm)	ChNWs/SPI = 6/94 SPI/MgO = 95/5	5.2 ± 0.25 6 ± 0.18	73
			ChNWs/SPI/MgO = 6/93/1	5 ± 0.28	
			ChNWs/SPI/MgO = 6/89/5	6.5 ± 0.25	
		Thermal stability (residual mass, %)	SPI	12.23	
			ChNWs/SPI/MgO = 6/93/1	18.62	
			ChNWs/SPI/MgO = 6/89/5	17.95	
		Storage modulus (<i>G'</i>), Pa	SPI gel	75.6 ± 3.2	183
			ChNCs/SPI = 0.25/99.75	265.7 ± 9.1	
			ChNCs/SPI = 0.50/99.50	573.2 ± 9.5	
			ChNCs/SPI = 0.75/99.25	897.3 ± 76.3	
			ChNCs/SPI = 1.00/99.00	1024.3 ± 81.6	
		Recovery rate in creep-recovery test, %	SPI gel	80.27 ± 1.11	
			ChNCs/SPI = 0.25/99.75	83.53 ± 1.69	
			ChNCs/SPI = 0.50/99.50	84.47 ± 0.81	
			ChNCs/SPI = 0.75/99.25	84.73 ± 1.21	
			ChNCs/SPI = 1.00/99.00	85.47 ± 1.16	
		Thermal transition temperature, °C	SPI gel	121.43	
			ChNCs/SPI = 0.25/99.75	128.35	
			ChNCs/SPI = 0.50/99.50	129.87	
			ChNCs/SPI = 0.75/99.25	131.72	
			ChNCs/SPI = 1.00/99.00	132.43	
		Crossover modulus, Pa	HA	82	88
			ChNWs/HA = 90.91/9.09	82	
			ChNWs/HA = 97.22/2.78	120	
			ChNWs/HA = 98.04/1.96	83	
		Tensile modulus, GPa	HA	2.58	
			ChNWs/HA = 50.00/50.00	2.6	
			ChNWs/HA = 90.91/9.09	3.2	
			ChNWs/HA = 93.75/6.25	3.5	
			ChNWs/HA = 97.22/2.78	3.95	
			ChNWs/HA = 98.04/1.96	4.54	
		Yield stress, MPa	HA	69.64	
			ChNWs/HA = 50.00/50.00	75	
			ChNWs/HA = 90.91/9.09	77	
			ChNWs/HA = 93.75/6.25	79.00	
			ChNWs/HA = 97.22/2.78	84	
			ChNWs/HA = 98.04/1.96	80.54	

^a The values were estimated from the graphs. ^b The amounts of tannic acid as the crosslinking agent are given in mg of tannic acid per 1 g of chitosan. ^c ChNWs suspensions with different degrees of deacetylation (%DA) were formed under different environmental conditions by optimizing three variables in the deacetylation step: concentration of NaOH (% NaOH), temperature of the oil bath, and reaction time. ^d While coating, the CA film was affixed to a hot plate regulated at a consistent temperature (spray coating temperature, *T*_{spray}). ^e Once the films were formed, they were placed in an oven at a specific temperature (thermal coating temperature, *T*_{thermal}) for one hour and then conditioned. ^f For the optimization of the film properties, the *T*_{spray} and *T*_{thermal} were tuned. ^g *T*_n indicates films that were not thermally treated.

DeChNW load, with both lower and higher concentrations resulting in a decreased tear index. The superior performance of DeChNWs is attributed to their ability to form hydrogen bonds with fiber surfaces and neutralize charges between the positively charged DeChNWs and negatively charged fibers. This improves binding and retention at low concentrations. However, excessive DeChNWs result in uneven dispersion and reduced strength. In contrast, TOChNWs only improve paper strength through hydrogen bonding, lacking the charge-neutralization benefit, making DeChNWs overall more effective.¹²¹

Similarly, microcrystalline cellulose composite cryogels incorporating low concentrations of ChNWs (1 and 2.5 wt%) showed enhanced mechanical properties, as indicated by increased compressive modulus (Table 8, entry 9). However, higher concentrations (5 and 10 wt% ChNWs) reduced the compressive modulus, likely due to ChNW aggregation, which disrupted their uniform distribution, stress redistribution, and reduced cellulose molecule mobility.⁷⁹ The study also evaluated the effect of freezing time on the properties of the MCC cryogels. Extending freezing time to 10 days resulted in a three-fold increase in compressive modulus,⁷⁹ highlighting the importance of optimizing both nanofiller concentration and processing conditions to achieve maximum mechanical performance.

Cellulose acetate (CA), an ester derivative of cellulose, is formed by partially or completely *O*-alkylating the hydroxyl groups in the cellulosic glucose units with acetyl groups. While CA has been used in the biocomposites and bioplastics formation for different industries, it suffers from limitations, such as low stability, mechanical resistance, and reduced adsorption levels. To address these challenges, CA has been reinforced with plant- or animal-derived materials such as chitin, chitosan, *etc.*¹⁷⁷ Incorporating ChNCs into CA films enhanced their hydrophilicity, antifungal activity, and slightly improved (up to 1.2 times) the Young's modulus at a 0.5 wt% concentration (Table 8, entry 10).¹⁷⁸ However, ChNCs negatively affected tensile strength and elongation at break and generally decreased light transmittance in the composite films.¹⁷⁸

Other studies explored the combined effects of chitin nanowhiskers (ChNWs) and cellulose nanocrystals (CNCs) as coatings for CA-based films, particularly for food packaging applications.^{140,141} One of the objectives of the studies was to optimize deacetylation conditions for crab shell chitin to tune the charge and size of the resulting ChNWs and investigate their impact on oxygen permeability in layered film structures (Table 8, entry 11). It was observed that more aggressive deacetylation conditions (higher NaOH concentration, temperature, and longer time) produced shorter ChNWs, but significant surface charge alterations only occurred beyond a specific threshold condition (35% NaOH, 140 °C, 140 min).¹⁴⁰ Despite a ~10% decrease in ultimate tensile strength and no significant change in failure strain, the ChNW-CNC coatings reduced the water vapor transmission rate by ~20% compared to uncoated CA films. Optimized coatings achieved a 91–99% reduction in oxygen permeability (132–16.7 cm³ μm m⁻² day⁻¹

kPa⁻¹ compared to 1553 cm³ μm m⁻² day⁻¹ kPa⁻¹ for uncoated CA films).¹⁴⁰ The follow-up study further evaluated spray-coated ChNWs and CNCs on CA films and tuned the film properties by adjusting the spray coating temperature (T_{spray}) and the post thermal treatment temperature (T_{thermal}).¹⁴¹ By increasing T_{spray} (from 40 to 100 °C) and T_{thermal} (from 40 to 140 °C), the oxygen permeability (OP) decreased by 48% and 62%, respectively. The optimal OP of 11.5 cm³ μm m⁻² day⁻¹ kPa⁻¹ was achieved at T_{thermal} of 140 °C with a controlled T_{spray} of 80 °C (Table 8, entry 12), which is comparable to that of commercial oriented poly(ethylene terephthalate). Higher temperatures also enhanced transmittance and reduced haze, approaching the clarity of bare CA films. The mechanical and water vapor barrier properties of the coated films were improved by an average of 20% and 11%, respectively, compared to pure CA, with minimal impact from temperature variations.¹⁴¹ These findings highlight the potential of chitin nanomaterials as effective reinforcing materials for cellulose acetate-based composites.

4.1.4. Starch. Chitin nanomaterials have demonstrated effective reinforcement of starch-based biocomposites. When added to potato starch through casting and evaporation, chitin nanoparticles (ChNPs) increased the tensile strength and reduced the elongation at break (Table 8, entry 13). This improvement is primarily attributed to enhanced packing rather than the formation of percolation networks. The strong interfacial interaction between ChNPs and potato starch matrix, facilitated by their similar polysaccharide structures, promoted better dispersion and alignment of the reinforcing material within the matrix.⁴⁸ This enhanced packing results in a more cohesive and stable composite structure. The study also investigated water vapor permeability (WVP), a measure of moisture transport through the film. It was observed that WVP of the ChNP-reinforced potato starch composites decreased with increasing ChNPs concentration. Specifically, WVP significantly dropped when the ChNPs content increased from 1 to 3 wt%, with a slight additional decrease as the concentration rose from 3 to 5 wt%. While ChNPs improved water resistance compared to the unreinforced potato starch matrix, their incorporation created a more complex pathway for water molecules to navigate.¹⁷⁹ At low ChNPs concentrations, the nanoparticles were uniformly dispersed within the composite matrix, minimizing paths for water molecules and effectively reducing water permeability. However, at higher concentrations, the excess ChNP tended to aggregate, disrupting the uniform dispersion and inadvertently facilitating water vapor permeation.⁴⁸

In thermoplastic corn starch-based biocomposites, chitin nanofillers notably enhanced mechanical properties (Table 8, entry 14).²⁰ To understand the role of the chitin filler's morphology and aspect ratio in determining the final properties of the composite material, the study individually evaluated two types of chitin nanofillers – nanocrystals (ChNCs) and nanofibers (ChNFs) – by incorporating them one at a time into a corn-starch matrix *via* melt-mixing.²⁰ The incorporation of both ChNC and ChNF improved mechanical performance,



including increased Young's modulus and tensile strength. For instance, increase of ChNCs loading from 5 to 20 wt% enhanced Young's modulus from 222 to 390 MPa and tensile strength from 7.1 to 10.8 MPa. The addition of ChNFs produced significantly better results, with Young's modulus increasing from 330 MPa to 520 MPa and tensile strength rising from 9.9 MPa to 15.0 MPa at 5% and 20% ChNF content, respectively (Table 8, entry 14). These improvements resulted in a notable reduction in elongation at break, decreasing from 38% to 15% for 5 wt% and 20 wt% ChNC loadings, respectively, and from 26% to 9% for 5 wt% and 20 wt% ChNF loadings, respectively. The enhanced mechanical performance of the ChNCs/corn-starch and ChNFs/corn-starch composites is primarily attributed to: (a) the formation of a rigid network of ChNCs or ChNFs, driven by intra- and intermolecular hydrogen bonds; (b) the interlocking or mutual entanglement of the chitin nanofillers with the starch matrix; and (c) the effective stress transfer from the matrix to the chitin nanofillers.^{48,180}

It also appears from the study that the mechanical behavior of the ChNCs/corn-starch composites may be enhanced by increased crystallinity attributed to the nucleating effect of ChNCs. In contrast, the superior mechanical properties of ChNFs/corn-starch composites are primarily due to the percolation effect. ChNFs, due to their high aspect ratio ($L/d = 60$) and extended fibrillar structure, form an interconnected network within the starch matrix. The entanglement of long chitin fibrils with the starch molecules also reinforces the matrix by creating multiple points of interaction, further increasing the composite's resistance to mechanical stress. This percolation effect is particularly significant because it allows for the formation of a continuous and rigid phase even at relatively low filler concentrations. As a result, the ChNFs/corn-starch composites exhibited better mechanical performance, such as higher tensile strength and Young's modulus, compared to the ChNC/corn-starch counterparts.²⁰ Furthermore, incorporating chitin nanofillers into corn-starch matrix improved both thermal and storage modulus compared to the starch matrix, with the nanofiber-based materials outperforming those with nanoparticles.²⁰

4.1.5. Gelatin. Gelatin, a natural biopolymer, derived from the partial hydrolysis of collagens, is an abundant structural protein found in various parts of the animal and human tissues. It offers excellent film-forming ability, transparency, oxygen barrier, and UV-light absorption. Additionally, gelatin serves as a versatile vehicle for incorporating a wide range of additives and can be modified through its diverse functional groups. However, like some other natural polymers, gelatin faces challenges, including high sensitivity to moisture, and poor mechanical and thermal properties, limiting its use in the food industry, drug delivery systems, and biomedical tissue engineering fields. To enhance its functionality, gelatin is often reinforced with chitin nanomaterials, or *via* a combined approach of crosslinking and nanochitin reinforcement. Several studies have demonstrated the significant reinforcing effects of chitin nanomaterial on gelatin composites and films, as summarized in Table 8, entries 15–18. Most of these

studies demonstrate significant improvements in mechanical properties such as enhanced Young's modulus and tensile strength, due to the reinforcement effect of nanochitin in the matrix. However, the extent of these effects is influenced by various factors such as the preparation conditions of the nanochitin/gelatin composite, the concentration of both gelatin and nanochitin, and the nature and strength of interactions between nanochitin and the gelatin matrix.

For example, Etxabide *et al.* developed glucose-crosslinked gelatin films reinforced with ChNWs and observed a significant increase in Young's modulus and tensile strength, reaching 2921 MPa, and 77 MPa, respectively at the 4 wt% ChNW content (Table 8, entry 15).⁷⁸ These property alterations were reportedly attributed to the following factors. First, the reaction enhances the organized structure of the matrix (*i.e.*, increases crystallinity), contributing to greater stiffness and thermal stability. Second, the Maillard reaction, which involves the interaction of glucose (used as a crosslinking agent) with amino groups in gelatin, forms covalent bonds that improve mechanical properties. Finally, to a lesser extent, the formation of noncovalent interactions between ChNWs and gelatin also plays a role.⁷⁸

Additionally, the addition of ChNWs in the films notably improve UV-Vis light absorption capacity and thermal stability of the films. However, the reinforced films became less flexible and less transparent likely due to increased density of crosslinks which reduces molecular mobility and changes the films' light-scattering characteristics.⁷⁸

Another study used the immersion method for composites preparation, where the gelatin films have been soaked in a solution containing the chitin nanofibers, followed by drying at room temperature to form the composite. The improved mechanical performance along with high transparency were achieved (Table 8, entry 16).¹⁴³ The Young's modulus of the 50.2%-ChNFs/gelatin (with a ChNF content of 50.2%) was approximately 5192 MPa – nearly double that of pure gelatin. Furthermore, this parameter increased as the ChNF content in the gelatin increased attributed to the reinforcing effect of the ChNF nano-networks and the hydrogen bond formation between gelatin and chitin molecules.

This group also investigated the effect of surface-deacetylated chitin nanofibers (S-ChNFs, DA = $63 \pm 2\%$) on gelatin nanocomposites and observed a significant improvement in composites' tensile properties.¹⁸¹ Furthermore, when comparing the performance of the S-ChNFs/gelatin to ChNWs/gelatin composites at the same component ratio, the S-ChNFs/gelatin composite exhibited higher stress and Young's modulus (Table 8, entry 17). This enhancement is attributed to surface deacetylation, which reduces fiber diameter and increases the aspect ratio of nanofibers, facilitating the formation of densely interconnected nanonetworks within the gelatin matrix.¹⁸² The strong interactions between chitin and gelatin molecules further contributed to the improved mechanical properties of S-ChNFs/gelatin composites.¹⁸¹

A recent study provided a promising approach for developing biocompatible and conductive hydrogels, leveraging the



synergistic effects of gelatin, cellulose-based nanofibers, and chitin-derived nanowhiskers. It successfully fabricated conductive gelatin-based hydrogels by integrating a gelatin solution with suspensions of dialdehyde microfibrillated cellulose (DAMFC) and carboxylated chitin nanowhiskers (ChNWs). The fabrication process involved mixing these components, casting the resulting mixture, and incubating it at room temperature. The improved mechanical strength along with good electrical conductivity and freezing tolerance were achieved (Table 8, entry 18).¹²⁰ When DAMFC was incorporated without ChNWs, the resulting hydrogel exhibited an increased compressive stress reaching 1.949 MPa, which is ~ 4 times higher than that of pure gelatin. This enhancement was attributed to the formation of a robust dynamic 3D network, arising from the Schiff base reaction between the aldehyde groups on the surface of the DAMFC fibrils and the amino groups of the gelatin.¹²⁰ When both DAMFC and ChNWs were introduced, the compressive stress of the composite hydrogels increased further, reaching a the highest level at 2 wt% of ChNWs (Table 8, entry 18). At higher ChNWs loadings (>2 wt%), aggregation of the excessive ChNWs led to the stress concentration in the hydrogel ultimately impairing its mechanical performance.¹²⁰

This group also investigated the conductivity and freezing-tolerance of 2 wt% ChNW-reinforced DAMFC/Gel hydrogels through ion immersion. The researchers found that soaking the hydrogels in NaCl solution significantly enhanced their ionic conductivity, making it approximately four times higher than that of hydrogels soaked in pure water. Additionally, the hydrogels maintained their flexibility even at -20 °C, demonstrating excellent freezing resistance.¹²⁰ Overall, the reinforcing effects of chitin nanomaterials on gelatin composites are attributed to good compatibility and interactions between chitin and gelatin. These properties make ChNW-reinforced DAMFC/Gel hydrogels promising materials for applications in biomedical, food packaging, and active packaging industries where mechanical strength, conductivity, and temperature resilience are critical.

4.1.6. Silk. A recent study focused on creating composite membranes by combining silk nanowhiskers (SNWs) with partially deacetylated chitin nanofibers (DeChNFs) for applications requiring high mechanical strength and flexibility.¹³¹ Silk nanowhiskers (SNWs) were incorporated into DeChNFs at a pH of 3 to form SNW-DeChNF composite membranes, whose mechanical performance was evaluated. DeChNF membranes alone exhibited a tensile stress of 102.00 ± 1.09 MPa, tensile strain of $9.06 \pm 2.80\%$, and Young's modulus of 3802.91 ± 563.04 MPa (Table 8, entry 19). The addition of SNWs significantly enhanced performance. The study identified 2 wt% SNWs as the optimal concentration for balancing mechanical performance and material integrity, resulting in membranes with tensile stress of 184.05 ± 13.86 MPa and Young's modulus of 7987.96 ± 403.88 MPa. At higher SNW loadings ($\sim 50\%$), aggregation disrupted uniformity and reduced the material's ability to evenly distribute stress, highlighting importance of controlling filler dispersion as a critical factor to optimizing performance.

4.1.7. Soy protein isolate. Recent studies have investigated the reinforcing effects of chitin nanomaterials on soy protein isolate (SPI) films and gels.^{73,74,183,184} Koshy *et al.* successfully developed pH-sensitive SPI-based films modified with ChNWs and *Clitoria ternatea* flower extract (CTE).⁷⁴ Incorporating 8 wt% ChNWs into the SPI matrix enhanced tensile strength by ~ 4.3 times compared to pure SPI (Table 8, entry 20). While the inclusion of CTE slightly reduced the tensile strength of ChNWs/SPI films, it imparted pH sensitivity, making the films suitable for use as pH indicators for monitoring the freshness of packaged food products.⁷⁴ This group further evaluated the effect of ChNWs combined with magnesium oxide nanoparticles (MgO) as hybrid nanofillers on SPI films. The addition of MgO and ChNWs significantly improved thermal stability and antibacterial activity, making these films promising for active food packaging applications (Table 8, entry 21).⁷³

Another recent study successfully developed strong acid-induced SPI gels by incorporating ChNCs and proposing a gelatinization mechanism (Table 8, entry 22).¹⁸³ The process involved mixing SPI powder with a ChNC suspension at pH 3 to form a SPI-ChNC solution, adding gluconolactone (GDL), which hydrolyzed into gluconic acid, gradually reducing the solution's pH, and lowering the net surface charge of protein aggregates, leading to acid-induced gel formation. The addition of ChNCs into SPI gels improved the storage modulus, recovery rate, and thermal stability of SPI gels. These improvements are attributed to strong interactions between ChNC and SPI matrix, including electrostatic interactions and hydrogen bonding.¹⁸³

Raman spectroscopy revealed that ChNCs altered the secondary protein structure of SPI gels. With the addition of 1.00% ChNCs, the α -helix content decreased from 19.7% to 12.1% whereas β -sheet increased from 46.5% to 52.6%. This transformation indicates that ChNCs promote protein unfolding and orderly aggregation, forming a densely cross-linked gel network. Additionally, the incorporation of ChNCs strengthened the SPI gel by enhancing hydrophobic interactions, electrostatic interactions, and hydrogen bonding further stabilizing the gel matrix.¹⁸³

4.1.8. Hyaluronic acid. Hyaluronic acid (HA), also known as hyaluronan is a glycosaminoglycan, an anionic polysaccharide made up of glucuronic acid and *N*-acetylglucosamine disaccharide units, each containing one carboxyl group.¹⁸⁵ HA is widely used due to its biocompatibility, nontoxicity, and healing properties. It can be processed into various forms, such as hydrogels,¹⁸⁶ fibers,¹⁸⁷ or scaffolds.¹⁸⁸ However, HA suffers from poor mechanical stability, rapid degradation,¹⁸⁹ and lacks antimicrobial properties, which limit its use, particularly in tissue engineering and drug delivery applications. To overcome these challenges, recent research has explored reinforcing HA hydrogels and biofilms with nanofillers. Studies have demonstrated that partially deacetylated chitin nanowhiskers (ChNWs) (DA = 73%) significantly enhance the mechanical properties of HA biofilms. This reinforcement is evident through increased crossover modulus, tensile modulus, and yield stress (Table 8, entry 23).



The crossover modulus of ChNWs/HA composites increased nearly linearly from 82 Pa to 120 Pa as the ChNW content rose to 35 vol%. However, at 50 vol% of ChNWs, the modulus dropped to 83 Pa, suggesting excessive nanofiller aggregation compromised the mechanical network. Tensile modulus and stress was also considerably enhanced, with the highest improvements observed at 35–50 vol% of ChNWs in the HA matrix. Furthermore, the nanocomposite biofilms demonstrated strong antibacterial properties while maintaining cytocompatibility, which improved as the volume fraction of ChNWs in the HA matrix increased.⁸⁸

4.2. Reinforcement of elastomers with chitin nanomaterials

4.2.1. Natural rubber. Natural rubber (NR), a type of rubber derived from the latex of rubber trees (*Hevea brasiliensis*), is primarily composed of polyisoprene.^{190–192} Natural rubber is known for its excellent elasticity, flexibility, and resistance to wear, making it an important material in a wide variety of applications, including tires, medical devices, footwear, industrial goods, and in aerospace technologies.¹⁹³ While natural rubber has many desirable properties, its limitations – especially associated with resistance to heat, UV, ozone, and certain chemicals – can impact its performance in specific applications.¹⁹⁴ For example, it often requires vulcanization (a process of heating with sulfur) to enhance its properties and improve its durability.¹⁹⁵ The degree of vulcanization affects the performance, and improper vulcanization can lead to inconsistencies in the rubber's properties, such as poor elasticity or excessive brittleness.^{196–198} Overcoming these limitations typically involves compounding with additives or blending with synthetic rubbers, and with reinforcing agents to enhance its durability and versatility.

Several studies have explored how nanochitin disperses in NR matrix with different modifications to evaluate the level of reinforcement as summarized in Table 9, entries 1–3. Comprehensive studies by Nair and coworkers^{25,51,147} explored the reinforcement effects of colloidal ChNW in NR latex. Their preliminary study exploited the role of ChNWs in reinforcing both unvulcanized and prevulcanized NR latex, with composites prepared using the casting-evaporation method (Table 9, entry 1).^{25,51} Both unvulcanized and prevulcanized NR latex exhibited similar tensile moduli, measuring 1.7 MPa and 1.6 MPa, respectively. The addition of ChNWs at all loadings significantly improved the tensile modulus, with the reinforced unvulcanized NR composites (229 MPa at 20 wt% load) outperforming vulcanized ones (111 MPa at the same load). A similar trend was also observed in the conventional modulus. It is suggested that the interference of chemical cross-linking reactions during vulcanization hinders the formation of chitin network, resulting in a lower reinforcing effect and consequently, lower tensile and conventional moduli in vulcanized samples.

The study further investigated the impact of the processing techniques on the properties of the unvulcanized-based composites.⁵¹ Two techniques, *i.e.*, water evaporation and freeze-drying followed by a hot-pressing step, were evaluated and

compared. The results that the composite films produced by the later method were up to 20 times mechanically weaker than those prepared by casting-evaporation (10.2 vs. 229 MPa, respectively, see Table 9, entries 1 and 2). This discrepancy is likely due to the insufficient formation of a robust 3-D rigid network through hydrogen bond interaction, caused by the rapid solvent removal in freeze-drying compared to the slower solvent removal in casting-evaporation.

Surface modification is often necessary for effectively dispersing nanochitin in NR latex due to the negatively charged phospholipid layers and protein in NR latex, which remain stable only in basic medium,¹⁹⁹ whereas amino groups in nanochitin are stable in mildly acidic medium.¹⁹⁸ To address this, Nair *et al.*¹⁴⁷ conducted a follow-up study where they modified ChNWs using three chemical coupling agents: phenyl isocyanate (PI), alkenyl succinic anhydride (ASA) (Accosize 18 from American Cyanamid), and 3-isopropenyl-R, R'dimethylbenzyl isocyanate (TMI). The study focused solely on 10 wt% ChNW reinforcement and used the casting-evaporation method to prepare NR composite films. SEM and swelling studies confirmed that the chemical modification improved the adhesion between NR and ChNWs. Regardless of the coupling agent used, the incorporation of surface-modified ChNWs moderately enhanced the tensile modulus (1.5 to 5.5-fold) and stress at break (2.3- to 4.3-fold) of the NR films, with ASA-modified ChNW films showing superior performance compared to TMI- and PI-modified ChNW films (Table 9, entry 3). The improved tensile properties of ASA-modified ChNW composite were attributed to the partial existence of a chitin-chitin network within the NR matrix. However, these enhance mechanical properties were significantly lower compared to the unmodified ChNWs/NR films in their previous study. For instance, the tensile modulus of the modified ChNW-ASA/NR films (Table 9, entry 3) was nearly half that of the unmodified ChNW/prevulcanized NR film (Table 9, entry 1). This significant reduction following chemical modification was likely due to the partial or total degradation of 3-D chitin network present in the unmodified films, with a more pronounced reduction observed in the case of isocyanate modifications.

Another study reported the successful fabrication of self-assembled ChNF-NR composite sheets using re-dispersed ChNFs and NR latex.¹⁹⁹ In this study, self-assembled ChNFs were redispersed in aqueous ammonia solution after being isolated as a film and then mixed with NR latex at various ChNF loadings (~1 to 17 wt%). SEM and XRD results confirmed that ChNFs were well re-dispersed in ammonia and evenly dispersed in the NR latex with increased crystallinity as the ChNF loading increased. With the addition of ChNFs up to 17 wt%, both tensile strength and Young's modulus of the NR latex increased by ~4.6-fold and 26–8, respectively (Table 9, entry 4), demonstrating the reinforcing effect of ChNFs. Meanwhile, elongation at break consistently dropped from 1125% for neat NR sheet to 247% at ~17 wt% loading, implying increased brittleness with higher ChNF content.

Rod-like structure ChNCs were used as a reinforcing agent for unvulcanized NR latex.¹³ When incorporated at different





Table 9 Reinforcement of rubbers with nanochitin

No.	Polymers	Property affected	Composition	Value	Ref.
1	Natural rubber Unvulcanized natural rubber latex (unvulc. NR) and prevulcanized natural rubber latex (prevulc. NR)/ChNWs (casting-evaporation method)	Tensile modulus, MPa	Unvulc. NR	1.7	25 and 51
			ChNWs/unvulc. NR = 2/98	5.6	
			ChNWs/unvulc. NR = 5/95	17.8	
			ChNWs/unvulc. NR = 10/90	—	
			ChNWs/unvulc. NR = 15/85	127	
			ChNWs/unvulc. NR = 20/80	229	
			Prevulc. NR	1.6	
			ChNWs/prevulc. NR = 2/98	2.5	
			ChNWs/prevulc. NR = 5/95	—	
			ChNWs/prevulc. NR = 10/90	25.9	
		Conventional modulus, %	ChNWs/prevulc. NR = 15/85	52.8	
			ChNWs/prevulc. NR = 20/80	111	
			Unvulc. NR	1.8	
			ChNWs/unvulc. NR = 2/98	2.5	
			ChNWs/unvulc. NR = 5/95	5	
			ChNWs/unvulc. NR = 10/90	—	
			ChNWs/unvulc. NR = 15/85	17	
			ChNWs/unvulc. NR = 20/80	23.9	
			Prevulc. NR	1.6	
			ChNWs/prevulc. NR = 2/98	2.1	
		Stress at break, MPa	ChNWs/prevulc. NR = 5/95	—	
			ChNWs/prevulc. NR = 10/90	6.8	
			ChNWs/prevulc. NR = 15/85	11.4	
			ChNWs/prevulc. NR = 20/80	15.3	
			Unvulc. NR	25.5	
			ChNWs/unvulc. NR = 2/98	21.7	
			ChNWs/unvulc. NR = 5/95	25	
			ChNWs/unvulc. NR = 10/90	—	
			ChNWs/unvulc. NR = 15/85	29.7	
			ChNWs/unvulc. NR = 20/80	9.8	
		Elongation at break, %	Prevulc. NR	395	
			ChNWs/prevulc. NR = 2/98	388	
			ChNWs/prevulc. NR = 5/95	—	
			ChNWs/prevulc. NR = 10/90	178	
			ChNWs/prevulc. NR = 15/85	128	
			ChNWs/prevulc. NR = 20/80	20.5	
			Unvulc. NR	248	
			ChNWs/unvulc. NR = 2/98	213	
			ChNWs/unvulc. NR = 5/95	192	
			ChNWs/unvulc. NR = 10/90	—	
			ChNWs/unvulc. NR = 15/85	133	
			ChNWs/unvulc. NR = 20/80	126	
			Prevulc. NR	11.8	
			ChNWs/prevulc. NR = 2/98	13.7	
			ChNWs/prevulc. NR = 5/95	—	
			ChNWs/prevulc. NR = 10/90	10.5	
			ChNWs/prevulc. NR = 15/85	9.4	
			ChNWs/prevulc. NR = 20/80	5.6	



Table 9 (Contd.)

No.	Polymers	Property affected	Composition	Value	Ref.
2	Unvulcanized natural rubber (unvulc. NR) latex/ChNWs (freeze-drying and hot pressing method)	Tensile modulus, MPa	Unvulc. NR	1.1	25 and 51
			ChNWs/unvulc. NR = 2/98	1.4	
			ChNWs/unvulc. NR = 5/95	2.1	
			ChNWs/unvulc. NR = 10/90	4.6	
			ChNWs/unvulc. NR = 15/85	8.7	
		Conventional modulus, %	ChNWs/unvulc. NR = 20/80	10.2	
			Unvulc. NR	0.71	
			ChNWs/unvulc. NR = 2/98	0.99	
			ChNWs/unvulc. NR = 5/95	1.7	
			ChNWs/unvulc. NR = 10/90	3.4	
		Stress at break, MPa	ChNWs/unvulc. NR = 15/85	7.2	
			ChNWs/unvulc. NR = 20/80	9.4	
			Unvulc. NR	41.6	
			ChNWs/unvulc. NR = 2/98	5.9	
			ChNWs/unvulc. NR = 5/95	115.5	
3	Natural rubber (NR) latex/chitin nanowhiskers grafted with alkenyl succinic anhydride (ASA), phenyl isocyanate (PI), and isopropenyl- α,α' -dimethylbenzylisocyanate (TMI) (casting-evaporation method)	Elongation at break, %	ChNWs/unvulc. NR = 10/90	21.7	
			ChNWs/unvulc. NR = 15/85	62.7	
			ChNWs/unvulc. NR = 20/80	83.9	
			Unvulc. NR	252	
			ChNWs/unvulc. NR = 2/98	176	
		Tensile modulus, MPa	ChNWs/unvulc. NR = 5/95	175	
			ChNWs/unvulc. NR = 10/90	160	
			ChNWs/unvulc. NR = 15/85	179	
			ChNWs/unvulc. NR = 20/80	176	
			NR	0.96	147
		Stress at break, MPa	ChNWs-ASA/NR = 10/90	5.5	
			ChNWs-TMI/NR = 10/90	2.5	
			ChNWs-PI/NR = 10/90	1.7	
			NR	2.4	
			ChNWs-ASA/NR = 10/90	10.3	
4	Natural rubber (NR) latex/chitin nanofibers (ChNFs)	Elongation at break, %	ChNWs-TMI/NR = 10/90	5.5	
			ChNWs-PI/NR = 10/90	5.5	
			NR	195	
			ChNWs-ASA/NR = 10/90	150	
			ChNWs-TMI/NR = 10/90	128	
		Young's modulus, MPa	ChNWs-PI/NR = 10/90	184	
			NR	0.4	199
			ChNFs/NR = 0.99/99.01	0.5	
			ChNFs/NR = 1.96/98.04	0.8	
			ChNFs/NR = 9.09/90.91	8.8	
		Tensile strength, MPa	ChNFs/NR = 16.67/83.33	10.7	
			NR	0.5	
			ChNFs/NR = 0.99/99.01	0.5	
			ChNFs/NR = 1.96/98.04	0.6	
			ChNFs/NR = 9.09/90.91	1.7	
4		Elongation at break, %	ChNFs/NR = 16.67/83.33	2.3	
			NR	1125	
			ChNFs/NR = 0.99/99.01	1002	
			ChNFs/NR = 1.96/98.04	945	
			ChNFs/NR = 9.09/90.91	602	
			ChNFs/NR = 16.67/83.33	247	



Table 9 (Contd.)

No.	Polymers	Property affected	Composition	Value	Ref.
5	Unvulcanized natural rubber latex (unvulc. NR)/chitin nanocrystals (ChNCs)	Tensile strength, MPa	Unvulc. NR	0.92 ± 0.12	13
			ChNCs/unvulc. NR = 1.0/99.0	2.26 ± 0.18	
		Tensile modulus at 100% strain, MPa	ChNCs/unvulc. NR = 2.5/97.5	2.82 ± 0.14	
			ChNCs/unvulc. NR = 5.0/95.0	3.30 ± 0.21	
			ChNCs/unvulc. NR = 7.5/92.5	4.90 ± 0.15	
			ChNCs/unvulc. NR = 10.0/90.0	5.75 ± 0.14	
			Unvulc. NR	0.40 ± 0.07	
			ChNCs/unvulc. NR = 1.0/99.0	0.40 ± 0.09	
		Tensile modulus at 300% strain, MPa	ChNCs/unvulc. NR = 2.5/97.5	0.57 ± 0.03	
			ChNCs/unvulc. NR = 5.0/95.0	0.59 ± 0.10	
			ChNCs/unvulc. NR = 7.5/92.5	1.53 ± 0.04	
			ChNCs/unvulc. NR = 10.0/90.0	1.83 ± 0.06	
			Unvulc. NR	0.49 ± 0.03	
			ChNCs/unvulc. NR = 1.0/99.0	0.47 ± 0.07	
		Tensile modulus at 500% strain, MPa	ChNCs/unvulc. NR = 2.5/97.5	0.81 ± 0.05	
			ChNCs/unvulc. NR = 5.0/95.0	0.96 ± 0.14	
			ChNCs/unvulc. NR = 7.5/92.5	3.14 ± 0.07	
			ChNCs/unvulc. NR = 10.0/90.0	4.20 ± 0.10	
			Unvulc. NR	0.56 ± 0.04	
			ChNCs/unvulc. NR = 1.0/99.0	0.68 ± 0.10	
		Elongation at break, %	ChNCs/unvulc. NR = 2.5/97.5	1.47 ± 0.08	
			ChNCs/unvulc. NR = 5.0/95.0	2.17 ± 0.11	
			ChNCs/unvulc. NR = 7.5/92.5	—	
			ChNCs/unvulc. NR = 10.0/90.0	—	
			Unvulc. NR	685.1 ± 28.0	
			ChNCs/unvulc. NR = 1.0/99.0	825.8 ± 36.5	
		Tear strength, kN m ⁻¹	ChNCs/unvulc. NR = 2.5/97.5	699.2 ± 20.8	
			ChNCs/unvulc. NR = 5.0/95.0	606.7 ± 30.0	
			ChNCs/unvulc. NR = 7.5/92.5	416.2 ± 22.0	
			ChNCs/unvulc. NR = 10.0/90.0	382.5 ± 24.6	
			Unvulc. NR	2.27	
			ChNCs/unvulc. NR = 1.0/99.0	4.93	
		Storage modulus, MPa (−100 °C)	ChNCs/unvulc. NR = 2.5/97.5	6.05	
			ChNCs/unvulc. NR = 5.0/95.0	6.91	
			ChNCs/unvulc. NR = 7.5/92.5	9.89	
			ChNCs/unvulc. NR = 10.0/90.0	12.33	
			Unvulc. NR	279.4	
			ChNCs/unvulc. NR = 1.0/99.0	206.36	
		Storage modulus, MPa (−40 °C)	ChNCs/unvulc. NR = 2.5/97.5	340.54	
			ChNCs/unvulc. NR = 5.0/95.0	602.68	
			ChNCs/unvulc. NR = 7.5/92.5	946.44	
			ChNCs/unvulc. NR = 10.0/90.0	2992.68	
			Unvulc. NR	1.2	
			ChNCs/unvulc. NR = 1.0/99.0	4.79	
		Storage modulus, MPa (30 °C)	ChNCs/unvulc. NR = 2.5/97.5	7.69	
			ChNCs/unvulc. NR = 5.0/95.0	12.13	
			ChNCs/unvulc. NR = 7.5/92.5	22.71	
			ChNCs/unvulc. NR = 10.0/90.0	218.01	
			Unvulc. NR	0.13	
			ChNCs/unvulc. NR = 1.0/99.0	0.42	
			ChNCs/unvulc. NR = 2.5/97.5	0.64	



Table 9 (Contd.)

No.	Polymers	Property affected	Composition	Value	Ref.
6	Prevulcanized NR latex/ChNFs	Tensile strength, ^a MPa	ChNCs/unvulc. NR = 5.0/95.0	1.65	201
			ChNCs/unvulc. NR = 7.5/92.5	2.44	
			ChNCs/unvulc. NR = 10.0/90.0	12.48	
			Prevulc. NR	6.37	
			ChNFs/prevulc. NR = 0.3/99.7	13.42	
		Elongation at break ^a , %	ChNFs/prevulc. NR = 0.5/99.5	13.62	
			ChNFs/prevulc. NR = 1.0/99.0	15.71	
			ChNFs/prevulc. NR = 2.0/98.0	13.92	
			Prevulc. NR	843.9	
			ChNFs/prevulc. NR = 0.3/99.7	913.2	
		Toughness ^a , MJ m ⁻³	ChNFs/prevulc. NR = 0.5/99.5	877.3	
			ChNFs/prevulc. NR = 1.0/99.0	842.5	
			ChNFs/prevulc. NR = 2.0/98.0	707.9	
			Prevulc. NR	17.87	
			ChNFs/prevulc. NR = 0.3/99.7	35.18	
7	Prevulcanized NR latex/zwitterionic ChNFs (Z-ChNFs) and carboxylated ChNFs (C-ChNFs)	Young's modulus ^a , MPa	ChNFs/prevulc. NR = 0.5/99.5	38.79	202
			ChNFs/prevulc. NR = 1.0/99.0	41.58	
			ChNFs/prevulc. NR = 2.0/98.0	54.58	
			Prevulc. NR	0.47	
			C-ChNFs/prevulc. NR ^b ≈ 0.50/99.50	0.67	
		Stress at 100% strain ^a , MPa	C-ChNFs/prevulc. NR ≈ 0.99/99.01	0.8	
			C-ChNFs/prevulc. NR ≈ 1.96/98.04	1.39	
			C-ChNFs/prevulc. NR ≈ 3.38/96.62	2.71	
			Z-ChNFs/prevulc. NR ^b ≈ 0.50/99.50	0.47	
			Z-ChNFs/prevulc. NR ≈ 0.99/99.01	0.52	
			Z-ChNFs/prevulc. NR ≈ 1.96/98.04	0.61	
			Z-ChNFs/prevulc. NR ≈ 3.38/96.62	1.98	
			Prevulc. NR	0.58	
			C-ChNFs/prevulc. NR ^b ≈ 0.50/99.50	0.76	
			C-ChNFs/prevulc. NR ≈ 0.99/99.01	1.01	
			C-ChNFs/prevulc. NR ≈ 1.96/98.04	0.76	
			C-ChNFs/prevulc. NR ≈ 3.38/96.62	2.17	
			Z-ChNFs/prevulc. NR ^b ≈ 0.50/99.50	0.55	
			Z-ChNFs/prevulc. NR ≈ 0.99/99.01	0.63	
			Z-ChNFs/prevulc. NR ≈ 1.96/98.04	0.7	
			Z-ChNFs/prevulc. NR ≈ 3.38/96.62	0.99	



Table 9 (Contd.)

No.	Polymers	Property affected	Composition	Value	Ref.
8	Synthetic rubbers Acrylonitrile butadiene rubber (NBR)/ChNWs	Stress at 300% strain ^a , MPa	Prevulc. NR	0.94	18
			C-ChNFs/prevulc. NR ^b ≈ 0.50/ 99.50	1.76	
			C-ChNFs/prevulc. NR ≈ 0.99/ 99.01	3.14	
			C-ChNFs/prevulc. NR ≈ 1.96/ 98.04	3.01	
			C-ChNFs/prevulc. NR ≈ 3.38/ 96.62	4.26	
			Z-ChNFs/prevulc. NR ^b ≈ 0.50/ 99.50	1.07	
			Z-ChNFs/prevulc. NR ≈ 0.99/ 99.01	1.07	
			Z-ChNFs/prevulc. NR ≈ 1.96/ 98.04	1.31	
			Z-ChNFs/prevulc. NR ≈ 3.38/ 96.62	1.82	
		Tensile strength, MPa	NBR	2.75 ± 0.25	
			ChNWs/NBR ^b = 3.84/96.16	5.95 ± 0.67	
			ChNWs/NBR = 7.41/92.59	5.02 ± 0.89	
			ChNWs/NBR = 10.71/89.29	4.69 ± 0.37	
			NBR	1.95 ± 0.20	
			ChNWs/NBR ^b = 3.84/96.16	4.27 ± 0.49	
			ChNWs/NBR = 7.41/92.59	4.71 ± 0.38	
			ChNWs/NBR = 10.71/89.29	5.87 ± 0.25	
			Tensile modulus at 300% strain, MPa	NBR	
ChNWs/NBR ^b = 3.84/96.16	354 ± 11				
ChNWs/NBR = 7.41/92.59	363 ± 12				
ChNWs/NBR = 10.71/89.29	371 ± 14				
NBR	19.76 ± 0.75				
ChNWs/NBR ^b = 3.84/96.16	24.85 ± 0.61				
ChNWs/NBR = 7.41/92.59	28.98 ± 0.69				
ChNWs/NBR = 10.71/89.29	31.25 ± 0.67				
Elongation at break, %	NBR	45 ± 1			
	ChNWs/NBR ^b = 3.84/96.16	48 ± 1			
	ChNWs/NBR = 7.41/92.59	51 ± 1			
	ChNWs/NBR = 10.71/89.29	53 ± 1			
	NBR	10.23 ± 0.25			
	ChNWs/NBR ^b = 3.84/96.16	18.43 ± 0.25			
	ChNWs/NBR = 7.41/92.59	14.38 ± 0.29			
	ChNWs/NBR = 10.71/89.29	15.75 ± 0.25			
	Tear strength, N mm ⁻¹	NBR	180 ± 5		
ChNWs/NBR ^b = 3.84/96.16		192 ± 3			
ChNWs/NBR = 7.41/92.59		186 ± 4			
ChNWs/NBR = 10.71/89.29		183 ± 5			
NBR		207 ± 2			
ChNWs/NBR ^b = 3.84/96.16		204 ± 1			
ChNWs/NBR = 7.41/92.59		205 ± 1			
ChNWs/NBR = 10.71/89.29		209 ± 2			
Hardness, shore A		NBR	2.75 ± 0.25		
	ChNWs/NBR ^b = 3.84/96.16	5.95 ± 0.67			
	ChNWs/NBR = 7.41/92.59	5.02 ± 0.89			
	ChNWs/NBR = 10.71/89.29	4.69 ± 0.37			
	NBR	1.95 ± 0.20			
	ChNWs/NBR ^b = 3.84/96.16	4.27 ± 0.49			
	ChNWs/NBR = 7.41/92.59	4.71 ± 0.38			
	ChNWs/NBR = 10.71/89.29	5.87 ± 0.25			
	Compression set, %	NBR	395 ± 15		
ChNWs/NBR ^b = 3.84/96.16		354 ± 11			
ChNWs/NBR = 7.41/92.59		363 ± 12			
ChNWs/NBR = 10.71/89.29		371 ± 14			
NBR		19.76 ± 0.75			
ChNWs/NBR ^b = 3.84/96.16		24.85 ± 0.61			
ChNWs/NBR = 7.41/92.59		28.98 ± 0.69			
ChNWs/NBR = 10.71/89.29		31.25 ± 0.67			
Abrasion resistance index, ARI		NBR	45 ± 1		
	ChNWs/NBR ^b = 3.84/96.16	48 ± 1			
	ChNWs/NBR = 7.41/92.59	51 ± 1			
	ChNWs/NBR = 10.71/89.29	53 ± 1			
	NBR	10.23 ± 0.25			
	ChNWs/NBR ^b = 3.84/96.16	18.43 ± 0.25			
	ChNWs/NBR = 7.41/92.59	14.38 ± 0.29			
	ChNWs/NBR = 10.71/89.29	15.75 ± 0.25			
	Swelling index, %	NBR	180 ± 5		
ChNWs/NBR ^b = 3.84/96.16		192 ± 3			
ChNWs/NBR = 7.41/92.59		186 ± 4			
ChNWs/NBR = 10.71/89.29		183 ± 5			
NBR		207 ± 2			
ChNWs/NBR ^b = 3.84/96.16		204 ± 1			
ChNWs/NBR = 7.41/92.59		205 ± 1			
ChNWs/NBR = 10.71/89.29		209 ± 2			



Table 9 (Contd.)

No.	Polymers	Property affected	Composition	Value	Ref.
9	Carboxylated styrene butadiene rubber (XSBR) latex/ChNWs	Cross-link density, mol g ⁻¹ × 10 ⁻⁴	NBR	1.31 ± 0.05	146
			ChNWs/NBR ^b = 3.84/96.16	1.38 ± 0.03	
			ChNWs/NBR = 7.41/92.59	1.34 ± 0.05	
		Storage modulus, MPa (25 °C)	ChNWs/NBR = 10.71/89.29	1.29 ± 0.06	
			NBR	3.651	
			ChNWs/NBR ^b = 3.84/96.16	6.157	
		Storage modulus, MPa (−40 °C)	ChNWs/NBR = 10.71/89.29	5.968	
			NBR	1189	
			ChNWs/NBR ^b = 3.84/96.16	1473	
		<i>T_g</i> , °C	ChNWs/NBR = 10.71/89.29	1384	
			NBR	−4.09	
			ChNWs/NBR ^b = 3.84/96.16	2.78	
		tan δ maximum	ChNWs/NBR = 10.71/89.29	1.07	
			NBR	1.535	
			ChNWs/NBR ^b = 3.84/96.16	0.985	
		Storage modulus at 25 °C, MPa (non-annealed)	ChNWs/NBR = 10.71/89.29	1.119	
			XSBR	1.39	
			ChNWs/XSBR = 4.1/95.9	3.95	
		Storage modulus at 25 °C, MPa (annealed at 100 °C)	ChNWs/XSBR = 6.6/93.4	8.9	
			ChNWs/XSBR = 9.0/91.0	17.7	
			XSBR	1.44	
		Loss modulus at 25 °C, MPa (non-annealed)	ChNWs/XSBR = 4.1/95.9	3.95	
			ChNWs/XSBR = 6.6/93.4	6.25	
			ChNWs/XSBR = 9.0/91.0	25.25	
10	XSBR latex/chitin nanocrystals (ChNCs)	Loss modulus at 25 °C, MPa (annealed at 100 °C)	XSBR	0.18	41
			ChNWs/XSBR = 4.1/95.9	1.03	
			ChNWs/XSBR = 6.6/93.4	3.08	
		<i>T_g</i> from DSC analysis, °C (non-annealed)	ChNWs/XSBR = 9.0/91.0	1.7	
			XSBR	0.15	
			ChNWs/XSBR = 4.1/95.9	0.7	
		<i>T_g</i> from DSC analysis, °C (annealed at 100 °C)	ChNWs/XSBR = 6.6/93.4	1.13	
			ChNWs/XSBR = 9.0/91.0	3.99	
			XSBR	10	
		Young's modulus, MPa	ChNWs/XSBR = 4.1/95.9	14.2	
			ChNWs/XSBR = 6.6/93.4	12.2	
			ChNWs/XSBR = 9.0/91.0	16	
		Tensile modulus at 100% strain, MPa	XSBR	13.8	
			ChNWs/XSBR = 4.1/95.9	13.3	
			ChNWs/XSBR = 6.6/93.4	14.6	
		Tensile modulus at 100% strain, MPa	ChNWs/XSBR = 9.0/91.0	16.7	
			XSBR	14.1	
			ChNCs/XSBR = 1/99	14.3	
		Tensile modulus at 100% strain, MPa	ChNCs/XSBR = 2/98	24.3	
			ChNCs/XSBR = 3/97	31.1	
			ChNCs/XSBR = 4/96	36.2	
		Tensile modulus at 100% strain, MPa	ChNCs/XSBR = 5/95	39.2	
			XSBR	1.85	
			ChNCs/XSBR = 1/99	2.07	
		Tensile modulus at 100% strain, MPa	ChNCs/XSBR = 2/98	3.17	
			ChNCs/XSBR = 3/97	4.12	
			ChNCs/XSBR = 4/96	4.63	
		Tensile modulus at 100% strain, MPa	ChNCs/XSBR = 5/95	5.54	



Table 9 (Contd.)

No.	Polymers	Property affected	Composition	Value	Ref.
		Tensile modulus at 300% strain, MPa	XSBR		
			ChNCs/XSBR = 1/99	3.7	
			ChNCs/XSBR = 2/98	4.07	
			ChNCs/XSBR = 3/97	5.88	
			ChNCs/XSBR = 4/96	7.76	
			ChNCs/XSBR = 5/95	9.37	
		Tensile strength, MPa	XSBR	10.22	
			ChNCs/XSBR = 1/99	4.29	
			ChNCs/XSBR = 2/98	6.26	
			ChNCs/XSBR = 3/97	8.68	
		Elongation at break, %	ChNCs/XSBR = 4/96	9.42	
			ChNCs/XSBR = 5/95	10.51	
			XSBR	10.4	
			ChNCs/XSBR = 1/99	374.5	
			ChNCs/XSBR = 2/98	423.5	
		Storage modulus, MPa (−100 °C)	ChNCs/XSBR = 3/97	419.7	
			ChNCs/XSBR = 4/96	389.1	
			ChNCs/XSBR = 5/95	296.7	
			XSBR	240.8	
			ChNCs/XSBR = 1/99	1768.4	
		Storage modulus, MPa (30 °C)	ChNCs/XSBR = 2/98	1718.9	
			ChNCs/XSBR = 3/97	1854	
			ChNCs/XSBR = 4/96	1823.5	
			ChNCs/XSBR = 5/95	1924.3	
			XSBR	2184.3	
		Storage modulus, MPa (80 °C)	ChNCs/XSBR = 1/99	38.2	
			ChNCs/XSBR = 2/98	31.5	
			ChNCs/XSBR = 3/97	41.8	
			ChNCs/XSBR = 4/96	43.7	
			ChNCs/XSBR = 5/95	51.7	
			XSBR	80.4	
			ChNCs/XSBR = 1/99	1.6	
			ChNCs/XSBR = 2/98	1.1	
			ChNCs/XSBR = 3/97	2.4	
			ChNCs/XSBR = 4/96	3	
			ChNCs/XSBR = 5/95	4.3	
				7.5	

^a The values of the mechanical properties were estimated from the graphs. ^b The composition ratio is reported in wt.%, calculated from the ChNF or ChNW content expressed in phr.

concentrations into the NR latex *via* the solution-casting method to form composite films, ChNCs formed liquid crystalline phases at concentrations above 5 wt%, which lead to enhanced mechanical properties (Table 9, entry 5). The tensile strength of ChNC/NR film containing 10 wt% ChNC is 5.75 MPa, which is 6.25 multiples of pure NR. Additionally, the tensile modulus at various strains and tear strength of the films increased with increasing ChNC loadings. For instance, the tear strength of the composites with 10 wt% ChNC content is 12.33 kN m⁻¹, 5.43 times that of neat NR. Similarly, the modulus at 500% strain for the composite with 5 wt% ChNC content is 2.17 MPa, 3.88 times that of the pure NR.

The study further explored the impact of ChNCs on the dynamic properties of NR as a function of temperature.¹³ The results revealed that all composites displayed a glassy-rubbery state transition within the temperature range of -100 °C to 50 °C. The storage modulus (E') of the composites increased with ChNC loading, except for the composite with 1 wt% ChNCs in the glassy state at -100 °C, when compared to neat NR. For example, at 10 wt% loading, the storage modulus at -40 °C and 30 °C were 218.01 and 12.48 MPa, respectively -181.7 and 96 times greater than that of neat NR. These findings demonstrate that ChNC networks effectively transfer load from the rubber matrix to the rigid nanoparticles. The slight decrease in E' for the rubber composite with 1 wt% ChNCs in the glassy state likely stems from changes in the rubber's conformation and free volume due to the addition of a small amount of ChNCs.^{13,200} Additionally, the incorporation of ChNCs improved the thermal stability of ChNCs/NR composites, which is attributed to the restricted mobility of the rubber chains resulting from interfacial interactions.

Another study reinforced a prevulcanized NR matrix with rigid ChNFs.²⁰¹ In this study, ChNFs were self-assembled from a dilute α -chitin/potassium hydroxide (KOH)/urea aqueous solution. The highly stable ChNFs demonstrated better compatibility with NR latex and dispersed at nanoscale within the NR matrix. The mechanical properties of the ChNFs/NR nanocomposites showed a remarkable improvement with small loadings (0.3–2 wt%, see Table 9, entry 6). At just 0.3 wt% ChNFs, both the tensile strength and toughness of the composites were more than doubled. These improvements were attributed to the large aspect ratio of ChNFs and their homogeneous dispersion in the NRL matrix.²⁰¹

Another study by Yin *et al.*²⁰² fabricated prevulcanized NR (pervulc.NR)/ChNFs nanocomposites by incorporating zwitterionic ChNFs (Z-ChNFs) and carboxylated ChNFs (C-ChNFs) *via* dip molding technique. The oxidation of ChNFs with 2,2,6,6-tetramethylpiperidinyloxy (TEMPO) produced C-ChNFs with negatively charged COO groups, which was stable in basic medium, but unstable in acidic medium due to the possibility of hydrogen bonding tempted by COOH groups. In contrast, zwitterionic ChNFs, formed through partial deacetylation and subsequent TEMPO oxidation, contain both carboxyl and amino groups, making them stable across various pH conditions. The study found that C-ChNFs exhibited better dispersion in the prevulcanized NR matrix than Z-ChNFs. As

shown in Table 9, entry 7, incorporating both C-ChNFs and Z-ChNFs into NR improved stresses at 100% and 300% strain. When C-ChNFs reached approximately 3.4 wt%, the stress at 100% strain and 300% strain in C-ChNFs/pervulc.NR composites was about four times greater than that of neat NR. In contrast, at the same loading, Z-ChNFs increased the stress at both 100% strain and 300% strain by 2-fold compared to neat NR. However, for ChNF content below 3.4 wt%, the stress at 100% strain and 300% strain in Z-ChNFs/pervulc.NR increased more gradually with higher nanofiber content compared to C-ChNFs/pervulc.NR. The Young's modulus followed a similar trend, with C-ChNFs enhancing the modulus by nearly 1.37 times more than Z-ChNFs reinforcement.

4.2.2. Synthetic rubber. Synthetic rubbers are man-made elastomers created through the polymerization of monomers like butadiene and styrene. The most well-known types of synthetic rubbers include styrene-butadiene rubber (SBR), butyl rubber (IIR), nitrile butadiene rubber (NBR), and neoprene (CR), each offering distinct properties suited for specific applications. These rubbers generally exhibit excellent flexibility, elasticity, resistance to abrasion, wear, chemical stability, making them ideal for use in products such as automotive tires, industrial belts, hoses, gaskets, seals and medical devices. Synthetic rubbers are often favored in industries where natural rubber may not perform well, such as in environments involving oils, fuels, or extreme temperatures. However, synthetic rubbers face challenges such as poor aging resistance, lower tensile strength and elasticity compared to NR, and their performance can degrade over time due to oxidation and UV exposure. Additionally, the stiffness of some synthetic rubbers at low temperatures and their poor tear resistance in specific conditions can hinder their performance. These challenges necessitate the incorporation of reinforcements like carbon black,^{203,204} nano silica,²⁰⁵ nanocrystalline cellulose,²⁰⁶ or nanochitin^{18,41,146} and use stabilizers or antioxidants to enhance their durability and strength. Modifications through cross-linking agents or blending with other materials also help improve the heat resistance, elasticity and environmental stability of synthetic rubbers, expanding their use in a broader range of applications.

A previous study¹⁸ successfully fabricated ChNWs/acrylonitrile-butadiene rubber (NBR) composites utilized a two-roll mill, starting with the formulation of a mixture of polymers and ChNWs, which was then compounded with vulcanizing agents. Subsequently, the reinforcing effects of ChNWs on processing and performance of NBR based nanocomposites were evaluated. The tensile strength of NBR increased from 2.75 MPa to 5.95 MPa at 3.84 wt% ChNWs, but decreased at higher ChNW concentrations (Table 9, entry 8). This improvement was attributed to several factors, including hydrogen bonding interactions between the -OH groups of ChNWs and the nitrile group of NBR rubber at the interface, the 3-D intra- and inter-hydrogen bonding networks within the ChNWs, their uniform dispersion, and ChNW high aspect ratio. However, at higher ChNW loadings, ChNWs was prone to agglomerating into bundles, with filler-filler interactions dominating over matrix-



filler interactions. This caused debonding at the interface and created voids that may act as stress concentration sites, reducing the tensile strength.¹⁸ Meanwhile, the modulus at 300% strain and tear strength increased with the increasing ChNW loadings, attributed to improved interfacial compatibility and the reinforcing efficiency of ChNWs, as well as the obstruction they created in the tear path. Although the tensile strength peaked at 3.84 wt% ChNW loading, the tear strength was highest at 10.71 wt%, showing a 58% increase. This trend aligned with their previous study, where cellulosic nanofibers were used as a filler in NR.²⁰⁷ A similar trend in tear strength was also observed in the hardness property of the ChNW/NBR composites, which was ascribed to the improved rigidity.

Incorporating ChNWs also increased cross-link density, peaking at 3.84 wt% ChNW loading due to hydrogen bond interaction between ChNWs and NBR. However, at 10.71 wt% ChNW loading, cross-link density decreased as increased intramolecular hydrogen bonding within ChNWs reduced matrix-filler interactions. Dynamical mechanical analysis (DMA) studies revealed that the glass transition temperature of the composite at 3.84 wt% ChNW loading was approximately 6 °C higher than that of neat NBR. Additionally, the addition of ChNWs lowered the loss tangent peak height and shifted the maximum $\tan \delta$ peak to a higher temperature region (Table 9, entry 8), indicating effective interaction of ChNW with the NBR matrix.

ChNWs derived from crab shell waste have also effectively reinforced the thermo-mechanical properties of carboxylated styrene-butadiene rubber (XSBR) composites.¹⁴⁶ DMA results revealed that the storage modulus (G') of the composites increased across the entire studied temperature range with higher ChNW content. At 25 °C, the addition of up to 9 wt% ChNWs increased the storage modulus of the composite nearly 13 times compared to neat XSBR, while the loss modulus doubled (Table 9, entry 9). Differential scanning calorimetry results indicated a slight increase in glass transition temperature (T_g) with increasing ChNW content.

The study also assessed the effect of annealing the XSBR-based composites at 100 °C to improve their durability for specific applications (back coating for textiles and carpets).¹⁴⁶ Compared to non-annealed composites, the annealing treatment had a limited effect on the loss modulus profile, with only a small increase of the G' values at 25 °C, likely due to stiffening. A slight increase in T_g was also observed following the annealing process. However, SEM results highlighted an exfoliation of the rubber matrix upon toluene absorption, indicating the weak interface between the XSBR and ChNW aggregates.

On the other hand, a study by Liu *et al.*⁴¹ reported that when added to XSBR *via* casting-evaporation method, with loadings below 4 wt%, improved both the tensile strength and elongation at break of the composites (Table 9, entry 10). For instance, the composite with 3 wt% ChNCs exhibited a tensile strength of 9.16 MPa and elongation at break of 396%, which were 2.23 times and 11.0% higher, respectively, compared to neat XSBR. The strength continued to increase with higher

ChNC loading, reaching a maximum value of 10.4 MPa; however, the elongation at break decreased compared to neat XSBR. A similar trend was also observed in the Young's modulus and tensile moduli at 100% and 300% strain, indicating that the small amount of ChNCs acted as the physical crosslinker of the XSBR, enhancing the mobility of the polymer chains. On the other hand, excessive ChNCs loading resulted in a stiffer network, reducing the flexibility of the rubber chains and decreasing elongation at break.

The reinforcement effect of ChNCs was also evident in the DMA properties of the composites under dynamic stress, facilitated by a 3-D network formed by the interconnection of polysaccharide nanocrystals, stabilized by hydrogen bonding.⁴¹ As the ChNC concentration increased, both the rubbery and glassy regions showed a significant increase in E' , except for the composite with 1 wt% ChNCs. The reinforcement effect became more pronounced with rising temperature. For example, the E' values for the composite with 5 wt% CNCs at -100, 30, and 80 °C were 2184.3, 80.4, and 7.5 MPa, respectively -23.5%, 110.5% and 368.8% higher than those of neat XSBR (Table 9, entry 10). This trend aligned with the results from the static tensile tests.

4.3. Reinforcement of poly(lactic) acid with nanochitin

Poly(lactic) acid (PLA) is a widely recognized thermoplastic bio-based polymer, almost exclusively sourced from renewable resources like potato, corn, cassava, rice, cane sugar, or other carbohydrate-rich crops through a fermentation process into lactic acid followed by polymerization.^{208,209} It has captured broad interest because it offers high mechanical strength and stiffness, UV stability, clarity, and easy processability – it can be molded, extruded, or 3D-printed.²¹⁰ The properties of PLA are affected by various factors, such as the component isomers (L-, D-, or DL-), the molecular weights, and processing routes. Thus, the tensile strength of poly(L-lactide) (PLLA) is 15.5–150 MPa, whereas the tensile strength of poly(DL-lactide) (PDLLA) is 0.04–0.05 MPa.²¹¹

PLA could replace many petroleum-based plastics to fabricate biomedical materials such as sutures, drug delivery systems, and tissue engineering devices, due to its biocompatibility. In packaging and consumer goods, PLA is a popular material for biodegradable food containers, disposable cutlery, and sustainable textiles. The limitations of PLA are associated with its intrinsic brittleness, low impact resistance, slow crystallization, and insufficient thermal stability.²¹² Several researchers have reported on the use of polysaccharide nanofillers such as cellulose, starch, clay, wood fibers *etc.*, to reinforce PLA by forming a hydrogen-bonded or chemically crosslinked network,²¹³ *via* blending them with a non-polar thermoplastic matrix.²¹⁴ A few of the studies have probed into the dispersion of chitin nanoparticles in PLA based matrix using several techniques to assess the degree of reinforcement (Table 10, entries 1–10). Zhang *et al.*⁹³ reported a significant improvement in tensile strength and Young's modulus of PLA composites reinforced with acetylated chitin nanocrystals (Ac-ChNCs). The enhancements surpassed those of neat PLA (25 MPa and 1148





Table 10 Reinforcement of polylactic acid (PLA) with nanochitin

No.	Polymers	Affected properties	Composition	Value	Ref.
1	Polylactic acid (PLA)/acetylated chitin nanocrystals (Ac-ChNCs)	Young's modulus, MPa	PLA	1148	93
			Ac-ChNCs/PLA = 1/99	1200	
			Ac-ChNCs/PLA = 2/98	1400	
			Ac-ChNCs/PLA = 4/96	1580	
			Ac-ChNCs/PLA = 6/94	1500	
			Ac-ChNCs/PLA = 8/92	1250	
			Ac-ChNCs/PLA = 10/90	1100	
			PLA	25	
			Ac-ChNCs/PLA = 1/99	33	
			Ac-ChNCs/PLA = 2/98	35	
			Ac-ChNCs/PLA = 4/96	38	
			Ac-ChNCs/PLA = 6/94	28	
			Ac-ChNCs/PLA = 8/92	23	
			Ac-ChNCs/PLA = 10/90	21	
			PLA	33	
			Ac-ChNCs/PLA = 1/99	10	
			Ac-ChNCs/PLA = 2/98	10	
2	PLA-grafted maleic anhydride (PLA-g-MA)/α-ChNWs	Elongation at break, %	Ac-ChNCs/PLA = 4/96	7	91
			Ac-ChNCs/PLA = 6/94	6	
			Ac-ChNCs/PLA = 8/92	4	
			Ac-ChNCs/PLA = 10/90	4	
			PLA-g-MA	0.6	
			ChNWs/PLA-g-MA = 0.5/99.5	0.175	
			ChNWs/PLA-g-MA = 1.0/99.0	0.175	
			ChNWs/PLA-g-MA = 2.0/98.0	0.16	
			ChNWs/PLA-g-MA = 5.0/95.0	0.15	
			PLA-g-MA	45	
			ChNWs/PLA-g-MA = 0.5/99.5	53	
			ChNWs/PLA-g-MA = 1.0/99.0	50	
			ChNWs/PLA-g-MA = 2.0/98.0	48.5	
			ChNWs/PLA-g-MA = 5.0/95.0	35	
			PLA-g-MA	550	
			ChNWs/PLA-g-MA = 0.5/99.5	650	
			ChNWs/PLA-g-MA = 1.0/99.0	675	
3	PLA-(grafted)-MA/ChNWs/poly(3-hydroxybutyrate-co-3-hydroxyvalerate) (PHBV)/ChNWs	Elongation at break, %	ChNWs/PLA-g-MA = 2.0/98.0	650	91
			ChNWs/PLA-g-MA = 5.0/95.0	600	
			PLA-g-MA/PHBV	0.56	
			ChNWs/PLA-g-MA/PHBV = 0.5/84.6/14.9	0.25	
			ChNWs/PLA-g-MA/PHBV = 1.0/84.5/14.8	0.25	
			ChNWs/PLA-g-MA/PHBV = 2.0/84.4/14.7	0.38	
			ChNWs/PLA-g-MA/PHBV = 5.0/80.7/14.3	0.07	
			PLA-g-MA/PHBV	39	
			ChNWs/PLA-g-MA/PHBV = 0.5/84.6/14.9	44	
			ChNWs/PLA-g-MA/PHBV = 1.0/84.5/14.8	42	
			Ultimate tensile strength, MPa		
			Young's modulus, MPa		
			Ultimate tensile strength, MPa		
			Young's modulus, MPa		
			Ultimate tensile strength, MPa		
			Young's modulus, MPa		
			Ultimate tensile strength, MPa		



Table 10 (Contd.)

No. Polymers	Affected properties	Composition	Value	Ref.
Poly(lactic acid (PLA)	Young's modulus, MPa	ChNWs/PLA-g-MA/PHBV = 2.0/84.4/14.7	37	
		ChNWs/PLA-g-MA/PHBV = 5.0/80.7/14.3	27	
		PLA-g-MA/PHBV	550	
		ChNWs/PLA-g-MA/PHBV = 0.5/84.6/14.9	545	
		ChNWs/PLA-g-MA/PHBV = 1.0/84.5/14.8	575	
		ChNWs/PLA-g-MA/PHBV = 2.0/84.4/14.7	500	
		ChNWs/PLA-g-MA/PHBV = 5.0/80.7/14.3	495	
		PLA	350	92
		ChNWs/PLA = 1/99	460	
		ChNWs/PLA = 2/98	525	
Poly(lactic acid (PLA) grafted with maleic anhydride (PLA-g-MA)/α-ChNWs	Ultimate tensile strength, MPa	ChNWs/PLA = 5/95	480	
		PLA	56	
		ChNWs/PLA = 1/99	52.25	
		ChNWs/PLA = 2/98	51.25	
		ChNWs/PLA = 5/95	48	
		PLA-g-MA	350	92
		ChNWs/(PLA-g-MA) = 2/98	475	
		ChNWs/(PLA-g-MA) = 5/95	480	
		ChNWs/(PLA-g-MA) = 1/99	490	
		PLA-g-MA	56	
Poly(lactic acid (PLA, Mw 170 000)/chitin nanofibrils (ChNFs)/polyethylene glycol (PEG, Mw 400, and 8000)	Young's modulus, GPa	ChNWs/(PLA-g-MA) = 2/98	52.5	
		ChNWs/(PLA-g-MA) = 5/95	51.5	
		ChNWs/(PLA-g-MA) = 1/99	48.5	
		PLA	3.5 ± 0.1	165
		PEG400/PLA = 10/90	2.3 ± 0.3	
		PEG400/ChNFs/PLA = 10/2/88	1.8 ± 0.3	
		PEG8000/ChNFs/PLA = 10/2/88	2.5 ± 0.1	
		PEG400/ChNFs/PLA = 1/2/97	3.2 ± 0.8	
		PEG400/ChNFs/PLA = 5/2/93	2.8 ± 0.8	
		PEG400/ChNFs/PLA = 10/5/85	1.8 ± 0.3	
	Stress at yield, MPa	PEG400/ChNFs/PLA = 10/12/78	1.7 ± 0.3	
		PLA	60.4 ± 0.3	
		PEG400/PLA = 10/90	26 ± 0.3	
		PEG400/ChNFs/PLA = 10/2/88	23 ± 5.0	
		PEG8000/ChNFs/PLA = 10/2/88	45 ± 5.0	
		PEG400/ChNFs/PLA = 1/2/97	52 ± 6.0	
		PEG400/ChNFs/PLA = 5/2/93	47 ± 3.0	
		PEG400/ChNFs/PLA = 10/5/85	34 ± 2.0	
		PEG400/ChNFs/PLA = 10/12/78	23 ± 5.0	
		PLA	57 ± 1	
	Stress at break, MPa	PEG400/PLA = 10/90	33 ± 2	
		PEG400/ChNFs/PLA = 10/2/88	32 ± 2	
		PEG8000/ChNFs/PLA = 10/2/88	34 ± 2	
		PEG400/ChNFs/PLA = 1/2/97	40 ± 7	

Table 10 (Contd.)

No.	Polymers	Affected properties	Composition	Value	Ref.
7	Polylactic acid (PLA)/ α -ChNFs (water pretreatment method) ^a	Elongation at break, %	PEG ₄₀₀ /ChNFs/PLA = 5/2/93	32 ± 2	26
			PEG ₄₀₀ /ChNFs/PLA = 10/5/85	23 ± 2	
			PEG ₄₀₀ /ChNFs/PLA = 10/12/78	22 ± 6	
			PLA	4.1 ± 0.5	
			PEG ₄₀₀ /PLA = 10/90	180 ± 10.0	
		Bending strength, MPa	PEG ₄₀₀ /ChNFs/PLA = 10/2/88	160 ± 10.0	
			PEG ₈₀₀₀ /ChNFs/PLA = 10/2/88	160 ± 10.0	
			PEG ₄₀₀ /ChNFs/PLA = 1/2/97	10 ± 2.0	
			PEG ₄₀₀ /ChNFs/PLA = 5/2/93	11.4 ± 0.9	
			PEG ₄₀₀ /ChNFs/PLA = 10/5/85	160 ± 10.0	
		Bending modulus, MPa	PEG ₄₀₀ /ChNFs/PLA = 10/12/78	181 ± 6.0	
			PLA	14.6	
			ChNFs/PLA = 10/90	22.5	
			ChNFs/PLA = 20/80	27.5	
			ChNFs/PLA = 30/70	37.5	
		Impact toughness, J m ⁻¹	ChNFs/PLA = 40/60	41.2	
			PLA	1697	
			ChNFs/PLA = 10/90	1750	
			ChNFs/PLA = 20/80	2000	
			ChNFs/PLA = 30/70	3250	
		Storage modulus (temperature range -30 to 60 °C) ^b , GPa	ChNFs/PLA = 40/60	4153	
			PLA	8.4	
			ChNFs/PLA = 10/90	10	
			ChNFs/PLA = 20/80	15	
			ChNFs/PLA = 30/70	28	
8	Polylactic acid (PLA)/ α -ChNFs/polyethylene glycol (PEG) PEG pretreatment method	Bending strength, MPa	ChNFs/PLA = 40/60	35	26
			PLA	Significantly lower	
			ChNFs/PLA = 10/90	7.8	
			ChNFs/PLA = 20/80	7.8	
			ChNFs/PLA = 30/70	7.8	
		Bending modulus, MPa	ChNFs/PLA = 40/60	7.8	
			PLA	14.6	
			ChNFs/PLA/PEG = 10/80/10	22.5	
			ChNFs/PLA/PEG = 20/70/10	25	
			ChNFs/PLA/PEG = 30/60/10	35	
		Impact strength, J m ⁻¹	ChNFs/PLA/PEG = 40/50/10	37.5	
			PLA	1697	
			ChNFs/PLA/PEG = 10/80/10	2250	
			ChNFs/PLA/PEG = 20/70/10	2500	
			ChNFs/PLA/PEG = 30/60/10	3250	
		Storage modulus (temperature range -30 to 60 °C) ^b , GPa	ChNFs/PLA/PEG = 40/50/10	3550	
			PLA	8.4	
			ChNFs/PLA/PEG = 10/80/10	10	
			ChNFs/PLA/PEG = 20/70/10	15	
			ChNFs/PLA/PEG = 30/60/10	26	
			ChNFs/PLA/PEG = 40/50/10	30	
			PLA	Significantly lower	





Review

Table 10 (Contd.)

No. Polymers	Affected properties	Composition	Value	Ref.
9 Polylactic acid (PLA)/α-ChNFs/polyethylene oxide (PEO) PEO pretreatment method	Bending strength, MPa	ChNFs/PLA/PEG = 10/80/10	6.5	26
		ChNFs/PLA/PEG = 20/70/10	6.5	
		ChNFs/PLA/PEG = 30/60/10	6.5	
		ChNFs/PLA/PEG = 40/50/10	6.5	
		PLA	14.6	
	Bending modulus, MPa	ChNFs/PLA/PEO = 10/80/10	24	
		ChNFs/PLA/PEO = 20/70/10	26	
		ChNFs/PLA/PEO = 30/60/10	30	
		ChNFs/PLA/PEO = 40/50/10	34	
		PLA	1697	
	Impact strength, J m ⁻¹	ChNFs/PLA/PEO = 10/80/10	1550	
		ChNFs/PLA/PEO = 20/70/10	2250	
		ChNFs/PLA/PEO = 30/60/10	2500	
		ChNFs/PLA/PEO = 40/50/10	2900	
		PLA	8.4	
10 Polylactic acid (PLA)/α-ChNFs (freeze-dried, compounding method)	Storage modulus (temperature range −30 to 60 °C) ^b , GPa	ChNFs/PLA/PEO = 10/80/10	9.5	
		ChNFs/PLA/PEO = 20/70/10	14	
		ChNFs/PLA/PEO = 30/60/10	22.5	
		ChNFs/PLA/PEO = 40/50/10	28	
		PLA	Significantly lower	
	Bending strength, MPa	ChNFs/PLA/PEO = 10/80/10	6.1	26
		ChNFs/PLA/PEO = 20/70/10	6.1	
		ChNFs/PLA/PEO = 30/60/10	6.1	
		ChNFs/PLA/PEO = 40/50/10	6.1	
		PLA	14.6	
	Bending modulus, MPa	ChNFs/PLA = 10/90	24	
		ChNFs/PLA = 20/80	26	
		ChNFs/PLA = 30/70	27.5	
		ChNFs/PLA = 40/60	27.5	
		PLA	1697	
	Impact strength, J m ⁻¹	ChNFs/PLA = 10/90	1550	
		ChNFs/PLA = 20/80	1555	
		ChNFs/PLA = 30/70	1600	
		ChNFs/PLA = 40/60	1655	
		PLA	8.4	
	Storage modulus (temperature range −30 to 60 °C) ^b , GPa	ChNFs/PLA = 10/90	9	
		ChNFs/PLA = 20/80	12	
		ChNFs/PLA = 30/70	12.5	
		ChNFs/PLA = 40/60	15	
		PLA	Markedly lower	
		ChNFs/PLA = 10/90	5	
		ChNFs/PLA = 20/80	5	
		ChNFs/PLA = 30/70	5	
		ChNFs/PLA = 40/60	5	
		ChNFs/PLA = 40/60	5	

^a Four methods were conducted to evaluate the dispersion effect of nanofibers for the composite preparation. Two of these methods utilized either PEG or PEO as a surfactant and dispersing agent to optimize the dispersion of nanofibers within the PLA matrix. ^b The storage modulus of chitin nanofibers/PLA composites remains stable below 60 °C, while it gradually decreases with rising temperature. Additionally, compared to neat PLA, the storage modulus values of the nanocomposites show a notable increase. The loss modulus rises with temperature until it reaches the glass transition (*T_g*) of 55 °C, after which it decreases for all composites. In comparison to pure PLA, the loss modulus values of the nanocomposites are notably lower, indicating that adding fibers reduces the loss modulus.

MPa, respectively) across all loading levels (1 to 10 wt%), with the highest improvement observed at 4 wt% Ac-ChNCs, where tensile strength and Young's modulus peaked at 38 MPa and 1580 MPa, respectively (Table 10, entry 1). However, exceeding this threshold resulted in nanocrystal agglomeration, leading to the formation of a percolation network that disrupted the homogeneity and mechanical integrity of the PLA matrix. Additionally, elongation at break decreased at all concentrations, indicating increased stiffness and reduced flexibility of the composite.

Guan and Naguib⁹¹ investigated PLA-based and PLA/PHBV-based nanocomposites, incorporating maleic anhydride (MA) as a compatibilizing agent *via* grafting (Table 10, entries 2 and 3). It is well known that the hydrophobic nature of PLA results in poor interfacial adhesion when compounded with hydrophilic natural reinforcements. A strategic approach to address this challenge is compatibilizing one of the phases to improve interfacial interactions. Grafted MA, a widely studied compatibilizer, was employed in this study to promote interfacial wetting between PLA and chitin. For PLA-grafted maleic anhydride (PLA-*g*-MA)/ α -ChNWs, nanochitin loadings ranged from 0.5 to 5 wt%, with tensile strength increasing from 45 MPa for neat PLA-*g*-MA to a peak of 53 MPa at 0.5 wt%, before declining at higher loadings. Young's modulus improved from 550 MPa to a maximum of 675 MPa at 1 wt%, then gradually decreased. Elongation at break consistently dropped from 0.600 for neat PLA-*g*-MA to 0.150 at 5 wt%, indicating increased brittleness with higher nanochitin content. At elevated ChNW loadings (~5 wt%), mechanical property deterioration was attributed to solvolytic degradation caused by the dispersing agent (DMAc), which likely disrupted the polymer matrix. Similarly, for PLA-*g*-MA/PHBV-ChNWs, nanochitin loadings from 0.5 to 5 wt% exhibited a comparable trend. Tensile strength, which was 39 MPa for PLA-*g*-MA/PHBV, peaked at 44 MPa at 0.5 wt% but declined at higher loadings. Young's modulus increased from 550 MPa to a maximum of 575 MPa at 1 wt%, before gradually decreasing. Meanwhile, elongation at break consistently declined from 0.56 for PLA/PHBV to 0.07 at 5 wt%, further demonstrating the increased stiffness and brittleness with rising nanochitin content.

Rizvi *et al.*⁹² investigated the mechanical behavior of PLA-grafted maleic anhydride (PLA-*g*-MA)/ α -ChNWs composites, where MA was again used as a compatibilizer to enhance interfacial wetting. Here, however, to assess the influence of MA addition on mechanical properties, the study compared composites with and without MA (Table 10, entries 4 and 5). For neat PLA, Young's modulus was 350 MPa, which peaked at 525 MPa with 2 wt% ChNWs before declining at higher loadings. Similarly, for PLA-*g*-MA, Young's modulus increased from 350 MPa to 490 MPa at 1 wt% ChNWs, followed by a decrease at higher concentrations. However, tensile strength, which was 56 MPa for neat PLA, consistently decreased with the addition of ChNWs, regardless of loading percentage. A similar trend was observed in PLA-*g*-MA/ChNWs composites, indicating that while stiffness improved with nanochitin reinforcement, overall strength diminished which could be due to the

reduction in the molecular weight on account of the hydrolysis of PLA throughout the fabrication process, as explained by the authors.

Concerning the need for better dispersing agents for ChNWs to inhibit particle agglomeration, Coltelli *et al.*¹⁶⁵ employed PEGs with different molecular weights in combination with PLA (Table 10, entry 6). Similar to how MA was used in the study by Rizvi *et al.*⁹² as a compatibilizer to improve interfacial wetting between PLA and chitin, PEGs were utilized here as dispersing agents to enhance the uniform distribution of ChNWs within the PLA matrix. The incorporation of PEGs aimed to improve the dispersion and interaction of ChNWs within PLA, addressing the common challenge of nanoparticle agglomeration, which can negatively impact the mechanical properties of the composite.

The initial study on PEG/PLA composites without nanowhiskers revealed that adding PEG to PLA at 10/90 w/w significantly reduced mechanical properties, decreasing Young's modulus by 1.5-fold (from 3.5 to 2.3 GPa), stress at yield by 2.3-fold (from 60 to 26 MPa), and stress at break by 1.7-fold (from 57 to 33 MPa). However, elongation at break improved nearly 45-fold due to PEG's plasticizing effect. When nanofibers were introduced, the PEG400/ChNFs/PLA formulation with the same PEG content (10 wt%) exhibited similar or worse mechanical properties compared to PEG400/PLA alone. Specifically, Young's modulus decreased further to 1.7–1.8 GPa, regardless of nanofiber content (2, 5, or 12 wt%). Similarly, stress at break remained at 33 MPa for 2% ChNFs but dropped to 22–23 MPa at higher ChNFs loadings (5 and 12 wt%). Stress at yield showed mixed behavior, staying at 23 MPa for 2% and 12% ChNFs but increasing to 34 MPa at 5% ChNFs. These findings indicate that ChNFs failed to provide reinforcement, likely due to PEG's strong affinity for chitin, which inhibited proper interfacial bonding between ChNFs and PLA, preventing effective stress transfer. Instead, PEG's dominant plasticizing effect continued to weaken the composite. Regarding elongation at break, the PEG400/ChNFs/PLA formulations exhibited an elongation identical to that of PEG/PLA, indicating that the presence of nanowhiskers regardless of amount did not further alter the ductility introduced by PEG.

The inability of PEG to facilitate reinforcement in the previous study¹⁶⁵ contrasts with findings from another study (Table 10, entries 7–9),²⁶ where chitin nanofibers (ChNFs) extracted from crab shells were successfully used to reinforce PLA through extrusion molding. In this case, the dispersion issue of nanofibers within the PLA matrix was addressed using three different pretreatment methods: water pretreatment, polyethylene glycol (PEG) pretreatment, and polyethylene oxide (PEO) pretreatment.

In the first water-pretreatment method (Table 10, entry 7),²⁶ PLA powder was added to a 1 wt% ChNF water slurry, stirred, filtered, and freeze-dried to remove water while preserving nanofiber dispersion. The dried ChNF/PLA mixture was mechanically broken down before compounding and extrusion. Increasing ChNFs content from 10 to 40 wt% led to



improvements, reaching 41.2 MPa, a 180% increase compared to neat PLA. Similarly, the bending modulus increased to 4153 MPa, a 144% improvement, and impact toughness rose from 8.4 J m⁻¹ in neat PLA to 35 J m⁻¹. Storage modulus was significantly improved, reaching 7.8 GPa, but remained independent of ChNF content, suggesting effective load distribution across the polymer matrix.

In the PEG pretreatment method (Table 10, entry 8),²⁶ PEG powder was dissolved in distilled water at 2 wt% and heated to 80 °C before adding a 1 wt% ChNF aqueous slurry. The thickened mixture was freeze-dried, broken down, and compounded with PLA. The results were comparable to the water pretreatment method, with bending strength increasing to 37.5 MPa, bending modulus to 3550 MPa, and impact toughness to 30 J m⁻¹ at 40 wt% ChNFs. Storage modulus improved to 6.5 GPa, again independent of ChNF content. While PEG facilitated dispersion, the absolute mechanical improvements were slightly lower than those from water pretreatment, suggesting that residual PEG at the interface might have reduced stiffness and interfacial bonding between ChNFs and PLA.

The PEO pretreatment method (Table 10, entry 9) conducted in the same manner as PEG-pretreatment²⁶ yielded similar results to PEG, though mechanical properties were slightly lower: bending strength reached 34 MPa, bending modulus 2900 MPa, and impact toughness 28 J m⁻¹, while storage modulus stabilized at 6.1 GPa. Unlike the previous study, where direct PEG addition hindered reinforcement by coating ChNFs and preventing stress transfer, these pretreatment strategies improved dispersion and integration within PLA. The use of pre-dissolved PEG or PEO as a dispersing medium before compounding likely reduced aggregation and enhanced interfacial adhesion.

The freeze-dried chitin nanofibers were also directly extruded with PLA granules as a control (Table 10, entry 10). In the control sample, where freeze-dried ChNFs were directly extruded with PLA, bending strength improved from 14.6 MPa to 27.5 MPa with 40 wt% ChNFs. However, bending modulus slightly decreased to 1550–1655 MPa compared to the original 1697 MPa. Impact strength increased from 8.4 J m⁻¹ to 15 J m⁻¹, while storage modulus reached 5 GPa.

These results indicate that although the direct extrusion method provided some improvement in strength and impact resistance, it did not achieve the same level of reinforcement as the water, PEG, or PEO pretreatment methods. The lower bending modulus suggests that without proper dispersion, the chitin nanofibers might not have been fully integrated into the PLA matrix, leading to suboptimal load transfer. The comparative study underscores the importance of pretreatment strategies in enhancing the dispersion and interfacial adhesion of ChNFs, ultimately leading to better mechanical performance in PLA composites.

4.4. Reinforcement of poly(vinyl) alcohol with nanochitin

Polyvinyl alcohol (PVA) is a linear, synthetic, nontoxic, biodegradable polymer, with a semicrystalline structure.^{215,216} Its

physical and chemical properties vary depending on the molecular weight.²¹⁷ Owing to its excellent optical properties, high storage capacity, and superior dielectric strength, PVA is widely utilized in electronics and bioengineering.²¹⁸ However, its poor mechanical and thermal stability, along with limited compatibility with other polymers often necessitate doping with nanofillers to enhance its physicochemical properties for demanding applications. This includes customizing shape, size, and interactions with other polymers.^{219,220} In recent decades, nano-dimensional fillers – such as quantum dots, metal oxides, metal sulfides, silicates, nanotubes – have been broadly explored as candidates for the reinforcement of PVA.²²¹ Among these, cellulose nanofillers have been extensively examined as sustainable, high-performing biofillers compatible with PVA.²²² More recently, chitin nanofillers have gained increasing research interest, particularly for fabricating PVA-based nanocomposite materials such as hydrogels, beads, fibers, films, membranes, scaffolds and many more.

Numerous studies have reported the reinforcement of PVA with chitin nanomaterials, particularly highlighting improvements in tensile properties as summarized in Table 11, entries 1–18. However, direct comparisons between these studies are challenging due to the use of PVA with different MWs (DP 550–2700) and alcoholysis degree, which significantly influence the material's mechanical properties. Despite this variability, the results consistently show that nanochitin incorporation enhances mechanical performance, attributed to the strong interfacial interactions between chitin nanofillers and the PVA matrix.

It has also been reported that nanochitin can function both as a primary component in PVA-based composites (Table 11, entries 1–7), and as a reinforcement filler (Table 11, entries 8–17), depending on the desired material properties. Generally, when added at lower concentrations, nanochitin primarily enhances tensile strength and mechanical properties while still allowing PVA to retain flexibility and processability, whereas at higher concentrations, nanochitin contributes significantly to the composite's rigidity, strength, and structural integrity, making it the dominant phase rather than just a reinforcing agent.^{80,149} This dual functionality allows nanochitin–PVA composites to be tailored for various applications, ranging from flexible, high-strength materials to rigid, high-performance biopolymers, depending on the composition.

Previous studies indicated that when chitin function as the primary component in PVA-based composites, higher concentrations of nanochitin improve tensile strength, whereas the addition of PVA reduced material rigidity.¹⁵⁰ This implies PVA, rather than acting as the matrix material, served as an adhesive to combine the ChNWs.⁸⁰ Optimal tensile strength was observed at nanochitin concentrations between 60–80% in all cases, with lower or higher concentrations yielding less favorable results (Table 11, entries 1–7). When incorporating PVA at higher concentrations, tensile strength of the composites decreased to levels comparable to or even lower than pure PVA (Table 11, entry 2). It is also important to note that the reinforcement of PVA composites with ChNFs (Table 11, entry



Table 11 Reinforcement of polyvinyl alcohol (PVA) with nanochitin

Polyvinyl alcohol (PVA)								
No.	Polymers	Property affected	Composition	Value	Ref.			
1	Polyvinyl alcohol (PVA, 99% hydrolyzed, DP = 1700)/ChNFs	Ultimate tensile strength, MPa	ChNFs	163	16			
			PVA	65				
		Young's modulus, MPa	ChNFs/PVA = 60/40	127				
			ChNFs	7160				
		Elongation at break, %	PVA	2500				
			ChNFs/PVA = 60/40	5700				
			ChNFs	4.0				
			PVA	22.0				
		2	Polyvinyl alcohol (PVA, DP = 2500) and β -ChNWs	Tensile strength, MPa (dry state)		ChNFs/PVA = 60/40	4.4	149
						β -ChNWs	5.00 $\pm$ 0.12	
PVA	2.17 $\pm$ 0.04							
β -ChNWs/PVA = 90/10	4.46 $\pm$ 0.08							
β -ChNWs/PVA = 80/20	3.04 $\pm$ 0.09							
β -ChNWs/PVA = 70/30	5.17 $\pm$ 0.16							
β -ChNWs/PVA = 60/40	4.09 $\pm$ 0.09							
β -ChNWs/PVA = 50/50	3.18 $\pm$ 0.05							
β -ChNWs/PVA = 40/60	2.53 $\pm$ 0.02							
β -ChNWs/PVA = 30/70	1.75 $\pm$ 0.02							
Elongation at break, % (dry state)	β -ChNWs			5.8 $\pm$ 0.15				
	PVA			487 $\pm$ 11.50				
	β -ChNWs/PVA = 90/10			13.1 $\pm$ 0.31				
	β -ChNWs/PVA = 80/20			13.6 $\pm$ 0.42				
	β -ChNWs/PVA = 70/30			26.1 $\pm$ 0.94				
	β -ChNWs/PVA = 60/40			41.1 $\pm$ 0.62				
	β -ChNWs/PVA = 50/50			87.5 $\pm$ 1.97				
	β -ChNWs/PVA = 40/60			77.4 $\pm$ 2.05				
	β -ChNWs/PVA = 30/70			129.4 $\pm$ 5.97				
	Tensile strength, MPa (wet state)			β -ChNWs	0.4 $\pm$ 0.01			
PVA				3.10 $\pm$ 0.01				
β -ChNWs/PVA = 90/10				0.9 $\pm$ 0.02				
β -ChNWs/PVA = 80/20				0.35 $\pm$ 0.01				
β -ChNWs/PVA = 70/30				0.38 $\pm$ 0.01				
β -ChNWs/PVA = 60/40				0.37 $\pm$ 0.01				
β -ChNWs/PVA = 50/50				0.25 $\pm$ 0.01				
β -ChNWs/PVA = 40/60				0.12 $\pm$ 0.00				
β -ChNWs/PVA = 30/70				0.24 $\pm$ 0.01				
Elongation at break, % (wet state)				β -ChNWs	20 $\pm$ 0.65			
	PVA			423 $\pm$ 15.64				
	β -ChNWs/PVA = 90/10	15.6 $\pm$ 0.42						
	β -ChNWs/PVA = 80/20	21.3 $\pm$ 0.12						
	β -ChNWs/PVA = 70/30	29.2 $\pm$ 0.12						
	β -ChNWs/PVA = 60/40	45.4 $\pm$ 1.24						
	β -ChNWs/PVA = 50/50	47.2 $\pm$ 1.35						
	β -ChNWs/PVA = 40/60	44.3 $\pm$ 1.02						
	β -ChNWs/PVA = 30/70	77.1 $\pm$ 2.34						
	3	Polyvinyl alcohol (PVA, DP = 4300)/ChNWs	Stress, MPa	Chitin	4.0	123		
ChNWs/PVA = 76.92/23.08				9.0				
ChNWs/PVA = 83.33/16.66				7.0				
ChNWs/PVA = 90.91/9.09				6.5				
ChNWs/PVA = 95.24/4.76				5.5				
Strain, %			ChNWs/PVA = 99.01/0.99	5.0				
			Chitin	0.20				
			ChNWs/PVA = 76.92/23.08	0.34				
			ChNWs/PVA = 83.33/16.66	0.30				
			ChNWs/PVA = 90.91/9.09	0.25				
4	Polyvinyl alcohol (PVA)/ β -ChNWs	Tensile strength, MPa	ChNWs/PVA = 95.24/4.76	0.20	150			
			ChNWs/PVA = 99.01/0.99	0.15				
			Pure β -ChNWs	5.1				
			PVA	0.7				
			β -ChNWs/PVA = 20/80	2.0				
		Elongation at break, %	β -ChNWs/PVA = 40/60	2.2				
			β -ChNWs/PVA = 50/50	2.5				
			β -ChNWs/PVA = 60/40	2.7				
			β -ChNWs/PVA = 80/20	5.1				
			Pure β -ChNWs	2.9				
			PVA	165.2				
			β -ChNWs/PVA = 20/80	15.0				
			β -ChNWs/PVA = 40/60	5.0				



Table 11 (Contd.)

Polyvinyl alcohol (PVA)					
No.	Polymers	Property affected	Composition	Value	Ref.
5	Polyvinylalcohol (PVA)/partially deacetylated α -ChNWs	Compressive fracture stress, MPa	β -ChNWs/PVA = 50/50	4.0	133
			β -ChNWs/PVA = 60/40	3.0	
			β -ChNWs/PVA = 80/20	2.9	
			PVA	1.55	
			ChNWs/PVA = 20/80	3.70	
			ChNWs/PVA = 30/70	6.22	
			ChNWs/PVA = 40/60	26.59	
6	Poly(vinyl alcohol) (PVA, DP = 1799)/ionic shielded chitin nanowhiskers (IsChNWs), followed by alkali treatment (at)	Elongation at break, %	ChNWs/PVA = 50/50	<20.22	40
			ChNWs/PVA = 60/40	<20.22	
			PVA	9.6 $\pm$ 2.2	
			IsChNWs/PVA = 80/20	1.0 $\pm$ 0.2	
			IsChNWs/PVA = 70/30	3.7 $\pm$ 0.5	
			IsChNWs/PVA = 60/40	13.2 $\pm$ 0.7	
			IsChNWs/PVA = 50/50	78.0 $\pm$ 2.5	
		Tensile strength, MPa	ChNWs/PVA = 70/30	4.7 $\pm$ 0.9	
			At-ChNWs/PVA = 70/30	4.1 $\pm$ 1.3	
			At-IsChNWs/PVA = 70/30	4.1 $\pm$ 0.5	
			PVA	52.1 $\pm$ 1.4	
			IsChNWs/PVA = 80/20	30.3 $\pm$ 1.6	
			IsChNWs/PVA = 70/30	39.4 $\pm$ 1.2	
			IsChNWs/PVA = 60/40	34.3 $\pm$ 1.1	
		Young's modulus, MPa	IsChNWs/PVA = 50/50	32.9 $\pm$ 1.2	
			ChNWs/PVA = 70/30	33.4 $\pm$ 1.7	
			At-ChNWs/PVA = 70/30	50.4 $\pm$ 0.6	
			At-IsChNWs/PVA = 70/30	67.0 $\pm$ 1.2	
			PVA	2464.9 $\pm$ 391.7	
			IsChNWs/PVA = 80/20	4334.0 $\pm$ 153.5	
			IsChNWs/PVA = 70/30	3619.6 $\pm$ 351.7	
			IsChNWs/PVA = 60/40	1092.3 $\pm$ 61.3	
			IsChNWs/PVA = 50/50	870.9 $\pm$ 68.4	
			ChNWs/PVA = 70/30	1895 $\pm$ 187.0	
			At-ChNWs/PVA = 70/30	3588.8 $\pm$ 169.5	
			At-IsChNWs/PVA = 70/30	5307.1 $\pm$ 106.2	
		Elongation at break, %	At-IsChNWs/PVA	9.3 $\pm$ 0.7	80
			1.0 ^{at} -at-IsChNWs/PVA = 60/40	7.2 $\pm$ 2.2	
			1.5-at-IsChNWs/PVA = 60/40	20.3 $\pm$ 2.3	
			2.0-at-IsChNWs/PVA = 60/40	31.6 $\pm$ 4.1	
			2.5-at-IsChNWs/PVA = 60/40	28.0 $\pm$ 5.6	
			3.0-at-IsChNWs/PVA = 60/40	40.7 $\pm$ 5.6	
		Young's modulus, MPa	At-IsChNWs/PVA	1133.4 $\pm$ 31.7	
			1.0-at-IsChNWs/PVA = 60/40	2830.1 $\pm$ 102.5	
			1.5-at-IsChNWs/PVA = 60/40	983.7 $\pm$ 220.1	
			2.0-at-IsChNWs/PVA = 60/40	1003.5 $\pm$ 108.9	
			2.5-at-IsChNWs/PVA = 60/40	1246.2 $\pm$ 154.9	
			3.0-at-IsChNWs/PVA = 60/40	1155.2 $\pm$ 89.7	
		Tensile strength, MPa	At-IsChNWs/PVA	38.6 $\pm$ 1.0	
			1.0-at-IsChNWs/PVA = 60/40	46.3 $\pm$ 1.8	
			1.5-at-IsChNWs/PVA = 60/40	65.9 $\pm$ 2.7	
			2.0-at-IsChNWs/PVA = 60/40	76.2 $\pm$ 2.6	
			2.5-at-IsChNWs/PVA = 60/40	94.4 $\pm$ 3.0	
			3.0-at-IsChNWs/PVA = 60/40	115.2 $\pm$ 9.3	
8	Polyvinyl alcohol (PVA)/ α -ChNWs	Tensile strength, MPa	PVA	55.5	95
			ChNWs/PVA = 0.74/99.26	65.0	
			ChNWs/PVA = 1.48/98.52	70.0	
			ChNWs/PVA = 2.96/97.34	83.3	
			ChNWs/PVA = 7.40/92.60	82.0	



Table 11 (Contd.)

Polyvinyl alcohol (PVA)					
No.	Polymers	Property affected	Composition	Value	Ref.
9	Polyvinyl alcohol (PVA, DP = 1773)/ α -ChNWs	Elongation at break, %	ChNWs/PVA = 14.80/85.20	81.0	96
			ChNWs/PVA = 22.20/77.80	81.0	
			ChNWs/PVA = 29.60/70.40	80.0	
			PVA	15.0	
			ChNWs/PVA = 0.74/99.26	12.0	
			ChNWs/PVA = 1.48/98.52	9.8	
			ChNWs/PVA = 2.96/97.34	7.8	
			ChNWs/PVA = 7.40/92.60	7.8	
			ChNWs/PVA = 14.8/85.20	6.0	
			ChNWs/PVA = 22.2/77.80	6.5	
			ChNWs/PVA = 29.6/70.40	5.0	
			PVA	3.94	
			ChNWs/PVA = 2.5/97.5	5.92	
10	Polyvinyl alcohol (PVA, DP = ~1705)/ α -ChNWs (electrospun mats)	Tensile strength, MPa	ChNWs/PVA = 5.0/95.0	4.50	49
			ChNWs/PVA = 7.5/92.5	4.00	
			PVA	4.3	
			ChNWs/PVA = 2.55/97.45	4.9	
			ChNWs/PVA = 5.11/94.89	5.7	
			ChNWs/PVA = 7.66/92.34	5.0	
			ChNWs/PVA = 10.11/89.89	5.1	
			ChNWs/PVA = 12.76/87.24	4.2	
			ChNWs/PVA = 15.17/84.83	4.0	
			ChNWs/PVA = 17.74/82.26	3.8	
			ChNWs/PVA = 25.38/74.62	3.4	
			PVA	35	
			11	Polyvinyl alcohol (PVA, DP = ~1705)/ α -ChNWs (solution-casted films)	
ChNWs/PVA = 5.11/94.89	140				
ChNWs/PVA = 7.66/92.34	230				
ChNWs/PVA = 10.11/89.89	255				
ChNWs/PVA = 12.76/87.24	270				
ChNWs/PVA = 15.17/84.83	280				
ChNWs/PVA = 17.74/82.26	275				
ChNWs/PVA = 25.38/74.62	220				
PVA	60				
ChNWs/PVA = 2.55/97.45	32				
ChNWs/PVA = 5.11/94.89	53				
ChNWs/PVA = 7.66/92.34	20				
11	Polyvinyl alcohol (PVA, DP = ~1705)/ α -ChNWs (solution-casted films)	Young's modulus, MPa			ChNWs/PVA = 10.11/89.89
			ChNWs/PVA = 12.76/87.24	24	
			ChNWs/PVA = 15.17/84.83	5	
			ChNWs/PVA = 17.74/82.26	4	
			ChNWs/PVA = 25.38/74.62	6	
			PVA	20	
			ChNWs/PVA = 2.55/97.45	32	
			ChNWs/PVA = 5.11/94.89	36	
			ChNWs/PVA = 7.66/92.34	30	
			ChNWs/PVA = 10.11/89.89	35	
			ChNWs/PVA = 12.76/87.24	37	
			ChNWs/PVA = 15.17/84.83	34	
			ChNWs/PVA = 17.74/82.26	45	
ChNWs/PVA = 25.38/74.62	34				
11	Polyvinyl alcohol (PVA, DP = ~1705)/ α -ChNWs (solution-casted films)	Elongation at break, %	PVA	50	49
			ChNWs/PVA = 2.55/97.45	150	
			ChNWs/PVA = 5.11/94.89	300	
			ChNWs/PVA = 7.66/92.34	350	
			ChNWs/PVA = 10.11/89.89	650	
			ChNWs/PVA = 12.76/87.24	725	
			ChNWs/PVA = 15.17/84.83	850	
			ChNWs/PVA = 17.74/82.26	1300	
			ChNWs/PVA = 25.38/74.62	1500	
			PVA	300	
			ChNWs/PVA = 2.55/97.45	265	
			ChNWs/PVA = 5.11/94.89	290	
			ChNWs/PVA = 7.66/92.34	275	
ChNWs/PVA = 10.11/89.89	235				
ChNWs/PVA = 12.76/87.24	230				
ChNWs/PVA = 15.17/84.83	225				



Table 11 (Contd.)

Polyvinyl alcohol (PVA)						
No.	Polymers	Property affected	Composition	Value	Ref.	
12	Polyvinyl alcohol (PVA)/ α -ChNWs	Storage modulus, GPa (25 °C)	ChNWs/PVA = 17.74/82.26	220	94	
			ChNWs/PVA = 25.38/74.62	105		
			PVA	1.66		
			ChNWs/PVA = 3/97	3.35		
			ChNWs/PVA = 5/95	3.77		
			ChNWs/PVA = 10/90	4.48		
			ChNWs/PVA = 15/85	4.90		
			ChNWs/PVA = 20/80	6.16		
			ChNWs/PVA = 30/70	6.18		
			Storage modulus, GPa (150 °C)	PVA		0.14
		ChNWs/PVA = 3/97		0.22		
		ChNWs/PVA = 5/95		0.36		
		ChNWs/PVA = 10/90		0.47		
		ChNWs/PVA = 15/85		0.57		
		ChNWs/PVA = 20/80		0.86		
		ChNWs/PVA = 30/70		1.18		
		Retention ratio, %		PVA		8
				ChNWs/PVA = 3/97		7
				ChNWs/PVA = 5/95		10
			ChNWs/PVA = 10/90	11		
ChNWs/PVA = 15/85	12					
ChNWs/PVA = 20/80	14					
ChNWs/PVA = 30/70	19					
13	Polyvinyl alcohol (PVA, DP = 591)/ α -ChNWs		Young modulus, MPa	Sandwich-like structure, ratio not shown		52
				PVA	207.41	
			Elongation at break, %	Heat treated PVA/ChNWs	311.23	
		PVA		85.4		
		Tensile strength, MPa	PVA/ChNWs	51.0		
			Heat treated PVA/ChNWs	46.0		
		Water-resistant pressure, mm	PVA	42.5		
			PVA/ChNWs	46.5		
		Oxygen transmission rate, cc m ⁻² day ⁻¹	Heat treated PVA/ChNWs	48.0		
			PVA	375		
			PVA/ChNWs	385		
			Heat treated PVA/ChNWs	768.72		
			PVA	6.32		
			PVA/ChNWs	2.75		
		14	Boron nitride modified with silane (BNSi)/ChNWs/PVA	Electrical resistance, Ω	Heat treated PVA/ChNWs	
PVA	5.7×10^{10}					
Thermal conductivity, W m ⁻¹ K ⁻¹	BNSi-ChNWs/PVA = 4.35/21.74/73.91			5.5×10^9		
	PVA			0.353		
15	Boron nitride modified with poly-vinylpyrrolidone (BNPVP)/ChNWs/PVA	Electrical resistance, Ω	BNSi-ChNWs/PVA = 4.35/21.74/73.91	1.034		
			PVA	5.70×10^{10}		
		Thermal conductivity, W m ⁻¹ K ⁻¹	BNPVP-ChNWs/PVA = 4.35/21.74/73.91	1.57×10^9		
			PVA	0.353		
16	Montmorillonite/PVA/ChNWs ^b	Tensile strength, MPa	BNPVP-ChNWs/PVA = 4.35/21.74/73.91	1.049	83	
			MMT/PVA = 50/50	68.99 $\pm$ 5.26		
			MMT/ChNWs = 50/50	10.89 $\pm$ 2.10		
			PVA/ChNWs = 50/50	45.37 $\pm$ 6.14		
		Elongation at break, %	ChNWs/MMT/PVA = 33.33/33.33/33.33	263.50 $\pm$ 4.01		
			MMT/PVA = 50/50	1.54 $\pm$ 0.34		
			MMT/ChNWs = 50/50	0.41 $\pm$ 0.12		
			PVA/ChNWs = 50/50	0.26 $\pm$ 0.03		
		Young's modulus, GPa	ChNWs/MMT/PVA = 33.33/33.33/33.33	0.60 $\pm$ 0.03		
			MMT/PVA = 50/50	4.48 $\pm$ 1.12		
			MMT/ChNWs = 50/50	2.66 $\pm$ 0.97		
			PVA/ChNWs = 50/50	17.45 $\pm$ 1.04		
		Toughness, J m ⁻³	ChNWs/MMT/PVA = 33.33/33.33/33.33	43.92 $\pm$ 1.28		
			MMT/PVA = 50/50	61.34		
	MMT/ChNWs = 50/50	2.33				



Table 11 (Contd.)

Polyvinyl alcohol (PVA)					
No.	Polymers	Property affected	Composition	Value	Ref.
17	PVA (DP = ~2727) crosslinked with borax (PB)/acid hydrolyzed ChNCs (AChNCs)/TEMPO-oxidized ChNCs (TChNCs)	Transmittance, %	PVA/ChNWs = 50/50	5.88	223
			ChNWs/MMT/PVA = 33.33/33.33/33.33	102.15	
			MMT/PVA = 50/50	20	
			MMT/ChNWs = 50/50	10	
			PVA/ChNWs = 50/50	80	
			ChNWs/MMT/PVA = 33.33/33.33/33.33	40	
		Tensile strength, kPa	Borax crosslinked PVA (PB)	1.3	
			AChNCs/PB = 0.5/99.5	13.8	
			AChNCs/PB = 1.0/99.0	18.3	
			AChNCs/PB = 1.5/98.5	31.5	
			AChNCs/PB = 2.0/98.0	54.3	
			TChNCs/PB = 0.5/99.5	3.3	
		Elongation at break, %	TChNCs/PB = 1.0/99.0	5.0	
			TChNCs/PB = 1.5/98.5	6.8	
			TChNCs/PB = 2.0/98.0	9.3	
			PB	1426	
			AChNCs/PB = 0.5/99.5	746	
			AChNCs/PB = 1.0/99.0	658	
		Work of fracture, kJ m ⁻³	AChNCs/PB = 1.5/98.5	582	
			AChNCs/PB = 2.0/98.0	424	
			TChNCs/PB = 0.5/99.5	1132	
			TChNCs/PB = 1.0/99.0	787	
			TChNCs/PB = 1.5/98.5	745	
			TChNCs/PB = 2.0/98.0	542	
		Self-healing efficiency, %	PB	1074	
			AChNCs/PB = 0.5/99.5	5918	
			AChNCs/PB = 1.0/99.0	7786	
			AChNCs/PB = 1.5/98.5	8989	
			AChNCs/PB = 2.0/98.0	10 995	
			TChNCs/PB = 0.5/99.5	2721	
		Conductivity, S m ⁻¹	TChNCs/PB = 1.0/99.0	3184	
			TChNCs/PB = 1.5/98.5	3732	
			TChNCs/PB = 2.0/98.0	4541	
			PB	99.4	
			AChNCs/PB = 1.0/99.0	90.4	
			AChNCs/PB = 1.5/98.5	87.8	
			TChNCs/PB = 1.0/99.0	96.0	
			TChNCs/PB = 1.5/98.5	89.5	
			PB	2.02 × 10 ⁻⁵	
			AChNCs/PB = 1.0/99.0	2.08 × 10 ⁻⁶	
			AChNCs/PB = 1.5/98.5	1.51 × 10 ⁻⁶	
			TChNCs/PB = 1.0/99.0	6.94 × 10 ⁻⁶	
			TChNCs/PB = 1.5/98.5	1.25 × 10 ⁻⁵	

^aThe dried ChNCs/PVA composite films were swollen and then stretched at various draw ratios ranging from 1 to 3, using a stretching speed of 10 mm min^{-1} . Here, "x" in x-ChNCs/PVA denotes the specific stretch ratio applied to the films, while maintaining a constant ChNCs/PVA composition. ^bFour distinct films were created: MMT/PVA, MMT/ChNCs, PVA/ChNCs, and ChNCs/MMT/PVA and the properties of each film were then compared.

1) is substantially amplified compared to that with ChNCs (Table 11, entries 2–7). While tensile strength and Young's modulus increased significantly compared to neat PVA, elongation showed only a modest increase at a 60 wt% nanochitin concentration.

Other studies developed novel strategies to prepare ChNCs/PVA films with improved strength and durability, where ChNCs acted as building blocks and essential components and PVA acted as adhesive.^{40,80} One of the strategies of the studies was introducing a two-step treatment process using

salt and alkali, respectively into the mixture of ChNCs and PVA.⁴⁰ It was observed that among all ionic shielded ChNCs (IsChNCs) composite films, the film with 70 wt% ionic shielded ChNCs exhibited the optimal overall performance (Table 11, entry 6). At the same ChNC load, the Young's modulus of the IsChNCs/PVA film is nearly twice that of the ChNCs/PVA film, while maintaining comparable elongation at break, suggesting that the ionic shield effect of salt greatly weakened the electrostatic repulsion on the ChNC surface, resulting in aggregation of the ChNCs in a certain extent.



Furthermore, integrating the ionic shielding effect of salt and hydrogen bond remodeling effect of alkali resulted in significantly improved performance, with Young's modulus and tensile strength increasing to 5307.1 ± 106.2 MPa and 67.0 ± 1.2 MPa, respectively – 1.7 and 1.5 times higher than those of the IsChNW/PVA film. Alkali treatment of IsChNWs/PVA films disrupted interparticle hydrogen bonds among ChNWs, allowing PVA to penetrate ChNW aggregates and fill the interspace, thereby enhancing the hydrogen bond interaction between ChNWs and PVA.⁴⁰

The follow-up study further evaluated the alkali-treated IsChNWs/PVA films and tuned the film properties by developing a tensile-induced orientation and hydrogen bond reconstruction strategy⁸⁰ to initiate inter-layer sliding (Table 11, entry 7). The alkali-treated IsChNWs/PVA films were first swollen in deionized water and stretched at a certain draw ratio, then soaked in alkali to reconstruct the hydrogen bonds and stabilize the orientational structure. The films, which underwent stretching and hydrogen-bond reconstruction, exhibited enhanced tensile strength and elongation from 38.6 to 115.2 MPa and 9.37% to 40.7%, respectively. Additionally, morphological analysis of these films before and after tensile failure revealed that the mechanisms responsible for strengthening and toughening were linked to intra-layer ordering and inter-layer sliding, respectively. The stacked multilayer structure and organized arrangement of the ChNWs allowed external stress to be efficiently transferred through the aligned ChNWs within the layers. This stress was then dissipated through the layering effect and inter-layer sliding, leading to a combination of reinforcing and toughening effects.⁸⁰

When nanochitin was utilized specifically as a reinforcement filler, the tensile strength peaked at 3–5 wt% nanochitin concentrations of (Table 11, entries 8–10), depending on the nature of the material, the preparation method, and the material's intended brittleness and strength. Consistently, elongation at break decreased with increasing chitin content, but increased with higher PVA content when chitin was the primary substrate. Other mechanical properties, such as Young's modulus, storage modulus, and compressive fracture stress, also improved with higher nanoparticles content.

Junkasem *et al.* fabricated electrospun nanocomposite fibers and solvent-casted films with PVA serving as the matrix.⁴⁹ This group evaluated the ChNW reinforcement effect, and the compatibility of the composite components prepared from different methods on the composite mechanical integrity (Table 11, entries 10 and 11). Although the tensile strengths of both as-spun PVA/ChNWs fiber mats and as-cast PVA/ChNWs films increased with the addition of ChNWs, the critical thresholds were distinct. The tensile strength of the as-spun fiber mats reached its threshold (5.7 ± 0.6 MPa) at approximately 5.1 wt% and decreased with further increases in ChNW content (Table 11, entry 10). In contrast, the tensile strength of the as-cast films reached its threshold (45.2 ± 3.6 MPa) at 17.7 wt% (Table 11, entry 11). A similar disparity was observed in the case of Young's modulus for both composites. The strength initially increased for the as-spun fibers, reaching a

threshold at 15.2%, whereas for the as-cast films, it continued to increase with each addition of ChNWs. The author reported that the discrepancy was possibly attributed to the difference in the dimensionality of the two sample types. The observed decrease in Young's modulus of the as-spun fibers above 15.2% ChNW load was likely due to the ChNW aggregation arising from the confinement effect, which was not observed in the as-cast films, unless the thickness of the films approached the sizes of the nanosized reinforcing fillers.⁴⁹

Another study focused on the preparation of PVA blends with hybrid materials, that combined ChNWs and modified boron nitride, to enhance the thermal and electrical conductivity of the final composites (Table 11, entries 14 and 15).⁸¹ Leveraging the high thermal conductivity of boron nitride to create an efficient thermal conductivity network within the polymer matrix, two modified boron nitrides – silane coupling agent-treated boron nitride (BNSi) and poly-vinylpyrrolidone-treated boron nitride (BNPVP) – were combined with ChNWs before being compounded with PVA to produce BNSi-ChNWs/PVA and BNPVP-ChNWs/PVA composites. The incorporation of the hybrid materials into the PVA matrix resulted in enhanced thermal conductivity (192.9–197.2% higher than neat PVA), with the BNPVP-ChNWs-reinforced composite outperforming the BNSi-ChNWs version ($1.049 \text{ W m}^{-1} \text{ K}^{-1}$ vs. $1.034 \text{ W m}^{-1} \text{ K}^{-1}$, respectively). The improvement in both reinforced composites was attributed to the enhanced interface compatibility of the hybrid materials, which allowed for more even dispersion in PVA and the formation of effective thermal conductivity networks.⁸¹ However, no significant improvements were observed in the electrical insulation performance in the composites with these hybrid materials. Instead, the electrical resistance of the reinforced composites is an order of magnitude lower than that of the neat PVA, with BNPVP-ChNW/PVA showing the lowest resistance ($1.57 \times 10^9 \Omega$), which was attributed to the proton-conductive nature of PVP. Meanwhile, the slightly lower electrical resistance of BNSi-ChNW/PVA indicated that silanization primarily improved the dispersion of the boron nitride in the matrix and enhanced interfacial bonding between boron nitride particles, ChNWs, and PVA. Despite their relatively low electrical resistance, both PVA composites still exhibited stable electrical insulation performance for practical applications.

Wu *et al.*⁸³ evaluated the degree of ChNW reinforcement on the properties of montmorillonite (MMT)/PVA films (Table 11, entry 16). Four types of films, each with the same weight percent ratio – MMT/PVA, MMT/ChNWs, PVA/ChNWs, and ChNWs/MMT/PVA – were prepared using the casting-evaporation approach, and the properties of each film were then compared. Among all the films, the ChNWs/MMT/PVA composites demonstrated superior tensile strength and Young's modulus, although toughness decreased (Table 11, entry 16). As highlighted by the authors, the enhancement was attributed to the presence of a new crystalline structure arising from the intercalation of PVA and ChNW in the layer of MMT sheet through hydrogen bond and van der Waals forcing.⁸³

Another recent study by Jiao *et al.*²²³ highlighted how the surface charge state of ChNCs significantly affects the structure



and properties of borax-crosslinked PVA (PB) hydrogels (Table 11, entry 17). The study examined two types of ChNCs with opposite surface charges—positively charged ChNCs (AChNCs) prepared by acid hydrolysis and negatively charged ChNCs (TChNCs) prepared by TEMPO oxidation—as reinforcements for PB hydrogels. The results showed that among hydrogels containing from 0.5 to 2 wt% AChNCs, those with 2 wt% exhibited the highest tensile strength, a 17-fold increase compared to unreinforced PB hydrogels, while maintaining high elongation at break. A similar trend was observed with TChNCs, but their reinforcement was less effective. Additionally, both AChNCs and TChNCs improved the fracture work of the hydrogels, with AChNCs showing greater effectiveness. Maximum fracture work was achieved at a 2 wt% load for both reinforcements. The superior performance of AChNCs is associated with electrostatic attraction between the hydroxyl groups of AChNCs and borax ions, forming a second network in addition to the borax-crosslinked PVA network, which enhances mechanical performance. In contrast, the TChNCs created charge repulsion with the borax crosslinker and attracted a lesser amount of borax ions, leading to a relatively loose network structure in the composite hydrogels.²²³

The study also evaluated the impact of charged ChNCs on the self-healing efficiency and conductivity of the composite hydrogels. It was found that TChNCs enhance the self-healing ability and ionic conductivity more effectively than AChNCs, with values of 89.5% and $1.25 \times 10^{-5} \text{ S m}^{-1}$ compared to 87.8% and 1.51×10^{-6} , respectively, at a 1 wt% load. The authors suggest that this difference is due to the energy required during healing and the mobility of borax ions in the composite hydrogels. Specifically, the strong electrostatic attraction in the AChNCs/PB hydrogel leads to more dynamic borate bonds, which increases the fracture work and requires more energy for healing, resulting in lower self-healing efficiency. Furthermore, this attraction restricts the movement of borax ions in the AChNCs/PB hydrogel, reducing conductivity. In contrast, the repulsive interaction between TChNCs and borax ions facilitates ion movement, improving both conductivity and self-healing performance.²²³

4.5. Reinforcement of epoxy resins with nanochitin

Epoxy resins are synthetic thermosetting polymers formed from two or more active epoxide groups. Known for their strong adhesion and effective crosslinking with various curing agents,²²⁴ epoxy resins typically cure between 0 and 180 °C without producing by-products, transforming into an insoluble 3-D network polymer.²²⁵ Despite their advantageous properties, epoxy resins face limitations, including brittleness, weak impact resistance, and poor resilience.²²⁶ To address these issues, they are often reinforced with nanofillers such as graphene oxide, carbon nanotubes, nano silica, and more.^{227–229} Recently, research has focused on reinforcing epoxy resins with renewable, and sustainable nanofillers like nanochitin to improve their performance.²³⁰ These nanocomposite materials have wide-ranging applications in biomedical fields, aerospace, adhesives, packaging, and coatings.²³¹

Several studies have explored the reinforcement of epoxy resin with chitin nanoparticles under various conditions (Table 12, entries 1–10). (DGEBA) based chitin nanocomposites substantially brought about an improvement in much of the mechanical properties (Table 12, entries 1–3). Wang *et al.*²³ synthesized high-strength ChNWs/epoxy resin bisphenol A diglycidyl ether (DGEBA) nanocomposites using 1-ethyl-3-methylimidazolium acetate ([Emim][OAc]) ionic liquid for effective dispersion of ChNWs (Table 12, entry 1). Results showed a significant improvement in mechanical properties with the ChNWs incorporation from 0.75 to 2 wt%. The addition of 2 wt% led to a maximum increase of 8.3% in Young's modulus, 34.5% in tensile strength, and 80% in strain compared to the neat polymer. Energy to failure and impact strength also exhibited substantial increases of 174.7% and 91.4%, respectively, at the same critical concentration. However, upon comparing the percentage increase in all the defined properties, a minimal improvement in Young's modulus was observed, likely due to the plasticizing effect of the ionic liquid that might have counteracted the reinforcing impact of ChNWs.

A similar trend was observed by Wang *et al.*²⁷ where ChNWs were loaded at concentrations ranging from 0.5 to 2.5 wt%. The properties such as tensile strength, modulus, elongation at break, and toughness showed remarkable improvements (49%, 16%, 150%, and 357%, respectively) up to 2.5 wt% of ChNWs (Table 12, entry 2). Comparing these studies,^{23,27} it can be inferred that beyond 3 wt%, all properties began to decline,²³ highlighting the optimal ChNW concentration at around 2 to 2.5 wt%.

On the other hand, Anwer *et al.*³ studied the effects of ChNWs in epoxy resins cured with triethylenetetramine (TETA), with ChNW loadings ranging from 0.25 to 0.75 wt% (Table 12, entry 3). This group observed significant increases in tensile modulus, tensile strength, and storage modulus, with 0.25 wt% ChNWs achieving the highest improvements. The addition of ChNWs resulted in a stable covalent network among the epoxy, fillers, and hardeners (*e.g.*, TETA), providing high strength without immediate failure.²⁷

In studies involving bio-based sorbitol polyglycidyl ether (SPE) epoxy resins, tensile properties such as tensile strength, modulus, and elongation at break were investigated before and after the addition of ChNFs, under the influence of several curing agents at different conditions (Table 12, entries 4–10).^{148,161} Shibata *et al.*¹⁴⁸ fabricated bio-nanocomposites composed of SPE, ChNFs, and chitosan (CS) and/or a commercial water-soluble polyamidoamine (PAA) or polyetheramine (PEA) as amine-type hardeners *via* the casting or compression molding method (Table 12, entries 4–7). They synthesized the nanocomposite resins by curing ChNFs/SPE with CS alone, or with CS-PAA (CA) and CS-PEA (CE) under different active hydrogen ratios. The CS/PAA was evaluated at two ratios, *i.e.*, 1 : 1 (CA11) and 2 : 1 (CA21), while CS/PEA was assessed only at 2 : 1 ratio (CE21). For the cured resins without ChNFs, SPE-CS exhibited higher tensile strength and modulus (46.9 MPa and 2078 MPa, respectively) compared to the other three resins





Table 12 Reinforcement of epoxy resins with nanochitin

No.	Polymers	Affected properties	Composition	Value	Ref.
Epoxy resins					
Epoxy resin: bisphenol A diglycidyl ether (DGEBA)					
1	Epoxy resin bisphenol A diglycidyl ether (DGEBA)/ChNWs	Young's modulus, MPa	DGEBA ChNWs/DGEBA = 0.75/99.25 ChNWs/DGEBA = 1.0/99.0 ChNWs/DGEBA = 1.5/98.5 ChNWs/DGEBA = 2.0/98.0 ChNWs/DGEBA = 3.0/97.0	948.83 ± 8.70 978.92 ± 20.89 956.33 ± 15.28 967.62 ± 7.93 1028.06 ± 37.31 946.70 ± 13.34 69.76 ± 2.93	23
		Tensile strength, MPa	DGEBA ChNWs/DGEBA = 0.75/99.25 ChNWs/DGEBA = 1.0/99.0 ChNWs/DGEBA = 1.5/98.5 ChNWs/DGEBA = 2.0/98.0 ChNWs/DGEBA = 3.0/97.0	84.33 ± 0.17 89.59 ± 2.47 91.08 ± 3.09 93.80 ± 2.06 83.92 ± 2.00 0.10 ± 0.0048	
		Tensile strain, mm mm ⁻¹	DGEBA ChNWs/DGEBA = 0.75/99.25 ChNWs/DGEBA = 1.0/99.0 ChNWs/DGEBA = 1.5/98.5 ChNWs/DGEBA = 2.0/98.0 ChNWs/DGEBA = 3.0/97.0	0.12 ± 0.0067 0.15 ± 0.012 0.16 ± 0.017 0.18 ± 0.0098 0.13 ± 0.011 4.07 ± 0.36	
		Energy to failure, J cm ⁻³	DGEBA ChNWs/DGEBA = 0.75/99.25 ChNWs/DGEBA = 1.0/99.0 ChNWs/DGEBA = 1.5/98.5 ChNWs/DGEBA = 2.0/98.0 ChNWs/DGEBA = 3.0/97.0	5.90 ± 0.43 8.08 ± 1.08 9.14 ± 0.55 11.18 ± 1.08 6.43 ± 0.85 68.17 ± 3.83	
		Impact strength, J m ⁻²	DGEBA ChNWs/DGEBA = 0.75/99.25 ChNWs/DGEBA = 1.0/99.0 ChNWs/DGEBA = 1.5/98.5 ChNWs/DGEBA = 2.0/98.0 ChNWs/DGEBA = 3.0/97.0	90.70 ± 6.07 120.44 ± 1.93 124.03 ± 2.84 130.48 ± 1.21 115.48 ± 3.08	27
2	Epoxy resin bisphenol A diglycidyl ether (DGEBA)/ChNWs	Tensile strength, MPa	DGEBA ChNWs/DGEBA = 0.5/99.5 ChNWs/DGEBA = 1.0/99.0 ChNWs/DGEBA = 2.5/97.5	51.6 67.4 72.8	
		Tensile modulus, MPa	DGEBA ChNWs/DGEBA = 0.5/99.5 ChNWs/DGEBA = 1.0/99.0 ChNWs/DGEBA = 2.5/97.5	77.1 2410 2733	
		Elongation at break, %	DGEBA ChNWs/DGEBA = 0.5/99.5 ChNWs/DGEBA = 1.0/99.0 ChNWs/DGEBA = 2.5/97.5	2760 2812 3.31	
		Toughness J m ⁻³ 10 ⁴	DGEBA ChNWs/DGEBA = 0.5/99.5 ChNWs/DGEBA = 1.0/99.0 ChNWs/DGEBA = 2.5/97.5	5.02 6.35 8.27	
		Tensile modulus, MPa	DGEBA ChNWs/DGEBA = 0.25/99.75 ChNWs/DGEBA = 1.0/99.0 ChNWs/DGEBA = 2.5/97.5	99.7 213.0 309.0	3
3	Epoxy resin bisphenol A diglycidyl ether (DGEBA)/ChNWs	Tensile strength, MPa	DGEBA ChNWs/DGEBA = 0.25/99.75 ChNWs/DGEBA = 0.50/99.50 ChNWs/DGEBA = 0.75/99.25	456.0 1000 1250	
		Tensile strain at failure, mm/mm	DGEBA ChNWs/DGEBA = 0.25/99.75 ChNWs/DGEBA = 0.50/99.50 ChNWs/DGEBA = 0.75/99.25	1200 1050 70	
			DGEBA ChNWs/DGEBA = 0.25/99.75 ChNWs/DGEBA = 0.50/99.50 ChNWs/DGEBA = 0.75/99.25	78 76 75	
			DGEBA ChNWs/DGEBA = 0.25/99.75	0.120 0.100	



Table 12 (Contd.)

No.	Polymers	Affected properties	Composition	Value	Ref.
4	Epoxy resin: sorbitol polyglycidyl ether (SPE)/ Epoxy resin sorbitol polyglycidyl ether (SPE)/ ChNFs/chitosan nanofibers (CSNFs)/chitosan (CS)	Storage modulus, MPa	ChNWs/DGEBA = 0.50/99.50	0.110	148
			ChNWs/DGEBA = 0.75/99.25	0.124	
			DGEBA	2240	
			ChNWs/DGEBA = 0.25/99.75	2450	
		Loss modulus, MPa	ChNWs/DGEBA = 0.50/99.50	2420	
			ChNWs/DGEBA = 0.75/99.25	2400	
		Energy to tensile failure, J cm ⁻³	DGEBA	50	
			ChNWs/DGEBA = 0.25/99.75	53	
			ChNWs/DGEBA = 0.50/99.50	54	
			ChNWs/DGEBA = 0.75/99.25	63	
			DGEBA	5.2	
			ChNWs/DGEBA = 0.25/99.75	5.0	
			ChNWs/DGEBA = 0.50/99.50	5.2	
			ChNWs/DGEBA = 0.75/99.25	6.5	
5	Epoxy resin sorbitol polyglycidyl ether (SPE)/ChNFs(chitosan (CS)/polyamidoamine (PAA)	Tensile strength, MPa	SPE/CS	46.9	148
			ChNFs/SPE/CS = 33/66.25/30.75	49.6	
			ChNFs/SPE/CS = 5/64.88/30.11	37	
			ChNFs/SPE/CS = 10/61.47/28.53	59.3	
		Tensile modulus, MPa	SPE/CS	2078	
			ChNFs/SPE/CS = 33/66.25/30.75	2390	
			ChNFs/SPE/CS = 5/64.88/30.11	1723	
			ChNFs/SPE/CS = 10/61.47/28.53	1736	
		Elongation at break, %	SPE/CS	2.78	
			ChNFs/SPE/CS = 33/66.25/30.75	3.96	
			ChNFs/SPE/CS = 5/64.88/30.11	3.58	
			ChNFs/SPE/CS = 10/61.47/28.53	5.16	
		Tensile strength, MPa	SPE/CA11 ^a	11.1	
			ChNFs/SPE/CA11 = 3/53.54/43.46	16.1	
6	Epoxy resin sorbitol polyglycidyl ether (SPE)/ChNFs(chitosan (CS)/polyamidoamine (PAA)		ChNFs/SPE/CA11 = 5/52.44/42.56	15.6	148
			ChNFs/SPE/CA11 = 10/49.68/40.32	11.7	
		Tensile modulus, MPa	SPE/CA11	46.2	
			ChNFs/SPE/CA11 = 3/53.54/43.46	622.0	
			ChNFs/SPE/CA11 = 5/52.44/42.56	498.0	
			ChNFs/SPE/CA11 = 10/49.68/40.32	416.0	
		Elongation at break, %	SPE/CA11	11.8	
			ChNFs/SPE/CA11 = 3/53.54/43.46	7.51	
			ChNFs/SPE/CA11 = 5/52.44/42.56	7.42	
			ChNFs/SPE/CA11 = 10/49.68/40.32	4.50	
		Tensile strength, MPa	SPE/CA21 ^b	11.8	
			ChNFs/SPE/CA21 = 3/53.54/43.46	25.5	
			ChNFs/SPE/CA21 = 5/52.44/42.56	17.9	
			ChNFs/SPE/CA21 = 10/49.68/40.32	17.1	
7	Epoxy resin sorbitol polyglycidyl ether (SPE)/ChNFs(chitosan (CS)/polyetheramine (PEA)	Tensile modulus, MPa	SPE/CA21	37.3	148
			ChNFs/SPE/CA21 = 3/53.54/43.46	1051.0	
			ChNFs/SPE/CA21 = 5/52.44/42.56	394.0	
			ChNFs/SPE/CA21 = 10/49.68/40.32	753.0	
		Elongation at break, %	SPE/CA21	8.94	
			ChNFs/SPE/CA21 = 3/53.54/43.46	5.12	
			ChNFs/SPE/CA21 = 5/52.44/42.56	5.15	
			ChNFs/SPE/CA21 = 10/49.68/40.32	3.39	
		Tensile strength, MPa	SPE/CE21 ^c	9.07	
			ChNFs/SPE/CE21 = 3/53.54/43.46	14.10	
			ChNFs/SPE/CE21 = 5/52.44/42.56	18.30	
			ChNFs/SPE/CE21 = 10/49.68/40.32	11.50	
		Tensile modulus, MPa	SPE/CE21	36.8	
			ChNFs/SPE/CE21 = 3/53.54/43.46	453.0	



Table 12 (Contd.)

No.	Polymers	Affected properties	Composition	Value	Ref.
8	Epoxy resin (sorbitol poly glycidyl ether (SPE))/(ChNFs/lysine (Lys))	Elongation at break, %	ChNFs/SPE/CE21 = 5/52.44/42.56	676.0	161
			ChNFs/SPE/CE21 = 10/49.68/40.32	147.0	
			SPE/CE21	7.03	
			ChNFs/SPE/CE21 = 3/53.54/43.46	4.77	
		Tensile modulus, MPa	ChNFs/SPE/CE21 = 5/52.44/42.56	4.20	
			ChNFs/SPE/CE21 = 10/49.68/40.32	3.92	
			SPE/Lys	855	
			ChNFs/SPE/Lys = 3.00/82.94/14.07	1257	
		Tensile strength, MPa	ChNFs/SPE/Lys = 5.00/81.23/13.78	537	
			ChNFs/SPE/Lys = 10.00/76.95/13.05	220	
			SPE/Lys	26.7	
			ChNFs/SPE/Lys = 3.00/82.94/14.07	45.6	
		Elongation at break, %	ChNFs/SPE/Lys = 5.00/81.23/13.78	33.5	
			ChNFs/SPE/Lys = 10.00/76.95/13.05	28.7	
			SPE/Lys	2.1	
			ChNFs/SPE/Lys = 3.00/82.94/14.07	3.9	
9	Epoxy resin (sorbitol poly glycidyl ether (SPE))/(ChNFs/arginine (Arg))	Tensile modulus, MPa	ChNFs/SPE/Lys = 5.00/81.23/13.78	7.9	161
			ChNFs/SPE/Lys = 10.00/76.95/13.05	5.3	
			SPE/Arg	422	
			ChNFs/SPE/Arg = 3.00/84.79/12.21	263	
		Tensile strength, MPa	ChNFs/SPE/Arg = 5.00/83.05/11.95	64	
			ChNFs/SPE/Arg = 10.00/78.68/11.32	505	
			SPE/Arg	8.5	
			ChNFs/SPE/Arg = 3.00/84.79/12.21	4	
		Elongation at break, %	ChNFs/SPE/Arg = 5.00/83.05/11.95	2.2	
			ChNFs/SPE/Arg = 10.00/78.68/11.32	9.1	
			SPE/Arg	3.3	
			ChNFs/SPE/Arg = 3.00/84.79/12.21	3.6	
		Tensile modulus, MPa	ChNFs/SPE/Arg = 5.00/83.05/11.95	10.6	
			ChNFs/SPE/Arg = 10.00/78.68/11.32	11.4	
			SPE/Cys	584	
			ChNFs/SPE/Cys = 3.00/84.79/12.21	30	
10	Epoxy resin (sorbitol poly glycidyl ether (SPE))/(ChNFs/cysteine (Cys))	Tensile strength, MPa	ChNFs/SPE/Cys = 5.00/83.05/11.95	128	161
			ChNFs/SPE/Cys = 10.00/78.68/11.32	236.8	
			SPE/Cys	10	
			ChNFs/SPE/Cys = 3.00/84.79/12.21	4.8	
		Elongation at break, %	ChNFs/SPE/Cys = 5.00/83.05/11.95	8.45	
			ChNFs/SPE/Cys = 10.00/78.68/11.32	7.99	
			SPE/Cys	19.5	
			ChNFs/SPE/Cys = 3.00/84.79/12.21	30.7	
			ChNFs/SPE/Cys = 5.00/83.05/11.95	27.74	
			ChNFs/SPE/Cys = 10.00/78.68/11.32	11.8	

^aThe abbreviation of CA11 represents CS/PAA active hydrogen ratio 1/1. ^bThe abbreviation of CE21 represents CS/PEA active hydrogen ratio 2/1. ^cThe abbreviation of CA21 represents CS/PEA active hydrogen ratio 2/1.

(11.1 MPa and 46.2 MPa for SPE-CA11, 11.8 MPa and 37.3 MPa for SPE-CA21, and 9.07 MPa and 36.8 MPa for SPE-CE21). However, SPE-CS showed a much lower elongation at break, indicating that the CS-cured SPE has higher rigidity, while the PAA- or PEA-cured SPE shows greater flexibility. Adding ChNFs into all the bio-nanocomposite resins significantly improved their strength and rigidity with tensile strength and modulus peaking at 3 wt% ChNFs for most SPE-cured resins, except for the CS-PEA system, which reached its threshold at 5 wt% ChNFs. Among all the ChNWs/SPE composites with CA and CE curing agents, the ChNFs/SPE/CA21 nanocomposites showed the highest values for tensile strength (25.5 MPa) and modulus (1051 MPa) at 3 wt% ChNFs. Meanwhile, the ChNFs/SPE/CS composites showed even higher values of strength (49.6 MPa) and modulus (2390 MPa). However, elongation at break decreased consistently across all ChNFs/SPE-CA and ChNFs/SPE-CE composites. In contrast, the elongation at break increased in the ChNFs/SPE/CS resins with all ChNFs additions (up to 10 wt%). Upon comparing all the properties, the addition of ChNFs acted as an efficient reinforcing agent, while CS served as a more effective hardener, providing high rigidity, and PAA enhanced brittleness.¹⁴⁸

Further studies by the same authors investigated the use amino acids including lysine (Lys), arginine (Arg), and cysteine (Cys), as curing agents for SPE based composites (Table 12, entries 8–10).¹⁶¹ The results indicated that, except for ChNFs/SPE/Lys bionanocomposites, no reinforcement effect was observed in ChNFs/SPE-Arg and ChNFs/SPE-Cys systems. Specifically, the tensile strength (26.7 MPa) and modulus (855 MPa) of neat SPE/Lys composites improved with the addition of ChNFs, reaching 45.6 MPa and 1257 MPa, respectively, at a concentration of 3 wt% (Table 12, entry 8). Nevertheless, the addition of ChNFs significantly enhanced the elongation at break in all nanocomposites, reaching peak improvement at 5 wt% for ChNFs/SPE/Lys and ChNFs/SPE-Cys (Table 12, entries 8 and 10), and at 10 wt% for ChNFs/SPE-Arg (Table 12, entry 9), implying the reduction in crosslink density.

4.6. Reinforcement of other plastics with nanochitin

4.6.1. Thermoplastic synthetic polymers: poly(ϵ -caprolactone) (PCL), polycarbonate (PC), and poly(styrene-*co*-butyl acrylate). Poly(ϵ -caprolactone) (PCL), polycarbonate (PC), and poly(styrene-*co*-butyl acrylate) (poly(S-*co*-BuA)) are thermoplastic synthetic polymers known for their excellent processability and film-forming ability.^{76,97,232–234} While PCL is semi-crystalline, PC and poly(S-*co*-BuA) are mostly amorphous, influencing their mechanical properties and flexibility. These polymers can be processed using various techniques such as casting, extrusion, and molding, making them versatile for different applications. These polymers have been also studied for composite reinforcement with nanomaterials like chitin nanowhiskers (ChNWs).

The incorporation of nanochitin into PCL resulted in only a marginal improvement in tensile properties, regardless of whether the casting and evaporation method or hot pressing was used for composite fabrication (Table 13, entry 1).⁹⁷

However, a slight increase in tensile strength was observed with higher nanochitin concentrations, with tensile values increasing from 8.50 Pa for neat PCL to 8.86 Pa and 8.98 Pa for composites containing 5 wt% and 10 wt% chitin nanowhiskers (ChNW), respectively. Similarly, the incorporation of ChNWs into poly(S-*co*-BuA) led to only a minor improvement in tensile modulus, independent of the fabrication method used (Table 13, entry 2).⁹⁷ For cast-evaporated poly(S-*co*-BuA), the tensile modulus increased from 5.75 Pa to 6.75 Pa at 5 wt% ChNWs. In hot-pressed poly(S-*co*-BuA), the tensile modulus increased from 8.5 Pa to 8.9 Pa at 5 wt% ChNWs. These findings suggest that while nanochitin incorporation provides some enhancement in mechanical properties, the improvements remain limited.⁹⁷ The likely reason is the poor interaction between ChNWs and the polymers due to differences in surface chemistry, which leads to ineffective stress transfer from the polymer to the nanowhiskers, resulting in minimal reinforcement.

When composite membranes were fabricated using a phase inversion process, incorporating polycarbonate (PC) recovered from waste compact discs, polysulfone (PSf), and chitin nanowhiskers (ChNWs) to enhance their mechanical properties and performance,⁷⁶ the improvements observed were also minor (Table 13, entry 3). The tensile strength of the composite membranes exhibited only minor improvements with the incorporation of chitin nanowhiskers (ChNWs). As the ChNW content increased from 2% to 10% in 2% increments, the corresponding tensile strength (MPa) values increased from 2.0 MPa for rPC/PSf = 1/1 to 2.2 MPa for the same composite with 10% ChNWs incorporated. These results suggest that the mechanical enhancement achieved with increasing ChNW concentration remains limited.

The elongation at break of the composite membranes varied with the incorporation of chitin nanowhiskers (ChNWs), see Table 13, entry 3. For rPC/PSf = 50/50, the elongation at break was 12.0%. As the ChNW content increased from 2% to 10% in 2% increments, the corresponding values fluctuated, decreasing to 8.5% at 2% ChNW and further to 8.0% at 4% ChNW. A slight recovery was observed at 6% ChNW, reaching 10.0%, followed by a peak of 15.0% at 8% ChNW before declining to 11.0% at 10% ChNW. These results indicate a non-linear trend in elongation at break, with the highest value observed at 8% ChNW.

The pure water flux (PWF), which represents the volume of pure water passing through a membrane per unit area and time ($\text{L m}^{-2} \text{h}^{-1}$), is a key parameter in evaluating membrane permeability and efficiency.^{235,236} It is crucial in membrane applications such as water treatment and filtration, where maintaining high permeability while ensuring effective separation is essential. In this study, the PWF of the composite membranes varied with the incorporation of chitin nanowhiskers (ChNWs), see Table 13, entry 3. For rPC/PSf = 50/50, the PWF was $225 \text{ L m}^{-2} \text{h}^{-1}$. As the ChNW content increased from 2% to 10% in 2% increments, the PWF initially increased, peaking at $350 \text{ L m}^{-2} \text{h}^{-1}$ at 4% ChNW. However, at higher ChNW concentrations, a decline was observed, suggesting that



Table 13 Reinforcement of other plastics with nanochitin

No.	Polymers	Affected properties	Composition	Value	Ref.
1	Poly-(ε-caprolactone) (PCL)/ChNWs	Tensile modulus, Pa at 330 K (water evaporation) ^a	PCL	8.52	97
			ChNWs/PCL = 0.5/99.5	8.36	
			ChNWs/PCL = 1.0/99.0	8.70	
			ChNWs/PCL = 2.5/97.5	8.78	
			ChNWs/PCL = 5.0/95.0	8.50	
		Tensile modulus, Pa at 298 K (hot pressed) ^a	PCL	8.58	97
			ChNWs/PCL = 0.5/99.5	8.64	
			ChNWs/PCL = 1.0/99.0	8.72	
			ChNWs/PCL = 2.5/97.5	8.86	
			ChNWs/PCL = 5.0/95.0	8.98	
2	Poly(styrene-co-butyl acrylate) (poly(S-co-BuA))/ChNWs	Tensile modulus, Pa at 298 K (water evaporation) ^a	ChNWs/PCL = 10/90.0	5.75	97
			Poly(S-co-BuA)	5.85	
			ChNWs/poly(S-co-BuA) = 0.5/99.5	6.05	
			ChNWs/poly(S-co-BuA) = 1.0/99.0	6.50	
			ChNWs/poly(S-co-BuA) = 2.5/97.5	6.75	
		Tensile modulus, Pa (hot pressed) ^a	ChNWs/poly(S-co-BuA) = 5.0/95.0	8.50	97
			Poly(S-co-BuA)	8.55	
			ChNWs/poly(S-co-BuA) = 0.5/99.5	8.70	
			ChNWs/poly(S-co-BuA) = 1.0/99.0	8.80	
			ChNWs/poly(S-co-BuA) = 2.5/97.5	8.90	
3	Recycled polycarbonate/polysulfone Recycled polycarbonate (rPC, MW 45 000)/ polysulfone (PSf, MW 75 000–81 000)/ChNWs	Tensile strength, MPa	rPC/PSf = 50/50	2.0	76
			ChNWs/rPC/PSf = 2/49/49	1.6	
			ChNWs/rPC/PSf = 4/48/48	1.6	
			ChNWs/rPC/PSf = 6/47/47	1.8	
			ChNWs/rPC/PSf = 8/46/46	2.2	
		Elongation at break, %	ChNWs/rPC/PSf = 10/45/45	2.2	76
			rPC/PSf = 50/50	12.0	
			ChNWs/rPC/PSf = 2/49/49	8.5	
			ChNWs/rPC/PSf = 4/48/48	8.0	
			ChNWs/rPC/PSf = 6/47/47	10.0	
		Pure water flux (PWF) rejection, L m ⁻² h ⁻¹	ChNWs/rPC/PSf = 8/46/46	15.0	76
			ChNWs/rPC/PSf = 10/45/45	11.0	
			rPC/PSf = 50/50	225	
			ChNWs/rPC/PSf = 2/49/49	275	
			ChNWs/rPC/PSf = 4/48/48	350	
		Bovine serum albumin (BSA) rejection, %	ChNWs/rPC/PSf = 6/47/47	250	76
			ChNWs/rPC/PSf = 8/46/46	255	
			rPC/PSf = 50/50	58	
			ChNWs/rPC/PSf = 2/49/49	70	
			ChNWs/rPC/PSf = 4/48/48	90	
		Flux recovery ratio, %	ChNWs/rPC/PSf = 6/47/47	60	76
			ChNWs/rPC/PSf = 8/46/46	62	
			rPC/PSf = 50/50	60	
			ChNWs/rPC/PSf = 2/49/49	80	
			ChNWs/rPC/PSf = 4/48/48	78	
		Flux recovery ratio, %	ChNWs/rPC/PSf = 6/47/47	98	98
			ChNWs/rPC/PSf = 8/46/46	98	
			rPC/PSf = 50/50	98	
			ChNWs/rPC/PSf = 2/49/49	98	
			ChNWs/rPC/PSf = 4/48/48	98	





Table 13 (Contd.)

No.	Polymers	Affected properties	Composition	Value	Ref.
4	Polyaniline Polyaniline (PANI)/ZnO nanoparticles (ZnO NPs)/ β-chitin chitin nanowhiskers (β ChNWs)	Elastic modulus, MPa	ChNWs	27.0	87
			β ChNWs/ZnO = 97.09/2.91	32.5	
		Elongation at break, %	β ChNWs/PANI = 99.01/0.99	4.0	
			β ChNWs/ZnO/PANI = 96.15/2.88/0.96	2.5	
			ChNWs	3.0	
			ChNWs/ZnO = 97.09/2.91	2.0	
		Tensile strength, MPa	ChNWs/PANI = 99.01/0.99	2.5	
			ChNWs/ZnO/PANI = 96.15/2.88/0.96	2.2	
			ChNWs	13.8	
			ChNWs/ZnO = 97.09/2.91	11.8	
5	Polyolefins Polypropylene (PP) ^b /α-ChNWs/TEMPO cellulose nanofibers (TCNFs)	Oxygen transmission rate, ^c cc m ⁻² day ⁻¹	ChNWs and TCNFs coated in sequence on PP film, ratio not shown	1118.00	82
			PP	108.30	
		Water vapor transmission rate, g m ⁻² day ⁻¹	ChNWs suspension = 0.8 wt%	13.10	
			ChNWs suspension = 1.6 wt%	21.67	
			ChNWs suspension = 2.4 wt%	49.71	
			ChNWs suspension = 3.2 wt%	2.43	
		Young's modulus, MPa	PP	2.13	
			PP/20 (ChNWs/TCNFs) bilayers	1290	
			PP/10(ChNWs/TCNFs) bilayers	1215	
			PP/20(ChNWs/TCNFs) bilayers	1371	
6	PP/ChNWs	Tensile strength, MPa	PP/30(ChNWs/TCNFs) bilayers	1356	19
			PP	45.96	
		Elongation at break, %	PP/10(ChNWs/TCNFs) bilayers	36.83	
			PP/20(ChNWs/TCNFs) bilayers	29.01	
			PP/30(ChNWs/TCNFs) bilayers	36.01	
			PP	636	
		Elastic modulus, MPa	PP/10(ChNWs/TCNFs) bilayers	495	
			PP/20(ChNWs/TCNFs) bilayers	367	
			PP/30(ChNWs/TCNFs) bilayers	461	
			PP	1120	
		Ultimate tensile strength, MPa	ChNWs/PP = 1/99	1330	
			ChNWs/PP = 2/98	1370	
			ChNWs/PP = 5/95	1280	
			ChNWs/PP = 10/90	1180	
		Elongation at break, %	PP	34.0	
			ChNWs/PP = 1/99	37.0	
			ChNWs/PP = 2/98	39.0	
			ChNWs/PP = 5/95	37.5	
			ChNWs/PP = 10/90	34.0	
			PP	2.00	
			ChNWs/PP = 1/99	0.65	
			ChNWs/PP = 2/98	0.10	
			ChNWs/PP = 5/95	0.15	
			ChNWs/PP = 10/90	0.05	



Review

Table 13 (Contd.)

No.	Polymers	Affected properties	Composition	Value	Ref.
7	Maleated polypropylene (MAPP)/ChNWs	Elastic modulus, MPa	PP	1120	19
			ChNWs/MAPP = 1/99	1280	
			ChNWs/MAPP = 2/98	1300	
			ChNWs/MAPP = 5/95	1320	
			ChNWs/MAPP = 10/90	1080	
		Ultimate tensile strength, MPa	PP	34.0	
			ChNWs/MAPP = 1/99	36.5	
			ChNWs/MAPP = 2/98	38.0	
			ChNWs/MAPP = 5/95	40.0	
			ChNWs/MAPP = 10/90	34.0	
		Elongation at break, %	PP	2.00	
			ChNWs/MAPP = 1/99	0.60	
			ChNWs/MAPP = 2/98	0.20	
			ChNWs/MAPP = 5/95	0.15	
			ChNWs/MAPP = 10/90	0.40	
8	Biodegradable polyesters PBAT/ChNFs	Tensile strength ^d , MPa	PBAT	12.5	240
			ChNFs/PBAT = 0.5/99.5	22.8	
			ChNFs/PBAT = 1.0/99.0	14.7	
			ChNFs/PBAT = 2.0/98.0	16.3	
			ChNFs/PBAT = 4.0/96/0	9.7	
		Elongation at break ^d , %	ChNFs/PBAT = 8.0/92.0	8.1	
			PBAT	536	
			ChNFs/PBAT = 0.5/99.5	882	
			ChNFs/PBAT = 1.0/99.0	673	
			ChNFs/PBAT = 2.0/98.0	645	
		Glass transition temperature (<i>T_g</i>), °C	ChNFs/PBAT = 4.0/96/0	428	
			ChNFs/PBAT = 8.0/92.0	231	
			PBAT	-22.1	
			ChNFs/PBAT = 0.5/99.5	-21.5	
			ChNFs/PBAT = 1.0/99.0	-20.9	
		Degree of crystallinity (<i>χ_c</i>), %	ChNFs/PBAT = 2.0/98.0	-21.0	
			ChNFs/PBAT = 4.0/96/0	-20.9	
			ChNFs/PBAT = 8.0/92.0	-20.0	
			PBAT	8.6	
			ChNFs/PBAT = 0.5/99.5	11.4	
		The melting enthalpy (<i>ΔH_m</i>), J g ⁻¹	ChNFs/PBAT = 1.0/99.0	10.8	
			ChNFs/PBAT = 2.0/98.0	10.9	
			ChNFs/PBAT = 4.0/96/0	9.7	
			ChNFs/PBAT = 8.0/92.0	8.7	
			PBAT	9.9	
		The enthalpy of crystallization (<i>ΔH_c</i>), J g ⁻¹	ChNFs/PBAT = 0.5/99.5	12.9	
			ChNFs/PBAT = 1.0/99.0	12.2	
			ChNFs/PBAT = 2.0/98.0	12.2	
			ChNFs/PBAT = 4.0/96/0	10.6	
			ChNFs/PBAT = 8.0/92.0	9.2	
			PBAT	14.7	
			ChNFs/PBAT = 0.5/99.5	15.2	
			ChNFs/PBAT = 1.0/99.0	14.2	
			ChNFs/PBAT = 2.0/98.0	16.3	
			ChNFs/PBAT = 4.0/96/0	15.3	
			ChNFs/PBAT = 8.0/92.0	13.3	



Table 13 (Contd.)

No.	Polymers	Affected properties	Composition	Value	Ref.
9	Poly(butylene adipate-co-terephthalate) (PBAT) made <i>in situ</i> from adipic acid (AA) and dimethylterephthalate/sulfated α -chitin nanowhiskers (S-ChNWs)	Young's modulus, MPa	PBAT	170 $\pm$ 4	105
			S-ChNWs/PBAT = 0.1/99.9	136 $\pm$ 0.4	
		Tensile strength, MPa	S-ChNWs/PBAT = 0.3/99.7	146 $\pm$ 3	
			S-ChNWs/PBAT = 0.7/99.3	150 $\pm$ 5	
			S-ChNWs/PBAT = 1.0/99.0	149 $\pm$ 3	
			PBAT	57 $\pm$ 4	
		Elongation at break, %	S-ChNWs/PBAT = 0.1/99.9	62 $\pm$ 2	
			S-ChNWs/PBAT = 0.3/99.7	70 $\pm$ 0.5	
			S-ChNWs/PBAT = 0.7/99.3	64 $\pm$ 2	
			S-ChNWs/PBAT = 1.0/99.0	63 $\pm$ 2	
10	Poly(butylene adipate-co-furanoate) (PBAF) made <i>in situ</i> from adipic acid (AA) and dimethyl 2,5-furandicarboxylate (DMFD)/sulfated α -chitin nanowhiskers (S-ChNWs)	Young's modulus, MPa	PBAT	980 $\pm$ 39	105
			S-ChNWs/PBAT = 0.1/99.9	926 $\pm$ 7	
		Tensile strength, MPa	S-ChNWs/PBAT = 0.3/99.7	919 $\pm$ 11	
			S-ChNWs/PBAT = 0.7/99.3	962 $\pm$ 21	
			S-ChNWs/PBAT = 1.0/99.0	988 $\pm$ 14.7	
			PBAF	60 $\pm$ 0.5	
		Elongation at break, %	S-ChNWs/PBAF = 0.1/99.9	63 $\pm$ 2.0	
			S-ChNWs/PBAF = 0.3/99.7	65 $\pm$ 1.0	
			S-ChNWs/PBAF = 0.7/99.3	55 $\pm$ 0.2	
			S-ChNWs/PBAF = 1.0/99.0	53 $\pm$ 0.9	
11	Methacrylate (MA) resin/ChNWs	Tensile strength, MPa	PBAF	53 $\pm$ 0.6	1
			S-ChNWs/PBAF = 0.1/99.9	83 $\pm$ 3.0	
		Elongation at break, %	S-ChNWs/PBAF = 0.3/99.7	73 $\pm$ 3.0	
			S-ChNWs/PBAF = 0.7/99.3	47 $\pm$ 0.4	
			S-ChNWs/PBAF = 1.0/99.0	47 $\pm$ 3.0	
			PBAF	1007 $\pm$ 11	
		Ultimate tear strength, N cm ⁻¹	S-ChNWs/PBAF = 0.1/99.9	1107 $\pm$ 19	
			S-ChNWs/PBAF = 0.3/99.7	933 $\pm$ 14	
			S-ChNWs/PBAF = 0.7/99.3	1116 $\pm$ 13	
			S-ChNWs/PBAF = 1.0/99.0	1128 $\pm$ 51	
12	Methacrylate (MA) resin/ChNWs	Extension at break, mm	PBAF	730 $\pm$ 20	1
			S-ChNWs/PBAF = 0.1/99.9	1029 $\pm$ 39	
		Tear toughness, J cm ⁻¹	S-ChNWs/PBAF = 0.3/99.7	814 $\pm$ 8	
			S-ChNWs/PBAF = 0.7/99.3	827 $\pm$ 20	
			S-ChNWs/PBAF = 1.0/99.0	761 $\pm$ 45	
			PBAF	94 $\pm$ 9	
		Tensile strength, MPa	S-ChNWs/PBAF = 0.1/99.9	93 $\pm$ 11	
			S-ChNWs/PBAF = 0.3/99.7	91 $\pm$ 4	
			S-ChNWs/PBAF = 0.7/99.3	82 $\pm$ 6	
			S-ChNWs/PBAF = 1.0/99.0	96 $\pm$ 6	
13	Methacrylate (MA) resin/ChNWs	Tensile strength, MPa	PBAF	52 $\pm$ 4	1
			S-ChNWs/PBAF = 0.1/99.9	73 $\pm$ 2	
		Elongation at break, %	S-ChNWs/PBAF = 0.3/99.7	58 $\pm$ 2	
			S-ChNWs/PBAF = 0.7/99.3	52 $\pm$ 6	
			S-ChNWs/PBAF = 1.0/99.0	47 $\pm$ 7	
			PBAF	32 $\pm$ 1.5	
		Ultimate tear strength, N cm ⁻¹	S-ChNWs/PBAF = 0.1/99.9	37	
			S-ChNWs/PBAF = 0.3/99.7	46 $\pm$ 1.2	
			S-ChNWs/PBAF = 0.7/99.3	36 $\pm$ 1.6	
			S-ChNWs/PBAF = 1.0/99.0	36 $\pm$ 1.6	

Methacrylate

11 Methacrylate (MA) resin/ChNWs

Tensile strength, MPa

MA

ChNWs/MA = 0.5/99.5
ChNWs/MA = 1.0/99.0
ChNWs/MA = 1.5/98.5



Table 13 (Contd.)

No.	Polymers	Affected properties	Composition	Value	Ref.			
12	Methacrylate (MA)/α-chitin photocurable nanowhiskers (pChNWs, DDA ~ 6.4%, $M_w \sim 150$ kDa)	Elongation at break, %	MA	6.4 ± 0.5	77			
		Tensile modulus, GPa	ChNWs/MA = 0.5/99.5	7.8				
			ChNWs/MA = 1.0/99.0	8.4 ± 0.5				
			ChNWs/MA = 1.5/98.5	3.6 ± 0.4				
			MA	0.8 ± 0.1				
			ChNWs/ MA = 0.5/99.5	0.9				
			ChNWs/ MA = 1.0/99.0	1.1				
		Storage modulus, MPa (−50 °C)	ChNWs/ MA = 1.5/98.5	1.4 ± 0.1				
			MA	3165.4				
		Storage modulus, MPa (85 °C)	pChNWs/MA = 0.2/99.8	3585.4				
			pChNWs/MA = 0.5/99.5	4179.5				
			pChNWs/MA = 1.0/99.0	4688.9				
MA	59.1							
pChNWs/MA = 0.2/99.8	71.6							
pChNWs/MA = 0.5/99.5	89.3							
13	Polyethylene glycol dimethacrylate (PEGDMA, $M_n = 6000$ Da)/chitosan (CS, $M_w = 100\,000$ Da)/ChNWs	Storage modulus, MPa (200 °C)	pChNWs/MA = 1.0/99.0	125.2	90			
			MA	8.1				
			pChNWs/MA = 0.2/99.8	11.4				
		Tensile strength, MPa	pChNWs/MA = 0.5/99.5	17.7		90		
			pChNWs/MA = 1.0/99.0	15.5				
			MA	36.8 ± 2.6				
		Elongation at break, %	pChNWs/MA = 0.2/99.8	50			90	
			pChNWs/MA = 0.5/99.5	65.6 ± 3.7				
			pChNWs/MA = 1.0/99.5	30				
		Tensile modulus, GPa	MA	6				90
			pChNWs/MA = 0.2/99.8	8.9				
			pChNWs/MA = 0.5/99.5	6.7				
Adhesion, kPa	pChNWs/MA = 1.0/99.0	~2.0	90					
	MA	0.85 ±						
	pChNWs/MA = 0.2/99.8	0.13						
	pChNWs/MA = 0.5/99.5	1.1 ± 0.13						
	pChNWs/MA = 1.0/99.5	1.45 ±						
	pChNWs/MA = 1.0/99.5	0.13						
14	Polyethylene glycol dimethacrylate (PEGDMA, $M_n = 6000$ Da)/chitosan (CS, $M_w = 100\,000$ Da)/ChNWs	Adhesion, kPa		MA	1.7 ± 0.13	90		
				PEGDMA	2.1			
				PEGDMA/CS = 88.24/11.76	3.1			
		Elongation at break, %		PEGDMA/CS/ChNWs = 68.18/9.09/22.73	4.2		90	
				PEGDMA	100			
				PEGDMA/CS = 88.24/11.76	125			
		Tensile strength, kPa	PEGDMA/CS/ChNWs = 68.18/9.09/22.73	145	90			
			PEGDMA	5.0				
			PEGDMA/CS	9.0				
		Swelling, %	PEGDMA/CS/ChNWs = 68.18/9.09/22.73	11.2				90
			PEGDMA	277				
			PEGDMA/CS	300				
Oxygen permeability, cm ³ μm m ^{−2} day ^{−1} kPa ^{−1}	PEGDMA/CS/ChNWs = 68.18/9.09/22.73	289	90					
	PEGDMA	300						
	PEGDMA/CS	289						
15	Polyesters	Oxygen permeability, cm ³ μm m ^{−2} day ^{−1} kPa ^{−1}		ChNWs/CNCs = 50/50 coated in sequence on PET film		129	129	
				ChNWs/CNCs = 50/50 coated in sequence on PET film		129		
				ChNWs/CNCs = 50/50 coated in sequence on PET film		129		
		Oxygen permeability, cm ³ μm m ^{−2} day ^{−1} kPa ^{−1}		ChNWs/CNCs = 50/50 coated in sequence on PET film	129	129		
				ChNWs/CNCs = 50/50 coated in sequence on PET film	129			
				ChNWs/CNCs = 50/50 coated in sequence on PET film	129			
		Oxygen permeability, cm ³ μm m ^{−2} day ^{−1} kPa ^{−1}		ChNWs/CNCs = 50/50 coated in sequence on PET film	129			129
				ChNWs/CNCs = 50/50 coated in sequence on PET film	129			
				ChNWs/CNCs = 50/50 coated in sequence on PET film	129			
		Oxygen permeability, cm ³ μm m ^{−2} day ^{−1} kPa ^{−1}	ChNWs/CNCs = 50/50 coated in sequence on PET film	129	129			
			ChNWs/CNCs = 50/50 coated in sequence on PET film	129				
			ChNWs/CNCs = 50/50 coated in sequence on PET film	129				
Oxygen permeability, cm ³ μm m ^{−2} day ^{−1} kPa ^{−1}	ChNWs/CNCs = 50/50 coated in sequence on PET film	129	129					
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
Oxygen permeability, cm ³ μm m ^{−2} day ^{−1} kPa ^{−1}	ChNWs/CNCs = 50/50 coated in sequence on PET film	129		129				
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
Oxygen permeability, cm ³ μm m ^{−2} day ^{−1} kPa ^{−1}	ChNWs/CNCs = 50/50 coated in sequence on PET film	129				129		
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
Oxygen permeability, cm ³ μm m ^{−2} day ^{−1} kPa ^{−1}	ChNWs/CNCs = 50/50 coated in sequence on PET film	129			129			
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
Oxygen permeability, cm ³ μm m ^{−2} day ^{−1} kPa ^{−1}	ChNWs/CNCs = 50/50 coated in sequence on PET film	129	129					
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
Oxygen permeability, cm ³ μm m ^{−2} day ^{−1} kPa ^{−1}	ChNWs/CNCs = 50/50 coated in sequence on PET film	129		129				
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
Oxygen permeability, cm ³ μm m ^{−2} day ^{−1} kPa ^{−1}	ChNWs/CNCs = 50/50 coated in sequence on PET film	129				129		
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
Oxygen permeability, cm ³ μm m ^{−2} day ^{−1} kPa ^{−1}	ChNWs/CNCs = 50/50 coated in sequence on PET film	129			129			
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
Oxygen permeability, cm ³ μm m ^{−2} day ^{−1} kPa ^{−1}	ChNWs/CNCs = 50/50 coated in sequence on PET film	129	129					
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
Oxygen permeability, cm ³ μm m ^{−2} day ^{−1} kPa ^{−1}	ChNWs/CNCs = 50/50 coated in sequence on PET film	129		129				
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
Oxygen permeability, cm ³ μm m ^{−2} day ^{−1} kPa ^{−1}	ChNWs/CNCs = 50/50 coated in sequence on PET film	129				129		
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
Oxygen permeability, cm ³ μm m ^{−2} day ^{−1} kPa ^{−1}	ChNWs/CNCs = 50/50 coated in sequence on PET film	129			129			
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
Oxygen permeability, cm ³ μm m ^{−2} day ^{−1} kPa ^{−1}	ChNWs/CNCs = 50/50 coated in sequence on PET film	129	129					
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
Oxygen permeability, cm ³ μm m ^{−2} day ^{−1} kPa ^{−1}	ChNWs/CNCs = 50/50 coated in sequence on PET film	129		129				
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
Oxygen permeability, cm ³ μm m ^{−2} day ^{−1} kPa ^{−1}	ChNWs/CNCs = 50/50 coated in sequence on PET film	129				129		
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
Oxygen permeability, cm ³ μm m ^{−2} day ^{−1} kPa ^{−1}	ChNWs/CNCs = 50/50 coated in sequence on PET film	129			129			
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
Oxygen permeability, cm ³ μm m ^{−2} day ^{−1} kPa ^{−1}	ChNWs/CNCs = 50/50 coated in sequence on PET film	129	129					
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
Oxygen permeability, cm ³ μm m ^{−2} day ^{−1} kPa ^{−1}	ChNWs/CNCs = 50/50 coated in sequence on PET film	129		129				
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
Oxygen permeability, cm ³ μm m ^{−2} day ^{−1} kPa ^{−1}	ChNWs/CNCs = 50/50 coated in sequence on PET film	129				129		
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
Oxygen permeability, cm ³ μm m ^{−2} day ^{−1} kPa ^{−1}	ChNWs/CNCs = 50/50 coated in sequence on PET film	129			129			
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
Oxygen permeability, cm ³ μm m ^{−2} day ^{−1} kPa ^{−1}	ChNWs/CNCs = 50/50 coated in sequence on PET film	129	129					
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
Oxygen permeability, cm ³ μm m ^{−2} day ^{−1} kPa ^{−1}	ChNWs/CNCs = 50/50 coated in sequence on PET film	129		129				
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
Oxygen permeability, cm ³ μm m ^{−2} day ^{−1} kPa ^{−1}	ChNWs/CNCs = 50/50 coated in sequence on PET film	129				129		
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
Oxygen permeability, cm ³ μm m ^{−2} day ^{−1} kPa ^{−1}	ChNWs/CNCs = 50/50 coated in sequence on PET film	129			129			
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
Oxygen permeability, cm ³ μm m ^{−2} day ^{−1} kPa ^{−1}	ChNWs/CNCs = 50/50 coated in sequence on PET film	129	129					
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
Oxygen permeability, cm ³ μm m ^{−2} day ^{−1} kPa ^{−1}	ChNWs/CNCs = 50/50 coated in sequence on PET film	129		129				
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
Oxygen permeability, cm ³ μm m ^{−2} day ^{−1} kPa ^{−1}	ChNWs/CNCs = 50/50 coated in sequence on PET film	129				129		
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
Oxygen permeability, cm ³ μm m ^{−2} day ^{−1} kPa ^{−1}	ChNWs/CNCs = 50/50 coated in sequence on PET film	129			129			
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
Oxygen permeability, cm ³ μm m ^{−2} day ^{−1} kPa ^{−1}	ChNWs/CNCs = 50/50 coated in sequence on PET film	129	129					
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
Oxygen permeability, cm ³ μm m ^{−2} day ^{−1} kPa ^{−1}	ChNWs/CNCs = 50/50 coated in sequence on PET film	129		129				
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
Oxygen permeability, cm ³ μm m ^{−2} day ^{−1} kPa ^{−1}	ChNWs/CNCs = 50/50 coated in sequence on PET film	129				129		
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
Oxygen permeability, cm ³ μm m ^{−2} day ^{−1} kPa ^{−1}	ChNWs/CNCs = 50/50 coated in sequence on PET film	129			129			
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
Oxygen permeability, cm ³ μm m ^{−2} day ^{−1} kPa ^{−1}	ChNWs/CNCs = 50/50 coated in sequence on PET film	129	129					
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
Oxygen permeability, cm ³ μm m ^{−2} day ^{−1} kPa ^{−1}	ChNWs/CNCs = 50/50 coated in sequence on PET film	129		129				
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
Oxygen permeability, cm ³ μm m ^{−2} day ^{−1} kPa ^{−1}	ChNWs/CNCs = 50/50 coated in sequence on PET film	129				129		
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
Oxygen permeability, cm ³ μm m ^{−2} day ^{−1} kPa ^{−1}	ChNWs/CNCs = 50/50 coated in sequence on PET film	129			129			
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
Oxygen permeability, cm ³ μm m ^{−2} day ^{−1} kPa ^{−1}	ChNWs/CNCs = 50/50 coated in sequence on PET film	129	129					
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
Oxygen permeability, cm ³ μm m ^{−2} day ^{−1} kPa ^{−1}	ChNWs/CNCs = 50/50 coated in sequence on PET film	129		129				
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
Oxygen permeability, cm ³ μm m ^{−2} day ^{−1} kPa ^{−1}	ChNWs/CNCs = 50/50 coated in sequence on PET film	129				129		
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
Oxygen permeability, cm ³ μm m ^{−2} day ^{−1} kPa ^{−1}	ChNWs/CNCs = 50/50 coated in sequence on PET film	129			129			
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
Oxygen permeability, cm ³ μm m ^{−2} day ^{−1} kPa ^{−1}	ChNWs/CNCs = 50/50 coated in sequence on PET film	129	129					
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
Oxygen permeability, cm ³ μm m ^{−2} day ^{−1} kPa ^{−1}	ChNWs/CNCs = 50/50 coated in sequence on PET film	129		129				
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
Oxygen permeability, cm ³ μm m ^{−2} day ^{−1} kPa ^{−1}	ChNWs/CNCs = 50/50 coated in sequence on PET film	129				129		
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
Oxygen permeability, cm ³ μm m ^{−2} day ^{−1} kPa ^{−1}	ChNWs/CNCs = 50/50 coated in sequence on PET film	129			129			
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
Oxygen permeability, cm ³ μm m ^{−2} day ^{−1} kPa ^{−1}	ChNWs/CNCs = 50/50 coated in sequence on PET film	129	129					
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
Oxygen permeability, cm ³ μm m ^{−2} day ^{−1} kPa ^{−1}	ChNWs/CNCs = 50/50 coated in sequence on PET film	129		129				
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
Oxygen permeability, cm ³ μm m ^{−2} day ^{−1} kPa ^{−1}	ChNWs/CNCs = 50/50 coated in sequence on PET film	129				129		
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
Oxygen permeability, cm ³ μm m ^{−2} day ^{−1} kPa ^{−1}	ChNWs/CNCs = 50/50 coated in sequence on PET film	129			129			
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
Oxygen permeability, cm ³ μm m ^{−2} day ^{−1} kPa ^{−1}	ChNWs/CNCs = 50/50 coated in sequence on PET film	129	129					
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
Oxygen permeability, cm ³ μm m ^{−2} day ^{−1} kPa ^{−1}	ChNWs/CNCs = 50/50 coated in sequence on PET film	129		129				
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
Oxygen permeability, cm ³ μm m ^{−2} day ^{−1} kPa ^{−1}	ChNWs/CNCs = 50/50 coated in sequence on PET film	129				129		
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
Oxygen permeability, cm ³ μm m ^{−2} day ^{−1} kPa ^{−1}	ChNWs/CNCs = 50/50 coated in sequence on PET film	129			129			
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
Oxygen permeability, cm ³ μm m ^{−2} day ^{−1} kPa ^{−1}	ChNWs/CNCs = 50/50 coated in sequence on PET film	129	129					
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
Oxygen permeability, cm ³ μm m ^{−2} day ^{−1} kPa ^{−1}	ChNWs/CNCs = 50/50 coated in sequence on PET film	129		129				
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
Oxygen permeability, cm ³ μm m ^{−2} day ^{−1} kPa ^{−1}	ChNWs/CNCs = 50/50 coated in sequence on PET film	129				129		
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
Oxygen permeability, cm ³ μm m ^{−2} day ^{−1} kPa ^{−1}	ChNWs/CNCs = 50/50 coated in sequence on PET film	129			129			
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
	ChNWs/CNCs = 50/50 coated in sequence on PET film	129						
Oxygen permeability, cm ³ μm m ^{−2} day ^{−1} kPa ^{−1}	ChNWs/CNCs = 50/50 coated in sequence on PET film	129	129					



Table 13 (Contd.)

No.	Polymers	Affected properties	Composition	Value	Ref.
15	Polyethylene terephthalate (PET)/ChNWs/ cellulose nanocrystals (CNCs)	Water vapor transmission rate, $\text{g } \mu\text{m}^{-2} \text{ day}^{-1}$	PET	17.3 ± 0.0	
			PET-ChNWs	12.6 ± 0.9	
			PET-CNCs	5.9 ± 0.7	
			PET-ChNWs-CNCs	5.2 ± 0.4	
			PET-blend	10.2 ± 1.2	
			PET	148	
			PET-ChNWs	141	
			PET-CNCs	148	
			PET-ChNWs-CNCs	155	
			PET-blend	140	
			PET	87.1	
			PET-ChNWs	87.1	
			PET-CNCs	87.7	
			PET-ChNWs-CNCs	86.9	
			PET-blend	86.9	
16	Polyethylene terephthalate (PET)/α-short chitin nanowhiskers (SCHNWs 114 nm) or α-long chitin nanowhiskers (LChNWs, 230 nm)	Transmittance, %	PET	1.8	
			PET-ChNWs	1.3	
			PET-CNCs	2.4	
			PET-ChNWs-CNCs	1.2	
			PET-blend	3.3	
			PET	15.9 ± 0.4	130
			PET/SCHNWs	11.1 ± 0.3	
			PET/LChNWs	16.5 ± 0.4	
			PET	85	
			PET/SCHNWs	85	
			PET/LChNWs	87.5	
			PET	90	
			PET/SCHNWs	78	
			PET/LChNWs	80	
			PET	42	
16	Polyethylene terephthalate (PET)/α-ChNWs/ chitosan (CS); α-short chitin nanowhiskers (SCHNWs 114 nm) or α-long chitin nanowhiskers (LChNWs, 230 nm)/chitosan (CS)/ polyethylene terephthalate (PET)	Failure strain, %	PET/SCHNWs	40	
			PET/LChNWs	46	
			PET	15.9 ± 0.4	130
			CS	11.0 ± 0.3	
			SCHNWs/CS = 66.67/33.33	7.0 ± 0.3	
			SCHNWs/CS = 50/50	5.1 ± 0.1	
			SCHNWs/CS = 33.33/66.67	6.9 ± 0.2	
			LChNWs/CS = 66.67/33.33	13.1 ± 0.3	
			LChNWs/CS = 50/50	13.2 ± 0.3	
			LChNWs/CS = 33.33/66.66	8.2 ± 0.3	
			PET	85	
			CS	85	
			SCHNWs/CS = 66.67/33.33	85	
			LChNWs/CS = 66.67/33.33	85	
			SCHNWs/CS = 50/50	87.5	
16	Polyethylene terephthalate (PET)/α-ChNWs/ chitosan (CS); α-short chitin nanowhiskers (SCHNWs 114 nm) or α-long chitin nanowhiskers (LChNWs, 230 nm)/chitosan (CS)/ polyethylene terephthalate (PET)	Transmittance, %	LChNWs/CS = 50/50	85	
			SCHNWs/CS = 33.33/66.67	87.5	
			LChNWs/CS = 33.33/66.67	85	
			PET	90	
			CS	70	
16	Polyethylene terephthalate (PET)/α-ChNWs/ chitosan (CS); α-short chitin nanowhiskers (SCHNWs 114 nm) or α-long chitin nanowhiskers (LChNWs, 230 nm)/chitosan (CS)/ polyethylene terephthalate (PET)	Tensile strength, MPa	SCHNWs/CS = 66.67/33.33	78	
			LChNWs/CS = 66.67/33.33	76	



Table 13 (Contd.)

No.	Polymers	Affected properties	Composition	Value	Ref.
17	Polyethylene terephthalate (PET)/ α -short chitin nanowhiskers (sChNWs 114 nm) or α -long chitin nanowhiskers (lChNWs, 230 nm)/chitosan (CS)/cellulose nanocrystals (CNCs)	Failure strain, %	SChNWs/CS = 50/50	77	130
			lChNWs/CS = 50/50	78	
			SChNWs/CS = 33.3366.67	80	
			lChNWs/CS = 33.3366.67	77	
			PET	42	
			CS	42	
			SChNWs/CS = 66.67/33.33	42	
			lChNWs/CS = 66.67/33.33	41	
			SChNWs/CS = 50/50	38	
			lChNWs/CS = 50/50	46	
			SChNWs/CS = 33.3366.67	46	
			lChNWs/CS = 33.3366.67	42	
			PET	148	
			SChNWs/CS = 50/50	200	
			lChNWs/CS = 50/50	200	
			PET	175	
			SChNWs/CS = 50/50	180	
		Water vapor transmission rate, g $\mu\text{m m}^{-2} \text{day}^{-1}$ (under RH 45%, without thermal treatment)	lChNWs/CS = 50/50	180	130
			ChNWs spread over PET substrate ^e	15.9 $\pm$ 0.4	
			PET	3.6 $\pm$ 0.1	
			(SChNW/CS)-CNC	4.0 $\pm$ 0.1	
			(lChNW/CS)-CNC	8.0 $\pm$ 0.2	
			CNCs	85	
			PET	85	
			SChNWs/CS-CNCs	85	
			lChNWs/CS-CNC	85.5	
			CNCs	90	
			PET	77	
			SChNWs/CS-CNCs	74	
			lChNWs/CS-CNCs	76	
			CNCs	42	
			PET	40	
			SChNWs/CS-CNCs	40	
			lChNWs/CS-CNCs	38	
		Water vapor transmission rate, g $\mu\text{m m}^{-2} \text{day}^{-1}$ (under RH 45%, without thermal treatment)	CNCs	148	89
			PET	150	
			SChNWs/CS-CNCs	149	
			lChNWs/CS-CNCs	175	
			CNCs	175	
			PET	175	
			SChNWs/CS-CNCs	175	
			lChNWs/CS-CNCs	155	
			CNCs	175	
			ChNWs and CNFs coated in sequence on PET film, ratio not shown	38.28	
			PET	0.97	
			(ChNWs/CNFs) ₁₀	0.48	
			(ChNWs/CNFs) ₂₀	0.57	
			(ChNWs/CNFs) ₃₀	0.59	
			(ChNWs/CNFs) ₄₀	0.51	
			(ChNWs/CNFs) ₅₀		
18	Polyethylene terephthalate (PET)/ α -ChNWs/cellulose nanofibers (CNFs) _f	Oxygen transmission rate, mL $\text{m}^{-2} \text{day}^{-1}$			

Table 13 (Contd.)

No.	Polymers	Affected properties	Composition	Value	Ref.
		Transmittance, %	PET	92	
			(ChNWs/CNFs) ₁₀	89	
			(ChNWs/CNFs) ₂₀	89	
			(ChNWs/CNFs) ₃₀	88.5	
			(ChNWs/CNFs) ₄₀	88	
			(ChNWs/CNFs) ₅₀	87.5	
		Haze, %	PET	2.9	
			(ChNWs/CNFs) ₁₀	2.5	
			(ChNWs/CNFs) ₂₀	2.0	
			(ChNWs/CNFs) ₃₀	1.8	
			(ChNWs/CNFs) ₄₀	1.7	
			(ChNWs/CNFs) ₅₀	1.6	

^a Two methods were utilized to produce nanocomposite films: water evaporation and hot-pressing. The mechanical tests were conducted on both the evaporated and hot-pressed materials to evaluate their properties. ^b The PP substrates were dipped alternatively in a suspension of ChNWs (forming the first coating layer), then rinsed with deionized water, followed by immersion in a TCNF suspension and rinsed again with deionized water. This process constituted one complete dip coating cycle, resulting in one bilayer of ChNWs/TCNFs. The cycle was repeated until the desired number of (ChNWs/TCNF) bilayers was achieved. The concentrations of the suspensions for TCNF and ChNWs were adjusted in order to evaluate the barrier performance of the layers. ^c The oxygen transmission rates were measured for films coated with 0.4 wt% TCNF suspension and ChNWs suspensions under different concentrations. ^d Data were estimated from the graphs. ^e PET substrates were coated with layers of ChNW/CS suspension and CNCs suspension. A single layer was created using either SCHNW/CS or LCHNW/CS coatings on PET while a bilayer was formed with (SCHNW/CS)-CNC or (LCHNW/CS)-CNC coatings on PET, where the mass ratio of ChNWs to CS for bilayers was 1 : 1. ^f Gas barrier coatings were generated using multilayers of (ChNWs/CNFs)_n (in which *n* indicates the number of bilayers, that tend to vary from 10 to 50 bilayers). For example, the sequential assembly of ChNWs and CNFs afforded a bilayer of (ChNWs/CNFs)₁.

excessive ChNW content may lead to structural modifications that reduce water permeability. These results indicate that while lower ChNW concentrations enhance water flux, an optimal balance is required to prevent a decline in efficiency due to excessive filler incorporation.

The bovine serum albumin (BSA) rejection, which refers to the membrane's ability to prevent BSA molecules from passing through, is a critical measure of separation efficiency in filtration applications, particularly in biomedical processes.^{76,237} A higher BSA rejection indicates improved selectivity, reducing protein contamination. In this study, the addition of 4% ChNW resulted in the highest BSA rejection of 90%, compared to 58% in membranes without ChNWs, demonstrating a significant enhancement in filtration performance (Table 13, entry 3). However, the flux recovery ratio (FRR), which indicates the membrane's ability to regain permeability after cleaning, showed an unclear trend, with the highest values observed at 6% and 8% ChNW. This suggests that while moderate ChNW incorporation enhances protein rejection efficiency, its impact on membrane fouling resistance and cleaning efficiency varies with concentration, highlighting the need for an optimal balance between permeability, selectivity, and antifouling properties.

The study conducted by Andre *et al.*⁸⁷ reported the development of a disposable ethanol sensor based on nanochitin composite films (Table 13, entry 4), designed as a nature-friendly and cost-effective electronic device without the need for metallic electrodes. Unlike traditional reinforcement fillers, ChNWs served as a primary electrode component. The sensor was fabricated using a casting method, incorporating ZnO nanoparticles and polyaniline (PANI) into chitin-based films. Three different suspensions were prepared with varying compositions of ZnO and PANI, followed by ultrasound treatment and homogenization. The films were cast into acrylic molds, dried, and conditioned before characterization and ethanol vapor detection tests. The resulting films were classified as ChNWs–ZnO, ChNWs–PANI, and ChNWs–ZnO/PANI, along with a pure ChNW control film. While ChNWs were not used as a filler in this study, we considered it relevant to include them in this review due to their significant role as a primary electrode component.

4.6.2. Polyolefins. Polyolefins are a distinct class of thermoplastic polymers derived from olefin monomers, primarily ethylene and propylene, setting them apart from other thermoplastics due to their low density, chemical resistance, and cost-effectiveness.^{238,239} Unlike engineering thermoplastics such as polycarbonate (PC) or poly(ε-caprolactone) (PCL), polyolefins exhibit a simpler molecular structure, making them highly processable and widely recyclable. The most common types include polyethylene (PE), with variations like LDPE, HDPE, and LLDPE, as well as polypropylene (PP), known for its high rigidity and heat resistance. These materials are extensively used in packaging, automotive components, medical devices, textiles, and construction due to their lightweight nature, water resistance, and excellent electrical insulation properties.



The incorporation of ChNWs was first attempted by coating. Nguyen *et al.*⁸² fabricated polypropylene (PP) films through a sequential dip-coating process, alternating between chitin nanowhiskers (ChNWs) and TEMPO-oxidized cellulose nanofibers (TCNFs) (Table 13, entry 5). The PP substrates were first immersed in a ChNW suspension to form the initial coating layer, rinsed with deionized water, then dipped into a TCNF suspension, followed by another rinse. This sequence constituted a complete dip-coating cycle, resulting in a single bilayer of ChNWs/TCNFs, with the process repeated until 10 to 30 bilayers were achieved. The concentrations of ChNWs and TCNF suspensions were systematically adjusted to evaluate the barrier performance of the multilayer coatings.

The incorporation of chitin nanowhiskers (ChNWs) and TEMPO-oxidized cellulose nanofibers (TCNFs) as sequential coatings on polypropylene (PP) films significantly influenced the oxygen transmission rate (OTR), water vapor transmission rate (WVTR), and mechanical properties. The OTR of uncoated PP was 1118.00 cc m⁻² day⁻¹, but after coating with ChNWs at different suspension concentrations, a drastic reduction was observed, reaching 13.10 cc m⁻² day⁻¹ at 1.6 wt% ChNWs. However, a slight increase was seen at higher concentrations, with values of 21.67 cc m⁻² day⁻¹ at 2.4 wt% and 49.71 cc m⁻² day⁻¹ at 3.2 wt%, indicating that an optimal filler concentration enhances barrier properties before diminishing effects arise. Similarly, the WVTR showed a minor reduction, from 2.43 g m⁻² day⁻¹ for uncoated PP to 2.13 g m⁻² day⁻¹ for PP with 20 bilayers of ChNWs/TCNFs, reflecting improved moisture resistance.

Regarding mechanical properties, the Young's modulus increased with the addition of bilayers, rising from 1290 MPa in pure PP to 1371 MPa in PP with 20 bilayers, with a slight decrease at 30 bilayers (1356 MPa), suggesting increased stiffness due to nanocoating. However, tensile strength declined, from 45.96 MPa in pure PP to 29.01 MPa at 20 bilayers, before partially recovering at 30 bilayers (36.01 MPa). Likewise, elongation at break followed a decreasing trend, from 636% in pure PP to 367% in the 20-bilayer coated film, but slightly increased to 461% at 30 bilayers. These results indicate that while multilayer coatings enhance stiffness and barrier performance, they also reduce flexibility and tensile strength, likely due to stress retention at the interface and increased rigidity of the coatings.

Another study evaluated the mechanical properties of polypropylene (PP) and maleated polypropylene (MAPP) composites reinforced with chitin nanowhiskers (ChNWs), with a focus on elastic modulus, ultimate tensile strength, and elongation at break across different ChNW loadings (Table 13, entries 6 and 7).¹⁹ For PP/ChNW composites (Table 13, entry 6), the elastic modulus increased with ChNW content up to 5 wt% (1370 MPa) but decreased at 10 wt% (1180 MPa), suggesting that while ChNWs enhance stiffness at lower concentrations, excessive filler content may lead to agglomeration, reducing reinforcement efficiency. The ultimate tensile strength followed a similar trend, increasing from 34 MPa in pure PP to 39 MPa at 5 wt% ChNWs, before slightly decreasing

at higher concentrations. However, elongation at break significantly declined, from 2.00% in pure PP to just 0.05% at 10 wt% ChNWs, indicating a drastic loss in ductility due to the rigid nanofiller.

In MAPP/ChNW composites (Table 13, entry 7), a more gradual increase in elastic modulus was observed, peaking at 1320 MPa at 10 wt% ChNWs, which suggests better interfacial adhesion between MAPP and ChNWs compared to unmodified PP. Similarly, ultimate tensile strength improved consistently with ChNW content, reaching 40 MPa at 10 wt% ChNWs, showing a stronger reinforcing effect. However, elongation at break followed a decreasing trend, from 2.00% in pure MAPP to 0.15% at 10 wt% ChNWs, with slightly better retention than in the unmodified PP composites. Overall, the results indicate that ChNWs improve stiffness and strength in both PP and MAPP, with MAPP composites showing better mechanical performance due to enhanced interfacial adhesion. However, higher ChNW concentrations reduce ductility, which could limit applications where flexibility is required.

4.6.3. Biodegradable polyesters. Biodegradable polyesters are a group of synthetic polymers that break down naturally into environmentally friendly products through biological processes, typically involving microorganisms such as bacteria, fungi, or algae.^{240,241} These polyesters are designed to degrade over time, reducing environmental pollution compared to traditional non-biodegradable plastics. Among the biodegradable polymers developed to date, poly(butylene adipate-co-terephthalate) (PBAT) and poly(butylene adipate-co-furanoate) (PBAF) have gained research interest for their strong film performance. PBAT, composed of adipic acid and terephthalic acid, has a random copolymer structure, offering high flexibility and toughness but less mechanically strong than conventional non-biodegradable plastics. In contrast, PBAF replaces the terephthalic acid component of PBAT with furan-2,5-dicarboxylic acid (FDCA) in the polymer backbone, making it more biodegradable, more elastic and more mechanically competitive than PBAT. However, PBAF's tensile strength and tear toughness still need improvement to match commercial bio-based and biodegradable plastic films.²⁴² Compositing with reinforcing agents or blending with other polymers are effective strategies for enhancing the mechanical and thermal properties of these materials.

The incorporation of chitin nanofibers (ChNFs) into biodegradable PBAT was successfully achieved through melt bending and compression molding methods. SEM revealed that the nanochitin was uniformly dispersed throughout the PBAT matrix at low contents (<2 wt%). The physical, thermal and mechanical properties of the composites were found to be highly influenced by both the concentration of ChNFs and their dispersion within the matrix (Table 13, entry 8). A significant 82.5% increase in the tensile strength was observed when 0.5 wt% ChNFs was melt blended with PBAT, but this increase sharply declined at higher ChNF concentrations. This result suggests that the addition of a small amount of ChNFs improved ChNF dispersion within the PBAT matrix, promoting effective heterogeneous nucleation of PBAT crystallites and



providing excellent interfacial adhesion between ChNFs and PBAT chains. These factors likely contributed to enhanced rigidity and tensile strength of the composite. A closely similar trend was observed in the elongation at break, with 64.5% enhancement at the 0.5 wt% ChNF loading. This indicates that the small amount of ChNFs not only improved the tensile strength but also enhanced the composite's flexibility. However, as with the tensile strength, the elongation at break decreased at higher ChNF concentrations, suggesting that excessive ChNFs may hinder the polymer's ability to stretch, likely due to agglomeration or poor dispersion.²⁴⁰

Dynamic mechanical analysis results revealed an increase in the glass transition temperature (T_g) as the nanochitin content in the composites increased. This suggests that the movement of PBAT polymer chains was more restricted due to the interfacial bonding between ChNFs and PBAT matrix. The differential scanning calorimetry results indicated that the addition of ChNFs increased the enthalpy of melting, the enthalpy of crystallization, and the degree of crystallinity, however, the optimal enhancements were still observed at 0.5 wt%, further supporting the idea that a small amount of ChNFs indeed created a heterogeneous nucleation effect, promoting the formation of crystallites in the PBAT matrix during cooling from the melt.²⁴⁰

Another study first investigated the use of sulfated ChNWs (S-ChNWs) to enhance the mechanical properties of PBAT and PBAF through an *in situ* polycondensation method. S-ChNWs were produced by sulfuric acid hydrolysis of bulk α -ChNWs, which removed the amorphous regions and simultaneously converted some primary hydroxy (C_6-OH) and acetamide groups on the surface into sulfate-half esters (OSO_3^-) and protonated amino (NH_3^+) groups. This surface sulfation allowed for better dispersion of S-ChNWs in the monomer solution, maximizing their reinforcing effect in the final polymer matrix (Table 13, entries 9 and 10). For PBAT's mechanical properties, the tensile strength increased with S-ChNW addition, rising from 57 MPa in neat PBAT to 70 MPa at 0.3 wt% loading, though it slightly decrease at 0.7 and 1.0 wt% (Table 13, entry 9). This result aligns with the previous study by Meng *et al.*,²⁴⁰ which found significant improvements in PBAT tensile strength with low nanochitin addition. However, the Young's modulus decreased from 170 MPa in neat PBAT to 146 MPa at 0.3 wt% S-ChNW loading, before partially recovering to 150 MPa and 149 MPa at 0.7 wt% and 1 wt% loading, respectively. Elongation at break followed a similar trend, decreasing from 980% in neat PBAT to 919% at 0.3 wt% S-ChNW loading, but increasing to 988% at 1.0 wt% loading. This result indicate that S-ChNWs were efficiently dispersed in the PBAT matrix during *in situ* polymerization, facilitating beneficial interactions between the NH_3^+ groups of S-ChNWs and the polymer's carbonyl groups, which led to improved mechanical attributes.¹⁰⁵

The mechanically reinforcing effects of the S-ChNWs on PBAF are more pronounced than on PBAT. Adding just 0.1 wt% S-ChNWs increased the tensile strength by 1.6 times (53 MPa in neat PBAF vs. 83 MPa in the S-ChNWs/PBAF), and

enhanced tear toughness by 1.4 times (52 J cm^{-1} in neat PBAF vs. 73 J cm^{-1} in the S-ChNWs/PBAF; see Table 13, entry 10). The *in situ* PBAF composite with 0.1 wt% S-ChNWs exhibited 1.2 times higher tensile strength and slightly lower elongation at break compared to the *in situ* PBAT composite with 0.3 wt% S-ChNWs. The superior performance of the PBAF composite with 0.1 wt% S-ChNWs was attributed to the higher polarity of the furan ring compared to the nonpolar benzene ring, promoting better dispersion of the hydrophilic nanofiller.^{105,243} Additionally, the angular structure of the furan ring in PBAF allowed S-ChNWs to fit between polymer chains, and their high aspect ratio created large filler/matrix interfaces.^{105,244}

The optimal reinforcement for all properties, except elongation at break, was observed at 0.1 wt% for PBAF and 0.3 wt% for PBAT. Beyond these points, the properties of both composites declined, indicating unfavorable reinforcement effects. This decline is attributed to particle aggregation due to excessive hydrogen bonding from the excess nanoparticles in the matrix. Additionally, the increasing elongation at break is likely due to the less mobile chitin nanoparticles, which may act as a plasticizer, enhancing elongation at break.¹⁰⁵

4.6.4. Methacrylate and polyethylene glycol dimethacrylate. Methacrylate (MA) and its derivative, polyethylene glycol dimethacrylate (PGDMA) are commonly used in hydrogels, tissue engineering, and 3D printing applications, due to their excellent transparency, tunable mechanical properties, and ease of processing.^{1,77,90,245} However, these methacrylate-based polymers are brittle at low strains, thermally unstable at elevated temperatures, and exhibit weak interface toughness and high pH dependence, limiting their use in certain applications.^{1,90,246} To overcome these limitations in 3D printing application, Maalihan and coworkers employed a slurry compounding method to develop MA resin reinforced with ChNWs for stereolithography (SLA) 3D printing. Transmission electron microscope (TEM) results showed that ChNWs were well dispersed within the bulk of MA at 1.0 wt% loading, implying good interfacial adhesion, likely due to hydrogen bonding interactions.

Tensile tests revealed that neat MA polymer had a tensile strength of $32 \pm 1.5 \text{ MPa}$, which increased by 44% with the addition of 1.0 wt% ChNWs ($46 \pm 1.2 \text{ MPa}$) as shown in Table 13, entry 11. The maximum strain at break also improved with ChNW inclusion at the same loading ($8.4 \pm 0.5\%$), marking 31% increase compared to neat MA ($6.4 \pm 0.5\%$). Consequently, the combined increase in the tensile strength and strain at break enhanced the tensile toughness. These improvements were attributed to the enhanced interfacial adhesion between ChNWs and MA, as confirmed by their TEM results¹ and previous FTIR analysis.^{3,41} However, further increasing ChNWs loading to 1.5 wt% led to a reduction in both tensile strength and strain at break by 22% and 57%, respectively compared to the 1.0 wt% loading. This decline was ascribed to the aggregation of excess ChNWs in the MA matrix.

The study also observed an improvement in the tensile modulus with increasing ChNW loading. Incorporating



ChNWs at 1.5 wt% loading increased the tensile modulus by 75% (1.4 ± 0.1 GPa) compared to neat MA (0.8 ± 0.1 GPa), demonstrating the direct impact of ChNW intrinsic stiffness on the composite modulus. Furthermore, the overall property improvements were primarily influenced by matrix–filler interactions, driven by hydrogen-bonded functional groups between MA and ChNWs.^{1,41,247} Upon application in SLA 3D printing, the resulting 3D-printed nanocomposites, even at higher ChNW loadings, demonstrated high resolution and accuracy without requiring adjustments to the settings of a standard SLA 3D printer, confirming the enhanced applicability of MA for 3D printing.

A subsequent study by this group⁷⁷ evaluated the use of surface modified ChNWs to reinforce SLA MA-based resin (Table 13, entry 12). In this study, ChNWs were functionalized with reactive acrylate groups to produce surface-modified, photocurable ChNWs (pChNWs). The DMA temperature studies showed that incorporation pChNWs into the MA resin improved the polymer chain mobility and energy dissipation. For instance, at -50 °C, the inclusion of 0.2, 0.5, and 1.0 wt% pChNW increased storage modulus of neat MA from 3165.4 to 3585.4 MPa (13.3%), 4179.5 MPa (32.0%), as shown in Table 13, entry 12. This improvement was attributed to the stiffer nature of ChNWs compared to the polymer matrix at this temperature. As temperature increased, the storage modulus decreased, with a rapid drop observed in the transition zone at 85 °C. At this temperature, the storage modulus of neat MA increased from 59.1 to 71.6 MPa (21.2%), 89.3 MPa (51.1%), and 125.2 MPa (111.8%) MPa, with the addition of 0.2, 0.5, and 1.0 wt% pChNW, respectively, due to the reinforcing ability of pChNW in the transition zone where the chain mobility begins.⁷⁷ The modulus improvement for pChNW-filled composites was still evident at 200 °C, a temperature corresponding to second rubbery plateau region. At this temperature, the storage modulus of neat MA increased from 8.1 MPa to 17.7 MPa (118.5%) with the addition of 0.5 wt% pChNWs and slightly decreased to 15.5 MPa at 1.0 wt% pChNW loading. Likewise, the tensile modulus also increased with increasing pChNW content.

The incorporation of pChNWs also increased the composite tensile strength, reaching a maximum strength of 65.6 MPa at 0.5 wt% pChNW loading. The elongation at break of the composites increased with addition of 0.2 and 0.5 wt% (from 6.0 for neat MA to 8.9 and 6.7%, respectively). However, the addition of 1.0 wt% decreased significantly to $\sim 2.0\%$, indicating brittle behavior. These improvements were attributed to the strong interfacial adhesion induced by the physical and chemical crosslinking between pChNW filler and MA matrix.⁷⁷

Another study examined the reinforcement effects of ChNWs on PEGDMA and PEGDMA/Chitosan (CS) hydrogels by assessing their adhesion, tensile properties, and swelling behavior (Table 13, entry 13).⁹⁰ The reinforced hydrogels were synthesized *via* free radical polymerization under the UV light, enabling the crosslinking of PEGDMA and CS to form interpenetrating network hydrogels. The addition of CS and ChNWs improved adhesion strength, increasing it from 2.1 kPa in neat

PEGDMA to 3.1 kPa in PEGDMA/CS and 4.2 kPa in PEGDMA/CS/ChNWs, suggesting that CS enhanced interface adhesion and ChNWs further strengthened it. The hydrogels' tensile properties also improved with the incorporation of CS and ChNWs. Elongation at break increased from 100% in neat PEGDMA to 125% with CS, and further to 145% with both CS and ChNWs. Breaking strength also rose from 5.0 kPa to 9.0 kPa, and further to 11.2 kPa, demonstrating excellent toughness. Swelling tests showed that all hydrogels – PEGDA, PEGDA/CS, and PEGDA/CS/ChNWs – had high swelling rates, reaching 277%, 300%, and 289% respectively. This suggested that the hydrogels expand to a larger volume, which supports faster wound healing and provides an ideal mechanical micro-environment for tissue regeneration.⁹⁰

4.6.5. Poly(ethylene terephthalate) (PET). Poly(ethylene terephthalate) (PET) is the most widely used polyester in packaging due to its low cost and film-forming characteristics. However, it is primarily derived from nonrenewable petroleum resources and is not biodegradable. While it can be synthesized from renewable sources, this process has not yet become widespread commercially. Although PET is recyclable and provides a good water vapor barrier, its oxygen barrier properties often require the addition of other materials, which are typically nonrenewable. This raises environmental concerns and complicates recycling within current infrastructure. To address these concerns, researchers have been exploring the use of bio-based materials, aiming to combine a renewable barrier layer with PET for more sustainable packaging solutions.

Several studies have highlighted the use of nanochitin as reinforcing agent in the coating layer of PET films.^{89,129,130} Ji *et al.* investigated multilayer films with PET as the model substrate, using ChNWs and cellulose nanocrystals (CNCs) as bilayer barrier coatings (Table 13, entry 14). ChNWs and CNCs were applied in equal ratios as sequential coatings, with ChNW as the bottom layer and CNCs as the top layer on PET films. The properties – including oxygen permeability, water vapor transmission rate, transmittance, and haze – were then evaluated. To further understand the reinforcement effects of ChNWs compared to CNCs, additional PET films were coated with single layers of ChNW, CNC, or a blend of both (1:1 mass ratio, PET-blend), and their properties were also assessed. The bilayer ChNWs–CNCs–PET film exhibited an oxygen permeability (OP) $5.2 \text{ cm}^3 \mu\text{m m}^{-2} \text{ day}^{-1} \text{ kPa}^{-1}$, representing a 70% reduction compared to uncoated PET ($17.3 \text{ cm}^3 \mu\text{m m}^{-2} \text{ day}^{-1} \text{ kPa}^{-1}$). However, the OP value of this bilayer film was not significantly different from the single-layer CNCs–PET film. In contrast, the OP value of PET-blend ($10.2 \text{ cm}^3 \mu\text{m m}^{-2} \text{ day}^{-1} \text{ kPa}^{-1}$) was lower than that of ChNWs–PET but higher than that of CNCs–PET, confirming that applying ChNWs and CNCs as bilayers provides a better oxygen barrier performance than blending. While the water vapor barrier properties of the coated films were similar to those of the uncoated PET films, the bilayer ChNWs–CNCs–PET film exhibited the lowest transmittance and haze.



Yu *et al.*¹³⁰ reported the use of blade coating to apply single-layer coatings of ChNWs and blended ChNW/CS, and bilayer coatings of these materials layered with CNCs, on PET substrates (Table 13, entries 15–17). Two ChNWs with different sizes and degrees of acetylation were selected as the basic coating materials. Short ChNWs (114 nm, SChNWs), with lower degree of acetylation (76.4% DA) than long ChNW (230 nm, 85.1% DA, LChNWs), showed better barrier performance with 30% reduction in OP ($11.1 \text{ cm}^3 \mu\text{m m}^{-2} \text{ day}^{-1} \text{ kPa}^{-1}$ under 50% RH) compared to uncoated PET ($15.9 \text{ cm}^3 \mu\text{m m}^{-2} \text{ day}^{-1} \text{ kPa}^{-1}$ under 50% RH, see Table 13, entry 15). SChNWs were found to be efficient in forming a dense packed structure over LChNWs. Further, CS was added to fill and close the pores formed in the SChNW-based coating layer. With an optimal mass ratio of 1 : 1 between these two components, the OP dropped to $5.1 \pm 0.1 \text{ cm}^3 \mu\text{m m}^{-2} \text{ day}^{-1} \text{ kPa}^{-1}$ under 50% RH (Table 13, entry 16). This ChNW/CS-based coating led to a less than 2% and 15% decrease in light transmittance and tensile strength compared to uncoated PET films, respectively. The O_2 barrier properties were further improved by adding a CNC layer to the ChNW/CS-coated PET. Under 50% RH, the OP of (SChNW/CS)-CNC-coated PET film was as low as $3.6 \pm 0.1 \text{ cm}^3 \mu\text{m m}^{-2} \text{ day}^{-1} \text{ kPa}^{-1}$ (Table 13, entry 17). Moreover, after thermal treatment (120 °C, 2.5 h), the OP dropped to $2.2 \text{ cm}^3 \mu\text{m m}^{-2} \text{ day}^{-1} \text{ kPa}^{-1}$ (50% RH) and $4.8 \text{ cm}^3 \mu\text{m m}^{-2} \text{ day}^{-1} \text{ kPa}^{-1}$ (80% RH). This improvement was attributed to the formation of a densely compacted interface between SChNW/CS and CNC.¹³⁰ The tensile properties of the coated PET substrates, in all cases, decreased compared to the uncoated PET due to substantial residual stress at the interface between the coatings and the base polymer.

A study by Kim *et al.*⁸⁹ reported the design of a highly flexible coating on commercial PET film that is transparent to visible light and radio frequency (Table 13, entry 18). Nanoscale blending was achieved through spray-assisted layer-by-layer assembly, where negatively charged cellulose nanofibers (CNFs) and positively charged ChNWs were combined. The degree of reinforcement of ChNWs in combination with CNFs was evaluated across multilayers (ranging from 10 to 50 numbers of bilayers) on commercial PET film. The oxygen transmission rate (OTR) of PET film decreased sharply to below $1.0 \text{ mL m}^2 \text{ day}^{-1}$ upon multilayer coating of ChNWs and CNCs (compared to $38.28 \text{ mL m}^2 \text{ day}^{-1}$ for pristine PET film). This enhanced oxygen barrier performance plateaued at $0.48 \pm 0.02 \text{ mL m}^2 \text{ day}^{-1}$ at 20 bilayers. This indicates that the synergistic interplay between these highly crystalline nanomaterials results in a flexible film with superior barrier properties. This synergy arises from electrostatic interactions or ionic cross-linking between the respective amine and carboxylate groups, which reduced the free volume in the film. The coating also notably reduces the haziness of PET (2.9% for neat PET vs. 87.5 for 50 bilayers of ChNWs and CNFs coated on PET), with a negligible loss of transparency, and provides effective inhibition of antibacterial growth. The reduced light scattering of the coated PET is due to the reduction in surface roughness, as confirmed by AFM results.

5. Applications

The improvements observed across various property categories with the addition of chitin nanomaterials, as demonstrated in different studies, mark a significant advancement in materials science. The inclusion of nanochitin as fillers has enhanced the strength of several polymers, enabling them to meet the desired specifications for applications in diverse industries, including biomedicine, packaging, automotive, electronics, and the paper industry, among others.

5.1. In biomedical sciences

Nanochitin is highly regarded for its beneficial properties, including its biodegradability, nontoxicity, and antimicrobial activity, making it an excellent substrate and filler for creating various biomedical frameworks.²⁴⁸ These characteristics make nanochitin particularly valuable in the development of advanced drug delivery systems, as biobased matrices commonly used in these applications often face significant challenges.^{249,250} This is why fillers, especially in the form of chitin nanomaterials have been extensively studied in conjunction with various biopolymers, particularly in materials like hydrogels, which are essential for drug delivery.

A growing body of research has focused on designing advanced, biocompatible wound healing scaffolds, hydrogels, films, and nano-based drug delivery systems using chitin nanomaterials. Conventional wound dressings, for instance, often suffers from issues such as low mechanical strength, poor flexibility, reduced antimicrobial activity, and inadequate adhesion and absorption capacity.^{4,90} Furthermore, scaffolds made from polymers like polycaprolactone and gelatin, which are typically used to support cell growth, tissue regeneration, and tissue/organ replacement, also face challenges such as improper pore size, incorrect shape, and structural instability and fragility.^{251,252} However, studies reviewed in this article confirm that the integration of nanochitin significantly improves the morphology, mechanical strength, swelling behavior, compression strength, cytotoxicity, thermal stability, and antibacterial activity of nanocomposite hydrogels made from biobased polymers such as PEGDA,⁹⁰ alginate,¹³² PVA,¹³³ chitosan,¹⁰⁶ and gelatin.¹²⁰ These enhancements make hydrogels more stable, flexible, and stronger, positioning them as improved drug carriers for advancing medical therapies.

5.2. In packaging

Another significant application of chitin nanomaterials is their use as fillers in packaging materials. As the shift towards replacing petroleum-based products gain momentum, the adoption of bio-based polymers in packaging is becoming a key concern. While a wide range of biomaterials is available to create food packaging materials, their potential is often limited by poor mechanical, barrier, and thermal properties, making it difficult for them to compete with conventional polymers. However, the crosslinking of polymers with nanochitin has proven to substantially enhance the inherent characteristics of these base polymers.



Barrier properties are especially critical in packaging applications, and reports indicate that the use of nanochitin as a filler has significantly improved the performance of polymers such as soy protein isolate,⁷³ gelatin,⁷⁸ polypropylene,⁸² and PVA.⁵² Specifically, nanochitin integration has enhanced properties such as water vapor transmission rate, oxygen permeability, UV-blocking capacity, and thermal tolerance, often surpassing the required standards for food storage. These enhancements make bio-based packaging materials more competitive with traditional petroleum-based polymers. Furthermore, the addition of nanochitin improves antimicrobial activity, which extends the longevity and preservation of sealed materials without compromising food quality.⁷³ The improvements in mechanical properties, biodegradability, and overall enhancement support multifunctionality, biocompatibility, and sustainability, aligning with the growing demand for eco-friendly packaging solutions.

5.3. In other applications

Chitin nanomaterials also have significant applications in various industries, including rubber, paper, electronics, adhesives, hardeners, and more. For example, the inclusion of nanochitin as fillers in cellulose papers has enhanced their antibacterial properties (~99% resistance), crystallinity, tensile strength, and color detection properties.⁷² These improved properties papers are crucial for a wide range of applications, whether in packaging, medical and healthcare supplies, stationery, construction, or industrial uses. The enhanced antimicrobial properties are particularly valuable for applications like filters, wound dressings, food packaging, and personal care products. The improved tensile strength benefits materials such as laminates, insulation components, wall coverings, and surgical materials. Additionally, the enhanced color detection properties are useful for environmental monitoring, including water and air quality testing, diagnostic substrates, and indicators.

In the rubbery industry, nanochitin has proven effective in reinforcing elastomeric materials, offering advantages such as improved color, lightweight characteristics, increased thermal stability, and superior mechanical properties (tensile, tear, and swelling potential) compared to traditional natural rubber.^{13,18,25,51,53,147} Since natural rubber is not ideal for engineering applications in its raw form, its vulcanized version is more commonly used. The incorporation of nanochitin into these materials shows promising results for advanced rubber-based elastomeric applications, such as in the automotive industry (tires, seals, gaskets, belts), flooring mats, aerospace components (vibration dampers, conveyor belts, rollers), electronics, and medical uses. Furthermore, ChNWs contribute to producing mechanically enhanced materials and are also believed to exhibit strong bio-adhesive properties. Their higher adhesive performance, which is comparable to cellulose, offers significant advantages in structuring various material frameworks for a wide range of interdisciplinary applications.^{90,101,106}

In summary, chitin nanomaterials have emerged as promising green nanofillers and base polymers in material science. While their advantages over conventional polymers are still being explored, their exceptional properties, which surpass those of many natural and synthetic polymers, are gradually becoming more evident. However, studies clearly indicate that achieving optimal material performance requires careful optimization of the amount of chitin nanowhiskers used. It is also important to note that the potential use of chitin in its nanoform as has not yet been fully explored across a wide range of polymers. Moreover, there is still an exciting scope that remains unexplored in utilizing nanochitin as natural polymers in sustainable chemistry. For instance, they can be explored as a catalyst support for carbon monoxide oxidation reaction²⁵³ and as activated chitin-based carbon sheet for oxygen reduction and evolution reactions.²⁵⁴ Therefore, it is essential to conduct further research to enhance the characteristics of nanochitin. Overcoming challenges related to its production, processing, and compatibility with various polymers is crucial for advancing its use in diverse applications.

6. Conclusion and outlook

In this review, we summarized various strategies for preparing nanochitin-reinforced composite plastics and examined how nanochitin influences polymer properties for diverse applications. Nanochitin, with its varying size and morphology, can be synthesized through several methods discussed in this review. We analyzed these strategies from the perspective of identifying simpler, more efficient methods compared to more complex ones. For example, researchers have explored casting methods and ways to optimize these processes to enhance both efficiency and environmental sustainability. While composites reinforced with nanochitin can be fabricated using various techniques and conditions, the effectiveness of chitin reinforcement and its interactions with polymer matrix can vary even when the same method is used. The nature, size, shape, loading and interaction of chitin nanomaterials are crucial factors that determine their role in reinforcing polymers.

Additionally, the large amount of free reactive hydroxyl and acetyl amine groups on the nanochitin surface enables a range of chemical modifications and functionalization through chemical derivatization or post-functionalization. These modifications have distinct effects on different polymers, showcasing the tunability of nanochitin to meet specific application needs. For instance, the incorporation of carboxylated nanochitin in the form of ChNWs notably improves the mechanical properties of paper handsheets at low loading (1 wt%),¹²¹ whereas for natural rubber reinforcements, a higher loading (3.4 wt%) resulted in a more significant improvement in mechanical properties.²⁰²

Several challenges remain in fully realizing the potential of nanochitin as a reinforcing agent in polymer matrices and as a natural polymer. As highlighted in this review, many studies have reported the agglomeration of nanochitin particles at



higher loading levels, with the extent of agglomeration varying across different polymers. This agglomeration negatively impacts the reinforcement efficiency of nanochitin, as the agglomerates hinder uniform dispersion and disrupt interactions within the polymer matrix, ultimately influencing the material's overall properties. The degree of agglomeration is influenced by factors such as the polymer type, nanochitin loading, and processing conditions during composite preparation. In certain cases, pretreatment methods like PEG or PEO to improve nanochitin dispersion in PLA have shown some positive effects, but this has also led to a decrease in the tensile indices of the composites. On the other hand, curing agents like chitosan and lysine contributed to both improved nanochitin dispersion in the epoxy resin matrix and enhanced mechanical properties of the composites. However, agents like arginine and cysteine improved nanochitin dispersion but had adverse effects on the epoxy mechanical properties. The scalability of nanochitin-based composites is another crucial concern. While the production of nanochitin may be scalable, its success depends on the techniques used to produce chitin, create nanochitin/polymer composites, and ensure their efficiency. Another major concern is the cost of nanochitin and nanochitin-reinforced composites, as high production costs could limit their widespread use in various applications.

Finally, in most cases nanochitin has been used primarily as nanofillers or supportive materials, although its potential for other applications remains to be explored. Therefore, further investigation into its full potential is essential to realize a circular economy with sustainable practices. Overall, challenges remain in the areas of large-scale manufacturing, consistent dispersion in hydrophobic matrices, and comprehensive biodegradation profiling under both laboratory and real-world conditions. Advancing understanding in these areas—particularly regarding long-term environmental fate and degradation behavior—will be critical for unlocking the full commercial and ecological potential of ChNW-based composites across diverse industries.

Conflicts of interest

The authors declare the following competing financial interests: J. L. Shamshina is an inventor of the related patents and applications and has partial ownership of Chitalyst, LLC and Mirus Boletus, LLC.

Data availability

The data supporting this article have been included as part of the article and the ESI.†

Acknowledgements

The authors gratefully acknowledge support from the Cotton Incorporated project titled “Chitin Nanowhisker-Encapsulated

Herbicides for Sustainable Release, Superior Leaf Adhesion, and Enhanced Safety in Cotton Protection” (Project Number: 25-123, Project Year: 2025).

References

- 1 R. D. Maalihan, B. B. Pajarito and R. C. Advincula, 3D-printing methacrylate/chitin nanowhiskers composites via stereolithography: Mechanical and thermal properties, *Mater. Today: Proc.*, 2020, **33**, 1819–1824, DOI: [10.1016/j.matpr.2020.05.063](https://doi.org/10.1016/j.matpr.2020.05.063).
- 2 L. Bai, L. Liu, M. Esquivel, B. L. Tardy, S. Huan, X. Niu, S. Liu, G. Yang, Y. Fan and O. J. Rojas, Nanochitin: Chemistry, structure, assembly, and applications, *Chem. Rev.*, 2022, **122**(13), 11604–11674, DOI: [10.1021/acs.chemrev.2c00125](https://doi.org/10.1021/acs.chemrev.2c00125).
- 3 M. A. S. Anwer, J. Wang, A. Guan and H. E. Naguib, Chitin nano-whiskers (CNWs) as a bio-based bio-degradable reinforcement for epoxy: Evaluation of the impact of CNWs on the morphological, fracture, mechanical, dynamic mechanical, and thermal characteristics of dgeba epoxy resin, *RSC Adv.*, 2019, **9**(20), 11063–11076, DOI: [10.1039/C9RA00769E](https://doi.org/10.1039/C9RA00769E).
- 4 M. Jones, M. Kujundzic, S. John and A. Bismarck, Crab vs. Mushroom: A review of crustacean and fungal chitin in wound treatment, *Mar. Drugs*, 2020, **18**(1), 64, DOI: [10.3390/md18010064](https://doi.org/10.3390/md18010064).
- 5 N. A. Z. Abidin, F. Kormin, N. A. Z. Abidin, N. A. F. M. Anuar and M. F. A. Bakar, The potential of insects as alternative sources of chitin: An overview on the chemical method of extraction from various sources, *Int. J. Mol. Sci.*, 2020, **21**(14), 1–25, DOI: [10.3390/ijms21144978](https://doi.org/10.3390/ijms21144978).
- 6 A. G. J. Tacon, World aquaculture trends and future prospects, in *World Aquaculture*, 2023. <https://www.was.org/Magazine/2023/04/22/#zoom=true>.
- 7 P. Romano, H. Fabritius and D. Raabe, The exoskeleton of the lobster homarus americanus as an example of a smart anisotropic biological material, *Acta Biomater.*, 2007, **3**(3 SPEC. ISS.), 301–309, DOI: [10.1016/j.actbio.2006.10.003](https://doi.org/10.1016/j.actbio.2006.10.003).
- 8 L. Barandiaran, B. Alonso, A. Reifs, I. Larraza, R. Olmos-juste, A. F. Calvo, A. Eceiza and R. Perez-jimenez, Enzymatic upgrading of nanochitin using an ancient lytic polysaccharide monooxygenase, *Commun. Mater.*, 2022, **3**(55), 1–23, DOI: [10.1038/s43246-022-00277-9](https://doi.org/10.1038/s43246-022-00277-9).
- 9 N. E. Mushi, S. Utsel and L. A. Berglund, Nanostructured biocomposite films of high toughness based on native chitin nanofibers and chitosan, *Front. Chem.*, 2014, **2**, 1–11, DOI: [10.3389/fchem.2014.00099](https://doi.org/10.3389/fchem.2014.00099).
- 10 B. Joseph, R. Mavelil Sam, P. Balakrishnan, H. J. Maria, S. Gopi, T. Volova, S. C. M. Fernandes and S. Thomas, Extraction of nanochitin from marine resources and fabrication of polymer nanocomposites: Recent advances, *Polymers*, 2020, **12**(8), 1664, DOI: [10.3390/polym12081664](https://doi.org/10.3390/polym12081664).



- 11 S. Ling, D. L. Kaplan and M. J. Buehler, Nanofibrils in nature and materials engineering, *Nat. Rev. Mater.*, 2018, **3**, 1–15, DOI: [10.1038/natrevmats.2018.16](#).
- 12 S. N. Patek and R. L. Caldwell, Extreme impact and cavitation forces of a biological hammer: Strike forces of the peacock mantis shrimp odontodactylus scyllarus, *J. Exp. Biol.*, 2005, **208**(19), 3655–3664, DOI: [10.1242/jeb.01831](#).
- 13 Y. Liu, M. Liu, S. Yang, B. Luo and C. Zhou, Liquid crystalline behaviors of chitin nanocrystals and their reinforcing effect on natural rubber, *ACS Sustainable Chem. Eng.*, 2018, **6**(1), 325–336, DOI: [10.1021/acssuschemeng.7b02586](#).
- 14 J. L. Shamshina and N. Abidi, Isolation of chitin nanowhiskers directly from crustacean biomass waste in a single step with acidic ionic liquids, *ACS Sustainable Chem. Eng.*, 2022, **10**(36), 11846–11855, DOI: [10.1021/acssuschemeng.2c02461](#).
- 15 S. Gopi, P. Balakrishnan, C. Divya, S. Valic, E. Govorcina Bajsic, A. Pius and S. Thomas, Facile synthesis of chitin nanocrystals decorated on 3D cellulose aerogels as a new multi-functional material for waste water treatment with enhanced anti-bacterial and anti-oxidant properties, *New J. Chem.*, 2017, **41**(21), 12746–12755, DOI: [10.1039/c7nj02392h](#).
- 16 Q. Deng, J. Li, J. Yang and D. Li, Optical and flexible α -chitin nanofibers reinforced poly(vinyl alcohol) (PVA) composite film: Fabrication and property, *Composites, Part A*, 2014, **67**, 55–60, DOI: [10.1016/j.compositesa.2014.08.013](#).
- 17 Y. Fan, H. Fukuzumi, T. Saito and A. Isogai, Comparative characterization of aqueous dispersions and cast films of different chitin nanowhiskers/nanofibers, *Int. J. Biol. Macromol.*, 2012, **50**(1), 69–76, DOI: [10.1016/j.ijbiomac.2011.09.026](#).
- 18 C. D. M. Dominic, R. Joseph, P. M. Sabura Begum, A. Raghunandanan, N. T. Vackkachan, D. Padmanabhan and K. Formela, Chitin nanowhiskers from shrimp shell waste as green filler in acrylonitrile-butadiene rubber: Processing and performance properties, *Carbohydr. Polym.*, 2020, **245**, 116505, DOI: [10.1016/j.carbpol.2020.116505](#).
- 19 S. C.-Y. Li, Y.-C. Sun, Q. Guan and H. Naguib, Effects of chitin nanowhiskers on the thermal, barrier, mechanical, and rheological properties of polypropylene nanocomposites, *RSC Adv.*, 2016, **6**(76), 72086–72095, DOI: [10.1039/C6RA11623J](#).
- 20 A. M. Salaberria, J. Labidi and S. C. M. Fernandes, Chitin nanocrystals and nanofibers as nano-sized fillers into thermoplastic starch-based biocomposites processed by melt-mixing, *Chem. Eng. J.*, 2014, **256**, 356–364, DOI: [10.1016/j.cej.2014.07.009](#).
- 21 F. J. Alvarez, The effect of chitin size, shape, source and purification method on immune recognition, *Molecules*, 2014, **19**(4), 4433–4451, DOI: [10.3390/molecules19044433](#).
- 22 Y. Feng, J. Li, B. Wang, X. Tian, K. Chen, J. Zeng, J. Xu and W. Gao, Novel nanofibrillated cellulose/chitin whisker hybrid nanocomposites and their use for mechanical performance enhancements, *BioResources*, 2018, **13**(2), 3030–3044.
- 23 J. Wang, Z. Chen, A. Guan, N. R. Demarquette and H. E. Naguib, Ionic liquids facilitated dispersion of chitin nanowhiskers for reinforced epoxy composites, *Carbohydr. Polym.*, 2020, **247**, 116746, DOI: [10.1016/j.carbpol.2020.116746](#).
- 24 J. Araki, Y. Yamanaka and K. Ohkawa, Chitin-chitosan nanocomposite gels: Reinforcement of chitosan hydrogels with rod-like chitin nanowhiskers, *Polym. J.*, 2012, **44**(7), 713–717, DOI: [10.1038/pj.2012.11](#).
- 25 K. Gopalan Nair and A. Dufresne, Crab shell chitin whisker reinforced natural rubber nanocomposites. 1. Processing and swelling behavior, *Biomacromolecules*, 2003, **4**(3), 657–665, DOI: [10.1021/bm020127b](#).
- 26 J. Li, Y. Gao, J. Zhao, J. Sun and D. Li, Homogeneous dispersion of chitin nanofibers in polylactic acid with different pretreatment methods, *Cellulose*, 2017, **24**(4), 1705–1715, DOI: [10.1007/s10570-017-1216-y](#).
- 27 M. Wang, H. Xue, Z. Feng, B. Cheng and H. Yang, Increase of tensile strength and toughness of bio-based diglycidyl ether of bisphenol a with chitin nanowhiskers, *PLoS One*, 2017, **12**(6), 1–12, DOI: [10.1371/journal.pone.0177673](#).
- 28 S. Ifuku, S. Morooka, N. Nakagaito and H. Saimoto, Preparation and characterization of optically transparent chitin nanofiber/(meth)acrylic resin composites, *Green Chem.*, 2011, 1708–1711, DOI: [10.1039/c1gc15321h](#).
- 29 E. Ben Ayed, N. Ghorbel, A. Kallel, J. L. Putaux and S. Boufi, Polyaniline-grafted chitin nanocrystals as conductive reinforcing nanofillers for waterborne polymer dispersions, *Biomacromolecules*, 2022, **23**(10), 4167–4178, DOI: [10.1021/acs.biomac.2c00635](#).
- 30 M. Esmailzadeh, E. Tammari, T. Safarpour, S. M. Razavian and L. Pezzato, Anti-corrosion effect of chitin and chitosan nanoparticles in epoxy coatings, *Mater. Chem. Phys.*, 2024, **317**, 129097–129097, DOI: [10.1016/j.matchemphys.2024.129097](#).
- 31 M. Zhou, Z. Liu, T. Liu, Y. Zhu and N. Lin, Tradeoff between amino group and crystallinity of chitin nanocrystals as a functional component in fluorescent nail coatings, *ACS Sustainable Chem. Eng.*, 2022, **10**(31), 10327–10338, DOI: [10.1021/acssuschemeng.2c03024](#).
- 32 S. Y. Baraki, Y. Zhang, X. Li, L. Ding, D. K. Debeli, D. K. Macharia, B. Wang, X. Feng, Z. Mao and X. Sui, Regenerated chitin reinforced polyhydroxybutyrate composites via pickering emulsion template with improved rheological, thermal, and mechanical properties, *Compos. Commun.*, 2021, **25**, 100655, DOI: [10.1016/j.coco.2021.100655](#).
- 33 J. Liao, Y. Zhou, B. Hou, J. Zhang and H. Huang, Nano-chitin: Preparation strategies and food biopolymer film reinforcement and applications, *Carbohydr. Polym.*, 2023, **305**, 120553–120553, DOI: [10.1016/j.carbpol.2023.120553](#).
- 34 C. Muñoz-Núñez, M. Fernández-García and A. Muñoz-Bonilla, Chitin nanocrystals: Environmentally friendly



- materials for the development of bioactive films, *Coatings*, 2022, **12**(2), 1–17, DOI: [10.3390/coatings12020144](https://doi.org/10.3390/coatings12020144).
- 35 P. Morganti, M. Palombo, G. Tishchenko, V. E. Yudin, F. Guarneri, M. Cardillo, P. Del Ciotto, F. Carezzi, G. Morganti and G. Fabrizi, Chitin-hyaluronan nanoparticles: A multifunctional carrier to deliver anti-aging active ingredients through the skin, *Cosmetics*, 2014, **1**(3), 140–158, DOI: [10.3390/cosmetics1030140](https://doi.org/10.3390/cosmetics1030140).
 - 36 P. Heidarian and A. Z. Kouzani, Starch-g-acrylic acid/magnetic nanochitin self-healing ferrogels as flexible soft strain sensors, *Sensors*, 2023, **23**(3), 1138, DOI: [10.3390/s23031138](https://doi.org/10.3390/s23031138).
 - 37 D. Liu, Y. Chang, D. Tian, W. Wu, A. Lu, N. Prempeh, M. Tan and Y. Huang, Lyotropic liquid crystal self-assembly of H_2O_2 -hydrolyzed chitin nanocrystals, *Carbohydr. Polym.*, 2018, **196**, 66–72, DOI: [10.1016/j.carbpol.2018.04.098](https://doi.org/10.1016/j.carbpol.2018.04.098).
 - 38 M. M. Haider, G. Jian, T. Zhong, H. Li, C. A. Fernandez, L. S. Fifield, M. Wolcott and S. Nassiri, Insights into setting time, rheological and mechanical properties of chitin nanocrystals- and chitin nanofibers-cement paste, *Cem. Concr. Compos.*, 2022, **132**, 104623–104623, DOI: [10.1016/j.cemconcomp.2022.104623](https://doi.org/10.1016/j.cemconcomp.2022.104623).
 - 39 T. Zhong, G. Jian, Z. Chen, M. Wolcott, S. Nassiri and C. A. Fernandez, Interfacial interactions and reinforcing mechanisms of cellulose and chitin nanomaterials and starch derivatives for cement and concrete strength and durability enhancement: A review, *Nanotechnol. Rev.*, 2022, **11**(1), 2673–2713, DOI: [10.1515/ntrev-2022-0149](https://doi.org/10.1515/ntrev-2022-0149).
 - 40 Y. Shi, G. Wu, S.-C. Chen, F. Song and Y.-Z. Wang, Green fabrication of high-performance chitin nanowhiskers/PVA composite films with a “brick-and-mortar” structure, *ACS Sustainable Chem. Eng.*, 2020, **8**(48), 17807–17815, DOI: [10.1021/acssuschemeng.0c06736](https://doi.org/10.1021/acssuschemeng.0c06736).
 - 41 M. Liu, Q. Peng, B. Luo and C. Zhou, The improvement of mechanical performance and water-response of carboxylated sbr by chitin nanocrystals, *Eur. Polym. J.*, 2015, **68**, 190–206, DOI: [10.1016/j.eurpolymj.2015.04.035](https://doi.org/10.1016/j.eurpolymj.2015.04.035).
 - 42 M. Etcheverry and S. E. Barbosa, Glass fiber reinforced polypropylene mechanical properties enhancement by adhesion improvement, *Materials*, 2012, **5**(6), 1084–1113, DOI: [10.3390/ma5061084](https://doi.org/10.3390/ma5061084).
 - 43 S. Imani Yengejeh, S. A. Kazemi and A. Öchsner, Carbon nanotubes as reinforcement in composites: A review of the analytical, numerical and experimental approaches, *Comput. Mater. Sci.*, 2017, **136**, 85–101, DOI: [10.1016/j.commatsci.2017.04.023](https://doi.org/10.1016/j.commatsci.2017.04.023).
 - 44 A. Kiziltas, W. Liu, S. Tamrakar and D. Mielewski, Graphene nanoplatelet reinforcement for thermal and mechanical properties enhancement of bio-based polyamide 6, 10 nanocomposites for automotive applications, *Compos., Part C: Open Access*, 2021, **6**, 100177–100177, DOI: [10.1016/j.jcocom.2021.100177](https://doi.org/10.1016/j.jcocom.2021.100177).
 - 45 P. C. LeBaron and T. J. Pinnavaia, Clay nanolayer reinforcement of a silicone elastomer, *Chem. Mater.*, 2001, **13**(10), 3760–3765, DOI: [10.1021/cm010982m](https://doi.org/10.1021/cm010982m).
 - 46 A. Barzegar and T. Ghaffari, Nanoclay-reinforced polymethylmethacrylate and its mechanical properties, *Dent. Res. J.*, 2018, **15**(4), 295–301, DOI: [10.4103/1735-3327.237246](https://doi.org/10.4103/1735-3327.237246).
 - 47 A. Y. Goldman, J. A. Montes, A. Barajas, G. Beall and D. D. Eisenhour, Effect of aging on mineral-filled nanocomposites, in *Annual Technical Conference - ANTEC, Conference Proceedings*, 1999, vol. 2, pp. 195–209. DOI: [10.1016/B978-188420775-4.50022-2](https://doi.org/10.1016/B978-188420775-4.50022-2).
 - 48 P. R. Chang, R. Jian, J. Yu and X. Ma, Starch-based composites reinforced with novel chitin nanoparticles, *Carbohydr. Polym.*, 2010, **80**(2), 420–425, DOI: [10.1016/j.carbpol.2009.11.041](https://doi.org/10.1016/j.carbpol.2009.11.041).
 - 49 J. Junkasem, R. Rujiravanit and P. Supaphol, Fabrication of α -chitin whisker-reinforced poly(vinyl alcohol) nanocomposite nanofibres by electrospinning, *Nanotechnology*, 2006, **17**(17), 4519–4528, DOI: [10.1088/0957-4484/17/17/039](https://doi.org/10.1088/0957-4484/17/17/039).
 - 50 G. Schmidt and M. M. Malwitz, Properties of polymer – nanoparticle composites, *Curr. Opin. Colloid Interface Sci.*, 2003, **8**(1), 103–108, DOI: [10.1016/S1359-0294\(03\)00008-6](https://doi.org/10.1016/S1359-0294(03)00008-6).
 - 51 K. G. Nair and A. Dufresne, Crab shell chitin whisker reinforced natural rubber nanocomposites. 2. Mechanical behavior, *Biomacromolecules*, 2003, 666–674, DOI: [10.1021/bm0201284](https://doi.org/10.1021/bm0201284).
 - 52 C. Peng and G. Chen, Preparation and assessment of heat-treated α -chitin nanowhiskers reinforced poly(vinyl alcohol) film for packaging application, *Materials*, 2018, **11**(10), 1883, DOI: [10.3390/ma11101883](https://doi.org/10.3390/ma11101883).
 - 53 W. O. Egbujuo, P. I. Anyanwu and H. C. Obasi, Utilization of chitin powder as a filler in natural rubber vulcanizates: In comparison with carbon black filler, *Int. Rev. Appl. Sci. Eng.*, 2020, **11**(1), 43–51, DOI: [10.1556/1848.2020.00006](https://doi.org/10.1556/1848.2020.00006).
 - 54 S. H. Kamarudin, M. S. Mohd Basri, M. Rayung, F. Abu, S. b. Ahmad, M. N. Norizan, S. Osman, N. Sarifuddin, M. S. Z. M. Desa, U. H. Abdullah, *et al.*, A Review on natural fiber reinforced polymer composites (nfrpc) for sustainable industrial applications, *Polymers*, 2022, **14**(17), 1–36, DOI: [10.3390/polym14173698](https://doi.org/10.3390/polym14173698).
 - 55 A. Murawski, R. Diaz, S. Inglesby, K. Delabar and R. L. Quirino, Synthesis of bio-based polymer composites: Fabrication, fillers, properties, and challenges, in *Lecture Notes in Bioengineering*, 2019, pp. 29–55. DOI: [10.1007/978-3-030-04741-2_2](https://doi.org/10.1007/978-3-030-04741-2_2).
 - 56 E. Habib, R. Wang, Y. Wang, M. Zhu and X. X. Zhu, Inorganic fillers for dental resin composites: Present and future, *ACS Biomater. Sci. Eng.*, 2016, **2**(1), 1–11, DOI: [10.1021/acsbomaterials.5b00401](https://doi.org/10.1021/acsbomaterials.5b00401).
 - 57 H. P. S. A. Khalil, E. W. N. Chong, F. A. T. Owolabi, M. Asniza, Y. Y. Tye, M. R. N. Fazita, M. K. M. Haa, Z. Nurmiati and M. T. Paridah, Enhancement of basic properties of polysaccharide-based composites with organic and inorganic fillers: A review, *J. Appl. Polym. Sci.*, 2018, **136**(12), 47251, DOI: [10.1002/app.47251](https://doi.org/10.1002/app.47251).
 - 58 T. P. Sathishkumar, S. Satheshkumar and J. Naveen, Glass fiber-reinforced polymer composites - a review,



- J. Reinf. Plast. Compos.*, 2014, **33**(13), 1258–1275, DOI: [10.1177/0731684414530790](https://doi.org/10.1177/0731684414530790).
- 59 I. S. Abbood, S. A. Odaa, K. F. Hasan and M. A. Jasim, Properties evaluation of fiber reinforced polymers and their constituent materials used in structures - a review, *Mater. Today: Proc.*, 2021, **43**, 1003–1008, DOI: [10.1016/j.matpr.2020.07.636](https://doi.org/10.1016/j.matpr.2020.07.636).
- 60 B. S. Okan, Y. Menciloglu, B. G. Ozunlu and Y. E. Yagci, Graphene from waste tire by recycling technique for cost-effective and light-weight automotive plastic part production, *AIP Conf. Proc.*, 2020, **2205**(1), 020046, DOI: [10.1063/1.5142961](https://doi.org/10.1063/1.5142961).
- 61 P. Cataldi, A. Athanassiou and I. S. Bayer, Graphene nanoplatelets-based advanced materials and recent progress in sustainable applications, *Appl. Sci.*, 2018, **8**(9), 1438, DOI: [10.3390/app8091438](https://doi.org/10.3390/app8091438).
- 62 N. M. Nurazzi, M. R. M. Asyraf, A. Khalina, N. Abdullah, F. A. Sabaruddin, S. H. Kamarudin, S. b. Ahmad, A. M. Mahat, C. L. Lee, H. A. Aisyah, *et al.*, Fabrication, functionalization, and application of carbon nanotube-reinforced polymer composite: An overview, *Polymers*, 2021, **13**(7), 1047, DOI: [10.3390/polym13071047](https://doi.org/10.3390/polym13071047).
- 63 M. Jawaid, A. e. k. Qaiss and R. Bouhfid, *Nanoclay reinforced polymer composites*, 2016.
- 64 R. N. Rethon, *Mineral fillers in thermoplastics i*, 1999.
- 65 R. H. Marchessault, F. F. Morehead and N. M. Walter, Liquid crystal systems from fibrillar polysaccharides, *Nature*, 1959, **184**(4686), 632–633, DOI: [10.1038/184632a0](https://doi.org/10.1038/184632a0).
- 66 S. P. Druzian, N. P. Zanatta, L. N. Côrtes, A. Fátima and M. Streit, Preparation of chitin nanowhiskers and its application for crystal violet dye removal from wastewaters, *Environ. Sci. Pollut. Res. Int.*, 2019, **26**, 28548–28557, DOI: [10.1007/s11356-018-3547-0](https://doi.org/10.1007/s11356-018-3547-0).
- 67 J. Revel and R. H. Marchessault, In vitro chiral nematic ordering of chitin crystallites, *Int. J. Biol. Macromol.*, 1993, **15**, 329–335, DOI: [10.1016/0141-8130\(93\)90049-r](https://doi.org/10.1016/0141-8130(93)90049-r).
- 68 Y. Yamamoto, T. Nishimura, T. Saito and T. Kato, CaCO₃/chitin-whisker hybrids: Formation of CaCO₃ crystals in chitin-based liquid-crystalline suspension, *Polym. J.*, 2010, **42**(7), 583–586, DOI: [10.1038/pj.2010.32](https://doi.org/10.1038/pj.2010.32).
- 69 Q. Guan, *WIPO Patent*, WO2015/000055A1, 2015.
- 70 Q. Guan, US2017/0183459A1, 2017.
- 71 T. Jin, T. Liu, E. Lam and A. Moores, Chitin and chitosan on the nanoscale, *Nanoscale Horiz.*, 2021, **6**(7), 505–542, DOI: [10.1039/d0nh00696c](https://doi.org/10.1039/d0nh00696c).
- 72 Z. Li, M. Zhang, D. Cheng and R. Yang, Preparation of silver nano-particles immobilized onto chitin nano-crystals and their application to cellulose paper for imparting antimicrobial activity, *Carbohydr. Polym.*, 2016, **151**, 834–840, DOI: [10.1016/j.carbpol.2016.06.012](https://doi.org/10.1016/j.carbpol.2016.06.012).
- 73 R. R. Koshy, A. Reghunadhan, S. K. Mary, L. A. Pothan and S. Thomas, Mgonp/chitin nanowhiskey-based hybrid filler bound soy protein thin films for bioactive packaging applications, *Int. J. Food Sci. Technol.*, 2022, **57**(9), 5650–5662, DOI: [10.1111/ijfs.15805](https://doi.org/10.1111/ijfs.15805).
- 74 R. R. Koshy, A. Reghunadhan, S. K. Mary, P. S. Pillai, S. Joseph and L. A. Pothan, pH indicator films fabricated from soy protein isolate modified with chitin nanowhiskey and clitoria ternatea flower extract, *Curr. Res. Food Sci.*, 2022, **5**, 743–751, DOI: [10.1016/j.crfs.2022.03.015](https://doi.org/10.1016/j.crfs.2022.03.015).
- 75 S. C. Furtado, B. Srinivasan, J. Anbu and S. Abraham, Lyophilized biocomposite chitin-alginate matrices for wound healing application, *Mater. Today: Proc.*, 2023, DOI: [10.1016/j.matpr.2023.03.803](https://doi.org/10.1016/j.matpr.2023.03.803).
- 76 D. Saijun, P. Boonsuk and W. Chinpa, Conversion of polycarbonate from waste compact discs into antifouling ultrafiltration membrane via phase inversion, *J. Polym. Res.*, 2022, **29**(6), 220, DOI: [10.1007/s10965-022-03073-8](https://doi.org/10.1007/s10965-022-03073-8).
- 77 R. D. Maalihan, Q. Chen, H. Tamura, J. R. H. Sta. Agueda, B. B. Pajarito, E. B. Caldona and R. C. Advincula, Mechanically and thermally enhanced 3D-printed photocurable polymer nanocomposites containing functionalized chitin nanowhiskers by stereolithography, *ACS Appl. Polym. Mater.*, 2022, **4**(4), 2513–2526, DOI: [10.1021/acscapm.1c01816](https://doi.org/10.1021/acscapm.1c01816).
- 78 A. Etxabide, P. A. Kilmartin, J. I. Maté and J. Gómez-Estaca, Characterization of glucose-crosslinked gelatin films reinforced with chitin nanowhiskers for active packaging development, *LWT-Food Sci. Technol.*, 2022, **154**, 112833, DOI: [10.1016/j.lwt.2021.112833](https://doi.org/10.1016/j.lwt.2021.112833).
- 79 I. V. Tyshkunova, I. V. Gofman, D. G. Chukhchin, A. V. Malkov, A. I. Mishanin, A. S. Golovkin, E. N. Pavlova, D. N. Poshina and Y. A. Skorik, Biophysical characterization and cytocompatibility of cellulose cryogels reinforced with chitin nanowhiskers, *Polymers*, 2022, **14**(13), 1–18, DOI: [10.3390/polym14132694](https://doi.org/10.3390/polym14132694).
- 80 Y. Shi, S. C. Chen, W. T. Xiong and Y. Z. Wang, Simultaneous toughening and strengthening of chitin-based composites via tensile-induced orientation and hydrogen bond reconstruction, *Carbohydr. Polym.*, 2022, **275**, 118713–118713, DOI: [10.1016/j.carbpol.2021.118713](https://doi.org/10.1016/j.carbpol.2021.118713).
- 81 Y. Zhang, H. He, B. Huang, S. Wang and X. He, Enhanced thermal conductivity of polyvinyl alcohol insulation composites with m-bn@cnw hybrid materials, *Compos. Sci. Technol.*, 2021, **208**, 108766–108766, DOI: [10.1016/j.compscitech.2021.108766](https://doi.org/10.1016/j.compscitech.2021.108766).
- 82 H. L. Nguyen, T. H. Tran, L. T. Hao, H. Jeon, J. M. Koo, G. Shin, D. S. Hwang, S. Y. Hwang, J. Park and D. X. Oh, Biorenewable, transparent, and oxygen/moisture barrier nanocellulose/nanochitin-based coating on polypropylene for food packaging applications, *Carbohydr. Polym.*, 2021, **271**, 118421–118421, DOI: [10.1016/j.carbpol.2021.118421](https://doi.org/10.1016/j.carbpol.2021.118421).
- 83 Y. Wu, Y. Guan, H. Gao, L. Zhou and F. Peng, Novel high-strength montmorillonite/polyvinyl alcohol composite film enhanced by chitin nanowhiskers, *J. Appl. Polym. Sci.*, 2021, **138**(18), e50344, DOI: [10.1002/app.50344](https://doi.org/10.1002/app.50344).
- 84 A. G. B. Pereira, E. C. Muniz and Y.-L. Hsieh, Chitosan-sheath and chitin-core nanowhiskers, *Carbohydr. Polym.*, 2014, **107**, 158–166, DOI: [10.1016/j.carbpol.2014.02.046](https://doi.org/10.1016/j.carbpol.2014.02.046).



- 85 A. G. B. Pereira, E. C. Muniz and Y.-L. Hsieh, 1 h nmr and 1h–13c hsqc surface characterization of chitosan–chitin sheath-core nanowhiskers, *Carbohydr. Polym.*, 2015, **123**, 46–52, DOI: [10.1016/j.carbpol.2015.01.017](#).
- 86 A. A. Oun and J. W. Rhim, Preparation of multifunctional chitin nanowhiskers/zno-ag nps and their effect on the properties of carboxymethyl cellulose-based nanocomposite film, *Carbohydr. Polym.*, 2017, **169**, 467–479, DOI: [10.1016/j.carbpol.2017.04.042](#).
- 87 R. S. Andre, D. M. Santos, L. A. Mercante, M. H. M. Facure, S. P. Campana-filho, L. H. C. Mattoso and D. S. Correa, Nanochitin-based composite films as a disposable ethanol sensor, *J. Environ. Chem. Eng.*, 2020, **8**(5), 104163–104163, DOI: [10.1016/j.jece.2020.104163](#).
- 88 R. M. Abdelrahman, A. M. Abdel-Mohsen, M. Zboncak, J. Frankova, P. Lepcio, L. Kobera, M. Steinhart, D. Pavlinak, Z. Spotaz, R. Sklenářová, *et al.*, Hyaluronan biofilms reinforced with partially deacetylated chitin nanowhiskers: Extraction, fabrication, *in vitro* and antibacterial properties of advanced nanocomposites, *Carbohydr. Polym.*, 2020, **235**, 115951, DOI: [10.1016/j.carbpol.2020.115951](#).
- 89 T. Kim, T. H. Tran, S. Y. Hwang, J. Park, D. X. Oh and B. S. Kim, Crab-on-a-tree: All biorenewable, optical and radio frequency transparent barrier nanocoating for food packaging, *ACS Nano*, 2019, **13**(4), 3796–3805, DOI: [10.1021/acsnano.8b08522](#).
- 90 X. Liu, S. Qin, L. Xu, G. Fu, Y. Huang, C. Yu, G. Cheng, Y. Li, Y. He, Y. Qi, *et al.*, A tough and mechanically stable adhesive hydrogel for non-invasive wound repair, *Front. Bioeng. Biotechnol.*, 2023, **11**, 1–10, DOI: [10.3389/fbioe.2023.1173247](#).
- 91 Q. Guan and H. E. Naguib, Fabrication and characterization of PLA/phbv-chitin nanocomposites and their foams, *J. Polym. Environ.*, 2014, **22**(1), 119–130, DOI: [10.1007/s10924-013-0625-8](#).
- 92 R. Rizvi, B. Cochrane, H. Naguib and P. C. Lee, Fabrication and characterization of melt-blended polylactide-chitin composites and their foams, *J. Cell. Plast.*, 2011, **47**(3), 283–300, DOI: [10.1177/0021955X11402549](#).
- 93 Q. Zhang, S. Wei, J. Huang, J. Feng and P. R. Chang, Effect of surface acetylated-chitin nanocrystals on structure and mechanical properties of poly(lactic acid), *J. Appl. Polym. Sci.*, 2014, **131**(2), 2–9, DOI: [10.1002/app.39809](#).
- 94 A. J. Uddin, J. Araki, M. Fujie, S. Sembo and Y. Gotoh, Interfacial interaction and mechanical properties of chitin whisker-poly(vinyl alcohol) gel-spun nanocomposite fibers, *Polym. Int.*, 2012, **61**(6), 1010–1015, DOI: [10.1002/pi.4174](#).
- 95 J. Sriupayo, P. Supaphol, J. Blackwell and R. Rujiravanit, Preparation and characterization of α -chitin whisker-reinforced poly(vinyl alcohol) nanocomposite films with or without heat treatment, *Polymer*, 2005, **46**(15), 5637–5644, DOI: [10.1016/j.polymer.2005.04.069](#).
- 96 S. J. Kim, B. M. Hong and W. H. Park, The effects of chitin/chitosan nanowhiskers on the thermal, mechanical and dye adsorption properties of electrospun PVA nanofibrous membranes, *Cellulose*, 2020, **27**(10), 5771–5783, DOI: [10.1007/s10570-020-03191-w](#).
- 97 A. Morin and A. Dufresne, Nanocomposites of chitin whiskers from riftia tubes and poly(caprolactone), *Macromolecules*, 2002, **35**(6), 2190–2199, DOI: [10.1021/ma011493a](#).
- 98 A. M. Salaberria, R. H. Diaz, J. Labidi and S. C. M. Fernandes, Preparing valuable renewable nanocomposite films based exclusively on oceanic biomass - chitin nanofillers and chitosan, *React. Funct. Polym.*, 2015, **89**, 31–39, DOI: [10.1016/j.reactfunctpolym.2015.03.003](#).
- 99 M. C. Li, Q. Wu, K. Song, A. D. French, C. Mei and T. Lei, Ph-responsive water-based drilling fluids containing bentonite and chitin nanocrystals, *ACS Sustainable Chem. Eng.*, 2018, **6**(3), 3783–3795, DOI: [10.1021/acssuschemeng.7b04156](#).
- 100 F. Larbi, A. García, L. J. Valle, A. Hamou, J. Puiggali, N. Belgacem and J. Bras, Comparison of nanocrystals and nanofibers produced from shrimp shell α -chitin: From energy production to material cytotoxicity and pickering emulsion, *Carbohydr. Polym.*, 2018, **196**, 385–397, DOI: [10.1016/j.carbpol.2018.04.094](#).
- 101 L. G. Greca, K. J. De France, J. Majoinen, N. Kummer, O. I. V. Luotonen, S. Campioni, O. J. Rojas, G. Nyström and B. L. Tardy, Chitin-amyloid synergism and their use as sustainable structural adhesives, *J. Mater. Chem. A*, 2021, **9**(35), 19741–19753, DOI: [10.1039/d1ta03215a](#).
- 102 Z. Li, H. Wang, S. An and X. Yin, Nanochitin whisker enhances insecticidal activity of chemical pesticide for pest insect control and toxicity, *J. Nanobiotechnol.*, 2021, **19**(1), 1–13, DOI: [10.1186/s12951-021-00792-w](#).
- 103 K. P. S. Killiona, M. Zhou, Y. Zhu, P. Lan and N. Lin, Preparation and surface modification of crab nanochitin for organogels based on thiol-ene click cross-linking, *Int. J. Biol. Macromol.*, 2020, **150**, 756–764, DOI: [10.1016/j.ijbiomac.2020.02.125](#).
- 104 Y. Wang, L. Zhu, J. You, F. Chen, L. Zong, X. Yan and C. Li, Catecholic coating and silver hybridization of chitin nanocrystals for ultrafiltration membrane with continuous flow catalysis and gold recovery, *ACS Sustainable Chem. Eng.*, 2017, **5**(11), 10673–10681, DOI: [10.1021/acssuschemeng.7b02633](#).
- 105 T. V. Thanh, L. T. Hao, H. Y. Cho, H. Kim, S. A. Park, M. Lee, H. J. Kim, H. Jeon, S. Y. Hwang, J. Park, *et al.*, Sustainable poly(butylene adipate- co-furanoate) composites with sulfated chitin nanowhiskers: Synergy leading to superior robustness and improved biodegradation, *ACS Sustainable Chem. Eng.*, 2022, **10**(26), 8411–8422, DOI: [10.1021/acssuschemeng.2c01395](#).
- 106 J. Pang, S. Bi, T. Kong, X. Luo, Z. Zhou, K. Qiu, L. Huang, X. Chen and M. Kong, Mechanically and functionally strengthened tissue adhesive of chitin whisker complexed chitosan/dextran derivatives based hydrogel, *Carbohydr. Polym.*, 2020, **237**, 116138–116138, DOI: [10.1016/j.carbpol.2020.116138](#).



- 107 Y. Fan, T. Saito and A. Isogai, Chitin nanocrystals prepared by tempo-mediated oxidation of α -chitin, *Biomacromolecules*, 2008, **9**(1), 192–198, DOI: [10.1021/bm700966g](https://doi.org/10.1021/bm700966g).
- 108 A. M. Salaberria, J. Labidi and S. C. M. Fernandes, Different routes to turn chitin into stunning nano-objects, *Eur. Polym. J.*, 2015, **68**, 503–515, DOI: [10.1016/j.eurpolymj.2015.03.005](https://doi.org/10.1016/j.eurpolymj.2015.03.005).
- 109 C. Hou, J. Zhang, X. Zhang, Y. Wang, T. Li, B. Xia, J. Jiang and W. Dong, High strength chitin nanocrystal/alginate filament prepared by wet-spinning in “green” coagulating bath, *Cellulose*, 2022, **29**(16), 8611–8621, DOI: [10.1007/s10570-022-04814-0](https://doi.org/10.1007/s10570-022-04814-0).
- 110 K. Zhang and P. Liu, *US Pat.*, US11718689B2, 2023.
- 111 P. Liu, H. Liu, T. Schäfer, T. Gutmann, H. Gibhardt, H. Qi, L. Tian, X. C. Zhang, G. Buntkowsky and K. Zhang, Unexpected selective alkaline periodate oxidation of chitin for the isolation of chitin nanocrystals, *Green Chem.*, 2021, **23**(2), 745–751, DOI: [10.1039/D0GC04054A](https://doi.org/10.1039/D0GC04054A).
- 112 L. Zhang, B. Zhan and L. Yan, Preparation of nanochitin using deep eutectic solvents, *iScience*, 2024, **27**(3), 109312, DOI: [10.1016/j.isci.2024.109312](https://doi.org/10.1016/j.isci.2024.109312).
- 113 A. A. Oun and J. W. Rhim, Effect of oxidized chitin nanocrystals isolated by ammonium persulfate method on the properties of carboxymethyl cellulose-based films, *Carbohydr. Polym.*, 2017, **175**, 712–720, DOI: [10.1016/j.carbpol.2017.08.052](https://doi.org/10.1016/j.carbpol.2017.08.052).
- 114 A. Isogai, T. Hänninen, S. Fujisawa and T. Saito, Review: Catalytic oxidation of cellulose with nitroxyl radicals under aqueous conditions, *Prog. Polym. Sci.*, 2018, 122–148, DOI: [10.1016/j.progpolymsci.2018.07.007](https://doi.org/10.1016/j.progpolymsci.2018.07.007).
- 115 R. Chen, W. C. Huang, W. Wang and X. Mao, Characterization of tempo-oxidized chitin nanofibers with various oxidation times and its application as an enzyme immobilization support, *Mar. Life Sci. Technol.*, 2021, **3**(1), 85–93, DOI: [10.1007/s42995-020-00054-y](https://doi.org/10.1007/s42995-020-00054-y).
- 116 J. Sun, Y. Du, J. Ma, Y. Li, L. Wang, Y. Lu, J. Zou, J. Pang and C. Wu, Transparent bionanocomposite films based on konjac glucomannan, chitosan, and tempo-oxidized chitin nanocrystals with enhanced mechanical and barrier properties, *Int. J. Biol. Macromol.*, 2019, **138**, 866–873, DOI: [10.1016/j.ijbiomac.2019.07.170](https://doi.org/10.1016/j.ijbiomac.2019.07.170).
- 117 Y. Yue, X. Wang, Q. Wu, J. Han and J. Jiang, Highly recyclable and super-tough hydrogel mediated by dual-functional tio2 nanoparticles toward efficient photodegradation of organic water pollutants, *J. Colloid Interface Sci.*, 2020, **564**, 99–112, DOI: [10.1016/j.jcis.2019.12.069](https://doi.org/10.1016/j.jcis.2019.12.069).
- 118 J. Jiang, J. Yu, L. Liu, Z. Wang, Y. Fan, T. Saito and A. Isogai, Preparation and hydrogel properties of pH-sensitive amphoteric chitin nanocrystals, *J. Agric. Food Chem.*, 2018, **66**(43), 11372–11379, DOI: [10.1021/acs.jafc.8b02899](https://doi.org/10.1021/acs.jafc.8b02899).
- 119 J. Jiang, W. Ye, J. Yu, Y. Fan, Y. Ono, T. Saito and A. Isogai, Chitin nanocrystals prepared by oxidation of α -chitin using the o2/laccase/tempo system, *Carbohydr. Polym.*, 2018, **189**, 178–183, DOI: [10.1016/j.carbpol.2018.01.096](https://doi.org/10.1016/j.carbpol.2018.01.096).
- 120 Y. Yue, J. Liu, S. Gao, Y. Pei, Y. Jiang, K. Tang, J. Zhang, J. Liu and X. Zheng, Ionically conductive gelatin-based hybrid composite hydrogels with high mechanical strength, self-healing, and freezing-tolerant properties, *Eur. Polym. J.*, 2022, **172**, 111230–111230, DOI: [10.1016/j.eurpolymj.2022.111230](https://doi.org/10.1016/j.eurpolymj.2022.111230).
- 121 H. Tang, J. Wu, D. Li, C. Shi, G. Chen, M. He and J. Tian, High-strength paper enhanced by chitin nanowhiskers and its potential bioassay applications, *Int. J. Biol. Macromol.*, 2020, **150**, 885–893, DOI: [10.1016/j.ijbiomac.2020.02.154](https://doi.org/10.1016/j.ijbiomac.2020.02.154).
- 122 Z. Li, C. Liu, S. Hong, H. Lian, C. Mei, J. Lee, Q. Wu, M. A. Hubbe and M. C. Li, Recent advances in extraction and processing of chitin using deep eutectic solvents, *Chem. Eng. J.*, 2022, **446**(P2), 136953–136953, DOI: [10.1016/j.ccej.2022.136953](https://doi.org/10.1016/j.ccej.2022.136953).
- 123 J.-i. Kadokawa, A. Takegawa, S. Mine and K. Prasad, Preparation of chitin nanowhiskers using an ionic liquid and their composite materials with poly (vinyl alcohol), *Carbohydr. Polym.*, 2011, **84**(4), 1408–1412, DOI: [10.1016/j.carbpol.2011.01.049](https://doi.org/10.1016/j.carbpol.2011.01.049).
- 124 S. Hong, Y. Yuan, K. Zhang, H. Lian and H. Liimatainen, Efficient hydrolysis of chitin in a deep eutectic solvent synergism for production of chitin nanocrystals, *Nanomaterials*, 2020, **10**(5), 869, DOI: [10.3390/nano10050869](https://doi.org/10.3390/nano10050869).
- 125 Y. Fan, T. Saito and A. Isogai, Preparation of chitin nanofibers from squid pen β -chitin by simple mechanical treatment under acid conditions, *Biomacromolecules*, 2008, **9**(7), 1919–1923, DOI: [10.1021/bm800178b](https://doi.org/10.1021/bm800178b).
- 126 M. C. Li, Q. Wu, K. Song, H. N. Cheng, S. Suzuki and T. Lei, Chitin nanofibers as reinforcing and antimicrobial agents in carboxymethyl cellulose films: Influence of partial deacetylation, *ACS Sustainable Chem. Eng.*, 2016, **4**(8), 4385–4395, DOI: [10.1021/acssuschemeng.6b00981](https://doi.org/10.1021/acssuschemeng.6b00981).
- 127 Y. Fan, T. Saito and A. Isogai, Individual chitin nano-whiskers prepared from partially deacetylated α -chitin by fibril surface cationization, *Carbohydr. Polym.*, 2010, **79**(4), 1046–1051, DOI: [10.1016/j.carbpol.2009.10.044](https://doi.org/10.1016/j.carbpol.2009.10.044).
- 128 N. E. Mushi, N. Butchosa, M. Salajkova, Q. Zhou and L. A. Berglund, Nanostructured membranes based on native chitin nanofibers prepared by mild process, *Carbohydr. Polym.*, 2014, **112**, 255–263, DOI: [10.1016/j.carbpol.2014.05.038](https://doi.org/10.1016/j.carbpol.2014.05.038).
- 129 Y. Ji, D. E. Shen, Y. Lu, G. T. Schueneman, M. L. Shofner and J. C. Meredith, Aqueous-based recycling of cellulose nanocrystal/chitin nanowhisker barrier coatings, *ACS Sustainable Chem. Eng.*, 2023, **11**(29), 10874–10883, DOI: [10.1021/acssuschemeng.3c02457](https://doi.org/10.1021/acssuschemeng.3c02457).
- 130 Z. Yu, Y. Ji and J. C. Meredith, Multilayer chitin–chitosan–cellulose barrier coatings on poly(ethylene terephthalate), *ACS Appl. Polym. Mater.*, 2022, **4**(10), 7182–7190, DOI: [10.1021/acsapm.2c01059](https://doi.org/10.1021/acsapm.2c01059).
- 131 Y. Hu, L. Liu, J. Yu, Z. Wang and Y. Fan, Preparation of silk nanowhisker-composited amphoteric cellulose/chitin nano fiber membranes, *Biomacromolecules*, 2020, **21**(4), 1625–1635, DOI: [10.1021/acs.biomac.0c00223](https://doi.org/10.1021/acs.biomac.0c00223).
- 132 V. A. Petrova, V. Y. Elovskiy, S. V. Raik, D. N. Poshina, D. P. Romanov and Y. A. Skorik, Alginate gel reinforce-



- ment with chitin nanowhiskers modulates rheological properties and drug release profile, *Biomolecules*, 2019, **9**(7), 291, DOI: [10.3390/biom9070291](https://doi.org/10.3390/biom9070291).
- 133 C. Peng, J. Xu, G. Chen, J. Tian and M. He, The preparation of α -chitin nanowhiskers-poly (vinyl alcohol) hydrogels for drug release, *Int. J. Biol. Macromol.*, 2019, **131**, 336–342, DOI: [10.1016/j.ijbiomac.2019.03.015](https://doi.org/10.1016/j.ijbiomac.2019.03.015).
 - 134 R. Fernández-Marín, F. Hernández-Ramos, A. M. Salaberria, M.Á. Andrés, J. Labidi and S. C. M. Fernandes, Eco-friendly isolation and characterization of nanochitin from different origins by microwave irradiation: Optimization using response surface methodology, *Int. J. Biol. Macromol.*, 2021, **186**, 218–226, DOI: [10.1016/j.ijbiomac.2021.07.048](https://doi.org/10.1016/j.ijbiomac.2021.07.048).
 - 135 H. V. D. Nguyen, R. de Vries and S. D. Stoyanov, Chitin nanowhiskers with improved properties obtained using natural deep eutectic solvent and mild mechanical processing, *Green Chem.*, 2022, **24**(9), 3834–3844, DOI: [10.1039/D2GC00305H](https://doi.org/10.1039/D2GC00305H).
 - 136 A. J. Uddin, M. Fujie, S. Sembo and Y. Gotoh, Outstanding reinforcing effect of highly oriented chitin whiskers in PVA nanocomposites, *Carbohydr. Polym.*, 2012, **87**(1), 799–805, DOI: [10.1016/j.carbpol.2011.08.071](https://doi.org/10.1016/j.carbpol.2011.08.071).
 - 137 M. Yanat and K. Schroën, Advances in chitin-based nanoparticle use in biodegradable polymers: A review, *Carbohydr. Polym.*, 2023, **312**, 120789, DOI: [10.1016/j.carbpol.2023.120789](https://doi.org/10.1016/j.carbpol.2023.120789).
 - 138 R. Fernández Marín, PhD Thesis, University of the Basque Country (UPV/EHU), 2021.
 - 139 N. Lin, S. Wei, T. Xia, F. Hu, J. Huang and A. Dufresne, Green bionanocomposites from high-elasticity “soft” polyurethane and high-crystallinity “rigid” chitin nanocrystals with controlled surface acetylation, *RSC Adv.*, 2014, **4**(90), 49098–49107, DOI: [10.1039/C4RA07899C](https://doi.org/10.1039/C4RA07899C).
 - 140 Y. Ji, S. Waters, E. Lim, A. W. Lang, P. N. Ciesielski, M. L. Shofner, J. R. Reynolds and J. C. Meredith, Minimizing oxygen permeability in chitin/cellulose nanomaterial coatings by tuning chitin deacetylation, *ACS Sustainable Chem. Eng.*, 2022, **10**(1), 124–133, DOI: [10.1021/acssuschemeng.1c05051](https://doi.org/10.1021/acssuschemeng.1c05051).
 - 141 Y. Ji, D. E. Shen, E. K. Young, C. L. Goins, J. R. Reynolds, M. L. Shofner and J. C. Meredith, Optimization of spray-coated nanochitin/nanocellulose films as renewable oxygen barrier layers via thermal treatment, *Mater. Adv.*, 2022, **3**(22), 8351–8360, DOI: [10.1039/d2ma00832g](https://doi.org/10.1039/d2ma00832g).
 - 142 A. G. B. Pereira, A. R. Fajardo, A. P. Gerola, J. H. S. Rodrigues, C. V. Nakamura, E. C. Muniz and Y. L. Hsieh, First report of electrospun cellulose acetate nanofibers mats with chitin and chitosan nanowhiskers: Fabrication, characterization, and antibacterial activity, *Carbohydr. Polym.*, 2020, **250**, 116954, DOI: [10.1016/j.carbpol.2020.116954](https://doi.org/10.1016/j.carbpol.2020.116954).
 - 143 C. Chen, S. Deng, Y. Yang, D. Yang, T. Ye and D. Li, Highly transparent chitin nanofiber/gelatin nanocomposite with enhanced mechanical properties, *Cellulose*, 2018, **25**(9), 5063–5070, DOI: [10.1007/s10570-018-1915-z](https://doi.org/10.1007/s10570-018-1915-z).
 - 144 H. Lisboa, Reinforcement of poly (vinyl alcohol) films with alpha-chitin nanowhiskers, *Polimeros*, 2018, **28**(1), 69–75, DOI: [10.1590/0104-1428.07916](https://doi.org/10.1590/0104-1428.07916).
 - 145 H. Jafari, M. Shahrousvand and B. Kaffashi, Preparation and characterization of reinforced poly (ϵ -caprolactone) nanocomposites by cellulose nanowhiskers, *Polym. Compos.*, 2020, **41**(2), 624–632, DOI: [10.1002/pc.25393](https://doi.org/10.1002/pc.25393).
 - 146 P. M. Visakh, M. Monti, D. Puglia, M. Rallini, C. Santulli, F. Sarasini, S. Thomas and J. M. Kenny, Mechanical and thermal properties of crab chitin reinforced carboxylated sbr composites, *EXPRESS Polym. Lett.*, 2012, **6**(5), 396–409, DOI: [10.3144/expresspolymlett.2012.42](https://doi.org/10.3144/expresspolymlett.2012.42).
 - 147 K. G. Nair, A. Dufresne, A. Gandini and M. N. Belgacem, Crab shell chitin whiskers reinforced natural rubber nanocomposites. 3. Effect of chemical modification of chitin whiskers, *Biomacromolecules*, 2003, **4**(6), 1835–1842, DOI: [10.1021/bm030058g](https://doi.org/10.1021/bm030058g).
 - 148 M. Shibata, M. Enjoji, K. Sakazume and S. Ifuku, Bio-based epoxy/chitin nanofiber composites cured with amine-type hardeners containing chitosan, *Carbohydr. Polym.*, 2016, **144**, 89–97, DOI: [10.1016/j.carbpol.2016.02.033](https://doi.org/10.1016/j.carbpol.2016.02.033).
 - 149 Y. M. Lee, S. H. Kim and S. J. Kim, Preparation and characteristics of β -chitin and poly (vinyl alcohol) blend, *Polymer*, 1996, **37**(26), 5897–5905.
 - 150 M. Peesan, R. Rujiravanit and P. Supaphol, Characterisation of beta-chitin/poly(vinyl alcohol) blend films, *Polym. Test.*, 2003, **22**(4), 381–387, DOI: [10.1016/S0142-9418\(02\)00118-6](https://doi.org/10.1016/S0142-9418(02)00118-6).
 - 151 A. Amalraj, S. Jude and S. Gopi, Chapter 1 - polymer blends, composites and nanocomposites from chitin and chitosan; manufacturing, characterization and applications, in *Handbook of chitin and chitosan*, ed. S. Gopi, S. Thomas and A. Pius, Elsevier, 2020.
 - 152 T. Basak and J. L. Shamshina, Design of chitin cell culture matrices for 3D tissue engineering: The importance of chitin types, solvents, cross-linkers, and fabrication techniques, *Pharmaceutics*, 2024, **16**(6), 777, DOI: [10.3390/pharmaceutics16060777](https://doi.org/10.3390/pharmaceutics16060777).
 - 153 Y. Zhou, S. Fu, Y. Pu, S. Pan and A. J. Ragauskas, Preparation of aligned porous chitin nanowhisker foams by directional freeze-casting technique, *Carbohydr. Polym.*, 2014, **112**, 277–283, DOI: [10.1016/j.carbpol.2014.05.062](https://doi.org/10.1016/j.carbpol.2014.05.062).
 - 154 E. Robles, A. M. Salaberria, R. Herrera, S. C. M. Fernandes and J. Labidi, Self-bonded composite films based on cellulose nanofibers and chitin nanocrystals as antifungal materials, *Carbohydr. Polym.*, 2016, **144**, 41–49, DOI: [10.1016/j.carbpol.2016.02.024](https://doi.org/10.1016/j.carbpol.2016.02.024).
 - 155 Y. Lu, L. Weng and L. Zhang, Morphology and properties of soy protein isolate thermoplastics reinforced with chitin whiskers, *Biomacromolecules*, 2004, **5**(3), 1046–1051, DOI: [10.1021/bm034516x](https://doi.org/10.1021/bm034516x).



- 156 L. Broers, S. van Dongen, V. de Goederen, M. Ton, J. Spaen, J. Boeriu and K. Schroën, Addition of chitin nanoparticles improves polylactic acid film properties, *Nanotechnol. Adv. Mater. Sci.*, 2018, **1**(2), 1–8, DOI: [10.31038/NAMS.2018121](#).
- 157 M. N. M. Azlin, S. M. Sapuan, E. S. Zainudin, M. Y. M. Zuhri and R. A. Ilyas, Chapter 3 - natural polylactic acid-based fiber composites: A Review, in *Advanced processing, properties, and applications of starch and other bio-based polymers*, ed. F. M. Al-Oqla and S. M. Sapuan, Elsevier, 2020.
- 158 M. Rajabi, A. Ali, M. McConnell and J. Cabral, Keratinous materials: Structures and functions in biomedical applications, *Mater. Sci. Eng., C*, 2020, **110**, 110612, DOI: [10.1016/j.msec.2019.110612](#).
- 159 D. Dixit, R. Pal, G. Kapoor and M. Stabenau, 6 - light-weight composite materials processing, in *Lightweight ballistic composites*, ed. A. Bhatnagar, Woodhead Publishing, 2nd edn, 2016.
- 160 A. Hannibal and B. Weir, 11 - ballistic material processing, in *Lightweight ballistic composites*, ed. A. Bhatnagar, Woodhead Publishing, 2006.
- 161 M. Shibata, J. Fujigasaki, M. Enjoji, A. Shibata, N. Teramoto and S. Ifuku, Amino acid-cured bio-based epoxy resins and their biocomposites with chitin- and chitosan-nanofibers, *Eur. Polym. J.*, 2018, **98**, 216–225, DOI: [10.1016/j.eurpolymj.2017.11.024](#).
- 162 A. Wood, Practical methods of mixing additives with polymers, in *Plastics additives: An a-z reference*, ed. G. Pritchard, Springer Netherlands, Dordrecht, 1998.
- 163 L. A. Utracki, G. Z.-H. Shi, D. Rodrigue and R. Gonzalez-Núñez, Compounding polymer blends, in *Polymer blends handbook*, ed. L. A. Utracki and C. A. Wilkie, Springer Netherlands, Dordrecht, 2014.
- 164 P. Hold, Mixing of polymers— an overview part i, *Adv. Polym. Technol.*, 1982, **2**(2), 141–151, DOI: [10.1002/adv.1993.060020205](#).
- 165 M. B. Coltelli, P. Cinelli, V. Gigante, L. Aliotta, P. Morganti, L. Panariello and A. Lazzeri, Chitin nanofibrils in poly(lactic acid) (PLA) nanocomposites: Dispersion and thermo-mechanical properties, *Int. J. Mol. Sci.*, 2019, **20**(3), 504, DOI: [10.3390/ijms20030504](#).
- 166 N. Fijoł, A. Aguilar Sanchez, A. Mautner and A. P. Mathew, 3D-printed polylactic acid-based biocomposite filters reinforced with tempo-oxidized cellulose nanofibers and chitin nanofibers for removal of metal ions and microplastics from water, *SSRN Electron. J.*, 2022, 4156467, DOI: [10.2139/ssrn.4156467](#).
- 167 J. Xue, T. Wu, Y. Dai and Y. Xia, Electrospinning and electrospun nanofibers: Methods, materials, and applications, *Chem. Rev.*, 2019, **119**(8), 5298–5415, DOI: [10.1021/acs.chemrev.8b00593](#).
- 168 A. Frenot and I. S. Chronakis, Polymer nanofibers assembled by electrospinning, *Curr. Opin. Colloid Interface Sci.*, 2003, **8**(1), 64–75, DOI: [10.1016/S1359-0294\(03\)00004-9](#).
- 169 L. T. Hao, Y. Eom, T. H. Tran, J. M. Koo, J. Jegal, S. Y. Hwang, D. X. Oh and J. Park, Rediscovery of nylon upgraded by interactive biorenewable nano-fillers, *Nanoscale*, 2020, **12**(4), 2393–2405, DOI: [10.1039/C9NR08091K](#).
- 170 Y. Chen, L. Gan, J. Huang and A. Dufresne, Reinforcing mechanism of cellulose nanocrystals in nanocomposites, in *Nanocellulose: From Fundamentals to Advanced Materials*, 2019, pp. 201–250. DOI: [10.1002/9783527807437.ch7](#).
- 171 G. Satchanska, S. Davidova and P. D. Petrov, Natural and synthetic polymers for biomedical and environmental applications, *Polymers*, 2024, **16**(8), 1159, DOI: [10.3390/polym16081159](#).
- 172 F. A. Yihun, Nanochitin preparation and its application in polymer nanocomposites: A review, *Emergent Mater.*, 2022, **5**(6), 2031–2060, DOI: [10.1007/s42247-022-00427-2](#).
- 173 V. Rubentheren, T. A. Ward, C. Y. Chee and C. K. Tang, Processing and analysis of chitosan nanocomposites reinforced with chitin whiskers and tannic acid as a cross-linker, *Carbohydr. Polym.*, 2015, **115**, 379–387, DOI: [10.1016/j.carbpol.2014.09.007](#).
- 174 F. Zhu, C. Wang, S. Yang, Q. Wang, F. Liang, C. Liu, D. Qiu, X. Qu, Z. Hu and Z. Yang, Injectable tissue adhesive composite hydrogel with fibroblasts for treating skin defects, *J. Mater. Chem. B*, 2017, **5**(13), 2416–2424, DOI: [10.1039/c7tb00384f](#).
- 175 M. Santos, O. Del Carlo, J. M. Hong, Z. Liu, S. Jiang, S. Hrapovic, E. Lam, T. Jin and A. Moores, Effect of surface functionality on the rheological and self-assembly properties of chitin and chitosan nanocrystals and use in biopolymer films, *Biomacromolecules*, 2023, **24**(9), 4180–4189, DOI: [10.1021/acs.biomac.3c00513](#).
- 176 Y. Huang, M. Yao, X. Zheng, X. Liang, X. Su, Y. Zhang, A. Lu and L. Zhang, Effects of chitin whiskers on physical properties and osteoblast culture of alginate based nanocomposite hydrogels, *Biomacromolecules*, 2015, **16**(11), 3499–3507, DOI: [10.1021/acs.biomac.5b00928](#).
- 177 K. Kurita, Chitin and chitosan: Functional biopolymers from marine crustaceans, *Mar. Biotechnol.*, 2006, **8**(3), 203–226, DOI: [10.1007/s10126-005-0097-5](#).
- 178 P. Ravikumar and S. Sagadevan, Influence of the addition of chitin nanocrystals on the characteristics of cellulose acetate films, *Polimery*, 2021, **66**(2), 98–104, DOI: [10.14314/polimery.2021.2.2](#).
- 179 J. Yu, J. Yang, B. Liu and X. Ma, Preparation and characterization of glycerol plasticized-pea starch/zno-carboxymethylcellulose sodium nanocomposites, *Bioresour. Technol.*, 2009, **100**(11), 2832–2841, DOI: [10.1016/j.biortech.2008.12.045](#).
- 180 F. Xie, E. Pollet, P. J. Halley and L. Avérous, Starch-based nano-biocomposites, *Prog. Polym. Sci.*, 2013, **38**(10), 1590–1628, DOI: [10.1016/j.progpolymsci.2013.05.002](#).
- 181 C. Chen, Y. Wang, Y. Yang, M. Pan, T. Ye and D. Li, High strength gelatin-based nanocomposites reinforced by



- surface-deacetylated chitin nanofiber networks, *Carbohydr. Polym.*, 2018, **195**, 387–392, DOI: [10.1016/j.carbpol.2018.04.095](#).
- 182 L. Liu, R. Wang, J. Yu, J. Jiang, K. Zheng, L. Hu, Z. Wang and Y. Fan, Robust self-standing chitin nanofiber/nanowhisker hydrogels with designed surface charges and ultralow mass content via gas phase coagulation, *Biomacromolecules*, 2016, **17**(11), 3773–3781, DOI: [10.1021/acs.biomac.6b01278](#).
- 183 Q. Zhang, P. Sun, Z. Xu, W. Qu, Y. Zhang and X. Sui, Chitin nanocrystals as natural gel modifier for yielding stronger acid-induced soy protein isolate gel, *Carbohydr. Polym.*, 2024, **323**, 121446, DOI: [10.1016/j.carbpol.2023.121446](#).
- 184 Q. Zhang, L. Jiang and X. Sui, Incorporating chitin nanocrystal yields stronger soy protein gel: Insights into linear and nonlinear rheological behaviors by oscillatory shear tests, *Food Hydrocolloids*, 2023, **135**, 108177, DOI: [10.1016/j.foodhyd.2022.108177](#).
- 185 A. M. Abdel-Mohsen, J. Jancar, R. M. Abdel-Rahman, L. Vojtek, P. Hyřl, M. Dušková and H. Nejezchlebová, A novel in situ silver/hyaluronan bio-nanocomposite fabrics for wound and chronic ulcer dressing: In vitro and in vivo evaluations, *Int. J. Pharm.*, 2017, **520**(1), 241–253, DOI: [10.1016/j.ijpharm.2017.02.003](#).
- 186 L. David, V. Dulong, D. Le Cerf, L. Cazin, M. Lamacz and J.-P. Vannier, Hyaluronan hydrogel: An appropriate three-dimensional model for evaluation of anticancer drug sensitivity, *Acta Biomater.*, 2008, **4**(2), 256–263, DOI: [10.1016/j.actbio.2007.08.012](#).
- 187 A. M. Abdel-Mohsen, D. Pavliňák, M. Čileková, P. Lepcio, R. M. Abdel-Rahman and J. Jančář, Electrospinning of hyaluronan/polyvinyl alcohol in presence of *in situ* silver nanoparticles: Preparation and characterization, *Int. J. Biol. Macromol.*, 2019, **139**, 730–739, DOI: [10.1016/j.ijbiomac.2019.07.205](#).
- 188 H. Tan, J. Wu, L. Lao and C. Gao, Gelatin/chitosan/hyaluronan scaffold integrated with plga microspheres for cartilage tissue engineering, *Acta Biomater.*, 2009, **5**(1), 328–337, DOI: [10.1016/j.actbio.2008.07.030](#).
- 189 J. Lou, F. Liu, C. D. Lindsay, O. Chaudhuri, S. C. Heilshorn and Y. Xia, Dynamic hyaluronan hydrogels with temporally modulated high injectability and stability using a biocompatible catalyst, *Adv. Mater.*, 2018, **30**(22), 1705215, DOI: [10.1002/adma.201705215](#).
- 190 V. C. Chandrasekaran, Chapter 11 - storage and service life of rubber seals, in *Rubber seals for fluid and hydraulic systems*, ed. V. C. Chandrasekaran, William Andrew Publishing, Oxford, 2010.
- 191 R. Amna, H. Mittal and S. M. Alhassan, Sulfur copolymers used for the removal of heavy metals from wastewater, in *Reference module in materials science and materials engineering*, Elsevier, 2024.
- 192 A. P. Mathew, Elastomeric nanocomposites reinforced with nanocellulose and nanochitin, in *Handbook of nanocellulose and cellulose nanocomposites*, ed. H. Kargarzadeh, I. Ahmad, S. Thomas and A. Dufresne, Wiley-VCH Verlag GmbH & Co. KGaA, Estolcomo, 2017.
- 193 R. A. Chowdhury, A. M. Sadri and M. E. Hoque, 18 - industrial implementations of biocomposites, in *Green biocomposites for biomedical engineering*, ed. M. E. Hoque, A. Sharif and M. Jawaid, Woodhead Publishing, 2021.
- 194 V. K. Abitha, S. Thomas, A. V. Rane and K. Kanny, 3 - raw materials—rubber dam, in *Hydraulic rubber dam*, ed. S. Thomas, A. V. Rane, V. K. Abitha, K. Kanny and A. Dutta, William Andrew Publishing, 2019.
- 195 A. Y. Coran, Chapter 7 - vulcanization, in *The science and technology of rubber*, ed. J. E. Mark, B. Erman and C. M. Roland, Academic Press, Boston, 4th edn, 2013.
- 196 A. bin Samsuri, 3.33 - degradation of natural rubber and synthetic elastomers, in *Shreir's corrosion*, ed. B. Cottis, M. Graham, R. Lindsay, S. Lyon, T. Richardson, D. Scantlebury and H. Stott, Elsevier, Oxford, 2010.
- 197 A. Dorigato, D. Rigotti and G. Fredi, Recent advances in the devulcanization technologies of industrially relevant sulfur-vulcanized elastomers, *Adv. Ind. Eng. Polym. Res.*, 2023, **6**(3), 288–309, DOI: [10.1016/j.aiepr.2022.11.003](#).
- 198 A. S. Sethulekshmi, A. Saritha and K. Joseph, A comprehensive review on the recent advancements in natural rubber nanocomposites, *Int. J. Biol. Macromol.*, 2022, **194**, 819–842, DOI: [10.1016/j.ijbiomac.2021.11.134](#).
- 199 A. Kawano, K. Yamamoto and J.-i. Kadokawa, Preparation of self-assembled chitin nanofiber-natural rubber composite sheets and porous materials, *Biomolecules*, 2017, **7**(3), 47, DOI: [10.3390/biom7030047](#).
- 200 M. E. Mackay, T. T. Dao, A. Tuteja, D. L. Ho, B. Van Horn, H.-C. Kim and C. J. Hawker, Nanoscale effects leading to non-einstein-like decrease in viscosity, *Nat. Mater.*, 2003, **2**(11), 762–766, DOI: [10.1038/nmat999](#).
- 201 B. Ding, S. Huang, K. Shen, J. Hou, H. Gao, Y. Duan and J. Zhang, Natural rubber bio-nanocomposites reinforced with self-assembled chitin nanofibers from aqueous koh/urea solution, *Carbohydr. Polym.*, 2019, **225**, 115230, DOI: [10.1016/j.carbpol.2019.115230](#).
- 202 J. Yin, J. Hou, S. Huang, N. Li, M. Zhong, Z. Zhang, Y. Geng, B. Ding, Y. Chen, Y. Duan, *et al.*, Effect of surface chemistry on the dispersion and pH-responsiveness of chitin nanofibers/natural rubber latex nanocomposites, *Carbohydr. Polym.*, 2019, **207**, 555–562, DOI: [10.1016/j.carbpol.2018.12.025](#).
- 203 H. Angellier, S. Molina-Boisseau, L. Lebrun and A. Dufresne, Processing and structural properties of waxy maize starch nanocrystals reinforced natural rubber, *Macromolecules*, 2005, **38**(9), 3783–3792, DOI: [10.1021/ma050054z](#).
- 204 Y.-P. Wu, G.-H. Liang and L.-Q. Zhang, Influence of starch on the properties of carbon-black-filled styrene-butadiene rubber composites, *J. Appl. Polym. Sci.*, 2009, **114**(4), 2254–2260, DOI: [10.1002/app.30649](#).
- 205 H. M. Eyssa, D. E. Abulyazied, M. Abdulrahman and H. A. Youssef, Mechanical and physical properties of nanosilica/nitrile butadiene rubber composites cured by



- gamma irradiation, *Egypt. J. Pet.*, 2018, 27(3), 383–392, DOI: [10.1016/j.ejpe.2017.06.004](https://doi.org/10.1016/j.ejpe.2017.06.004).
- 206 E. S. Abdul Rashid, N. B. Muhd Julkapli and W. Abdul Hadi Yehya, Reinforcement effect of nanocellulose on thermal stability of nitrile butadiene rubber (NBR) composites, *J. Appl. Polym. Sci.*, 2018, 135(32), 46594, DOI: [10.1002/app.46594](https://doi.org/10.1002/app.46594).
- 207 M. C. D. Dominic, R. Joseph, P. M. S. Begum, M. Joseph, D. Padmanabhan, L. A. Morris, A. S. Kumar and K. Formela, Cellulose nanofibers isolated from the cuscuta reflexa plant as a green reinforcement of natural rubber, *Polymers*, 2020, 12(4), 814, DOI: [10.3390/POLYM12040814](https://doi.org/10.3390/POLYM12040814).
- 208 A. Paul, K. Sreedevi, S. S. Sharma and V. N. Anjana, Polylactic acid (PLA), in *Handbook of biopolymers*, ed. S. Thomas, A. Ar, C. Jose Chirayil and B. Thomas, Springer Nature Singapore, Singapore, 2022.
- 209 D. Garlotta, A literature review of poly(lactic acid), *J. Polym. Environ.*, 2001, 9(2), 63–84, DOI: [10.1023/A:1020200822435](https://doi.org/10.1023/A:1020200822435).
- 210 M. F. Ashby, Chapter 15 - material profiles, in *Materials and the environment*, ed. M. F. Ashby, Butterworth-Heinemann, Boston, 2nd edn, 2013.
- 211 T. C. Mokhena, J. S. Sefadi, E. R. Sadiku, M. J. John, M. J. Mochane and A. Mtibe, Thermoplastic processing of PLA/cellulose nanomaterials composites, *Polymers*, 2018, 10(12), 1363, DOI: [10.3390/polym10121363](https://doi.org/10.3390/polym10121363).
- 212 R. Scaffaro, L. Botta, F. Lopresti, A. Maio and F. Suter, Polysaccharide nanocrystals as fillers for PLA based nanocomposites, *Cellulose*, 2017, 24(2), 447–478, DOI: [10.1007/s10570-016-1143-3](https://doi.org/10.1007/s10570-016-1143-3).
- 213 S. Farah, D. G. Anderson and R. Langer, Physical and mechanical properties of PLA, and their functions in widespread applications—a comprehensive review, *Adv. Drug Delivery Rev.*, 2016, 107, 367–392, DOI: [10.1016/j.addr.2016.06.012](https://doi.org/10.1016/j.addr.2016.06.012).
- 214 . Mayilswamy and B. Kandasubramanian, Green composites prepared from soy protein, polylactic acid (PLA), starch, cellulose, chitin: A review, *Emergent Mater.*, 2022, 5(3), 727–753, DOI: [10.1007/s42247-022-00354-2](https://doi.org/10.1007/s42247-022-00354-2).
- 215 Z. W. Abdullah, Y. Dong, I. J. Davies and S. Barbhuiya, PVA, PVA blends, and their nanocomposites for biodegradable packaging application, *Polym.-Plast. Technol. Eng.*, 2017, 56(12), 1307–1344, DOI: [10.1080/03602559.2016.1275684](https://doi.org/10.1080/03602559.2016.1275684).
- 216 I. Saini, A. Sharma, R. Dhiman, S. Aggarwal, S. Ram and P. K. Sharma, Grafted sic nanocrystals: For enhanced optical, electrical and mechanical properties of polyvinyl alcohol, *J. Alloys Compd.*, 2017, 714, 172–180, DOI: [10.1016/j.jallcom.2017.04.183](https://doi.org/10.1016/j.jallcom.2017.04.183).
- 217 M. Aslam, M. A. Kalyar and Z. A. Raza, Fabrication of reduced graphene oxide nanosheets doped PVA composite films for tailoring their opto-mechanical properties, *Appl. Phys. A: Mater. Sci. Process.*, 2017, 123(6), 424, DOI: [10.1007/s00339-017-1035-x](https://doi.org/10.1007/s00339-017-1035-x).
- 218 M. Aslam, M. A. Kalyar and Z. A. Raza, Polyvinyl alcohol: A review of research status and use of polyvinyl alcohol based nanocomposites, *Polym.-Plast. Technol. Eng.*, 2018, 58(12), 2119–2132, DOI: [10.1002/pen.24855](https://doi.org/10.1002/pen.24855).
- 219 G. S. A. Suleiman, X. Zeng, R. Chakma, I. Y. Wakai and Y. Feng, Recent advances and challenges in thermal stability of PVA-based film: A review, *Polym. Adv. Technol.*, 2024, 35(2), e6327, DOI: [10.1002/pat.6327](https://doi.org/10.1002/pat.6327).
- 220 X. Zhou, X. Zhou, L. Zhou, M. Jia and Y. Xiong, Nanofillers in novel food packaging systems and their toxicity issues, *Foods*, 2024, 13(13), 2014, DOI: [10.3390/foods13132014](https://doi.org/10.3390/foods13132014).
- 221 S. Moulay, Review: Poly(vinyl alcohol) functionalizations and applications, *Polym.-Plast. Technol. Eng.*, 2015, 54(12), 1289–1319, DOI: [10.1080/03602559.2015.1021487](https://doi.org/10.1080/03602559.2015.1021487).
- 222 N. L. Bhandari, G. Bhandari, K. Bist, D. Adhikari, K. N. Dhakal, R. Adhikari, R. Lach, A. A. Kim, D. J. Yoo and M. B. Poudel, Comparative investigation of fillers loading effect on morphological, micromechanical, and thermal properties of polyvinyl alcohol/cellulosic fillers-based composites, *Int. J. Biol. Macromol.*, 2024, 280, 136192, DOI: [10.1016/j.ijbiomac.2024.136192](https://doi.org/10.1016/j.ijbiomac.2024.136192).
- 223 S. Jiao, X. Yang, X. Zheng, Y. Pei, J. Liu and K. Tang, Effects of charge state of nano-chitin on the properties of polyvinyl alcohol composite hydrogel, *Carbohydr. Polym.*, 2024, 330, 121776, DOI: [10.1016/j.carbpol.2024.121776](https://doi.org/10.1016/j.carbpol.2024.121776).
- 224 J. L. Massingill and R. S. Bauer, Epoxy resins, in *Applied polymer science: 21st century*, ed. C. D. Craver and C. E. Carraher, Pergamon, Oxford, 2000.
- 225 S. Bello, J. Agunsoye, B. Hassan, M. Zebaze Kana and I. Raheem, Epoxy resin based composites, mechanical and tribological properties: A Review, *Tribol. Ind.*, 2015, 37, 500–524.
- 226 M. A. Rashid, M. A. Islam, M. N. Hasan, M. N. N. Anu and M. H. Ikbali, A critical review of dynamic bonds containing curing agents for epoxy resin: Synthesis, challenges, and emerging applications, *Polym. Degrad. Stab.*, 2024, 229, 110980, DOI: [10.1016/j.polymdegradstab.2024.110980](https://doi.org/10.1016/j.polymdegradstab.2024.110980).
- 227 M. Wang, L. Ma, L. Shi, P. Feng, X. Wang, Y. Zhu, G. Wu and G. Song, Chemical grafting of nano-sio₂ onto graphene oxide via thiol-ene click chemistry and its effect on the interfacial and mechanical properties of go/epoxy composites, *Compos. Sci. Technol.*, 2019, 182, 107751, DOI: [10.1016/j.compscitech.2019.107751](https://doi.org/10.1016/j.compscitech.2019.107751).
- 228 Q. Hao, S. Liu, X. Wang, P. Zhang, Z. Mao and X. Zhang, Progression from graphene and graphene oxide to high-performance epoxy resin-based composite, *Polym. Degrad. Stab.*, 2024, 223, 110731, DOI: [10.1016/j.polymdegradstab.2024.110731](https://doi.org/10.1016/j.polymdegradstab.2024.110731).
- 229 H. Dong, Y. Qiao, K. Yang, Y. Zhen, W. Tan, Q. Cheng and Y. Wang, Epoxy resin coatings doped with layered double hydroxide for enhanced anti-permeation performance, *Appl. Clay Sci.*, 2024, 258, 107505, DOI: [10.1016/j.clay.2024.107505](https://doi.org/10.1016/j.clay.2024.107505).
- 230 A. J. Chandran, S. M. Rangappa, I. Suyambulingam and S. Siengchin, Micro/nano fillers for value-added polymer composites: A comprehensive review, *J. Vinyl Addit. Technol.*, 2024, 30(5), 1083–1123, DOI: [10.1002/vnl.22106](https://doi.org/10.1002/vnl.22106).



- 231 T. Aziz, F. Haq, A. Farid, L. Cheng, L. F. Chuah, A. Bokhari, M. Mubashir, D. Y. Y. Tang and P. L. Show, The epoxy resin system: Function and role of curing agents, *Carbon Lett.*, 2024, **34**(1), 477–494, DOI: [10.1007/s42823-023-00547-7](#).
- 232 B. Azimi, P. Nourpanah, M. Rabiee and S. Arbab, Poly (ϵ -caprolactone) fiber: An overview, *J. Eng. Fibers Fabr.*, 2014, **9**(3), 155892501400900320, DOI: [10.1177/155892501400900309](#).
- 233 F. Taghizadeh, M. Heidari, S. Mostafavi, S. M. Mortazavi and A. Haeri, A review of preparation methods and biomedical applications of poly(ϵ -caprolactone)-based novel formulations, *J. Mater. Sci.*, 2024, **59**(24), 10587–10622, DOI: [10.1007/s10853-024-09774-3](#).
- 234 E. V. Antonakou and D. S. Achilias, Recent advances in polycarbonate recycling: A Review of degradation methods and their mechanisms, *Waste Biomass Valorization*, 2013, **4**(1), 9–21, DOI: [10.1007/s12649-012-9159-x](#).
- 235 Y. H. Teow, A. W. Mohammad, S. Ramli, M. S. Sajab and N. Mohamad Mazuki, Potential, of membrane technology for treatment and reuse of water from old mining lakes, *Sains Malays.*, 2018, **47**, 2887–2897, DOI: [10.17576/jsm-2018-4711-32](#).
- 236 A. Tiraferri, M. Malaguti, M. Mohamed, M. Giagnorio and F. J. Aschmoneit, Standardizing practices and flux predictions in membrane science via simplified equations and membrane characterization, *npj Clean Water*, 2023, **6**(1), 58, DOI: [10.1038/s41545-023-00270-w](#).
- 237 N. Alele and M. Ulbricht, Membrane-based purification of proteins from nanoparticle dispersions: Influences of membrane type and ultrafiltration conditions, *Sep. Purif. Technol.*, 2016, **158**, 171–182, DOI: [10.1016/j.seppur.2015.11.031](#).
- 238 F. Christakopoulos, P. M. H. van Heugten and T. A. Tervoort, Additive manufacturing of polyolefins, *Polymers*, 2022, **14**(23), 5147, DOI: [10.3390/polym14235147](#).
- 239 M. Zakaria, M. A. R. Bhuiyan, M. S. Hossain, N. M. M. U. Khan, M. A. Salam and K. Nakane, Advances of polyolefins from fiber to nanofiber: Fabrication and recent applications, *Discover Nano*, 2024, **19**(1), 24, DOI: [10.1186/s11671-023-03945-y](#).
- 240 D. Meng, J. Xie, G. I. N. Waterhouse, K. Zhang, Q. Zhao, S. Wang, S. Qiu, K. Chen, J. Li, C. Ma, *et al.*, Biodegradable poly(butylene adipate-co-terephthalate) composites reinforced with bio-based nanochitin: Preparation, enhanced mechanical and thermal properties, *J. Appl. Polym. Sci.*, 2020, **137**(12), 48485, DOI: [10.1002/app.48485](#).
- 241 C. Zhang, Biodegradable polyesters: Synthesis, properties, applications, in *Biodegradable polyesters*, 2015.
- 242 H. Kim, T. Kim, S. Choi, H. Jeon, D. X. Oh, J. Park, Y. Eom, S. Y. Hwang and J. M. Koo, Remarkable elasticity and enzymatic degradation of bio-based poly(butylene adipate-co-furanoate): Replacing terephthalate, *Green Chem.*, 2020, **22**(22), 7778–7787, DOI: [10.1039/D0GC01688H](#).
- 243 U. M. Shrestha, L. Han, T. Saito, K. S. Schweizer and M. D. Dadmun, Mechanism of soft nanoparticle diffusion in entangled polymer melts, *Macromolecules*, 2020, **53**(17), 7580–7589, DOI: [10.1021/acs.macromol.0c00870](#).
- 244 Y. Liu, J. Zhao, Y. Peng, J. Luo, L. Cao and X. Liu, Comparative study on the properties of epoxy derived from aromatic and heteroaromatic compounds: The role of hydrogen bonding, *Ind. Eng. Chem. Res.*, 2020, **59**(5), 1914–1924, DOI: [10.1021/acs.iecr.9b05904](#).
- 245 J. Z. Manapat, Q. Chen, P. Ye and R. C. Advincula, 3D printing of polymer nanocomposites via stereolithography, *Macromol. Mater. Eng.*, 2017, **302**(9), 1600553, DOI: [10.1002/mame.201600553](#).
- 246 H. Liu, X. Hu, W. Li, M. Zhu, J. Tian, L. Li, B. Luo, C. Zhou and L. Lu, A highly-stretchable and adhesive hydrogel for noninvasive joint wound closure driven by hydrogen bonds, *Chem. Eng. J.*, 2023, **452**, 139368, DOI: [10.1016/j.cej.2022.139368](#).
- 247 N. B. Palaganas, J. D. Mangadlao, A. C. C. de Leon, J. O. Palaganas, K. D. Pangilinan, Y. J. Lee and R. C. Advincula, 3D printing of photocurable cellulose nanocrystal composite for fabrication of complex architectures via stereolithography, *ACS Appl. Mater. Interfaces*, 2017, **9**(39), 34314–34324, DOI: [10.1021/acsami.7b09223](#).
- 248 J. Zhang, F. Mohd Said, N. F. S. Daud and Z. Jing, Present status and application prospects of green chitin nanowhiskers: A comprehensive review, *Int. J. Biol. Macromol.*, 2024, **278**, 134235, DOI: [10.1016/j.ijbiomac.2024.134235](#).
- 249 K. Elumalai, S. Srinivasan and A. Shanmugam, Review of the efficacy of nanoparticle-based drug delivery systems for cancer treatment, *Biomed. Technol.*, 2024, **5**, 109–122, DOI: [10.1016/j.bmt.2023.09.001](#).
- 250 A. Haider, S. Khan, D. N. Iqbal, M. Shrahili, S. Haider, K. Mohammad, A. Mohammad, M. Rizwan, Q. Kanwal and G. Mustafa, Advances in chitosan-based drug delivery systems: A comprehensive review for therapeutic applications, *Eur. Polym. J.*, 2024, **210**, 112983, DOI: [10.1016/j.eurpolymj.2024.112983](#).
- 251 M. E. Hoque, Y. L. Chuan and I. Pashby, Extrusion based rapid prototyping technique: An advanced platform for tissue engineering scaffold fabrication, *Biopolymers*, 2012, **97**(2), 83–93, DOI: [10.1002/bip.21701](#).
- 252 D. Gogoi, M. Kumar and J. Singh, A comprehensive review on hydrogel-based bio-ink development for tissue engineering scaffolds using 3D printing, *Ann. 3D Print. Med.*, 2024, **15**, 100159, DOI: [10.1016/j.stlm.2024.100159](#).
- 253 X. Pei, Y. Li, Y. Deng, L. Lu, W. Li, R. Shi, A. Lei and L. Zhang, Chitin microsphere supported Pd nanoparticles as an efficient and recoverable catalyst for CO oxidation and heck coupling reaction, *Carbohydr. Polym.*, 2021, **251**, 117020, DOI: [10.1016/j.carbpol.2020.117020](#).
- 254 H. Yuan, L. Deng, X. Cai, S. Zhou, Y. Chen and Y. Yuan, Nitrogen-doped carbon sheets derived from chitin as non-metal bifunctional electrocatalysts for oxygen reduction and evolution, *RSC Adv.*, 2015, **5**, 56121–56129, DOI: [10.1039/C5RA05461C](#).

