

Journal of Materials Chemistry C

Materials for optical, magnetic and electronic devices

Accepted Manuscript

This article can be cited before page numbers have been issued, to do this please use: M. Morán-Pedroso, D. O. Tiede, C. Romero-Pérez, M. E. Calvo, J. F. Galisteo-Lopez and H. Míguez, *J. Mater. Chem. C*, 2024, DOI: 10.1039/D4TC02362E.



This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.

Interplay between Connectivity and Passivating Agents in Perovskite Quantum Dot Networks

View Article Online
DOI: 10.1039/D4TC02362E

María Morán-Pedroso[#], David O. Tiede[#], Carlos Romero-Pérez, Mauricio E. Calvo, Juan F. Galisteo-López*, Hernán Míguez*.

Instituto de Ciencias de Materiales de Sevilla (Consejo Superior de Investigaciones Científicas-Universidad de Sevilla), C/Américo Vespucio, 49, Sevilla, 41092, Spain.

*E-mail: juan.galisteo@csic.es, h.miguez@csic.es

#Equal contributors

Introducing quantum dots (QDs) as the active element of an optoelectronic device demands its incorporation in the shape of interconnected arrays that allow for some degree of electronic coupling in order to inject/extract charge carriers. In doing so, beyond reducing the degree of quantum confinement, carriers are exposed to an enhanced defect landscape as they can access adjacent QDs, which is at the origin of the strong reduction of photoluminescence observed in QD solids when compared to that of the isolated QDs. In this work we demonstrate how a proper defect passivating strategy or atmospheric treatment can greatly enhance charge diffusion in a QD film, needed for an optimal carrier injection/extraction demanded for optoelectronic applications, and also improved its stability against external radiation. From a fundamental perspective, we provide evidence showing that trap density distribution, rather than QD size distribution, is mostly responsible for the observed variations in emission decay rates present in the QD networks under analysis.

Keywords: Semiconductor quantum-dot networks, halide perovskites, trap states, lifetime, carrier recombination

1. Intro:

Over the past decade, halide perovskites (HPs) have emerged as a family of semiconductors with potential for applications in diverse fields from photovoltaics, [1] light emission, [2,3] photocatalysis [4] or radiation detection [5] having achieved state-of-the-art performances in many cases. An appropriate choice of precursors allows for attaining conventional three-dimensional (3D) perovskites having the chemical formula ABX_3 (with A being a monovalent cation, B a bivalent metallic cation and X a halide anion), low-dimensional structures comprising n-dimensional inorganic films separated by large organic molecules [6] or other structures such as double perovskites. [7] The choice of the A cation has strong implications on the material stability and can further contribute to reduce structural defects acting as charge traps or affect the electronic bandgap edges. [8] Replacing methylammonium (MA) in the prototypical formulation $MAPbI_3$, employed for record photovoltaic devices in the initial stages of the field, with formamidinium (FA) allowed for a material with enhanced thermal stability and a bandgap close to the optimum value of the Shockley-Queisser limit. This has led to FA-based photovoltaic devices with record efficiencies over the past few years. [9-11] Recently, it has been shown that the Br-containing counterpart $FAPbBr_3$ presents a high phase, moisture and temperature stability, [12] along with high photoluminescence (PL) quantum yield (QY), particularly when synthesized in the shape of quantum dots, [13] which has risen the interest in this material for light emitting applications.



When used in solar cells or light emitting diodes (LEDs), semiconductor QDs must be incorporated in the shape of films, in which a certain degree of electronic coupling between the QDs is necessary to allow for charge injection and transport. [14] Among the different routes to fabricate such QD ensembles, ligand-free synthesis within the pores of nanoporous metal oxide matrices has been recently demonstrated as a suitable approach to prepare HP QD films with optical quality and versatility regarding QD size, composition and concentration. [15-20] When deployed as films, the recombination properties of QD undergo pronounced changes and a bulk-like or isolated QD-like behavior is present depending on QD connectivity. [21] The presence of structural defects strongly affects recombination in QD films as photogenerated carriers have access to a larger defect landscape since they can diffuse across many QDs.

In this work we study the role of crystalline defects in charge carrier recombination of ligand-free FAPbBr₃ QD films grown within metal oxide nanoporous matrices. In order to evaluate the effect of defects of different nature we explore polymeric encasement, which has been recently shown to act as efficient surface trap passivators, [22] as well as different environmental agents which are known to interact with the defect structure of lead halide perovskites. [23,24] These results are interpreted in the light of recent literature dealing with the defect structure of FA-based HPs and the role of different trap states in carrier recombination is discussed. We demonstrate how a proper defect passivating strategy can greatly enhance charge diffusion in a QD film, needed for an optimal carrier injection/extraction demanded for optoelectronic applications, and also improved its stability against external radiation. From a fundamental perspective, we provide evidence showing that trap density distribution, rather than QD size distribution, is mostly responsible for the observed variations in emission decay rates present in the QD networks under analysis.

2. Results and discussion:

2.1 Bare QD films in an inert N₂ atmosphere:

FAPbBr₃ QDs were synthesized within the pores of nanoporous SiO₂ films (see **Figure 1a**) following an already published procedure, [22] detailed in the Supporting Information (S.I.). These samples, labeled FAPbBr₃@SiO₂, were kept in an air-tight chamber through which different gasses can be flown. Initial measurements were performed in a N₂ atmosphere. By increasing the precursor concentration (C_{prec}), we are able to enhance the connectivity between the QDs embedded within the porous scaffold, since the average inter-QD separation is reduced as we increase their number density. [21] This approach also implies a rise of the average NC size, as it can be seen in **Figure 1b-c**, where a reduction in precursor concentration leads to a blueshift in both the absorption edge and PL peak, as expected for NC sizes falling within the quantum confinement regime (estimations for average QD size and separation are given in **Table S1** of the S.I.). It is also observed that the average QD separation affects the time resolved photo luminescence (TRPL): [21,22] the higher the connectivity, the lower the PL intensity measured from FAPbBr₃@SiO₂ samples excited under identical irradiation conditions (see **Figure S2** in the S.I.). Such drop cannot be explained only in terms of a reduced quantum confinement for larger QDs. As QDs get closer, electronic coupling allows charges to diffuse across different QDs, thus expanding the defect landscape they have access to, leading to a reduced PL QY. [21,22] This is further reflected in the PL decay of the different samples (**Figure 1d**) where a lower PL intensity is accompanied by a faster decay, evidencing additional non-radiative trap-assisted



recombination. The measured PL decays were fluence independent for all three samples (**Figure 1d**). While this is expected for the lowest precursor concentration, for which a set of isolated QDs is anticipated, [25] the situation for the interconnected QD array should be different, as a bulk-like behavior has been previously reported. [21] This unexpected behavior will be discussed below after analyzing how the defect structure in our samples is modified via different treatments.


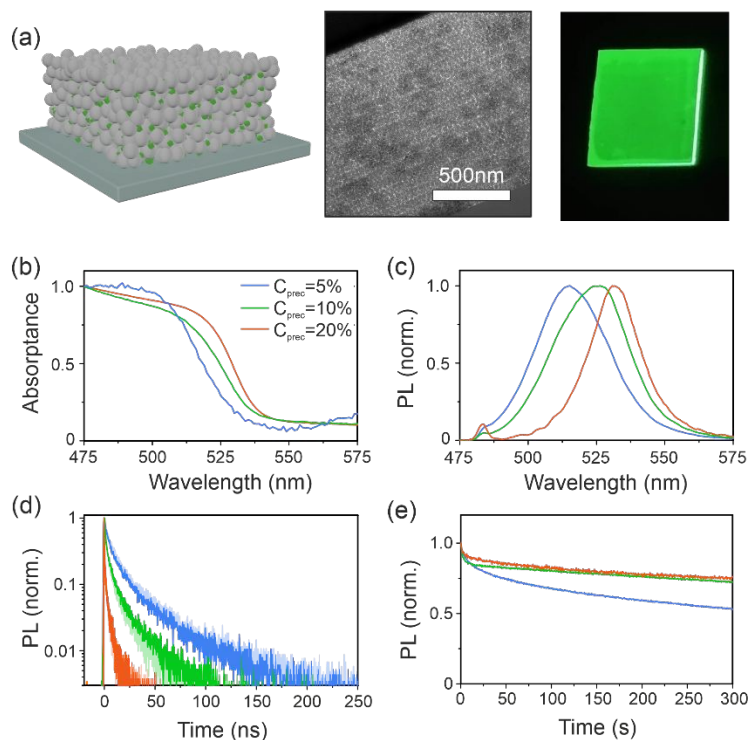



Figure 1: (a) Scheme of a QD array grown within a SiO₂ nanoporous matrix (left), TEM image of a sample infiltrated with a 20% precursor solution (middle) and PL image of a real sample under UV illumination (right). (b) Absorption (normalized at $\lambda=475\text{nm}$), (c) normalized PL, (d) PL decays for high ($3\mu\text{W}$, dark curves) and low (30nW , light curves) and (e) evolution of PL under CW irradiation for samples with different precursor load/interparticle separation. Color code is the same for all four panels: 5%/28nm (blue), 10%/22nm (green) and 20%/15nm (red curve.)

We next monitored the time evolution of the PL under continuous wave (CW) irradiation over longer time-scales (seconds to minutes) to evaluate the photo-stability of the samples (**Figure 1e**). Here an irreversible drop in the PL is observed (**Figure S3**) indicating the onset of material degradation. Notice that for this and all measurements reported in this work, reversibility of photoinduced changes was evaluated in the same atmosphere as irradiation. This change in emission presents clear differences depending on the sample connectivity (see **Figure S4**). If we consider the two extreme cases (5 and 20% precursor concentration) we can see that for the sample consisting of a collection of isolated QDs ($C_{\text{prec}}=5\%$), where the PL spectrum is expected to comprise the convolution of spectra from different QDs, [21] emission quenching is more pronounced and affects particularly the red part of the spectrum (**Figure S4a**), as evidenced by the blueshift of the final emission spectrum compared to the initial one (**Figure S5**). Such behavior points at non-radiative recombination processes occurring in the bulk of the larger



QDs, which emit in the longer wavelength region. For the case of connected QDs (**Figure S4c**), PL quenching is less pronounced and does not involve spectral changes. The latter agrees with the fact that, for QD arrays, PL is expected to come from those QDs with smaller bandgap after a carrier diffusion process following the energy landscape of the array. The photostability of FAPbBr₃ has been dealt with only recently [26] for macroscopic single crystals where a bulk reversible PL darkening was observed and associated with the perovskite lattice decomposition upon irradiation. In such process, byproducts in gas phase can recombine with other byproducts leading to the re-composition of the lattice. The possible origin of our findings will be further discussed when results for different treatments are dealt with.

To gain further insight into the role of structural defects on both the carrier transport in QD films as well as on the observed photo-instability, we next consider identical samples to the ones discussed above, but with the remaining empty volume of the nanopores infiltrated with Poly(methyl methacrylate) (PMMA) after FAPbBr₃ QD synthesis (labeled as FAPbBr₃@PMMA@SiO₂) (see fabrication details in S.I.). This approach, expected to act on surface traps, has been observed in the past to lead to defect passivation and improved PLQY on similar samples. [22] These results are in line with recent ab-initio studies for FAPbI₃, which have shown that, while bulk defects are expected to be more abundant in this material due to a lower defect energy formation, [27] only surface defects occurring for some terminations are expected to introduce deep traps that lead to non-radiative recombination paths. [28] For the case of isolated QDs in FAPbBr₃@PMMA@SiO₂ films with C_{prec}=5%, an enhanced PL is accompanied by a much longer PL decay evidencing the passivation of deep traps. As before, PL decays are independent of fluence as expected for a collection of isolated QDs (**Figure 2a**). For the case of FAPbBr₃@PMMA@SiO₂ films with larger QD load, where increasingly higher QD interconnectivity is expected, we observe that not only PL decays become longer than in the presence of N₂, but also they show a clear fluence dependence (**Figure 2b**). The latter is indicative of a system of interconnected QDs, where recombination dynamics depend on the global population density of charge carriers that can freely move and distribute within the excited area. [21] The stark difference in PL dynamics of FAPbBr₃@PMMA@SiO₂ samples before and after surface passivation with PMMA highlights the detrimental role of deep traps in carrier recombination in QD solids. From these data, it becomes apparent that in the presence of a large density of deep traps (as in FAPbBr₃@SiO₂ samples), carriers generated in one QD recombine non-radiatively at traps either within the QD where they are generated, or at nearby ones where they can diffuse in the case of samples with a higher QD load. In this case, the fact that the carrier can diffuse across QDs increases its defect landscape, effectively leading to a lower PLQY and, since carriers are trapped before they can diffuse far from its origin, to a negligible effect of the excitation fluence. This situation, which explain the results reported in Fig. S2 for FAPbBr₃@SiO₂ samples, is represented in the top panel of **Scheme 1**. On the other hand, as deep traps are passivated, as in FAPbBr₃@PMMA@SiO₂ samples, carriers can diffuse across many QDs eventually finding an opposite charge to recombine with (bottom panel in **Scheme 1**) and presenting a fluence dependence on recombination that reflects its dependence on global population density.




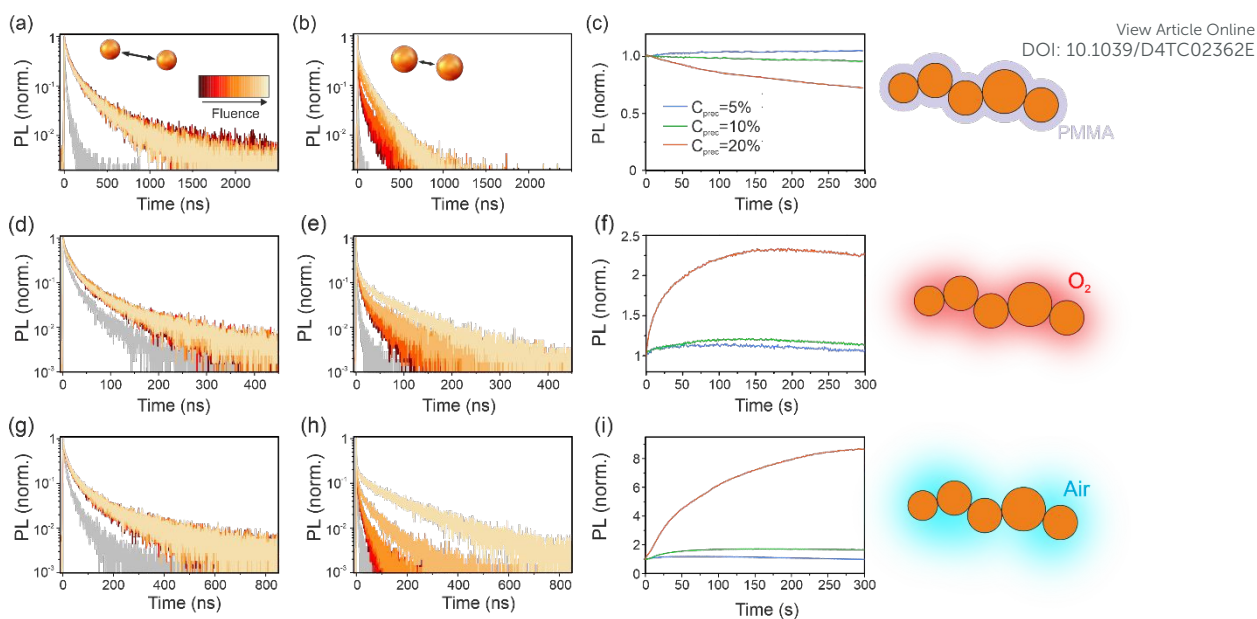


Figure 2: TRPL for samples with (a) low ($C_{\text{prec}}=5\%$) and (b) high ($C_{\text{prec}}=20\%$) connectivity infiltrated with PMMA. (c) Time evolution of PL under CW irradiation for the three different samples under study: $C_{\text{prec}}=5\%$ (blue), $C_{\text{prec}}=10\%$ (green) and $C_{\text{prec}}=20\%$ (red curve). (d-f) and (g-i) show identical data for bare samples exposed to O_2 and humid air respectively. In all cases, the TRPL data for the same samples in N_2 are plotted as grey curves for the sake of comparison.

Trap passivation in $\text{FAPbBr}_3@PMMA@SiO_2$ samples not only influences emission properties but also photostability. Now, samples having the lower QD loads and thus expected to consist of a collection of isolated QDs do not show any variation in PL, evidencing the absence of structural changes taking place (see **Figure 2c**). The fact that irreversible degradation is now absent for this sample indicates that surface traps, beyond acting as deep traps leading to the quenching of PL, also represent seed points where degradation is triggered. For the case of the samples with higher precursor load where QD interconnectivity is expected ($C_{\text{prec}}=20\%$) we now observe a photo-induced PL darkening that is reversible when CW irradiation is removed (see **Figure S6**). Two types of mechanisms have been reported for reversible photodarkening in HPs. A decomposition of the HP lattice into its precursors and further formation of gaseous byproducts was invoked in Ref. 26 as the process leading to reversible darkening of FAPbBr_3 single crystals when excitation is performed in the bulk and byproducts cannot escape the crystal. If this mechanism was behind our observations, PL darkening should be observed for all QD films regardless of their load. On the other hand, Motti and co-workers proposed [29] the formation of I_2 upon annihilation of halide-related Frenkel pairs as a possible origin for PL quenching. This would explain the present results in the event that halide defects could migrate across different QDs in our interconnected samples. Br_2 forming as a result of the annihilation of Frenkel pairs could not escape the film due to the presence of the PMMA film and the process could be reversed upon removing the CW irradiation.



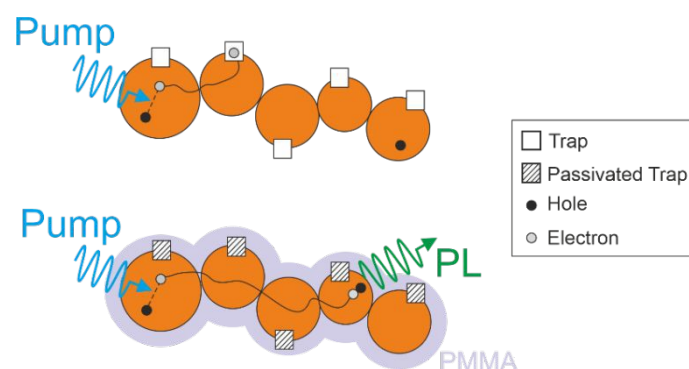

View Article Online
DOI: 10.1039/D4TC02362E

Scheme 1: Proposed picture for carrier recombination and the role of deep traps. (Top) for bare QD films carriers generated in a given QD rapidly recombine non-radiatively at a trap within the same or an adjacent QD. (Bottom) Upon passivation of the surface traps, carriers can diffuse across the QD film before recombining.

Next, we consider the surrounding atmosphere as a treatment with potential to modify the defect landscape in $\text{FAPbBr}_3@SiO_2$ samples. The role of the environment on HP photophysics and stability has been extensively studied over the past decade. There is nowadays a consensus that certain gases can strongly modify the defect landscape in LHP at the expense of reducing material stability so that a compromise must be attained if one wants to employ this approach to optimize their optoelectronic properties. [30,31] In this work we have explored the role of O_2 and moisture. We first exposed our sample to a continuous flow of dry O_2 (<3ppm background humidity according to the provider, Linde) for 5 minutes prior to study their optical properties. TRPL data shows a slight slowing in the PL decays for all samples under study (**Figure 2d-e**). This is likely related with the interaction of O_2 with a certain population of deep traps, as evidenced by the fact that TRPL becomes again fluence dependent for the highly connected sample. This interaction takes place via weak binding of O_2 to FAPbBr_3 (physisorption) as the effect is rapidly reversed upon restoring a N_2 atmosphere.

More evident changes appear when the effect of O_2 is combined with that of CW irradiation and we monitor the sample PL (**Figure 2f**). Here we can observe that samples with small connectivity barely experience any change in their PL but highly connected samples undergo a >2 fold enhancement, pointing to the photoinduced interaction of deep traps with this reactive atmosphere. As with the case of samples infiltrated with PMMA, no spectral changes were observed for the highly connected samples (**Figure S7**). While reports on the interaction of O_2 with FAPbBr_3 are lacking, recent evidence showing emission changes of other MA-based HP may hold the key to explain the present results. In particular, a photoinduced PL rise in the presence of O_2 has been previously reported [32,33,34,35,36,37,38] and associated with the formation of superoxide species [35,36, 37,38] which may interact with surface halide vacancies which, as in the present case, act as deep traps. This effect is reversible over times longer than those needed for activation following a two-step process with different time scales of seconds and tens of minutes (see **Figure S8**).

Finally, $\text{FAPbBr}_3@SiO_2$ samples were exposed to humid air to explore the combined action of O_2 and moisture. H_2O is known to accelerate phase instability for FAPbI_3 while, for the case of FAPbBr_3 , is known to have little effect on its stability. [12] Further, the combination of H_2O and



O₂ has been recently reported to lead to accelerated degradation in iodide based mixed Cs-Pb HPs. [39] As in the case of exposure to pure O₂, the TRPL of all samples undergo a slowing of the PL dynamics (**Figure 2g**), although more pronounced. For the more connected QDs, a significantly stronger fluence dependence is observed (**Figure 2h**), indicating a larger population of defects interacting with H₂O and O₂ than with O₂ alone. Again, irradiating with CW light in the presence of humid air leads to more dramatic changes in emission, as shown in **Figure 2i**. Here a small (ca. 10-30%) PL enhancement is observed for the case of isolated QDs while connected ones undergo a remarkable 10-fold enhancement. Resorting to previous reports for MA-based HP, the combined action of H₂O and light has been suggested to improve the HP emission according to two mechanisms. Brenes and co-workers proposed the partial dissolution of the HP lattice at the surface, leading to the formation of an amorphous film that could act as a passivator. [36, 38]. Alternatively, other oxide species can form at the HP surface, namely peroxide [37] and hydrogen peroxide. [40] These species can further react with uncoordinated lead, in different charge states, present at the HP surface which can be oxidized into lead oxide. [37,40] Both processes would lead to the irreversible passivation of traps and thus a different mechanism is expected in our case as, while much longer recovery times are observed than when using only O₂, (see **Figure S9**) our sample returns to its initial low PL state. Hence, further work will be needed in order to unveil the photoinduced processes involving water that lead to such efficient interaction of atmospheric agents with traps in FAPbBr₃ QDs.

For the case of FAPbBr₃@SiO₂ films exposed to non-inert atmospheres, while the population of traps interacting with the surrounding atmosphere is expected to be the same for all different samples, the photoinduced PL enhancement is more pronounced for the case of connected QDs. The reason behind this observation is the stronger effect of traps on the sample emission for connected QD arrays (see **Scheme 1**), where a larger defect landscape arises as a consequence of carriers being able to diffuse across several QDs. To evaluate and quantify the role of the different treatments, we consider the C_{prec}=5% samples, i.e. those having the lowest connectivity, where fluence does not play a role in the emission. We compare the PL decay under different atmospheres as representative of the weight of non-radiative processes. To extract a parameter for comparison we fit the TRPL to a lognormal distribution of decays, ρ(Γ) (see **Figure 3a** for the FAPbBr₃@PMMA@SiO₂ sample, and **Figure S10** for FAPbBr₃@SiO₂ exposed to different atmospheres). As previously reported, [21] the mode of the distribution (Γ_m) represents an average value of the decay rate of the distribution of QDs. The width of this distribution will be affected by the size dispersion but could also be influenced by the defect distribution in different QD. From the comparison of all Γ_T it becomes clear that the treatment that more efficiently de-activates deep traps is that of PMMA (**Figure 3b**), further highlighting the detrimental role of surface defects in this material. Additional information can be extracted from a comparison of the actual decay rate distribution for QD films in N₂ and with the different treatments (see **Figure 3c**). The average value of the decay rate distribution Γ_T comprises a radiative (Γ_R) and a non-radiative (Γ_{NR}) component. While the former is assumed to be identical for all samples, the latter depends on the defect landscape as:

$$\Gamma_{NR} = \sigma_{trap} v_{th} N_T$$

Hence the non-radiative recombination is directly affected by the number of trap sites in the system, (N_T) their capture cross section (σ_{trap}) and the thermal velocity of the free charge carriers



(v_{th}), the latter remaining unchanged for the different treatments. The reduction of the number of trap sites can be explained as halide related defects interact with environmental gas molecules, while a change in σ_{trap} can be assigned to a change in the energy level of a trap state, such as the one predicted for interstitial iodide in the presence of O_2 . [41] To shed more light into the exact origin of the reduction in Γ_{NR} , the distribution of recombination rates is analyzed in the following. Here it can be seen that adding the polymer as a passivating agent not only reduces the average decay rate, evidencing the reduction of non-radiative recombination paths, but also homogenizes the PL dynamics of the QD distribution as its width is reduced by an order of magnitude (**Figure 3c**). This latter fact further evidences that trap density distribution, rather than size distribution, is mostly responsible for the observed variation in decay rates in the present QD films.

The distribution of decay rates can be associated to both the non-radiative (Γ_{NR}) and radiative (Γ_R) components, where non-radiative components are expected to show both larger decay times and a broader distribution of decay times. As the different treatments (atmosphere and PMMA) are acting on the sample, a reduction of the decay rate distribution is observed (**Figure 3c**). The continuous decrease of both the average values of the distribution and its width is observed as surface defects interact with one of the abovementioned agents. Since both parameters decrease in the same monotonic way, the global reduction in decay rates can be solely assigned to the reduction in the number of trap states. A significant change in the distribution of defect states would involve a more drastic change in the width $\Delta\Gamma$, rather than in the mean rate Γ_m . Further, an assignment of the broad distribution to a size and energy dispersion due to the heterogeneity of the crystals is discarded, as in this case, $\Delta\Gamma$ and Γ_m would not follow identical dynamics.


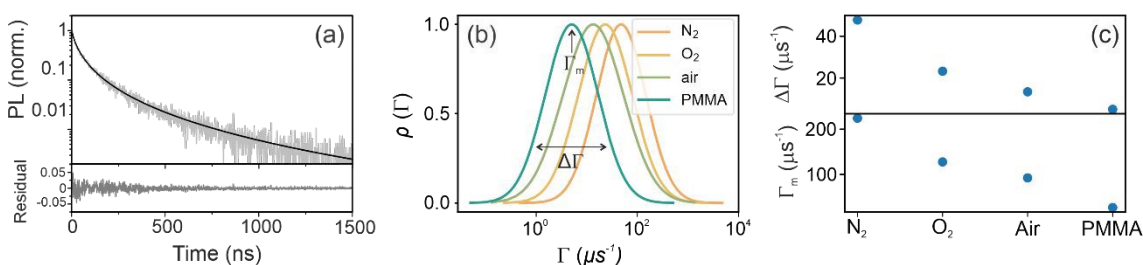


Figure 3: (a) TRPL for a sample with low connectivity ($C_{prec}=5\%$) infiltrated with PMMA. Grey (black) curve represents experimental data (fit to a lognormal distribution of decay rates). Bottom panel shows the residual of the fit. (b) Lognormal distribution of decay rates from fit of experimental data for samples exposed to different treatments, as indicated in the horizontal axis. (c) Width (top) and average value (bottom panel) of the distributions of the $C_{prec}=5\%$ sample under the different treatments.



Conclusions:

In summary, we have explored the role of defects in charge recombination for HP QD films using ligand-free QDs fabricated within the pores of silicon oxide matrices. The use of different treatments evidences that surface traps are a main source of non-radiative recombination in FA-based HP and its presence constitutes a burden for carrier transport in QD films. Thus, a proper passivation approach represents an efficient avenue for avoiding this issue and improving the performance of devices containing these materials. Further, surface traps have also been shown to represent a source of instability leading to irreversible material degradation in the absence of appropriate passivation. Finally, we have presented the first evidence of photo-induced PL activation in FA-based HP as a consequence of the combined action of irradiation and exposure to reactive atmospheres. This latter effect is mainly related with defect reactivity at the HP surface and thus previous reports dealing with larger samples could not observe it.

Acknowledgements:

We are thankful for the financial support of the Spanish Ministry of Science and Innovation under grants PID2020-116593RB-I00, funded by MCIN/AEI/10.13039/501100011033 and TED2021-129679B-C22, funded by MCIN/AEI/ 10.13039/501100011033 and by Unión Europea NextGenerationEU/PRTR. We also acknowledge the support by the Junta de Andalucía under grant P18-RT-2291 (FEDER/UE). DOT acknowledge financial support from the European Union's Horizon 2020 research and innovation program under the Marie Skłodowska-Curie grant agreement No 956270 (Persephone).

Data availability

The data underlying this study are openly available in the Digital CSIC repository: [http://\(to be defined\)](http://(to be defined)). The codes used to fit the TRPL data are provided at <https://github.com/Multifunctional-Optical-Materials-Group>.

-
- ¹ Jena, A. K.; Kulkarni, A.; Miyasaka, T. Halide Perovskite Photovoltaics: Background, Status, and Future Prospects. *Chem. Rev.* **2019**, *119*, 3036–3103.
 - ² Ji, K.; Anaya, M.; Abfalterer, A.; Stranks, S. D. Halide Perovskite Light-Emitting Diode Technologies. *Adv. Opt. Mater.* **2021**, *9*, 2002128.
 - ³ Lei, L.; Dong, Q.; Gundogdu, K.; So, F. Metal Halide Perovskites for Laser Applications. *Adv. Funct. Mater.* **2021**, *31*, 2010144.
 - ⁴ Huang, H.; Pradhan, B.; Hofkens, J.; Roeffaers, M. B. J.; Steele, J. A. Solar-Driven Metal Halide Perovskite Photocatalysis: Design, Stability, and Performance. *ACS Energy Lett.* **2020**, *5*, 1107–1123.
 - ⁵ Wei, H.; Huang, J. Halide Lead Perovskites for Ionizing Radiation Detection. *Nat. Commun.* **2019**, *10*, 1066.
 - ⁶ Lin, H.; Zhou, C.; Tian, Y.; Siegrist, T.; Ma, B. Low-Dimensional Organometal Halide Perovskites. *ACS Energy Lett.* **2018**, *3*, 54–62.



- ⁷ Muscarella, L. A.; Hutter, E. M. Halide Double-Perovskite Semiconductors beyond Photovoltaics. *ACS Energy Lett.* **2022**, *7*, 2128–2135.
- ⁸ Lee, J.; Tan, S.; Seok, S.; Yang, Y.; Park, N. Rethinking the A cation in halide perovskites. *Science* **2022**, *375*, eabj1186
- ⁹ Jeong, M.; Choi, I. W.; Go, E. M.; Cho, Y.; Kim, M.; Lee, B.; Jeong, S.; Jo, Y.; Choi, H. W.; Lee, J.; Bae, J. H.; Kwak, S. K.; Kim, D. S.; Yang, C. Stable Perovskite Solar Cells with Efficiency Exceeding 24.8% and 0.3-V Voltage Loss. *Science* **2020**, *369*, 1615–1620.
- ¹⁰ Jeong, J.; Kim, M.; Seo, J.; Lu, H.; Ahlawat, P.; Mishra, A.; Yang, Y.; Hope, M. A.; Eickemeyer, F. T.; Kim, M.; Yoon, Y. J.; Choi, I. W.; Darwich, B. P.; Choi, S. J.; Jo, Y.; Lee, J. H.; Walker, B.; Zakeeruddin, S. M.; Emsley, L.; Rothlisberger, U.; Hagfeldt, A.; Kim, D. S.; Grätzel, M.; Kim, J. Y. Pseudo-Halide Anion Engineering for α -FAPbI₃ Perovskite Solar Cells. *Nature* **2021**, *592*, 381–385.
- ¹¹ Min, H.; Lee, D. Y.; Kim, J.; Kim, G.; Lee, K. S.; Kim, J.; Paik, M. J.; Kim, Y. K.; Kim, K. S.; Kim, M. G.; Shin, T. J.; Il Seok, S. Perovskite Solar Cells with Atomically Coherent Interlayers on SnO₂ Electrodes. *Nature* **2021**, *598*, 444–450.
- ¹² Raval, P.; Kennard, R. M.; Vasileiadou, E. S.; Dahlman, C. J.; Spanopoulos, I.; Chabinyk, M. L.; Kanatzidis, M.; Manjunatha Reddy, G. Understanding Instability in Formamidinium Lead Halide Perovskites: Kinetics of Transformative Reactions at Grain and Subgrain Boundaries. *ACS Energy Lett.* **2022**, *7*, 1534–1543.
- ¹³ Bhatia, H.; Ghosh, B.; Debroye, E. Colloidal FAPbBr₃ Perovskite Nanocrystals for Light Emission: What's Going On?. *J. Mater. Chem. C* **2022**, *10*, 13437–13461.
- ¹⁴ Zhang, Y.; Wu, G.; Liu, F.; Ding, C.; Zou, Z.; Shen, Q. Photoexcited Carrier Dynamics in Colloidal Quantum Dot Solar Cells: Insights into Individual Quantum Dots, Quantum Dot Solid Films and Devices. *Chem. Soc. Rev.* **2020**, *49*, 49–84.
- ¹⁵ Dirin, D.N.; Protesescu, L.; Trummer, D.; Kochetygov, I.V.; Yakunin, S.; Krumeich, F.; Stadie, N.P.; Kovalenko, M.V. Harnessing Defect-Tolerance at the Nanoscale: Highly Luminescent Lead Halide Perovskite Nanocrystals in Mesoporous Silica Matrixes, *Nano Lett.* **2016**, *16*, 5866–5874.
- ¹⁶ Anaya, M.; Rubino, A.; Rojas, T. C.; Galisteo-López, J. F.; Calvo, M. E.; Míguez, H. Strong Quantum Confinement and Fast Photoemission Activation in CH₃NH₃PbI₃ Perovskite Nanocrystals Grown within Periodically Mesoporous Films. *Adv. Opt. Mater.* **2017**, *5*, 1601087.
- ¹⁷ Malgras, V.; Tominaka, S.; Ryan, J.W.; Henzie, J.; Takei, T.; Ohara, K.; Yamauchi, Y. Observation of Quantum Confinement in Monodisperse Methylammonium Lead Halide Perovskite Nanocrystals Embedded in Mesoporous Silica, *J. Am. Chem. Soc.* **2016**, *138*, 13874–13881.
- ¹⁸ Demchyshyn, S.; Roemer, J.M.; Groi, H.; Heilbrunner, H.; Ulbricht, C.; Apaydin, D.; Böhm, A.; Rütt, U.; Bertram, F.; Hesser, G.; Scharber, M.C.; Sariciftci, N.S.; Nickel, B.; Bauer, S.; Glowacki, E.D.; Kaltenbrunner, M. Confining Metal-halide Perovskites in Nanoporous Thin Films. *Sci. Adv.* **2017**, *3*, e1700738.
- ¹⁹ Malgras, V.; Henzie, J.; Takei, T.; Yamauchi, Y.; Stable Blue Luminescent CsPbBr₃ Perovskite Nanocrystals Confined in Mesoporous Thin Films. *Angew. Chem. Int. Ed.* **2018**, *57*, 8881–8885.
- ²⁰ Rubino, A.; Calì, L.; García-Bennett, A.; Calvo, M. E.; Míguez, H. Mesoporous Matrices as Hosts for Metal Halide Perovskite Nanocrystals. *Advanced Optical Materials*, **2020**, *8*, 1901868.



- ²¹ Tiede, D.O.; Romero-Pérez, C.; Koch, K.A.; Ucer, B.; Calvo, M.E.; Kandada, A.R.K.; Galisteo-López, J.F.; Míguez, H. Effect of Connectivity on the Carrier Transport and Recombination Dynamics of Perovskite Quantum-Dot Networks. *ACS Nano* **2024**, *18*, 2325-2334.
- ²² Romero-Pérez, C.; Fernández-Delgado, N.; Herrera-Collado, M.; Calvo, M. E.; Míguez, H. Ultrapure Green High Photoluminescence Quantum Yield from FAPbBr₃ Nanocrystals Embedded in Transparent Porous Films. *Chem. Mater.* **2023**, *35*, 14, 5541–5549.
- ²³ Andaji-Garmaroudi, Z.; Anaya, M.; Pearson, A. J.; Stranks, S. D. Photobrightening in Lead Halide Perovskites: Observations, Mechanisms, and Future Potential. *Adv. Energy Mater.* **2020**, *10*, 1903109.
- ²⁴ Galisteo-López, J. F.; Calvo, M. E.; Míguez, H. The Complex Interplay of Lead Halide Perovskites with their Surroundings. *Adv. Opt. Mater.* **2021**, *9*, 2100133.
- ²⁵ Akkerman, Q. A.; Nguyen, T. P.; Boehme, S. C.; Montanarella, F.; Dirin, D. N.; Wechsler, P.; Beiglbök, F.; Rainò, G.; Erni, R.; Katan, C.; Even, J.; Kovalenko, M. V. Controlling the Nucleation and Growth Kinetics of Lead Halide Perovskite Quantum Dots. *Science*, **2022**, *377*, 1406-1412.
- ²⁶ Ceratti, D. R.; Rakita, Y.; Cremonesi, L.; Tenne, R.; Kalchenko, V.; Elbaum, M.; Oron, D.; Potenza, M.A.C.; Hodes, G.; Cahen, D. Self Healing inside APbBr₃ Halide Perovskite Crystals. *Adv. Mater.* **2018**, *30*, 1706273.
- ²⁷ Tan, S.; Yavuz, I.; Weber, M. H.; Huang, T.; Chen, C.-H.; Wang, R.; Wang, H.-C.; Ko, J. H.; Nuryyeva, S.; Xue, J.; et al. Shallow Iodine Defects Accelerate the Degradation of α -phase Formamidinium Perovskite. *Joule* **2020**, *4*, 2426–2442.
- ²⁸ Oner, S. M.; Sezen, E.; Yordanli, M. S.; Karakoc, E.; Deger, C.; Yavuz, I. Surface Defect Formation and Passivation in Formamidinium Lead Triiodide (FAPbI₃) Perovskite Solar Cell Absorbers. *J. Phys. Chem. Lett.* **2022**, *13*, 324–330.
- ²⁹ Motti, S. G.; Meggiolaro, D.; Barker, A. J.; Mosconi, E.; Perini, C. A. R.; Ball, J. M.; Gandini, M.; Kim, M.; De Angelis, F.; Petrozza, A. Controlling Competing Photochemical Reactions Stabilizes Perovskite Solar Cells. *Nat. Photonics* **2019**, *13*, 532–539.
- ³⁰ Andaji-Garmaroudi, Z.; Anaya, M.; Pearson, A. J.; Stranks, S. D. Photobrightening in Lead Halide Perovskites: Observations, Mechanisms, and Future Potential. *Adv. Energy Mater.* **2020**, *10*, 1903109.
- ³¹ Galisteo-López, J. F.; Calvo, M. E.; Míguez, H. The Complex Interplay of Lead Halide Perovskites with their Surroundings. *Adv. Opt. Mater.* **2021**, *9*, 2100133.
- ³² Galisteo-López, J. F.; Anaya, M.; Calvo, M. E.; Míguez, H. Environmental Effects on the Photophysics of Organic–Inorganic Halide Perovskites. *J. Phys. Chem. Lett.* **2015**, *6*, 2200–2205.
- ³³ Tian, Y.; Peter, M.; Unger, E.; Abdellah, M.; Zheng, K.; Pullerits, T.; Yartsev, A.; Sundström, V.; Scheblykin, I. G. Mechanistic Insights into Perovskite Photoluminescence Enhancement: Light Curing with Oxygen can Boost Yield Thousandfold. *Phys. Chem. Chem. Phys.* **2015**, *17*, 24978–24987.
- ³⁴ Motti, S. G.; Gandini, M.; Barker, A. J.; Ball, J. M.; Srimath Kandada, A. R.; Petrozza, A. Photoinduced Emissive Trap States in Lead Halide Perovskite Semiconductors. *ACS Energy Lett.* **2016**, *1*, 726–730.
- ³⁵ Feng, X.; Su, H.; Wu, Y.; Wu, H.; Xie, J.; Liu, X.; Fan, J.; Dai, J.; He, Z. Photon-generated Carriers Excite Superoxide Species Inducing Long-term Photoluminescence Enhancement of MAPbI₃ Perovskite Single Crystals. *J. Mater. Chem. A* **2017**, *5* (24), 12048–12053.



- ³⁶ Brenes, R.; Guo, D.; Osherov, A.; Noel, N. K.; Eames, C.; Hutter, E. M.; Pathak, S. K.; Niroui, F.; Friend, R. H.; Islam, M. S. Metal Halide Perovskite Polycrystalline Films Exhibiting Properties of Single Crystals. *Joule* **2017**, *1*, 155–167.
- ³⁷ Anaya, M.; Galisteo-López, J. F.; Calvo, M. E.; Espinós, J. P.; Míguez, H. Origin of Light-Induced Photophysical Effects in Organic Metal Halide Perovskites in the Presence of Oxygen. *J. Phys. Chem. Lett.* **2018**, *9* (14), 3891–3896.
- ³⁸ Brenes, R.; Eames, C.; Bulović, V.; Islam, M. S.; Stranks, S. D. The Impact of Atmosphere on the Local Luminescence Properties of Metal Halide Perovskite Grains. *Adv. Mater.* **2018**, *30*, 1706208.
- ³⁹ Hidalgo, J.; Kaiser, W.; An, Y.; Li, R.; Oh, Z.; Castro-Méndez, A. F.; LaFollette, D. K.; Kim, S.; Lai, B.; Breternitz, J.; Schorr, S.; Perini, C. A. R.; Mosconi, E.; De Angelis, F.; Correa-Baena, J. P. Synergistic Role of Water and Oxygen Leads to Degradation in Formamidinium-Based Halide Perovskites. *J. Am. Chem. Soc.* **2023**, *145*, 24549–24557.
- ⁴⁰ Godding, J. S. W.; Ramadan, J. A.; Lin, Y.-H.; Schutt, K.; Snaith, H. J.; Wenger, B. Oxidative Passivation of Metal Halide Perovskites. *Joule* **2019**, *3* (11), 2716–2731.
- ⁴¹ D.; Mosconi, E.; De Angelis, F. Mechanism of Reversible Trap Passivation by Molecular Oxygen in Lead-Halide Perovskites. *ACS Energy Lett.* **2017**, *2*, 2794–2798.



Interplay between Connectivity and Passivating Agents in Perovskite Quantum Dot Networks

View Article Online
DOI: 10.1039/D4TC02362E

María Morán-Pedroso, David O. Tiede, Carlos Romero-Pérez, Mauricio E. Calvo, Juan F. Galisteo-López, Hernán Míguez.

Instituto de Ciencias de Materiales de Sevilla (Consejo Superior de Investigaciones Científicas-Universidad de Sevilla), C/Américo Vespucio, 49, Sevilla, 41092, Spain.

Data Availability

The data underlying this study are openly available in the Digital CSIC repository: <https://digital.csic.es/>. The codes used to fit the TRPL data are provided at <https://github.com/Multifunctional-Optical-Materials-Group>.

(A DOI is generated by Digital CSIC in case the manuscript is accepted)

