

Environmental Science Nano

Accepted Manuscript

This article can be cited before page numbers have been issued, to do this please use: R. Svensson, J. García Martínez, M. T. Ekvall, A. Kraus, K. Bernfur, T. Leiding, M. Lundqvist and T. Cedervall, *Environ. Sci.: Nano*, 2025, DOI: 10.1039/D4EN00795F.



This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.

Environmental significance

View Article Online
DOI: 10.1039/D4EN00795F

Our understanding of the effect of ultraviolet radiation (UV) on the breakdown of nanoplastic in nature is negligible. While the effects on larger plastics have been studied there is, to our knowledge, a current gap when it comes to nanoplastic (<100 nm) breakdown and how this UV mediated breakdown may affect the material and the potential toxicity of the material. We show how UV exposure affects polystyrene nanoparticles, resulting in particle breakdown and a reduced toxicity of an amine-modified particle that is toxic towards the freshwater zooplankter *Daphnia magna* in its pristine form. We also show that a complex toxic mixture of small molecules is released during the breakdown process. This study highlights potential outcomes of UV mediated nanoplastic breakdown.

Environmental Science: Nano Accepted Manuscript

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

Open Access Article. Published on 17 October 2024. Downloaded on 29/12/2024 05:27:39.
This article is licensed under a Creative Commons Attribution 3.0 Unported Licence.



UV-B degradation affects nanoplastic toxicity and leads to release of small toxic substances

Mikael T. Ekvall^{a,b,§}, Raluca Svensson^a, Josep García Martínez^c, Annette Kraiss^c, Katja Bernfur^a, Thom Leiding^a, Martin Lundqvist^{a,b,§} and Tommy Cedervall^{a,b*}

^a *Biochemistry and Structural, Biology, Lund University, P.O. Box 124, SE-221 00, Lund, Sweden*

^b *NanoLund, Lund University, P.O. Box 118, SE-221 00, Lund, Sweden.*

^c *Centre for Analysis and Synthesis (CAS), Lund University, Lund, Sweden*

^{*} *Corresponding author*

[§] *Equal contribution*

Abstract

Fragmented micro- and nanoplastics are widespread pollutants with adverse effects on the environment. However, the breakdown process does not end with micro- and nanoplastics but is expected to continue until carbon dioxide has been formed. During this process the plastics will undergo chemical changes and small molecules may be released. We have broken down small amine-modified (\varnothing 53 nm) and carboxyl-modified (\varnothing 62 nm) polystyrene nanoparticles by UV-B irradiation during 100 days. We see a decreasing size and an oxidation of the nanoparticles over time. Simultaneously, the acute toxicity to zooplankton *Daphnia magna* decreases. The UV-B irradiation releases small, dissolved molecules that are toxic to *Daphnia magna*. The dissolved molecules include aminated alkyls, styrene remnants and

secondary circularization products. The study show that UV-B radiation can change the original toxicity of nanoplastics and release new toxic substances.

View Article Online
DOI: 10.1039/D4EN00795F

Introduction

Micro- and nanoplastic particles are today ubiquitous and present in all compartments of the natural environment where they can be retained and taken up by organisms and induce ecotoxicological issues, both direct toxicological effect at species level and through cascading effects¹⁻³. Nanoplastics are defined as plastic pieces that have been degraded in nature to a size below 100 nm⁴ or 1 µm⁵. Nanoplastics are, due to their small size, difficult to isolate in nature but were first demonstrated in the Atlantic in 2017⁶. Studies confirm the abundance of nanoplastics and suggest there is up to 0.5 mg/L nanoplastics in Swedish lakes close to cities⁷. The size distribution between micro- and nanoplastics has recently been measured in mussels with the interesting result that the mass (187 ng/mg) of the nanoplastic fraction (20-200nm) is similar to the mass (216 ng/mg) of the microplastic fraction (≥2.2 µm)⁸. In a comparison based on particle number or surface area, nanoplastics will dominate and may therefore have a greater impact on biological effects. For example, small carboxylated polystyrene nanoparticles inhibit plasma coagulation by binding to the active site in Factor12a int the coagulation cascade, whereas larger particles activate coagulation by providing a surface for the activation complex⁹.

Polystyrene is the 6th most consumed plastics¹⁰, but none or only small amounts of polystyrene nanoplastics were found in Swedish lakes⁷. However, in mussels, the ratio

1
2
3 followed the expected pattern for polystyrene nanoplastics ⁸. Polystyrene nanoplastics have
4 also been found in soil ¹¹. The release of polystyrene nanoplastics after ultraviolet (UV)
5 irradiation of polystyrene coffee cup lids was shown in 2016 ¹², and from plastic sheets and
6 boxes in 2023 ^{13, 14}. The release of micro- and nanoplastics from commercial micro-sized
7 polystyrene beads after UV irradiation has been demonstrated ^{15, 16}. Furthermore, the
8 release of nanoplastics from expanded polystyrene foam and coffee cup lids after being
9 subjected to mechanical force was shown in 2019 ¹⁷ and, in 2021, from expanded
10 polystyrene after mild mechanical forces mimicking the mechanical friction in the ocean ¹⁸.
11 The nanoplastics formed from the mechanical degradation were chemically transformed, as
12 compared to the starting material, and a higher level of oxygen was found in the formed
13 nanoparticles ^{17, 18}. Furthermore, styrene oligomers have been detected worldwide in sand
14 and seawater at mean concentrations of 3679 ± 8199.2 ng/g and 5.1 ± 6.4 ng/L, respectively
15 ¹⁹. In the Pacific Ocean, the mean concentration of styrene oligomers has been measured to
16 1.48 $\mu\text{g/L}$ and 1.32 $\mu\text{g/L}$ in surface water and deep water, respectively ²⁰. The styrene
17 oligomers are expected to originate from polystyrene indicating that the presence of styrene
18 oligomers is a result of the degradation occurring in nature.

19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

Many possible intermediate breakdown products can originate from polystyrene subjected to UV irradiation during the degradation process, but continued UV irradiation ultimately results in carbon dioxide ²¹. The mechanisms behind UV mediated degradation of polystyrene have been studied for decades and are reviewed in for example Yousif and Haddard, 2013 ²², and later from a micro-/nanoplastics in the environment perspective by Andrady, et al., 2022 ²³. High intensity UV irradiation of carboxyl-modified polystyrene

1
2
3 beads, 0.1 to 2.5 μm continued the degradation processes until the polystyrene was totally
4 broken down to mostly carbon dioxide and other volatile compounds ²⁴. Volatile compounds
5
6 broken down to mostly carbon dioxide and other volatile compounds ²⁴. Volatile compounds
7
8 such as benzene, toluene, styrene and phenol have been detected after UV irradiation ²⁵. In
9
10 addition, cyclization products were found after long-term irradiation of polystyrene films ²⁶.
11
12 Different additives and stabilizers will also affect the resulting degradation products ^{21, 22}. In
13
14 conclusion, it seems likely that there is a complex mixture of various compounds released
15
16 during the UV-mediated degradation of polystyrene.
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

An interesting aspect of micro- and especially nanoplastics is that the penetration depth of the UV radiation is much larger than the particle diameter ²⁷, which also affects the energy absorption of the polystyrene. An effect of this may have been seen in the degradation of carboxyl-modified polystyrene microbeads as they were reported to start to degrade from the inside first and that decreasing diameter of the particles came later in the degradation process ²⁴, whereas other studies have only reported a shrinking diameter ^{15, 28}, suggesting that the particles are degraded from the outside. The detection of only surface oxidation following short-term irradiation of radiolabeled 230 nm polystyrene nanoparticles indicates that surface degradation is occurring. ²⁹. Higher UV intensity, longer irradiation time, and smaller size of the microbeads accelerated the release of dissolved organic matter ²⁸. The contents in the media, as e.g., dissolved organic matter ³⁰, also affect the UV mediated degradation. The impact of UV irradiation on microplastics behaviour and effects on the environment has been reviewed (see e.g., Cheng et al. 2021³¹), and include effects on migration, release of additives, interactions with pollutants, and toxicity.

1
2
3 Although there is a rapidly growing number of articles describing the UV mediated View Article Online
DOI: 10.1039/D4EN00795F

4
5 degradation of microplastics, particles with an original size smaller than 100 nm have, to our

6
7 knowledge, not been studied. Furthermore, the link between toxicity and UV mediated

8
9 degradation needs to be examined in more detail to predict potential environmental effects

10
11 related to the degradation process. Small positively charged, amine-modified polystyrene

12
13 nanoparticles are a good starting material to study. These particles have previously been

14
15 shown to be acutely toxic to the freshwater zooplankton *Daphnia magna*³². However, in the

16
17 same study it was shown that larger polystyrene particles, with similar or different surface

18
19 modifications, were not acutely toxic³². Similar results were shown for amine-modified

20
21 polystyrene nanoparticles ranging between 20 and 100 nm, where all particles were toxic

22
23 but 20 and 40 nm exhibited stronger toxicity^{33, 34}. A size dependent toxicity seems to be a

24
25 general feature among plastic nanoparticles as reviewed by Pikuda et al, 2023³⁵. We have

26
27 here studied the physical degradation of 53 nm amine-modified polystyrene nanoparticles

28
29 and compared the degradation with 62 nm carboxyl-modified polystyrene nanoparticles. We

30
31 have further followed the acute toxicity which was shown to decrease for the 53 nm

32
33 particles after UV irradiation. However, also a dissolved fraction from the degradation

34
35 products was shown to be toxic to *D. magna*.

36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

Materials and methods

Model particles and UV-B lamp Two different polystyrene particles were bought from Bangs Laboratories Inc., USA. Particle 1 had a mean diameter of 53 nm and amine-modified surface (catalogue code: PA02N, Lot nr.: 15045). Particle 2 had a mean diameter of 62 nm and carboxyl-modified surface (catalogue code: PC02N, Lot nr.: 11652). Both particles were

delivered in a colloidal suspension with a concentration of $\approx 10\%$ solids (w/w) according to the manufacturer.

To remove additives, the particle solution was transferred to a dialyzation tube, (MilliPore MWCO 3000), and thoroughly dialyzed against MilliQ H₂O before further use.

The UV-B lamps, ExoTerra Reptile UV-B 200, 25W, were purchased from a local pet shop.

The lamps emitted wavelength spectra, taken with an air-coupled Avantes Mini, Czerny-Turner Spectrometer with 2048 pixels, a 10 μm slit with a 1 ms integration time, can be found in Supplementary Information Figure S1.

UV-B treatment of particles The dialyzed 53 nm amine-modified particles were diluted 40x with MilliQ H₂O, to a final concentration of $\approx 0.25\%$ (w/w) or ≈ 2.5 mg/mL. 80 ml of the solution was transferred to Petri dishes, either made of quartz or glass, and placed in a fridge. Three UV-B lamps were fitted in a cardboard box to shield the surrounding environment from UV radiation, see Figure S2, so the lamps tips were 10 cm over the Petri dishes. When the three lamps were on the temperature in the cardboard box, inside the fridge on maximum cooling, was stable at 21 ± 1 °C.

The 62 nm carboxyl-modified particles were treated the same way except that they were diluted 2000x with MilliQ H₂O, to a final concentration of $\approx 0.005\%$ (w/w) or ≈ 0.05 mg/mL.

The quartz petri dish was chosen as the material allows for wavelengths in the UV range to pass through the material while the glass petri dish was chosen as a control since it was expected to filter out the UV wavelengths.

DLS measurements The size distribution of the 53 nm amine-modified and 62 nm carboxyl-modified samples were analysed using a DynaPro Plate Reader II from Wyatt Technology, USA. Measurements were carried out in 96-well half width plates manufactured by Corning. Four 100 μ L sub-samples of each treatment (UV-B exposed and un-exposed, respectively) were loaded into separate well. The measured value from each well is based on 10 consecutive measurements at 25 $^{\circ}$ C.

DSC measurements After the end of the exposure period the particles were diluted five times in MilliQ H₂O and 100 μ L of each sample was applied to an 8-24% sucrose gradient capped with 0.5 mL of dodecane and analysed at 24000 rpm on a DC24000 disc centrifuge (CPS Instruments, USA).

Zeta potential measurements The zeta potentials were determined using a Zetasizer Ultra, Mavern Panalytical, United Kingdom. The software used was ZS XPLOER 2.0.1.1. Cuvettes, DTS1070, from Malvern Panalytical were used for all measurements. Each sample was measured three times with at least 30 runs for each measurement and the temperature was set to 25 $^{\circ}$ C. The analysis model was set to auto.

FTIR measurements A Spectrum Two FTIR equipped with a UATR Two unit from (PerkinElmer) was used to record the FTIR spectra. 6-10 μ L of the sample was placed on the

1
2
3 crystal of the UATR unit, and the H₂O was allowed to evaporate for 30-45 minutes before the View Article Online
DOI: 10.1039/D4EN00795F
4
5 spectrum was recorded. This process does not always work due to how the particles
6
7 migrates during the drying, see Figure S8. The spectrum was processed using the
8
9 PerkinElmer Spectrum IR application, version 10.7.2.1630. The data presented in this article
10
11 has been corrected using Data Tune-up and Interactive Baseline Correction.
12
13
14
15

16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
Acute toxicity tests An acute toxicity test on the UV-B exposed and UV-B shaded particle
dispersions (i.e. 53 nm and 62 nm, see above) was performed using the freshwater
zooplankter *D. magna*. One neonate was put in a 50 mL Falcon tube containing 40 mL of
either UV-B exposed or UV-B shaded particle dispersed in tap water with a nanoplastic
concentration of 5 mg/L. A control treatment containing tap water only was prepared and
run alongside the particle exposures as a reference. Each treatment was replicated 15 times
and all experimental groups were kept at 18 °C temperature with 16:8 hours light:dark cycle.
The experiment lasted for 48 hours, and the *D. magna* were not fed during the experiment.

4
4
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
Particle separation and acute toxicity tests The 53 nm particles were separated from small
molecules by applying 250 µL on a PD10 column (Cytoviva). An additional 750 µL H₂O was
added before the samples were eluted in 1 mL steps with H₂O. Each fraction was analysed by
measuring the absorbance at 230 nm. Fractions 3 to 5 containing the particles or particle
remnants, and fractions 8-9 containing the smaller breakdown molecules were pooled. For
the toxicity tests on *D. magna* 12 separations were made and pooled. The toxicity tests were
carried out in 10 replicates in a total volume of 9 mL of which the collected fractions were

1
2
3 1.5 mL and 7.5 mL ISO test water or 1.5 mL Milli-Q water and 7.5 mL ISO test water in the
4
5
6 controls testing the 53 nm particle. The ISO test water used was prepared according to OECD
7
8 202 test guidelines³⁶. The particle concentration was approximately 50 mg/L. The survival
9
10 was checked regularly for 24 hours.
11
12
13
14
15
16

17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

Detection of small molecules Fractions 10-11 from the separation were analysed by mass spectrometry (MS). MS spectra were acquired using a Autoflex Speed MALDI TOF/TOF mass spectrometer (Bruker Daltonics, Bremen, Germany) in positive reflector mode. The sample was acidified to a concentration of 0.5 % trifluoroacetic acid (TFA) before 1 μ L sample was mixed with 0.5 μ L Matrix solution, consisting of 5 mg/mL α -cyano-4-hydroxy cinnamic acid, 80% acetonitrile, 0.1% TFA, and added to a MALDI stainless steel plate. The spectrum was externally calibrated using Peptide calibration standard II (Bruker Daltonics) containing 9 internal standard peptides.

The fractions 8-9 were subjected to non-targeted analysis using an Agilent HPLC 1290 equipped with a Acquity HSS C18 column (3.0 x 100 mm, 1.8 μ m), connected to a Bruker timsTOF Pro 2 via a 6-port valve which allowed to inject calibration solution in each injection and recalibrate mass and mobility for more accurate results. The calibration solution used was a mixture of Agilent ESI-Low concentration Mix for mobility and sodium formate for mass calibration. The calibration segment was 0.5 min and total analysis time 18 min. Acetonitrile (0.1% FA) and water (0.1% FA) were used as mobile phase with a flow of 0.4 mL/min. The range of m/z was 20-1300, and the range of mobility was set according to that range to find small molecules. The sample was analysed in positive and negative mode



1
2
3 together with an instrument blank, each in triplicates. The data obtained was later processed
4 with Metaboscope (2022b) and using the NORMAN target list³⁷ to tentatively identify
5
6 with Metaboscope (2022b) and using the NORMAN target list³⁷ to tentatively identify
7
8 compounds. Thereafter, the data was further processed by an in-house R script to filter out
9
10 false positives by using the repetitions and blanks. InChIKeys were used to predict mobility
11
12 and MS/MS fragmentation. If the prediction was not good enough (>5% for mobility)
13
14 features were deleted.
15
16

17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
Statistical analysis Size differences between UV-B exposed and unexposed materials were
evaluated using t-tests. *D. magna* survival in acute toxicity tests was evaluated using Kaplan-
Meier survival analysis and the p-value was attained from the log-rank (Mantel-Cox) test. All
statistical evaluations were performed using GraphPad Prism (version 8.4.3).

Results and discussion

UV-B exposure of 53 nm amine-modified polystyrene particles – size The overall aim of this
study was to investigate if UV radiation affects the acute toxicity to *D. magna* exhibited by
small, positively charged, amine-modified polystyrene nanoparticles. Two characteristics of
these particles, their small size and positive charge, are thought to confer the toxicity. Both
these characteristics can possibly be changed by UV-B exposure. Therefore, we exposed 53
nm amine-modified polystyrene particles to UV-B radiation in a controlled laboratory setup,
see Figure S2. After 100 days of UV-B exposure, optical examination revealed striking
differences between the sample and the control as the 53 nm particle dispersion has
changed colour from white to brownish and from opaque to clear, compared to the UV-B

shaded control, Figures S3 and S4. The particle size was characterized using DLS after the UV-B exposure. The DLS measurements show that UV-B exposure significantly decreases the size of the particles compared to unexposed particles ($t=4.796$, $df=6$, $p=0.003$), Figure 1 and Table 1. A decreasing size of micro-sized polystyrene particles after high intensity UV exposure has been demonstrated before¹⁵. The results confirm that in low intensity UV-B exposure the same processes can be seen, however, the time scale is much longer.

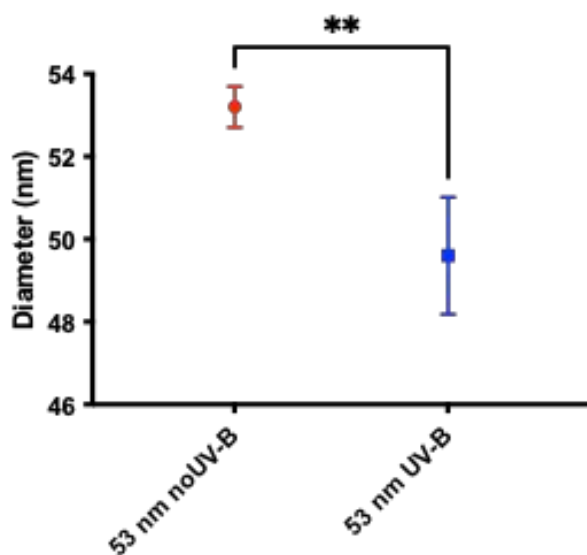


Figure 1. The size difference measured by DLS after 100 days UV-B exposure showing that the particle size significantly decreased after UV-B treatment compared to the control.

The size of the particles was further characterized with DSC, which, in contrast to DLS, shows that UV-B exposure increases the particle size and broadens the size distribution, Figure 2.

The techniques differ, as DLS calculates the particle size based on Brownian motions and DSC from the sedimentation time through a sucrose gradient. Therefore, a possible interpretation of the contrasting results is that UV-B irradiation breaks up the polystyrene

chain resulting in less compressed particles or particles with less material due to partial degradation in the entire particle²⁴. Both cases would facilitate the exchange of water to sucrose in the internal of the particles, resulting in a higher density of the newly formed particles which could explain the observed results.

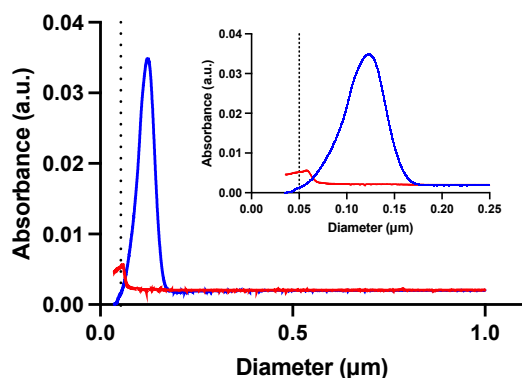


Figure 2. The size difference measured by DSC after 100 days UV-B exposure. UV-B treated particles are in blue and untreated in red. The dotted vertical line indicates the nominal size of the starting material, i.e. 53 nm. The inserted plot shows a zoom of the size range of 0-250 nm.

UV-B exposure of 53 nm amine-modified polystyrene particles – chemistry

As mentioned above, a possible explanation for the acute toxicity exhibited by the small amine-modified polystyrene particles is their positive surface charge. However, the zeta potential did not significantly change after 100 days of UV-B exposure (Table 1, Figure S5). These results could lead to various interpretations, such as the possibility that most amine groups remain intact or that the chemical changes still resulted in positively charged surface groups. However, as thoroughly reviewed by S. Bhattacharjee, measuring the zeta potential of nanoparticles reveals very little about the actual surface charge of the nanoparticles³⁸.




Table 1. Size and zeta potential of the particles.View Article Online
DOI: 10.1039/D4EN00795F

Method	DLS ¹	Zeta
	Size (nm)	potential ² (mV)
Control 53 nm	53.2 ± 0.5	27.8 ± 1.3
UV-B 53 nm	49.6 ± 1.4	28.8 ± 0.6

¹ DynaPro² Zetasizer Ultra

The UATR-FTIR spectra for the control (red) and UV-B-treated (blue) samples are shown in Figure 3. Four grey arrows indicate regions in the spectra exhibiting differences. Three of these, arrows 1, 2 and 4, areas are associated with oxygen-bonds. The carbonyl index is used to measure the chemical oxidations of polymers. Almond et al. extensively reviewed various methods for calculating the carbonyl index (CI), in their article they recommended the use of the specified area under band, SAUB, methodology³⁹. The CIs were computed using the formula $CI = \text{Area under band } 1850 - 1650 \text{ cm}^{-1} / \text{Area under band } 1500 - 1420 \text{ cm}^{-1}$. The carbonyl index (CI) values, see Figure S6, further underscore the distinction between the control (CI ≈ 1.0) and UV-B treated (CI ≈ 2.0) samples.

Arrow 3 indicates the absorbance peak at 1602 cm^{-1} , which is indicative of conjugated C=C systems. A closer inspection of the signal reveals that the absorbance at 1602 cm^{-1} increases compared to the C-H regions, $3100 - 2840$ and $1500 - 1440 \text{ cm}^{-1}$. Hence, the chemistry of the polystyrene nanoparticles is altered by the UV-B irradiation.

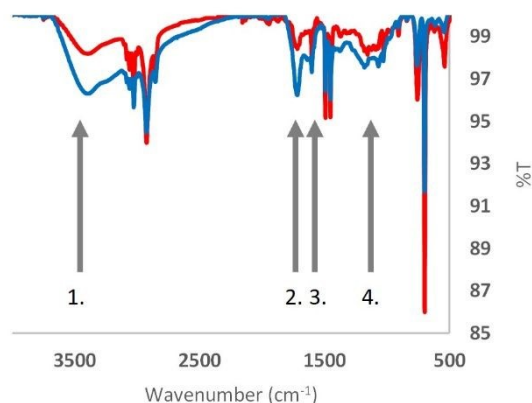

View Article Online
DOI: 10.1039/D4EN00795F


Figure 3. UATR-FTIR spectra for the 53 nm PS-NH₂ particles. Red is the control, placed in a glass petri dish during the experiment, sample. Blue is the UV-B treated, placed in a quartz petri dish during the experiment, sample. The grey arrows indicate some of the changes in the FTIR spectrum.

UV-B exposure of 53 nm amine-modified polystyrene particles – toxicity

The untreated 53 nm amine-modified polystyrene particles were, as expected, toxic to *D. magna*,

($\chi^2_{(df=1)}=24.18$, $p<0.0001$), Figure 4, which has been reported before³². The UV-B exposed sample was still toxic to *D. magna*, ($\chi^2_{(df=1)}=32.81$, $p<0.0001$) compared to the control.

However, the toxicity was significantly reduced ($\chi^2_{(df=1)}=32.81$, $p<0.0001$) compared to the untreated particles. It is likely that the oxidation by UV-B exposure have changed the particles to more resemble polystyrene and oxidized polystyrene than the starting material amine-modified polystyrene. This could explain the decreased toxicity as neither plain nor carboxyl-modified polystyrene nanoparticles are acutely toxic³².

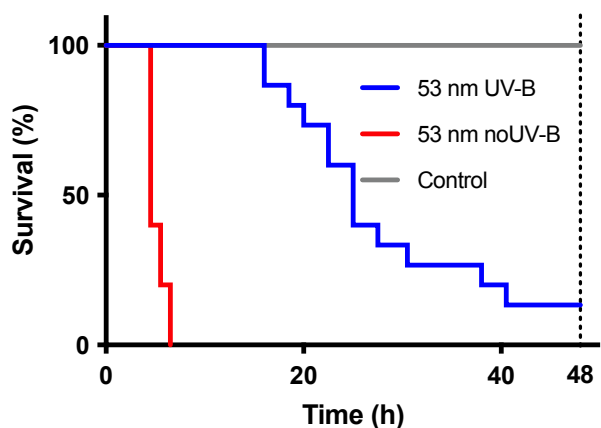

View Article Online
DOI: 10.1039/D4EN00795F

Figure 4. Acute toxicity test with 53 nm amine-modified polystyrene particles. Kaplan-Meier survival curves for *D. magna* exposed to UV-B exposed (blue line) and UV-B shaded (red line) nanoplastics. Grey line shows a control treatment only containing water. Total exposure time is 48 hours as highlighted by the dotted vertical line.

UV-B exposure of 53 nm amine-modified polystyrene particles – dissolved fraction It has been reported that intense UV irradiation of polystyrene results in the release of many different small dissolved organic compounds into the media^{25, 26, 40}. We therefore expect that UV-B exposure also can result in the release of small molecules. To further analyse the samples, the small, dissolved molecules were separated from particles by applying the UV-B exposed mixture to a PD10 column. The 53 nm particles elute in fractions 3-5, and the small, dissolved molecules elute in fractions 10-11, Figure 5A. The total amount of carbon and nitrogen was determined using a Shimadzu TOC-V CPH equipped with a nitrogen detector, before and after separation, Table 2. The carbon/nitrogen ratio is higher for the particle fractions but lower for the dissolved molecules after separation, which is consistent with that nitrogen disappear from the surface of the particles.

Table 2. Carbon and nitrogen content in the fractions after separation

Sample	Carbon (mg/L)	Nitrogen (mg/L)	Carbon/Nitrogen
Unseparated	2614	32.9	79.5
NP fraction	257	2.0	128.5
DM fraction	21.4	1.3	16.5


View Article Online
DOI: 10.1039/D4EN00795F

¹ Diluted 8-10 times compared to unseparated fraction

The separated samples were tested for toxicity with an acute toxicity test, see Figure 5.

Interestingly, the fractions containing the dissolved molecules produced from the UV-B exposure, exhibited a significant toxicity compared to the control ($\chi^2_{(df=1)}=19.41$, $p<0.0001$).

In agreement with the first experiment, Figure 4, the UV-B exposed particles are less toxic than untreated particles ($\chi^2_{(df=1)}=16.35$, $p<0.0001$). The time when immobilization occurs and the resolution between the samples are different, this could be due to several reasons. As we aimed for a higher concentration of dissolved breakdown molecules, the concentration here is 10X higher as compared to the previous test. The experimental design, with a smaller volume compared to the other assay, was limited by the sample volume and aimed at determining if the dissolved compounds are toxic.

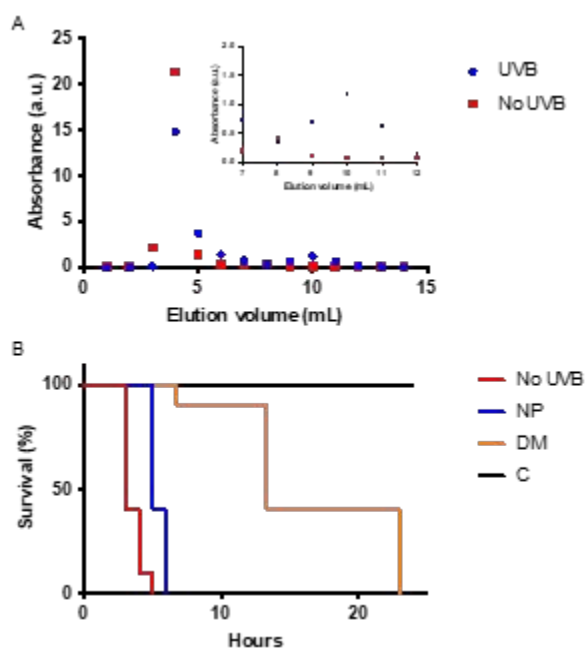

View Article Online
DOI: 10.1039/D4EN00795F

Figure 5. The acute toxicity of the separated samples after passing the PD10 column. The separation of untreated and treated articles by a PD10 column. The acute toxicity of the different fractions (B). In the red is the pooled fractions 3 to 5 of the UV-B shaded sample. In blue is the pooled fractions 3 to 5 of the UV-B exposed sample. In orange is the pooled fractions 10 to 11 of the UV-B exposed sample. In black is the control sample (no particle fraction added).

The dissolved small molecules were analysed by mass spectrometry, Figure S7. Notably in the spectra is a 44-mass unit repeat. This could be an oxidized two carbon unit as C_2OH_4 has a molecular mass of 44. The smallest weight we can detect is 626 which would mean a chain with 28 carbons.

The dissolved fraction was further described with untargeted analysis. The detected compounds are shown in Table 3 and with the structure in Table S1. It is evident that the UV-B exposure results in a very complex mixture of dissolved compounds, including molecules containing nitrogen. There are examples of molecules indicating ring opening resulting in long carbon chains. There are oxidized carbon chains which support the results from the

mass spectrometry data described above. In four molecules the nitrogen is within closed ring indicating complexed secondary cyclization reactions which have been described before ²⁶. Sulphone groups are present which is probably from the original polystyrene nanoparticles that are aminated. We have previously shown that aminated polystyrene nanoparticles have a batch dependent FTIR signal, probably due to the level of amination ⁴¹. Three molecules, amine alkyls, 12-Aminododecanoic acid, and 4-Methyl-2-pentylpyridine are labelled with health/environmental hazards. Nine of the identified molecules can be described as amine detergents. The evaluation of the toxicity of 20 amine detergents to *D. magna* showed that alkyl chains with a single nitrogen at the end were more toxic than oxidized amine alkyls ⁴². The found amine alkyls may therefore contribute more to the toxicity than the 8 oxidized amine detergents. Prolonged UV irradiation should induce more oxidation and thereby with time decrease the toxicity. Furthermore, the production of amine detergents could affect the physical behaviour and toxicity of the remaining polystyrene nanoparticles ⁴³. However, many of the other identified molecules may contribute to the toxicity but are to our knowledge not tested.

Table 3. Non-targeted analysis of the compounds in the dissolved fractions 10-11. After UV-B breakdown of the aminated polystyrene nanoparticles the dissolved molecules were separated from the remaining particle and analysed for the contents.

	Name	Molecular Formula	Hazard
1	(2-Neopentylallyl)succinic acid	C ₁₂ H ₂₀ O ₄	
2	(2Z,4S,5S,6S,7R,8Z)-2,9-diphenyldeca-2,8-diene-3,4,5,6,7,8-hexol	C ₂₂ H ₂₆ O ₆	
3	(5-Ethyl-2,2-dimethyl-1,3-dioxan-5-yl)methyl acrylate	C ₁₂ H ₂₀ O ₄	
4	1-Propanamine, 3-(hexadecyloxy)-	C ₁₉ H ₄₁ NO	

5	12-(Methylamino)dodecanoic acid	$C_{13}H_{27}NO_2$	View Article Online DOI: 10.1039/D4EN00795F
6	12-Aminododecanoic acid	$C_{12}H_{25}NO_2$	Health
7	2-Hydroxypropyl hexanoate	$C_9H_{18}O_3$	
8	3-(Hexadecylamino)propane-1,2-diol	$C_{19}H_{41}NO_2$	
9	3-Ethylaniline	$C_8H_{11}N$	
10	3-[(Acetoxy)methyl]nonan-1-oic acid	$C_{12}H_{22}O_4$	
11	4-Methyl-2-pentylpyridine	$C_{11}H_{17}N$	Environment
12	5-Amino-1,1-dimethylhexyl acetate	$C_{10}H_{21}NO_2$	
13	5-Butyl-2-methylpyridine	$C_{10}H_{15}N$	
14	A-[(2-methylpropoxy)methyl]pyrrolidine-1-ethanol	$C_{11}H_{23}NO_2$	
15	A-hydroxy-p-methoxytoluene-a-sulphonic acid	$C_8H_{10}O_5S$	
16	Amines, C16-22-alkyl	$C_{19}H_{41}N$	Health /Environment
17	C13 Alkyl dimethyl betaine	$C_{17}H_{35}NO_2^1$	
18	C15 Alkyl dimethyl betaine	$C_{19}H_{39}NO_2^1$	
19	C17 Alkyl dimethyl amine oxide	$C_{19}H_{41}NO^2$	
20	Calcium bis(hydroxybenzenesulphonate)	$C_{12}H_{10}CaO_8S_2$	
21	Cyclohexylmethyl-2,3-Dihydroxy-5-Methyl-Hexylamide	$C_{14}H_{29}NO_2$	
22	Dodec-2-enedioic acid	$C_{12}H_{20}O^4$	
23	Piperidine-1,2-diethanol	$C_9H_{19}NO_2$	
24	TRADECAMIDE	$C_{15}H_{31}NO_2$	

62 nm carboxyl-modified polystyrene nanoparticles

We wanted to further explore the UV-B efficiency in breaking down polystyrene and to see if the process could generate small toxic molecules from a nanoparticle that is not acutely toxic for *D. magna*. The choice fell upon 62 nm carboxyl-modified polystyrene nanoparticles. In contrast to the 53 nm amine-modified polystyrene nanoparticles the 62 nm carboxyl-modified polystyrene nanoparticles exhibit no acute toxicity³².



The size of the carboxyl-modified nanoparticles during degradation was followed using DLS, Figure 6A. The effect of the UV-B radiation is slow during the first 20 days; after that, it accelerates, and DLS cannot detect any particles in the treated sample after 79 days of treatment. The degradation of the 62 nm particles is significantly faster than the degradation of the 53 nm particles. A plausible explanation for this is the lower concentration, 50x less, of the particle dispersion in the 62 nm experiment which means that the light will hit each particle in the sample more often. Another difference between the two UV-B experiments is that new UV lamps were used in the 62 nm carboxyl-modified polystyrene particle experiment. Based on our later lamp characterization, see supplementary figure S1, it is clear that the lamp age affects the spectral intensity of the lamp. The combination of lower particle concentration and new UV-B lamps could explain the faster photo-degradation observed in the 62 nm carboxyl-modified polystyrene particle experiment, see Figure 6.

The degradation process of the 62 nm carboxyl-modified polystyrene particles was followed by UATR-FTIR. Figure S8 shows the spectra from five different time points and Figure S6 shows the calculated CI. Compared to the CI for the amine-modified particles, the CI is higher for the carboxyl-modified particles and is decreasing for the first two time points after which it fluctuates. In the later time points (data not shown) the data is difficult to collect.

The samples were too diluted to give a reliable determination of the Zeta potential.

Toxicity test with 62 nm carboxyl-modified polystyrene nanoparticles and its breakdown products

As shown previously, the degradation products from the amine-modified particles caused acute toxicity. In light of this, we wanted to investigate if the degradation products from a normally benign particle, the 62 nm carboxyl-modified polystyrene particle, would be acutely toxic to *D. magna*. After 79 days of UV-B exposure, there were no detectable particles, indicating complete or near complete particle degradation, hence the sample only contains degradation products. This sample was tested for toxicity to *D. magna*, Figure 6B. As expected, no toxicity was observed for the untreated particles ($p>0.05$) although the concentration of particles was the same as for the amine-modified polystyrene nanoparticles. Likewise, there was no toxicity observed for the UV-B treated sample either ($p>0.05$). Although the concentration of dissolved compounds is unknown the potential concentration is probably higher for the dissolved fraction originating from the carboxyl-modified than from the amine-modified polystyrene particles, since only a small fraction of the amine-modified particles was degraded. This may suggest that the degradation products from the amine-modified polystyrene are much more toxic. However, since the degrading process was faster for the 62 nm carboxyl-modified polystyrene particles, due to lower particle concentration and new lamps, there is a possibility that we missed a point on the degradation road that would be toxic, but the compounds have either evaporated or degraded further before we started the toxicity test. The answer to this question is beyond the scope of this article.

View Article Online
DOI: 10.1039/D4EN00795F

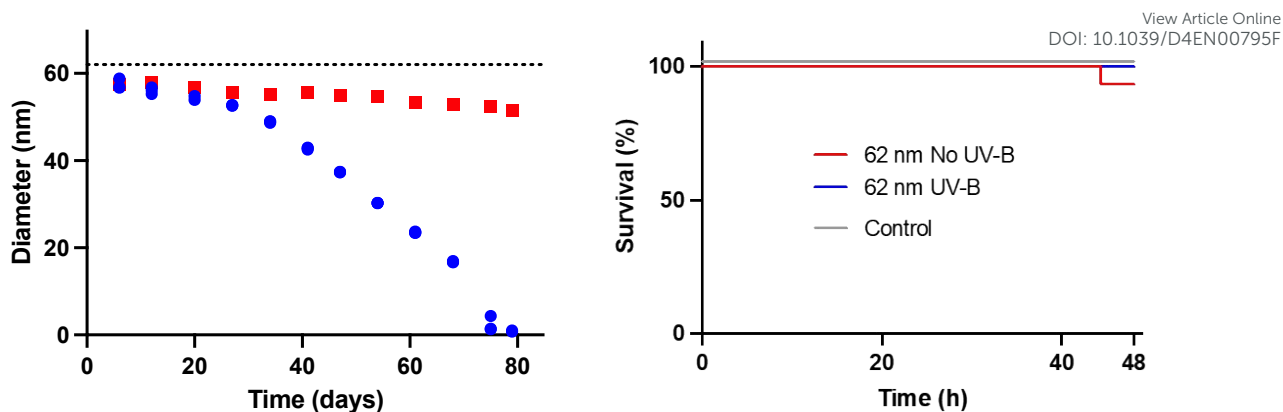


Figure 6. UV-B exposure of 62 nm carboxyl-modified polystyrene particles. Left. Particle size was followed by DLS. The UV-B treated samples are shown in blue, and the UV-B shaded samples are shown in red. The dotted horizontal line represents nominal size of the particles as stated by the manufacturer (i.e. 62 nm). Right. Acute toxicity test with 62 nm carboxyl-modified polystyrene particles. Kaplan-Meier survival curves for *D. magna* exposed to UV-B exposed (blue line) and UV-B shaded (red line) nanoplastics. Grey line shows a control treatment only containing water. Each treatment was replicated 15 times, and the exposure concentration is 5 mg/L. No significant differences were identified, $p > 0.05$.

Conclusions

- UV-B exposure decrease the size of 53 nm amine-modified and 62 nm carboxyl-modified polystyrene particles.
- The toxicity to *D. magna* decreases after UV-B exposure of the 53 nm amine-modified polystyrene particles.
- The UV-B degradation release a complex mixture of small molecules that are toxic when originating from the 53 nm amine-modified nanoparticles.
- The UV-B degradation of the 62 nm carboxyl-modified nanoparticles did not result in any, for *D. magna*, acutely toxic compound.



References

View Article Online
DOI: 10.1039/D4EN00795F

1. B. R. Kiran, H. Kopperi and S. V. Mohan, Micro/nano-plastics occurrence, identification, risk analysis and mitigation: challenges and perspectives, *Reviews in Environmental Science and Bio-Technology*, 2022, **21**, 169-203.
2. F. Stábile, M. T. Ekvall, J. A. Gallego-Urrea, T. Nwachukwu, W. G. C. U. Soorasena, P. I. Rivas-Comerlati and L.-A. Hansson, Fate and biological uptake of polystyrene nanoparticles in freshwater wetland ecosystems, *Environmental Science: Nano*, 2024, DOI: 10.1039/D3EN00628J.
3. M. T. Ekvall, F. Stábile and L.-A. Hansson, Nanoplastics rewire freshwater food webs, *Communications Earth & Environment*, 2024, **5**, 486.
4. J. Gigault, H. El Hadri, B. Nguyen, B. Grassl, L. Roweczyk, N. Tufenkji, S. Y. Feng and M. Wiesner, Nanoplastics are neither microplastics nor engineered nanoparticles, *Nature Nanotechnology*, 2021, **16**, 501-507.
5. N. B. Hartmann, T. Hüffer, R. C. Thompson, M. Hassellöv, A. Verschoor, A. E. Daugaard, S. Rist, T. Karlsson, N. Brennholt, M. Cole, M. P. Herrling, M. C. Hess, N. P. Ivleva, A. L. Lusher and M. Wagner, Are We Speaking the Same Language? Recommendations for a Definition and Categorization Framework for Plastic Debris, *Environmental Science & Technology*, 2019, **53**, 1039-1047.
6. A. Ter Halle, L. Jeanneau, M. Martignac, E. Jarde, B. Pedrono, L. Brach and J. Gigault, Nanoplastic in the North Atlantic Subtropical Gyre, *Environ. Sci. Technol.*, 2017, **51**, 13689-13697.
7. D. Materic, M. Peacock, J. Dean, M. Futter, T. Maximov, F. Moldan, T. Röckmann and R. Holzinger, Presence of nanoplastics in rural and remote surface waters, *Environmental Research Letters*, 2022, **17**.
8. S. Fraissinet, G. E. De Benedetto, C. Malitesta, R. Holzinger and D. Materic, Microplastics and nanoplastics size distribution in farmed mussel tissues, *Communications Earth & Environment*, 2024, **5**.
9. E. Sanfins, C. Augustsson, B. Dahlbäck, S. Linse and T. Cedervall, Size-Dependent Effects of Nanoparticles on Enzymes in the Blood Coagulation Cascade, *Nano Lett.*, 2014, **14**, 4736-4744.
10. Statista).
11. A. Wahl, C. Le Juge, M. Davranche, H. El Hadri, B. Grassl, S. Reynaud and J. Gigault, Nanoplastic occurrence in a soil amended with plastic debris, *Chemosphere*, 2021, **262**, 127784.
12. S. Lambert and M. Wagner, Characterisation of nanoplastics during the degradation of polystyrene, *Chemosphere*, 2016, **145**, 265-268.
13. L. M. Hernandez, J. Grant, P. S. Fard, J. M. Farner and N. Tufenkji, Analysis of ultraviolet and thermal degradations of four common microplastics and evidence of nanoparticle release, *Journal of Hazardous Materials Letters*, 2023, **4**.
14. F. G. Zha, J. M. Dai, Y. X. Han, P. Liu, M. J. Wang, H. Y. Liu and X. T. Guo, Release of millions of micro(nano)plastic fragments from photooxidation of disposable plastic boxes, *Science of the Total Environment*, 2023, **858**.
15. Z. Y. Liu, Y. J. Zhu, S. S. Lv, Y. X. Shi, S. F. Dong, D. Yan, X. S. Zhu, R. Peng, A. A. Keller and Y. X. Huang, Quantifying the Dynamics of Polystyrene Microplastics UV-Aging Process, *Environmental Science & Technology Letters*, 2022, **9**, 50-56.
16. H. Tong, X. Zhong, Z. Duan, X. Yi, F. Cheng, W. Xu and X. Yang, Micro- and nanoplastics released from biodegradable and conventional plastics during degradation: Formation, aging factors, and toxicity, *Sci Total Environ*, 2022, **833**, 155275.
17. M. T. Ekvall, M. Lundqvist, E. Kelpsiene, E. Sileikis, S. B. Gunnarsson and T. Cedervall, Nanoplastics formed during the mechanical breakdown of daily-use polystyrene products, *Nanoscale Advances*, 2019, **1**, 1055-1061.

- 1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
18. K. Mattsson, F. Bjorkroth, T. Karlsson and M. Hassellto, Nanofragmentation of Expanded Polystyrene Under Simulated Environmental Weathering (Thermooxidative Degradation and Hydrodynamic Turbulence), *Frontiers in Marine Science*, 2021, **7**.
19. B. G. Kwon, K. Koizumi, S. Y. Chung, Y. Kodera, J. O. Kim and K. Saido, Global styrene oligomers monitoring as new chemical contamination from polystyrene plastic marine pollution, *Journal of Hazardous Materials*, 2015, **300**, 359-367.
20. B. G. Kwon, K. Amamiya, H. Sato, S. Y. Chung, Y. Kodera, S. K. Kim, E. J. Lee and K. Saido, Monitoring of styrene oligomers as indicators of polystyrene plastic pollution in the North-West Pacific Ocean, *Chemosphere*, 2017, **180**, 500-505.
21. C. P. Ward, C. J. Armstrong, A. N. Walsh, J. H. Jackson and C. M. Reddy, Sunlight Converts Polystyrene to Carbon Dioxide and Dissolved Organic Carbon, *Environmental Science & Technology Letters*, 2019, **6**, 669-674.
22. E. Yousif and R. Haddad, Photodegradation and photostabilization of polymers, especially polystyrene: review, *Springerplus*, 2013, **2**.
23. A. L. Andrady, P. W. Barnes, J. F. Bornman, T. Gouin, S. Madronich, C. C. White, R. G. Zepp and M. A. K. Jansen, Oxidation and fragmentation of plastics in a changing environment; from UV-radiation to biological degradation, *Science of the Total Environment*, 2022, **851**.
24. G. Balakrishnan, F. Lagarde, C. Chassenieux, A. Martel, E. Deniau and T. Nicolai, Fate of polystyrene and polyethylene nanoplastics exposed to UV in water, *Environmental Science-Nano*, 2023, **10**, 2448-2458.
25. X. Y. Wu, X. Chen, R. F. Jiang, J. You and G. F. Ouyang, New insights into the photo-degraded polystyrene microplastic: Effect on the release of volatile organic compounds, *Journal of Hazardous Materials*, 2022, **431**.
26. N. M. Ainali, D. N. Bikiaris and D. A. Lambropoulou, Aging effects on low- and high-density polyethylene, polypropylene and polystyrene under UV irradiation: An insight into decomposition mechanism by Py-GC/MS for microplastic analysis, *Journal of Analytical and Applied Pyrolysis*, 2021, **158**.
27. K. W., *Ultraviolet germicidal irradiation handbook*, 2009.
28. S. Peng, L. P. Li, D. B. Wei, M. Chen, F. P. Wang, Y. Gui, X. Y. Zhao and Y. G. Du, Releasing characteristics of toxic chemicals from polystyrene microplastics in the aqueous environment during photoaging process, *Water Research*, 2024, **258**.
29. L. L. Tian, Q. Q. Chen, W. Jiang, L. H. Wang, H. X. Xie, N. Kalogerakis, Y. N. Ma and R. Ji, A carbon-14 radiotracer-based study on the phototransformation of polystyrene nanoplastics in water versus in air, *Environmental Science-Nano*, 2019, **6**, 2907-2917.
30. X. R. Qiu, S. R. Ma, J. X. Zhang, L. C. Fang, L. Y. Zhu and X. T. Guo, Dissolved Organic Matter Promotes the Aging Process of Polystyrene Microplastics under Dark and Ultraviolet Light Conditions: The Crucial Role of Reactive Oxygen Species, *Environmental Science & Technology*, 2022, **56**, 10149-10160.
31. F. Cheng, T. Zhang, Y. Liu, Y. Zhang and J. Qu, Non-Negligible Effects of UV Irradiation on Transformation and Environmental Risks of Microplastics in the Water Environment, *J Xenobiot*, 2021, **12**, 1-12.
32. K. Mattsson, E. V. Johnson, A. Malmendal, S. Linse, L. A. Hansson and T. Cedervall, Brain damage and behavioural disorders in fish induced by plastic nanoparticles delivered through the food chain, *Scientific Reports*, 2017, **7**.
33. Z. Meng, R. Recoura-Massaquant, A. Chaumot, S. Stoll and W. Liu, Acute toxicity of nanoplastics on Daphnia and Gammarus neonates: Effects of surface charge, heteroaggregation, and water properties, *Science of The Total Environment*, 2023, **854**, 158763.
34. A. Pochelon, S. Stoll and V. I. Slaveykova, Polystyrene Nanoplastic Behavior and Toxicity on Crustacean Daphnia magna: Media Composition, Size, and Surface Charge Effects, *Environments*, 2021, **8**, 101.
35. O. Pikuda, E. Roubeau Dumont, Q. Chen, J.-R. Macairan, S. A. Robinson, D. Berk and N. Tufenkji, Toxicity of microplastics and nanoplastics to Daphnia magna: Current



- status, knowledge gaps and future directions, *TrAC Trends in Analytical Chemistry*, 2023, **167**, 117208. View Article Online
DOI: 10.1039/D4EN00795F
36. OECD, *Test No. 202: Daphnia sp. Acute Immobilisation Test*, 2004.
37. NORMAN Network, R. Aalizadeh, N. Alygizakis, E. Schymanski, J. Solobodnik, S. Fischer, L. Cirka and H. Mohammed Taha, S0 | SUSDAT | Merged NORMAN Suspect List: SusDat (NORMAN-SLE-S0.0.5.1). *Journal*, 2024, DOI: 10.5281/zenodo.2664077.
38. S. Bhattacharjee, DLS and zeta potential - What they are and what they are not?, *J Control Release*, 2016, **235**, 337-351.
39. J. Almond, P. Sugumaar, M. N. Wenzel, G. Hill and C. Wallis, Determination of the carbonyl index of polyethylene and polypropylene using specified area under band methodology with ATR-FTIR spectroscopy, *e-Polymers*, 2020, **20**, 369-381.
40. C. Romera-Castillo, M. Pinto, T. M. Langer, X. A. Alvarez-Salgado and G. J. Herndl, Dissolved organic carbon leaching from plastics stimulates microbial activity in the ocean, *Nature Communications*, 2018, **9**.
41. E. Kelpsiene, I. Brandts, K. Bernfur, M. T. Ekvall, M. Lundqvist, M. Teles and T. Cedervall, Protein binding on acutely toxic and non-toxic polystyrene nanoparticles during filtration by *Daphnia magna*, *Environmental Science-Nano*, 2022, **9**, 2500-2509.
42. W. Liu, X. Wang, X. Zhou, H. Duan, P. Zhao and W. Liu, Quantitative structure-activity relationship between the toxicity of amine surfactant and its molecular structure, *Science of The Total Environment*, 2020, **702**, 134593.
43. N. Phasukarratchai, Effects and applications of surfactants on the release, removal, fate, and transport of microplastics in aquatic ecosystem: a review, *Environmental Science and Pollution Research*, 2023, **30**, 121393-121419.

Data availability statements

The data supporting this article will be included as part of the Supplementary Information

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

Open Access Article. Published on 17 October 2024. Downloaded on 29/12/2024 05:27:39.
This article is licensed under a Creative Commons Attribution 3.0 Unported Licence.

