

Journal of Materials Chemistry C

Materials for optical, magnetic and electronic devices

Accepted Manuscript

This article can be cited before page numbers have been issued, to do this please use: H. McPhillips, P. Manuel, G. B. G. Stenning, I. da Silva, S. Ramos and D. Arnold, *J. Mater. Chem. C*, 2025, DOI: 10.1039/D4TC03777D.



This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.

View Article Online
DOI: 10.1039/D4TC03777D

Investigation of the magnetic spin correlations in the layered molybdenates
Mn₂Mo₃O₈ and MnAMo₃O₈ (A = Fe, Co, Zn)

Holly L. McPhillips^{1,2}, Pascal Manuel³, Gavin B. G. Stenning³, Ivan da Silva³, Silvia Ramos^{1*}
and Donna C. Arnold^{2*}

¹ *School of Physics and Astronomy, University of Kent, Canterbury, Kent, C
T2 7NH, UK*

² *School of Chemistry and Forensic Science, University of Kent, Canterbury, Kent, CT2 7NH,
UK*

³ *ISIS Neutron and Muon Source, Rutherford Appleton Laboratory, Harwell Science and
Innovation Campus, Didcot, OX11 0QX, UK*

* *Corresponding authors: d.c.arnold@kent.ac.uk and s.ramos-perez@kent.ac.uk*

Abstract

An exotic range of magnetic (and other) properties have been observed in A₂Mo₃O₈ materials (where A is a single or mix of transition metals) making understanding their chemistry and physics timely. We have investigated the structural-property relationships in Mn₂Mo₃O₈ and the related materials, MnFeMo₃O₈, MnCoMo₃O₈ and MnZnMo₃O₈. We report a detailed powder diffraction analysis confirming ferrimagnetic structures for Mn₂Mo₃O₈ and MnFeMo₃O₈. Differing rates of spin ordering on crystallographically distinct sites (tetrahedral or octahedral) gives rise to magnetic hysteresis, which abruptly disappears in 2 K data. This appears correlated with ion displacement and/or electrostriction effects, which also relax at 2 K. We confirm an antiferromagnetic structure type for MnCoMo₃O₈ and no discernible magnetic ordering within the temperature range studied for MnZnMo₃O₈. For MnZnMo₃O₈ we suggest a small amount of site disorder acts to suppress magnetic ordering. This suggests that magnetic properties can be tuned both through A-site cation order and choice of A-site cations.

Introduction


The A₂Mo₃O₈ family of materials (where A = Mn²⁺, Fe²⁺, Co²⁺ or Ni²⁺) have been attracting recent attention due to their exotic magnetic properties and magnetoelectric coupling^{1–5} and potential applications for renewable energy technologies (batteries^{6–9}, supercapacitors^{10,11} and in water splitting^{12–15}). These materials exhibit a complex layered arrangement, which crystallizes with a hexagonal structure in the *P6₃mc* space group (# 186). The structure consists of Kagomé-type MoO₆ layers which are separated by two-dimensional honeycomb



layers stacked in the lattice *c*-direction (figure 1). The AO layer comprises two crystallographically distinct tetrahedral (AO₄) and octahedral (AO₆) corner shared sites which alternate in the lattice *a/b* plane to form a bipartite buckling honeycomb layer¹⁶. No magnetic contribution (as might be expected from Mo⁴⁺) arises from the Mo₆ layer due to an orbital driven Peierls effect which gives rise to a trimerization of MoO₆ resulting in a shared electronic ground state and no unpaired electrons. Instead, magnetic order arises from magnetic A²⁺ ions situated within the honeycomb layer⁶. Computational studies have demonstrated that lack of Mo contribution to the magnetic ground state in A₂Mo₃O₈ (A = Fe, Co and Mn) materials¹⁶. At room temperature, the materials are considered pyroelectric, arising as a result of the presence of the AO₄ tetrahedra, with the polarisation vector directed along the crystallographic *c*-direction^{17–19}. Below the magnetic transition type 1 multiferroic character is realised owing to the coexistence of spontaneous polarisation and magnetic ordering and large linear magnetoelectric coupling in both the *a/b* plane and lattice *c*-direction have been reported²⁰.

By far the most studied members of the family are Fe₂Mo₃O₈ and Co₂Mo₃O₈, with both compounds reported to exhibit antiferromagnetic ordering at Néel temperatures (T_N) of 59.5 K and 40.8 K respectively²¹. Fe²⁺ ions in Fe₂Mo₃O₈ are antiferromagnetically coupled between tetrahedral and octahedral sites in the *a/b* plane with a long range collinear antiferromagnetic structure realised through antiferromagnetic coupling of tetrahedral or octahedral units across layers²². Additionally, Fe₂Mo₃O₈ has been shown to exhibit exciting electronic and magnetic properties such as giant magnetoelectric effect,^{2,4,23} optical magnetoelectric effect,²⁴ strong magnon-phonon coupling²² and distinct electric field and terahertz magnetic excitations²⁰. Co₂Mo₃O₈ shows a sharp transition in temperature dependent susceptibility consistent with antiferromagnetic ordering⁵. Neutron diffraction demonstrated the magnetic Bragg peaks identifiable at 10 K could be indexed with $\mathbf{k} = (0,0,0)$ with similar magnitudes for the magnetic moments for Co²⁺ observed on both the tetrahedral (3.44 μ_B) and octahedral sites (3.35 μ_B) and C-type connectivity similar to that observed for Fe₂Mo₃O₈⁵. However, in contrast Fe₂Mo₃O₈, shows no evidence for a magnetic field induced transition to a ferrimagnetic state is observed in Co₂Mo₃O₈⁵. This is suggested to be as a result of the small differences in magnitude of the magnetic moments in Co₂Mo₃O₈ when compared to Fe₂Mo₃O₈⁵. Recently, the dependence of the magnetoelectric effect up to fields of 60 T in Co₂Mo₃O₈ has been studied²⁵. These authors reported at high applied fields of 27 T and 31 T spin-flop transitions (towards canted antiferromagnetically ordered states) were observed at 1.7 K which result in colossal changes of the electric polarisation²⁵.

In contrast, no magnetic order down to 2 K was initially reported for Ni₂Mo₃O₈ from both computational and experimental studies²¹. Recent computational studies have suggested that



the magnetic order in $\text{Ni}_2\text{Mo}_3\text{O}_8$ is far more complex with strong antiferromagnetic coupling expected within layers whilst weak interlayer coupling is expected due to the small magnetic moment of Ni^{2+} ¹⁶. More recently, it has been reported that $\text{Ni}_2\text{Mo}_3\text{O}_8$ orders non-collinearly with a $T_N \approx 5.5$ K with the magnetic moments lying in the a/b plane rather than the crystallographic c -direction as observed for both $\text{Fe}_2\text{Mo}_3\text{O}_8$ and $\text{Co}_2\text{Mo}_3\text{O}_8$ ¹. Initially the magnetic structure was reported to exhibit a zig-zag-type magnetic ordering such that pairs of antiferromagnetically connected ferromagnetic zig-zag chains are formed within the a/b plane²⁶ or as a complex mixture between zig-zag and stripy structures²⁷. More recently, powder neutron diffraction data has shown the magnetic structure to be stripy (whereby order within these chains is antiferromagnetic rather than ferromagnetic and connectivity between the chains is ferromagnetic)¹. In high magnetic fields metamagnetic phase transitions have also been reported for $\text{Ni}_2\text{Mo}_3\text{O}_8$ ²⁸.

Comparatively, very little has been reported on the magnetic behaviour of $\text{Mn}_2\text{Mo}_3\text{O}_8$. Both computational and experimental studies have suggested that $\text{Mn}_2\text{Mo}_3\text{O}_8$ exhibits ferrimagnetic order with a transition temperature of approximately 40 K^{16,21}. In real terms the picture is far more complex. Typically, ferrimagnetic behaviour arises as a result of the coexistence of species with very different magnetic moments on a magnetic lattice such that antiferromagnetic ordering of these species does not result in the complete cancellation of the magnetic moment, leading to a net magnetic moment in a particular crystallographic direction. Neutron diffraction studies performed by Bertrand *et al.* at 4.5 K suggest that the magnetic moments in $\text{Mn}_2\text{Mo}_3\text{O}_8$ are ordered along the crystallographic c -axis²⁹. The authors proposed four different magnetically ordered states, C-type antiferromagnetic, A-type antiferromagnetic, ferrimagnetic (where connections between a particular site (octahedral or tetrahedral) are ferromagnetic whilst those across sites are antiferromagnetic) and ferromagnetically ordered. From the magnetic Bragg peak line strength the authors proposed that the magnetic moments associated with Mn^{2+} on the tetrahedral and octahedral sites have different magnitudes leading to ferrimagnetic ordering²⁹. However, it is now more commonly accepted (from SQUID magnetometry studies) that below T_N the magnetic moments associated with the octahedral and tetrahedral sublattices cancel out completely (giving rise to antiferromagnetic ordering) at zero temperatures but not at finite temperatures where ferrimagnetic ordering is observed¹⁸. However, the mechanism for this remains unclear. Given the plethora of exciting magnetic states that can be realised in this family of materials it can be expected that the magnetic behaviour of $\text{Mn}_2\text{Mo}_3\text{O}_8$ is perhaps not as simplistic as has been reported thus far, warranting more detailed structural and magnetic studies.



Furthermore, many studies have looked at cooperative doping on the lattice A-site since the presence of both octahedral and tetrahedral A-sites provides a versatile playground to study interesting magnetic phenomenon and control magnetic behaviour^{30–38}. For example, giant thermal Hall effects have been reported in $\text{Fe}_{2-x}\text{Zn}_x\text{Mo}_3\text{O}_8$ materials³⁰. The magnetoelectric effect has been shown to be tuneable with the transition between antiferromagnetically and ferrimagnetically ordered states with Zn doping in $\text{Fe}_2\text{Mo}_3\text{O}_8$ ^{31,33,34} and $\text{Co}_2\text{Mo}_3\text{O}_8$ ³⁹. However, as with the parent materials comparatively few studies have been performed with manganese despite the potential for site preference leading to exotic behaviour. Recently, Chang *et al.*, prepared single crystals of $(\text{Mn}_{1-x}\text{Co}_x)_2\text{Mo}_3\text{O}_8$ ($0 \leq x \leq 1$)¹⁷. Magnetic data have been collected using SQUID magnetometry with the applied magnetic field aligned along the crystallographic *c* direction (magnetic easy axis). At *x* values below 0.35 (corresponding to $\text{Mn}_{1.3}\text{Co}_{0.7}\text{Mo}_3\text{O}_8$) these materials exhibit ferrimagnetic ordering owing to the differences in magnetic moment between Co^{2+} and Mn^{2+} with suppression of T_N on increasing Co^{2+} contents. Above $x = 0.35$ there is an abrupt change from ferrimagnetic to antiferromagnetic ordering whereby T_N increases with increasing Co^{2+} contents¹⁷. Kurumaji *et al.*, have also looked at the variation of the magnetoelectric response in $\text{Mn}_{2-x}\text{Fe}_x\text{Mo}_3\text{O}_8$ ¹⁸. At $x = 0$ they report a negative correlation of the spin-induced modulation of the pyroelectric current. They also demonstrated that increasing Fe^{2+} incorporation results in a change from ferrimagnetic to antiferromagnetic ordering at $x \approx 1.2$ and significant changes to the pyroelectric current, which in turn “tunes” magnetoelectric coupling in these materials¹⁸. In addition, spin-flop behaviour has been reported for $\text{Mn}_2\text{Mo}_3\text{O}_8$ films (~140 nm) when a 0.5% tensile strain is applied suggesting that further exotic magnetic states might be realised on doping $\text{Mn}_2\text{Mo}_3\text{O}_8$ materials⁴⁰.

Despite extensive work in the area, there remains a lack of fundamental understanding of the structure-property correlations in the manganese material in particular. In this paper, we report a comprehensive powder neutron diffraction study of $\text{Mn}_2\text{Mo}_3\text{O}_8$ and MnAMo_3O_8 (where A is Co, Fe and Zn). We have determined the magnetic structures of these materials and importantly correlate our findings with temperature dependent structural behaviour and magnetic property measurements. This work highlights that the magnetic behaviour of $\text{Mn}_2\text{Mo}_3\text{O}_8$ is not a simplistic ferrimagnetic. We see clear correlations between the spin behaviour on the tetrahedral site and ionic displacement/electrostriction behaviour in $\text{Mn}_2\text{Mo}_3\text{O}_8$. In contrast the octahedral site remains largely unchanged as a function of temperature. These data provide new insight into the complex magnetic behaviour in these materials. Magnetic structure determination from powder neutron diffraction studies for $\text{MnCoMo}_3\text{O}_8$ and $\text{MnFeMo}_3\text{O}_8$ favour antiferromagnetic and ferrimagnetic spin arrangements respectively. Furthermore, A-site cation order is important in the $\text{MnZnMo}_3\text{O}_8$ material for stabilising magnetic states with a small amount of A-site disorder resulting in no



magnetic correlations over the temperature range studied. More work needs to be done in order to understand the role of order/disorder in magnetic co-doped materials.

View Article Online
DOI: 10.1039/D4TC03777D

Experimental

Polycrystalline $\text{Mn}_2\text{Mo}_3\text{O}_8$ and MnAMo_3O_8 ($A^{2+} = \text{Fe}, \text{Co}, \text{Zn}$) were synthesised using the ceramic method in an evacuated, sealed quartz tube²⁹. Stoichiometric amounts of MnO , ZnO , FeO or CoO (all Sigma Aldrich, >99%) and MoO_2 (Alfa Aesar, >99%) were mixed in an agate mortar and sealed in evacuated quartz tubes. The tubes were heated at 1223 K for 16 hours at a heating rate of 10 K min^{-1} . The tubes were subsequently cooled to 1073 K and quenched to room temperature. X-ray diffraction data were collected for these materials at room temperature and 12 K using the PANalytical Empyrean diffractometer ($\text{Cu } \alpha \lambda = 1.5406 \text{ \AA}$) fitted with an Oxford Instruments PHENIX cryostat. Data were collected over a 2θ range of 10° to 70° with a step size of 0.05° (total run time 10 hours).

Magnetic property measurements were performed using a Quantum Design MPMS SQUID magnetometer. Temperature dependent data were collected between 2 K and 300 K in both Zero Field Cooled (ZFC) and Field Cooled (FC) environments with an applied magnetic field (H) of 0.1 T or 5 T. Field dependent susceptibility data were collected at discrete temperatures of 2 K, 30 K, 60 K and 100 K applying magnetic fields between -5 T and 5 T. Heat capacity measurements were performed using a Quantum Design Physical Properties Measurement System (PPMS). Data were collected with the materials pressed into small pellets ($\text{Mn}_2\text{Mo}_3\text{O}_8 = 3.2 \text{ mg}$, $\text{MnCoMo}_3\text{O}_8 = 3.2 \text{ mg}$, $\text{MnFeMo}_3\text{O}_8 = 2.7 \text{ mg}$, $\text{MnZnMo}_3\text{O}_8 = 3.0 \text{ mg}$) over a temperature range of 2 K to 150 K in zero applied fields.

Powder neutron diffraction data for $\text{Mn}_2\text{Mo}_3\text{O}_8$, $\text{MnCoMo}_3\text{O}_8$ and $\text{MnFeMo}_3\text{O}_8$ were collected on the WISH diffractometer at the ISIS Neutron and Muon user facility^{41,42}. Samples were loaded into 3 mm vanadium cans (265 mg $\text{Mn}_2\text{Mo}_3\text{O}_8$, 731 mg $\text{MnCoMo}_3\text{O}_8$, 312 mg $\text{MnFeMo}_3\text{O}_8$) and data were collected across 12 temperature points between 2 K and 200 K for the $\text{Mn}_2\text{Mo}_3\text{O}_8$ material. Data were collected for 15 minutes except for temperatures of 2 K and 200 K where data were collected for 2 hours. Data for $\text{MnFeMo}_3\text{O}_8$ and $\text{MnCo}_2\text{Mo}_3\text{O}_8$ were collected at 2 K and 200 K for 2 hours. Powder neutron diffraction data for $\text{MnZnMo}_3\text{O}_8$ (618 mg) were collected using the GEM diffractometer at the ISIS Neutron and Muon user facility at 200 K and 5 for 6 hours and at temperatures of 150 K, 100 K and 50 K for 2 hours with the sample loaded into a 3 mm vanadium can^{43,44}.



Results and Discussion

View Article Online
DOI: 10.1039/D4TC03777D

Powder diffraction data collected for $\text{Mn}_2\text{Mo}_3\text{O}_8$ confirmed the formation of the expected hexagonal phase. A small amount of second phase is identified as MnMoO_4 (~5%). Rietveld refinements of the data collected at both room temperature (298 K) and 12 K were performed using the GSAS suite of programs^{45,46} in the proposed $P6_3mc$ space group⁴⁷. Refinements were performed for 26 variables which included lattice parameters, atomic positions, zero point, 12 shifted Chebyshev background terms and peak shape fitted using a pseudo-Voigt function. The refinement also included the MnMoO_4 ($C2/m$) phase⁴⁸. Good agreement between the model and the data was observed as shown in figure 2 with no perceivable change in structure between room temperature and 12 K, consistent with reported studies for other $\text{A}_2\text{Mo}_3\text{O}_8$ analogues^{1,5,27,29}. We see no evidence for symmetry lowering ($P6_3mc \rightarrow P6_3$) as has recently been reported for $\text{Fe}_2\text{Mo}_3\text{O}_8$ by spectroscopic studies⁴⁹. Full refinement details and refined parameters are given in table S1 in the ESI[†].

Heat capacity measurements were carried out in order to look at potential magnetic phase transitions in $\text{Mn}_2\text{Mo}_3\text{O}_8$ (figure 3(a)). As expected, the molar heat capacity (C_p) decreases with decreasing temperature until ~40 K where a sharp peak is observed. This is consistent with the magnetic Néel temperature (T_N) reported for $\text{Mn}_2\text{Mo}_3\text{O}_8$ ^{50,51}. A second weak peak in C_p is observed at ~10 K and is associated with the expected magnetic transition in the secondary phase, MnMoO_4 ⁵². Magnetic susceptibility data shows a more complex magnetic behaviour. Zero field cooled (ZFC) and field cooled (FC) temperature dependent data collected in an applied magnetic field of 0.1 T are shown in figure 3(b). A peak in the susceptibility at 39.6(4) K is observed (extracted from a plot of $d\chi/dT$ shown in figure S1(a) in the ESI[†]) with no deviation between ZFC and FC data consistent with long range antiferromagnetic (AFM) ordering. Whilst the shape of the magnetic curve is consistent with previous reported literature^{7,17,21,47}, it is neither suggestive of a sharp phase transition to long-range AFM order nor low dimensional magnetic order (which typically show broader transitions)⁵³. It has been suggested previously that the magnetic anisotropy observed in the magnetic susceptibility data originates from differences in the magnitude of the magnetic moments associated with the tetrahedral and octahedral sites²⁹. However, the differences in energies associated with the crystal field splitting of each of these sites is expected to be small with spin only values on each site predicted to be almost identical potentially ruling out more traditional origins of ferrimagnetism in this material. Another study has suggested the possibility of mixed valence states (+2 and +3) across the octahedral and tetrahedral sites presumably arising as a result of structural defects such as oxygen vacancies which subsequently leads to ferrimagnetic character⁴⁷. In these cases, we would expect to see divergence between ZFC and FC magnetometry data as a result of large differences in the



magnitude of the magnetic moment failing to cancel and resulting in a net magnetic moment in a single crystallographic direction, which we do not see in our studies. It has also been suggested that the magnetic moments associated with the octahedral and tetrahedral sublattices do not cancel each other out over finite temperatures¹⁸. That is, there is possibly a transition from a partially ordered (ferrimagnetic) to a fully ordered (antiferromagnetic state) such that one or both magnetic sites remain dynamic until well below T_N or there is an intermediate canted antiferromagnetic spin state (below T_N). The shape of the temperature dependent susceptibility curve is, however, consistent with a Néel ferrimagnetically ordered state whereby equal magnitude spins are ordered antiferromagnetically across crystallographically distinct sites but where saturation of the spin state has different time scales (temperature) dependencies leading to ferrimagnetic behaviour²¹.


At temperatures between 150 and 300 K $\text{Mn}_2\text{Mo}_3\text{O}_8$ obeys Curie-Weiss behaviour (figure 3(b)). A total effective magnetic moment per formula unit is calculated as $8.52 \mu_B$ consistent with that calculated ($8.35 \mu_B$) using the spin only formula. A negative Weiss constant (θ) of $-132.5(2)$ K is determined consistent with antiferromagnetic ordering. Calculation of the frustration index, f ($f = -T_N/\theta$) gives a value of 3.2 suggesting some level of magnetic frustration in $\text{Mn}_2\text{Mo}_3\text{O}_8$ and is consistent with what we have observed in similarly layered materials⁵³. Magnetic hysteresis loops collected at temperatures of 60 K and 100 K show a linear relationship of the magnetisation as a function of applied field consistent with paramagnetic behaviour. At 2 K we see no hysteric behaviour with the data exhibiting a slight “s” shape as would be expected for long-range antiferromagnetic ordering consistent with our temperature dependent susceptibility measurements and previous literature^{7,17,21,47}. However, at 30 K we see distinct hysteric behaviour with a clear opening of the hysteresis loop at low fields consistent with observations by Das *et al.* who reported similar hysteresis in data collected at 20 K⁷. This indicates that there is a net magnetic moment in these materials, consistent with formation of the ferrimagnetic state (arising from different spin orientations or spin magnitudes on the octahedral and tetrahedral sites) or a transition from a weakly ferromagnetic to antiferromagnetic state within a relatively short temperature range.

In order to shed further insight into the magnetic behaviour of $\text{Mn}_2\text{Mo}_3\text{O}_8$ we collected ZFC cooled magnetic susceptibility data at an applied of 5 T (figure S1(b) in the ESI[†]). These data indicated that at 5 T a sharper magnetic transition is observed, consistent with that expected for antiferromagnetic ordering. This is further confirmed by the negative Weiss constant (θ) of -121.5 K extracted from fitting the Curie-Weiss law between 150 and 300 K at 5 T. The magnetic moment per formula unit ($8.83(1) \mu_B$) is also consistent with that expected for $\text{Mn}_2\text{Mo}_3\text{O}_8$ and that observed at 0.1 T and with data published previously for $\text{Mn}_2\text{Mo}_3\text{O}_8$ ²¹. It



can be suggested that increased field strengths enables the simultaneous long-range order and saturation of the magnetic moments on both tetrahedral and octahedral sites resulting in no net magnetic moment being observed. Equally, this could suggest a field driven phase transition to an antiferromagnetically ordered state similarly to those seen for $\text{Fe}_2\text{Mo}_3\text{O}_8$ and $\text{Co}_2\text{Mo}_3\text{O}_8$ but we have not considered this further here^{25,31}. Lastly, we see no evidence of low temperature spin-flop behaviour, which may have been expected, based on previous studies¹⁸. However, our data has been collected at the lower limits of both the expected temperature and applied magnetic field range previously reported and we cannot confidently rule this out from our data¹⁸.

To further investigate the magnetic spin relationships and understand the temperature dependence observed in magnetometry measurements in $\text{Mn}_2\text{Mo}_3\text{O}_8$ we performed neutron powder diffraction experiments on the WISH diffractometer at the ISIS neutron and muon user facility (UK)⁴¹. Data were refined using the FULLPROF suite of programs to enable determination of both the nuclear and magnetic structures⁵⁴. At temperatures above T_N the data can be readily be fitted to $P6_3mc$ $\text{Mn}_2\text{Mo}_3\text{O}_8$ phase with a small contribution from the MnMoO_4 secondary phase (~5%). Refinements were performed as detailed in the ESI[†]. The refinement profiles for data collected at 200 K and 2 K are shown in figure 4 with refinement profiles and refined parameters for all temperature points given in figures S2, S3 and S4 and tables S2 through S5 in the ESI[†] respectively. With decreasing temperature, we see no change in the $P6_3mc$ nuclear structure consistent with the observations from our powder x-ray diffraction study discussed above. Temperature dependence of the lattice parameters are shown in figure S5 in the ESI[†]. We see that generally the lattice parameters and cell volume decrease with decreasing temperature as expected. However, the a and c lattice parameters show slightly different behaviour. The c lattice parameter plateaus at approximately 60 K. This is consistent with what has been seen in $\text{Fe}_2\text{Mo}_3\text{O}_8$ ⁵⁵ and other layered systems⁵³ and is suggestive of the onset of short-range magnetic correlations. In the a/b plane the lattice parameters show a slight kink at ~40 K and a change in slope consistent with the onset of magnetic order at T_N before reaching a plateau at ~25 K. At T_N we also see an increase in the $\text{Mn}_{\text{tet}}\text{-O-Mn}_{\text{oct}}$ bond angle (~1.76 %) with decreasing temperature. These observations are consistent with ionic displacements, which occur in tandem with ferroelectricity⁵⁶, and suggest the onset potentially of either switchable behaviour or symmetric exchange striction^{57,58} at T_N within $\text{Mn}_2\text{Mo}_3\text{O}_8$. In order to investigate this further we have considered temperature driven changes in the MnO_4 tetrahedral and MnO_6 octahedral units. Previous work has suggested that the pyroelectric (above T_N) and ferroelectric (below T_N) behaviour is linked to the AO_4 tetrahedra, with the polarisation vector directed along the crystallographic c -direction^{17–19}. If we first consider the tetrahedral site, we can see that the bond length between the central Mn



ion (Mn1) and the oxygen at the apex of the tetrahedron (O2) steadily increases ($\sim 2.9\%$) as temperature decreases below ~ 60 K until we reach T_N (figure S6 in the ESI[†]). This is consistent with the onset of the invariant behaviour in the c lattice parameter and ionic displacement in the lattice c -direction. The (Mn1-O2) bond length is then fairly consistent until 2 K where we see a sudden drop to values more consistent with those observed above T_N . The origin of this behaviour is not well understood and may signify the loss of ferroelectric character at low temperature. This could be related to the loss of hysteric behaviour observed in the field dependent magnetometry data and be driven by saturation of the magnetic moments on both the tetrahedral and octahedral sites resulting in an equalisation of the observed moment and loss of the ferrimagnetic ordering. This is interesting as it would suggest that evolution of any possible ferroelectric state is linked to the temperature dependence of the magnetic spin dynamics as opposed to static magnetic order. Alternatively, this may arise as a result of complexities of the refinements at this temperature with two nuclear and two magnetic phases present due to the magnetic ordering of the impurity phase, although we believe this to be unlikely. The bond angles at the base of the tetrahedron (Mn1-O3) decrease slightly at T_N . In contrast the bond lengths in the MnO_6 octahedra vary only slightly (less than 1%) with temperature (figure S6 in the ESI[†]) consistent with thermal effects and isotropic compression of the octahedra with decreasing temperature. This confirms that the onset of multiferroic behaviour is primarily linked to the tetrahedral sites which is consistent with displacements reported for $\text{Fe}_2\text{Mo}_3\text{O}_8$ ^{17–19}. Moreover, Tang *et al*, suggested that the ferroelectric behaviour is correlated to the ferromagnetic coupling in $\text{Co}_2\text{Mo}_3\text{O}_8$ ⁵. As such it is important to understand the magnetic spin state in $\text{Mn}_2\text{Mo}_3\text{O}_8$.

Below 40 K we see the clear onset of increased peak intensity which can be linked to magnetic order on the (101), (103), (201) and (211) reflections. Below this temperature, all data were fit using both the nuclear ($P6_3mc$) structure and a $\text{Mn}_2\text{Mo}_3\text{O}_8$ magnetic phase discussed below. Additionally, below 10 K we also see the evolution of additional magnetic Bragg peaks which are attributable to the magnetic structure of the MnMoO_4 phase⁵⁹ and at 2 K we have refined this phase alongside the $\text{Mn}_2\text{Mo}_3\text{O}_8$ (magnetic and nuclear) phases. For $\text{Mn}_2\text{Mo}_3\text{O}_8$ the magnetic reflections were indexed using a commensurate propagation vector, $\mathbf{k} = (0,0,0)$ in the hexagonal unit cell. Irreducible representations and their corresponding magnetic space groups were determined using the ISODISTORT suite⁶⁰. Four common irreducible representations (IR) and their corresponding magnetic space groups and numbers were determined (as shown in table 1) alongside the direction (\uparrow or \downarrow) of the magnetic moment relative to the crystallographic site and axes. Previous reports have suggested that the magnetic moments aligning along the lattice c -direction are favoured in hexagonal crystal systems^{21,29}. However, in $\text{Ni}_2\text{Mo}_3\text{O}_8$ the complex magnetic order has been shown to give rise



to spins which lie in the lattice a/b plane¹. Refinements performed using the magnetic structures determined from the $\Gamma(5)$ and $\Gamma(6)$ IRs (where the magnetic moments are orientated within the lattice a/b plane) failed to provide magnetic intensity in the correct places leading to unstable refinements. This allows us to rule out both of these models. This leaves structures associated with $\Gamma(2)$ where the magnetic moments are orientated in the so called ferrimagnetic order such that coupling across the two different sites (tetrahedral and octahedral) is AFM whilst between magnetic cations on the same site (either tetrahedral – tetrahedral or octahedral – octahedral) coupling is ferromagnetic and $\Gamma(3)$ where all interactions are antiferromagnetic. We have evaluated both spin structures using data collected at 10 K (since this data is free from the magnetic impurity phase) using the SARAH⁶¹ and FULLPROF suite of programs⁵⁴ (as described in the ESI[†]). The $\Gamma(3)$ model resulted in an unstable refinement such that convergence was never achieved whilst refinements using the $\Gamma(2)$ model resulted in a stable refinement which exhibited an excellent fit to the data (figure S3, ESI[†]). This, confirms that $\text{Mn}_2\text{Mo}_3\text{O}_8$ exhibits a (TT-OO, $\uparrow\uparrow\downarrow\downarrow$) antiferromagnetic (ferrimagnetic) spin order as shown in figure 5(a) and as has been suggested in previous computational^{16,49} and magnetometry work^{21,62} and by peak indexing²⁹. Refinements performed allowing the magnetic moments to be refined independently on the tetrahedral and octahedral sites results in unstable refinements for both the $\Gamma(2)$ and $\Gamma(3)$ models. Since both sites are expected to have the same d^5 electron configuration the magnetic moments across the sites were constrained to have the same value in all refinements. At 2 K the same magnetic structure fit consistently with the data as shown in figure 2(b). This suggests that no magnetic phase transition occurs at low temperature. The magnetic moment was also determined as $4.2 \mu_B$ on each of the Mn^{2+} sites at 2 K consistent with what is expected in neutron diffraction for $S = 5/2$ ions. We have further evaluated the critical exponent (β) extracted from the refined magnetic moments (M) in our powder neutron diffraction data as a function of temperature (T) and given by the equation below (using $T_N = 39.6$ K) and shown in figure S7 in the ESI[†]. This gives $\beta = 0.31(1)$ which is indicative of a 3D Ising antiferromagnetic consistent with both the SQUID magnetometry and powder neutron diffraction data. Furthermore, the fit is robust over a wide temperature range suggesting that there are no new interactions emerging at the lowest temperature measured consistent with the absence of a secondary magnetic phase transition.

$$M_T = M_0 \left(1 - \frac{T}{T_N}\right)^\beta$$

Given the ferrimagnetic spin structure we note that the model for ferroelectric ordering may also be distinct in $\text{Mn}_2\text{Mo}_3\text{O}_8$. In contrast with both $\text{Fe}_2\text{Mo}_3\text{O}_8$ and $\text{Co}_2\text{Mo}_3\text{O}_8$ where the ferromagnetic component is coupled inter-site (i.e. oct-tet) to form ferromagnetic chains, the



ferromagnetic coupling in $\text{Mn}_2\text{Mo}_3\text{O}_8$ is intra-site (i.e. tet-tet or oct-oct). As such $\text{Mn}_2\text{Mo}_3\text{O}_8$ may show exciting magnetoelectric behaviour and this warrants further investigation.

Doping the A-site in $\text{Fe}_2\text{Mo}_3\text{O}_8$ and $\text{Co}_2\text{Mo}_3\text{O}_8$ have been shown to be an effective route for tuning the magnetic properties of these materials^{30–38}. We have prepared materials, MnAMo_3O_8 , where Mn^{2+} is replaced with Fe^{2+} , Zn^{2+} or Co^{2+} in order to investigate A-site cation dependence (tetrahedral versus octahedral) and the role this plays in magnetic ordering. Rietveld refinement of powder x-ray diffraction data collected at 298 K using the GSAS suite of programs^{45,46} confirmed the formation of the expected primary hexagonal phase ($P6_3mc$) for all three MnAMo_3O_8 materials. Refinement profiles and full details are given in table S6 and figure S8 the ESI[†]. We found no evidence for secondary phases in the $\text{MnCoMo}_3\text{O}_8$ material but small amounts of MnMoO_4 were evident in the x-ray diffraction data collected for $\text{MnFeMo}_3\text{O}_8$ (4.2(1) %) and $\text{MnZnMo}_3\text{O}_8$ (3.4(1) %) and were included in our refinements. Lattice parameters extracted for these materials show the expected relationships with atomic size when compared with the end members of the solid solutions ($\text{Zn}_2\text{Mo}_3\text{O}_8$, $\text{Co}_2\text{Mn}_3\text{O}_8$ and $\text{Fe}_2\text{Mo}_3\text{O}_8$) and are consistent with what is expected from previous literature^{29,47}.

Heat capacity data collected for both $\text{MnCoMo}_3\text{O}_8$ and $\text{MnFeMo}_3\text{O}_8$ show a sharp feature at temperature points 35.7(4) K and 49.5(5) K respectively consistent with what we observed for $\text{Mn}_2\text{Mo}_3\text{O}_8$ and are suggestive of the onset of a magnetically ordered phase (figure S9 in ESI[†]). There are clear shifts in temperature on doping which increases $\text{Co} < \text{Mn} < \text{Fe}$. In contrast no features are seen in the C_p data collected for $\text{MnZnMo}_3\text{O}_8$, suggesting that no magnetically ordered state is realised in this material over the temperature range studied. For both $\text{MnFeMo}_3\text{O}_8$ and $\text{MnZnMo}_3\text{O}_8$ we see small contributions in the C_p data at ~ 10 K consistent with the magnetic ordering associated with the secondary phases. Temperature dependent SQUID magnetometry data collected for these materials in an applied field of 0.1 T clearly demonstrates that the type of magnetic ordering is critically dependent upon the transition metal, which are doped on to the A-site (figure 6). Similarly, to $\text{Mn}_2\text{Mo}_3\text{O}_8$, $\text{MnFeMo}_3\text{O}_8$ shows a humped shaped transition at $T_N = 46.8(\text{K})$ (as extracted from a plot of $d\chi/dT$ vs temperature shown in the inset of figure 6(a)) and is consistent with observations from heat capacity data showing an increase in T_N on incorporating Fe^{2+} . We see clear deviation between ZFC and FC data potentially as a result of small differences between the expected magnetic moments for $\text{Mn}^{2+} d^5$ ($5.91 \mu_B$ spin only) and $\text{Fe}^{2+} d^6$ ($4.90 \mu_B$ spin only) electronic configurations. These data suggest that the ferrimagnetic structure is still favoured for $\text{MnFeMo}_3\text{O}_8$ consistent with work performed on the $\text{Fe}_2\text{Mn}_3\text{O}_8 - \text{Mn}_2\text{Mo}_3\text{O}_8$ solid solution which suggests the Fe^{2+} doping leads to an increase in T_N with the ferrimagnetic structure stable to $x \approx 1.2$ (in $\text{Mn}_{2-x}\text{Fe}_x\text{Mo}_3\text{O}_8$)¹⁸. We also see a broad feature in the susceptibility data at approximately 100 K



this is consistent with the Verwey transition in Fe_3O_4 ^{63–65}. Whilst we did not observe any iron oxide based secondary phases in our diffraction data for $\text{MnFeMo}_3\text{O}_8$, it is well known that very small (below the limits of detection in conventional diffraction experiments) iron oxide phases can have a large impact on magnetometry data. Since T_c for Fe_3O_4 is expected to be 856 K⁶⁶ we have not been able to extract meaningful data from the Curie-Weiss fits of the inverse susceptibility. Field dependent data (figure S10(a) in ESI[†]) showed pinched hysteric behaviour characteristic of Fe_3O_4 and no further information can be inferred from these data. However, it would be expected that we would see the same low temperature closure of the hysteresis loops as we observed for $\text{Mn}_2\text{Mo}_3\text{O}_8$ and which is characteristic of the complex interplay between tetrahedral and octahedral sites in these materials.

In contrast with $\text{Mn}_2\text{Mo}_3\text{O}_8$ we see a sharp antiferromagnetic transition in the magnetic susceptibility in $\text{MnCoMo}_3\text{O}_8$ at $T_N = 36.2(1)$ K consistent with what is typically observed for $\text{Co}_2\text{Mn}_3\text{O}_8$ ⁵. This suggests that there is a transition away from the ferrimagnetic structure determined from $\text{Mn}_2\text{Mo}_3\text{O}_8$ towards the antiferromagnetic spin structure expected for $\text{Co}_2\text{Mo}_3\text{O}_8$ which is consistent with the expected transition at $x \approx 0.7$ (in $\text{Mn}_{2-x}\text{Co}_x\text{Mo}_3\text{O}_8$) recently reported by Cheng *et al.*¹⁷. Again we see a some divergence between the ZFC and FC data collected for $\text{MnCoMo}_3\text{O}_8$ consistent with some traditional ferrimagnetic behaviour (net magnetic moment) arising as a result of the differences in magnetic moments between $\text{Mn}^{2+} d^5$ ($5.91 \mu_B$ spin only) and $\text{Co}^{2+} d^7$ ($3.87 \mu_B$ spin only) electronic configurations. This may also be suggestive of some magnetic behaviour arising as a result of incomplete trimerization of the Mo sub-lattice, clustering effects or glassy behaviour. Between 150 K and 300 K we are able to fit the inverse susceptibility to the Curie-Weiss law giving $\theta = -100.1(1)$ K confirming antiferromagnetic order with an effective magnetic moment of $7.69 \mu_B$ per formula unit consistent with what would be expected from the spin only calculation ($7.08 \mu_B$). Calculation of the frustration index gives a value of $f = 2.8$ in line with the value observed for $\text{Mn}_2\text{Mo}_3\text{O}_8$ and suggestive of some weak geometric frustration in $\text{MnCoMo}_3\text{O}_8$. We see no hysteric behaviour at either 300 K or 12 K in $\text{MnCoMo}_3\text{O}_8$ consistent with type A antiferromagnetic order as is described by $\text{Co}_2\text{Mo}_3\text{O}_8$ (figure S10(b) in ESI[†])⁵.

Finally, we see no evidence of any magnetic order within the measured temperature range in the susceptibility data collected for $\text{MnZnMo}_3\text{O}_8$. Previous work investigating Zn doping in $\text{Fe}_2\text{Mo}_3\text{O}_8$ suggests that $\text{FeZnMo}_3\text{O}_8$ is ferrimagnetic with an expected transition to a paramagnetic phase at a composition of approximately $\text{Fe}_{0.75}\text{Zn}_{1.25}\text{Mo}_3\text{O}_8$ ³⁴. Gao *et al.*, have predicted that $\text{CoZnMo}_3\text{O}_8$ (where Zn^{2+} occupies the tetrahedral sites and Co^{2+} the octahedral sites) would be expected to exhibit a striped magnetic order⁶⁷. It therefore, seems reasonable to expect that $\text{MnZnMo}_3\text{O}_8$ could have been predicted to show long-range magnetic order.



However, Gao *et al.* suggested that intersite mixing leads to the suppression of magnetic order in $\text{CoZnMo}_3\text{O}_8$ materials⁶⁷. This suggests that in $\text{MnZnMo}_3\text{O}_8$ there may be intersite mixing too, which results in the observation of paramagnetic behaviour on the level of our measurements. At high temperatures $\text{MnZnMo}_3\text{O}_8$ follows Curie-Weiss behaviour with fits to the inverse susceptibility providing values for $\theta = -21.6(1)$ K and a magnetic moment of $5.4 \mu_B$ consistent with the magnetic moment on Mn^{2+} . The negative Weiss constant may suggest a weakly AFM ordered state with T_N below 2 K but equally these may relate to the small amount of MnMoO_4 impurities present in this material. Likewise, field dependent data (figure S10(c) in ESI[†]) collected at 300 K shows paramagnetic behaviour. In contrast, we see a slight “s” shape to data collected at 2 K. This again may be suggestive of weak (short-range) magnetic order in this material or be related to the small amount of MnMoO_4 . Either way, these data provide no evidence for magnetic order in $\text{MnZnMo}_3\text{O}_8$ over the temperature range studied.

In order to explore cation (dis)order and magnetic structure in these materials we have performed powder neutron diffraction experiments on the WISH ($\text{MnFeMo}_3\text{O}_8$ and $\text{MnCoMo}_3\text{O}_8$)⁴¹ and GEM ($\text{MnZnMo}_3\text{O}_8$)⁴³ diffractometers at the ISIS Neutron and Muon User facility. As expected, the 100 K data for $\text{MnFeMo}_3\text{O}_8$ and $\text{MnCoMo}_3\text{O}_8$ and 298 K data $\text{MnZnMo}_3\text{O}_8$ show excellent fits to the $P6_3mc$ model⁴⁷. Refinement profiles (figures S11 and S12), parameters (tables S7 to S9) and details are given in the ESI[†]. Refinements were performed with secondary phases refined as observed in our powder x-ray diffraction study discussed above. We noted a small amount of MoO_2 in the $\text{MnCoMo}_3\text{O}_8$ sample, which was not detectable in our powder diffraction data. Additionally, for $\text{MnFeMo}_3\text{O}_8$ it was necessary to include both the Fe_3O_4 nuclear and magnetic phases⁶⁸ in our refinements. In order to explore A-site cation (dis)order all refinements were performed with Mn^{2+} and the dopant A-site cation situated on both tetrahedral (Mn1) and octahedral (Mn2) sites and allowed to refine. For both $\text{MnFeMo}_3\text{O}_8$ and $\text{MnCoMo}_3\text{O}_8$ we determined that both A-site cations are randomly distributed across both tetrahedral and octahedral sites. This may explain some of the differences observed in previous studies within SQUID magnetometry data which were performed on single crystals and assumed to exhibit A-site order. This suggests that the magnetic phases obtainable (and thus other properties such as magnetoelectric coupling) can be further tuned through order and/or disorder and more complex cation doping regimes. Refinements performed for $\text{MnZnMo}_3\text{O}_8$ suggests that there is a strong preference for Zn^{2+} to adopt the tetrahedral site with Mn^{2+} on the octahedral site. However, we do see a small amount of intersite mixing (approximately 10%) which may be enough to destabilise the expected magnetic ordering in this material as has been reported by Gao *et al.*⁶⁷.



At low temperature, we see no change in symmetry with all materials readily refined to the $P6_3mc$ model⁴⁷. Refinement details, full refinement profiles (figures S11 and S12) and parameters (tables S7 to S9) are given in the ESI[†]. On visual inspection of the 2 K powder neutron diffraction data collected for $MnFeMo_3O_8$ and $MnCoMo_3O_8$ there are clear differences between the magnetic phases observed, as expected from SQUID magnetometry data. For $MnFeMo_3O_8$ additional magnetic Bragg intensity is observed on the (101), (103), (201) and (211) reflections similarly to those observed for $Mn_2Mo_3O_8$. In contrast, $MnCoMo_3O_8$ shows additional magnetic Bragg intensity on the (100), (101), (200), (210) and (204) reflections. For $MnZnMo_3O_8$ no magnetic Bragg contributions were observed as expected from the SQUID magnetometry measurements. Furthermore, we see no ion displacement or exchange striction effects in either the tetrahedral or octahedral bond lengths which remain reasonably constant over the temperature range studied (as shown in figure S13 in the ESI[†]). This confirms the lack of both magnetic and multiferroic character in $MnZnMo_3O_8$. Following the same procedure, we outlined for $Mn_2Mo_3O_8$ using ISODISTORT⁶⁹ and $\mathbf{k} = (0,0,0)$, gives the same IRs shown in table 1. Refinements were subsequently performed using the $\Gamma(2)$ and $\Gamma(3)$ models since those models derived using IRs $\Gamma(5)$ and $\Gamma(6)$ failed to successfully account for the magnetic intensity observed for both $MnFeMo_3O_8$ and $MnCoMo_3O_8$. For $MnFeMo_3O_8$ we only achieved a stable refinement using the $\Gamma(2)$ model whilst the opposite was true for $MnCoMo_3O_8$ as expected from our previous discussions for $Mn_2Mo_3O_8$ and our SQUID magnetometry data. The extracted magnetic structure for $MnFeMo_3O_8$ is identical to the ferrimagnetic model determined for $Mn_2Mo_3O_8$ (as shown in figure 7) where the magnetic spins are antiferromagnetically coupled across the crystallographically distinct A-sites (tetrahedral – octahedral) and ferromagnetically coupled across the same site (tetrahedral – tetrahedral or octahedral – octahedral). The average magnetic moment on both sites was determined to be $4.20(1) \mu_B$ which is consistent with what we have observed for $Mn_2Mo_3O_8$ although perhaps a little bit higher than might be expected in a mixed system. However, we note that in the 2 K refinement of the $MnFeMo_3O_8$ data, we have a small amount of intensity, which is unaccounted for. Refinements for this phase were complex containing five phases, $MnFeMo_3O_8$ nuclear and magnetic phases, $MnMoO_4$ nuclear phase and Fe_3O_4 nuclear magnetic phases. It is likely that this is either an artefact due to correlations of the fitting parameters across phases or it may be some magnetic intensity we have not accounted for in these refinements. Alternatively, we have considered that this may arise as a result of the Mo trimers not fully compensating. Previous computational studies have suggested that Mo does not contribute to the magnetic ground state¹⁶. Chen *et al.* investigated the possibility of spin liquid magnetic ground states in $A_2Mo_3O_8$ materials (where A is non-magnetic ions, Mg, Sc and Zn)⁷⁰. They observed weak (low magnetic moment) magnetic ordering in these materials at approximately 15 K using SQUID magnetometry. However, they were unable to determine between ferromagnetic



and canted antiferromagnetic ground states with neutron diffraction data demonstrating no discernible magnetic Bragg scattering⁷⁰. Sheckelton *et al.* looked at disrupting the Mo trimers through the addition of lithium in the material, $\text{LiZn}_2\text{Mo}_3\text{O}_8$ ⁷¹. They suggest that $\frac{2}{3}$ of the Mo magnetic spins condense into singlet states below 96 K. However, no long-range static magnetically ordered state is observed with no magnetic Bragg peaks observed in powder neutron diffraction data⁷¹. This suggests that whilst small contributions to SQUID magnetometry data may arise as a result of incomplete trimerization of the Mo sub-lattice it is unlikely to be observable within our powder neutron powder diffraction study as either resolvable magnetic Bragg character or additional intensity. Lastly, given that a transition to the antiferromagnetic state is expected at $x \sim 1.2$, it is plausible that a mixed magnetically ordered state is observed with both ferrimagnetic and antiferromagnetic order present within our sample potentially as a result of cation inhomogeneity¹⁸. However, due to the complexity of these refinements we have not been able to investigate this further. Additionally, since that the magnetic structure we have derived for this material is consistent with the SQUID magnetometry data we are confident in our structural solution. Additionally, we did not see any contribution from the magnetic phase of MnMoO_4 presumably because the signal from this component is too weak to detect. Likewise, for $\text{MnCoMo}_3\text{O}_8$ we also see no evidence of magnetic contributions from MnMoO_4 in our data. Refinement of the magnetic structure (shown schematically in figure 7) indicates antiferromagnetic coupling both across crystallographically distinct sites (tetrahedral and octahedral) and importantly between crystallographically identical sites (tetrahedral – tetrahedral and octahedral – octahedral) consistent with what is expected for $\text{Co}_2\text{Mo}_3\text{O}_8$ ⁵. Magnetic moments were calculated to be $3.38(1) \mu_B$ consistent with what is expected for a mixed $\text{Co}^{2+}/\text{Mn}^{2+}$ material.

Conclusions

We have investigated the structure-property correlations in $\text{Mn}_2\text{Mo}_3\text{O}_8$, $\text{MnFeMo}_3\text{O}_8$, $\text{MnCoMo}_3\text{O}_8$ and $\text{MnZnMo}_3\text{O}_8$ using powder neutron diffraction and magnetic property measurements. For $\text{Mn}_2\text{Mo}_3\text{O}_8$ we confirm the ferrimagnetic model for the magnetic structure such that magnetic moments are coupled antiferromagnetically across crystallographically distinct A-sites (tetrahedral-octahedral) and ferromagnetically for individual sites (tetrahedral – tetrahedral or octahedral – octahedral). Interestingly, ionic displacements and/or exchange striction behaviour on the tetrahedral site appears to be critically dependent on the spin behaviour on the tetrahedral site with a sudden drop in the Mn-O bond length at the apex of the tetrahedral unit at 2 K. This is important, as it is coincident with the loss of hysteric behaviour and the realisation of a compensated antiferromagnetic state. The driving forces behind this are not known. It remains undetermined if a switchable ferroelectric state is achieved at T_N with some kind of re-entrant non-switchable or alternative state realised at 2 K



or if a fully switchable ferroelectric state is not obtainable until 2 K. We note that whilst the ferroelectric state has been shown to exist in both $\text{Fe}_2\text{Mo}_3\text{O}_8$ and $\text{Co}_2\text{Mo}_3\text{O}_8$ it has yet to be confirmed in $\text{Mn}_2\text{Mo}_3\text{O}_8$ ^{5,72}. This warrants further investigation to fully understand any electronic behaviour and potential magnetoelectric coupling (as has been reported for $\text{Fe}_2\text{Mo}_3\text{O}_8$, $\text{Ni}_2\text{Mo}_3\text{O}_8$ and $\text{Co}_2\text{Mn}_3\text{O}_8$ ^{5,23,28,72}) in this material.

The magnetic structures for $\text{MnFeMo}_3\text{O}_8$ and $\text{MnCoMo}_3\text{O}_8$ have been determined as ferrimagnetic and antiferromagnetic respectively. In contrast $\text{MnZnMo}_3\text{O}_8$ shows no long range magnetic order down to 2 K. Our data suggests that these materials are cation disordered with A^{2+} and Mn^{2+} distributed randomly on both tetrahedral and octahedral sites in both the Co and Fe analogues whilst some site preference is shown in the Zn material (~90% site order for Mn on the octahedral site and Zn on the tetrahedral site). Further work is required to understand the roles of cation (dis)order in these systems for tuning the magnetic character in these materials^{34,67}

Overall, this work demonstrates that there is still much to unravel with respect to the structure-property correlations in $\text{Mn}_2\text{Mo}_3\text{O}_8$ and related systems. This is a magnetically rich family of materials with the potential for careful property tuning leading to many exciting and technologically important applications.

Acknowledgements

DCA, SR, HLM are grateful for the award of a Leverhulme Research grant (RPG_2019_220). We are grateful for the provision of beamtime RB222055¹⁴¹ and XB2390084⁴³ at the ISIS Neutron and Muon Source (UK). We are also grateful for access to the Materials Characterisation laboratory (MCL) at the ISIS Neutron and Muon Source (UK) for access to magnetic property measurements.

Conflicts of interest

We report no conflicts of interest

Data availability

Electronic supplementary information (ESI[†]) includes all refinement details (including information about which refinement software has been used, what has been refined and how the data has been treated) and refined data alongside supporting magnetic property data for all materials presented in this work. Powder neutron diffraction raw data is available through the ISIS data gateway with <https://doi.org/10.5286/ISIS.E.RB222055> and <https://doi.org/10.5286/ISIS.E.XB2390084> for the WISH and GEM data respectively^{41,43}.



References

- 1 P. Yadav, S. Lee, G. L. Pascut, J. Kim, M. J. Gutmann, X. Xu, B. Gao, S. W. Cheong, V. Kiryukhin and S. Choi, *Phys Rev Res*, DOI:10.1103/PhysRevResearch.5.033099.
- 2 I. V. Solovyev and S. V. Streltsov, DOI:10.1103/PhysRevMaterials.3.114402.
- 3 S. Reschke, D. G. Farkas, A. Strinić, S. Ghara, K. Guratinder, O. Zaharko, L. Prodan, V. Tsurkan, D. Szaller, S. Bordács, J. Deisenhofer and I. Kézsmárki, *NPJ Quantum Mater*, DOI:10.1038/s41535-021-00417-3.
- 4 M. Eremin, K. Vasin and A. Nurmukhametov, *Materials*, DOI:10.3390/ma15228229.
- 5 Y. S. Tang, S. M. Wang, L. Lin, C. Li, S. H. Zheng, C. F. Li, J. H. Zhang, Z. B. Yan, X. P. Jiang and J. M. Liu, *Phys Rev B*, DOI:10.1103/PhysRevB.100.134112.
- 6 J. Ding, Y. Huang, Z. Liu, X. Wang, Y. Zhang, Y. Guo, R. Sheng, D. Jia, X. Tang and L. Wang, *Chemical Engineering Journal*, DOI:10.1016/j.cej.2021.133984.
- 7 B. Das, M. V. Reddy, C. Krishnamoorthi, S. Tripathy, R. Mahendiran, G. V. S. Rao and B. V. R. Chowdari, *Electrochim Acta*, 2009, **54**, 3360–3373.
- 8 S. Gao, Y. Tang, Y. Gao, L. Liu, H. Zhao, X. Li and X. Wang, *ACS Appl Mater Interfaces*, 2019, **11**, 7006–7013.
- 9 S. Petnikota, S. K. Marka, V. V. S. S. Srikanth, M. V. Reddy and B. V. R. Chowdari, *Electrochim Acta*, 2015, **178**, 699–708.
- 10 O. R. Ankinapalli, B. N. V. Krishna, Y. Hua and J. S. Yu, *J Alloys Compd*, DOI:10.1016/j.jallcom.2022.167063.
- 11 A. M. Patil, N. R. Chodankar, E. Jung, S. Roy, D. P. Dubal, G. Guan, Y. K. Han and S. C. Jun, *J Mater Chem A Mater*, 2021, **9**, 26135–26148.
- 12 T. Ouyang, X. T. Wang, X. Q. Mai, A. N. Chen, Z. Y. Tang and Z. Q. Liu, *Angewandte Chemie - International Edition*, 2020, **59**, 11948–11957.
- 13 L. J. Xie, C. F. Li, J. W. Zhao, L. F. Gu, J. Q. Wu, Y. Wang and G. R. Li, *Chemical Engineering Journal*, DOI:10.1016/j.cej.2021.133119.
- 14 W. Hu, Q. Shi, Z. Chen, H. Yin, H. Zhong and P. Wang, *ACS Appl Mater Interfaces*, 2021, **13**, 8337–8343.
- 15 R. Nadarajan, A. V. Gopinathan, N. P. Dileep, A. S. Sidharthan and M. M. Shaijumon, *Nanoscale*, 2023, **15**, 15219–15229.
- 16 L. Wen, J. Zhai, J. Song, H. Jiang, R. Cui, Y. Xu, K. Sun and X. Hao, *J Solid State Chem*, DOI:10.1016/j.jssc.2022.122910.
- 17 Y. Chang, B. You, Y. Xie, Y. Liu, R. Xiong, C. Lu and J. M. Liu, *Appl Phys Lett*, DOI:10.1063/5.0163761.
- 18 T. Kurumaji, S. Ishiwata and Y. Tokura, *Phys Rev B*, DOI:10.1103/PhysRevB.95.045142.



- 19 M. V. Eremin, K. V. Vasin and A. R. Nurmukhametov, *Journal of Experimental and Theoretical Physics*, 2023, **137**, 506–519. Article Online
DOI: 10.1039/D4TC03777D
- 20 T. Kurumaji, Y. Takahashi, J. Fujioka, R. Masuda, H. Shishikura, S. Ishiwata and Y. Tokura, *Phys Rev B*, DOI:10.1103/PhysRevB.95.020405.
- 21 S. P. Mcalister and P. Strobel, *MAGNETIC ORDER IN M2M030 s SINGLE CRYSTALS (M = Mn, Fe, Co, Ni)*, North-Holland Publishing Company, 1983, vol. 30.
- 22 S. Bao, Z. L. Gu, Y. Shangguan, Z. Huang, J. Liao, X. Zhao, B. Zhang, Z. Y. Dong, W. Wang, R. Kajimoto, M. Nakamura, T. Fennell, S. L. Yu, J. X. Li and J. Wen, *Nat Commun*, DOI:10.1038/s41467-023-41791-9.
- 23 Y. Chang, Y. Weng, Y. Xie, B. You, J. Wang, L. Li, J. M. Liu, S. Dong and C. Lu, *Phys Rev Lett*, DOI:10.1103/PhysRevLett.131.136701.
- 24 K. V. Vasin, A. Strinić, F. Schilberth, S. Reschke, L. Prodan, V. Tsurkan, A. R. Nurmukhametov, M. V. Eremin, I. Kézsmárki and J. Deisenhofer, *Phys Rev B*, 2024, **110**, 054401.
- 25 Y. S. Tang, G. Z. Zhou, L. Lin, R. Chen, J. F. Wang, C. L. Lu, L. Huang, J. H. Zhang, Z. B. Yan, X. M. Lu, X. K. Huang, X. P. Jiang and J. M. Liu, *Phys Rev B*, DOI:10.1103/PhysRevB.105.064108.
- 26 S. Li, M. D. Le, V. Loganathan and A. H. Nevidomskyy, *Phys Rev Mater*, DOI:10.1103/PhysRevMaterials.6.014405.
- 27 J. R. Morey, A. Scheie, J. P. Sheckelton, C. M. Brown and T. M. McQueen, *Phys Rev Mater*, DOI:10.1103/PhysRevMaterials.3.014410.
- 28 Y. S. Tang, J. H. Zhang, L. Lin, R. Chen, J. F. Wang, S. H. Zheng, C. Li, Y. Y. Zhang, G. Z. Zhou, L. Huang, Z. B. Yan, X. M. Lu, D. Wu, X. K. Huang, X. P. Jiang and J. M. Liu, *Phys Rev B*, DOI:10.1103/PhysRevB.103.014112.
- 29 D. Bertrand and H. Kerner-Czeskleba, *Journal de Physique*, DOI:10.1051/jphys:01975003605037900i.
- 30 T. Ideue, T. Kurumaji, S. Ishiwata and Y. Tokura, *Nat Mater*, 2017, **16**, 797–802.
- 31 T. Kurumaji, S. Ishiwata and Y. Tokura, *Phys Rev X*, DOI:10.1103/PhysRevX.5.031034.
- 32 W. Wang, C. Wang, P. Li, J. Li, J. Xian, K. Cheng, C. M. Leung and M. Zeng, *Ceram Int*, 2022, **48**, 24326–24331.
- 33 W. Wang, P. Z. Li, Y. T. Chang, M. F. Liu, C. L. Lu, X. B. Lu, M. Zeng and J. M. Liu, *Appl Phys Lett*, DOI:10.1063/5.0044565.
- 34 S. Nakayama, R. Nakamura, M. Akaki, D. Akahoshi and H. Kuwahara, *J Physical Soc Japan*, DOI:10.1143/JPSJ.80.104706.
- 35 C. Zhang, Y. Zhao, H. Nie, C. Zheng, F. Li, D. Zhou, R. Gao, H. Shen, S. Jiang, L. Zhang and J. Sun, *Phys Status Solidi B Basic Res*, DOI:10.1002/pssb.202200558.
- 36 B. Csizi, S. Reschke, A. Strinić, L. Prodan, V. Tsurkan, I. Kézsmárki and J. Deisenhofer, *Phys Rev B*, DOI:10.1103/PhysRevB.102.174407.
- 37 J. Yang, D. Su, J. He, Y. Ji, Q. Guo, Y. Meng, X. Li, L. Wang, X. Shen, Y. Yao, Y. Long, Y. Sun and R. Yu, *Phys Rev B*, DOI:10.1103/PhysRevB.107.104408.



- 38 Z. Yu, H. Ding, K. Zhai, C. Mu, A. Nie, J. Cong, J. Huang, H. Zhou, Q. Wang, F. Wen, J. Xiang, B. Wang, T. Xue, Z. Zeng and Z. Liu, *Phys Rev B*, DOI:10.1103/PhysRevB.109.024442.
- 39 L. Prodan, I. Filippova, A. O. Zubtsovskii, S. Shova, S. Widmann, A. A. Tsirlin, I. Kézsmárki and V. Tsurkan, *Phys Rev B*, DOI:10.1103/PhysRevB.106.174421.
- 40 S. Mo, T. Katayama, A. Chikamatsu, M. Kitamura, K. Horiba, H. Kumigashira and T. Hasegawa, *Chemistry of Materials*, 2021, **33**, 7713–7718.
- 41
- 42 L. C. Chapon, P. Manuel, P. Radaelli, C. Benson, L. Perrot, S. Ansell, N. J. Rhodes, D. Raspino, D. Duxbury, E. Spill and J. Norris, *Neutron News*, 2011, **22**, 22–25.
- 43
- 44 A. C. Hannon, *Nuclear Instruments and Methods in Physics Research A*, 2005, **551**, 88–107.
- 45 A. C. , Larson and R. B. von Dreele, *Los Alamos National Report LAUR*, 1994, **96**, 86.
- 46 B. H. Toby, *J. Appl. Cryst.*, 2001, **34**, 210–213.
- 47 H. Abe, A. Sato, N. Tsujii, T. Furubayashi and M. Shimoda, *J Solid State Chem*, 2010, **183**, 379–384.
- 48 S. C. Abrahams and J. M. Reddy, *Journal of Chemical Physics*, 1965, **43**, 2533–2543.
- 49 T. N. Stanislavchuk, G. L. Pascut, A. P. Litvinchuk, Z. Liu, S. Choi, M. J. Gutmann, B. Gao, K. Haule, V. Kiryukhin, S. W. Cheong and A. A. Sirenko, *Phys Rev B*, DOI:10.1103/PhysRevB.102.115139.
- 50 T. Kurumaji, Y. Takahashi, J. Fujioka, R. Masuda, H. Shishikura, S. Ishiwata and Y. Tokura, *Phys Rev B*, DOI:10.1103/PhysRevB.95.020405.
- 51 V. G. Bessergenev, Y. A. Kovalevskaya, I. E. Paukov, M. A. Starikov, H. Oppermann and W. Reichelt, *J. Chem. Thermodynam.*, 1992, **24**, 85–98.
- 52 G. Lautenschlager, H. Weitzel, H. Fuess and E. Ressouche, *Zeitschrift fur Kristallographie*, 1994, **209**, 936–940.
- 53 L. J. Vera Stimpson, E. E. Rodriguez, C. M. Brown, G. B. G. Stenning, M. Jura and D. C. Arnold, *J Mater Chem C Mater*, 2018, **6**, 4541–4548.
- 54 J. Rodriguez Carvajal, *Physic B.*, 1993, **192**, 55–69.
- 55 S. Reschke, A. A. Tsirlin, N. Khan, L. Prodan, V. Tsurkan, I. Kézsmárki and J. Deisenhofer, *Phys Rev B*, DOI:10.1103/PhysRevB.102.094307.
- 56 S.-W. Cheong and M. Mostovoy, *Nat Mater*, 2007, **6**, 13–20.
- 57 J. A. McAllister and J. P. Atfield, *J. Mater. Chem.*, 1998, **8**, 1291–1294.
- 58 M. Eremin, K. Vasin and A. Nurmukhametov, *Materials*, DOI:10.3390/ma15228229.
- 59 G. Lautenschlager, H. Weitzel, H. Fuess and E. Ressouche, *Zeitschrift fur Kristallographie*, 1994, **209**, 936–940.
- 60 B. J. Campbell, H. T. Stokes, D. E. Tanner and D. M. Hatch, *J. Appl. Cryst.*, 2006, **39**, 607–614.



- 61 R. Grethe, K. J. W. Etherdo-Sibley, C. Tang, S. Day, D. C. Arnold and E. Schofield, *J Cult Herit*, 2022, **55**, 221–227. New Article Online
DOI: 10.1039/D4TC03777D
- 62 D. Szaller, K. Szász, S. Bordács, J. Viirok, T. Rőöm, U. Nagel, A. Shuvaev, L. Weymann, A. Pimenov, A. A. Tsirlin, A. Jesche, L. Prodan, V. Tsurkan and I. Kézsmárki, *Phys Rev B*, DOI:10.1103/PhysRevB.102.144410.
- 63 Senn M. S., I. Loa, J. P. Wright and J. P. Attfield, *Phys. Rev. B.*, 2012, **85**, 125119.
- 64 E. J. W. Verwey, *Nature*, 1939, **144**, 327–328.
- 65 R. Zierold, C. Le Lann, J. Dendooven and F. Walz, *J. Phys: Condensed Matter*, 2002, **14**, R285.
- 66 D. Levy, R. Giustetto and A. Hoser, *Physics and Chemistry of Materials*, 2012, **39**, 169–176.
- 67 B. Gao, T. Chen, C. L. Huang, Y. Qiu, G. Xu, J. Liebman, L. Chen, M. B. Stone, E. Feng, H. Cao, X. Wang, X. Xu, S. W. Cheong, S. M. Winter and P. Dai, *Phys Rev B*, DOI:10.1103/PhysRevB.108.024431.
- 68 M. E. Fleet, *Act Cryst. B.*, 1981, **37**, 917–920.
- 69 B. J. Campbell, H. T. Stokes, D. E. Tanner and D. M. Hatch, *J. Appl. Cryst.*, 2006, **39**, 607–614.
- 70 Q. Chen, R. Sinclair, A. Akbari-Sharbat, Q. Huang, Z. Dun, E. S. Choi, M. Mourigal, A. Verrier, R. Rouane, X. Bazier-Matte, J. A. Quilliam, A. A. Aczel and H. D. Zhou, *Phys Rev Mater*, DOI:10.1103/PhysRevMaterials.6.044414.
- 71 J. P. Sheckelton, J. R. Neilson, D. G. Soltan and T. M. McQueen, *Nat Mater*, 2012, **11**, 493–496.
- 72 Y. Wang, G. L. Pascut, B. Gao, T. A. Tyson, K. Haule, V. Kiryukhin and S. W. Cheong, *Sci Rep*, DOI:10.1038/srep12268.



List of Figures and Tables

View Article Online
DOI: 10.1039/D4TC03777D

Table 1: Irreducible representations (IRs) and corresponding magnetic space groups generated for $Mn_2Mo_3O_8$ within the parent $P6_3mc$ space group and $k = (0,0,0)$ using the ISODISTORT suite. Information related to spin direction and orientation is also provided for each IR. Note TTOO relates to tetrahedral-tetrahedral-octahedral-octahedral spin coupling and 0000 denotes that the spins lie perpendicular to the lattice c -direction.

IR	Magnetic Space Group	Space Group Number	Moment parallel to lattice c -direction TTOO	a/b plane moment allowed
$\Gamma(2)$	$P6_3m'c$	186.207	$\uparrow\uparrow\downarrow\downarrow$	No
$\Gamma(3)$	$P6_3m'c'$	186.205	$\uparrow\uparrow\downarrow\downarrow$	No
$\Gamma(5)$	$Cmc2_1$	36.172	0000	Yes
	$Cm'c'2_1$	36.176	$\uparrow\uparrow\downarrow\downarrow$	Yes
	$P2_1$	4.7	$\uparrow\uparrow\downarrow\downarrow$	Yes
$\Gamma(6)$	$Cmc'2_1'$	36.175	0000	Yes
	$Cm'c2_1'$	36.174	$\uparrow\uparrow\downarrow\downarrow$	Yes
	$P2_1'$	4.9	$\uparrow\uparrow\downarrow\downarrow$	Yes

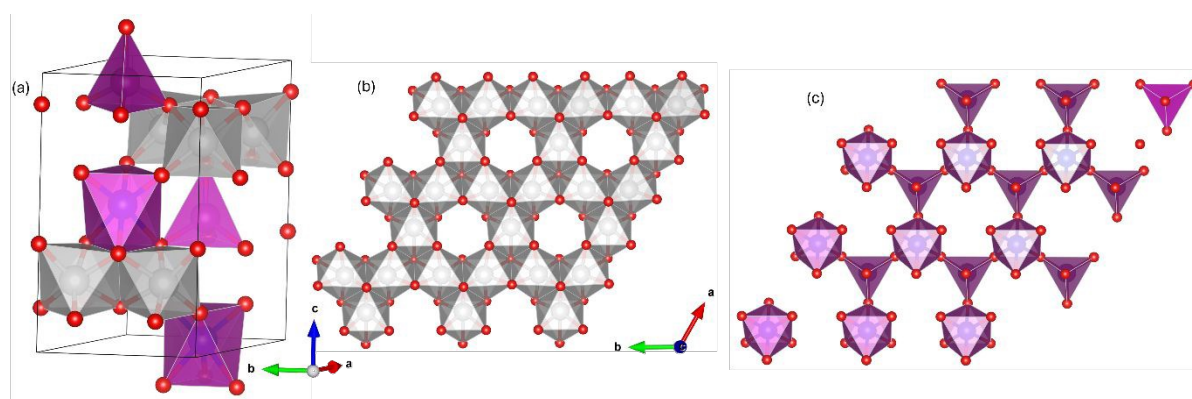



Figure 1: Schematic representation of the $A_2Mo_3O_8$ structure where (a) shows the stacking of the Mo_6 Kagomé and AO honeycomb lattices in the lattice c -direction, (b) shows the MoO_6 layer in the lattice a/b plane showing the trimerization of the Mo ions and (c) shows the alternating honeycomb connectivity of AO_6 octahedra and AO_4 tetrahedra. The pink polyhedra and triangles represent the A-site octahedra and tetrahedra respectively, the grey polyhedral the MoO_6 octahedra and the red sphere the oxygen atoms respectively.



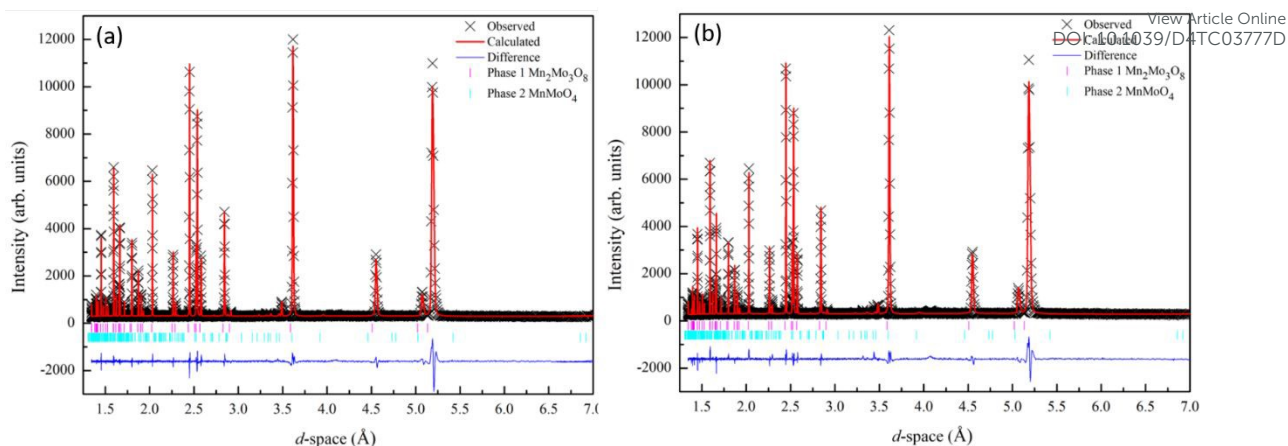


Figure 2: Rietveld refinement of the x-ray diffraction data collected for $\text{Mn}_2\text{Mo}_3\text{O}_8$ and fitted to the $P6_3mc$ model⁴⁷ at (a) 298 K ($wRp = 7.5\%$, $Rp = 5.74$, $\chi^2 = 2.7$) and (b) 12 K ($wRp = 8.6\%$, $Rp = 6.3\%$, $\chi^2 = 3.5$). Black crosses represent observed data, red line represents the calculated model and the blue line represents the difference between the observed and calculated data. $\text{Mn}_2\text{Mo}_3\text{O}_8$ is represented by the magenta tick marks (top) and MnMoO_4 by the cyan tick marks (bottom).

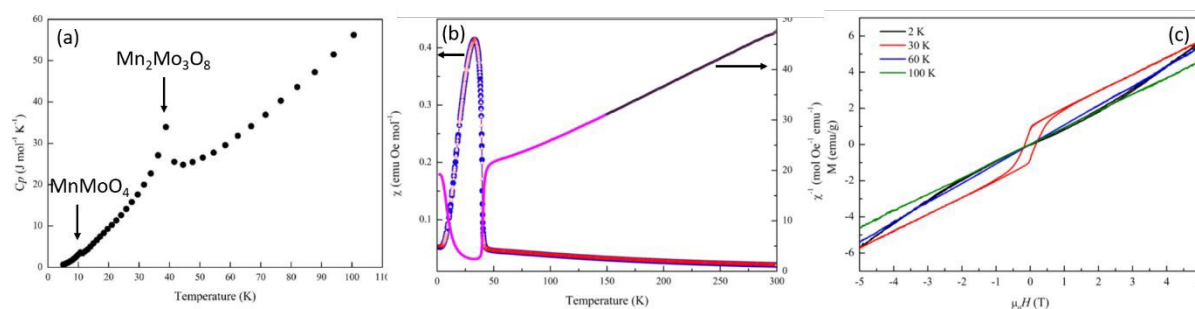


Figure 3: Physical property data collected for $\text{Mn}_2\text{Mo}_3\text{O}_8$ showing (a) Molar heat capacity (C_p) data indicating a sharp increase in C_p at approximately 40 K consistent with T_N for $\text{Mn}_2\text{Mo}_3\text{O}_8$ and a weaker inflection at ~ 10 K attributable to the magnetic transition in MnMoO_4 , (b) Zero field cooled (blue) and field cooled (red) data measured at 0.1 T and inverse ZFC susceptibility data where the black line shows the fit to the Curie-Weiss law and (c) field (H) dependent magnetisation data collected at 2 K (black), 30 K (red), 60 K (blue) and 200 K (green).



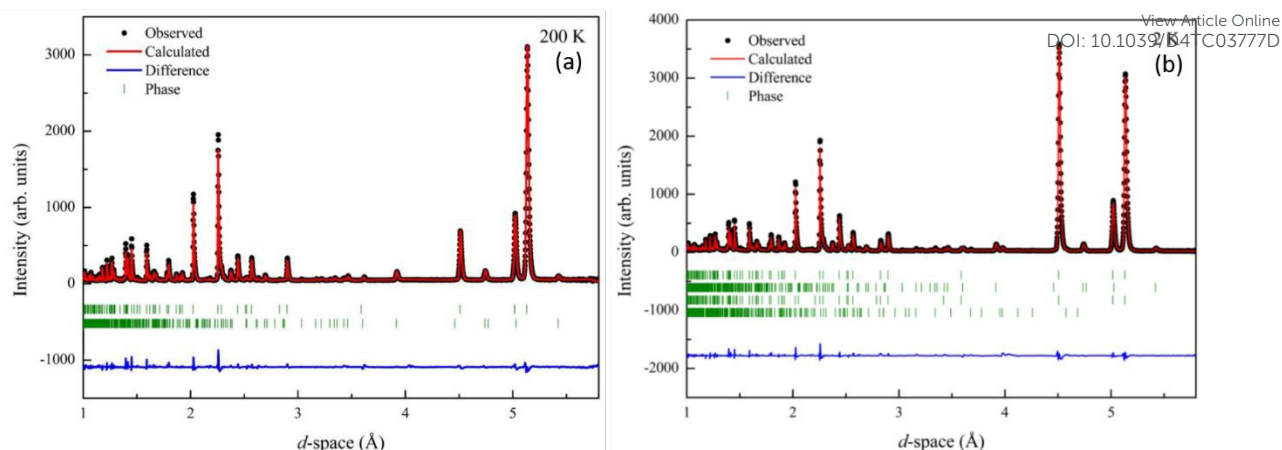


Figure 4: Rietveld refinement of the powder neutron diffraction (WISH) data collected for $Mn_2Mo_3O_8$ and fitted to the $P6_3mc$ model⁴⁷ at (a) 200 K ($wRp = 13.9\%$, $Rp = 11.5$, $\chi^2 = 0.8$) and (b) 2 K ($wRp = 11.9\%$, $Rp = 8.65\%$, $\chi^2 = 0.92$). Black crosses represent observed data, red line represents the calculated model and the blue line represents the difference between the observed and calculated data. From top to bottom the tick marks represent the $Mn_2Mo_3O_8$ (nuclear phase), $MnMoO_4$ (nuclear phase), $Mn_2Mo_3O_8$ (magnetic phase) and $MnMoO_4$ (magnetic phase) respectively.

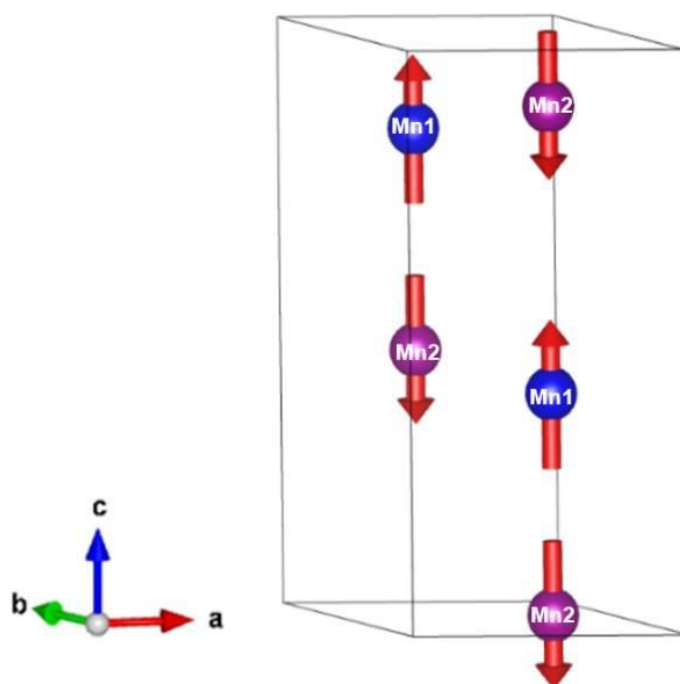


Figure 5: Magnetic spin structure (red arrows) determined for $Mn_2Mo_3O_8$ within the unit cell (black outline) at 10 K from the Rietveld refinement of powder neutron diffraction data. The blue and pink spheres represent manganese on the Mn1 (tetrahedral) and Mn2 (octahedral) crystallographic sites respectively.



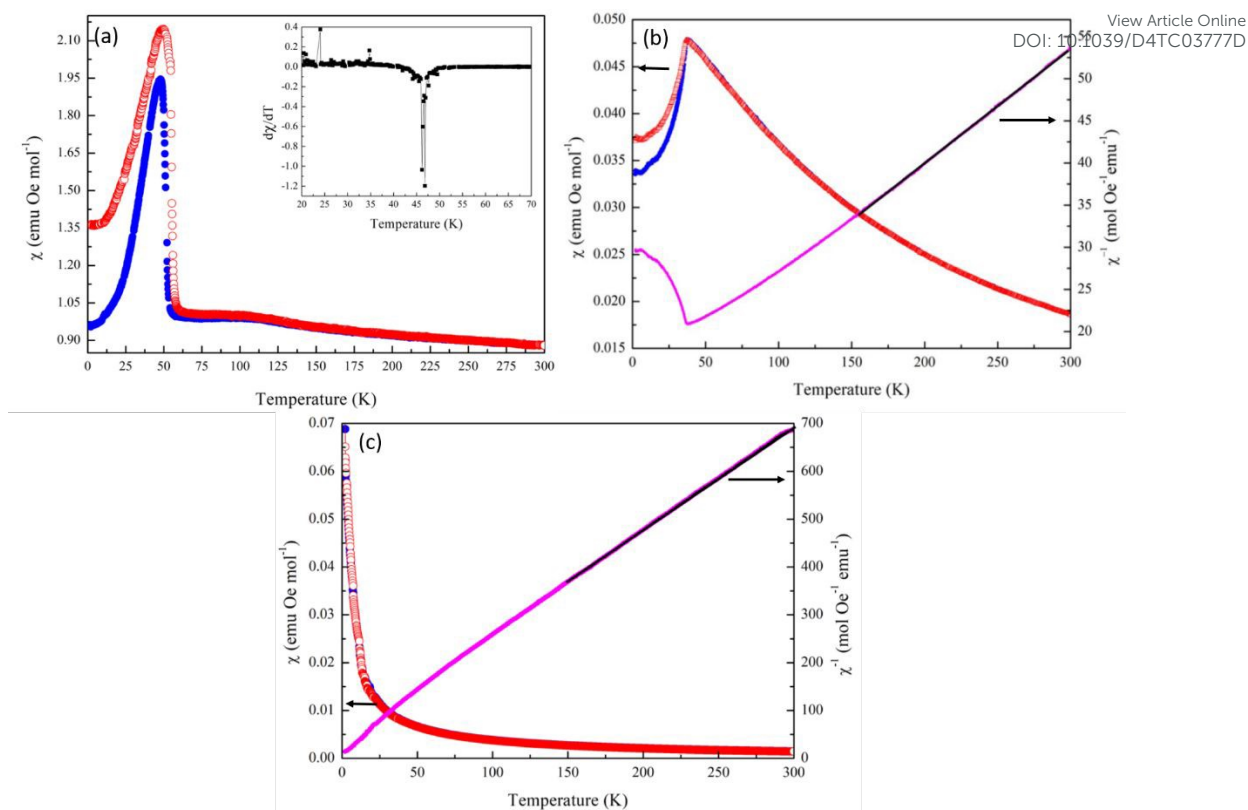


Figure 6: Zero field cooled (blue) and field cooled (red) SQUID magnetometry data collected at 0.1 T and inverse ZFC susceptibility data where the black line shows the fit to the Curie-Weiss law for (a) $\text{MnFeMo}_3\text{O}_8$ inset shows the $d\chi/dT$ data highlighting T_N at ≈ 46 K, (b) $\text{MnCoMo}_3\text{O}_8$ showing $T_N \approx 35$ K and (c) $\text{MnZnMo}_3\text{O}_8$ showing paramagnetic character.

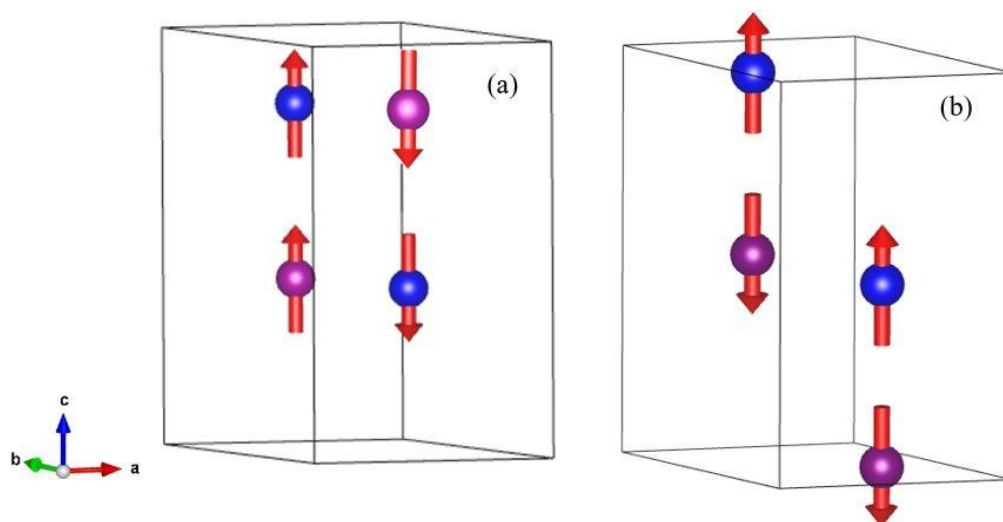


Figure 7: Magnetic spin structure (red arrows) determined for (a) $\text{MnCoMo}_3\text{O}_8$ and (b) $\text{MnFeMo}_3\text{O}_8$ within the unit cell (black outline) at 2 K from the Rietveld refinement of powder neutron diffraction data. The blue and pink spheres represent manganese on the Mn1 (tetrahedral) and Mn2 (octahedral) crystallographic sites respectively.



Data statementView Article Online
DOI: 10.1039/D4TC03777D

Electronic supplementary information (ESI[†]) includes all refinement details (including information about which refinement software has been used, what has been refined and how the data has been treated) and refined data alongside supporting magnetic property data for all materials presented in this work. Powder neutron diffraction raw data is available through the ISIS data gateway with <https://doi.org/10.5286/ISIS.E.RB222055> and <https://doi.org/10.5286/ISIS.E.XB2390084> for the WISH and GEM data respectively. These have been referenced in the manuscript.

