

Cite this: *Chem. Sci.*, 2016, 7, 5294

Theranostic metal–organic framework core–shell composites for magnetic resonance imaging and drug delivery†

Huai-Xin Zhao,^{‡b} Quan Zou,^{‡a} Shao-Kai Sun,^a Chunshui Yu,^{ac} Xuejun Zhang,^a Rui-Jun Li^a and Yan-Yan Fu^{*a}

Metal–organic frameworks (MOFs) have shown great potential in designing theranostic probes for cancer diagnosis and therapy due to their unique properties, including versatile structures and composition, tunable particle and pore size, enormous porosity, high surface area, and intrinsic biodegradability. In this study, we demonstrate novel MOF-based theranostic Fe₃O₄@UiO-66 core–shell composites constructed by *in situ* growth of a UiO-66 MOF shell on a Fe₃O₄ core for simultaneous drug delivery and magnetic resonance (MR) imaging. In the composites, the UiO-66 shell is devoted for encapsulating the drug, whereas the Fe₃O₄ core serves as a MR contrast agent. The Fe₃O₄@UiO-66 core–shell composites show good biocompatibility, high drug loading capacity, sustained drug release, and outstanding MR imaging capability, as well as effective chemotherapeutic efficacy, demonstrating the feasibility of designing theranostic Fe₃O₄@UiO-66 core–shell composites for cancer diagnosis and therapy.

Received 27th March 2016

Accepted 25th April 2016

DOI: 10.1039/c6sc01359g

www.rsc.org/chemicalscience

Introduction

Metal–organic frameworks (MOFs) are an emerging class of organic–inorganic hybrid porous materials built from metal ion or cluster nodes and organic linkers, which have already been explored for a variety of applications, including separation, catalysis, and gas storage.^{1,2} In recent years, MOFs have been scaled down to nanometer sizes to form nanoscale MOFs and focused on their preliminary biomedical applications in drug delivery and bioimaging.^{3–6}

MOFs have been successfully employed as drug delivery vehicles owing to their unique properties suitable for drug loading and release.⁷ Different from most of the existing pure organic and inorganic carrier materials, MOFs have exceptionally high surface area and enormous porosity, which are favorable for entrapment of large amounts of drugs, tunable pore size and hydrophilic–hydrophobic cavities to host a variety of drugs with different physico-chemical properties, controllable host–guest interactions and intrinsic biodegradability. Since

Ferey's group⁸ first reported the ability of iron-based MOFs as drug carriers to encapsulate ibuprofen molecules at unprecedented levels and deliver the drug continuously, with no burst effect, many researchers have developed other MOFs, such as UMCM-1, ZIF-8, MIL-53, MOF-74, Gd-MOF, UiO-66, Cu-BTC, and chiral MOFs, for drug delivery.^{9–18}

Paramagnetic metal ions-containing MOFs are also promising as contrast agents for magnetic resonance (MR) imaging.^{19,20} Compared with clinical small molecule contrast agents, the framework construction features ensure that MOFs not only possess large amounts of paramagnetic metal centers, but also exhibit enhanced per-metal-based relaxivity. Lin and co-workers first demonstrated the potential of Gd-based MOFs as MR contrast agents.²¹ The Gd-based MOFs show excellent longitudinal relaxivity; however, leaching of the free Gd³⁺ ions causes nephrogenic systemic fibrosis,²² which precludes their clinical applications. Given that Mn²⁺ and Fe³⁺ ions are also known as potent paramagnetic metal ions, with much lower toxicity than Gd³⁺ ions, low toxic Mn-based MOFs and non-toxic iron-carboxylate MOFs, have been developed for T₁/T₂-weighted MR contrast enhancement.^{23–25} The biocompatibility of Mn/Fe-MOFs-based MR contrast agents has been improved, but the moderate relaxivity of Fe/Mn-MOFs still limits the imaging sensitivity, which hinders their practical applications. To circumvent the problem and make full use of the extraordinary drug encapsulation capacity of MOFs, the incorporation of nanoparticles with unique magnetic properties into MOFs is indeed an effective strategy.

Iron oxide nanoparticles are prevalent in MR imaging due to their ability to significantly shorten transverse relaxation time

^aSchool of Medical Imaging, Tianjin Medical University, Tianjin 300203, China. E-mail: fuyanyan365@163.com

^bCollege of Chemistry, Research Center for Analytical Sciences, State Key Laboratory of Medicinal Chemical Biology (Nankai University), Tianjin Key Laboratory of Molecular Recognition and Biosensing, and Collaborative Innovation Center of Chemical Science and Engineering (Tianjin), Nankai University, 94 Weijin Road, Tianjin 300071, China

^cDepartment of Radiology, Tianjin Key Laboratory of Functional Imaging, Tianjin Medical University General Hospital, Tianjin 300052, China

† Electronic supplementary information (ESI) available: Materials, experimental details and characterization. See DOI: 10.1039/c6sc01359g

‡ These authors contributed equally to this work.

and excellent biocompatibility.²⁶ Moreover, various formulations of iron oxide nanoparticles, such as ferumoxsil, ferrioxan and ferumoxide, have already been approved by the FDA as T₂-MR contrast agents for clinical use. Recently, Fe₃O₄-based core-shell nanoparticles, such as Fe₃O₄@Au, Fe₃O₄@CuInS₂, Fe₃O₄@PDA, Fe₃O₄@PPy, Fe₃O₄@Cu_{2-x}S, have also drawn considerable attention owing to their superior contrast effect in MR imaging.^{27–33} For these reasons, the employment of Fe₃O₄ as magnetic nanoparticles to design multifunctional MOF-based composites with high relaxivity, large drug payload and good biocompatibility is feasible. Recently, two groups have developed multifunctional Fe₃O₄@PAA/AuNCs/ZIF-8 NPs³⁴ and RITC-Fe₃O₄@IRMOF-3/FA NPs³⁵ by coating Fe₃O₄ with two different Zn-based MOFs for imaging and drug delivery, which demonstrate the practicability of using MOF-based composites in biomedicine. However, the poor moisture stability of IRMOF-3 and the toxicity of Zn-based MOFs, originating from the ion channel/DNA damage caused by the competition of Zn²⁺ with Fe²⁺ and Ca²⁺, hinder their practical application in biomedicine.^{36,37} Furthermore, the synthesis procedures usually include multiple steps and the capability of MOF-based composites for imaging and drug delivery, as well as the toxicity should be further systematically investigated. Thus, further development of novel MOF-based theranostic agents *via* a simple method is necessary and of great interest.

Herein, we report our initial effort to simply incorporate Fe₃O₄ nanoparticles into the MOF UiO-66 to fabricate novel theranostic MOF core-shell composites (Fe₃O₄@UiO-66) for *in vitro* and *in vivo* MR imaging and drug delivery (Scheme 1). UiO-66, as one class of zirconium-based MOFs, is constructed with Zr(IV) and 2-amino-1,4-benzenedicarboxylate (NH₂-H₂BDC) ligands and has received great attention in drug delivery due to its excellent chemical and solvent stability.^{12,15} The coordination of a Zr(IV)-cluster and linear ligands forms a cubic rigid 3D porous structure comprising octahedral cavities with a diameter of 1.1 nm and tetrahedral cavities with a diameter of 0.6 nm.³⁸


The presence of Zr–O clusters, numerous open cavities, metal sites and amphiphilic character make UiO-66 advantageous for capturing and releasing anticancer drugs such as doxorubicin (DOX) based on the strong coordination interactions between the hydroxyl groups in DOX and Zr(IV) centers in UiO-66. In addition, the toxicity of UiO-66 has been demonstrated to be relatively low.³⁷ Thus, UiO-66, which not only exhibits exceptional chemical and solvent stability, but also possesses good biocompatibility, was selected to fabricate the shell over the Fe₃O₄ nanoparticles for DOX delivery. Fe₃O₄@UiO-66 core-shell composites were synthesized *via* a facile *in situ* growth method based on the controllable growth of a UiO-66 shell on a carboxylate-terminated Fe₃O₄ core. The formed Fe₃O₄@UiO-66 composites simultaneously possessed the T₂-MR contrast properties of the Fe₃O₄ cores and the drug delivery ability originating from the MOF shells. As a result, the Fe₃O₄@UiO-66 composites show excellent stability, high drug loading capacity, low cytotoxicity, negligible *in vivo* toxicity and obvious MR signal attenuation effect. Furthermore, the DOX encapsulated composites show a sustained drug release and exhibit long-lasting and efficient anticancer therapeutic efficacy. All the results demonstrate that the developed Fe₃O₄@UiO-66 core-shell composites possess great potential as a novel theranostic agent for MR imaging and drug delivery in biomedicine.

Results and discussion

Synthesis and characterization of Fe₃O₄ and Fe₃O₄@UiO-66

Fe₃O₄ nanoparticles were synthesized through a hydrothermal method according to the literature.³⁹ The as-synthesized Fe₃O₄ nanoparticles were spherical with a diameter of 150 nm (Fig. 1A) and in the cubic phase (JCPDS: 19-0629) (Fig. 1E). The Fe₃O₄@UiO-66 composites were then synthesized by an *in situ* self-assembly of UiO-66 on the surface of Fe₃O₄ to obtain the core-shell theranostic agent. In a typical process, Fe₃O₄ nanoparticles were directly dispersed into the synthetic precursor of UiO-66 composed of ZrCl₄, NH₂-H₂BDC and DMF, and the reaction was accomplished through a simple hydrothermal procedure. The developed method avoids time-consuming layer-by-layer MOF growth and further modification of core particles, which is much simpler than most of the previous methods of synthesizing MOF-based core-shell composites.^{40,41}

To control the morphology of the core-shell composites, the concentrations of the precursors of UiO-66 were optimized. After mixing with different concentrations of UiO-66 precursor solutions, the Fe₃O₄@UiO-66 composites with different UiO-66 shell thickness (5, 25, 50 nm) were obtained (Fig. S1, ESI†). The Fe₃O₄@UiO-66 composites show uniform core-shell morphology with a 25 nm thickness of the UiO-66 shell when the ratio of Fe₃O₄ and UiO-66 precursor reached 25 mg in 37.5 mg ZrCl₄ (29 mg NH₂-H₂BDC/18 mL DMF) (Fig. 1B). Either the UiO-66 shell was too thick or no shell was formed if the ratio was higher or lower than the optimized ratio. Thus, the Fe₃O₄@UiO-66 core-shell composites synthesized under the optimized condition were used for the following experiments. Furthermore, high angle annular dark field scanning transmission electron microscopy (HAADF-STEM) and elemental mapping

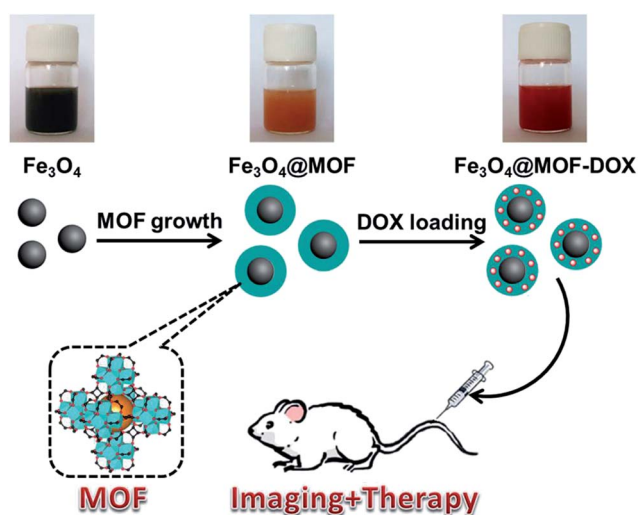

Scheme 1 Schematic of the fabrication of Fe₃O₄@MOF core-shell composites for imaging and therapy.



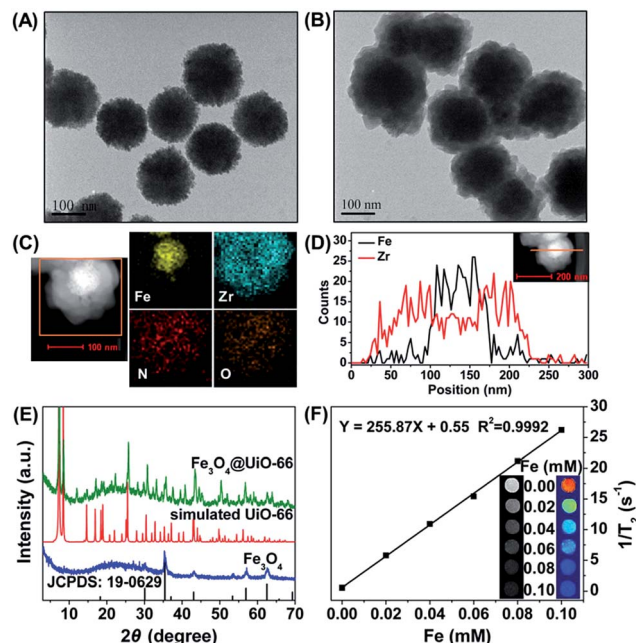


Fig. 1 (A and B) TEM images of the synthesized Fe_3O_4 (A) and the Fe_3O_4 @UiO-66 core-shell composites (B). (C) HAADF-STEM image and the corresponding elemental mapping of one core-shell Fe_3O_4 @UiO-66 composite. (D) HAADF-STEM image of Fe_3O_4 @UiO-66 composites and the corresponding EDS line scan. (E) XRD patterns of synthesized Fe_3O_4 @UiO-66, Fe_3O_4 , simulated UiO-66 and the JCPDS file of Fe_3O_4 . (F) T_2 -weighted MR images and transverse relaxivity of Fe_3O_4 @UiO-66 at different Fe concentrations.

analysis were used to verify the core-shell structure of the Fe_3O_4 @UiO-66 composite (Fig. 1C and D).

A clear contrast between the core and shell was obtained wherein the core appeared dark, whereas the shell appeared bright. Moreover, the EDS (energy dispersive spectrometry) line scanning data and elemental mapping analysis reveal that the Fe and Zr elements were distributed in the core and shell, respectively. All the results demonstrated the successful formation of a core-shell structure for the Fe_3O_4 @UiO-66 composite.

The simultaneous existence of the characteristic peaks of Fe_3O_4 and UiO-66 in the X-ray diffraction (XRD) pattern of Fe_3O_4 @UiO-66 indicated the successful formation of a UiO-66 shell on the surface of Fe_3O_4 nanoparticles without altering their crystallinity (Fig. 1E). The characteristic peaks of UiO-66 at 1570 cm^{-1} , 1435 cm^{-1} , and 1386 cm^{-1} and Fe_3O_4 at 1651 cm^{-1} and 595 cm^{-1} in the Fourier transform infrared (FT-IR) spectrum of Fe_3O_4 @UiO-66 indicated the formation of the Fe_3O_4 @UiO-66 composites (Fig. S2, ESI†). The two peaks at 3416 cm^{-1} and 3373 cm^{-1} in the spectrum of Fe_3O_4 @UiO-66, belonged to the asymmetric and symmetric stretching absorptions of the primary amine groups in the $\text{NH}_2\text{-H}_2\text{BDC}$ ligands, respectively, which further verified the successful growth of the UiO-66 shell on the Fe_3O_4 core. The contents of Fe and Zr elements in the prepared Fe_3O_4 @UiO-66 were 30.6% and 0.9%, respectively. Thermogravimetric analysis results showed that the Fe_3O_4 @UiO-66 composites decomposed at 340°C , which is

a similar breakdown temperature to that of the synthesized UiO-66 nanocrystals (Fig. S3, ESI†). The hydrodynamic size and surface zeta potential of Fe_3O_4 @UiO-66 composites in phosphate buffer solution (PBS) were $241.5 \pm 28.5\text{ nm}$ (polydispersity index = 0.340) and $-25.7 \pm 5.2\text{ mV}$, respectively (Fig. S4, ESI†). The results indicate that the composites had good dispersity and colloidal stability, which ensured their practical application in drug delivery and MR imaging.

The drug loading capacity of Fe_3O_4 @UiO-66 composites depends on the porosity of the UiO-66 shells. N_2 adsorption isotherms were used to characterize the surface area and porosity of Fe_3O_4 @UiO-66 (Fig. 2A). The total pore volume (V_{total}) and BET surface area (S_{BET}) of the synthesized Fe_3O_4 @UiO-66 were calculated to be $0.21\text{ cm}^3\text{ g}^{-1}$ and $149.75\text{ m}^2\text{ g}^{-1}$, respectively, which are large for drug loading yet much lower than those of the pure UiO-66 due to the inner nonporous Fe_3O_4 core. In addition, the Fe_3O_4 @UiO-66 composites possessed an inter-particle mesopore at 3.5 nm (Table S1, ESI†), which makes them efficient for drug delivery.

Superparamagnetism is essential to MR imaging. Thus, the magnetic properties of the Fe_3O_4 @UiO-66 composites were investigated in a magnetic field range from -70 to $+70\text{ kOe}$ at room temperature (Fig. 2B). The saturation magnetization (M_s) of the Fe_3O_4 @UiO-66 was 51.58 emu g^{-1} , smaller than that of Fe_3O_4 nanoparticles (69.69 emu g^{-1}) due to the encapsulation by the UiO-66 layer. The high M_s value and the existing hysteresis loop without significant coercivity and remanence in the magnetization hysteresis curves demonstrated the strong superparamagnetic character of the as-synthesized Fe_3O_4 @UiO-66 composites.⁴² Furthermore, the Fe_3O_4 @UiO-66 composites could be quickly collected using the magnet (Fig. S5, ESI†).

The strong superparamagnetism of the Fe_3O_4 @UiO-66 composites ensured their ability to act as a T_2 contrast agent for MR imaging. T_2 -weighted MR images of Fe_3O_4 @UiO-66 showed an obvious concentration-dependent darkening effect with a high transverse relaxivity (r_2) of $255.87\text{ mM}^{-1}\text{ s}^{-1}$ (Fig. 1F), and the r_2 values decreased as the thickness of the UiO-66 shell increased due to the reduced ratio of Fe_3O_4 to UiO-66 in the composite (Table S2 and Fig. S6, ESI†). Furthermore, the r_2 value of the prepared Fe_3O_4 @UiO-66 ($1396\text{ mg}^{-1}\text{ mL s}^{-1}$) was much higher than that of Fe_3O_4 @PAA/AuNCs/ZIF-8 NPs ($53.79\text{ mL mg}^{-1}\text{ s}^{-1}$)³⁴ and several clinical Fe-based T_2 -weighted contrast agents such as ferumoxsil ($72\text{ mM}^{-1}\text{ s}^{-1}$), ferumoxide

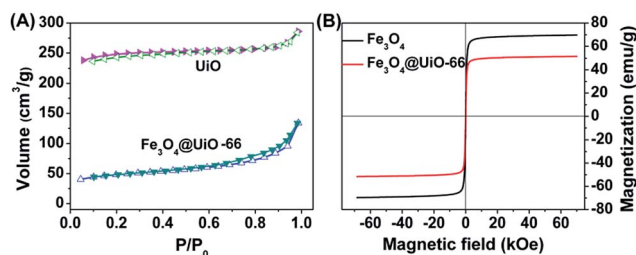


Fig. 2 (A) N_2 adsorption-desorption isotherms of UiO-66 and Fe_3O_4 @UiO-66. (B) Magnetization hysteresis curves of Fe_3O_4 and Fe_3O_4 @UiO-66.



(98.3 mM⁻¹ s⁻¹) and Resovist (150 mM⁻¹ s⁻¹).⁴³ These results show the great potential of Fe₃O₄@UiO-66 in T₂-MR imaging.

Drug loading/release of Fe₃O₄@UiO-66 composites

The stability of the nanocarrier in a wide pH range from basic to acidic is essential for drug loading/release. Thus, we investigated the stability of the as-synthesized Fe₃O₄@UiO-66 composites at different pH values (4.0, 5.0, 6.0, 7.4, 8.0). No significant changes in the XRD pattern (Fig. 3A) or the morphology (Fig. S7, ESI†) of the Fe₃O₄@UiO-66 composites at these pH values were observed. The results indicated that the composites had super stability.

To evaluate the drug loading capacity of the Fe₃O₄@UiO-66 composites, a commonly used anticancer drug, DOX, was mixed with Fe₃O₄@UiO-66 in PBS at pH 8.0 for 24 h. After removing the excess unloaded DOX, the drug loaded composites Fe₃O₄@UiO-66-DOX were obtained. UV-Vis-NIR spectra of Fe₃O₄@UiO-66 before and after encapsulation with DOX were measured. The appearance of the characteristic peak of DOX at 500 nm in the UV-Vis-NIR spectra of Fe₃O₄@UiO-66-DOX and the increase of the characteristic peak with the added DOX confirmed the successful loading of DOX into the Fe₃O₄@UiO-66 composites (Fig. 3B). Moreover, the presence of

characteristic absorption bands (indicated by green dashed rectangle) of DOX in the spectra of Fe₃O₄@UiO-66-DOX also indicated the incorporation of DOX molecules into Fe₃O₄@UiO-66 (Fig. 3C).

The drug loading capacity increased from 2.5 to 66.3 wt% as the amount of DOX increased from 0.15 to 15 mg (Fig. 3D). Furthermore, the drug loading capacity increased with the thickness of the UiO-66 shell (Table S2, ESI†). The DOX loading capacity of Fe₃O₄@UiO-66 could reach 66.3 wt% with an ultra-high loading content of 2.0 mg DOX per mg composites, which is almost the highest DOX payload among the MOFs carriers.^{25,44–46} The impressive result was meaningful for clinical applications, because the administration of high dosages could be realized using a small amount of composites.

The high drug loading capacity of Fe₃O₄@UiO-66 composites was probably attributed to the large surface area of the UiO-66 shell and the interactions between DOX and UiO-66. A remarkable fluorescence quenching of DOX along with color change from brown to wine for the Fe₃O₄@UiO-66-DOX dispersion confirmed the strong interaction between DOX and Fe₃O₄@UiO-66 (Fig. S5 and S8, ESI†). Potential interactions include π - π stacking between the aromatic anthracycline of DOX and the aromatic pore walls of UiO-66, hydrogen bonding between the oxygen atoms of DOX and the amino groups in UiO-66, van der Waals forces, electrostatic interactions, and coordination bonding.⁴⁷ Among the above interactions, stable coordination bonding between the deprotonated hydroxyls in DOX and the numerous Zr sites in the UiO-66 framework played the leading role in drug loading, as confirmed by ultraviolet-visible (UV-Vis) spectroscopy and X-ray photoelectron spectroscopy (XPS) (Fig. 3E and S9, ESI†). Red shift of the UV-Vis spectrum of Fe₃O₄@UiO-66-DOX in comparison with that of DOX after DOX loading into Fe₃O₄@UiO-66 indicates the formation of a DOX-Zr complex in the Fe₃O₄@UiO-66 framework, which is also supported by the similar spectral modification of DOX with free Zr(IV) ions (Fig. S9†). XPS results showed that the binding energy of Zr 3d shifted from 182.76 and 185.12 eV for Fe₃O₄@UiO-66 to 182.40 and 184.76 eV for Fe₃O₄@UiO-66-DOX (Fig. 3E). The binding energy of Zr 3d shifting to lower levels after DOX encapsulation could be attributed to electron transfer due to binding of DOX to active Zr sites.^{48–50} The formation of coordination bonds between DOX and metal centres (Zr, Fe, Zn) has also been described previously.^{44,51,52} Owing to the strong coordination bonding of DOX-Zr, the Fe₃O₄@UiO-66 showed a remarkable and efficient DOX payload.

The DOX release behavior of the Fe₃O₄@UiO-66-DOX composites was investigated at different pH values (4.0, 5.0, 6.0, and 7.4). The time-dependent accumulated drug release (ADR) curves showed a slow and sustained release pattern without any burst effect (Fig. 3F). The release rate would generate a stable drug concentration and provide sufficient time for the Fe₃O₄@UiO-66-DOX to accumulate at the tumor site. As shown in Fig. 3F, about 36.1% and 21.6% of the DOX were released in 41 days at pH 4.0 and 5.0, respectively, whereas 17.1% and 13.8% of DOX were released at pH 6.0 and 7.4, indicating the sensitivity of Fe₃O₄@UiO-66-DOX to acidic tumor microenvironments. The pH-responsive DOX release was controlled by the

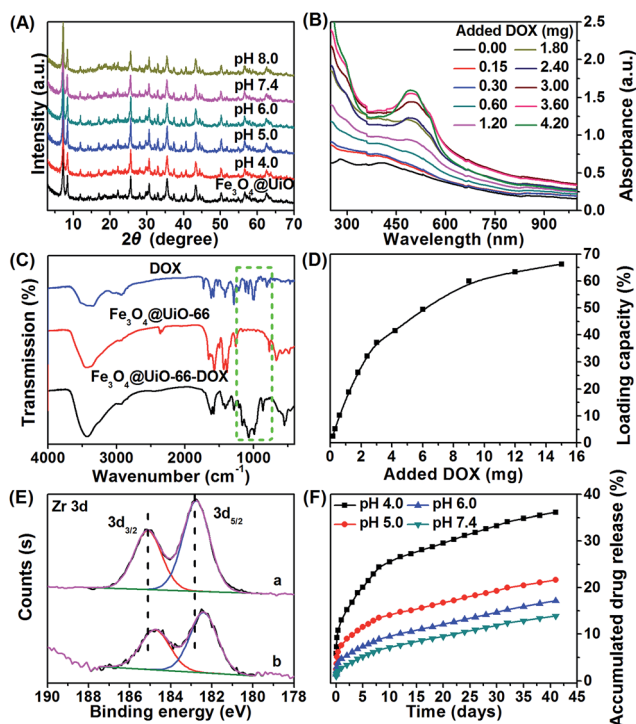


Fig. 3 (A) XRD patterns of Fe₃O₄@UiO-66 after immersion in different pH solutions for one week. (B) UV-Vis-NIR spectra of Fe₃O₄@UiO-66-DOX obtained at various DOX added contents after removal of excess free drug molecules. (C) FT-IR spectra of DOX, Fe₃O₄@UiO-66 and Fe₃O₄@UiO-66-DOX. (D) Drug loading capacity of Fe₃O₄@UiO-66 at different DOX added contents. (E) XPS spectra of Zr 3d for Fe₃O₄@UiO-66 (a) and Fe₃O₄@UiO-66-DOX (b). (F) Accumulated drug release (ADR) from Fe₃O₄@UiO-66-DOX composites in buffers with four different pH values.



drug-matrix interactions under acidic conditions. At acidic pH, the amino group in DOX was easily protonated, giving DOX a positive charge. Moreover, the surface zeta potential of $\text{Fe}_3\text{O}_4@\text{UiO}-66$ became less negative in acidic conditions (-9.8 ± 1.1 mV at pH 4.0 and -25.7 ± 5.2 mV at pH 7.4). Thus, the electrostatic interactions between $\text{Fe}_3\text{O}_4@\text{UiO}-66$ and DOX were weakened, which promoted the drug release in acidic conditions.⁵³ Moreover, the breakage of the coordination bonds between the protonated hydroxyls in DOX and Zr sites under acidic conditions would accelerate the DOX release. In addition to the pH dependent DOX release, the tendency of endogenous phosphate salts in the endosomes to coordinate to the Zr sites also facilitates the release of DOX from the $\text{Fe}_3\text{O}_4@\text{UiO}-66$ composites.^{52,54} These results indicate that $\text{Fe}_3\text{O}_4@\text{UiO}-66$ nanocarriers could deliver the drug to tumor tissue sustainably and effectively, which would be beneficial for the diminishing of toxic side effects and decreasing of patient discomfort.

In vitro cytotoxicity

In vitro cell viabilities of different concentrations of $\text{Fe}_3\text{O}_4@\text{UiO}-66$, $\text{Fe}_3\text{O}_4@\text{UiO}-66$ -DOX and free DOX on HeLa cells were evaluated by MTT assay to study the bio-toxicity of $\text{Fe}_3\text{O}_4@\text{UiO}-66$ and the therapeutic effect of $\text{Fe}_3\text{O}_4@\text{UiO}-66$ -DOX. The HeLa cells treated with $\text{Fe}_3\text{O}_4@\text{UiO}-66$ showed no obvious toxicity (nearly 100% cell viability), even at a concentration up to 500 mg L^{-1} , indicating the good biocompatibility of the synthesized $\text{Fe}_3\text{O}_4@\text{UiO}-66$ composites (Fig. 4A). In contrast, the $\text{Fe}_3\text{O}_4@\text{UiO}-66$ -DOX exhibited significant increase in anticancer activity against HeLa cells with the increase of the loaded DOX concentration (Fig. 4B). Nearly 60% of HeLa cells were killed after incubation with $\text{Fe}_3\text{O}_4@\text{UiO}-66$ -DOX, even at a low DOX loading concentration of 20 mg L^{-1} and the $\text{Fe}_3\text{O}_4@\text{UiO}-66$ -DOX had similar cell toxicity to that of free DOX. In addition, the $\text{Fe}_3\text{O}_4@\text{UiO}-66$ -DOX showed greater lethality against HeLa cells after incubating for a longer time (48 h), indicating the long-term and sustained DOX release from the $\text{Fe}_3\text{O}_4@\text{UiO}-66$ composites.

To demonstrate the low toxic and side effects of DOX loaded $\text{Fe}_3\text{O}_4@\text{UiO}-66$ on normal cells, we further evaluated the biocompatibility of different concentrations of $\text{Fe}_3\text{O}_4@\text{UiO}-66$ and $\text{Fe}_3\text{O}_4@\text{UiO}-66$ -DOX on 3T3 cells by MTT assay (Fig. 4C). As expected, the 3T3 cells treated with $\text{Fe}_3\text{O}_4@\text{UiO}-66$ showed high viability, further indicating the good biocompatibility of the $\text{Fe}_3\text{O}_4@\text{UiO}-66$ composites. Furthermore, the DOX loaded $\text{Fe}_3\text{O}_4@\text{UiO}-66$ also showed negligible toxicity on 3T3 cells, demonstrating the low side effect of $\text{Fe}_3\text{O}_4@\text{UiO}-66$ -DOX on normal cells. Although $\text{Fe}_3\text{O}_4@\text{UiO}-66$ -DOX could be phagocytized by both normal cells and cancer cells, the tremendous difference in cell viability between the HeLa cells and the 3T3 cells may be attributed to the different DOX release rates determined by the cellular microenvironments. The fast reproduction of cancer cells makes the cellular microenvironment acidic, which facilitates DOX release from $\text{Fe}_3\text{O}_4@\text{UiO}-66$ -DOX, and thus leads to high toxicity to cancer cells. These results demonstrate the availability of the $\text{Fe}_3\text{O}_4@\text{UiO}-66$ composites as drug carriers for cancer cell killing.

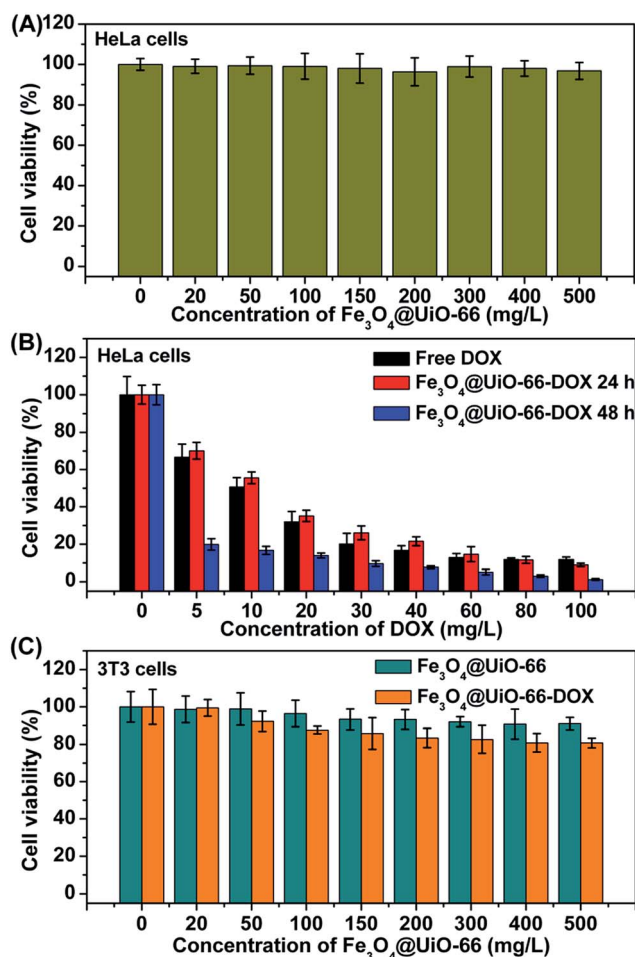


Fig. 4 (A) Cell viability of HeLa cells after incubation with different concentrations of $\text{Fe}_3\text{O}_4@\text{UiO}-66$. (B) Cell viability of HeLa cells after incubation with free DOX and $\text{Fe}_3\text{O}_4@\text{UiO}-66$ -DOX for 24 h or 48 h at the same concentration of DOX. (C) Cell viability of 3T3 cells after incubation with $\text{Fe}_3\text{O}_4@\text{UiO}-66$ and $\text{Fe}_3\text{O}_4@\text{UiO}-66$ -DOX for 24 h at the same concentration of $\text{Fe}_3\text{O}_4@\text{UiO}-66$.

In vitro and in vivo MR imaging

The high transverse relaxivity of the synthesized $\text{Fe}_3\text{O}_4@\text{UiO}-66$ core-shell composites gives them potential as a contrast agent for cancer diagnosis. The T_2 -weighted MR images of HeLa cells incubated with different concentrations of $\text{Fe}_3\text{O}_4@\text{UiO}-66$ composites (0, 25, 50, 100, 150 and 200 mg L^{-1}) became much darker with increasing of the concentration of $\text{Fe}_3\text{O}_4@\text{UiO}-66$ due to the dose-dependent cellular uptake. The results demonstrate the capability of $\text{Fe}_3\text{O}_4@\text{UiO}-66$ composites as a T_2 -weighted MR contrast agent for *in vitro* MR imaging (Fig. 5A).

The feasibility of the $\text{Fe}_3\text{O}_4@\text{UiO}-66$ composites for *in vivo* MR imaging was also tested. A significant darkening effect was observed in the liver region of the Kunming mouse at 10 min post-injection of $\text{Fe}_3\text{O}_4@\text{UiO}-66$ composites ($400 \mu\text{L}$, 5 mg mL^{-1} , 24 mg Fe per kg), indicating the ability of $\text{Fe}_3\text{O}_4@\text{UiO}-66$ to enhance *in vivo* T_2 -weighted images (Fig. 5B). The dramatic T_2 signal intensity decrease is probably due to the phagocytosis of the $\text{Fe}_3\text{O}_4@\text{UiO}-66$ composites by the liver macrophage cells in reticuloendothelial systems (RES).⁵⁵ Considering the excellent



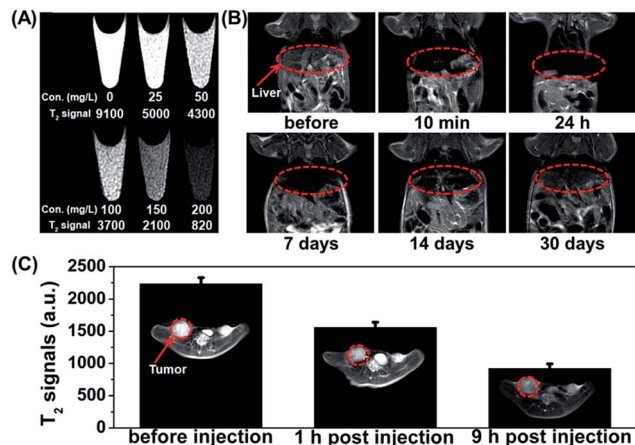


Fig. 5 (A) MR images of HeLa cells after incubation with different concentrations (0, 25, 50, 100, 150 and 200 mg L⁻¹) of Fe₃O₄@UiO-66 for 24 h. (B) T₂-weighted MR images of the Kunming mouse before and after intravenous injection of Fe₃O₄@UiO-66 at different time points (liver region marked by red cycles). (C) T₂-weighted MR images and T₂-MR signals of tumor on HeLa-tumor bearing mice before injection, 1 h and 9 h post injection of Fe₃O₄@UiO-66 intravenously (tumor region marked by red cycles).

MR imaging capability of Fe₃O₄@UiO-66 composites, MR imaging of HeLa tumor-bearing mice was then carried out. After being intravenously injected with Fe₃O₄@UiO-66 composites, remarkable darkening effect was observed in the tumor area just 1 h post-injection and the MR image became even darker at 9 h post-injection (Fig. 5C). The quantified T₂-weighted MR signals in the tumor also showed a gradual decrease over 9 h post-injection, demonstrating the accumulation of Fe₃O₄@UiO-66 composites in the tumor, which is probably due to the enhanced permeability and retention (EPR) effect of tumors.

Biodistribution and toxicology studies

The potential toxic effects of nanomaterials are a major concern for their biomedical applications. Thus, the metabolism, bio-distribution and long-term toxicity of the as-synthesized Fe₃O₄@UiO-66 core-shell composites were systematically investigated. For metabolism study, the T₂-weighted images of the Kunming mouse injected with the composites were collected after 1, 7, 14 and 30 days of injection. Strong darkening effect after injection and signal recovery at 30 days post-injection were observed in the liver region, but no time-dependent darkening effect was observed in the urinary bladder, indicating that Fe₃O₄@UiO-66 was not excreted from the kidneys but from the liver (Fig. 5B). For biodistribution study, the major organs (heart, liver, spleen, lung, kidney) of the mice treated with Fe₃O₄@UiO-66 for 1, 7 and 30 days were collected, weighed and solubilized by aqua regia for AAS measurement of Fe and ICP-MS determination of Zr concentrations, respectively. As expected and consistent with the T₂-weighted MR images, high levels of Fe and Zr contents mainly accumulated in mononuclear phagocyte systems such as the spleen and liver (Fig. 6A and S10, ESI†). The Fe levels in all measured organs constantly decreased as the post-injection

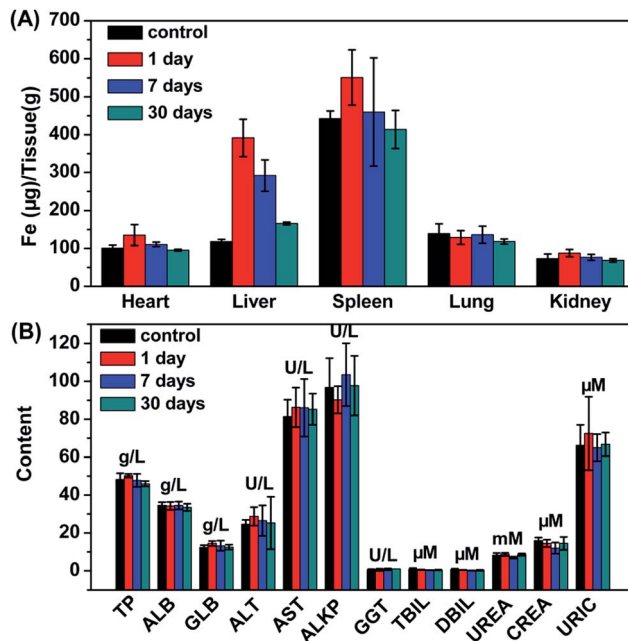


Fig. 6 (A) Time-dependent biodistribution of Fe in various organs of mice. (B) Blood biochemistry of mice treated with Fe₃O₄@UiO-66 at dose of 24 mg kg⁻¹ measured at 1, 7 and 30 days post-injection.

time prolonged and nearly dropped back to the normal levels after 30 days, except for the liver, in which the Fe content was slightly higher than the control. It was noteworthy that Zr was not detected in the heart, lung or kidney due to the absence of Zr in the organism and no accumulation of Fe₃O₄@UiO-66 in these organs. In addition, the Zr levels in the liver and spleen could be gradually metabolized over time, which was consistent with the biodistribution of Fe.

For *in vivo* long-term toxicity, the body weight and the blood analysis were evaluated. The body weights of the control group and the experimental group treated with Fe₃O₄@UiO-66 maintained similar increases over 30 days, and no death or significant body weight drop were observed in the experimental group, illustrating that the injection of the Fe₃O₄@UiO-66 composites did not perceptibly interfere with the growth of the mice (Fig. S11, ESI†). Blood analysis parameters, including liver function markers (total protein, TP; albumin, ALB; globulin GLB; alanine aminotransferase, ALT; aspartate aminotransferase, AST; alkaline phosphatase, ALKP; gamma glutamyl transaminase, GGT; total bilirubin, TBIL; direct bilirubin, DBIL) and kidney function markers (urea, UREA; creatinine, CREA; uric acid URIC), at different time points post-injection of Fe₃O₄@UiO-66 appeared to be normal compared with those in the control group, indicating that no obvious liver or kidney disorders were induced by the injection of Fe₃O₄@UiO-66 (Fig. 6B). All these results demonstrated that the as-synthesized Fe₃O₄@UiO-66 was a relatively safe theranostic agent for biomedical applications.

In vivo antitumor efficacy

Inspired by the biocompatibility of Fe₃O₄@UiO-66 and *in vitro* anticancer effect of the DOX-loaded Fe₃O₄@UiO-66, the *in vivo*



chemotherapy performance of $\text{Fe}_3\text{O}_4@\text{UiO}-66\text{-DOX}$ was investigated using the HeLa tumor-bearing nude mice. As shown in Fig. 7A, the tumors in the mice treated with PBS grew quickly. In contrast, the tumor growth on mice treated with $\text{Fe}_3\text{O}_4@\text{UiO}-66\text{-DOX}$ was effectively inhibited due to the preferential DOX accumulation and release at the tumor site *via* the EPR effect. Furthermore, the images and sizes of the tumor blocks isolated 30 days after being treated showed that the mice treated with $\text{Fe}_3\text{O}_4@\text{UiO}-66\text{-DOX}$ had the smallest tumor size (Fig. 7B and C). All these results make a proof of concept that $\text{Fe}_3\text{O}_4@\text{UiO}-66$ can efficiently carry and release drugs into tumors, leading to effective antitumor efficacy.

Although visualized tumor size could be observed from the images of the mice and tumor blocks, adopting non-invasive MR imaging to monitor tumor development is necessary to realize precision medicine. Thus, monitoring the tumor change of the mice after being treated with $\text{Fe}_3\text{O}_4@\text{UiO}-66\text{-DOX}$ *via* MR imaging was carried out to accurately evaluate the antitumor efficacy. The MR images of HeLa-tumor bearing mice injected with $\text{Fe}_3\text{O}_4@\text{UiO}-66\text{-DOX}$ (200 μL , 5 mg mL^{-1}) showed obvious darkening effect in the tumor region, indicating that the $\text{Fe}_3\text{O}_4@\text{UiO}-66\text{-DOX}$ could passively accumulate in the tumor at 7 days post-injection (Fig. 7D and S12, ESI†). Continuous monitoring of tumor development by MR imaging was performed

and efficient tumor growth inhibition in the mice treated with $\text{Fe}_3\text{O}_4@\text{UiO}-66\text{-DOX}$ was observed through the obtained MR images at 21 days post-injection. In contrast, the tumors of the mice treated with PBS grew rapidly, as revealed by MR images. All the results not only further convincingly demonstrated the efficient antitumor efficacy of $\text{Fe}_3\text{O}_4@\text{UiO}-66\text{-DOX}$ in terms of MR imaging, but also indicated the great potential of $\text{Fe}_3\text{O}_4@\text{UiO}-66$ in imaging-guided therapy.

Conclusions

In conclusion, we developed a novel $\text{Fe}_3\text{O}_4@\text{UiO}-66$ theranostic agent by *in situ* growth of a UiO-66 MOF shell on a Fe_3O_4 core. The obtained $\text{Fe}_3\text{O}_4@\text{UiO}-66$ core-shell composites can serve as nanocarriers and contrast agents for simultaneous drug delivery and T_2 -weighted MR imaging. The exceptionally high drug loading capacity (~ 63 wt%, 2.0 mg DOX per mg composites), and sustained and effective drug release make $\text{Fe}_3\text{O}_4@\text{UiO}-66$ an excellent drug delivery carrier. Moreover, high transverse relaxivity ($255.87 \text{ mM}^{-1} \text{ s}^{-1}$) revealed that $\text{Fe}_3\text{O}_4@\text{UiO}-66$ has the ability to act as a contrast agent for MR imaging. The cytotoxicity assay, biodistribution and *in vivo* toxicology studies demonstrated that the $\text{Fe}_3\text{O}_4@\text{UiO}-66$ composites possess low toxicity and good biocompatibility, which inspired us to explore their antitumor efficiency and MR imaging capability *in vitro* and *in vivo*. High cancer cell mortality, remarkable tumor size inhibition and significant darkening effect were obtained after treatment with $\text{Fe}_3\text{O}_4@\text{UiO}-66$ or $\text{Fe}_3\text{O}_4@\text{UiO}-66\text{-DOX}$ *in vitro* and *in vivo*. All the results indicate that the presented novel multifunctional MOF-based composites should be very promising in cancer therapy and diagnosis due to their effective drug delivery and MR imaging.

Acknowledgements

This study was supported by the National Natural Science Foundation of China (Grants 21505099, 21435001, 21405112) and the China Postdoctoral Science Foundation (Grants 2015M571270, 2014M550146).

Notes and references

- 1 D. Zhao, D. J. Timmons, D. Yuan and H.-C. Zhou, *Acc. Chem. Res.*, 2010, **44**, 123.
- 2 A. Carne, C. Carbonell, I. Imaz and D. Maspoch, *Chem. Soc. Rev.*, 2011, **40**, 291.
- 3 P. Horcajada, R. Gref, T. Baati, P. K. Allan, G. Maurin, P. Couvreur, G. Férey, R. E. Morris and C. Serre, *Chem. Rev.*, 2012, **112**, 1232.
- 4 A. C. McKinlay, R. E. Morris, P. Horcajada, G. Férey, R. Gref, P. Couvreur and C. Serre, *Angew. Chem., Int. Ed.*, 2010, **49**, 6260.
- 5 S. Keskin and S. Kızılel, *Ind. Eng. Chem. Res.*, 2011, **50**, 1799.
- 6 C. Wang, D. Liu and W. Lin, *J. Am. Chem. Soc.*, 2013, **135**, 13222.
- 7 J. Della Rocca, D. Liu and W. Lin, *Acc. Chem. Res.*, 2011, **44**, 957.

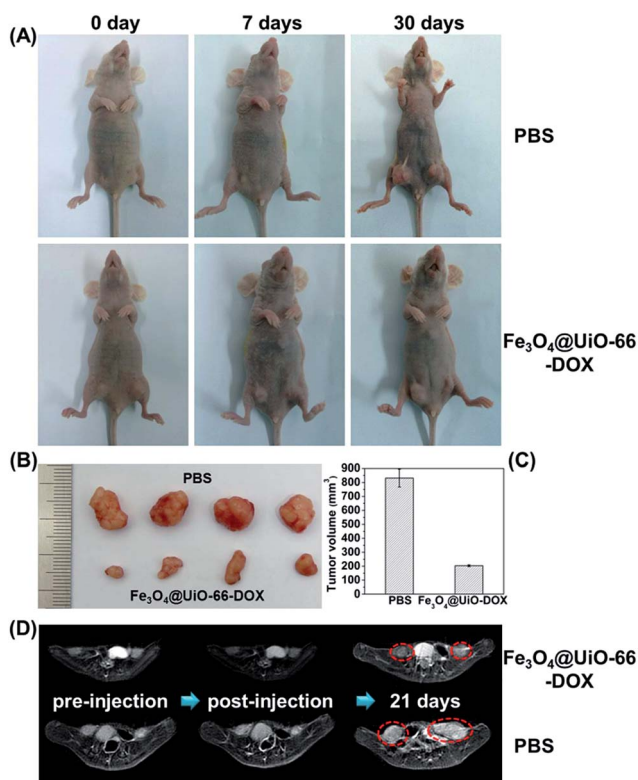


Fig. 7 *In vivo* antitumor efficacy. (A) Representative images of mice before and after intravenous injection with PBS or $\text{Fe}_3\text{O}_4@\text{UiO}-66\text{-DOX}$ after 7 and 30 days. (B) Images and (C) volumes of tumor blocks collected from PBS and $\text{Fe}_3\text{O}_4@\text{UiO}-66\text{-DOX}$ treated groups of mice on day 30. (D) MR images of HeLa-tumor bearing mice treated with PBS or $\text{Fe}_3\text{O}_4@\text{UiO}-66\text{-DOX}$ collected at different time points (tumor region marked by red cycles).



- 8 P. Horcajada, C. Serre, M. Vallet-Regi, M. Sebban, F. Taulelle and G. Férey, *Angew. Chem., Int. Ed.*, 2006, **45**, 5974.
- 9 L.-L. Tan, H. Li, Y.-C. Qiu, D.-X. Chen, X. Wang, R.-Y. Pan, Y. Wang, S. X.-A. Zhang, B. Wang and Y.-W. Yang, *Chem. Sci.*, 2015, **6**, 1640.
- 10 J. Zhuang, C.-H. Kuo, L.-Y. Chou, D.-Y. Liu, E. Weerapana and C.-K. Tsung, *ACS Nano*, 2014, **8**, 2812.
- 11 Y. Wu, M. Zhou, S. Li, Z. Li, J. Li, B. Wu, G. Li, F. Li and X. Guan, *Small*, 2014, **10**, 2927.
- 12 D. Cunha, M. Ben Yahia, S. Hall, S. R. Miller, H. Chevreau, E. Elkaim, G. Maurin, P. Horcajada and C. Serre, *Chem. Mater.*, 2013, **25**, 2767.
- 13 Q. Hu, J. Yu, M. Liu, A. Liu, Z. Dou and Y. Yang, *J. Med. Chem.*, 2014, **57**, 5679.
- 14 T. Kundu, S. Mitra, P. Patra, A. Goswami, D. Díaz Díaz and R. Banerjee, *Chem.-Eur. J.*, 2014, **20**, 10514.
- 15 X. Zhu, J. Gu, Y. Wang, B. Li, Y. Li, W. Zhao and J. Shi, *Chem. Commun.*, 2014, **50**, 8779.
- 16 C. He, K. Lu, D. Liu and W. Lin, *J. Am. Chem. Soc.*, 2014, **136**, 5181.
- 17 F. Ke, Y.-P. Yuan, L.-G. Qiu, Y.-H. Shen, A.-J. Xie, J.-F. Zhu, X.-Y. Tian and L.-D. Zhang, *J. Mater. Chem.*, 2011, **21**, 3843.
- 18 C.-Y. Sun, C. Qin, C.-G. Wang, Z.-M. Su, S. Wang, X.-L. Wang, G.-S. Yang, K.-Z. Shao, Y.-Q. Lan and E.-B. Wang, *Adv. Mater.*, 2011, **23**, 5629.
- 19 J. Della Rocca and W. Lin, *Eur. J. Inorg. Chem.*, 2010, **2010**, 3725.
- 20 D. Liu, K. Lu, C. Poon and W. Lin, *Inorg. Chem.*, 2014, **53**, 1916.
- 21 W. J. Rieter, K. M. L. Taylor, H. An, W. Lin and W. Lin, *J. Am. Chem. Soc.*, 2006, **128**, 9024.
- 22 D. R. Broome, M. S. Girguis, P. W. Baron, A. C. Cottrell, I. Kjellin and G. A. Kirk, *Am. J. Roentgenol.*, 2007, **188**, 586.
- 23 K. M. L. Taylor, W. J. Rieter and W. Lin, *J. Am. Chem. Soc.*, 2008, **130**, 14358.
- 24 K. M. L. Taylor-Pashow, J. D. Rocca, Z. Xie, S. Tran and W. Lin, *J. Am. Chem. Soc.*, 2009, **131**, 14261.
- 25 P. Horcajada, T. Chalati, C. Serre, B. Gillet, C. Sebrie, T. Baati, J. F. Eubank, D. Heurtaux, P. Clayette, C. Kreuz, J.-S. Chang, Y. K. Hwang, V. Marsaud, P.-N. Bories, L. Cynober, S. Gil, G. Férey, P. Couvreur and R. Gref, *Nat. Mater.*, 2010, **9**, 172.
- 26 N. Lee and T. Hyeon, *Chem. Soc. Rev.*, 2012, **41**, 2575.
- 27 S. V. Salihov, Y. A. Ivanenkov, S. P. Krechetov, M. S. Veselov, N. V. Sviridenkova, A. G. Savchenko, N. L. Klyachko, Y. I. Golovin, N. V. Chufarova, E. K. Beloglazkina and A. G. Majouga, *J. Magn. Magn. Mater.*, 2015, **394**, 173.
- 28 H. Cai, K. Li, J. Li, S. Wen, Q. Chen, M. Shen, L. Zheng, G. Zhang and X. Shi, *Small*, 2015, **11**, 4584.
- 29 J. Li, Y. Hu, J. Yang, P. Wei, W. Sun, M. Shen, G. Zhang and X. Shi, *Biomaterials*, 2015, **38**, 10.
- 30 J. Shen, Y. Li, Y. Zhu, X. Yang, X. Yao, J. Li, G. Huang and C. Li, *J. Mater. Chem. B*, 2015, **3**, 2873.
- 31 L.-S. Lin, Z.-X. Cong, J.-B. Cao, K.-M. Ke, Q.-L. Peng, J. Gao, H.-H. Yang, G. Liu and X. Chen, *ACS Nano*, 2014, **8**, 3876.
- 32 C. Wang, H. Xu, C. Liang, Y. Liu, Z. Li, G. Yang, H. Cheng, Y. Li and Z. Liu, *ACS Nano*, 2013, **7**, 6782.
- 33 Q. Tian, J. Hu, Y. Zhu, R. Zou, Z. Chen, S. Yang, R. Li, Q. Su, Y. Han and X. Liu, *J. Am. Chem. Soc.*, 2013, **135**, 8571.
- 34 R. Bian, T. Wang, L. Zhang, L. Li and C. Wang, *Biomater. Sci.*, 2015, **3**, 1270.
- 35 A. Ray Chowdhuri, D. Bhattacharya and S. K. Sahu, *Dalton Trans.*, 2016, **45**, 2963.
- 36 P. Guo, D. Dutta, A. G. Wong-Foy, D. W. Gidley and A. J. Matzger, *J. Am. Chem. Soc.*, 2015, **137**, 2651.
- 37 C. Tamames-Tabar, D. Cunha, E. Imbuluzqueta, F. Ragon, C. Serre, M. J. Blanco-Prieto and P. Horcajada, *J. Mater. Chem. B*, 2014, **2**, 262.
- 38 J. H. Cavka, S. Jakobsen, U. Olsbye, N. Guillou, C. Lamberti, S. Bordiga and K. P. Lillerud, *J. Am. Chem. Soc.*, 2008, **130**, 13850.
- 39 F. Xu, C. Cheng, D.-X. Chen and H. Gu, *ChemPhysChem*, 2012, **13**, 336.
- 40 F. Ke, L.-G. Qiu, Y.-P. Yuan, X. Jiang and J.-F. Zhu, *J. Mater. Chem.*, 2012, **22**, 9497.
- 41 N. T. Zhang, B. J. Zhu, F. M. Peng, X. Y. Yu, Y. Jia, J. Wang, L. T. Kong, Z. Jin, T. Luo and J. H. Liu, *Chem. Commun.*, 2014, **50**, 7686.
- 42 Z. Xiong, Y. Ji, C. Fang, Q. Zhang, L. Zhang, M. Ye, W. Zhang and H. Zou, *Chem.-Eur. J.*, 2014, **20**, 7389.
- 43 Y.-X. J. Wang, *Quant. Imaging Med. Surg.*, 2011, **1**, 35.
- 44 H. Zheng, Y. Zhang, L. Liu, W. Wan, P. Guo, A. M. Nyström and X. Zou, *J. Am. Chem. Soc.*, 2016, **138**, 962.
- 45 X. G. Wang, Z. Y. Dong, H. Cheng, S. S. Wan, W. H. Chen, M. Z. Zou, J. W. Huo, H. X. Deng and X. Z. Zhang, *Nanoscale*, 2015, **7**, 16061.
- 46 R. Chen, J. F. Zhang, Y. Wang, X. F. Chen, J. A. Zapien and C. S. Lee, *Nanoscale*, 2015, **7**, 17299.
- 47 P. Horcajada, R. Gref, T. Baati, P. K. Allan, G. Maurin, P. Couvreur, G. Férey, R. E. Morris and C. Serre, *Chem. Rev.*, 2012, **112**, 1232.
- 48 L. Shen, W. Wu, R. Liang, R. Lin and L. Wu, *Nanoscale*, 2013, **5**, 9374.
- 49 J. Yang, Y. Dai, X. Zhu, Z. Wang, Y. Li, Q. Zhuang, J. Shi and J. Gu, *J. Mater. Chem. A*, 2015, **3**, 7445.
- 50 Y.-M. Zheng, L. Yu and J. P. Chen, *J. Colloid Interface Sci.*, 2012, **367**, 362.
- 51 L. N. Nagy, J. Mihaly, A. Polyak, B. Debreczeni, B. Csaszar, I. C. Szigvarto, A. Wacha, Z. Czegeny, E. Jakab, S. Klebert, E. Drotar, G. Dabasi, A. Bota, L. Balogh and E. Kiss, *J. Mater. Chem. B*, 2015, **3**, 7529.
- 52 R. Anand, F. Borghi, F. Manoli, I. Manet, V. Agostoni, P. Reschiglian, R. Gref and S. Monti, *J. Phys. Chem. B*, 2014, **118**, 8532.
- 53 F. Gao, L. Li, T. Liu, N. Hao, H. Liu, L. Tan, H. Li, X. Huang, B. Peng, C. Yan, L. Yang, X. Wu, D. Chen and F. Tang, *Nanoscale*, 2012, **4**, 3365.
- 54 C. He, K. Lu, D. Liu and W. Lin, *J. Am. Chem. Soc.*, 2014, **136**, 5181.
- 55 C. He, Y. Hu, L. Yin, C. Tang and C. Yin, *Biomaterials*, 2010, **31**, 3657.

