

CrossMark  
click for updates

## Biofunctional metal–phenolic films from dietary flavonoids†

Nadja Bertleff-Zieschang, Md. Arifur Rahim, Yi Ju, Julia A. Braunger, Tomoya Suma, Yunlu Dai, Shuaijun Pan, Francesca Cavalieri and Frank Caruso\*

Cite this: *Chem. Commun.*, 2017, 53, 1068

Received 26th October 2016,  
Accepted 19th December 2016

DOI: 10.1039/c6cc08607a

www.rsc.org/chemcomm

**We assembled dietary, bioactive flavonoids into a metal coordinated network to form thin, surface-bound films and hollow capsules, overcoming the poor water solubility of free flavonoids. Films formed from quercetin, myricetin, luteolin and fisetin show radical scavenging activity, a renowned feature of their parent flavonoids, and can be reused over multiple cycles. These films are expected to have potential applications in the pharmaceutical and food industries.**

Dietary flavonoids constitute an important class of plant polyphenols and are present in abundance in fruits, vegetables and leaves, where they fulfill diverse biological functions from pigmentation to defense against chemical and radiation damage.<sup>1</sup> Due to their human health benefits flavonoids have gained increasing attention for applications in anticancer treatment, protection against cardiovascular disease, and mitigation of inflammation.<sup>2,3</sup> A drawback of most flavonoids is their poor water solubility. Strategies to address this issue range from encapsulation of flavonoids into liposome or polymeric carriers<sup>4</sup> to synthetic modifications.<sup>5,6</sup> However, the preparation of thin surface-bound or free-standing films from dietary flavonoids has largely remained unexplored.

Here, we report the one-step assembly of four different flavonoids upon coordination with Fe<sup>III</sup> ions into thin films on solid surfaces. Considerable effort has been given to the fabrication of bioinspired functional coatings for application in medicine, optics and catalysis.<sup>7,8</sup> One prominent example is polyphenolic films obtained *via* oxidative polymerization on templating surfaces.<sup>9,10</sup> We recently reported a coordination-driven approach to deposit thin amorphous films from a variety of phenolic ligands and metal ions.<sup>11–13</sup> Among the different ligands pyrocatechol (PC, *ortho*-dihydroxybenzene) was found to be the simplest phenolic ligand that assembles with Fe<sup>III</sup> into

a metal phenolic network (MPN).<sup>13</sup> Given that the *ortho*-dihydroxyphenyl group is a common structural feature of many bioactive flavonoids, we investigated whether flavonoids could be assembled into nanostructured coatings and free-standing films, as such materials could be of potential interest in the pharmaceutical and food industries.


Myricetin (Myr), quercetin (Que), fisetin (Fis) and luteolin (Lut) are well known for their antioxidant, anti-inflammatory and antibacterial properties. Due to these properties we were interested in studying the MPN formation of flavonoid/Fe<sup>III</sup> films and to analyze the resulting films regarding their biofunctionality. The flavonoids in this study share a common structural feature, the *ortho*-dihydroxyphenyl group, but the overall hydroxylation pattern varies from Myr to Lut. Scheme 1 depicts the molecular structures of the flavonoids and illustrates the preparation of surface-bound films and hollow capsules that can be obtained after template removal.

For characterization of flavonoid MPN films we focused on the systems Que/Fe<sup>III</sup> and Myr/Fe<sup>III</sup>. Simple mixing of the flavonoids with Fe<sup>III</sup> in the presence of solid substrates instantaneously produces colored films (Fig. 1a and Fig. S1, ESI†). Well-dispersed hollow capsules were obtained from particulate substrates after template removal (*e.g.* PS microparticles, Fig. 1bi and v). The zeta ( $\zeta$ )-potentials of Que/Fe<sup>III</sup> and Myr/Fe<sup>III</sup> capsules were found to be  $-26 \pm 3$  mV and  $-34 \pm 3$  mV, respectively, most likely because of the acidic hydroxyl groups in both flavonoids ( $pK_{a1} = 7.2$  (Que),<sup>14</sup>  $pK_{a1} = 6.6$  (Myr)<sup>15</sup>).  $\zeta$ -Potentials are in the range for colloiddally stable particles.<sup>16</sup> Que/Fe<sup>III</sup> and Myr/Fe<sup>III</sup> capsules did not agglomerate in aqueous solution and intact capsules were observed for both systems over 10 days (Fig. S2, ESI†). Considering the molecular structure of Que and Myr, network formation can be assumed to occur *via* several coordination sites. Que and Myr are flavonol-type flavonoids consisting of a 3-ring system with two aromatic rings (A and B) that are linked *via* a heterocyclic pyrane ring C (Scheme 1a).<sup>17</sup> Among the different aromatic hydroxyl groups, the 3',4'-dihydroxyphenyl group has been reported to show the highest affinity for Fe<sup>III</sup>.<sup>18,19</sup> Further coordination sites within the flavonols are presented by the carbonyl oxygen with either


Australian Research Council (ARC) Centre of Excellence in Convergent Bio-Nano Science and Technology, and the Department of Chemical and Biomolecular Engineering, The University of Melbourne, Parkville, Victoria 3010, Australia.  
E-mail: fcaruso@unimelb.edu.au

† Electronic supplementary information (ESI) available. See DOI: 10.1039/c6cc08607a



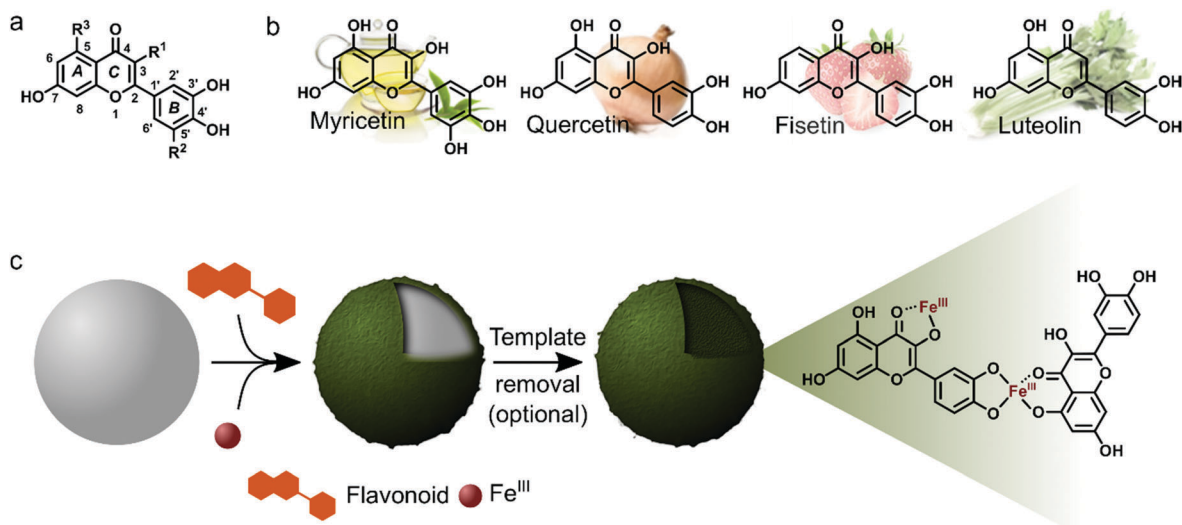

**Scheme 1** (a and b) Molecular structures of flavonoids investigated and their main source (myricetin: green tea; quercetin: onion; fisetin: strawberry; luteolin: celery). (c) Schematic illustration of coordination-driven assembly of flavonoids and  $\text{Fe}^{\text{III}}$  ions on a templating surface. The coordination-driven network formation is shown for Que/ $\text{Fe}^{\text{III}}$  where coordination can occur via three different coordination sites.

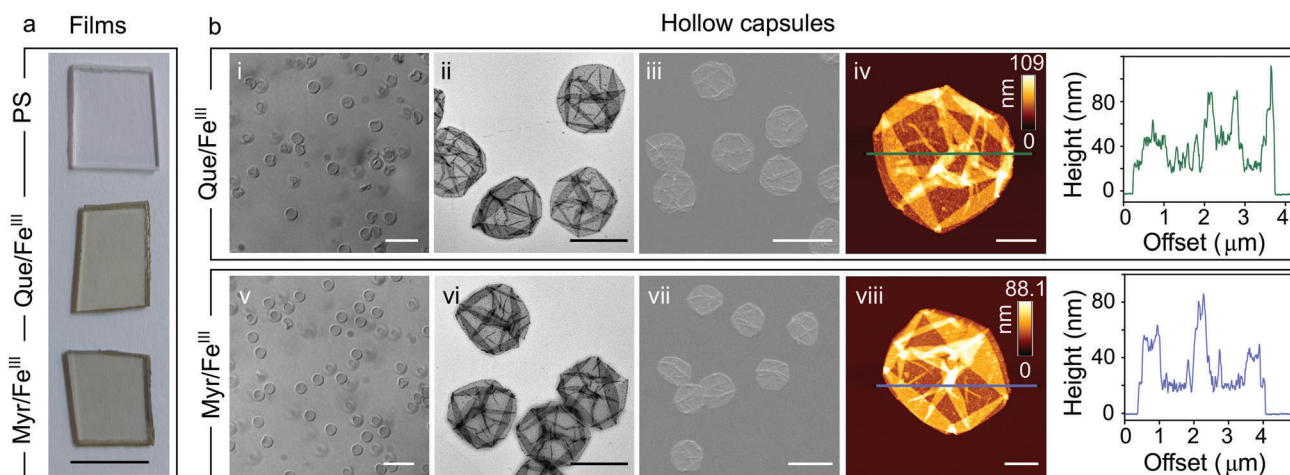

**Fig. 1** (a) Characterization of flavonoid/ $\text{Fe}^{\text{III}}$  films on planar PS substrates (scale bar 1 cm). From top to bottom: A piece of uncoated PS, PS coated with a Que/ $\text{Fe}^{\text{III}}$  film, and PS coated with a Myr/ $\text{Fe}^{\text{III}}$  film (five deposition cycles, respectively). (b) Characterization of Que/ $\text{Fe}^{\text{III}}$  and Myr/ $\text{Fe}^{\text{III}}$  hollow capsules that were obtained after film formation on PS particles and subsequent PS removal. From left to right: Differential interference contrast (DIC) microscopy (i and v), transmission electron microscopy (TEM) (ii and vi), scanning electron microscopy (SEM) (iii and vii) and atomic force microscopy (AFM) (with the height profile corresponding to the cross section indicated in green (iv) and blue (viii)) images. Scale bars are 10  $\mu\text{m}$  (i and v), 3  $\mu\text{m}$  (ii and vi), 5  $\mu\text{m}$  (iii and vii), and 1  $\mu\text{m}$  (iv and viii).

the 3-hydroxyl or 5-hydroxyl group.<sup>18,19</sup> The different reported coordination modes of Que to  $\text{Fe}^{\text{III}}$  are illustrated in Scheme 1c.

To further investigate metal coordination in the networks, UV/Vis absorption spectroscopy was performed on the Que/ $\text{Fe}^{\text{III}}$  and Myr/ $\text{Fe}^{\text{III}}$  capsules. UV/Vis absorption spectra of the Que/ $\text{Fe}^{\text{III}}$  and Myr/ $\text{Fe}^{\text{III}}$  systems showed two major absorption bands, each at 271 and 436 nm, and 265 and 437 nm, respectively (Fig. S3, ESI<sup>†</sup>). In contrast, free flavonoids showed absorption bands at shorter wavelengths (256 and 374 nm, and 254 and 378 nm for Que and Myr, respectively, Fig. S3, ESI<sup>†</sup>), which can be assigned to the  $\pi$ - $\pi^*$  transition of the A ring (benzoyl system, band II) and the B ring (cinnamoyl system, band I), respectively (Scheme 1a).<sup>17</sup>

A bathochromic shift upon metal coordination has been observed for the Que absorption band I previously<sup>17,20</sup> and has been ascribed to the extension of the conjugated  $\pi$ -system rather than to a ligand to metal charge transfer (LMCT)<sup>17</sup> characteristic of catechol- $\text{Fe}^{\text{III}}$  complexes.<sup>21</sup> This indicates that metal coordination at the B ring is the major driving force for film formation. Additionally, fluorescence spectroscopy of the Que/ $\text{Fe}^{\text{III}}$  system revealed that the emission of Que at 517 nm ( $\lambda_{\text{exc}} = 380$  nm) is efficiently quenched by  $\text{Fe}^{\text{III}}$  coordination (Fig. S4, ESI<sup>†</sup>), which is consistent with previous reports on Que complexes with  $\text{Cu}^{\text{II}}$ ,  $\text{Fe}^{\text{II}}$  and  $\text{Fe}^{\text{III}}$ .<sup>22,23</sup>

Next, we analyzed the morphology and composition of air-dried capsules by transmission electron microscopy (TEM, Fig. 1bii and vi),



scanning electron microscopy (SEM, Fig. 1biii and vii), and atomic force microscopy (AFM, Fig. 1biv and viii). AFM height analysis yielded single wall thicknesses of  $12.0 \pm 0.6$  nm and  $13.2 \pm 1.1$  nm for Que/Fe<sup>III</sup> and Myr/Fe<sup>III</sup> capsules, respectively, which are similar to values obtained for tannic acid(TA)/Fe<sup>III</sup> ( $10.4 \pm 0.6$  nm)<sup>11</sup> and PC/Fe<sup>III</sup> ( $11.4 \pm 0.4$  nm)<sup>13</sup> capsules in previous work. Surface roughness analyses resulted in values of  $3.6 \pm 0.4$  nm and  $2.3 \pm 0.6$  nm for Que/Fe<sup>III</sup> and Myr/Fe<sup>III</sup> capsules, respectively, which are higher than found for TA/Fe<sup>III</sup> ( $1.6 \pm 0.1$  nm)<sup>11</sup> and PC/Fe<sup>III</sup> (*ca.* 0.4 nm).<sup>13</sup> X-ray photoelectron spectroscopy (XPS) on Que/Fe<sup>III</sup> and Myr/Fe<sup>III</sup> capsules indicated that Fe<sup>III</sup> is the predominant species in the films with Fe 2p<sub>3/2</sub> and Fe 2p<sub>1/2</sub> signals at  $\sim 712$  eV and  $\sim 725$  eV (Fig. S5, ESI<sup>†</sup>).<sup>24</sup> Energy-dispersive X-ray (EDX) spectroscopy and elemental mapping further showed a uniform distribution of Fe, C and O within the capsules (Fig. S6 and S7, ESI<sup>†</sup>) of Que/Fe<sup>III</sup> and Myr/Fe<sup>III</sup>.

The underlying mechanism of the network formation is a pH-dependent process based on coordination chemistry between a flavonoid ligand and Fe<sup>III</sup>. At acidic pH, Que/Fe<sup>III</sup> and Myr/Fe<sup>III</sup> capsules readily disassembled, as monitored by optical microscopy. UV/Vis spectroscopy of the disassembled Que/Fe<sup>III</sup> system further revealed the disappearance of absorption bands assigned to the complex and the reappearance of bands at 256 and 374 nm found in free Que (Fig. S3a, ESI<sup>†</sup>). Interestingly, the absorption bands in the UV/Vis spectrum of acid-treated Myr/Fe<sup>III</sup> capsules did not match with those of free Myr, suggesting that Myr at least partly coordinates to Fe<sup>III</sup> under these conditions (Fig. S3b, ESI<sup>†</sup>). Similar to the UV/Vis spectroscopy findings, the fluorescence emission observed for free Que was restored when disassembling Que/Fe<sup>III</sup> capsules (Fig. S4, ESI<sup>†</sup>). The on/off fluorescence between capsules and free Que is potentially promising for application in

sensing and monitoring of Que release in a physiological context. In addition, pH-induced disassembly of Que/Fe<sup>III</sup> capsules served to quantitatively determine the amount of flavonoid and metal in a single capsule. The capsule concentration was first determined by flow cytometry and the amount of Que was subsequently estimated to be 0.67 fmol per capsule from UV/Vis spectroscopy of the acid-treated sample. Inductively coupled plasma optical emission spectroscopy (ICP-OES) experiments yielded a Fe concentration of *ca.* 0.23 fmol per capsule, leading to a ligand/metal ratio of  $\sim 3:1$ .

Finally, we investigated the biological activity of flavonoid/Fe<sup>III</sup> films. Among the plethora of functions attributed to dietary flavonoids the most renowned are their antioxidant properties and their ability to scavenge free radicals.<sup>25</sup> Radical oxygen species (ROS) play critical roles in inflammation processes. Therefore, films with radical scavenging properties have potential as cytoprotective and anti-inflammatory coatings of, for example, medical implants.<sup>9,26,27</sup> We probed the radical scavenging activity of the flavonoid/Fe<sup>III</sup> coatings with the well-established method based on the stable 2,2-diphenyl-1-picrylhydrazyl (DPPH) radical, which shows a characteristic absorption at 517 nm in ethanol.<sup>9,28</sup> Here, radical scavenging activity can be visually followed by discoloration of the purple ethanolic solution of DPPH (Fig. 2d) and quantified by UV/Vis spectroscopy. The decrease in absorption at 517 nm (Fig. 2a) can be correlated to the consumption of the DPPH radical (molecular structures of the DPPH radical and the reduced DPPH are shown in Fig. S8, ESI<sup>†</sup>). Films from Que, Myr and Fis showed strong scavenging activity with 80% or more DPPH consumption after 60 min (Fig. 2b), while the Lut/Fe<sup>III</sup> network consumed less than 40% (Fig. 2b), presumably due to the absence of the 3-hydroxyl group in the C ring.<sup>29,30</sup> Based on this finding, we compared the scavenging activity of free Que, Que/Fe<sup>III</sup> coatings

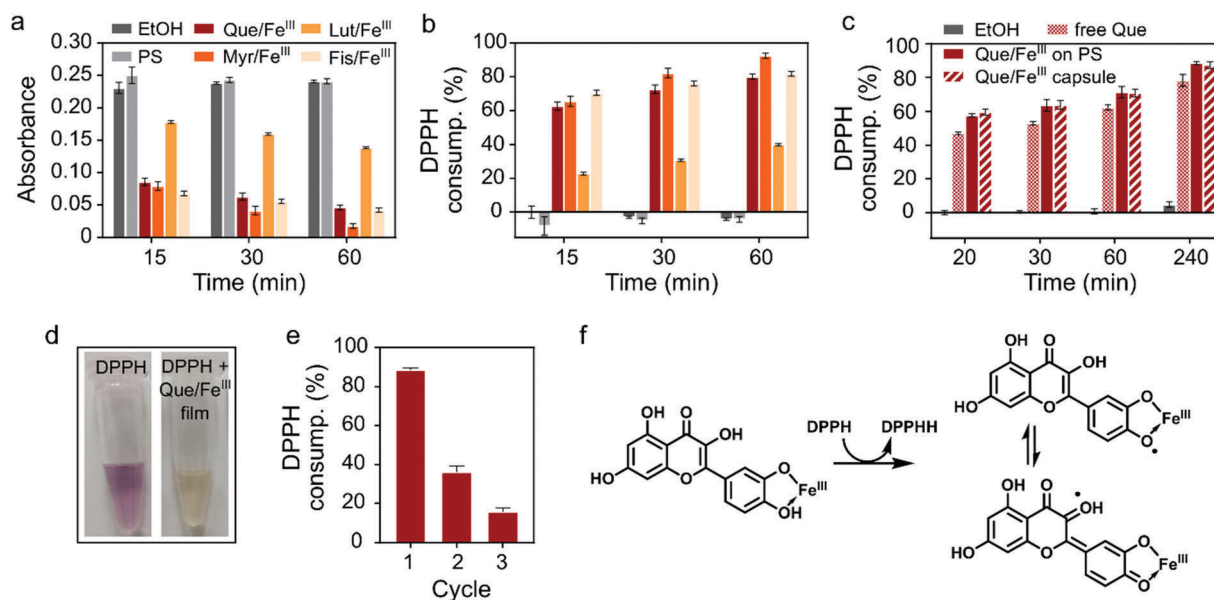


Fig. 2 Radical scavenging ability of flavonoid/Fe<sup>III</sup> films determined with the DPPH method. Decrease in absorption at 517 nm at different time points indicates radical scavenging (a) and correlates to consumption of DPPH (b, same color code as in (a)). DPPH consumption of free Que, Que/Fe<sup>III</sup> film and Que/Fe<sup>III</sup> capsules at different time points. Concentration of Que is 10  $\mu$ M in all systems (c). Ethanolic DPPH solution (left) discolored after exposure (1 h) to a Que/Fe<sup>III</sup> film (right) (d). Que/Fe<sup>III</sup> films showed repeated radical scavenging activity over 3 cycles of 30 min incubation with intermediate washing steps (e). Proposed mechanism of complexed quercetin oxidation. The intermediate radical is stabilized by the metal center and conjugation with the 3-OH group (f).





and Que/Fe<sup>III</sup> capsules of the same Que concentration (Fig. 2c). Both Que/Fe<sup>III</sup> films on PS particles and as capsules consumed the same amount of DPPH, as monitored over 4 h, which indicates that PS only acts as a template and does not interfere with the scavenging activity of the MPN layer. Further, Que/Fe<sup>III</sup> films showed ca. 10% higher activity than free Que. The higher scavenging activity of complexed flavonoids can be explained by the stabilization of the intermediate semiquinone radical by the iron center and the conjugation with the 3-OH group (Fig. 2f).<sup>20,30</sup> In addition to the higher scavenging activity of our Que/Fe<sup>III</sup> films, we found that the films can be reused and that the scavenging activity was lowered but preserved over at least three cycles (Fig. 2e). Que collected from the films that were exposed to DPPH for 30 min showed a decrease in the absorption band of the B ring at 374 nm while a new band appeared at 292 nm (Fig. S9, ESI†). We assume that oxidation of the films by DPPH decreases the amount of available antioxidant species and reduces the scavenging activity in the subsequent cycles. Taken together, the higher scavenging activity of the flavonoid/Fe<sup>III</sup> films, and the easy removal and reusability of coated particles provides advantages over free flavonoids.

In conclusion, we developed bifunctional films and capsules from dietary flavonoids (Que, Myr, Lut, and Fis), exploiting the rapid coordination-driven assembly with Fe<sup>III</sup>. Flavonoids have many attractive properties in a biomedical context, including antioxidant, anti-inflammatory, anticancer and antimicrobial activity. However, most flavonoids suffer from poor water solubility, limiting their therapeutic usefulness. We overcame this issue by making flavonoids available in thin metal-coordinated films with radical scavenging activity. We demonstrated that the antioxidant activity of the complexed Que is higher than that of the free molecule and is preserved over multiple scavenging cycles. The versatility and simplicity of this approach makes flavonoid MPN films and capsules attractive candidates for potential applications in biomedicine and the food industry. Part of our future studies is to investigate other metal ions to form flavonoid MPNs to combine the properties of flavonoids with those of different metal ions. For example, we have demonstrated previously that MPNs from tannic acid and biomedically relevant metals, such as Gd<sup>III</sup>, <sup>64</sup>Cu<sup>II</sup> and Eu<sup>III</sup>, show potential for diagnostics and bio-imaging.<sup>12</sup>

This research was conducted and funded by the Australian Research Council Centre of Excellence in Convergent Bio-Nano Science and Technology (project number CE140100036). This work was also supported by the Australian Research Council (ARC) under the Australian Laureate Fellowship (F. Caruso, FL120100030), Super Science Fellowship (F. Caruso, FS110200025), and Future Fellowship (F. Cavaliere, FT140100873) schemes.

This work was performed in part at the Materials Characterisation and Fabrication Platform (MCFP) at the University of Melbourne and the Victorian Node of the Australian National Fabrication Facility (ANFF).

## Notes and references

- 1 F. Ververidis, E. Trantas, C. Douglas, G. Vollmer, G. Kretzschmar and N. Panopoulos, *Biotechnol. J.*, 2007, **2**, 1214–1234.
- 2 A. Garcia-Lafuente, E. Guillaumon, A. Villares, M. A. Rostagno and J. A. Martinez, *Inflammation Res.*, 2009, **58**, 537–552.
- 3 M.-H. Pan, C.-S. Lai and C.-T. Ho, *Food Funct.*, 2010, **1**, 15–31.
- 4 F. Aqil, R. Munagala, J. Jayabalan and M. V. Vadhanam, *Cancer Lett.*, 2013, **334**, 133–141.
- 5 M. K. Kim, H. Choo and Y. Chong, *J. Med. Chem.*, 2014, **57**, 7216–7233.
- 6 H. Zhang, M. Zhang, L. Yu, Y. Zhao, N. He and X. Yang, *Food Chem. Toxicol.*, 2012, **50**, 1589–1599.
- 7 Y. L. Liu, K. L. Ai and L. H. Lu, *Chem. Rev.*, 2014, **114**, 5057–5115.
- 8 M. Krogsgaard, V. Nue and H. Birkedal, *Chem. – Eur. J.*, 2015, **22**, 844–857.
- 9 T. S. Sileika, D. G. Barrett, R. Zhang, K. H. A. Lau and P. B. Messersmith, *Angew. Chem., Int. Ed.*, 2013, **52**, 10766–10770.
- 10 T. S. Sileika, H.-D. Kim, P. Maniak and P. B. Messersmith, *ACS Appl. Mater. Interfaces*, 2011, **3**, 4602–4610.
- 11 H. Ejima, J. J. Richardson, K. Liang, J. P. Best, M. P. van Koevreden, G. K. Such, J. Cui and F. Caruso, *Science*, 2013, **341**, 154–157.
- 12 J. Guo, Y. Ping, H. Ejima, K. Alt, M. Meissner, J. J. Richardson, Y. Yan, K. Peter, D. von Elverfeldt, C. E. Hagemeyer and F. Caruso, *Angew. Chem., Int. Ed.*, 2014, **53**, 5546–5551.
- 13 M. A. Rahim, K. Kempe, M. Müllner, H. Ejima, Y. Ju, M. P. van Koevreden, T. Suma, J. A. Braunger, M. G. Leeming, B. F. Abrahams and F. Caruso, *Chem. Mater.*, 2015, **27**, 5825–5832.
- 14 J. M. Herrero-Martinez, M. Sanmartin, M. Rosés, E. Bosch and C. Ràfols, *Electrophoresis*, 2005, **26**, 1886–1895.
- 15 Y. S. Yao, G. B. Lin, Y. Xie, P. Ma, G. W. Li, Q. C. Meng and T. Wu, *Pharmazie*, 2014, **69**, 19–26.
- 16 Zetasizer Nano Series User Manual, Feb. 2004, MAN0317.
- 17 M. Guo, C. Perez, Y. Wei, E. Rapoza, G. Su, F. Bou-Abdallah and N. D. Chasteen, *Dalton Trans.*, 2007, 4951–4961.
- 18 G. M. Escandar and L. F. Sala, *Can. J. Chem.*, 1991, **69**, 1994–2001.
- 19 M. D. Engelmann, R. Hutcheson and I. F. Cheng, *J. Agric. Food Chem.*, 2005, **53**, 2953–2960.
- 20 R. F. V. de Souza and W. F. De Giovani, *Redox Rep.*, 2004, **9**, 97–104.
- 21 N. R. Perron and J. L. Brumaghim, *Cell Biochem. Biophys.*, 2009, **53**, 75–100.
- 22 S. Yang, B. Yin, L. Xu, B. Gao, H. Sun, L. Du, Y. Tang, W. Jiang and F. Cao, *Anal. Methods*, 2015, **7**, 4546–4551.
- 23 C. C. Yu and Z. H. Cheng, *Anal. Lett.*, 2003, **36**, 767–780.
- 24 T. Yamashita and P. Hayes, *Appl. Surf. Sci.*, 2008, **254**, 2441–2449.
- 25 G. B. Bubols, D. D. Vianna, A. Medina-Remon, G. von Poser, R. M. Lamuela-Raventos, V. L. Eifler-Lima and S. C. Garcia, *Mini-Rev. Med. Chem.*, 2013, **13**, 318–334.
- 26 M. M. Kasprzak, A. Erxleben and J. Ochocki, *RSC Adv.*, 2015, **5**, 45853–45877.
- 27 I. B. Afanas'ev, E. A. Ostrakhovitch, E. V. Mikhal'chik, G. A. Ibragimova and L. G. Korkina, *Biochem. Pharmacol.*, 2001, **61**, 677–684.
- 28 Y. Deligiannakis, G. A. Sotiriou and S. E. Pratsinis, *ACS Appl. Mater. Interfaces*, 2012, **4**, 6609–6617.
- 29 Y. Kwon, H. Kim, S. Park and S. Jung, *Bull. Korean Chem. Soc.*, 2010, **31**, 3035–3037.
- 30 M. Y. Moridani, J. Pourahmad, H. Bui, A. Siraki and P. J. O'Brien, *Free Radical Biol. Med.*, 2003, **34**, 243–253.

