



Cite this: *RSC Adv.*, 2017, 7, 5821

# Enhanced photocatalytic oxygen evolution over Mo-doped $\text{Ca}_2\text{NiWO}_6$ perovskite photocatalyst under visible light irradiation

Ying Luo,<sup>a</sup> Jiawei Xue,<sup>a</sup> Xiaodi Zhu,<sup>a</sup> Jose Daniel,<sup>a</sup> Xiang Gao,<sup>a</sup> Song Sun,<sup>\*a</sup> Chen Gao<sup>\*ab</sup> and Jun Bao<sup>\*a</sup>

A series of Mo-doped  $\text{Ca}_2\text{NiWO}_6$  ( $\text{Ca}_2\text{NiW}_{1-x}\text{Mo}_x\text{O}_6$ ,  $x = 0-0.05$ ) samples were synthesized by a solid-state reaction. The physical and optical properties of these photocatalysts were characterized by X-ray diffraction, X-ray absorption fine structure, UV-visible diffuse reflectance spectra, and the band structure along with density of states were calculated by the plane-wave-based density functional theory. The photocatalytic activity of oxygen evolution from water was evaluated under visible light irradiation. The Mo doping significantly increased the photocatalytic activity of  $\text{Ca}_2\text{NiWO}_6$ . The optimal  $\text{Ca}_2\text{NiW}_{0.97}\text{Mo}_{0.03}\text{O}_6$  showed an oxygen evolution rate approximately 2 times higher than that of the pure  $\text{Ca}_2\text{NiWO}_6$ . The characterization results indicated that the Mo-doped  $\text{Ca}_2\text{NiWO}_6$  maintained the double perovskite structure. The  $\text{Mo}^{6+}$  ions were substituted into the  $\text{W}^{6+}$  sites in the lattice, causing a certain amount of lattice distortion and promoting the formation of oxygen vacancies. Furthermore, the Mo doping introduced impurity energy levels into the band structure of  $\text{Ca}_2\text{NiWO}_6$ . Consequently, the conduction band changed from discrete to continuous and the bottom of the conduction band was shifted to more positive potential, compared to that of pure  $\text{Ca}_2\text{NiWO}_6$ , leading to a lower band gap and higher absorbance in the wider visible light region. These characteristics are responsible for the high photocatalytic activity of the oxygen evolution reaction.

Received 31st October 2016  
Accepted 20th December 2016

DOI: 10.1039/c6ra26072a

[www.rsc.org/advances](http://www.rsc.org/advances)

## Introduction

With increasing demands for clean energy, photocatalytic water splitting to generate hydrogen and oxygen has attracted significant attention because of the low energy consumption, simple operation process and mild reaction conditions.<sup>1-5</sup> An ideal photocatalyst for overall water splitting should have proper band position, *i.e.*, the conduction band minimum (CBM) should be more negative than the hydrogen evolution potential ( $\text{H}^+/\text{H}_2$  0.0 eV *vs.* normal hydrogen electrode (NHE)), meanwhile, the valence band maximum (VBM) should be more positive than the oxygen evolution potential ( $\text{O}_2/\text{H}_2\text{O}$  +1.23 eV *vs.* NHE). Despite several decades of intensive studies, to date, only a few photocatalysts have been discovered to be active for overall water splitting into hydrogen and oxygen under visible light irradiation.<sup>6-9</sup> Many attempts have been made to increase the activity of the half reaction of water splitting, the oxidation of water to form oxygen or the reduction of protons to produce

hydrogen.<sup>10</sup> For the oxygen evolution reaction (OER), high energy is required to undertake the O-H bond breaking and the attendant O-O bond formation, thus requiring a more positive VB level of the efficient photocatalyst.<sup>11-13</sup> In recent years, notable progress has been achieved in the search for highly active oxygen evolution photocatalysts, including simple oxides (*e.g.*  $\text{TiO}_2$  (ref. 14) and  $\text{CoO}_x$  (ref. 15)), complex oxides (*e.g.*  $\text{SrTiO}_3$  (ref. 16) and  $\text{BiVO}_4$  (ref. 17)), nitrides (*e.g.*  $\text{C}_3\text{N}_4$  (ref. 18)), and sulfides (*e.g.*  $\text{Cu}_2\text{ZnSnS}_4$  (ref. 19)).

Perovskite structured compounds have attracted significant attention as photocatalysts due to their unique physicochemical properties, demonstrating the potential for application in water splitting and decontamination.<sup>20-23</sup> It was found that the band structure, optical properties, and chemical stability of perovskite photocatalysts can be modified and the photocatalytic activity can be improved by doping or partial replacement, on the basis of maintaining the basic structure. Some researchers have reported that doping with transition metal ions such as rhodium, chromium, vanadium and tungsten results in the red shift of the light absorption of perovskite-type compounds to the visible light region.<sup>24-27</sup> For instance, Kim *et al.*<sup>28</sup> have found that the W-doped  $\text{Sr}_2\text{FeNbO}_6$  showed a photocatalytic quantum yield two times higher than that of the pristine sample under visible light irradiation. A similar conclusion was arrived at from  $\text{La}_2\text{Ti}_2\text{O}_7$  perovskite nanosheets with a narrow band gap

<sup>a</sup>National Synchrotron Radiation Laboratory & Collaborative Innovation Center of Chemistry for Energy Materials, University of Science and Technology of China, Hefei, Anhui, 230029, China. E-mail: [baoj@ustc.edu.cn](mailto:baoj@ustc.edu.cn); [suns@ustc.edu.cn](mailto:suns@ustc.edu.cn)

<sup>b</sup>CAS Key Laboratory of Materials for Energy Conversion, Department of Materials Science and Engineering, University of Science and Technology of China, Hefei, Anhui, 230026, China. E-mail: [cga@ustc.edu.cn](mailto:cga@ustc.edu.cn)



after Ni doping.<sup>29</sup> Cheng *et al.*<sup>30</sup> reported that the  $\text{La}_{1-x}\text{Sr}_x\text{CoO}_3$  perovskites have good photocatalytic activity for OER. The experimental and theoretical investigation confirmed that  $\text{Sr}^{3+}$  substitutions straightened the octahedral cage, aligned atoms along the Co–O–Co axis, and increased the average oxidation state of the Co ions. Consequently, the overlap between the occupied O 2p VB and the unoccupied Co 3d CB increased and thus improved the OER activity. Recently, the perovskite-type ( $\text{Ln}_{0.5}\text{Ba}_{0.5}$ ) $\text{CoO}_{3-x}$  (Ln = Pr, Sm, Gd and Ho) have also been reported as a family of efficient photocatalysts for the OER in alkaline solution.<sup>31</sup>

The double-perovskite-type compound  $\text{Ca}_2\text{NiWO}_6$  consists of a layered structure of corner-sharing regular octahedrons,  $\text{WO}_6$  and  $\text{NiO}_6$ , with a unique chain of the –Ni–W–O–. The VB of  $\text{Ca}_2\text{NiWO}_6$  is controlled by the hybrid O 2p and Ni  $t_{2g}$  orbitals, and the CB is composed of two discrete energy levels, the W 5d and Ni  $e_g$  levels.<sup>32</sup> The excited electrons from the VB to the W 5d CB are responsible for the absorption in the UV region, and the other from the VB to the Ni  $e_g$  CB corresponds to the absorption in the visible light region. Consequently, the  $\text{Ca}_2\text{NiWO}_6$  perovskite showed photocatalytic activity for oxygen evolution under visible light irradiation. However, the band gap (2.61 eV) is still relatively large, limiting its further application in the visible light region. It is expected that the doping modification may expand the spectral response of the photocatalyst and increase the photocatalytic activity by introducing the appropriate impurity level into the band gap. To the best of our knowledge, the study on the modification of  $\text{Ca}_2\text{NiWO}_6$  by metal doping has not been reported so far.

In this study, the role of the Mo dopant in the structural features of  $\text{Ca}_2\text{NiWO}_6$  and the photocatalytic activity for the OER were investigated. A series of Mo-doped  $\text{Ca}_2\text{NiWO}_6$  with different doping levels was synthesized by a conventional solid-state reaction. The Mo-doped samples showed much higher OER activity than that of the pristine sample under visible light irradiation. With a combination of experimental and theoretical investigations, the effects of  $\text{Mo}^{6+}$  ion doping on the crystal structure, band structure and optical properties of double-perovskite  $\text{Ca}_2\text{NiWO}_6$  were studied in detail and the structure–performance relationship was discussed.

## Experimental

$\text{Ca}_2\text{NiW}_{1-x}\text{Mo}_x\text{O}_6$  ( $x = 0, 0.01, 0.02, 0.03, 0.04, 0.05$ ) was prepared by a conventional solid-state reaction. The starting materials consisted of  $\text{CaCO}_3$ ,  $\text{WO}_3$ ,  $\text{NiO}$  and  $\text{MoO}_3$ , which were mixed in the molar ratio Ca : Ni : W : Mo = 2 : 1 : 1 –  $x$  :  $x$  ( $x = 0.01, 0.02, 0.03, 0.04, 0.05$ ). The solid mixture was ground thoroughly and then calcined in air at 1273 K for 20 h. After cooling to room temperature, the mixture was reground and calcined once again at 1553 K for 10 h.

The as-prepared samples were characterized by various analytical techniques. X-ray diffraction (XRD) patterns were recorded on a Rigaku (D/MAX-A) X-ray diffractometer using a Cu K $\alpha$  radiation source. UV-visible diffuse reflectance spectra (UV-vis DRS) were measured on a UV-visible spectrophotometer (Solidspec DUC-3700) using  $\text{BaSO}_4$  as a reference. The Mo K-

edge X-ray absorption fine structure (XAFS) measurements were performed at the endstation of 1W1B of the Beijing Synchrotron Radiation Facility (BSRF, China). The storage ring energy was 2.5 GeV with an average current of 200 mA. Spectra were collected in the fluorescence mode using a Si (111) double crystal monochromator. The energy calibration of the Mo K-edge was performed using a Mo foil. Data processing was carried out using the ATHENA software package.<sup>33</sup> The electronic band structures, along with densities of states were calculated by the plane-wave-based density functional theory (DFT), using the CASTEP program.<sup>34,35</sup> The exchange correlation potential and ultrasoft pseudopotentials for electron–ion interactions were modeled using the generalized gradient approximation (GGA) of Perdew–Burke–Ernzerhof (PBE). The kinetic energy cut-off was taken to be 380 eV for  $\text{Ca}_2\text{NiWO}_6$ . A supercell consisting of a ( $2 \times 2 \times 1$ ) unit cell was used in the calculations. The lattice parameter of  $\text{Ca}_2\text{NiW}_{1-x}\text{Mo}_x\text{O}_6$  was based on the structure of  $\text{Ca}_2\text{NiWO}_6$ :  $a = 5.4048 \text{ \AA}$ ,  $b = 5.5369 \text{ \AA}$ ,  $c = 7.6889 \text{ \AA}$ , which formed a layered crystal structure with the space group  $P21/n$ .

The photocatalytic  $\text{O}_2$  evolution of the as-prepared samples were evaluated on commercial water splitting equipment (LABSOLAR-IIAGA, Beijing PERFECTLIGHT Technology Co. Ltd.). In a typical test, 0.185 g of photocatalyst powder were dispersed into 100 ml of distilled water in a quartz reaction cell with an external cooling jacket.  $\text{AgNO}_3$  (1.85 mmol) was used as the sacrificial electron acceptor. A 300 W xenon arc lamp (PLS-SXE300 UV, Beijing Perfectlight Technology Co. Ltd) with a 400 nm cut-off filter was used as the light source. Prior to irradiation, the closed gas circulation system and reaction cell were well evacuated. The amounts of evolved gases were analyzed by an on-line gas chromatograph (GC1690, Hangzhou Kexiao Scientific Instruments Co. Ltd) equipped with a thermal conductivity detector (TCD) and a KX-112 packed column (Lanzhou Institute of Chemical Physics).

## Results and discussion

### Characterization of photocatalysts

The XRD patterns of  $\text{Ca}_2\text{NiW}_{1-x}\text{Mo}_x\text{O}_6$  ( $x = 0, 0.01, 0.02, 0.03, 0.04, 0.05$ ) are shown in Fig. 1. For the undoped sample, the positions and relative intensities of all diffraction peaks matched well with the standard data of  $\text{Ca}_2\text{NiWO}_6$  (JCPDS No. 47-0026), indicating that a pure perovskite phase was obtained.

After doping with  $\text{Mo}^{6+}$  ions, the XRD patterns did not show significant differences from that of the pure  $\text{Ca}_2\text{NiWO}_6$ , even at a relatively high Mo doping level ( $x = 0.05$ ). The results indicated that the doping of  $\text{Mo}^{6+}$  ions did not cause a significant change in the host structure or introduce any impurity phase. The Mo-doped  $\text{Ca}_2\text{NiWO}_6$  still maintained the perovskite structure. It is suggested that the doped  $\text{Mo}^{6+}$  ions can be substituted into the  $\text{W}^{6+}$  sites in the structure, due to their similar ionic radii. Further evidence came from the XAFS measurements, which can provide detailed information on the local coordination structure of center atoms.

Fig. 2 shows the Fourier transforms of Mo K-edge EXAFS of the  $\text{Ca}_2\text{NiW}_{1-x}\text{Mo}_x\text{O}_6$  ( $x = 0.01, 0.03$  and  $0.05$ ) and standard



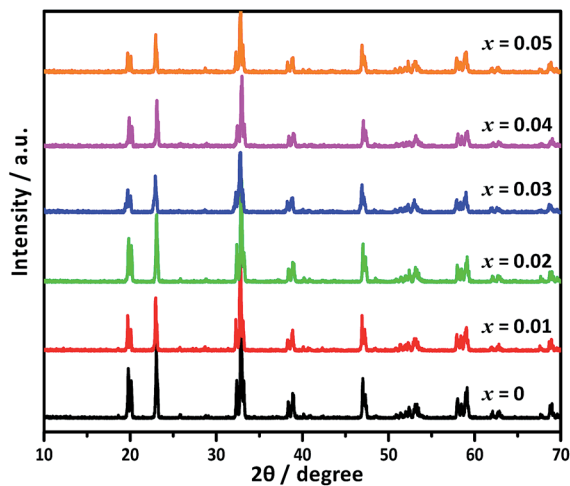


Fig. 1 XRD patterns of  $\text{Ca}_2\text{NiW}_{1-x}\text{Mo}_x\text{O}_6$  ( $x = 0, 0.01, 0.02, 0.03, 0.04,$  and  $0.05$ ).

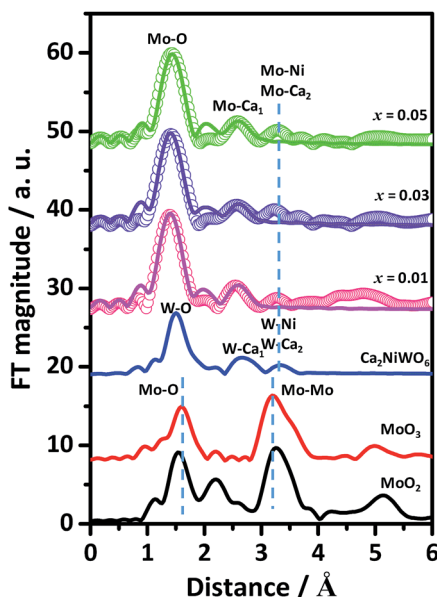


Fig. 2 RDFs of  $\text{Ca}_2\text{NiW}_{1-x}\text{Mo}_x\text{O}_6$  ( $x = 0.01, 0.03,$  and  $0.05$ ),  $\text{Ca}_2\text{NiWO}_6$ ,  $\text{MoO}_2$ , and  $\text{MoO}_3$  samples.

compounds  $\text{MoO}_2$  and  $\text{MoO}_3$ . For comparison, the theoretical radial distribution function (RDF) of W atoms of the  $\text{Ca}_2\text{NiWO}_6$  crystals was also calculated and presented in the figure. The fitting results are listed in Table 1. From the figure, it can be seen that the RDFs of the Mo-doped  $\text{Ca}_2\text{NiWO}_6$  were completely different from that of the  $\text{MoO}_3$  and  $\text{MoO}_2$ . In particular, no significant Mo–Mo coordination peaks assigned to  $\text{MoO}_3$  and  $\text{MoO}_2$  were found in the doped samples. Furthermore, the RDF curves of doped samples were very similar to those of pure  $\text{Ca}_2\text{NiWO}_6$ . The Mo–O and Mo–Ca coordination peaks at about 1.41 Å and 2.55 Å exhibited similar characteristics to those of W–O and W–Ca coordination peaks in  $\text{Ca}_2\text{NiWO}_6$ . These results confirmed that no isolated molybdenum oxides were formed at the present Mo doping levels. The Mo ions entered the crystal

Table 1 XAFS fitting results for  $\text{Ca}_2\text{NiW}_{1-x}\text{Mo}_x\text{O}_6$  ( $x = 0.01, 0.02,$  and  $0.05$ )

Sample	Shell	$R^a$ (Å)	$N^b$	$\sigma^c$ (Å <sup>2</sup> )
$\text{Ca}_2\text{NiWO}_6$	W–O	1.411	6.0	—
	W–Ca(i)	2.546	6.0	—
	W–Ca(ii)	3.221	2.0	—
	W–Ni	3.344	4.0	—
$x = 0.01$	Mo–O	1.411	5.21	0.001
	Mo–Ca(i)	2.577	6.00	0.011
$x = 0.03$	Mo–O	1.411	5.13	0.001
	Mo–Ca(i)	2.608	6.00	0.012
$x = 0.05$	Mo–O	1.442	4.87	0.001
	Mo–Ca(i)	2.608	6.00	0.010

<sup>a</sup> Coordination distance. <sup>b</sup> Coordination number. <sup>c</sup> Debye–Waller factor.

lattice of  $\text{Ca}_2\text{NiWO}_6$ , substituting for the hexa-coordinated  $\text{W}^{6+}$  sites.

According to the fitting structural parameters, the schematic diagrams of the crystal lattice of the samples were drawn by Materials Studio as shown in Fig. 3. For the pure  $\text{Ca}_2\text{NiWO}_6$  (Fig. 3a), each W atom was coordinated with six O atoms (the first shell) and six Ca atoms (the second shell). The Mo doping induced internal stresses and exerted a certain effect on the structure of  $\text{Ca}_2\text{NiWO}_6$ , leading to the lattice distortion, as illustrated in Fig. 3b. The coordination distances of Mo–O and Mo–Ca in  $\text{Ca}_2\text{NiW}_{1-x}\text{Mo}_x\text{O}_6$  were both larger than that of W–O and W–Ca in pure  $\text{Ca}_2\text{NiWO}_6$ . Furthermore, the coordination number of Mo–O atoms also decreased, leading to the formation of oxygen vacancies.

The UV-Vis DRS of  $\text{Ca}_2\text{NiW}_{1-x}\text{Mo}_x\text{O}_6$  ( $x = 0, 0.01, 0.02, 0.03, 0.04, 0.05$ ) are shown in Fig. 4a. The pure  $\text{Ca}_2\text{NiWO}_6$  had three distinct absorption bands in the range of 443–535 nm. The two steep absorption bands at 443 and 492 nm were assigned to the charge transition from the VB to the W 5d level and Ni 3d level, respectively.<sup>32</sup> The absorption band located at 535 nm may be due to the charge transition from the VB to the impurity or defect level. For the doped samples, the steps between different absorption edges were gradually elevated with an increase in Mo concentration, and finally combined into a gentle absorption edge. Furthermore, the absorption edge was shifted to longer wavelengths with increasing Mo content. Accordingly, the color of the samples changed from light green to yellow (the inset in Fig. 4a). The band gaps,  $E_g$ , of the samples were calculated using the Tauc equation.<sup>36,37</sup>

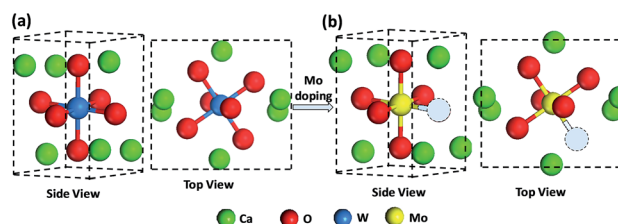


Fig. 3 Schematic of the crystal structure of (a) pure  $\text{Ca}_2\text{NiWO}_6$  and (b) Mo-doped  $\text{Ca}_2\text{NiWO}_6$ .



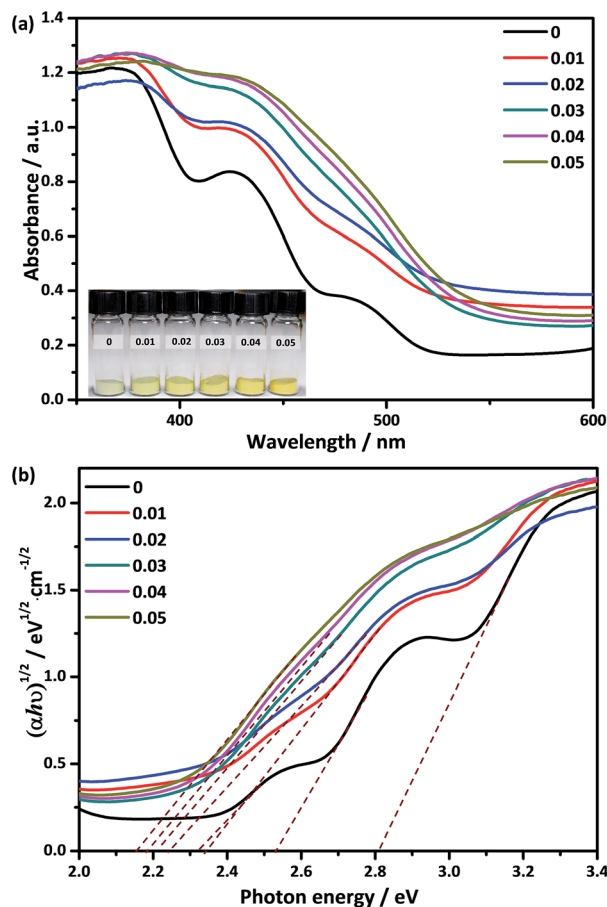


Fig. 4 (a) UV-visible DRS of  $\text{Ca}_2\text{NiW}_{1-x}\text{Mo}_x\text{O}_6$  ( $x = 0, 0.01, 0.02, 0.03, 0.04, 0.05$ ), the inset shows the color change after Mo doping; (b) the corresponding Kubelka–Munk transformed diffuse reflectance spectra.

$$\alpha hv = C_1(hv - E_g)^2 \quad (1)$$

where  $\alpha$  is the optical absorption coefficient measured as a function of photon energy  $hv$ , and  $C_1$  is the absorption constant determined by the transition probability. Fig. 4b shows the plots of  $(\alpha hv)^{1/2}$  versus the photon energy ( $hv$ ) for  $\text{Ca}_2\text{NiW}_{1-x}\text{Mo}_x\text{O}_6$  ( $x = 0, 0.01, 0.02, 0.03, 0.04, 0.05$ ). The band gap energy  $E_g$  was estimated from the intercept of the tangents to the plots. The pure  $\text{Ca}_2\text{NiWO}_6$  had three  $E_g$  values (2.32 eV, 2.52 eV and 2.81 eV), corresponding to the three absorption bands as shown in Fig. 4a. The  $E_g$  value of the Mo-doped samples monotonically decreased with an increase in Mo content. At the doping level of  $x = 0.05$ , the band gap  $E_g$  was estimated to be about 2.15 eV. The result indicated that the doping of Mo enhanced the absorption of  $\text{Ca}_2\text{NiWO}_6$  in the visible-light region.

To deeply understand the effect of Mo doping on the electronic structure of  $\text{Ca}_2\text{NiWO}_6$ , the band structure and the density of states (DOS) of the pure and doped samples were calculated and the results are shown in Fig. 5. For the pure  $\text{Ca}_2\text{NiWO}_6$ , shown in Fig. 5a, the partial density of states of the individual atoms clearly indicated that the Ni 3d level was split into two main segments corresponding to the Ni  $t_{2g}$  and Ni  $e_g$

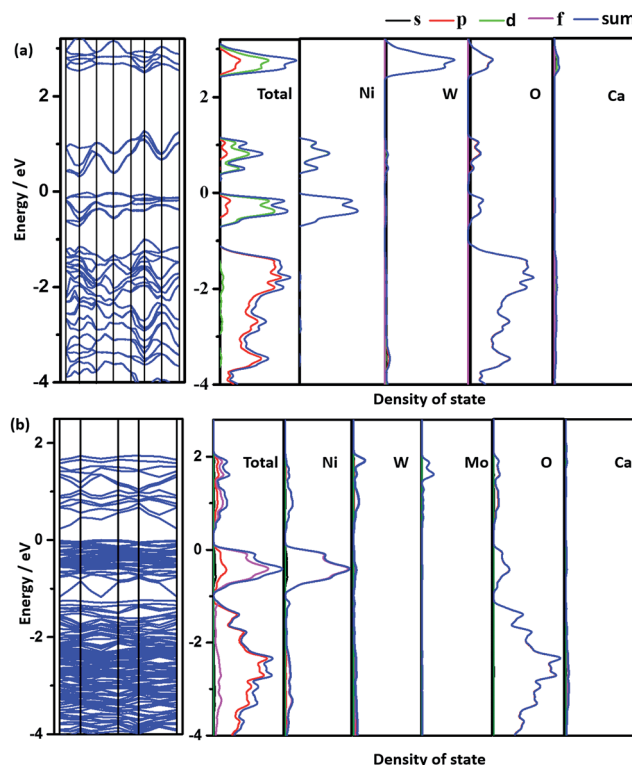


Fig. 5 Band structure and density of states of (a) pure  $\text{Ca}_2\text{NiWO}_6$  and (b) Mo-doped  $\text{Ca}_2\text{NiWO}_6$ .

levels, respectively. The W 5d level was located at a higher energy position than that of the Ni 3d level. From the total density of states curves, the CB contained two discrete subbands. The high energy one consisted of the W 5d orbital, and another was mainly derived from the Ni  $e_g$  level. The VB consisted of the hybridization of O 2p and Ni  $t_{2g}$  levels. The calculation results indicated that there were two intrinsic band gaps in the pure perovskite  $\text{Ca}_2\text{NiWO}_6$ , consistent with the DRS experiment (Fig. 4). Similar results were also reported by Zou *et al.*<sup>32</sup> The Mo doping had a significant impact on the band structure of  $\text{Ca}_2\text{NiWO}_6$ . As shown in Fig. 5b, the doped sample exhibited a higher DOS and more complex band structure with respect to pure  $\text{Ca}_2\text{NiWO}_6$ , confirming that the Mo doping formed impurity energy levels in the band gap of  $\text{Ca}_2\text{NiWO}_6$ . The CB of the  $\text{Ca}_2\text{NiW}_{1-x}\text{Mo}_x\text{O}_6$  mainly arose from the hybridization of Mo 3d, W 5d and Ni  $e_g$  orbitals. The electronic structure of CB changed from discrete to continuous with the Mo doping, consistent with the DRS result. It should be noted that the top of the VB remained unchanged after the  $\text{Mo}^{6+}$  doping, whilst the bottom of the CB was shifted to more positive potentials, compared to that of the pure  $\text{Ca}_2\text{NiWO}_6$ . The result indicated that the Mo dopant narrowed the band gap, thus extended the absorption in the visible light region, as revealed by UV-Vis DRS results.

### Photocatalytic activity

The photocatalytic  $\text{O}_2$  evolution from water under visible irradiation was applied to evaluate the photocatalytic performance





of the as-prepared photocatalysts and the results are shown in Fig. 6a. The pure  $\text{Ca}_2\text{NiWO}_6$  had a rather low  $\text{O}_2$  evolution rate of  $1.38 \mu\text{mol h}^{-1} \text{g}^{-1}$ . The Mo doping significantly enhanced the oxygen production. With an increase in the Mo doping, the oxygen evolution rate increased and reached the highest level at the Mo doping content of 3 at% ( $\text{Ca}_2\text{NiW}_{0.97}\text{Mo}_{0.03}\text{O}_6$ ). On this catalyst, the  $\text{O}_2$  evolution rate was  $2.65 \mu\text{mol h}^{-1} \text{g}^{-1}$ , approximately 2 times higher than that of pure  $\text{Ca}_2\text{NiWO}_6$ . Fig. 6b shows the cyclic tests of oxygen production of the optimized  $\text{Ca}_2\text{NiW}_{0.97}\text{Mo}_{0.03}\text{O}_6$  photocatalyst. No great change in the photocatalytic activity was observed after three cyclic tests, which suggested that the doped sample had good stability.

The XRD and XAFS results indicated that the  $\text{Mo}^{6+}$  ions entered the crystal lattice of  $\text{Ca}_2\text{NiWO}_6$ , substituting for the hexa-coordinated  $\text{W}^{6+}$  sites and promoting the formation of the oxygen vacancies. It is well known that the oxygen vacancies play an important role in the photocatalytic reaction. The surface oxygen vacancies can directly provide the formation sites of the active species for the photocatalytic reaction and thus increase the photocatalytic activity.<sup>38</sup> Furthermore, from the DRS and DOS results, the Mo doping introduced impurity energy levels into the band structure of  $\text{Ca}_2\text{NiWO}_6$ , leading to a lower band gap energy and higher absorbance in a wider visible light region, compared to that of pure  $\text{Ca}_2\text{NiWO}_6$ . These characteristics contributed to the generation of more photo-generated carriers and enhanced the photocatalytic activity. Based on the characterization results, the band structures of the as-prepared photocatalysts are proposed and shown in Fig. 7. The pure  $\text{Ca}_2\text{NiWO}_6$  had two discrete CBs, consistent with a previous report by Zou *et al.*<sup>32</sup> The high energy band consisted of the W 5d orbital and the low energy band was derived from the Ni eg level. The VB was composed of the hybridization of O 2p and Ni  $t_{2g}$  levels. Accordingly, there existed two intrinsic band gaps (Fig. 7a). For the Mo-doped  $\text{Ca}_2\text{NiWO}_6$ , shown in Fig. 7b, its CB was formed by the hybridization of the Mo 3d orbital with the W 5d and Ni 3d orbitals. With respect to the pure  $\text{Ca}_2\text{NiWO}_6$ , the CB of the Mo doped sample was continuous, due to the formation of impurity energy levels. The bottom of the CB of the doped sample was more positive, while the top level of the VB remained unchanged. The results indicated that the Mo doping broadened the absorption band in the visible light region, but had no influence on the oxidation

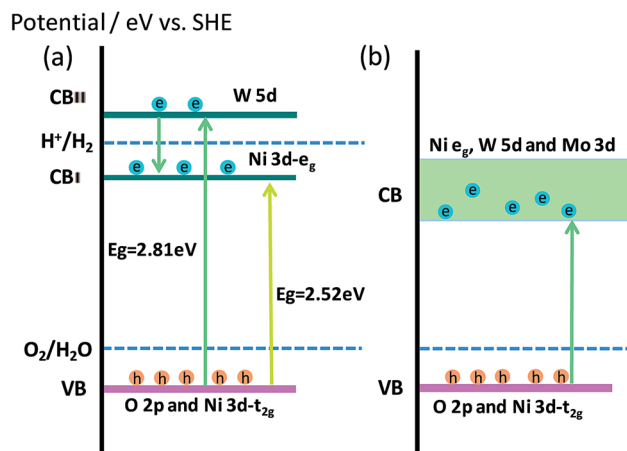


Fig. 7 Schematic of the band structure of (a) pure  $\text{Ca}_2\text{NiWO}_6$  and (b) Mo-doped  $\text{Ca}_2\text{NiWO}_6$ .

potential; therefore it was conducive to the oxygen evolution reaction. The photocatalytic activity of the Mo-doped  $\text{Ca}_2\text{NiWO}_6$  decreased when the Mo doping content exceeded 3 at%. The reason may be that the high dopant level increased the extent of defects in the oxide structure, which acted as electron-hole recombination centers, with a consequent decrease in the photocatalytic reaction rate.<sup>39</sup> Further investigation of the defects and electronic structure are in progress. This work provides some new insight into the dopant effects on the crystal, band structure and performance of photocatalysts.

## Conclusions

The  $\text{Ca}_2\text{NiW}_{1-x}\text{Mo}_x\text{O}_6$  ( $x = 0, 0.01, 0.02, 0.03, 0.04, 0.05$ ) photocatalysts with a double perovskite structure were successfully synthesized by a solid-state reaction method. The Mo-doped samples exhibited much higher photocatalytic activity for the oxygen evolution reaction under visible light irradiation than that of the pure  $\text{Ca}_2\text{NiWO}_6$ . The characterization results indicated that the  $\text{Mo}^{6+}$  ions can be substituted into the hexa-coordinated  $\text{W}^{6+}$  ions in the  $\text{Ca}_2\text{NiWO}_6$  lattice, leading to a certain degree of lattice distortion and the formation of oxygen vacancies. The Mo doping introduced impurity energy levels in the band structure of  $\text{Ca}_2\text{NiWO}_6$ , forming a continuous CB. The bottom of the CB was more positive, while the top level of the VB remained unchanged as compared to the pure  $\text{Ca}_2\text{NiWO}_6$ . As a result, the Mo-doped  $\text{Ca}_2\text{NiWO}_6$  had a lower energy band gap and higher absorbance in the wider visible light region, compared to that of pure  $\text{Ca}_2\text{NiWO}_6$ . These characteristics contributed to the generation of more photogenerated carriers and enhanced the photocatalytic activity of the oxygen evolution reaction.

## Acknowledgements

This work was supported by National Nature Science Foundation of China (U1632273, 11205159) and Chinese Academy of Sciences (CX3430000001).

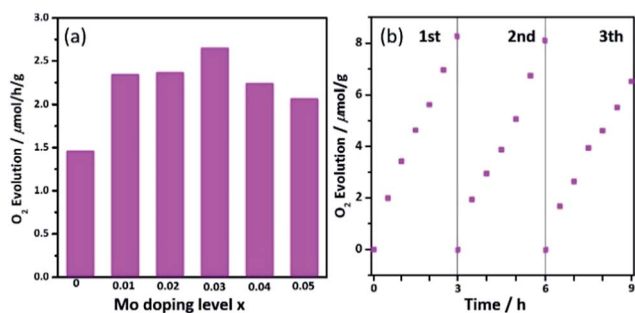


Fig. 6 (a) OER activity of  $\text{Ca}_2\text{NiW}_{1-x}\text{Mo}_x\text{O}_6$  ( $x = 0, 0.01, 0.02, 0.03, 0.04, \text{ and } 0.05$ ) under visible irradiation; (b) cyclic tests of oxygen production of the optimized  $\text{Ca}_2\text{NiW}_{0.97}\text{Mo}_{0.03}\text{O}_6$  photocatalyst.



## Notes and references

- Z. G. Zou, J. H. Ye, K. Sayama and H. Arakawa, *Nature*, 2001, **414**, 625–627.
- X. Zong, G. Wu, H. Yan, G. Ma, J. Shi, F. Wen, L. Wang and C. Li, *J. Phys. Chem. C*, 2010, **114**, 1963–1968.
- H. Husin, H. M. Chen, W. N. Su, C. J. Pan, W. T. Chuang, H. S. Sheu and B. J. Hwang, *Appl. Catal., B*, 2011, **102**, 343–351.
- K. Maeda, K. Teramura, D. Lu, N. Saito, Y. Inoue and K. Domen, *Angew. Chem., Int. Ed.*, 2006, **118**, 7970–7973.
- J. Ran, J. Zhang, J. Yu, M. Jaroniec and S. Z. Qiao, *Chem. Soc. Rev.*, 2014, **43**, 7787–7812.
- A. Kudo and Y. Miseki, *Chem. Soc. Rev.*, 2009, **38**, 253–278.
- S. U. M. Khan, M. Al-Shahry and W. B. Ingler, *Science*, 2002, **297**, 2243–2245.
- H. Kato, K. Asakura and A. Kudo, *J. Am. Chem. Soc.*, 2003, **125**, 3082–3089.
- F. E. Osterloh, *Chem. Mater.*, 2008, **20**, 35–54.
- W. N. Sua, D. W. Ayele, V. Ochie, C. J. Pan and B. J. Hwang, *Appl. Catal., B*, 2014, **150–151**, 363–369.
- X. Y. Yu, Y. Feng, B. Guan, X. W. Lou and U. Paik, *Energy Environ. Sci.*, 2016, **9**, 1246–1250.
- E. Fabbri, A. Habereder, K. Waltar, R. Kötz and T. J. Schmidt, *Catal. Sci. Technol.*, 2014, **4**, 3800–3821.
- J. Suntivich, K. J. May, H. A. Gasteiger, J. B. Goodenough and Y. Shao-Horn, *Science*, 2011, **334**, 1383–1385.
- Y. Li, Z. Liu, L. Liu and W. Gao, *J. Am. Chem. Soc.*, 2010, **132**, 13008–13015.
- S. Chen, S. Shen, G. Liu, Y. Qi, F. Zhang and C. Li, *Angew. Chem., Int. Ed.*, 2015, **54**, 3047–3051.
- H. Kato and A. Kudo, *J. Phys. Chem. B*, 2002, **106**, 5029–5034.
- D. Wang, R. Li, J. Zhu, J. Shi, J. Han, X. Zong and C. Li, *J. Phys. Chem. C*, 2012, **116**, 5082–5089.
- K. Maeda, X. Wang, Y. Nishihara, D. Lu, M. Antonietti and K. Domen, *J. Phys. Chem. C*, 2009, **113**, 4940–4947.
- P. Kush, K. Deori, A. Kumar and S. DeKa, *J. Mater. Chem. A*, 2015, **3**, 8098–8106.
- W. Eerenstein, N. D. Mathur and J. F. Scott, *Nature*, 2006, **442**, 759–765.
- A. Kudo, H. Kato and S. Nakagawa, *J. Phys. Chem. B*, 2000, **104**, 571–575.
- R. Hu, C. Li, X. Wang, Y. Sun, H. Jia, H. Su and Y. Zhang, *Catal. Commun.*, 2012, **29**, 35–39.
- T. Hatakeyama, S. Takeda, F. Ishikawa, A. Ohmura, A. Nakayama and Y. Yamada, *J. Ceram. Soc. Jpn.*, 2010, **118**, 91–95.
- Y. Okamoto, S. Ida, J. Hyodo, H. Hagiwara and T. Ishihara, *J. Am. Chem. Soc.*, 2011, **133**, 18034–18037.
- J. W. Liu, G. Chen, Z. H. Li and Z. G. Zhang, *J. Solid State Chem.*, 2006, **179**, 3704–3708.
- Y. Yang, Q. Chen, Z. Yin and J. Li, *J. Alloys Compd.*, 2009, **488**, 364–369.
- H. G. Kim, P. H. Borse, J. S. Jang, E. D. Jeong and J. S. Lee, *Mater. Lett.*, 2008, **62**, 1427–1430.
- P. H. Borse, K. T. Lim, J. H. Yoon, J. S. Bae, M. G. Ha, E. H. Chung, E. D. Jeong and H. G. Kim, *J. Korean Phys. Soc.*, 2014, **64**, 295–300.
- F. K. Meng, Z. L. Hong, J. Arndt, M. Li, M. J. Zhi, F. Yang and N. Q. Wu, *Nano Res.*, 2012, **5**, 213–221.
- X. Cheng, E. Fabbri, M. Nachtegaal, I. E. Castelli, M. Ei Kazzi, R. Haumont, N. Marzari and T. J. Schmidt, *Chem. Mater.*, 2015, **27**, 7662–7672.
- A. Grimaud, K. J. May, C. E. Carlton, Y. L. Lee, M. Risch, W. T. Hong, J. G. Zhou and Y. Shao-Horn, *Nat. Commun.*, 2013, **4**, 1–7.
- D. Li, J. Zheng and Z. Zou, *J. Phys. Chem. Solids*, 2006, **67**, 801–806.
- B. Ravel and M. Newville, *Phys. Scr., T*, 2005, **115**, 1007–1010.
- K. Yang, W. Q. Huang, L. Xu, K. W. Luo, Y. C. Yang and G. F. Huang, *Mater. Sci. Semicond. Process.*, 2016, **41**, 200–208.
- N. N. Wang, H. Y. Lu, Z. T. Lv, W. Wang, J. Q. He, L. Geng and S. Chen, *J. Low Temp. Phys.*, 2015, **181**, 242–252.
- W. Zhou, G. Du, P. Hu, G. Li, D. Wang, H. Liu and J. Wang, *J. Mater. Chem.*, 2011, **21**, 7937–7945.
- V. M. Huxter, T. Mirkovic, P. S. Nair and G. D. Scholes, *Adv. Mater.*, 2008, **20**, 2439–2443.
- M. Kong, Y. Li, X. Chen, T. Tian, P. Fang, F. Zheng and X. Zhao, *J. Am. Chem. Soc.*, 2011, **133**, 16414–16417.
- S. H. Shen, L. Zhao, Z. H. Zhou and L. J. Guo, *J. Phys. Chem. C*, 2008, **112**, 16148–16155.

