



Cite this: *RSC Adv.*, 2017, 7, 8567

Effect of tungsten surface density of $\text{WO}_3\text{-ZrO}_2$ on its catalytic performance in hydrogenolysis of cellulose to ethylene glycol†

Jiachun Chai,^{ab} Shanhui Zhu,^{*a} Youliang Cen,^{ab} Jing Guo,^{ab} Jianguo Wang^a and Weibin Fan^{*a}

One-pot hydrogenolysis of cellulose to ethylene glycol (EG) was carried out on WO_3 -based catalysts combined with Ru/C. To probe the active catalytic site for breaking the C–C bond of cellulose, a series of $\text{WO}_3\text{-ZrO}_2$ (WZr) catalysts were synthesized and systematically characterized with XRD, Raman, UV-Vis, H_2 -TPR, DRIFTS and XPS techniques and N_2 physisorption experiment. It was found that the WO_3 crystallites became more easily reduced to $\text{W}^{5+}\text{-OH}$ species with increasing crystallite size or tungsten surface density of the WZr catalyst owing to the decrease of their absorption edge energy (AEE) originating from weakening their interaction with ZrO_2 support. This, as a result, gave higher EG yield at higher tungsten surface density. The structure–activity relationship of the WZr catalyst reveals that the active catalytic site for cleaving the $\text{C}_2\text{-C}_3$ bond of the glucose molecule is the $\text{W}^{5+}\text{-OH}$ species.

Received 29th November 2016
Accepted 12th January 2017

DOI: 10.1039/c6ra27524a

www.rsc.org/advances

1. Introduction

Abundant sustainable lignocellulose is an alternative feedstock to fossil fuels for producing chemicals and oils with less emission of CO_2 .^{1–4} Generally, lignocellulose contains 35–50% of cellulose, 20–25% of hemicellulose, and 10–25% of lignin.^{5,6} Cellulose consists of glucose monomer units connected through β -1,4-glycosidic linkages, which leads to a fibrous crystalline structure with large amounts of intra- and intermolecular hydrogen bonds, and consequently, makes it difficult to be hydrolyzed.^{1,7,8} Therefore, selective transformation of cellulose into a specific chemical is a promising but challenging task.^{9,10}

To date, various catalytic systems have been developed to convert cellulose into profitable chemicals, including sugar alcohols, glucose, lactic acid, 5-hydroxymethylfurfural (5-HMF), levulinic acid (LA), ethylene glycol (EG), propylene glycol and alkanes.¹¹ Among them, EG is an important commodity chemical. It is widely used as a functional fluid such as antifreeze, coolant, and monomer for synthesis of polyester fiber and resin.^{12–14} Currently, EG is mainly produced through two-step transformation of petroleum-derived ethene, including selective oxidation of ethene to epoxide and subsequent hydrolysis of the generated epoxide.^{13,15}

Recently, a new route has been developed by direct hydrogenolysis of cellulose to EG over $\text{Ni-W}_2\text{C/AC}$ by Zhang and coworkers.¹⁶ This route provides a new potential approach for the production of EG. It will not only alleviate the dependence on the non-regenerated petroleum, but also reduce the net emission of CO_2 .^{14,17} Moreover, this process is highly atom-economic because most of the carbon atoms and hydroxyl groups from cellulose are well reserved in the products.¹⁸ Further studies reveal that the combination of W species with RANEY® Ni is effective for the selective conversion of cellulose to EG. Zhang and coworkers assumed that soluble H_xWO_3 species played a crucial role in selectively breaking the C–C bond of glucose.¹⁹ The detection of glycolaldehyde intermediate suggests that H_xWO_3 -catalyzed C–C cleavage of glucose should follow the retro-aldol pathway as it is subsequently hydrogenated into EG over Ru or Ni.^{20,21} This is, however, denied by Liu and coworkers, who found that 2-deoxy-glucose couldn't transform into EG on WO_3 and Ru/C under the same conditions.²² Therefore, they thought that the adjacent α -OH group in the sugar molecule underwent the C–C bond cleavage over WO_3 through the formation of complex. Their work demonstrated that W species are catalytically active for the synthesis of EG from cellulose, but the catalytic mechanism, especially the structure of active site has not been illustrated. This directly affects the design of advanced catalyst.

Among different types of WO_x -based catalysts employed in the cellulose conversion reaction, tungstated zirconia shows unique performance, because it has high stability under both reduction and hydrothermal conditions.²³ Besides, it has been confirmed that WO_x species on ZrO_2 can generate strong acid sites.²⁴ The lower surface free energy of WO_3 than that of ZrO_2

^aState Key Laboratory of Coal Conversion, Institute of Coal Chemistry, Chinese Academy of Sciences, Taiyuan, Shanxi 030001, PR China. E-mail: fanwb@sxicc.ac.cn; zhushanhui@sxicc.ac.cn

^bUniversity of Chinese Academy of Sciences, Beijing 100049, PR China

† Electronic supplementary information (ESI) available. See DOI: 10.1039/c6ra27524a



causes WO_3 to thermally spread on the ZrO_2 .²⁵ In general, the WO_x state on the ZrO_2 support depends on its surface density.²⁶ Below the monolayer surface coverage ($<4 \text{ W nm}^{-2}$), tungstate are monotungstate and polytungstate species. When the surface density is increased to $4\text{--}8 \text{ W nm}^{-2}$, polytungstate and crystalline WO_3 nanoparticles are the main phases. A further increase in the surface density to $>8 \text{ W nm}^{-2}$ leads to formation of bulky WO_3 crystals. It has been widely accepted that the structure and catalytic activity of WO_3 species on ZrO_2 is only determined by the tungsten surface density (W nm^{-2}).²⁷ Liu and coworkers found that the yield of EG increased with increasing tungsten surface density until the formation of primarily crystalline WO_3 . A further increase in the agglomeration degree of WO_3 did not change the EG yield. This indicates that WO_3 crystallites act as solid acid sites to catalytically cleave the C–C bonds in the intermediate sugar molecules.²²

However, we found that the EG yield still increased with further increasing WO_3 size by elevating calcination temperature or increasing tungsten loading supported on zirconia, showing that the reaction process has not been clearly understood yet. Hence, the process for hydrogenolysis of cellulose to EG over WO_3/ZrO_2 is investigated here for illustrating the structure of active catalytic site and the catalytic mechanism. It is shown that $\text{W}^{5+}\text{--OH}$ species is the active site for catalyzing the glucose to glycolaldehyde (GA).

2. Experimental

2.1. Catalyst preparation

The WZr catalysts were prepared according to the following procedures. First, $\text{Zr}(\text{OH})_4$ (Aladdin) was added in the aqueous solution of $(\text{NH}_4)_{10}\text{W}_{12}\text{O}_{41}$ (Sinopharm Chem. Reagent Co., Ltd), and refluxed at 110°C for 9 h. Then, the solid sample was dried at 80°C overnight in an oven. Finally, the sample was calcined at 600, 650, 700, 750, 800, 850 and 900°C for 3 h in air. The resultant sample was designated as $\text{ZW}_{x,t}$ with x and t representing the tungsten content (wt%) and the calcination temperature ($^\circ\text{C}$) respectively.

Tungsten oxide (WO_3), phosphotungstic acid ($\text{H}_3\text{PW}_{12}\text{O}_{40}$), silicotungstic acid ($\text{H}_4\text{SiW}_{12}\text{O}_{40}$) and cellulose (the crystalline can be seen in Fig. S1†) were purchased from Sinopharm Chem. Reagent Co., Ltd. Ru/C was obtained from Aladdin.

2.2. Catalyst characterization

N_2 physisorption isotherms were measured at -196°C on a Tristar II 3020 volumetric adsorption analyzer after the sample was pretreated at 150°C for 4 h under high vacuum conditions. The specific surface area was calculated by the Brunauer–Emmett–Teller (BET) method.

X-ray diffraction (XRD) patterns were recorded in the 2θ range of $20\text{--}70^\circ$ at a scanning rate of 4° min^{-1} on a Rigaku MiniFlex II desktop X-ray diffractometer equipped with $\text{CuK}\alpha$ radiation.

Raman spectra of raw powders were obtained at room temperature on a Horiba LabRAM HR800 spectrometer using the 514 nm argon ion laser with a long-distance objective ($50\times$).

The laser power density on the sample was kept low enough to assure that the material was not decomposed. The spectra of samples were obtained by directly focusing the laser on their upper parts.

Diffuse reflectance (DR) UV-Vis spectra were collected from 200 to 800 nm at a scanning rate of 600 nm min^{-1} on a Cary 5000 UV-Vis-NIR spectrophotometer with a spectral resolution of 2 nm. The Teflon reference was used for the baseline calibration.

The H_2 temperature-programmed reduction ($\text{H}_2\text{-TPR}$) was conducted on a Micromeritics AutoChem II 2920 chemisorption analyzer. First, 30 mg sample was loaded in a U-type reactor and heated to 300°C in Ar flow (30 mL min^{-1}). Then, the sample was cooled to room temperature after 2 h, and the Ar flow was switched to a 10% H_2/Ar flow (30 mL min^{-1}). Finally, the temperature was increased to 750°C at a rate of 5°C min^{-1} , and the consumed H_2 amount was monitored by a thermal conductivity detector (TCD).

In situ diffuse reflectance infrared spectra (DRIFS) of $\text{WZr}_{30,800}$ were measured on a Nicolet iS10 Fourier transform infrared spectrometer (Thermo Scientific) equipped with a MCT detector cooled with liquid N_2 , a diffuse reflectance accessory (Thermo Scientific Spectra-Tech Collector II) and an *in situ* cell (High Pressure Catalytic Chamber 0030-102). The spectra were collected at a resolution of 4 cm^{-1} by accumulating 32 scans at room temperature after the self-supported wafers were pretreated at 400°C for 2 h in Ar flow (50 mL min^{-1}). The sample reduction was conducted at 400°C for 2 h in 10% H_2/Ar flow (50 mL min^{-1}).

The X-ray photoelectron spectra (XPS) of $\text{WZr}_{30,800}$ before and after reduction were taken on a Kratos AXIS ULTRA DLD spectrometer equipped with a monochromated $\text{AlK}\alpha$ radiation source ($h\nu = 1486.6 \text{ eV}$) and a multichannel detector. All the spectra were recorded by using an aperture slot of $300 \times 700 \mu\text{m}$, and the survey spectra were recorded with the pass energy of 160 eV, while high-resolution spectra were collected with the pass energy of 40 eV. The binding energies were calibrated with adventitious C 1s peak (284.8 eV) as the reference. The experimental error was $\pm 0.1 \text{ eV}$.

2.3. Catalytic test

All the catalytic experiments were carried out in a batch reactor (100 mL stainless steel autoclave). The typical reaction conditions are as follows: 0.08 g $\text{WZr}_{x,t}$, 0.01 g Ru/C, 0.3 g cellulose, 40 mL water, initial H_2 pressure of 5.2 MPa, temperature of 215°C , reaction time of 1.5 h, and stirring rate of 1000 rpm. After reaction, the liquid sample was centrifuged to separate from the solid catalyst. The low boiling-point products were analyzed by a Shimadzu GC-2014C gas chromatograph equipped with a DB-WAX column and a flame ionization detector (FID) using *n*-butanol as internal standard, whereas the high boiling-point products were analyzed using the external standard method by a LC-10Avp HPLC equipped with an Aminex HPX-87H column and refractive index detector. The cellulose conversion was calculated by the total organic carbon (TOC) method in terms of the carbon content of the liquid products following the equation: $\text{conversion}_{\text{TOC}} (\%) = (\text{moles of total organic carbon in$



the reaction liquid)/(moles of carbon in cellulose charged into the reactor) \times 100%.²⁸ The yields of polyols were calculated by using the equation: yield (%) = (molar amount of the product \times carbon content in the product)/(molar amount of cellulose charged into the reactor \times 6) \times 100%.

3. Results and discussions

3.1. Characterization of samples

Fig. 1 shows that when the calcination temperature increased from 600 to 900 °C, the BET surface area of $WZr_{30,t}$ declined from 115 to 29 $m^2 g^{-1}$ due to the sintering of ZrO_2 , while the tungsten surface density rose from 7.2 to 27.9 $W nm^{-2}$. This makes the average distance among the dispersed WO_x particles shortened, resulting in the evolution of two-dimensional polytungstate clusters into three-dimensional WO_3 crystallites.²⁹ It was indicated by the catalyst color change from white to yellow at 650 °C,³⁰ and was confirmed by the XRD measurements. No obvious diffraction peaks (at 2θ range of 23–25°) characteristic of monoclinic WO_3 (ref. 31) was observed for the sample calcined at 600 °C (Fig. 2), but they were visible at 650 °C, and the intensity increased with the calcination temperature, showing the gradual increase of WO_3 particle size as a result of the severe agglomeration of surface WO_3 species. The supported surface WO_3 species can stabilize the tetragonal phase of ZrO_2 ,^{32,33} as substantiated by the finding that this structural phase was totally kept below 850 °C. Even when the calcination temperature reached 900 °C, only a very small amount of monoclinic ZrO_2 was formed.

Raman spectroscopy is a very sensitive technique for detecting the supported oxide species.³⁴ The round band at about 647 cm^{-1} is associated with tetragonal ZrO_2 (Fig. 3), while those around 960 and 996 cm^{-1} are ascribed to the symmetric stretching mode of terminal $W=O$ vibrations in hydrated polytungstate species and at the surface of WO_3 crystals.^{35,36} As for the two sharp bands at 716 and 807 cm^{-1} , they are attributed to $W-O$ bending and stretching modes in microcrystalline WO_3 .^{35,37} These two bands greatly intensify, while those at 960 and 996 cm^{-1} remain almost constant with the calcination temperature. This gives another piece of evidence for the more

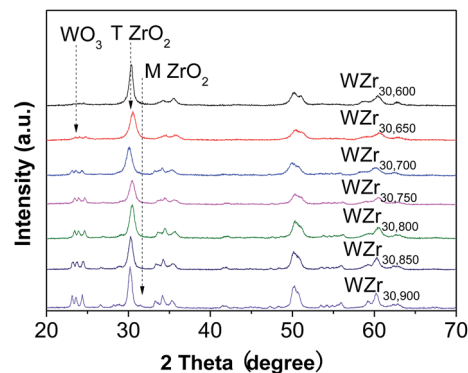


Fig. 2 XRD patterns of $WZr_{30,t}$ calcined at different temperature.

severe agglomeration of WO_3 species at higher calcination temperature.

The good charge-storage/delivery property of WO_3 originates from the redox reaction of $W^{6+} \leftrightarrow W^{5+}$.^{38,39} Fig. 4 shows the DR UV-Vis spectra of different W compounds. The lowest absorption edge energy (AEE) of six-coordinated W^{6+} in monoclinic WO_3 indicates that it contains an extended three-dimensional crystalline network of octahedra bonded to six neighboring octahedra. The isopolytungstates in phosphotungstic acid, silicotungstic acid and ammonium paratungstate connect octahedra bonded through corners and edges, and these samples share higher AEE. Moreover, the AEE value is relevant to not only the bonding geometry but also the crystallite size for small semiconductor nanocrystals.^{35,40} Fig. 5 compares the DR UV-Vis spectra of $WZr_{30,t}$ catalysts. The increase of the calcination temperature causes the shift of AEE to low value, which leads to a narrowing of HOMO–LUMO gap,⁴¹ and hence, would facilitate the reduction of WO_3 species. XRD and Raman spectroscopy results reveal that the particles increase in size with the increase of calcination temperature. In addition, for nano-sized WO_3 with an increased grain size, the bandgap generally decreases, which is attributed to the quantum-size effect.^{39,42} Thus, it can be inferred that the bigger the WO_3 crystallite size is, the more feasible the charge delocalization is,⁴³ and the more reducible the surface WO_3 species would be. Indeed, this is confirmed by the H_2 -TPR results of samples calcined at different temperature.

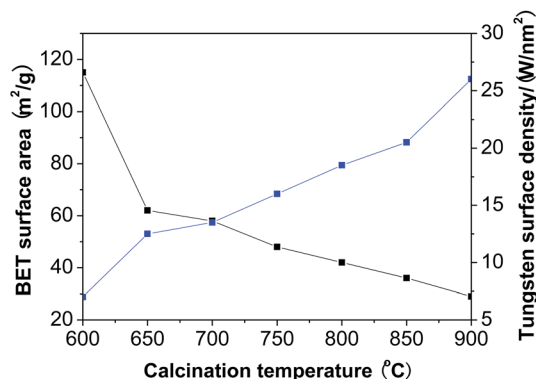


Fig. 1 Changes of the BET surface area and the tungsten surface density of $WZr_{30,t}$ with the calcination temperature.

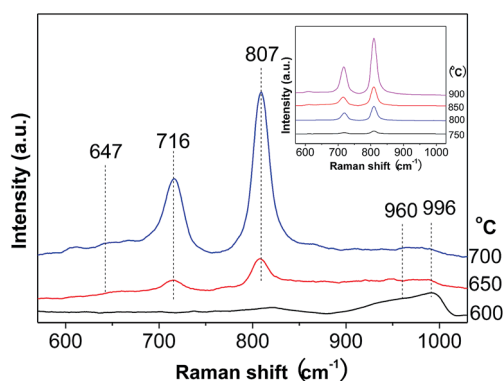


Fig. 3 Raman spectra of $WZr_{30,t}$ calcined at different temperature.



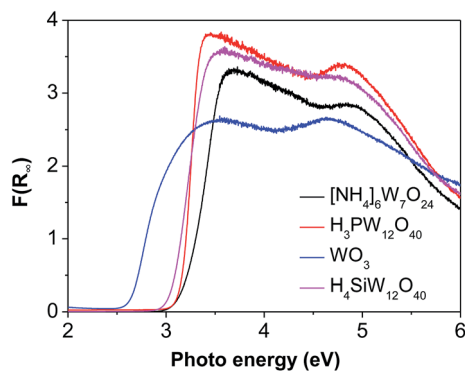


Fig. 4 DR UV-Vis spectra of different W-containing compounds.

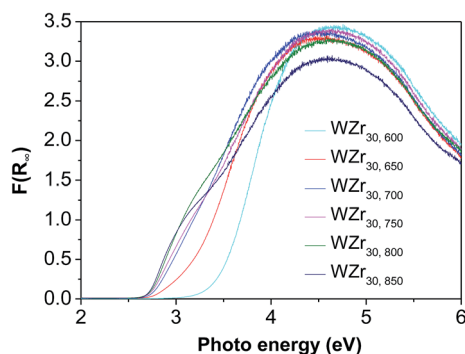


Fig. 5 DR UV-Vis spectra of various WZr_{30,t} catalysts.

Fig. 6 shows the H₂-TPR profiles of various WZr_{30,t} samples. The peak between 450 and 550 °C is due to reduction of WO₃ to WO_{2,9}, and that around 775 °C is ascribed to further reduction of WO_{2,9} to WO₂.^{31,44} Pure ZrO₂ does not show any detectable TPR peak at temperature <1000 °C. Clearly, no obvious reduction peak was present below 625 °C in the H₂-TPR profile of WZr_{30,600}, whereas all the other samples calcined in the temperature range of 650–850 °C showed a broad peak between 450 and 550 °C, and it shifted to low temperature with the calcination temperature. This confirms that the reduction degree of WO₃ increases with its particle size as a result of

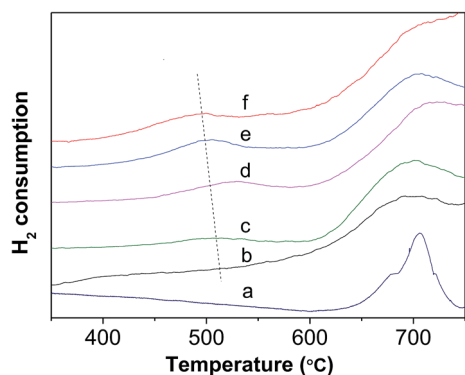


Fig. 6 H₂-TPR profile of (a) WZr_{30,600}, (b) WZr_{30,650}, (c) WZr_{30,700}, (d) WZr_{30,750}, (e) WZr_{30,800} and (f) WZr_{30,850}.

weakening of its interaction with ZrO₂ support. The same AEE of WZr_{30,850} and WZr_{30,900} (Fig. S2†) indicates that the reducibility of these two samples are similar, which is confirmed by their H₂-TPR results (Fig. S3†).

Fig. 7 shows the DRIFTS spectra of dehydrated and reduced WZr_{30,800}. The bending mode of water molecules at about 1617 cm⁻¹ could not be differentiated in the spectrum of dehydrated sample, evidencing the total removal of adsorbed water. In the dehydrated state, the W=O stretching vibration locates at 987 cm⁻¹ (not shown here). The two weak bands around 3738 and 3620 cm⁻¹ are characteristic of Zr–OH and W–OH groups respectively.⁴⁵ After reduction with H₂ at 400 °C, the broad band in the region from 3700 to 3500 cm⁻¹ significantly increased in the intensity, revealing generation of large numbers of OH groups. In addition, the band at 1617 cm⁻¹ became visible as a result of formation of H₂O during the reduction process. The DRIFTS results suggest that significant numbers of W⁶⁺=O groups are reduced to W⁵⁺–OH species, as also confirmed by the EPR spectroscopy result that the signal at *g*_⊥ = 1.84 assigned to the surface W⁵⁺ ions is generated after reduction of the tungstated zirconia with H₂.³⁶

Fig. 8 shows the XPS of fresh and spent WZr_{30,800} catalysts. The intense signals at 35.2 and 37.4 eV are attributed to the W_{4f} spin-orbit component of surface W⁶⁺ species and the less intense ones at 33.9 and 36.2 eV are due to surface W⁵⁺ species.⁴⁴ After reaction, the signals characteristic of W⁵⁺ species enhance in intensity, while those of W⁶⁺ species reduce. As a result, the ratio of W⁵⁺ to W⁶⁺ increased significantly. The increase of surface W⁵⁺ species arises from the reduction of WZr_{30,800} with pressured H₂ in the reaction process. It is in accordance with the result of the DRIFTS that W⁵⁺–OH species is formed.

3.2. Catalytic test

Table 1 summarizes the catalytic results for hydrogenolysis of cellulose obtained at 215 °C and 5.2 MPa over different WZr_{30,t} combined with Ru/C. Clearly, the EG yield increased to 58.8% with increasing calcination temperature to 850 °C, showing that the large WO₃ crystallites are beneficial to the transformation of cellulose to EG. However, when the calcination temperature was

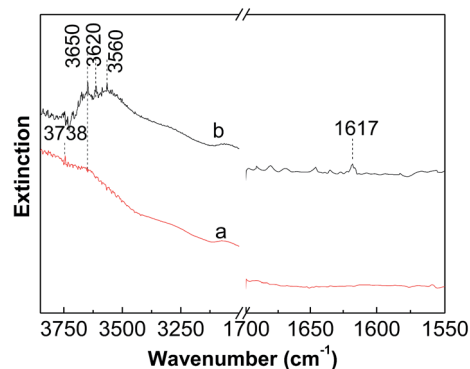


Fig. 7 *In situ* DRIFTS spectra measured at room temperature of (a) dehydrated and (b) reduced WZr_{30,800}.



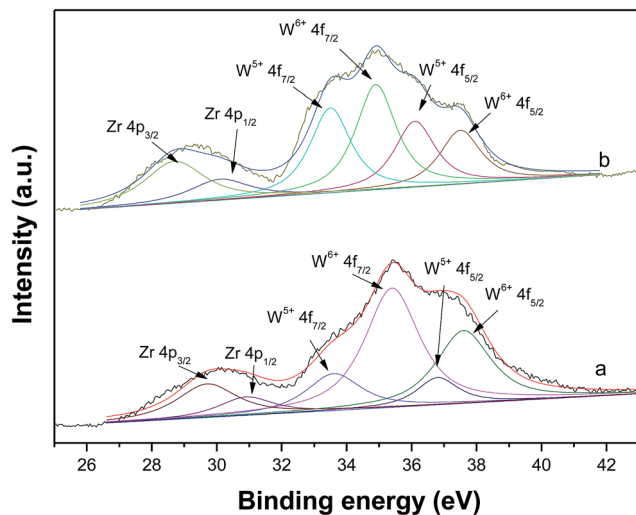


Fig. 8 Experimental and simulated XPS of (a) fresh and (b) spent $\text{WZr}_{30,800}$.

further ramped to 900 °C, the EG yield contrarily decreased. This is due to the transformation of some tetragonal ZrO_2 into monoclinic phase. It has been shown that monoclinic ZrO_2 has higher concentration and basicity of hydroxyl groups on this morphology. In addition, Zr^{4+} cations and O^{2-} anions of monoclinic ZrO_2 show stronger Lewis acidity and Lewis basicity than those of tetragonal ZrO_2 respectively.⁴⁶ The stronger basicity and Lewis acidity have been reported to promote the isomerization of glucose to fructose.^{47,48} Therefore, the EG yield declined.

Fig. 1–6 show that increase of tungsten surface density results in the growth of monoclinic WO_3 crystallite and facilitates their reduction to W^{5+} species owing to the lower AEE originating from weakening of their interaction with ZrO_2 support. The degree for the reduction of WO_3 to W^{5+} species was significantly promoted by Ru/C as it catalyzed the dissociation of H_2 (Fig. S3†). DRIFS and XPS results verify the formation of

Table 2 The structure–performance correlation of the EG yield with the surface $\text{W}^{5+}/\text{W}^{6+}$ ratio of the spent catalyst

| Spent catalyst | Surface $\text{W}^{5+}/\text{W}^{6+}$ ratio (%) | EG yield (%) |
|-----------------------|---|--------------|
| $\text{WZr}_{30,600}$ | 37.3 | 30.6 |
| $\text{WZr}_{30,700}$ | 42.2 | 43.3 |
| $\text{WZr}_{30,800}$ | 48.7 | 53.6 |
| $\text{WZr}_{30,850}$ | 52.6 | 58.8 |

OH groups and W^{5+} sites on the reduced WZr catalyst. Moreover, the Table 2 illustrates that the EG yield has a positive correlation with the surface $\text{W}^{5+}/\text{W}^{6+}$ ratio of the spent catalyst. Additionally, the formed W^{5+} -OH groups can act as Brønsted acid sites for hydrolysis of cellulose to glucose and further to GA by selectively cleaving C_2 - C_3 bond in glucose molecule. Thus, it can be deduced that W^{5+} -OH species is the active catalytic site.

Compared to $[\text{NH}_4]_6\text{W}_7\text{O}_{24}$, $\text{H}_3\text{PW}_{12}\text{O}_{40}$ and $\text{H}_4\text{SiW}_{12}\text{O}_{40}$, WO_3 has a lower AEE (Fig. 4), but gives a higher EG yield. This is agreement with that observed for the samples calcined at different temperature, suggesting that W species with low AEE exhibits high catalytic activity due to its high reduction degree.

The tungsten surface density can also be increased by increasing tungsten loading on ZrO_2 support (Table S1 and Fig. S4†).^{35,49} Fig. 9 compares the catalytic results obtained over the $\text{WZr}_{x,800}$ samples. The EG yield monotonously increases with the tungsten loading because of the increase in the crystallite size of WO_3 .

3.3. Catalytic mechanism of $\text{WZr}_{x,t}$ for hydrogenolysis of cellulose to EG

It is considered that the hydrogenolysis of cellulose to EG occurs by the following steps: (1) cellulose is hydrolyzed to glucose under the catalysis of reversibly generated H^+ in hot water;^{50,51} (2) glucose is transformed into GA *via* complexation to W species; (3) GA is rapidly hydrogenated to EG on Ru/C. However, to date, no direct evidence for the second step was acquired, for

Table 1 Catalytic results for hydrogenolysis of cellulose on different W-based catalysts^a

| Entry | Catalyst ^b | Conv. (%) | Product yield (%) | | | | | | |
|-------|--|-----------|-------------------|---------------------|---------------------|---------------------|------------------|------------------|------------------|
| | | | EG ^c | 1,2-PG ^c | 1,2-BD ^c | 1,2-HD ^c | Gly ^c | Ery ^c | Hex ^c |
| 1 | $\text{WZr}_{30,600}$ | 85 | 30.6 | 10.5 | 8.5 | 4.6 | 3.6 | 9.3 | 2.1 |
| 2 | $\text{W}/\text{Zr}_{30,650}$ | 88 | 40.6 | 9.6 | 7.8 | 3.9 | 3.2 | 9 | 2.4 |
| 3 | $\text{W}/\text{Zr}_{30,700}$ | 87 | 43.3 | 6.2 | 6 | 3.7 | 3 | 8.2 | 2.3 |
| 4 | $\text{W}/\text{Zr}_{30,750}$ | 90 | 47.2 | 5.1 | 5.2 | 3.4 | 2.7 | 7.3 | 1.9 |
| 5 | $\text{W}/\text{Zr}_{30,800}$ | 92 | 53.6 | 4.8 | 4.3 | 2.9 | 2.1 | 5.6 | 1.8 |
| 6 | $\text{W}/\text{Zr}_{30,850}$ | 90 | 58.8 | 4.5 | 4.6 | 2.6 | 1.8 | 4.5 | 1.8 |
| 7 | $\text{W}/\text{Zr}_{30,900}$ | 88 | 54.0 | 3.6 | 3.8 | 1.9 | 2 | 4.6 | 1.6 |
| 8 | WO_3 | 86 | 47.5 | 3.2 | 3.5 | 2.5 | 1.6 | 5.6 | 1.9 |
| 9 | $[\text{NH}_4]_6\text{W}_7\text{O}_{24}$ | 82 | 25.3 | 2.4 | 3.1 | 2.7 | 1.2 | 6.8 | 2.4 |
| 10 | $\text{H}_3\text{PW}_{12}\text{O}_{40}$ | 84 | 32.6 | 12.5 | 8.4 | 2.4 | 3.5 | 7.2 | 3 |
| 11 | $\text{H}_4\text{SiW}_{12}\text{O}_{40}$ | 80 | 31.8 | 14.2 | 8.9 | 3.2 | 3.2 | 7.6 | 2.8 |

^a Reaction conditions: 0.3 g cellulose, 0.08 g $\text{WZr}_{30,t}$, 0.01 g Ru/C, 40 mL H_2O , 215 °C, 5.2 MPa, 1000 rpm, 1.5 h. ^b 0.024 g Tungsten species for the other W-containing compounds. ^c EG, 1,2-PG, 1,2-BD, 1,2-HD, Gly, Ery and Hex refer to ethylene glycol, 1,2-propylene glycol, 1,2-butanediol, 1,2-hexanediol, glycerol, erythritol and hexanehexol, respectively.



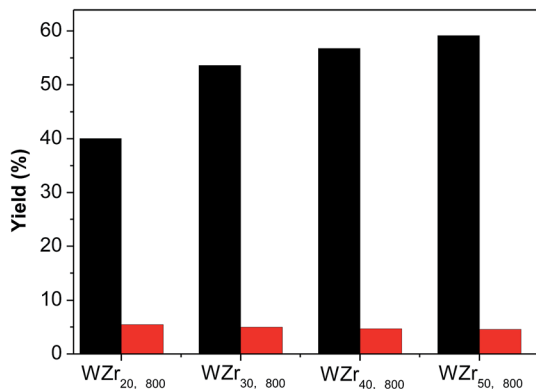


Fig. 9 The EG (black) and PG (red) yields obtained over the samples loading different amounts of WO_3 and being calcined at 800°C (reaction conditions: 0.3 g cellulose, 0.01 g Ru/C, 0.08 g $\text{WZr}_{x,800}$, 40 mL H_2O , 215°C , 5.2 MPa, 1000 rpm, 1.5 h).

they cannot be monitored by *in situ* characterization methods which are actually not available in the case of such kinds of gas/liquid/solid–solid reaction systems.^{51,52} Therefore, the catalytic mechanism for hydrogenolysis of cellulose to EG has not been clearly understood yet.

The above results show that $\text{W}^{5+}\text{-OH}$ species is the active catalytic site for selectively cleaving the $\text{C}_2\text{-C}_3$ bond of glucose

molecule. Thus, it can be deduced that the cleavage occurs through complexation of α - and β -OH groups to $\text{W}^{5+}\text{-OH}$ species. The detailed process is possibly as follows:

After hydrolysis of cellulose to glucose, the glucose molecule attacks the $\text{W}^{5+}\text{-OH}$ species (Fig. 10). Due to the electron-withdrawing effect of the carbonyl group, the H atom in the α -OH group is prone to be positively charged and attacks the exposed OH group of the $\text{W}^{5+}\text{-OH}$ species. Meanwhile, the O atom in the β -OH group coordinates to W atom by means of lone-pair electrons and forms a six-membered heterocyclic ring, which rapidly eliminates one H_2O molecule and one H^+ because of its instability. The circular flow of the electrons of the formed five-membered heterocycle breaks the C–C bond to form GA and erythrose through an oxidative-reductive process, which is the same as the catalytic mechanism for oxidation of diol by periodic acid.^{53,54} The erythrose molecule can be also decomposed into two GA molecules in a similar way.

GA is an unstable intermediate at high temperature. It would be easily polymerized or degraded if it is not timely hydrogenated to EG.⁵⁵ Indeed, it was found by us with GC-MS (Fig. S5†) and NMR spectrum (Fig. S6†) that 2,2'-oxydiacetaldehyde was a major byproduct at the reaction time of 0.5 h. This unsaturated compound is easily to be formed by polymerizing two GA molecules.⁵⁶ However, when the reaction was carried out for 1 h, 2,2'-oxydiacetaldehyde disappeared. This may be because it

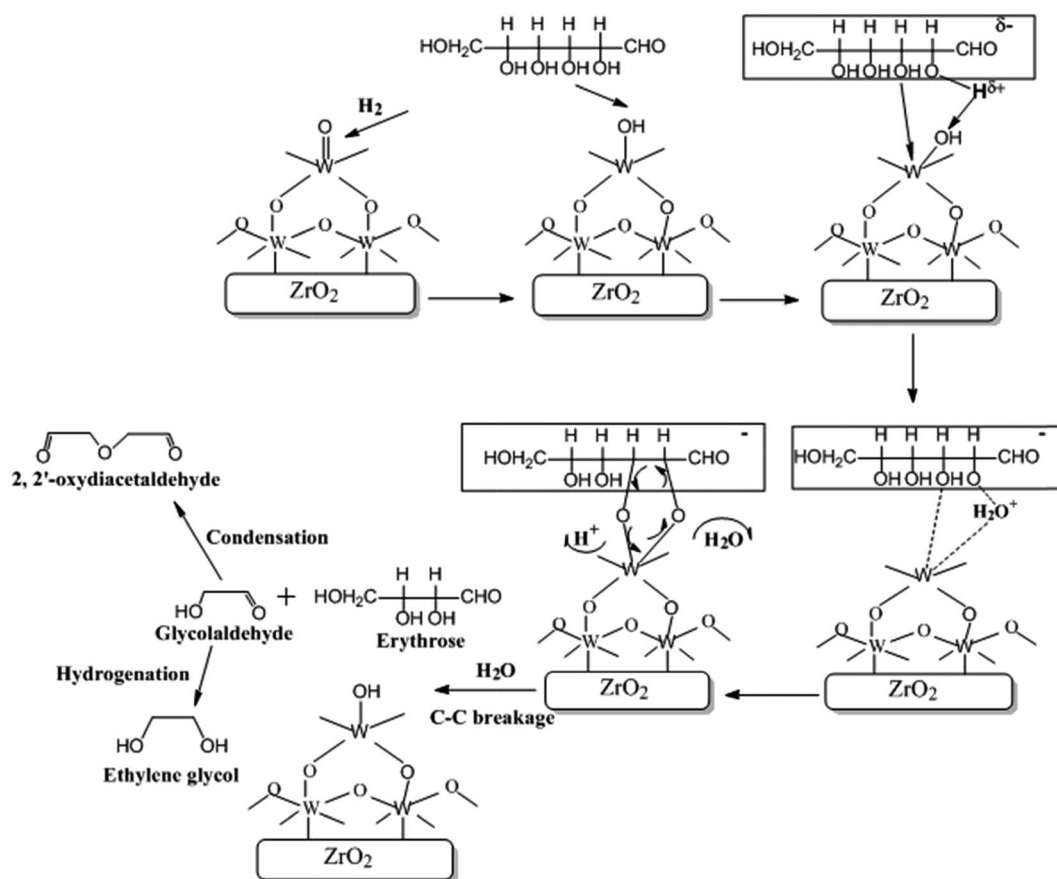


Fig. 10 Proposed reaction mechanism for selectively breaking the glucose C–C bond.



reversibly hydrolyzed into GA and was quickly hydrogenated into EG. Addition of both H₂ and Ru/C in the reaction mixture is necessary for obtaining EG. In the absence of H₂ and/or Ru/C, 2,2'-oxydiacetaldehyde was only generated without the detection of EG.

4. Conclusions

A series of ZrO₂-supported WO₃ catalysts have been hydrothermally prepared by changing calcination temperature and tungsten loading for hydrogenolysis of cellulose to EG. The EG yield obtained over these samples increased with the tungsten surface density as a result of severe agglomeration of WO₃ particles, which facilitates the reduction of WO₃ to W⁵⁺-OH species due to the weakening of its interaction with support. The cleavage of C₂-C₃ bond in glucose occurs on the W⁵⁺-OH species to form GA through formation of a complex. This is followed by hydrogenation to EG over Ru/C.

Acknowledgements

This work is financially supported by the National Natural Science Foundation of China (21403269), Shanxi Province of China (2016021033), Science Foundation for Youth Scholars of State Key Laboratory of Coal Conversion (2016BWZ002), and Youth Innovation Promotion Association CAS (2015140).

References

- 1 M. Benoit, A. Rodrigues, K. De Oliveira Vigier, E. Fourné, J. Barrault, J. M. Tatibouët and F. Jérôme, *Green Chem.*, 2012, **14**, 2212–2215.
- 2 W. Deng, Q. Zhang and Y. Wang, *J. Energy Chem.*, 2015, **24**, 595–607.
- 3 J. Xi, D. Ding, Y. Shao, X. Liu, G. Lu and Y. Wang, *ACS Sustainable Chem. Eng.*, 2014, **2**, 2355–2362.
- 4 Y. Yang, W. Zhang, F. Yang, D. E. Brown, Y. Ren, S. Lee, D. Zeng, Q. Gao and X. Zhang, *Green Chem.*, 2016, **18**, 3949–3955.
- 5 J. Song, H. Fan, J. Ma and B. Han, *Green Chem.*, 2013, **15**, 2619–2635.
- 6 C. Zhou, X. Xia, C. Lin, D. Tong and J. Beltramini, *Chem. Soc. Rev.*, 2011, **40**, 5588–5617.
- 7 N. Meine, R. Rinaldi and F. Schuth, *ChemSusChem*, 2012, **5**, 1449–1454.
- 8 S. Liu, M. Tamura, Y. Nakagawa and K. Tomishige, *ACS Sustainable Chem. Eng.*, 2014, **2**, 1819–1827.
- 9 R. Rinaldi and F. Schuth, *ChemSusChem*, 2009, **2**, 1096–1107.
- 10 S. Van de Vyver, J. Geboers, P. A. Jacobs and B. F. Sels, *ChemCatChem*, 2011, **3**, 82–94.
- 11 F. Yu, J. Thomas, M. Smet, W. Dehaen and B. F. Sels, *Green Chem.*, 2016, **18**, 1694–1705.
- 12 J. Sun and H. Liu, *Green Chem.*, 2011, **13**, 135–142.
- 13 R. Ooms, M. Dusselier, J. A. Geboers, B. Op de Beeck, R. Verhaeven, E. Gobechiya, J. A. Martens, A. Redl and B. F. Sels, *Green Chem.*, 2014, **16**, 695–707.
- 14 R. Sun, T. Wang, W. Deng, J. Pang, A. Wang, X. Wang and T. Zhang, *ACS Catal.*, 2015, **5**, 874–883.
- 15 S. Wang, J. Chen and L. Chen, *Catal. Lett.*, 2014, **44**, 1728–1734.
- 16 N. Ji, T. Zhang, M. Zheng, A. Wang, H. Wang, X. Wang and J. Chen, *Angew. Chem., Int. Ed.*, 2008, **47**, 8510–8513.
- 17 J. Pang, M. Zheng, A. Wang and T. Zhang, *Ind. Eng. Chem. Res.*, 2011, **50**, 6601–6608.
- 18 J. Pang, M. Zheng, R. Sun, L. Song, A. Wang, X. Wang and T. Zhang, *Bioresour. Technol.*, 2015, **175**, 424–429.
- 19 Z. Tai, J. Zhang, A. Wang, J. Pang, M. Zheng and T. Zhang, *ChemSusChem*, 2013, **6**, 652–658.
- 20 A. Wang and T. Zhang, *Acc. Chem. Res.*, 2013, **46**, 1377–1386.
- 21 R. Sun, M. Zheng, J. Pang, X. Liu, J. Wang, X. Pan, A. Wang, X. Wang and T. Zhang, *ACS Catal.*, 2016, **6**, 191–201.
- 22 Y. Liu, C. Luo and H. Liu, *Angew. Chem., Int. Ed.*, 2012, **51**, 3249–3253.
- 23 K. M. Parida, P. K. Pattnayak and P. Mohapatra, *J. Mol. Catal. A: Chem.*, 2006, **260**, 35–42.
- 24 A. Martinez, G. Prieto, M. Arribas, P. Concepcion and J. Sanchezroyo, *J. Catal.*, 2007, **248**, 288–302.
- 25 J. S. da Cruz, M. A. Fraga, S. Braun and L. G. Appel, *Appl. Surf. Sci.*, 2007, **253**, 3160–3167.
- 26 I. E. Wachs, T. Kim and E. I. Ross, *Catal. Today*, 2006, **116**, 162–168.
- 27 W. Zhou, E. I. Ross-Medgaarden, W. V. Knowles, M. S. Wong, I. E. Wachs and C. J. Kiely, *Nat. Chem.*, 2009, **1**, 722–728.
- 28 X. Wang, L. Meng, F. Wu, Y. Jiang, L. Wang and X. Mu, *Green Chem.*, 2012, **14**, 758–765.
- 29 S. L. Soled, C. D. Baertsch and E. Iglesia, *J. Phys. Chem. B*, 2001, **105**, 1320–1330.
- 30 J. Song, Z. Huang, L. Pan, J. Zou, X. Zhang and L. Wang, *ACS Catal.*, 2015, **5**, 6594–6599.
- 31 S. R. Vaudagna, R. A. Comelli and N. S. Fígoli, *Appl. Catal., A*, 1997, **164**, 265–280.
- 32 M. A. Cortes-Jacome, J. A. Toledo and C. Angeles-Chavez, *J. Phys. Chem. B*, 2005, **109**, 22730–22739.
- 33 C. Zhang, T. Liu, H. Wang, F. Wang and X. Pan, *Chem. Eng. J.*, 2011, **174**, 236–241.
- 34 S. S. Chan, I. E. Wachs, L. L. Murrell and N. C. Dispenziere, *J. Catal.*, 1985, **92**, 1–10.
- 35 D. G. Barton, M. Shtein, R. D. Wilson, S. L. Soled and E. Iglesia, *J. Phys. Chem. B*, 1999, **103**, 630–640.
- 36 S. Kuba, M. Che, R. K. Grasselli and H. Knozinger, *Phys. Chem. Chem. Phys.*, 2001, **3**, 146–154.
- 37 S. R. Vaudagna, S. A. Canavese, R. A. Comelli and N. S. Fõ Ágoli, *Appl. Catal., A*, 1998, **168**, 93–111.
- 38 H. Zheng, J. Ou, M. S. Strano, R. B. Kaner, A. Mitchell and K. Kalantar-zadeh, *Adv. Funct. Mater.*, 2011, **21**, 2175–2196.
- 39 Z. Huang, J. Song, L. Pan, X. Zhang, L. Wang and J. Zou, *Adv. Mater.*, 2015, **27**, 5309–5327.
- 40 A. P. Alivisatos, *Science*, 1996, **271**, 933–937.
- 41 R. S. Weber, *J. Catal.*, 1995, **151**, 470–474.
- 42 M. R. Waller, T. K. Townsend, J. Zhao, E. M. Sabio, R. L. Chamousis, N. D. Browning and F. E. Osterloh, *Chem. Mater.*, 2012, **24**, 698–704.



- 43 D. G. Barton, S. L. Soled and E. Iglesia, *Top. Catal.*, 1998, **6**, 87–99.
- 44 F. Di Gregorio and V. Keller, *J. Catal.*, 2004, **225**, 45–55.
- 45 S. Kuba, M. Che, R. K. Grasselli and H. Knozinger, *J. Phys. Chem. B*, 2003, **107**, 3459–3463.
- 46 K. Pokrovski, K. T. Jung and A. T. Bell, *Langmuir*, 2001, **17**, 4297–4303.
- 47 J. Guo, S. Zhu, Y. Cen, Z. Qin, J. Wang and W. Fan, *Appl. Catal., B*, 2017, **200**, 611–619.
- 48 C. Liu, S. Sun, K. Liu, S. Hao, J. Xu, Y. Zhu and Y. Li, *ACS Catal.*, 2015, **5**, 4612–4623.
- 49 E. Rossmedgaarden, W. Knowles, T. Kim, M. Wong, W. Zhou, C. Kiely and I. Wachs, *J. Catal.*, 2008, **256**, 108–125.
- 50 J. Xi, Y. Zhang, Q. Xia, X. Liu, J. Ren, G. g Lu and Y. Wang, *Appl. Catal., A*, 2013, **459**, 52–58.
- 51 K. Fabičovicová, M. Lucas and P. Claus, *Green Chem.*, 2015, **17**, 3075.
- 52 K. Fabičovicová, M. Lucas and P. Claus, *Green Chem.*, 2014, **16**, 3580.
- 53 A. Liu, *Ferriin oxidation of benzylic 1,2 -diols: A mechanistic approach*, West Virginia University, 1999.
- 54 P. Spanring, V. Yazerski, P. C. Bruijninx, B. M. Weckhuysen and R. J. Klein Gebbink, *Chem.–Eur. J.*, 2013, **19**, 15012–15018.
- 55 G. Zhao, M. Zheng, J. Zhang, A. Wang and T. Zhang, *Ind. Eng. Chem. Res.*, 2013, **52**, 9566–9572.
- 56 J. Zhang, B. Hou, A. Wang, Z. Li, H. Wang and T. Zhang, *AIChE J.*, 2014, **60**, 3804–3813.

