



CrossMark
 click for updates

Cite this: *RSC Adv.*, 2017, 7, 9373

Color change of alternating copolymers with phenyl vinyl ethylene carbonate and *N*-phenylmaleimide in a solution and in the solid-state, depending on their structure†

Yoshiaki Yoshida and Takeshi Endo*

Radical copolymerization, with various monomer feeds of phenyl vinyl ethylene carbonate (PVEC) and *N*-phenylmaleimide (PMI), successfully proceeded through selective vinyl and alternating polymerization to obtain copolymers having the maleimide unit in the main-chain and the five-membered cyclic carbonate group in the side-chain. The structure of these copolymers was analyzed in detail using NMR, IR, and UV-Vis methods. The UV-Vis spectra supported the tautomerization of the maleimide unit based on the solvent effect and the alternating and/or homo sequence constructed depending on the monomer feeds. Furthermore, these copolymers exhibited sensitive and reversible color changes based on acid–base switching not only in solution but also in the solid-state. In particular, the color change in the solid-state occurred immediately after exposure to the amine vapor.

Received 20th December 2016

Accepted 19th January 2017

DOI: 10.1039/c6ra28446a

rsc.li/rsc-advances

Introduction

Several types of sequence-controlled polymers have been prepared using various methods including a comonomer-selective reaction, iterative reaction and template reaction.^{1–8} In the comonomer-selective reaction, alternating copolymerization, the combination of the electron acceptor and electron donor monomers are commonly known to successfully achieve sequence-controlled polymerization.^{3–8} In particular, the maleimide derivatives are reported to be the electron acceptor monomers, which produce the AB or ABB alternating copolymer depending on the electron donor monomers such as styrene and non-conjugated olefin.^{3,4} Recently, we demonstrated that the radical polymerization of the vinyl ethylene carbonate (VEC) derivatives and various *N*-substituted maleimides (NMI) produced the sequence-controlled polymers due to the electron rich allylic moiety of VEC monomers and the electron poor maleimide moiety having a bulky and electron-withdrawing group as the *N*-substituents.⁸ Such copolymers with maleimide derivatives exhibited various properties, which include thermal stability, thermosetting, photoresponse, pH-response, nonlinear optics, molecular linkers and markers for a modification and chiral activity.^{4,9–14} The copolymers of VEC and NMI also exhibited a reversible color change based on an acid–base switching in solution.^{8,11} The color change was considered to be

a result of an enolate anion tautomerization of the maleimide moiety in basic solvent and/or in the presence of a strong basic reagent.^{8,11,15} Although the color change and luminescence properties of poly(NMI)s with an acid–base response in solution have been shown in several reports, these properties have not been demonstrated in the solid-state. Moreover, it has been considered that the color change of these polymers in the solid-state occurs with sufficiently strong basic reagents as well as that in solution. The reversible color change in the solid-state is well known to be due to various chromisms, which are thermochromism, photochromism, electrochromism, piezochromism and vapochromism.^{16–22} Moreover, PVEC and PMI copolymers have the five-membered cyclic carbonate group on the side-chain that proceeds through the selective vinyl radical polymerization of the PVEC monomer. This occurs because the ring-strain energy of the five-membered cyclic carbonate is low, and the activated state of the ring-opening process has a fairly high thermodynamic energy.^{8,23} Such polymers are applied to thermosetting coatings and polymer electrolytes of lithium ion batteries.²⁴ Furthermore, the polymers bearing the cyclic carbonate group on the side chain are also readily cross-linked with a diamine due to the high reactivity and chemoselectivity of the cyclic carbonate group with an amine.²⁵ In this study, the copolymers of phenyl vinyl ethylene carbonate (PVEC) and *N*-phenylmaleimide (PMI) were prepared with various monomer feeds using a radical initiator, and the sequential structure of these copolymers was analyzed in detail using NMR, IR, and UV-Vis methods. Furthermore, the color change of PVEC and PMI copolymers in the solid-state was studied using acid and base reagents, and the relationship between the composition ratio

Molecular Engineering Institute, Kindai University, 11-6 Kayanomori, Itzuka, Fukuoka 820-8555, Japan. E-mail: tendo@moleng.fuk.kindai.ac.jp

† Electronic supplementary information (ESI) available. See DOI: 10.1039/c6ra28446a



and color depth of the copolymers was summarized. These results indicated that the PVEC and PMI copolymers exhibited reversible acid–base responsivity and vapochromism in the solid-state.

Results and discussion

Radical copolymerization of PVEC and PMI with various monomer feeds

The radical polymerization of PVEC and PMI was carried out with DTBP as an initiator in bulk at 120 °C for 24 h, respectively (Table 1, Poly-100 and Poly-0). The yield and molecular weight of PVEC homopolymer (Poly-100) was fairly low due to a sluggish monomer toward free radical polymerization that originated from essentially a substituted allylic monomer, although that of the PMI homopolymer (Poly-0) was the highest.^{8,23,24b} On the other hand, the radical copolymerization of PVEC and PMI with various monomer feeds was also carried out under the same conditions. The yield and molecular weight increased linearly with increasing PMI feed, and the composition ratio of each monomer unit in the copolymers exhibited almost the same ratio as that of the monomer feed. In particular, the alternating copolymerization of Poly-50 (monomer feed; PVEC : PMI = 50 : 50) was suggested to be a result of the equivalent relationship between the monomer feed and composition ratio in the copolymers. On the other hand, the molecular weight of Poly-10 (monomer feed; PVEC : PMI = 10 : 90) was nonlinear out of all copolymers prepared with various monomer feeds due to the chain transfer reaction during polymerization, because the dispersity (M_w/M_n) of Poly-10 increased compared with that of the other copolymers, as well as that of the PMI homopolymer (Poly-0), as shown in Fig. S1.† Recently, we demonstrated that the copolymerization of PVEC and NMI was achieved in fairly high yield, and the molecular weight compared well with the homopolymerization of PVEC because these monomers exhibited a high reactivity that originated from the donor–accepter interaction due to the strong electron-donating character of the PVEC monomer.^{8,23} Therefore, the polymerization properties of PVEC monomer were improved with increases in the PMI feed.

The IR spectra of the produced homopolymers and copolymers are shown in Fig. 1. The IR spectra proved that the

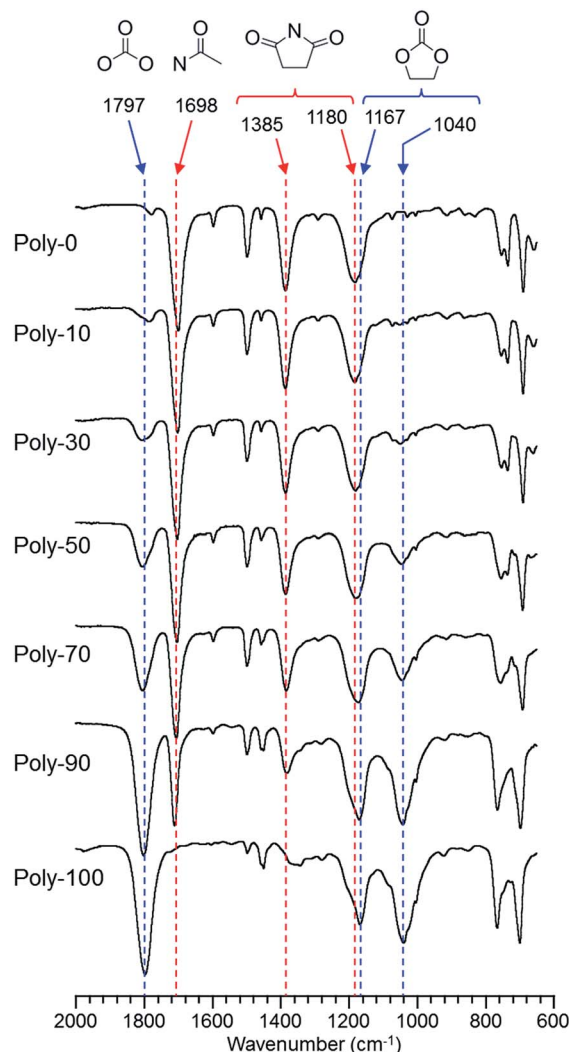


Fig. 1 IR spectra of PVEC and PMI copolymers prepared with various monomer feeds.

polymers having the five-membered cyclic carbonate group in the side-chain were prepared by proceeding through the selective vinyl polymerization because the characteristic peaks assigned to the five-membered ring and carbonyl moieties in

Table 1 Radical copolymerization of PVEC and PMI with various monomer feeds

Polymer	Monomer feed (mol%)		Composition ^a			
	PVEC	PMI	PVEC : PMI (%)	Yield ^b (%)	M_n^c ($\times 10^{-4}$)	M_w/M_n^c
Poly-0	0	100	—	92	1.2	6.61
Poly-10	10	90	14 : 86	82	1.0	5.12
Poly-30	30	70	31 : 69	75	2.1	2.47
Poly-50	50	50	50 : 50	73	1.2	2.16
Poly-70	70	30	72 : 28	68	0.7	2.30
Poly-90	90	10	88 : 12	48	0.4	1.91
Poly-100	100	0	—	39	0.4	1.86

^a Determined by IR using ATR. ^b Insoluble fraction in MeOH. ^c Determined using GPC analysis (PSt, DMF).



Table 2 Solubility of PVEC and/or PMI polymers prepared with various monomer feeds in common organic solvents^{a,b}


	Poly-0	Copolymers ^c	Poly-100
Toluene	X	X	X
EtOAc	X	X	X
CH ₃ CN	X	X	X
CHCl ₃	O	O	O
Acetone	X	O	O
PCA	X	O	O
i-PrOH	X	X	X
CPME ^d	X	X	X
THF	O	O	O
DO	O	O	X
DMSO	O	O	O
DMF	O	O	O
DMAc	O	O	O
NMP	O	O	O

^a Concentration of 2.0 mg/1.0 mL. ^b O: soluble, X: insoluble or partly soluble. ^c Copolymers: Poly-10, Poly-30, Poly-50, Poly-70, Poly-90. ^d CPME: cyclopentyl methyl ether.

the five-membered cyclic carbonate structure were observed around 1000–1200 cm⁻¹ and 1800 cm⁻¹, respectively. On the other hand, the five-membered ring and carbonyl moieties in the succinimide structure exhibited peaks around 1200–1400 cm⁻¹ and 1700 cm⁻¹, respectively. Furthermore, the peak intensity of the five-membered rings and carbonyl moieties changed linearly with the monomer feed. Therefore, these polymerization results and IR spectra indicated that the selective vinyl copolymers having the maleimide unit in the main-chain and the five-membered cyclic carbonate group in the side-chain were prepared without depending on the monomer feed, and also that these copolymers were constructed with the same composition ratio of each monomer unit as the monomer feed (Fig. 1 and S2†).

Color change of PVEC and PMI copolymers in a solution, depending on the composition ratio of each monomer unit


The solubility of the PVEC and/or PMI polymers in various solvents is shown in Table 2. Poly-0, Poly-100, and these copolymers were soluble in halogen, cyclic ether, ketone, and polar solvents such as carbonate, sulfoxide and amide, although Poly-0 was partly soluble in acetone and PCA. On the other hand, these polymers were insoluble in hydrocarbon, ester, nitrile, alcohol and ether. Furthermore, the color of the solution

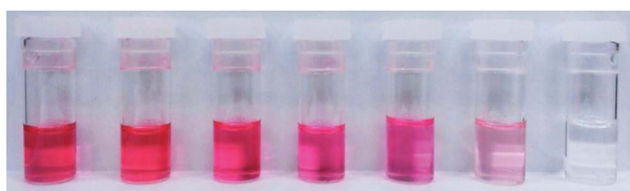**Fig. 2** Color change of PVEC and PMI copolymers in DMF depending on the composition ratio of each monomer unit.

of PVEC and PMI copolymers was red in DMF. Interestingly, the color of the solution changed from red to pale red with increases in the composition ratio of the PVEC unit (Fig. 2). In addition, the red color was observed in polar and/or basic solvents such as amine, amide, sulfoxide, and cyclic carbonate, although the polymer solution was colorless in nonpolar and/or acidic solvents such as CHCl₃ and CCl₄. On the other hand, the solution color of Poly-100 never changed not only in DMF but also in various other solvents. Therefore, the color change depending on the composition ratio of each monomer unit indicated that at least a 10% composition ratio of the PMI unit was essential in the copolymers to exhibit the red color.

Proposed main-chain structure and color change mechanism of PVEC and PMI copolymers based on tautomerization of PMI unit

The color change was studied in detail by collecting UV-Vis spectra of the PVEC and PMI copolymers in DMF, CHCl₃, and DMF/CHCl₃ (Fig. 3). In the UV-Vis spectra observed in DMF, the

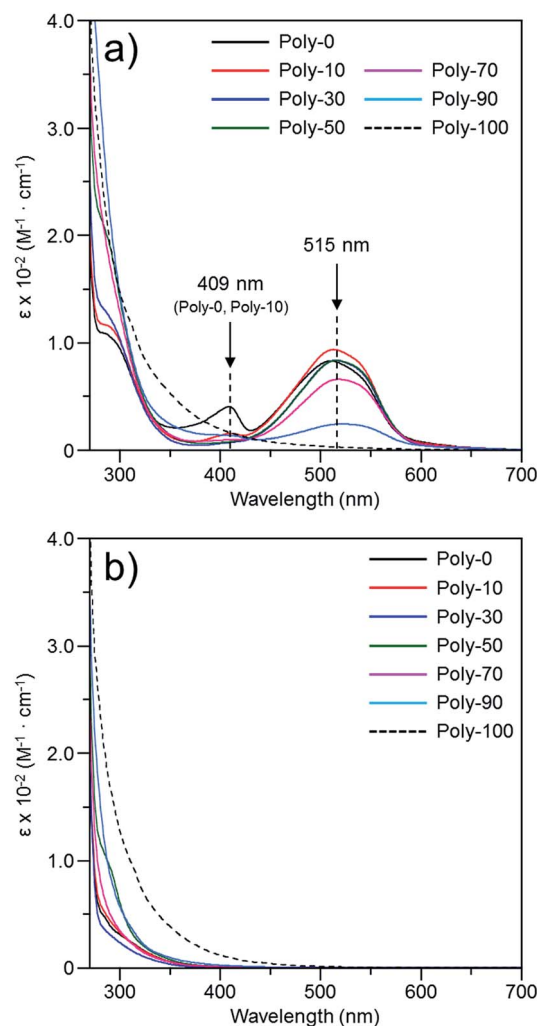**Fig. 3** UV-Vis spectra of PVEC and PMI copolymers prepared with various monomer feeds, observed in (a) DMF and (b) CHCl₃ (5.0 × 10⁻³ mol L⁻¹).

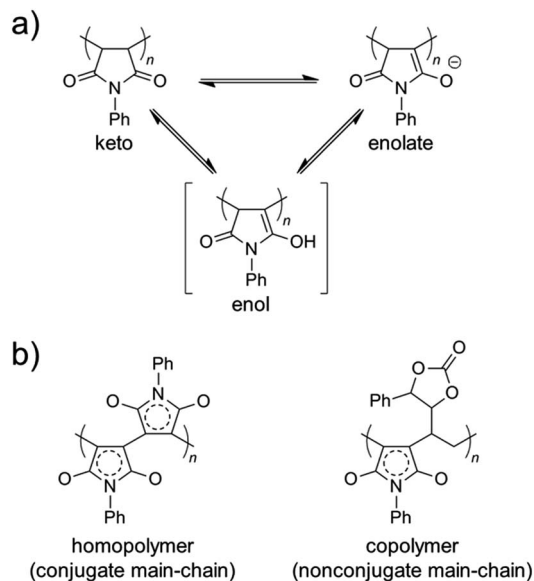


Fig. 4 (a) Tautomer structures of PMI unit in keto, enol, and enolate forms. (b) Conjugated main-chain sequence of PMI homopolymer and nonconjugated main-chain sequences of PVEC and PMI copolymers.

specific maximum absorptions (λ_{\max}) were at 409 nm and 515 nm (Fig. 3a), although such absorptions were never observed in CHCl_3 (Fig. 3b). The absorption observed at 515 nm was assigned to the enolate structure due to the tautomerization of the maleimide moiety, because the deprotonation occurred

from the maleimide unit in the main-chain under the basic condition (Fig. 4a).^{8b,11,15} On the other hand, the UV-Vis spectra of Poly-10 and Poly-0 suggested that the absorption observed at 409 nm was due to the expanded conjugation of the maleimide units in the main-chain because such an absorption was never observed in the copolymer having a high composition ratio of the PVEC unit (Fig. 4b).^{8b} Furthermore, the intensity of the λ_{\max} observed at 515 nm decreased with an increasing PVEC composition ratio in the copolymers, and this intensity change agreed with the tendency of the color change depending on the composition ratio of each monomer unit (Fig. 2 and 3a). These observations of the color change and UV-Vis spectra suggested that the main-chain structures of the PVEC and PMI copolymers were constructed from the alternating sequence and/or the block sequence of the rich monomer depending on the monomer feed (Fig. S3[†]). This was due to the fact that the alternating sequence of the PVEC and PMI copolymers could not be conjugated with each monomer unit. On the other hand, the copolymers having a high PMI composition ratio were constructed with part of the alternating sequence and the block sequence of the conjugated maleimide units (Fig. 4b and S3[†]). The UV-Vis spectra of Poly-0 and Poly-50 were measured in DMF/ CHCl_3 mix solvent (Fig. 5). The absorptions observed at 511 nm and 515 nm were assigned to the enolate tautomer of the maleimide unit in Poly-0 and Poly-50, respectively (Fig. 5a and b). The absorption intensity also decreased with increasing CHCl_3 ratios in the solvent mixture. This intensity change suggested that the keto-enolate sequence increased with

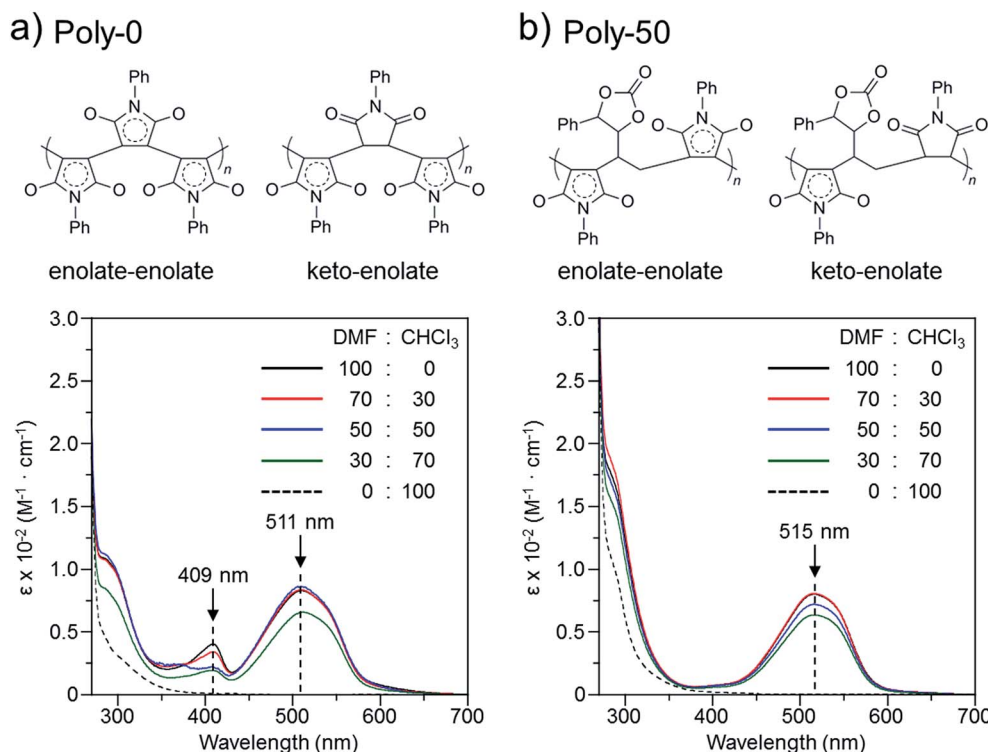


Fig. 5 UV-Vis spectra and main-chain structure of (a) Poly-0 and (b) Poly-50 observed in solvent mixtures of DMF and CHCl_3 ($5.0 \times 10^{-5} \text{ mol L}^{-1}$).



respect to the enolate–enolate sequence due to the tautomerization based on the solvent effect with increasing CHCl_3 ratios in the solvent mixture (Fig. 5). On the other hand, the absorption assigned to the conjugated sequence of the maleimide unit was observed at 409 nm only in the case of Poly-0, and the absorption intensity decreased with increasing CHCl_3 ratios in the solvent mixture as well as the increase of the PVEC composition ratio (Fig. 5a). This result suggested that the conjugated sequence in the main-chain disappeared together with decreases in the enolate–enolate sequence at high CHCl_3 ratios (Fig. 5a). Furthermore, the UV-Vis spectrum also suggested that the alternating structure of PVEC and PMI units never formed the conjugated sequence in the main-chain because such absorptions around 409 nm were never observed in the case of Poly-50 (Fig. 5b). Therefore, these color changes and UV-Vis spectra of PVEC and PMI copolymers supported that the tautomerization of the maleimide unit, based on the solvent effect, readily occurred in the main-chain. In addition, the alternating structure was constructed in a part of the copolymer sequence depending on the composition ratio of each monomer unit.

Color change of PVEC and PMI copolymers based on acid–base switching in solid-state

We have already reported that the solution of PVEC and NMI copolymer exhibited reversible color change between red and colorless based on acid–base switching.⁸ PVEC and PMI copolymers precipitated into insoluble solvent (ether) containing

a slight amount of trifluoroacetic acid (TFA) or triethylamine (Et_3N) to verify the color change of the copolymers based on acid–base switching in the solid-state. As shown in Fig. 6a, the white color of the synthesized copolymers immediately changed to a pink color in ether containing Et_3N . Then, the pink color changed back to white color in ether containing TFA, although the precipitated copolymers never dissolved in ether containing TFA or Et_3N . Furthermore, the initial white color of the copolymers changed to a pink color by exposure to Et_3N vapor (Fig. 6b). Then, the pink color also changed back to the white color under the acidic atmosphere. On the other hand, the depth of the color change depended on the composition ratio of each monomer unit in the copolymers. Specifically, the PVEC composition ratio in the copolymers increased displaying a change to the pale pink color. Moreover, this color change in the solid-state and in the solution occurred due to the tautomerization of the maleimide moiety. In the IR spectra of the polymer exposed to Et_3N in the solid-state, the enolate structure was observed at 1665 cm^{-1} as the weak shoulder assigned to the carbonyl peak of the maleimide moiety (Fig. 7). However, the conformation change was never observed in ^1H and ^{13}C NMR spectra under high concentrations of CDCl_3 and $\text{DMF-}d_7$ (Fig. S4 and S5[†]). In the previous reports, the shoulder peak of the NMI polymer observed around $1660\text{--}1670\text{ cm}^{-1}$ was assigned to $\text{C}=\text{N}^-$ formed by the tautomerization of the maleimide moiety (Fig. 7).^{26,27} In addition, the tautomerization of the maleimide moiety was also supported by the broadening of the carbonyl peak in the range of $1610\text{--}1700\text{ cm}^{-1}$ (Fig. 7). Moreover, the change in the depth of the color depending on the composition ratio indicated that the copolymer of the pale pink color was formed with a high composition ratio of the PVEC unit because the color change originated from the enolate

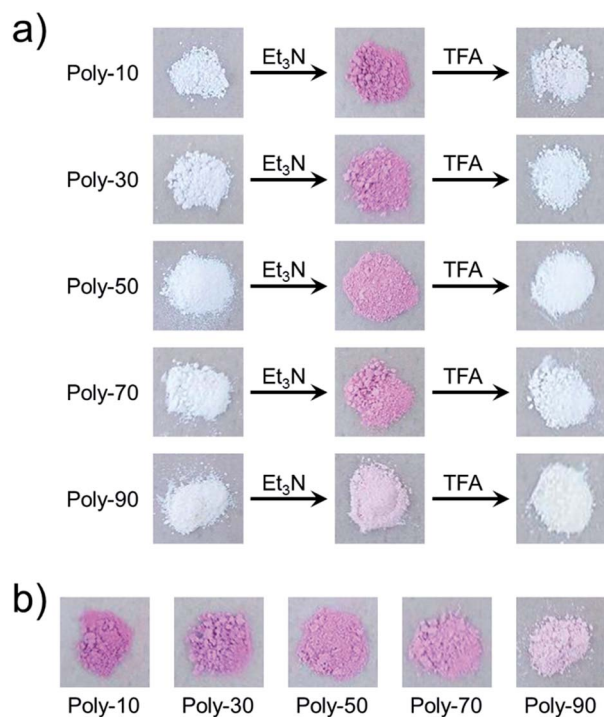


Fig. 6 Color change of PVEC and PMI copolymers based on acid–base switching in the solid-state, (a) in ether with Et_3N or TFA, (b) in Et_3N vapor.

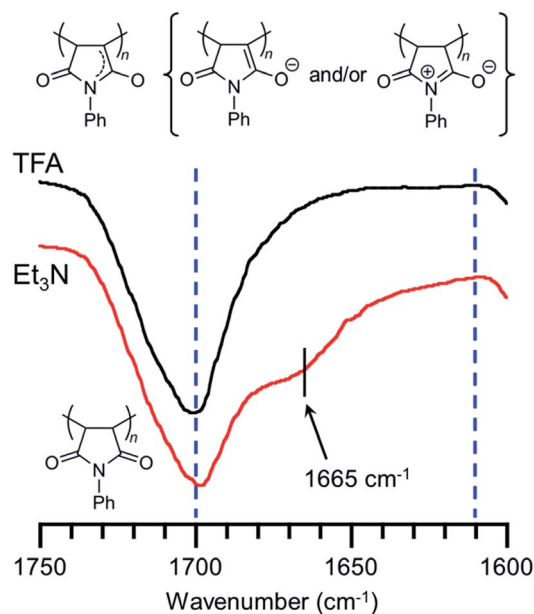


Fig. 7 IR spectra of PVEC and PMI copolymer exposed to TFA and Et_3N in the solid-state. $\text{C}=\text{O}$ peak of maleimide moiety was expanded at $1600\text{--}1750\text{ cm}^{-1}$.



structure of the maleimide unit, as shown above. Therefore, it was found that PVEC and PMI copolymers exhibited reversible color changes based on acid–base switching in the solid-state, and the depth of the color change was controlled depending on the composition ratio of the PVEC and/or PMI units. Furthermore, it was determined that the tautomerization of the maleimide moiety gave rise to the color change of these copolymers with acid–base switching and the solvent effect as the trigger.


Conclusion

The radical copolymerization with various monomer feeds of PVEC and PMI was carried out with DTBP as an initiator in bulk at 120 °C for 24 h. The yield, molecular weight, and composition ratio of the PMI unit in copolymers increased almost linearly with increasing PMI feed. IR spectra of these copolymers proved that the radical copolymerization of PVEC and PMI successfully proceeded through the selective vinyl polymerization without depending on the monomer feed. In the UV-Vis spectra, the absorptions observed at 409 nm and 515 nm were assigned to the expanded conjugation of the maleimide units in the intra-molecular and the enolate structure formed from the tautomerization of the maleimide moiety, respectively. The results of UV-Vis spectra revealed that the tautomerization of the maleimide unit, based on the solvent effect, readily occurred in the main-chain. Moreover, this suggested that the alternating and/or homo sequence was constructed depending on the monomer feed. Furthermore, these copolymers exhibited a sensitive and reversible color change based on acid–base switching not only in solution but also in the solid-state. In addition, the depth of the color change was controlled depending on the composition ratio of the PVEC and/or PMI units in solution and the solid-state. It was determined that the color change of these copolymers occurred due to the tautomerization of the maleimide moiety with acid–base switching and solvent effect as the trigger.

Experimental

Measurements

Gel permeation chromatography (GPC) was carried out on a TOSOH HLC-8220 system equipped with three consecutive polystyrene gel columns [TSK-gels (bead size, exclusion limited molecular weight), super-AW4000 (6 μm, >4 × 10⁵), super-AW3000 (4 μm, >6 × 10⁴) and super-AW2500 (4 μm, >2 × 10³)] and refractive index and ultraviolet detectors at 40 °C. The system was operated using 10 mM LiBr in DMF as eluent at

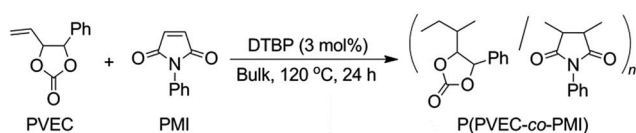

Scheme 1 Radical copolymerization of PVEC and PMI with DTBP in bulk.

a flow rate of 0.5 mL min⁻¹. Polystyrene standards were employed for calibration. ¹H and ¹³C NMR spectroscopy was performed with a JEOL ECS-400 NMR spectrometer operating at 400 MHz in chloroform-*d* (CDCl₃), dimethyl sulfoxide-*d*₆ (DMSO-*d*₆), *N,N*-dimethylformamide-*d*₇ (DMF-*d*₇) using tetramethyl silane (TMS) as an internal reference. ATR-FTIR spectra were recorded on a Thermo Fisher Scientific Nicolet iS10 spectrometer from 650 to 4000 cm⁻¹. UV-Vis absorption spectra were recorded on a Jasco V570 UV-Vis-NIR spectrophotometer in *N,N*-dimethylformamide (DMF) and chloroform (CHCl₃).

Materials

CDCl₃, DMSO-*d*₆, and DMF-*d*₇ solvents for NMR, TMS for an internal reference, and DMF and CHCl₃ for spectroscopy were purchased from Wako Pure Chemical Industry. *N*-Phenylmaleimide (PMI) and di-*tert*-butyl peroxide (DTBP) were purchased from Tokyo Chemical Industry. *N*-Phenylmaleimide was recrystallized before polymerization.

Preparation of monomers

Phenyl butadiene monoxide (PBO) and phenyl vinyl ethylene carbonate (PVEC) were prepared according to the methods reported in previous literature.^{8,23}

Polymerization

Polymerization of PVEC and/or PMI was carried out with di-*tert*-butyl peroxide (DTBP) as a radical initiator in bulk using a degassed and sealed tube (Scheme 1). A typical procedure of polymerization is as follows.^{8,23} The ¹H and ¹³C NMR spectra of poly(PVEC-*co*-PMI) prepared with monomer feeds of 90 : 10 (Poly-90), 70 : 30 (Poly-70), 30 : 70 (Poly-30), and 10 : 90 (Poly-10) of PVEC and PMI, respectively, exhibited the same chemical shifts as Poly-50 (Fig. S2†).

Radical polymerization of PVEC and/or PMI

A mixture of each monomer (6.0 mmol) of PVEC and/or PMI and 26.3 mg (0.18 mmol, 3 mol%) of DTBP was frozen in liquid nitrogen and degassed under reduced pressure (2–3 mm Hg) for 30 min. After repeating this operation exactly 3 times, the tube containing the mixture of the monomer and initiator was sealed, and the mixture was stirred at 120 °C for 24 h. The resulting solid was dissolved in DMF/acetone and the solution was poured into *n*-hexane/ethanol. The precipitated polymer was washed with methanol and dried under dynamic vacuum at 40 °C for 24 h.

Poly(phenyl vinyl ethylene carbonate), Poly-100. ¹H NMR (DMSO-*d*₆, TMS): δ = 0.21–2.23 (3H, –CH₂–CH–), 3.52–5.56 (2H, –CH–CH–), 6.45–7.86 (5H, C₆H₅–). ¹³C NMR (DMSO-*d*₆, TMS): δ = 28.60, 34.18, 82.06, 83.38, 126.80, 128.89, 129.53, 135.34, 153.42.

Poly(PVEC-*co*-PMI) with monomer feed of 50 : 50, Poly-50. ¹H NMR (DMSO-*d*₆, TMS): δ = 0.21–2.49 (3H, –CH₂–CH–), 4.06 (2H, –CH–CH–), 4.46–6.18 (2H, –COH–COH–), 7.40 (10H, C₆H₅C and C₆H₅N). ¹³C NMR (DMSO-*d*₆, TMS): δ = 28.7, 43.3, 82.3, 126.7, 128.9, 131.4, 135.1, 153.5, 175.9.



Poly(phenylmaleimide), Poly-0. ^1H NMR (DMSO- d_6 , TMS): $\delta = 4.11, 4.55$ (2H, $-\text{CH}-\text{CH}-$), $7.15, 7.41$ (5H, $\text{C}_6\text{H}_5\text{N}$). ^{13}C NMR (DMSO- d_6 , TMS): $\delta = 42.9, 126.7, 128.7, 131.5, 176.3$.

Acknowledgements

This study was financially supported by JSR Co., Ltd.

Notes and references

- (a) Y. Hibi, S. Tokuoka, T. Terashima, M. Ouchi and M. Sawamoto, *Polym. Chem.*, 2010, **2**, 341–347; (b) Y. Hibi, M. Ouchi and M. Sawamoto, *Angew. Chem., Int. Ed. Engl.*, 2011, **50**, 7434–7437; (c) K. Nakatani, Y. Ogura, Y. Koda, T. Terashima and M. Sawamoto, *J. Am. Chem. Soc.*, 2012, **134**, 4373–4383; (d) J.-F. Lutz, M. Ouchi, D. Liu and M. Sawamoto, *Science*, 2013, **341**, 1238149; (e) M. Ouchi, M. Nakano, T. Nakanishi and M. Sawamoto, *Angew. Chem., Int. Ed. Engl.*, 2016, **128**, 14804–14809.
- (a) S. Pfeifer and J. F. Lutz, *J. Am. Chem. Soc.*, 2007, **129**, 9542–9543; (b) M. Zamfir and J. F. Lutz, *Nat. Commun.*, 2012, **3**, 1138; (c) J. F. Lutz, B. Schmidt and S. Pfeifer, *Macromol. Rapid Commun.*, 2011, **32**, 127–135; (d) S. Srichan, D. Chan-Seng and J. F. Lutz, *ACS Macro Lett.*, 2012, **1**, 589–592; (e) S. Srichan, H. Mutlu and J. F. Lutz, *Eur. Polym. J.*, 2015, **62**, 338–346.
- (a) M. Matsuda, K. Satoh and M. Kamigaito, *J. Polym. Sci., Part A: Polym. Chem.*, 2013, **51**, 1774–1785; (b) T. Soejima, K. Satoh and M. Kamigaito, *J. Am. Chem. Soc.*, 2016, **138**, 944–954; (c) T. Soejima, K. Satoh and M. Kamigaito, *Polym. Chem.*, 2016, **7**, 4833–4841; (d) K. Satoh, *Polym. J.*, 2015, **47**, 527–536; (e) K. Satoh and M. Kamigaito, *Kobunshi Ronbunshu*, 2015, **72**, 421–432.
- (a) T. Otsu, A. Matsumoto, T. Kubota and S. Mori, *Polym. Bull.*, 1990, **23**, 43–50; (b) K. Takeda and A. Matsumoto, *Macromol. Chem. Phys.*, 2010, **211**, 782–790; (c) M. Hisano, K. Takeda, T. Takashima, Z. Jin, A. Shiibashi and A. Matsumoto, *Macromolecules*, 2013, **46**, 7733–7744; (d) M. Hisano, T. Takashima, Z. Jin, A. Shiibashi and A. Matsumoto, *Macromol. Chem. Phys.*, 2013, **214**, 1612–1620; (e) D. Yamamoto and A. Matsumoto, *Macromolecules*, 2013, **46**, 9526–9536; (f) A. Tsujii, M. Namba, H. Okamura and A. Matsumoto, *Macromolecules*, 2014, **47**, 6619–6626; (g) A. Tsujii, L. Lou, M. Nagashima, H. Okamura and A. Matsumoto, *J. Adhes. Soc. Jpn.*, 2015, **51**, 336–341.
- Y. Abiko, A. Matsumura, K. Nakabayashi and H. Mori, *React. Funct. Polym.*, 2015, **93**, 170–177.
- G. Q. Chen, Z. Q. Wu, J. R. Wu, Z. C. Li and F. M. Li, *Macromolecules*, 2000, **33**, 232–234.
- Y. Ren, Z. Zhu and J. Huang, *J. Polym. Sci., Part A: Polym. Chem.*, 2004, **42**, 3828–3835.
- (a) Y. Yoshida and T. Endo, *Polymer*, 2016, **102**, 167–175; (b) Y. Yoshida and T. Endo, *Polym. Chem.*, 2016, **7**, 6770–6778.
- I. Takase, K. Kawazu, H. Aida and H. Kohkame, *Kobunshi Ronbunshu*, 1990, **47**(7), 569–574.
- M. Mohamed, K. C. Hsu, J. L. Hong and S. W. Kuo, *Polym. Chem.*, 2015, **7**, 135–145.
- H. Ahn, J. Hong, S. Kim, I. Choi and M. Park, *ACS Appl. Mater. Interfaces*, 2015, **7**, 704–712.
- (a) P. Sung, C. Chen, S. Wu and J. Huang, *J. Polym. Sci., Part A: Polym. Chem.*, 1996, **34**, 2189–2194; (b) İ. Serhatli, Y. Yagci, E. Hattemer, R. Zentel, E. Schmäzlin, S. Hohenadl, C. Braüchle and K. Meerholz, *J. Polym. Sci., Part A: Polym. Chem.*, 2001, **39**, 1589–1595; (c) F. A. Nicolescu, V. V. Jerca, I. Dancus, A. Petris, T. V. Nicolescu, I. B. Rau, V. I. Vlad, D. S. Vasilescu and D. M. Vuluga, *J. Polym. Res.*, 2011, **18**, 1009–1016.
- (a) K. Koehler, K. Anseth and C. Bowman, *Biomacromolecules*, 2013, **14**, 538–547; (b) R. Klein, F. Übel and H. Frey, *Macromol. Rapid Commun.*, 2015, **36**, 1822–1828.
- (a) T. Oishi, H. Yamasaki and M. Fujimoto, *Polym. J.*, 1991, **23**, 795–804; (b) K. Onimura and T. Oishi, *Polymeric Chiral Catalyst Design and Chiral Polymer Synthesis*, Wiley, 2011, p. 356; (c) Y. Okamoto, T. Nakano, H. Kobayashi and K. Hatada, *Polym. Bull.*, 1991, **25**, 5–8.
- (a) H. C. Haas and R. L. MacDonald, *J. Polym. Sci., Polym. Chem. Ed.*, 1973, **11**, 327–343; (b) H. C. Haas and R. D. Moreau, *J. Polym. Sci., Polym. Chem. Ed.*, 1975, **13**, 2327–2334.
- (a) E. Hadjoudis and I. Mavridis, *Chem. Soc. Rev.*, 2004, **33**, 579–588; (b) R. Klajn, *Chem. Soc. Rev.*, 2013, **43**, 148–184; (c) A. Seeboth, D. Löttsch, R. Ruhmann and O. Muehling, *Chem. Rev.*, 2014, **114**, 3037–3068.
- (a) T. Yamase, *Chem. Rev.*, 1998, **98**, 307–326; (b) M. Irie, T. Fukaminato, K. Matsuda and S. Kobatake, *Chem. Rev.*, 2014, **114**, 12174–12277; (c) A. Fihey, A. Perrier, W. Browne and D. Jacquemin, *Chem. Soc. Rev.*, 2015, **44**, 3719–3759.
- (a) R. Mortimer, *Chem. Soc. Rev.*, 1997, **26**, 147–156; (b) P. Beaujuge and J. Reynolds, *Chem. Rev.*, 2010, **110**, 268–320; (c) Z. Liu, W. Qi and G. Xu, *Chem. Soc. Rev.*, 2015, **44**, 3117–3142.
- (a) O. Wenger, *Chem. Rev.*, 2013, **113**, 3686–3733; (b) J. Askim, M. Mahmoudi and K. Suslick, *Chem. Soc. Rev.*, 2013, **42**, 8649–8682.
- (a) C. Reichardt, *Chem. Soc. Rev.*, 1992, **21**, 147–153; (b) V. Machado, R. Stock and C. Reichardt, *Chem. Rev.*, 2014, **114**, 10429–10475.
- (a) V. Minkin, *Chem. Rev.*, 2004, **104**, 2751–2776; (b) E. Cariati, E. Lucenti, C. Botta, U. Giovanella, D. Marinotto and S. Righetto, *Coord. Chem. Rev.*, 2016, **306**, 566–614.
- (a) R. Motoshige, Y. Mawatari, A. Motoshige, Y. Yoshida, T. Sasaki, H. Yoshimizu, T. Suzuki, Y. Tsujita and M. Tabata, *J. Polym. Sci., Part A: Polym. Chem.*, 2014, **52**, 752–759; (b) Y. Mawatari, A. Motoshige, Y. Yoshida, R. Motoshige, T. Sasaki and M. Tabata, *Polymer*, 2014, **55**, 2356–2361.
- (a) B. Ochiai, M. Matsuki, D. Nagai, T. Miyagawa and T. Endo, *J. Polym. Sci., Part A: Polym. Chem.*, 2005, **43**, 584–592; (b) B. Ochiai and T. Endo, *J. Polym. Sci., Part A: Polym. Chem.*, 2007, **45**, 2827–2834.
- (a) D. Webster and A. Crain, *Prog. Org. Coat.*, 2000, **40**, 275–282; (b) D. Webster, *Prog. Org. Coat.*, 2003, **47**, 77–86; (c) Y. Wang, F. Fan, A. L. Agapov, T. Saito, J. Yang, X. Yu,



- K. Hong, J. Mays and A. P. Sokolov, *Polymer*, 2014, **55**, 4067–4076.
- 25 (a) N. Kihara and T. Endo, *Makromol. Chem.*, 1992, **193**, 1481–1492; (b) A. Suzuki, D. Nagai, B. Ochiai and T. Endo, *J. Polym. Sci., Part A: Polym. Chem.*, 2004, **42**, 5983–5989; (c) A. Sudo, H. Morishita and T. Endo, *J. Polym. Sci., Part A: Polym. Chem.*, 2010, **48**, 3896–3902.
- 26 G. V. Paesschen and D. Timmerman, *Makromol. Chem.*, 1964, **78**, 112–120.
- 27 (a) M. Yamada and I. Takase, *Kobunshi Kagaku*, 1966, **23**, 348–353; (b) M. Yamada, I. Takase and T. Mishima, *Kobunshi Kagaku*, 1967, **24**, 326–333.

