

Cite this: *RSC Adv.*, 2017, 7, 22187

Wasp-waisted behavior in magnetic hysteresis curves of CoFe_2O_4 nanopowder at a low temperature: experimental evidence and theoretical approach

Tibério Magno de Lima Alves,^{ab} Bruno Ferreira Amorim,^b Marco Antonio Morales Torres,^b Claudionor Gomes Bezerra,^{ib}*^b Suzana Nóbrega de Medeiros,^b Pedro Lana Gasteloi,^c Luis Eugenio Fernandez Outon^{cd} and Waldemar Augusto de Almeida Macedo^c

We theoretically and experimentally investigated wasp-waisted magnetic hysteresis curves at a low temperature for CoFe_2O_4 nanopowders. Our theoretical approach proposes a physical mechanism that leads to wasp-waisted behavior for a single magnetic phase with the same anisotropic field, contrary to that of typical multi-phase magnetic systems. Our simulations show that a combination of effects, namely easy-plane anisotropy configuration and dipolar interactions, results in a double peak in the magnetic susceptibility curve of a granular magnetic system. As experimental evidence of such an effect, we present a CoFe_2O_4 nanopowder and its structural and magnetic characterizations, which support a single magnetic phase. In addition, the evidence does not corroborate many explanations reported in the literature for wasp-waisted magnetic behavior. Our results provide evidence for a tetragonal crystalline phase of CoFe_2O_4 due to magneto-elastic coupling, recently reported in the literature.

Received 26th December 2016

Accepted 20th March 2017

DOI: 10.1039/c6ra28727a

rsc.li/rsc-advances

1 Introduction

Recently, some nanometric granular magnetic systems have displayed “wasp-waisted”-like magnetic hysteresis curves at low temperatures, especially CoFe_2O_4 nanoparticles, and such phenomena have been attributed to many mechanisms. Direct insight could lead to an interpretation of what occurs in the magnetic multi-phase systems of rocks,¹ where the material possesses a hard magnetic phase with a high value of the coercive field and a soft magnetic phase with a lower coercive field value. Some authors attribute this phenomenon to a superposition of superparamagnetic and single-domain phases, as presented in the work of Roberts *et al.*,² because the superparamagnetic phase has null coercivity and the hard blocked magnetic single-domain phase does not. Abrupt changes in the magnetization curve around a zero magnetic field could be expected in this case. However, a mixture of a single-domain phase (high coercivity) and a multi-domain

phase (low coercivity) could also reproduce the wasp-waisted magnetic hysteresis curves.²

For $\text{Co}_{0.6}\text{Sn}_{0.4}\text{Fe}_2\text{O}_4$ nanoparticles with an average grain size of approximately 20 nm,³ another explanation is based on the superexchange interaction configuration between metallic cations in the spinel structure being changed by the occupation number of Co^{2+} ions in the A-sites (tetrahedral), which tends to remove Fe^{3+} from the A-sites to B-sites (octahedral). This diminishes the effect of the superexchange coupling A-B interaction as compared to the A-A and B-B interactions. This leads to a magnetic structure that is changed from the well-established antiferromagnetic phase to competing ferromagnetic and antiferromagnetic phases. In the work of Chithra *et al.*,⁴ cobalt ferrite nanoparticles were also produced, and the wasp-waisted behavior was attributed to two groups of particles with different anisotropies leading to a double peak in the susceptibility curves and exhibiting an exchange-spring-like behavior. In the work of Song and Zhang,⁵ bimagnetic spinel cobalt ferrite and manganese ferrite with core-shell structures also reproduced the wasp-waisted hysteresis curves. However, concerning cobalt ferrite nanoparticles, Fu *et al.*⁶ showed that the CoFe_2O_4 nanoparticles exhibit the same behavior in a nanotube geometry, unlike that which occurs in nanorod⁷ and nanowire⁸ geometries. Xu *et al.*⁹ showed that jumps around $H = 0$ in the magnetic hysteresis cycles of CoFe_2O_4 nanoparticles can be attributed to spin re-orientation at low temperatures due to

^aInstituto Federal de Educação Ciência e Tecnologia do Rio Grande do Norte, 59015-000 Natal, RN, Brazil

^bDepartamento de Física Teórica e Experimental, Universidade Federal do Rio Grande do Norte, 59078-900 Natal, RN, Brazil. E-mail: cbezerra@fisica.ufrn.br

^cLaboratório de Física Aplicada, Centro de Desenvolvimento da Tecnologia Nuclear, CDTN, 31970-201 Belo Horizonte, MG, Brazil

^dDepartamento de Física, Universidade Federal de Minas Gerais, 31270-901 Belo Horizonte, MG, Brazil



canted spins on the surfaces of the nanoparticles. If the surface/volume ratio of the nanoparticles increases, the surface effects tend to dominate the magnetic properties.

Coated L_{10} tetragonal-phase FePt nanoparticles, presented in the work of Lee *et al.*,¹⁰ displayed “constricted” hysteresis curves and this effect was attributed to dipolar interactions between nanoparticles, which cause abrupt changes in magnetization around zero applied magnetic field in the hysteresis cycle. In this case, when the thickness of the encapsulation layer is increased, the effect of constriction in the hysteresis curves is suppressed considerably, demonstrating that wasp-waisted hysteresis curves could also be attributed to dipolar interactions between single-domain nanoparticles.

In this work, we propose a theoretical approach that presents another physical mechanism leading to wasp-waisted-like hysteresis curves. Our model is based on the coherent rotation of single-domain nanoparticles, considering a uniaxial easy-plane anisotropy configuration and dipolar interactions without the effects of temperature. Interactions are a topic of great interest in the literature concerning magnetic granular systems, especially concerning how their superposition with anisotropic fields can change the magnetic properties. Many efforts have been made to investigate dipolar fields in granular systems that have cubic¹¹ and easy-axis^{12–16} anisotropy configurations; however, studies concerning easy-plane configurations are scarce.

We also present experimental evidence from ball-milled CoFe_2O_4 nanopowders using various characterization methods to ensure that the proposed theoretical mechanism is likely to explain the static magnetic properties of our sample.

2 Experiment

Synthesis of the stoichiometric CoFe_2O_4 nanoparticles was performed in a planetary ball-mill (Fritsch Pulverisette 7 – Premium line), with a vial and balls made of hardened steel, in an air atmosphere, followed by thermal annealing. The process involved milling stoichiometric amounts of $\gamma\text{-Fe}_2\text{O}_3$ and Co_3O_4 powders, used as precursors, which were both purchased from Sigma-Aldrich. The balls and powder were placed in a vial and milled for 10 h, intercalating 10 min of rest for every 1 h of milling time to reduce heating. The parameters used in the milling were a ball-to-powder mass ratio of 20 : 1 and an angular velocity of 300 rpm. After milling, the powders were annealed at 900 °C for 2 h.

Phase characterization of the sample was performed *via* X-ray diffraction (XRD) using a Rigaku MiniFlex II diffractometer, with $\text{CuK}\alpha$ radiation of $\lambda = 1.541 \text{ \AA}$. The XRD data were collected at room temperature, with a 2θ range between 20° and 70°, scan rate of 5° min^{-1} and 0.02° step. The XRD pattern was identified using the JCPDS database and refined using the Rietveld method with the MAUD program, which was provided with the structural parameters. The sample density was estimated using the relationship $D_x = 8 \text{ wt}/N a^3$,¹⁷ where wt is the molecular weight of the sample, N is Avogadro's number, and a is the lattice parameter of the unit cell.

The morphologies and grain size distributions of the nanopowders were analyzed using a transmission electron microscope (TEM) (Jeol, JEM-2100) equipped with an energy dispersive X-ray spectroscopy (EDS).

Mössbauer spectra (MS) were recorded in transmission mode at a low temperature (12 K) and constant acceleration mode using a conventional commercial spectrometer (SEE Co), with gamma rays provided by a $^{57}\text{Co}(\text{Rh})$ source. The MS were analyzed using a non-linear least-squares routine, with a Lorentzian line shape. The isomer shift values are related to $\alpha\text{-Fe}$ at 300 K.

X-ray photoelectron spectroscopy analysis (XPS-Specs, Phoibos-150 electron analyzer), using monochromatized Al $\text{K}\alpha$ radiation (1486.6 eV) at a power of 350 W, was carried out to characterize the valence states of iron and cobalt in the sample. High-resolution spectra were acquired using 0.1 eV step energy and 20 eV passage energy. The spectra were fitted using Casa XPS software, resulting in RES STD <1.

The magnetic hysteresis loop was recorded in a commercial VSM – PPMS DynaCool from Quantum Design. The measurements were performed with magnetic fields between $\pm 140 \text{ kOe}$ at 5 K.

3 Model

Our modeling approach consists of building an L edge simulation square box, which contains a set of randomly positioned N single-domain nanoparticles with particle size determined from a log-normal size distribution, with a pre-defined concentration c (see Fig. 1(a)), and obeying a non-overlapping criterion. We choose a coordinate system that coincides with the edges of the simulation box. The i -th nanoparticle is characterized by the position \vec{r}_i (see Fig. 1(b)), and crystallographic orientation defined by the unitary vector \hat{u}_i , with polar angles θ_i^u and ϕ_i^u (see Fig. 1(c)), as well as by its magnetic moment $\vec{\mu}_i = M_s V_i \hat{m}_i$. Here, M_s is the saturation magnetization (considered the same for all particles), V_i is the volume of the nanoparticle, and \hat{m}_i is a dimensionless unitary vector, with polar angles θ_i and ϕ_i .

Let us describe the magnetic energy terms that compose the free magnetic energy. In a magnetic field \vec{H} , the i -th single-domain nanoparticle presents a Zeeman energy given by

$$E_i^Z = -\vec{\mu}_i \cdot \vec{H}. \quad (1)$$

Since our sample presents an average grain size of approximately 60 nm, we expect that the effects of the surface anisotropy will be suppressed by the magneto-crystalline anisotropy of the core material. Therefore, the magneto-crystalline anisotropy is the dominant anisotropy in the sample. We consider a magneto-crystalline anisotropy following uniaxial symmetry, *i.e.*,¹⁸

$$E_i^a = [K_1 \alpha_i^2 + K_2 \alpha_i^4] V_i. \quad (2)$$

Here, K_1 and K_2 are the uniaxial magneto-crystalline anisotropy constants. In addition, α_i is the direction cosines of the magnetization related to the uniaxial crystallographic axes of



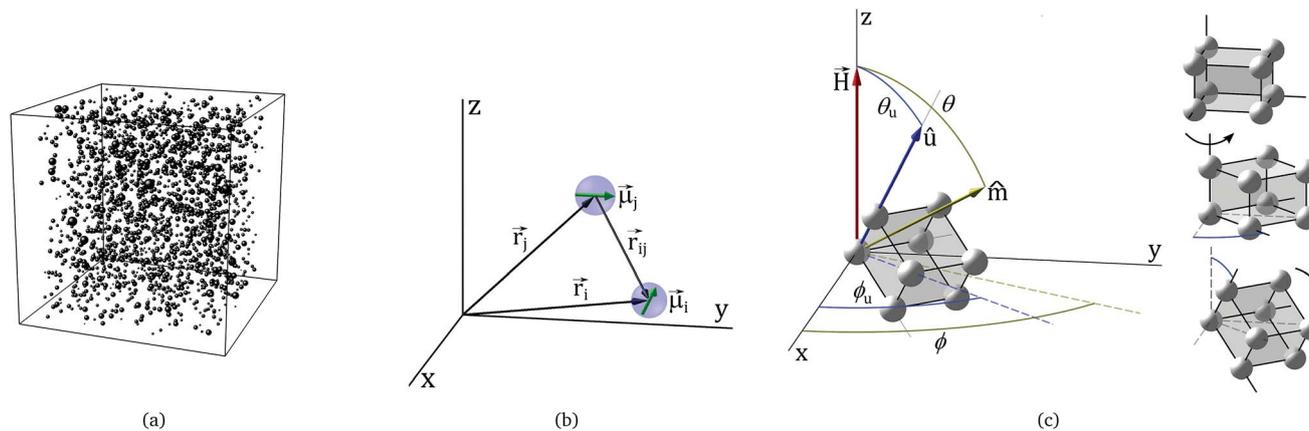


Fig. 1 Coordinate system adopted. In (a), we depict a box simulation containing 2000 particles, with $c = 10^{-2}$, and in (b), we present the quantities of interest for the dipolar field calculations. In (c), we illustrate the process of coordinate rotations used to transform the cosine directions of the anisotropic energy to the box simulation coordinate system.

the i -th nanoparticle. This quantity has to be transformed through inverse rotations θ_i^u and ϕ_i^u (see Fig. 1(c)) in order to formulate the anisotropic energy in terms of the coordinate system of the simulation box.

Regarding the interaction between particles, dipolar interactions are included in our model. If \vec{r}_i and \vec{r}_j are the positions of the i -th and j -th particles, respectively, the dipolar field H_{ij}^{dip} due to the j -th particle acting on the i -th particle is given by

$$\vec{H}_{ij}^{\text{dip}} = \frac{3(\vec{\mu}_j \cdot \vec{r}_{ij})(\vec{r}_{ij})}{r_{ij}^5} - \frac{\vec{\mu}_j}{r_{ij}^3}. \quad (3)$$

Here, $r_{ij} = |\vec{r}_i - \vec{r}_j|$ is the distance between the i -th and j -th particles. Therefore, the superposition of the dipolar fields acting on the i -th particle can be written as

$$\vec{H}_i^{\text{dip}} = \sum_{j \neq i} \left[\frac{3(\vec{\mu}_j \cdot \vec{r}_{ij})(\vec{r}_{ij})}{r_{ij}^5} - \frac{\vec{\mu}_j}{r_{ij}^3} \right], \quad (4)$$

so that the effective magnetic field acting on the i -th particle is given by

$$\vec{H}_i^{\text{eff}} = \vec{H} + \vec{H}_i^{\text{dip}}. \quad (5)$$

Considering the Zeeman, dipolar, and magneto-crystalline anisotropic energies, one can write the free magnetic energy of the i -th particle as

$$E_i = -\vec{H}_i^{\text{eff}} \cdot \hat{m}_i M_s V_i + [K_1 \alpha_i^2 + K_2 \alpha_i^4] V_i. \quad (6)$$

Since we are interested in describing the static magnetic properties at low temperatures, our approach consists of locally minimizing the free magnetic energy of each individual particle using the steepest descend method to find the equilibrium orientation state and then calculate the magnetization in a completely blocked state of temperature (temperature effects are not considered). In this regard, it is useful to reduce the number of parameters by dividing eqn (6) by $2|K_1|V_i$, which leads to the reduced free magnetic energy

$$e_i = -\vec{h}_i^{\text{eff}} \cdot \hat{m}_i + \frac{1}{2} [\text{sgn}(K_1) \alpha_i^2 + a \alpha_i^4]. \quad (7)$$

Here, $\vec{h}_i^{\text{eff}} = \vec{H}_i^{\text{eff}}/H_{k_i}$ is the reduced effective magnetic field, $H_{k_i} = 2|K_1|/M_s$, and $a = K_2/|K_1|$.

To implement our simulation, we consider a log-normal size distribution of particles

$$f(y) = \frac{1}{\sqrt{2\pi}\sigma y} \exp \left[-\frac{(\ln y)^2}{2\sigma^2} \right]. \quad (8)$$

Here, $y = d/d_m$, where d is the particle diameter, d_m is the average particle diameter, and σ is the standard deviation of the distribution. Because of the finite size of the simulation box, we applied a cut-off range for the dipolar field,^{19–21} which is defined by a critical radius, $r_c = 5d_m$. This means that, for a given particle, only the field produced by the surrounding particles within the range of r_c is considered. We should remark that, for different concentrations, slightly different values of r_c were observed. We have verified that a critical radius r_c larger than $5d_m$ does not substantially change the results.

We divide the edges of our box simulation by L , defining $\vec{r}' = \vec{r}/L$. The concentration is given by $c = \sum V_i/L^3$, which can be rewritten as $c = N\langle V \rangle/L^3$. Here, N is the number of particles and $\langle V \rangle$ is the average volume calculated from $f(y)$. Once $\langle V \rangle = \pi d_m^3 \langle y^3 \rangle / 6$, the concentration can be expressed as

$$c = \frac{N\pi(d'_m)^3 \langle y^3 \rangle}{6}, \quad (9)$$

where $d'_m = d_m/L$ is the reduced average diameter. Considering all of these features together, we can write the reduced effective magnetic field as follows:

$$\vec{h}_i^{\text{eff}} = \frac{\vec{H}}{H_{K_1}} + \frac{\pi M_s (d'_m)^3}{6 H_{K_1}} \sum_{j \neq i} \left[\frac{3(\hat{m}_j \cdot \vec{r}'_{ij})(\vec{r}'_{ij}) y_j^3}{(r'_{ij})^5} - \frac{\hat{m}_j y_j^3}{(r'_{ij})^3} \right] \quad (10)$$

or



$$\vec{h}_i^{\text{eff}} = h\hat{z} + \frac{c}{c_0} \frac{1}{N\langle y^3 \rangle} \sum_{j \neq i} \left[\frac{3(\hat{m}_j \cdot \vec{r}'_{ij})(\vec{r}'_{ij})y_j^3}{(r'_{ij})^5} - \frac{\hat{m}_j y_j^3}{(r'_{ij})^3} \right], \quad (11)$$

where $c_0 = H_k/M_s$. The ratio c/c_0 indicates the strength of the dipolar field/concentration ratio compared to the anisotropic field. Substituting eqn (11) into eqn (7), we can see that the energy depends on five parameters, the ratios c/c_0 , a , b , σ , and N .

The static magnetic properties are obtained by calculating the average component of the magnetization along the reduced magnetic field $h = H/H_k$, i.e.,

$$\langle m(h) \rangle = \frac{\sum_i m(h, \theta_u^i, \phi_u^i) \sin \theta_u^i}{\sum_i \sin \theta_u^i}, \quad (12)$$

where $m(h, \theta_u^i, \phi_u^i) = \hat{m}_i \cdot \hat{z}$ is the reduced component of the magnetization of the i -th particle as a function of the reduced magnetic field h . To compare our theoretical results with experimental data, we calculate the reduced coercive field h_c and the reduced remanent magnetization $\langle m(0) \rangle = m_r$, which are related to the experimental coercive field H_c , remanent magnetization M_r and saturation magnetization M_s by $h_c = H_c/H_k$ and $\langle m(0) \rangle = m_r = M_r/M_s$.

4 Numerical method

We can summarize our theoretical procedure as follows:

(i) We set the ratio a , as well as the concentration c and standard deviation σ . Then, we calculate d'_m and $\langle y^3 \rangle$ for N particles.

(ii) The packing process involves setting random positions (\vec{r}'_1, \vec{r}'_2) and sizes (y_1, y_2) in the reduced simulation box for the first and second particles. We perform a test to determine if this pair of particles obeys the non-overlapping criterion $r'_{12} > d'_m(y_1 + y_2)/2$. Then, we increase the number of particles one by one until N particles are created that obey the non-overlapping criterion, thus completing the packing process.

(iii) A set of coordinates $(\theta_u, \phi_u, \theta, \phi)$ is associated with each particle. Here, θ_u and ϕ_u are random in the intervals $0 \leq \theta_u \leq \pi$ and $0 \leq \phi_u \leq 2\pi$. We assume saturation in the $-\hat{z}$ direction as the initial configuration, which means taking $\theta = \pi$ and $\phi = 0$ for all particles.

(iv) The reduced dipolar field is calculated for all of the particles, following the cut-off criterion previously defined by $r_c = 5d_m$, and the reduced applied magnetic field is set as $\vec{h} = -h_{\text{sat}}\hat{z}$, where h_{sat} is the saturation reduced magnetic field.

(v) The effective magnetic field $\vec{h}_{\text{eff}} = \vec{h} + \vec{h}_{\text{dip}}$ is calculated, and a local minimization process is employed (steepest descent) to obtain the equilibrium positions (θ and ϕ) of all particles. Then, $\langle m(h) \rangle$ is numerically calculated.

(vi) The new reduced dipolar field is recalculated for all particles, and the reduced applied magnetic field is increased by a step of Δh . New equilibrium orientations as well as the new value of $\langle m(h) \rangle$ are calculated. This process continues until

$\vec{h} = h_{\text{sat}}\hat{z}$ is reached and returns to $\vec{h} = -h_{\text{sat}}\hat{z}$, completing the reduced hysteresis loop.

We should remark that, to avoid finite size and boundary effects, we evaluate $\langle m(h) \rangle$ considering particles inside a simulation box with edges equal to $0.9L$, centered within the original simulation box.

5 Results and discussion

5.1 Structural and chemical analysis

The X-ray diffraction patterns, along with the fitting data for the powders used as precursors and the CoFe_2O_4 sample, are shown in Fig. 2. The Rietveld refinement confirms the purity of the used precursor powders, the formation of a single phase, and the high degree of crystallinity of the sample. All of the diffraction peaks can be indexed to the cubic spinel structure of CoFe_2O_4 (JCPDS card no. 22-1086). Therefore, within the resolution limit of XRD, no second phase was detected. The lattice parameters, obtained through the Rietveld analysis, of the used precursor powders were 8.361 Å and 8.080 Å with $\chi^2 = 1.17$, for $\gamma\text{-Fe}_2\text{O}_3$ and Co_3O_4 , respectively. For the CoFe_2O_4 sample the lattice parameter obtained from the Rietveld analysis was 8.391 Å with $\chi^2 = 1.13$ and the calculated value of the X-ray density was 5.27 g cm^{-3} . Both are in close agreement with 8.394 Å and 5.29 g cm^{-3} , for bulk CoFe_2O_4 .²²

The EDS spectrum (Fig. 3) of the CoFe_2O_4 nanopowder shows the presence of Co, Fe, Cu and O. One can notice that, except for peaks related to Cu, no additional peaks due to impurities appear in the EDS spectrum. Table 1 shows the concentration of elements present in the sample, from which we can observe that the ratios of the elements slightly deviate from the ideal concentration.

TEM images of the CoFe_2O_4 nanopowder are shown in Fig. 4. From the micrograph in Fig. 4(a), we can observe that the grains

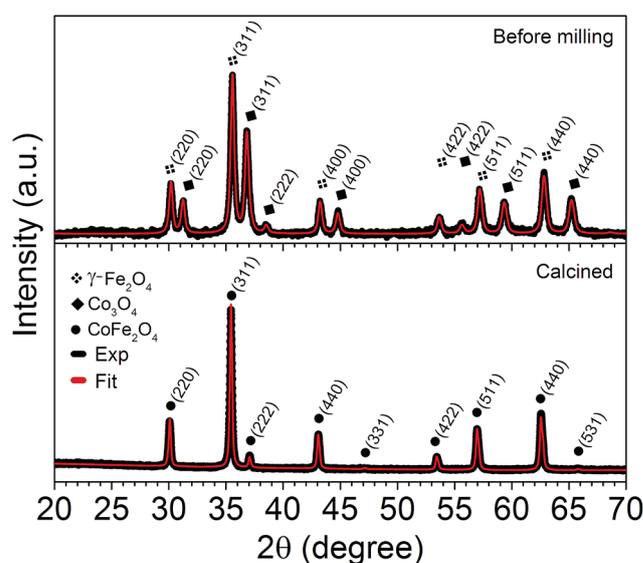


Fig. 2 The XRD patterns, including the Rietveld refinement (red solid line) of the precursor powders before milling and the CoFe_2O_4 sample indexed with the (hkl) reflections of the spinel structure.



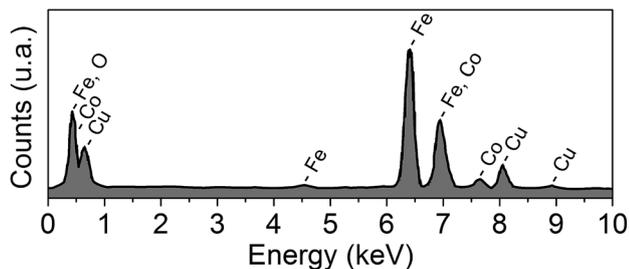



Fig. 3 The EDS spectrum of the CoFe₂O₄ nanopowder.

Table 1 Quantitative results (atom concentration) extracted from the EDS analysis of CoFe₂O₄ nanopowder


Element	Ideal (%)	Exp. (%)
Co	34.53	32.82
Fe	65.47	67.18

consist of agglomerates, with shapes that are not well defined, of nanoparticles without the presence of pores or fractures. The particle morphology is strongly affected by the ball milling process, which provides various shapes of nanoparticles during ferrite formation.^{23,24} The average grain size diameter (d_m) is determined from the histogram size, shown in Fig. 4(b), using a log-normal distribution function. The parameters obtained from the fit (black solid line) were $d_m = 57$ nm and $\sigma = 0.291$. Furthermore, the image in Fig. 4(c) clearly shows fringes separated by 0.294 nm, corresponding to the (220) crystalline planes of the CoFe₂O₄ spinel structure. In addition, in this figure, we can observe that the particles have well-ordered crystalline planes that extend to the particle boundaries. This makes us conclude that surface effects, such as an amorphous layer or second phases, are not present in our sample. The SAED pattern of the sample is shown in Fig. 4(d). According to this diffraction pattern, the measured lattice constant and the interplanar spacing (d_{hkl}) are in agreement with those calculated from XRD analysis.


⁵⁷Fe Mössbauer spectroscopy was performed at 12 K to determine the cation distribution in the CoFe₂O₄ structure. Fig. 5 depicts the Mössbauer spectrum of the precursor; a single

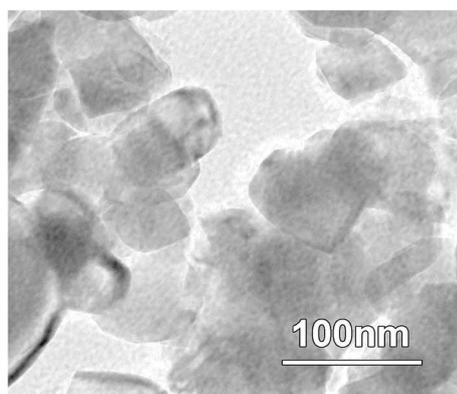


(a)

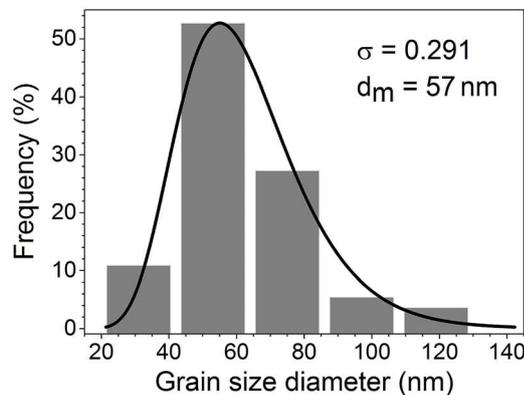

(b)

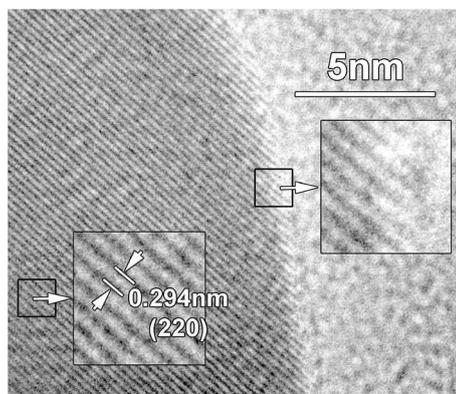

(c)

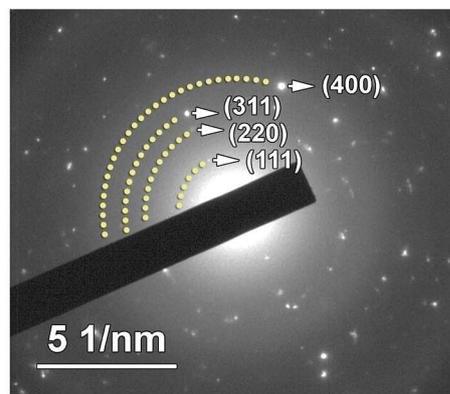

(d)

Fig. 4 (a) The TEM image of the particles, (b) the grain size histogram from 60 counts of the TEM image and the log-normal curve fitting (black solid line), (c) the TEM image with the magnified details of fringes corresponding to the (220) crystalline planes, and (d) the SAED image of the CoFe₂O₄ sample.



sixtets was used to fit the spectrum and the calculated hyperfine parameters were in close agreement with the γ - Fe_2O_4 phase.²⁵ The Mössbauer spectrum of the calcined sample shows a single-phase and magnetically blocked sample with a two-site pattern, indicating the presence of Fe located in tetrahedral (A) and octahedral (B) sites. These components were fitted to a sextet and to a distribution of hyperfine magnetic field sextets, respectively. The hyperfine parameters obtained from the fits are in close agreement with results reported by Morrish²⁶ and they indicate the presence of only Fe^{3+} . The average hyperfine magnetic field, $\langle H_{\text{Hf}} \rangle = 54$ T, for Fe at B-sites that is obtained from the fits is larger than the hyperfine field at A-sites ($H_{\text{Hf}} = 49$ T), as already reported. We have not observed any component related to a superparamagnetic phase or a second phase such as hematite or Fe oxy(hydroxide). These results are in agreement with the X-ray diffraction study. The chemical formula unit of the cobalt ferrites, $(\text{Co}_{1-i}^{2+}\text{Fe}_i^{3+})[\text{Co}_i^{2+}\text{Fe}_{2-i}^{3+}]\text{O}_4$, can be determined from the degree of inversion parameter (i), which is defined as the fraction of Fe cations occupying tetrahedral sites. In the ferrite formula, cations enclosed in rounded and squared brackets are ions at the A and B sites, respectively. Ferrites are completely inverted when $i = 1$, partially inverted when $0 < i < 1$, and normal spinel when $i = 0$. The degree of inversion can be calculated from the ratio of the relative absorption areas (RAAs); thus $\text{RAA (A)}/\text{RAA (B)} = f_{\text{A}}/f_{\text{B}} \cdot i/(2 - i)$, where $f_{\text{A}}/f_{\text{B}}$ is the ratio of the recoilless fraction between tetrahedral and octahedral sites. At 5 K, the ratio $f_{\text{B}}/f_{\text{A}}$ is equal to 0.96.²⁷ By assuming that $f_{\text{A}}/f_{\text{B}}$ at 12 K is similar to the value determined at 5 K, we have determined the inversion parameter of $i = 0.88$, and therefore, the distribution of cations will be $(\text{Co}_{0.12}^{2+}\text{Fe}_{0.88}^{3+})[\text{Co}_{0.88}^{2+}\text{Fe}_{1.12}^{3+}]\text{O}_4$.

The surface chemical bonding states of the CoFe_2O_4 spinel oxide sample were characterized using XPS analysis. Three typical signals of the O 1s, Fe 2p and Co 2p core levels were detected from the survey scan plotted in Fig. 6. The high resolution spectrum of adventitious C 1s (284.6 eV) was used as the

reference for the calibration of the binding energies of different elements. We have assumed in the fitting process that Fe and Co atoms occupy tetrahedral and octahedral sites based on XRD and Mössbauer spectra previously shown.

The high-resolution Fe 2p spectrum shown in Fig. 7 is composed of two spin-orbit doublets that are characteristic of Fe 2p_{3/2} (709.65 eV, Fe^{3+} in B-sites and 711.55 eV, Fe^{3+} in A-sites) and Fe 2p_{1/2} (723.08 eV, Fe^{3+} in B-sites and 725.73 eV, Fe^{3+} in A-sites) and the corresponding shake-up satellites (714.02, 718.57, 731.67, and 734.40 eV).^{28,29} However, the peak positions of the Fe 2p_{3/2} sub-spectra corresponding to Fe^{3+} in B-sites and its satellite coincide with the peak positions expected for Fe^{2+} , *i.e.*, 709.7 eV and 714.5 eV, respectively. Similarly, the binding energies of Fe^{2+} (2p_{1/2}) and its satellite (723.3 and 730.1 eV)³⁰ coincide with those corresponding to Fe^{3+} (2p_{1/2}) in B-sites and its satellite. Therefore, the octahedral sites could be occupied either by Fe^{2+} or Fe^{3+} cations.

The high-resolution Co 2p spectrum, depicted in Fig. 8, suggests the presence of Co^{2+} cations. This spectrum consists of two spin-orbit doublets Co 2p_{3/2} (779.40 eV, Co^{2+} in B-sites and 781.64 eV, Co^{2+} in A-sites) and Co 2p_{1/2} (794.95 eV, Co^{2+} in B-sites and 796.32 eV, Co^{2+} in A-sites) and the corresponding shake-up satellites (784.80, 718.57, 801.77, and 803.77 eV).^{28,29} Co^{3+} occupying octahedral and tetrahedral sites is expected to exhibit peaks centered at 783.3 eV and 798.5 eV, respectively (see the dashed arrows in Fig. 8). Note that the high-resolution spectrum obtained for Co 2p does not exhibit a defined peak around the Co^{3+} A-site position (798.5 eV). Therefore, it can be concluded that only Co^{2+} species are present in this sample. These results are complementary to those obtained by XRD and Mössbauer spectroscopy and supports the interpretation that the peaks observed in Fig. 7 are due to Fe^{3+} in tetrahedral and octahedral sites. Hence, only Fe^{3+} is present in this sample.

The Fe and Co 2p and shake-up satellite peaks confirmed the Fe and Co oxidation states inside the prepared CoFe_2O_4 nanopowder. These results demonstrate that the surface of the CoFe_2O_4 nanopowder has a composition containing Fe^{3+} and Co^{2+} species characteristic of the CoFe_2O_4 and indicate, in addition, the presence of Fe and Co in the octahedral and tetrahedral sites. Area peaks analysis revealed an inversion parameter of $i = 0.94$.

5.2 Magnetic analysis

Before performing an analysis of the experimental magnetic data, let us describe the theoretical approach employed in this work.

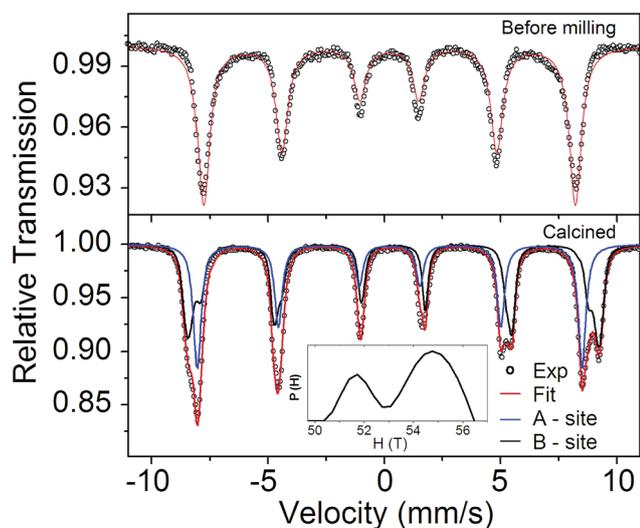


Fig. 5 Mössbauer spectra recorded at 12 K for the before milling precursor and calcined powders. The inset is the histogram for the hyperfine magnetic field distribution for Fe at B-sites.

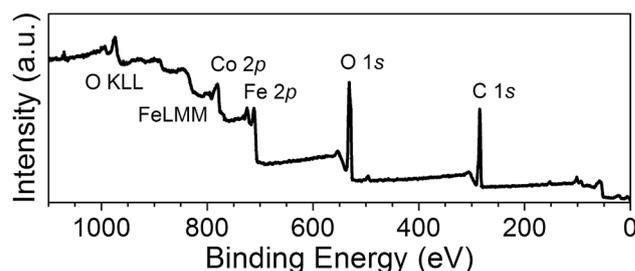


Fig. 6 XPS survey spectrum of the CoFe_2O_4 nanopowder.



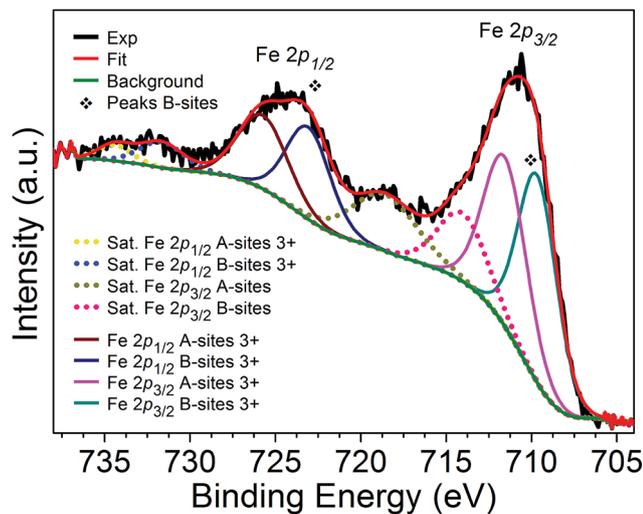


Fig. 7 XPS high resolution spectrum of Fe 2p of the CoFe_2O_4 nanopowder. Dashed lines correspond to shake-up satellite peaks.

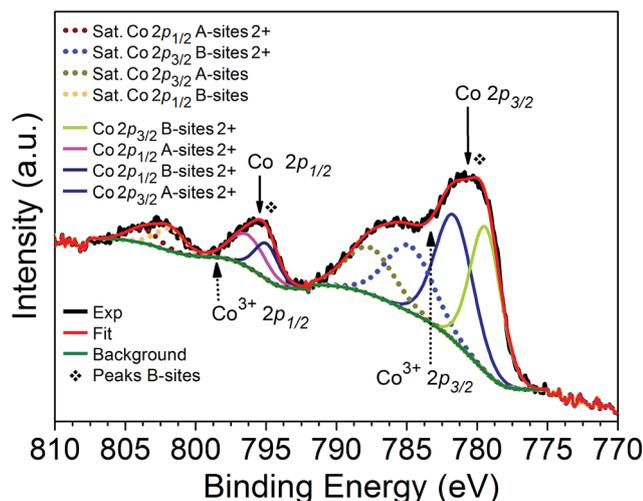


Fig. 8 XPS high resolution spectra of Co 2p of the CoFe_2O_4 nanopowder. Dashed arrows indicate the expected values²⁹ of the binding energies of the Co^{3+} species in octahedral (783.3 eV) and tetrahedral sites (798.5 eV). Dashed lines correspond to shake-up satellite peaks.

A topic of interest in the literature is the study of the roles of the dipolar interaction and magneto-crystalline anisotropy in influencing the magnetic properties of the system. In this regard, we study the influence of the dipolar field in granular systems presenting an easy-plane magneto-crystalline anisotropy using numerical simulations. Bearing this motivation in mind, we have performed numerical simulations of granular systems presenting easy-plane magneto-crystalline anisotropy with $K_1 > 0$ and $a = 0$. The results for $N = 2000$ particles, $\sigma = 0.3$, and different values of c/c_0 are depicted in Fig. 9. Our results indicate that, as the dipolar field increases (by decreasing c_0 and keeping c fixed), the so-called wasp-waisted hysteresis loop is produced.

Now, we present the experimental results of static magnetic hysteresis for our CoFe_2O_4 sample at a low temperature ($T = 5$

K). We must emphasize that our sample simply *does not fit into any* of the previously depicted scenarios, although it presents a wasp-waisted hysteresis loop (see Fig. 10(a)). For example, from the XRD data, only a single crystalline phase, namely a spinel structure, is observed. Additionally, the TEM images and EDS analysis show a high-purity CoFe_2O_4 compound, with cation concentrations slightly deviating from the theoretical stoichiometry, discarding the existence of other magnetic phases. The TEM images also show a set of ordered crystalline planes, which extend to the surface of the particles, thus resulting in negligible surface effects. The Mössbauer spectroscopy results show an inverse spinel parameter of $i = 0.88$, which means that there is no competition between AFM and FM coexisting magnetic ordered phases in the spinel structure, contrary to what was observed by Rahman *et al.*³ XPS analysis provides further characterization confirming the presence of only Co^{2+} and Fe^{3+} cations in the sample, compatible to the single-phase CoFe_2O_4 spinel structure and, besides, area peak analysis indicates an inversion parameter close to that which was found by Mössbauer spectroscopy ($i = 0.94$). The spin re-orientation at a low temperature being due to canted spins on the surface of the nanoparticles is very improbable because the surface/volume ratio of our particles is very small. The present scenario of a mixture of multi-domain and single-domain particles is not discarded; however, the high experimental squareness ($m_r = M_r/M(H_{\max}) = 0.79$) makes a dominant multi-domain phase leading to the wasp-waisted behavior of magnetization unlikely. A pure multi-domain phase system should exhibit a very low squareness compared to the single-domain phase.² In this regard, it is likely that a residual multi-domain phase will favor a smaller coercivity field value.

In Fig. 10(b), we show theoretical results for the reduced magnetic hysteresis. We performed a numerical simulation with 2000 particles, where $c/c_0 = 3.5 \times 10^{-5}$, $a = -0.7$, and $\sigma = 0.3$. The squareness and reduced coercivity are $m_r = 0.703$ and $h_c = 0.108$, respectively. If we compare with the experimental

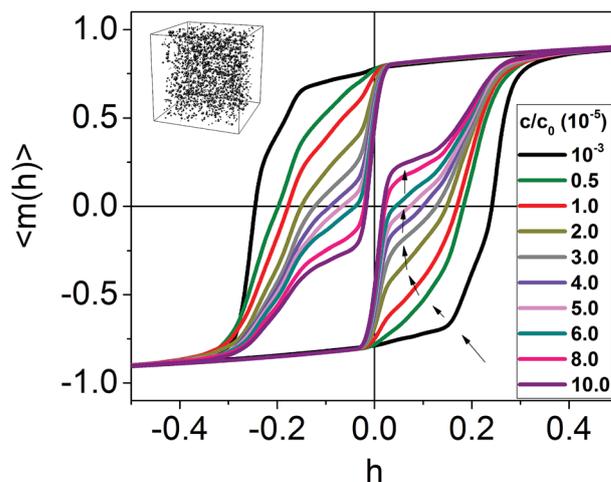


Fig. 9 Reduced magnetic hysteresis curves for different values of c/c_0 , with $N = 2000$ and $\sigma = 0.3$. The black arrows indicate the formation of "jumps" in the reduced hysteresis as c/c_0 increases.



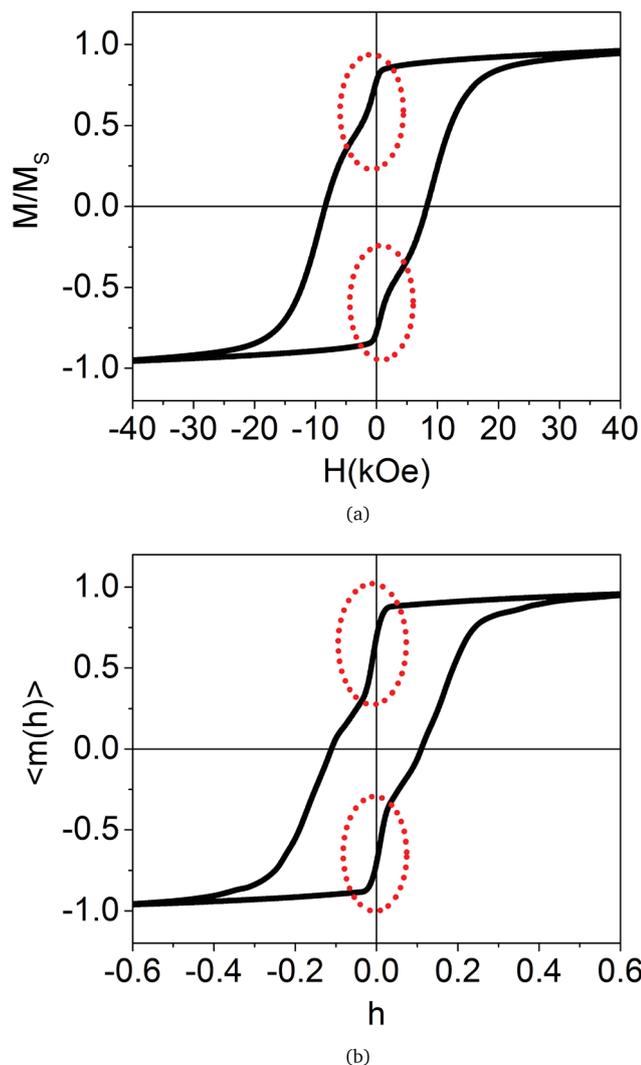


Fig. 10 (a) Experimental results for the isothermal magnetic hysteresis of CoFe_2O_4 ($T = 5$ K) and (b) the theoretical results. The red dots represent the region of curves in which the magnetization abruptly changes.

data, we obtain $M_s = 89.30 \text{ emu g}^{-1}$, which is close to the bulk value of CoFe_2O_4 .³¹ This supports the argument that surface effects are not relevant in our sample. Since we use $c = 10^{-2}$, corresponding to $c_0 = 285.71$, the anisotropic field $H_{k_1} = 134.4 \text{ kOe}$, and consequently, $K_1 = 3.16 \times 10^7 \text{ erg per cm}^3$ and $K_2 = -2.21 \times 10^7 \text{ erg per cm}^3$. Both values of the anisotropy constants are compatible with experimental values of similar samples produced by other methods and those determined from the law of approach to saturation.^{32,33} From H_{k_1} , we can calculate the coercivity using $H_c = h_c H_{k_1}$, which gives $H_c = 14.5 \text{ kOe}$. This theoretical value is larger than the experimental result obtained in the present work, which is $H_c = 8.4 \text{ kOe}$. This may be the effect of a residual multi-domain phase, which tends to reduce the coercivity values.² We must note an interesting implication about the magneto-crystalline configuration adopted in our model. The fact that the *uniaxial* symmetry corroborates with the experiment indicates that our sample exhibits,

at 5 K, a structure deviating from *cubic* symmetry. This result is in agreement with the tetragonal symmetry previously reported for cobalt ferrite.^{34,35}

To obtain greater insight into the origin of the wasp-waisted hysteresis loop, we determine, from our model, the number of switched magnetic moments (SMMs) as a function of the reduced applied magnetic field h , *i.e.*, we plot a histogram of the number of flipped magnetic moments for each value of the reduced applied magnetic field. In Fig. 11(a) (top), we show the results for the experimental isothermal magnetic susceptibility. We can clearly observe the presence of two peaks, instead of the usual single-peak pattern, indicating that our sample presents two switching field distributions centered at approximately $H = 0.63 \text{ kOe}$ (first peak) and $H = 9.10 \text{ kOe}$ (second peak). In Fig. 11(a) (middle), we present the theoretical plot of SMMs as a function of h . We can see that the SMMs present a behavior that is quite similar to the experimental susceptibility, with a two-peak pattern. This result is obtained from the combination of the dipolar field/concentration ratio and the easy-plane anisotropy, which originates from the two well-defined switching field distributions. In Fig. 11(a) (bottom), we present the plot of the SMMs as a function of h , but with $c/c_0 = 10^{-8}$. We can infer from Fig. 11(a) (bottom) that the absence of the dipolar field destroys the two-peak pattern, and the usual single-peak pattern is recovered. We conclude that the double-peak pattern is a signature of the easy-plane anisotropy and dipolar field interaction.

Fig. 11(b) and (c) show the polar distribution of θ_u related to the particles that were flipped around the peaks shown in Fig. 11(a). The polar distribution of SMMs around the first peak (solid blue line) is illustrated in Fig. 11(b). We can observe that the main contribution for the first peak comes from the particles with $\theta_u \approx \pi/4$ and $\theta_u \approx 3\pi/4$. The polar distribution of SMMs around the second peak (solid red line) is illustrated in Fig. 11(c). Now, the main contribution for the second peak comes from the particles with $\theta_u \approx \pi/2$.

Therefore, even with the same anisotropy constant, the combination of the dipolar field and easy-plane configuration leads to a wasp-waisted-like magnetic hysteresis loop by creating two well-defined peaks in the switching field distribution. In contrast to the work of Chithra *et al.*,⁴ our sample does not present two types of particles with different magnetic anisotropies, and this is well established by the structural and magnetic characterization previously described. Chithra *et al.* studied samples with higher values of coercivity ($H_c = 18.69 \text{ kOe}$ at $T = 10 \text{ K}$) than our sample and an average grain size of $\sim 22 \text{ nm}$. In this case, this average grain size indicates that the nanoparticles are almost entirely in a single-domain structure. This is compatible with our simulations and interpretation. Since we only consider the single-domain phase, the theoretical result for the coercivity is higher than experimental one; our sample still presents a residual multi-domain phase due to the average grain size of $\sim 57 \text{ nm}$ which tends to diminish the coercivity.

Let us investigate the trajectory of a particular magnetic moment in two specific cases: (i) $c/c_0 = 3.5 \times 10^{-5}$ (theoretical result in agreement with the experimental results) and (ii) $c/c_0 =$



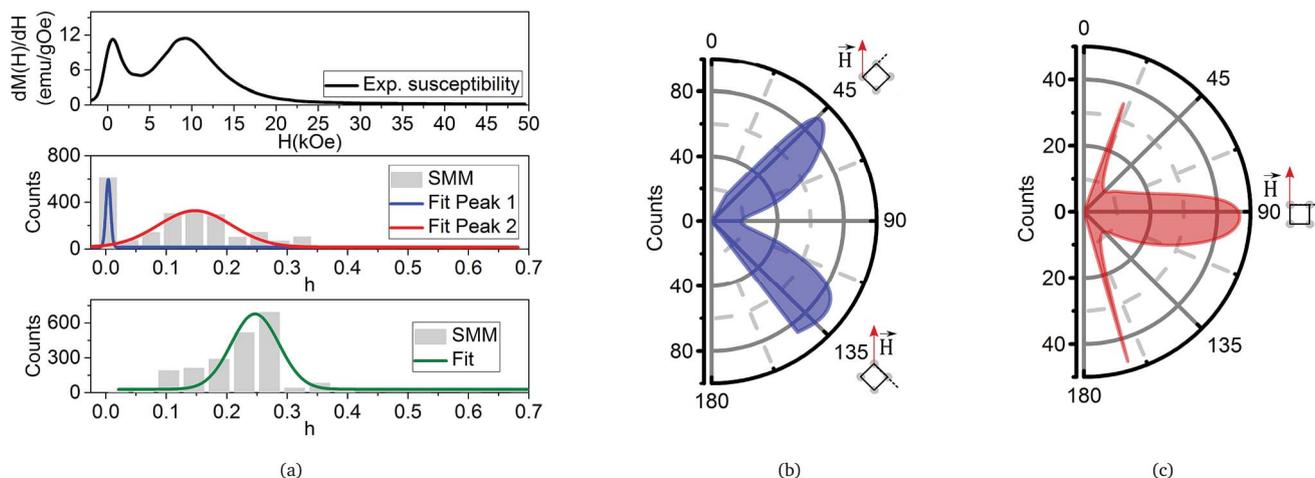


Fig. 11 In (a) (top), we show the experimental isothermal susceptibility $\frac{dM(H)}{dH}$, (middle) the SMM histogram for the simulation with $c/c_0 = 3.5 \times 10^{-5}$ showing the two-peak fits of the histogram, and (bottom) the SMM histogram for a very diluted sample with $c/c_0 = 10^{-8}$ (very weak dipolar interactions) showing only one peak. In (b), we show a polar distribution of SMMs around peak 1 and (c) the polar distribution of SMMs around peak 2.

10^{-8} , corresponding to a very diluted case (no dipolar interaction). Let us take, for example, a particle with $\theta_u = 44.93^\circ$ and $\phi_u = 84.24^\circ$ around the center of the simulation box. In Fig. 12(a) and (c), we have the reduced magnetic hysteresis loop for $c/c_0 = 10^{-8}$ and $c/c_0 = 3.5 \times 10^{-5}$, respectively. We clearly observe a strong reduction in coercivity h_c , from the first case to the second case, due to the presence of the dipolar field. To facilitate the visualization of the changes in the magnetization orientation, we labeled a few steps along the low branch of the hysteresis loop in the interval from $-h_{\text{sat}}$ to h_{sat} in Fig. 12(b) (zero dipolar field) and 12(d) (dipolar field). The reduced coercivity decreases from 0.226 to 0.047. If we consider $H_{k_1} = 134.4$ kOe (obtained from the numerical calculation), we obtain the corresponding coercivities 30.3 kOe and 6.31 kOe, respectively. We may interpret this huge reduction in the coercivity as a consequence of the symmetry and degeneracy of the easy-

plane anisotropy. In contrast to easy-axis symmetry, which has only one direction of equilibrium and where the transition over the surface of the energy is attenuated, easy-plane symmetry presents a plane of equilibrium orientation of the magnetization, and the transition over the surface of energy is facilitated. The blue ellipses indicated in Fig. 12(a) and (b) show the path of the magnetization that was suppressed by the dipolar field.

6 Conclusions

We have shown that the magnetization of easy-plane anisotropy single-domain particles that are affected by dipolar interactions has a field dependence in a wasp-waisted-like hysteresis curve. The number of switched magnetic particles as a function of the field indicated that the easy-plane anisotropy and dipolar interaction favor two switching fields, and these are related to

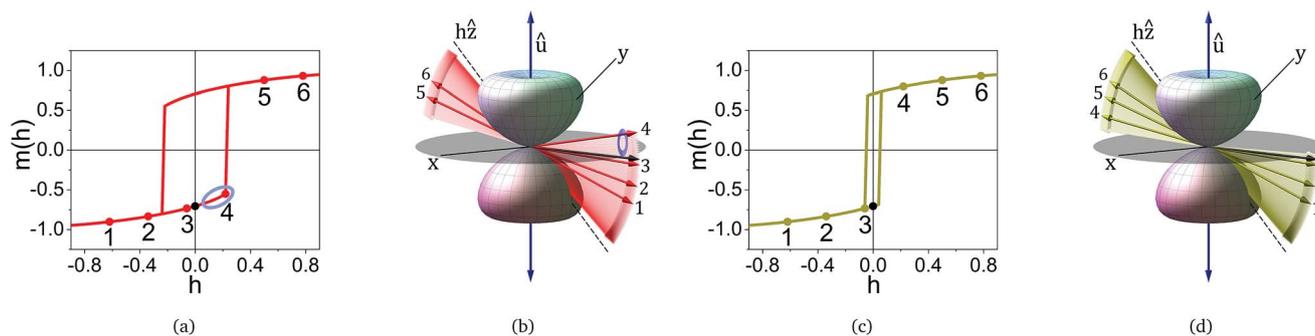


Fig. 12 In (a) and (c), the reduced hysteresis curves of the chosen nanoparticle for the very diluted case (red solid line and $c/c_0 = 10^{-8}$) and the simulation proposed for the experimental data (olive solid curve and $c/c_0 = 3.5 \times 10^{-5}$), respectively, are presented. In (b) and (d), we present the trajectory of the magnetization for the very diluted case and the simulation proposed for the experimental data, respectively. The stages of equilibrium orientation of the magnetization are labeled 1–6 in (b) and (d), and their respective values of reduced magnetization are given in (a) and (c). The black arrow indicates the stage at $h = 0$. The dashed black line indicates the direction of the applied field, and the double blue arrow indicates the crystallographic orientation. The colored rounded surfaces depict the anisotropic energy surface for sign (K_1) positive, $a = -0.7$, and the gray disc depicts the easy-plane anisotropy.



the particle concentration. Choosing a particular nanoparticle and comparing the very diluted case with $c/c_0 = 3.5 \times 10^{-5}$ we note a strong decrease in coercivity. These results presented trends that are in agreement with the experimental magnetization curves from cobalt ferrite prepared using annealed ball-milled nanoparticles. The proposed physical model is suitable for explaining the wasp-waisted behavior of magnetic hysteresis curves.

Acknowledgements

The authors thank the national agencies CAPES, CNPq, and INCT of Space Studies for financial support.

References

- 1 P. J. Wasilewski, *Earth Planet. Sci. Lett.*, 1973, **20**, 67.
- 2 A. P. Roberts, *et al.*, *J. Geophys. Res.: Solid Earth*, 1995, **100**, 17909.
- 3 A. U. Rahman, *et al.*, *J. Nanopart. Res.*, 2014, **16**, 1.
- 4 M. Chithra, *et al.*, *J. Magn. Magn. Mater.*, 2016, **401**, 1.
- 5 Q. Song and Z. J. Zhang, *J. Am. Chem. Soc.*, 2012, **134**, 10182.
- 6 J. Fu, *et al.*, *Nanoscale*, 2012, **4**, 3932.
- 7 Z. Zhang, *et al.*, *Adv. Mater.*, 2005, **17**, 1415–1419.
- 8 Z. Wang, *et al.*, *J. Phys. Chem. C*, 2008, **112**, 15171.
- 9 S. T. Xu, *et al.*, *Nanoscale*, 2015, **7**, 6520.
- 10 D. C. Lee, *et al.*, *J. Phys. Chem. B*, 2006, **110**, 11160.
- 11 M. Woińska, *et al.*, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 2013, **88**, 144421.
- 12 M. El-Hilo, *et al.*, *J. Appl. Phys.*, 1998, **84**, 5114.
- 13 J. Garcia-Otero, *et al.*, *J. Appl. Phys.*, 2000, **87**, 7376.
- 14 J. Garcia-Otero, *et al.*, *Phys. Rev. Lett.*, 2000, **84**, 167.
- 15 D. Kechrakos and K. N. Trohidou, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 1998, **58**, 12169.
- 16 H. T. Yang, *et al.*, *Appl. Phys. Lett.*, 2011, **98**, 153112.
- 17 B. D. Cullity and S. R. Stock, *Elements of X-ray diffraction*, Prentice Hall, 2001.
- 18 M. Getzlaff, *Fundamentals of Magnetism*, Springer, Berlin, Heidelberg, 2007.
- 19 V. Schaller, *et al.*, *J. Magn. Magn. Mater.*, 2009, **321**, 1400.
- 20 Z. Mao, *et al.*, *J. Magn. Magn. Mater.*, 2008, **320**, 2335.
- 21 V. Russier, *J. Appl. Phys.*, 2001, **89**, 1287.
- 22 B. D. Cullity and C. D. Graham, *Introduction to magnetic materials*, Wiley-IEEE Press, 2008.
- 23 C. Suryanarayana, *Prog. Mater. Sci.*, 2001, **46**, 1.
- 24 L. Kumar, *et al.*, *Int. Nano Lett.*, 2013, **3**, 1.
- 25 R. M. Cornell and U. Schwertmann, *The Iron Oxides*, Wiley-VCH, 2nd edn, 2003.
- 26 G. A. Sawatzky, *et al.*, *Phys. Rev.*, 1969, **187**, 747.
- 27 R. W. Grant, *et al.*, *J. Appl. Phys.*, 1967, **38**, 1455.
- 28 Z. Zhou, *et al.*, *Appl. Surf. Sci.*, 2008, **254**, 6972.
- 29 T.-C. Lin, *et al.*, *Appl. Surf. Sci.*, 1997, **119**, 83.
- 30 A. Demund, *et al.*, *Surf. Interface Anal.*, 2008, **40**, 27.
- 31 J. Smit and H. P. J. Wijn, *Ferrites*, Philips' Technical Library, 1959.
- 32 Y. Melikhov, *et al.*, *J. Appl. Phys.*, 2006, **99**, 08R102.
- 33 B. G. Toksha, *et al.*, *Solid State Commun.*, 2008, **147**, 479.
- 34 H. P. Rooksby and B. T. M. Willis, *Nature*, 1953, **172**, 1054.
- 35 S. Yang and X. Ren, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 2008, **77**, 014407.

