

CrossMark
click for updatesCite this: *RSC Adv.*, 2017, 7, 10570

Synthesis and physical properties of triphenylamine-functionalized twistacenes: blue-emitting fluorophores†

Jingdan Duan,^a Huahang Pan,^a Changting Wei,^b Jinchong Xiao,^{*a} Guixia Zhai^a and Wenming Su^{*b}

Received 29th December 2016

Accepted 29th January 2017

DOI: 10.1039/c6ra28814f

rsc.li/rsc-advances

Two novel triphenylamine-decorated twistacenes **SNPy** and **DNPY** have been synthesized and characterized. Both of them display bright blue luminescence with high quantum yields in dichloromethane and as thin films. Based on the TGA analyses, they present high thermal stability up to 385 °C and 450 °C, respectively. The fabricated electroluminescent devices using the resulting twistacenes as emitters show blue luminescence of 2856 cd m⁻² for **SNPy** and 4116 cd m⁻² for **DNPY**.


Introduction

As one of the most appealing branches of organic electronics, organic light emitting diodes (OLEDs) are a subject of considerable investigation in recent decades due to their potential applications in full color flat panel displays and solid state lighting.^{1–5} Compared with their inorganic counterparts, organic π -conjugated compounds display many advantages. In general, these organic molecules consist of many kinds of interesting molecular structures, which is beneficial for rationally and precisely tuning their physical properties.⁶ In some cases, this can provide more room to approach high electroluminescent performance in molecular level and supramolecular level.^{7–12} In addition, detailing intensively the optoelectronic behaviors can uncover some new phenomena. For example, the recent reported thermally activated delayed fluorescence (TADF) has received much attention because the exceptional high theoretical internal quantum efficiency of 100% might be fully used in OLEDs.^{13,14} By using an aggregation-induced emission (AIE) concept, highly fluorescent materials could be prepared through modifying the AIE moiety with other functional groups, where the as-formed novel molecules were utilized as active layers in nondoped OLEDs and fluorescent sensors for biomolecules with high specificity.^{15–18} Thus, the preparation of efficient luminescent materials has received a growing interest in scientific and technological opinions at present. Indeed,

since stable blue emitters play a crucial role in next-generation displays, how to design and synthesize these prototypes is still an urgent issue and a challenge.

Twistacenes, as a family of polycyclic aromatic hydrocarbons, usually refer to sterically encumbered acenes, which can be tracked back to last century.^{19–22} In 1987, Pascal and co-workers synthesized several linear polycyclic aromatic hydrocarbons showing exceptional nonplanar deformations.²³ These molecules were subsequently named as twisted acenes that exhibited highly stable and antioxidation than unsubstituted acenes. Wudl, Zhang and Pérez groups prepared in succession a series of symmetric and unsymmetric twistacenes containing pyrene unit in the terminal.^{24–31} More interesting, the resulting compounds can suppress the stacking interaction in the solid state to a certain extent, which were utilized as emitters in electroluminescent devices. Recently, in our group, some substituted twistacenes consisting of heterocycles and five-membered all-carbon rings replacing six-membered rings were designed and synthesized that displayed appealing electroluminescent performance and nonlinear optical properties.^{32–40}

In the continuous work, herein we have synthesized two novel triphenylamine-modified twistacenes **SNPy** and **DNPY** (Scheme 1). Triphenylamine presenting three-dimensional

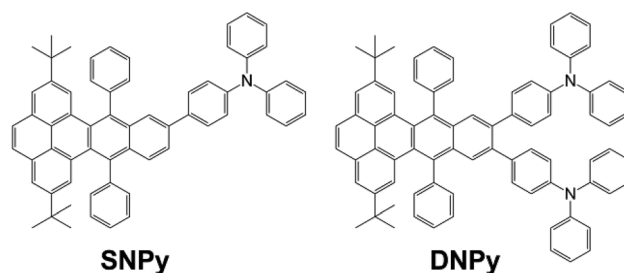

Scheme 1 Molecular structures of **SNPy** and **DNPY**.

^aCollege of Chemistry and Environmental Science, Key Laboratory of Chemical Biology of Hebei Province, Hebei University, Baoding 071002, P. R. China. E-mail: jcxiaoc@163.com

^bPrintable Electronics Research Centre, Suzhou Institute of Nanotech and Nanobionics, Chinese Academy of Sciences, Suzhou 215123, P. R. China. E-mail: wmsu2008@sinano.ac.cn

† Electronic supplementary information (ESI) available: TGA data, additional copies of FT-IR, ¹H, ¹³C NMR spectra and mass spectroscopy. See DOI: 10.1039/c6ra28814f

architecture could be decorated with different π -conjugated systems. The as-resulting compounds showed isotropic optical and charge-transport properties and could be used in electroluminescent materials, organic field effect transistor and photovoltaic conversion.^{41–44} As expected, the motif in the molecular design might improve the hole transporting behavior, decrease the stacking interaction and fluorescence quenching to some extent. Molecules **SNPy** and **DNPy** emitted strong blue light in dichloromethane and solid state. The fabricated electronic devices based on them exhibited fascinating electroluminescent performance.

Results and discussion

The synthetic procedure of **SNPy** and **DNPy** is depicted in Scheme 2. Molecules **2** and **3** were obtained according to the reported methods in our laboratory.^{32,34} Compounds **SNPy** (91%) and **DNPy** (86%) were successfully synthesized by a straightforward Suzuki coupling reactions between 4-(diphenylamino)phenylboronic acid (**1**) and **2/3** with $\text{Pd}(\text{PPh}_3)_4$ as catalyst. The formed molecules were characterized by melting points, FT-IR, ^1H NMR, ^{13}C NMR spectroscopy and MALDI-TOF mass spectroscopy. In addition, both of them can be dissolved in the common solvents such as dichloromethane, chloroform, toluene and THF. Thermogravimetric analysis (TGA) guaranteed their thermal stability (5% weight loss) to 385 °C for **SNPy** and 450 °C for **DNPy**, respectively, in nitrogen atmosphere (Fig. S1†).

The optical properties of compounds **SNPy** and **DNPy** were investigated in dilute dichloromethane solution (1×10^{-5} M) and in thin films. As shown in Fig. 1a and Table 1, molecules **SNPy** and **DNPy** in dichloromethane presented similar profile with broad featureless absorption bands. The maximum absorption peaks at 357 nm originated from the π - π^*


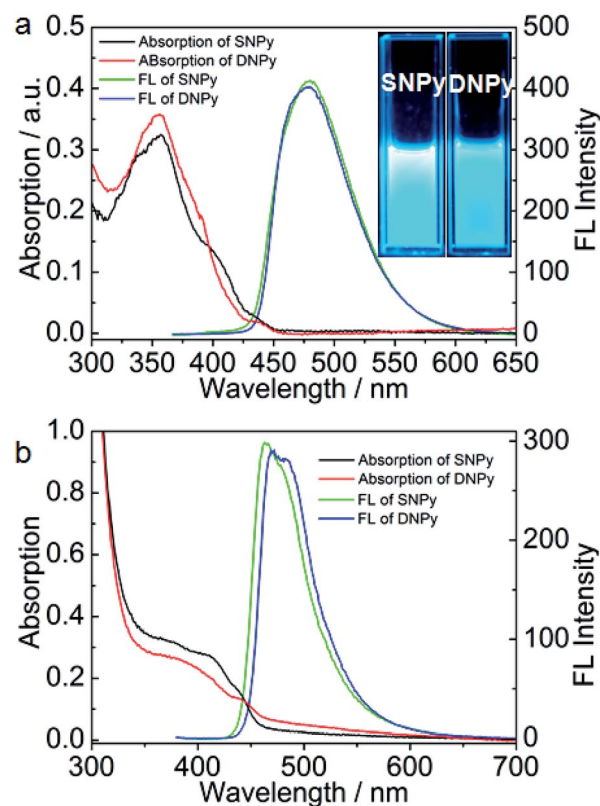


Fig. 1 UV-Vis absorption and fluorescence spectra of **SNPy** and **DNPy** in dichloromethane (a) and in thin film (b). Inset: the fluorescence image.

Table 1 Physical properties of molecules **SNPy** and **DNPy**

	SNPy	DNPy
Abs ^a /nm	357/400	357/390
PL ^a /nm	479	479
Φ_f	0.66	0.36
$E_{1/2}^{OX}$	0.46/0.83	0.45/0.90
HOMO [eV]	−5.26	−5.25
LUMO [eV]	−2.32	−2.38
Band gap ^b [eV]	2.94	2.87

^a In CH_2Cl_2 . ^b Obtained from the onset of the UV-Vis data.

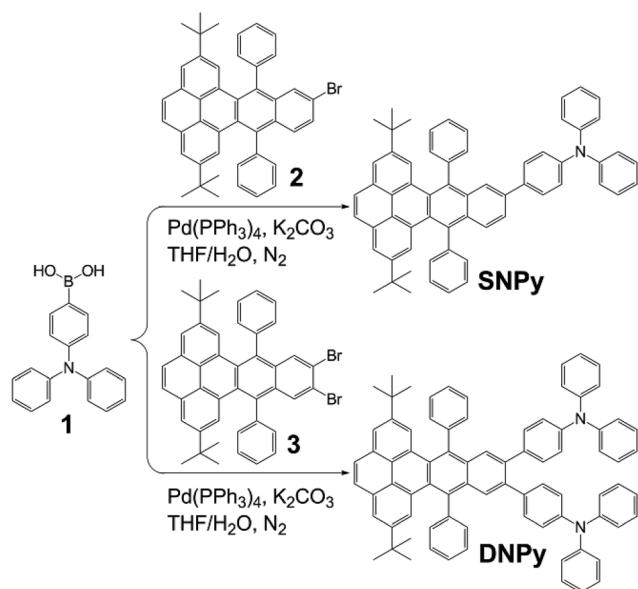

Scheme 2 Synthetic route to compounds **SNPy** and **DNPy**.

transitions of the skeleton. Note that **SNPy** exhibited a shoulder peak at 400 nm and **DNPy** presented the shoulder peak at 390 nm. When excited at 357 nm, both of them emitted strong blue light centered at 479 nm with the quantum yields (Φ_f) of 0.66 for **SNPy** and 0.36 for **DNPy**, respectively, using 9,10-diphenylanthracene ($\Phi_f = 0.95$) as a standard.³² Additionally, the optical energy gaps (E_g) calculated from the absorption edges in solution state are almost the same, which are 2.94 and 2.87 eV, respectively. The spectra of **SNPy** and **DNPy** in solid state also showed similar broad absorption, which might be assigned to the interaction between single molecules in the densely packed film. Their corresponding emission spectra exhibited negligible changes compared with those in dichloromethane. It should be pointed out that the full width at half



maxima of **SNPy**/**DNP**y in thin films are smaller than those in dichloromethane, inferring that such twisted structure was beneficial for suppressing the intermolecular interaction in large part.

The electrochemical behaviors of compounds **SNPy** and **DNP**y were studied in a three-electrode electrochemical cell with tetrabutyl ammonium hexafluorophosphate (Bu_4NPF_6 , 0.1 M) as electrode and the results are shown in Fig. 2 and Table 1. Note that the potentials are corrected against Fc/Fc^+ . Compounds **SNPy** and **DNP**y exhibit two reversible oxidation potentials ($E_{\text{onset}}^{\text{ox}}$) at 0.46 V/0.83 V for **SNPy** and 0.45 V/0.90 V for **DNP**y, respectively. These data mean that the first oxidation process results from the oxidation of amine units and the second belongs to the oxidation of the parent building blocks, which compared with the reported results.^{32,34–36} Notably, molecule **DNP**y displays slightly negatively oxidation waves compared to **SNPy**, being indicative of the stronger electron-donating ability. Based on the first oxidation potentials, the highest occupied molecular orbital (HOMO) energy levels were estimated to be -5.26 eV for **SNPy** and -5.25 eV for **DNP**y, respectively. Furthermore, the lowest-unoccupied molecular orbital (LUMO) energy levels of **SNPy** and **DNP**y were calculated to be -2.32 and -2.38 eV, respectively, from the HOMO levels and E_g values in solution. Accordingly, both **SNPy** and **DNP**y could be expected to be suitable candidates for blue emitters.

The organic light-emitting diodes (OLED) were fabricated to examine the electroluminescence performance for compounds **SNPy** and **DNP**y. The devices contain the following structures: ITO/TAPC (20 nm)/CBP: emitter (30 nm, x wt%)/TPBi (50 nm)/Liq (2 nm)/Al, where TAPC = 4,4'-cyclohexylidenebis[N,N -di(p -tolyl)aniline], CBP = 4,4'-di(9H-carbazol-9-yl)-1,1'-biphenyl, TPBi = 1,3,5-tris(2- N -phenylbenzimidazolyl)benzene. All the related chemical structures, device configurations, and the energy level diagrams are shown in Fig. 3. The concentrations of compounds **SNPy**/**DNP**y were tuned from 9% to 12%. Further increase of the doping concentration was helpless to enhance the electroluminescent performance.

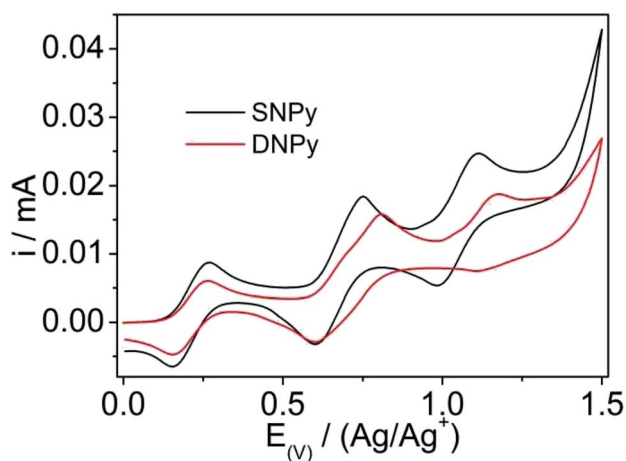


Fig. 2 Cyclic voltammogram of **SNPy** and **DNP**y in anhydrous dichloromethane containing tetrabutylammonium hexafluorophosphate (TBAPF_6). Scan rate: 50 mV s^{-1} .

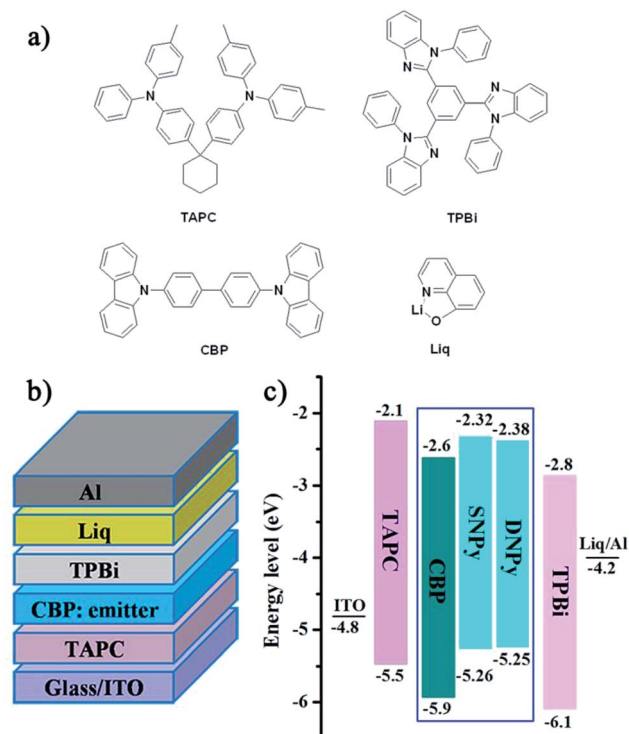


Fig. 3 (a) Chemical structures of the related materials, (b) schematic configurations and, (c) energy-level diagram.

Current density–voltage–luminance (J – V – L), current efficiency–luminance–power efficiency (CE – L – PE) and electroluminescence spectra of the resulting devices are shown in Fig. 4. Device **SNPy** turned on the low voltages (1.0 cd m^{-2}) at

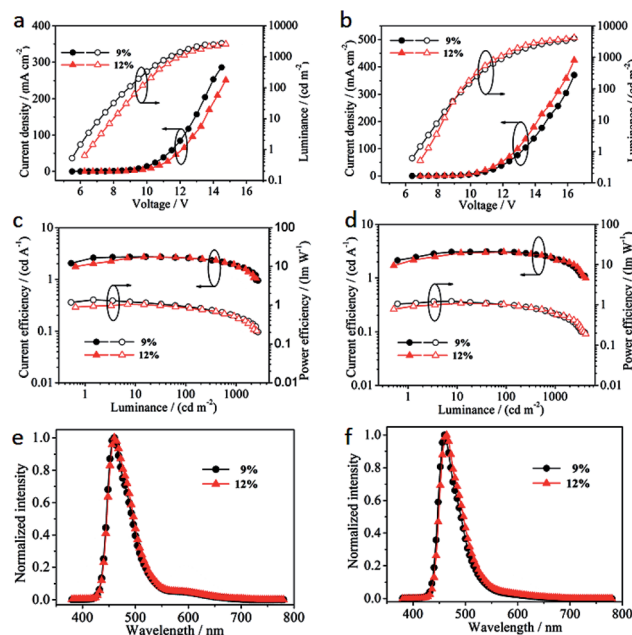


Fig. 4 J – V – L of device **SNPy** (a) and device **DNP** (b). CE – L – PE of device **SNPy** (c) and device **DNP** (d). EL spectra for device **SNPy** (e) and device **DNP** (f).



5.80 V for 9% and 6.51 V for 12%, respectively, which was smaller than those of device **DNPy** (the low voltages at 6.70 V for 9% and 7.23 V for 12%). All of the devices emitted strong blue light with the maximum brightness of 2856 cd m^{-2} at 14.6 V for **SNPy** (9%) and 4116 cd m^{-2} at 16.4 V for **DNPy** (9%). These data gained the advantage over that of 11,12-difluoro-9,14-diphenyl-dibenzo[*de,qr*]tetracene reported in our group.³⁵ However, when the doping concentrations were 12%, the brightness reduced to 2414 cd m^{-2} at 14.6 V for **SNPy** and was similar to that of **DNPy** at 16.4 V. The current density of **SNPy** is slightly higher than that of device **DNPy**, being indicative of a better charge-transport ability. Interestingly, the current efficiencies exhibited a negligible change (2.57 cd A^{-1} for **SNPy** and 3.05 cd A^{-1} for **DNPy**) as the dye concentration increased, inferring no obvious concentration quenching effect. Devices **SNPy** and **DNPy** displayed the power efficiency of 0.90 lm W^{-1} and 0.99 lm W^{-1} at 100 cd m^{-2} , respectively. In addition, the electroluminescent peaks of **SNPy** and **DNPy** were at 460 nm, which was obviously hypsochromic shift compared with those in solution and in thin film as presented in Fig. 3e and f. Considering the fluorescence quantum yields of **SNPy** and **DNPy**, device **DNPy** exhibited good hole/electron charge carrier balance. On the basis of all the experimental analyses, the doping concentration of 9% presented optimal electroluminescent performance.

Conclusions

In summary, two novel triphenylamine-modified twistacenes **SNPy** and **DNPy** were synthesized through one-step concise Suzuki coupling reaction. The effect on their optoelectronic and thermal properties have been carefully examined in a comparative manner. The electroluminescent devices using the formed twistacenes as functional layers emitted blue light with a perfect luminance. This study also demonstrates that functionalized twistacenes can be employed as an active candidates in OLED devices.

Experimental section

Device fabrication and measurements

Prior to use, the indium tin oxide (ITO) glass substrates were thoroughly cleaned with solvent and treated with oxygen plasma for 3 min. On the top of the substrates, the other layers were deposited in succession by the vacuum thermal evaporation. All of the organic materials and metal anode were deposited layer by layer under a vacuum of $5 \times 10^{-4} \text{ Pa}$. The related organic materials were used as purchased from commercial companies. The EL performances of the devices were measured with a Spectra Scan PR655 and a computer controlled Keithley 2400 Source-meter. The active device area was 4 mm^2 , and only the luminance in the forward direction was measured. The fabricated devices were performed under ambient conditions without further encapsulation.

Synthesis route

Synthesis of compound **SNPy.** A mixture of **2** (645 mg, 1 mmol), 4-(diphenylamino)phenylboronic acid (**1**, 578 mg, 2 mmol), $\text{Pd}(\text{PPh}_3)_4$ (115 mg, 0.1 mmol) and K_2CO_3 (1.1 g, 0.8 mmol) was stirred in THF/ H_2O (40 mL : 4 mL) at 85°C under nitrogen for 48 h. The cooled mixture was extracted with dichloromethane and then the collected organic phase was washed with brine, dried over Na_2SO_4 . After removing the solvent, the formed residue was purified by column chromatography (silica gel, petroleum ether) to give compound **SNPy** as a yellow solid (736 mg, 91%). Mp: $312.0\text{--}312.7^\circ\text{C}$. FT-IR (KBr): 3051, 2954, 2866, 1585, 1487, 1282, 696 cm^{-1} . ^1H NMR (600 MHz, CDCl_3 , 298 K): $\delta = 8.18$ (d, $J = 7.2 \text{ Hz}$, 2H), 8.08 (s, 1H), 7.92 (d, $J = 9.0 \text{ Hz}$, 1H), 7.86 (d, 4H), 7.72 (d, $J = 9.0 \text{ Hz}$, 1H), 7.66 (t, 4H), 7.59–7.56 (m, 4H), 7.54 (d, $J = 8.4 \text{ Hz}$, 2H), 7.50–7.46 (m, 2H), 7.30 (t, 4H), 7.16–7.14 (m, 6H), 7.07 (t, 2H), 1.13 (s, 18H). ^{13}C NMR (150 MHz, CDCl_3 , 298 K): $\delta = 147.7$, 147.3, 147.26, 147.23, 142.7, 137.2, 136.3, 136.0, 134.7, 132.5, 132.4, 131.1, 130.33, 130.32, 130.1, 129.7, 129.6, 129.5, 129.3, 127.9, 127.7, 127.6, 127.56, 127.5, 127.4, 126.9, 124.9, 124.6, 123.9, 123.88, 123.8, 123.7, 123.1, 122.2, 122.17, 34.8, 31.4. MS (MALDI-TOF): calc. for $\text{C}_{62}\text{H}_{51}\text{N}$: $[m/z]$ 809.4, found: $[m/z]$ 809.0.

Synthesis of compound **DNPy.** A mixture of **3** (363 mg, 0.5 mmol), 4-(diphenylamino)phenylboronic acid (**1**, 361 mg, 1.25 mmol), $\text{Pd}(\text{PPh}_3)_4$ (115 mg, 0.1 mmol) and K_2CO_3 (1.1 g, 0.8 mmol) was stirred in THF/ H_2O (40 mL : 4 mL) at 85°C under nitrogen for 48 h. After cooling to room temperature, brine was added to the mixture. The formed solution was extracted with dichloromethane. The collected organic phase was dried over Na_2SO_4 . After removing the solvent, the residue was purified by column chromatography (silica gel, petroleum ether) to give compound **DNPy** as a yellow solid (450 mg, 86%). Mp: $206.0\text{--}206.9^\circ\text{C}$. FT-IR (KBr): 3034, 2959, 2867, 1593, 1493, 1275, 806, 697 cm^{-1} . ^1H NMR (600 MHz, CDCl_3 , 298 K): $\delta = 8.14$ (s, 2H), 7.93 (s, 2H), 7.85 (d, $J = 5.4 \text{ Hz}$, 4H), 7.69 (d, $J = 7.2 \text{ Hz}$, 4H), 7.57 (t, $^1J = 7.8 \text{ Hz}$, $^2J = 7.2 \text{ Hz}$, 4H), 7.46 (t, $J = 7.2 \text{ Hz}$, 2H), 7.25 (t, $^1J = 7.8 \text{ Hz}$, $^2J = 7.2 \text{ Hz}$, 8H), 7.10 (d, $J = 7.8 \text{ Hz}$, 12H), 7.02 (T, $J = 7.2 \text{ Hz}$, 4H), 6.96 (d, $J = 8.4 \text{ Hz}$, 4H), 1.13 (s, 18H). ^{13}C NMR (150 MHz, CDCl_3 , 298 K): $\delta = 147.7$, 147.3, 146.3, 142.6, 138.4, 135.9, 135.8, 132.5, 131.3, 130.8, 130.3, 130.1, 129.7, 129.3, 129.27, 127.8, 127.6, 126.9, 124.4, 123.9, 122.9, 122.8, 122.2, 34.8, 31.4. MS (MALDI-TOF): calc. for $\text{C}_{80}\text{H}_{64}\text{N}_2$: $[m/z]$ 1052.5, found: $[m/z]$ 1051.9.

Acknowledgements

J. C. Acknowledges the financial support from the National Natural Science Foundation of China (21102031, 21442010 and 21672051), the Natural Science Foundation of Hebei Province for Distinguished Young Scholar (Cultivation Project, B2015201183), the Natural Science Foundation of Hebei Province (B2014201007), and the Natural Science Foundation of Hebei University (2015JQY02).

Notes and references

- 1 J. H. Burroughes, D. D. C. Bradley, A. R. Brown, R. N. Marks, K. Mackay, R. H. Friend, P. L. Burns and A. B. Holmes, *Nature*, 1990, **347**, 539–541.



- 2 C. W. Tang and S. A. Vanslyke, *Appl. Phys. Lett.*, 1987, **51**, 913–915.
- 3 J. Kido, M. Kimura and K. Nagai, *Science*, 1995, **267**, 1322–1324.
- 4 M. Romain, S. Thiery, A. Shirinskaya, C. Declairieux, D. Tondelier, B. Geffroy, O. Jeannin, J. Rault-Berthelot, R. Métivier and C. Poriol, *Angew. Chem., Int. Ed.*, 2015, **54**, 1176–1180.
- 5 M. Shimizu and T. Hiyama, *Chem.-Asian J.*, 2010, **5**, 1516–1531.
- 6 M. Shimizu, Y. Takeda, M. Higashi and T. Hiyama, *Angew. Chem., Int. Ed.*, 2009, **48**, 3653–3656.
- 7 Z. Zhao, S. Chen, C. Y. K. Chan, J. W. Y. Lam, C. K. W. Jim, P. Lu, Z. Chang, H. S. Kwok, H. Qiu and B. Tang, *Chem.-Asian J.*, 2012, **7**, 484–488.
- 8 U. H. F. Bunz, J. U. Engelhart, B. D. Lindner and M. Schaffroth, *Angew. Chem., Int. Ed.*, 2013, **52**, 3810–3821.
- 9 J. T. Markiewicz and F. Wudl, *ACS Appl. Mater. Interfaces*, 2015, **7**, 28063–28085.
- 10 W. Jiang, Y. Li and Z. Wang, *Chem. Soc. Rev.*, 2013, **42**, 6113–6127.
- 11 J. Xiao, B. Yang, J. I. Wong, Y. Liu, F. Wei, K. Tan, X. Teng, Y. Wu, L. Huang, C. Kloc, F. Boey, J. Ma, H. Zhang, H. Yang and Q. Zhang, *Org. Lett.*, 2011, **13**, 3004–3007.
- 12 J. Xiao, H. Yang, Z. Yin, J. Guo, F. Boey, H. Zhang and Q. Zhang, *J. Mater. Chem.*, 2011, **21**, 1423–1427.
- 13 S. Hirata, Y. Sakai, K. Masui, H. Tanaka, S. Y. Lee, H. Nomura, N. Nakamura, M. Yasumatsu, H. Nakanotani, Q. Zhang, K. Shizu, H. Miyazaki and C. Adachi, *Nat. Mater.*, 2015, **14**, 330–336.
- 14 Q. Zhang, B. Li, S. Huang, H. Nomura, H. Tanaka and C. Adachi, *Nat. Photonics*, 2014, **8**, 326–332.
- 15 X. Zhan, Z. Wu, Y. Lin, Y. Xie, Q. Peng, Q. Li, D. Ma and Z. Li, *Chem. Sci.*, 2016, **7**, 4355–4363.
- 16 L. Chen, G. Lin, H. Peng, S. Ding, W. Luo, R. Hu, S. Chen, F. Huang, A. Qin, Z. Zhao and B. Tang, *Mater. Chem. Front.*, 2017, **1**, 176–180.
- 17 D. Ding, K. Li, B. Liu and B. Tang, *Acc. Chem. Res.*, 2013, **46**, 2441–2453.
- 18 Y. Liu, C. Deng, L. Tang, A. Qin, R. Hu, J. Sun and B. Tang, *J. Am. Chem. Soc.*, 2011, **133**, 660–663.
- 19 R. A. Pascal Jr, *Chem. Rev.*, 2006, **106**, 4809–4819.
- 20 J. Lu, D. M. Ho, N. J. Vogelaar, C. M. Kraml, S. Bernhard, N. Byrne, L. R. Kim and R. A. Pascal Jr, *J. Am. Chem. Soc.*, 2006, **128**, 17043–17050.
- 21 J. Lu, D. M. Ho, N. J. Vogelaar, C. M. Kraml and R. A. Pascal Jr, *J. Am. Chem. Soc.*, 2004, **126**, 11168–11169.
- 22 X. Qiao, D. M. Ho and R. A. Pascal Jr, *Angew. Chem., Int. Ed.*, 1997, **36**, 1531–1532.
- 23 R. A. Pascal Jr, W. D. McMillan, D. V. Engen and R. G. Eason, *J. Am. Chem. Soc.*, 1987, **109**, 4660–4665.
- 24 J. Xiao, H. M. Duong, Y. Liu, W. Shi, L. Ji, G. Li, S. Li, X. Liu, J. Ma, F. Wudl and Q. Zhang, *Angew. Chem., Int. Ed.*, 2012, **51**, 6094–6098.
- 25 J. Xiao, C. D. Malliakas, Y. Liu, F. Zhou, G. Li, H. Su, M. G. Kanatzidis, F. Wudl and Q. Zhang, *Chem.-Asian J.*, 2012, **7**, 672–675.
- 26 J. Xiao, S. Liu, Y. Liu, L. Ji, X. Liu, H. Zhang, X. Sun and Q. Zhang, *Chem.-Asian J.*, 2012, **7**, 561–564.
- 27 J. Xiao, Y. Divayana, Q. Zhang, H. M. Doung, H. Zhang, F. Boey, X. Sun and F. Wudl, *J. Mater. Chem.*, 2010, **20**, 8167–8170.
- 28 H. M. Duong, M. Bendikov, D. Steiger, Q. Zhang, G. Sonmez, J. Yamada and F. Wudl, *Org. Lett.*, 2003, **5**, 4433–4436.
- 29 Q. Xu, H. M. Duong, F. Wudl and Y. Yang, *Appl. Phys. Lett.*, 2004, **85**, 3357–3359.
- 30 J. Li, Y. Zhao, J. Lu, G. Li, J. Zhang, Y. Zhao, X. Sun and Q. Zhang, *J. Org. Chem.*, 2015, **80**, 109–113.
- 31 D. Rodríguez-Lojo, D. Pérez, D. Pena and E. Guitián, *Chem. Commun.*, 2015, **51**, 5418–5420.
- 32 Z. Liu, J. Xiao, Q. Fu, H. Feng, X. Zhang, T. Ren, S. Wang, D. Ma, X. Wang and H. Chen, *ACS Appl. Mater. Interfaces*, 2013, **5**, 11136–11141.
- 33 X. Zhang, H. Song, J. Xiao, T. Ren, S. Wang, Z. Liu, X. Ba and Y. Wu, *Aust. J. Chem.*, 2015, **68**, 505–512.
- 34 B. Lv, X. Shen, J. Xiao, J. Duan, X. Wang and Y. Yi, *Chem.-Asian J.*, 2015, **10**, 2677–2682.
- 35 J. Xiao, Z. Liu, X. Zhang, W. Wu, T. Ren, B. Lv, L. Jiang, X. Wang, H. Chen, W. Su and J. Zhao, *Dyes Pigm.*, 2015, **112**, 176–182.
- 36 Z. Liu, W. Wang, W. Xu, H. Chen, X. Zhang, T. Ren, X. Wang, J. Zhao and J. Xiao, *Dyes Pigm.*, 2015, **115**, 143–148.
- 37 X. Zhang, S. Li, Z. Liu, S. Wang and J. Xiao, *NPG Asia Mater.*, 2015, **7**, e230.
- 38 S. Chen, J. Xiao, X. Zhang, X. Shen, X. Liu, F. Shen, Y. Yi and Y. Song, *Dyes Pigm.*, 2016, **134**, 9–18.
- 39 B. Lv, J. Xiao, J. Zhou, X. Zhang, J. Duan, W. Su and J. Zhao, *ACS Appl. Mater. Interfaces*, 2016, **8**, 18998–19003.
- 40 X. Wu, J. Xiao, R. Sun, T. Jin, J. Yang, G. Shi, Y. Wang, X. Zhang and Y. Song, *Adv. Opt. Mater.*, 2016, DOI: 10.1002/adom.201600712.
- 41 J. Wang, K. Liu, L. Ma and X. Zhan, *Chem. Rev.*, 2016, **116**, 14675–14725.
- 42 Y. Shirota, *J. Mater. Chem.*, 2005, **15**, 75–93.
- 43 M. Sonntag, K. Kreger, D. Hanft and P. Strohiegl, *Chem. Mater.*, 2005, **17**, 3031–3039.
- 44 S. Roquet, A. Cravino, P. Leriche, O. Alévêque, P. Frère and J. Roncali, *J. Am. Chem. Soc.*, 2006, **128**, 3459–3466.

