



CrossMark  
 click for updates

Cite this: *RSC Adv.*, 2017, 7, 9567

Received 1st January 2017  
 Accepted 27th January 2017

DOI: 10.1039/c7ra00014f

[rsc.li/rsc-advances](http://rsc.li/rsc-advances)

# Cupric oxide nanowires on three-dimensional copper foam for application in click reaction†

Chunxia Wang,<sup>‡ab</sup> Fan Yang,<sup>‡\*a</sup> Yan Cao,<sup>a</sup> Xing He,<sup>a</sup> Yushu Tang<sup>a</sup> and Yongfeng Li<sup>\*a</sup>

Readily prepared CuO nanowires (CuO NWs) have been found to be effective heterogeneous catalysts for the 1,3-dipolar cycloaddition (CuAAC) reaction without using any additional support and bases. Examination of CuO nanowire catalysts synthesized at various temperatures showed that the use of CuO-600 catalyst was the best choice for the success of the present click reaction. Not only aromatic and heteroaromatic alkynes but also alkylalkynes were catalyzed regioselectively, affording triazoles in excellent yields. Furthermore, we have identified that the reaction proceeded in a heterogeneous manner. It is noteworthy that the CuO-600 catalyst can be easily recovered and reused nine times.

## Introduction

1,2,3-Triazoles are one of the most vital class of N-containing heterocyclic compounds that have received a much attention, not only as biological active drugs but also as functional materials.<sup>1–9</sup> In addition, these compounds are attracting much attention mainly due to the fact that they are used in numerous fields, such as organic semiconductors, dyes, dehydroannulenes, and electroluminescent materials.<sup>10–21</sup> Due to their intrinsic importance, many methodologies have been developed for the preparation of 1,2,3-triazoles. Among them, Huisgen's 1,3-dipolar cycloaddition reaction of terminal alkynes and organic azides, catalysed by homogeneous CuI salts (CuAAC), was reported independently by Sharpless<sup>22</sup> and Meldal<sup>23</sup> (the so-called click reaction), which is known as one of the most efficient synthetic application tools in organic synthesis due to its 100% atom economy, mild reaction conditions, wide substrate scope and exclusive regioselectivity in the formation of the 1,4-disubstituted 1,2,3-triazoles. The click reaction can be catalysed also by heterogeneous copper, which strategy is immobilization of copper nanoparticles onto various heterogeneous organic and inorganic supports.<sup>24–28</sup> However, copper metal alone catalysed this click reaction is relatively slow and requires high catalyst loading with bases. Recently, Jin and co-workers developed an interesting monolithic nanoporous Cu catalysts, which nanoporosity structure of Cu surface led to a significant enhancement of catalytic activity in click chemistry without using any additional supports and bases.<sup>29,30</sup> Therefore, design of nanostructure on the surface of monolithic copper is not only feasible for

development of high catalytic activity catalysts application in click chemistry but also simplified for recovery of catalyst project.

Cupric oxide (CuO) are promising materials for gas sensors, heterogeneous catalysts, photovoltaics, infrared detectors, field emission emitters and lithium ion electrodes applications due to their unique properties such as direct band gap (1.2–1.7 eV), non-toxicity, chemical stability, abundant availability and low production cost.<sup>31–38</sup> To date, most of the ways used to generate CuO nanowires (CuO NWs) are physical and chemical routes, for instance, precursor methods, hydrothermal reaction, anodization, electrospinning, and seed-mediated growth solution.<sup>39–43</sup> Compared with these methods, the formation of CuO NWs by direct thermal oxidation of Cu has been recently given considerable attention due to its simplicity and large-scale growth.<sup>44</sup> Herein, we report an efficient approach for the synthesis of CuO NW and its remarkable catalytic properties in click chemistry without using any additional supports and bases. To the best of our knowledge, this is the first report on a monolithic CuO NWs catalysed organic molecular transformation.

## Experimental

### General information

All the chemicals are used as received without further purification: foam Cu, porosity  $\geq 98\%$ , purity  $\geq 99$ , PPI = 110, thickness = 1.5 mm, bulk density = 0.4–0.6 g cm<sup>-3</sup>, average pore size = 200–300  $\mu\text{m}$  (Kunshan desco electronics Co., Ltd); benzyl azide (Aladdin Industrial Corporation); the terminal alkyne, benzyl bromide (J&K Chemical); sodium azide (Micy Reagent); *t*-BuOH, toluene, hexane, THF, HCl (Beijing Chemical Works). Deionized water was used in this study.

### Synthesis of CuO NWs

In a typical procedure, a 3D CuO NWs network can be facile prepared by one step thermal oxidation of Cu foam in air. The

<sup>a</sup>State Key Laboratory of Heavy Oil Processing, China University of Petroleum, Beijing, 102249, China. E-mail: yangfan@cup.edu.cn; yfli@cup.edu.cn

<sup>b</sup>Institute of New Energy, China University of Petroleum, Beijing, 102249, China

† Electronic supplementary information (ESI) available. See DOI: 10.1039/c7ra00014f

‡ These authors contributed equally to this work.



Cu foam substrate was cleaned in an aqueous 1.0 M HCl solution for about 20 s, followed by repeated rinsing with distilled water. After it had been dried under a nitrogen gas flow, the Cu foam was placed in an alumina boat and immediately heated to the set-point temperature at ambient pressure in an oven and annealed in air for 4 hours. The growth process was accompanied with a change of colour from reddish to black, indicating the forming of CuO NWs. We have tested a number of temperatures: 400, 500, 600 and 700 °C, and the respective materials called CuO-*n*, (*n* = 400, 500, 600, 700).

### Characterization

X-ray diffraction (XRD, Bruker D8 Advance Germany) was applied to characterize the crystal structure of the hybrid materials, and the data were collected on a Shimadzu XD-3A diffractometer using Cu K $\alpha$  radiation. The X-ray photoelectron spectroscopy (XPS, Thermo Fisher K-Alpha American with an Al K $\alpha$  X-ray source) was used to measure the elemental composition of samples. Transmission electron microscopy (TEM, Tecnai G2, F20) combined with an energy dispersive X-ray spectroscopy (EDS) at an acceleration voltage of 200 kV were used to measure the size, morphology, size distribution and element content of nanoparticles.

### Representative procedure for the Cu NWs catalysed click reaction

To a H<sub>2</sub>O/*t*-BuOH (0.66 ml/0.33 ml) solution of 2 mg CuO NW (5 mol%), calculated the amount of catalyst basis of CuO) was added phenylacetylene 1a (0.5 mmol, 51 mg) and benzyl azide 2a (0.5 mmol, 67 mg) in a V-shaped reactor vial. The reaction mixture was stirred at room temperature for 12 h by using a bulky round-shaped magnetic stirring bar. After consumption of 1a and 2a which were monitored by TLC, the CuO NWs was picked out of the reaction mixture by tweezers. The recovered CuO NWs catalyst was washed with acetone and dried under vacuum to use for the next run. After concentrated of the filtrate, the white solid was purified *via* short silica gel chromatography by using a 3 : 1 mixture of hexane and ethyl acetate as an eluent, to afford 1-benzyl-4-phenyl-1*H*-1,2,3-triazole 3a as a white solid, yield: 116 mg (99%).

## Results and discussion

High-density CuO NWs were first grown by heating copper foam substrate in air for 4 h at a suitable range of temperature (400 °C, 500 °C, 600 °C, 700 °C), and the respective materials called CuO-*n*, (*n* = 400, 500, 600, 700). The morphology and structure of all CuO-*n* catalysts have been examined by scanning electron microscopy (SEM) (Fig. 1). For the Cu foam, the crack on the surface of the skeleton with 3D structure was distinctly observed as seen in Fig. 1a and b. When the Cu foam heated at 400 °C for 4 h in air, only the sparse nanowires related to CuO were formed on the surface of Cu foam (Fig. 1c and d). It was quite obvious that CuO NWs of CuO-500 were formed denser than that of CuO-400 (Fig. 1e and f). While the growth temperature enhanced to 600 °C, the density and length of CuO NWs were perfectly formed compared with CuO-400 and CuO-500 samples (Fig. 1g and h). When the temperature was higher than 700 °C, no CuO NWs were found and the growth of CuO NWs will be terminated, which is due to the free energy of CuO changes from negative to positive state,<sup>38</sup> as seen in Fig. 1i and j.

XRD is a useful method to characterize the crystal structure of these catalysts, and the crystal information of CuO-400, CuO-500, CuO-600 and CuO-700 are shown in Fig. 2. The characterized peaks locate at  $2\theta$  value of 43.5° and 50.6° were corresponding to the metal Cu (JCPDS PDF#85-1326). The characterized peaks locate at  $2\theta$  value of 36.6°, 42.5°, 61.6° and

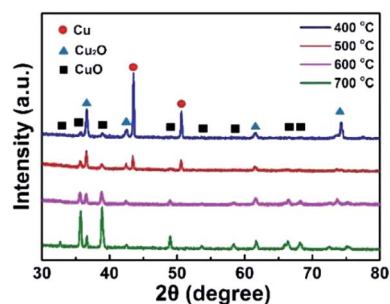


Fig. 2 The XRD patterns of CuO-400, CuO-500, CuO-600 and CuO-700.

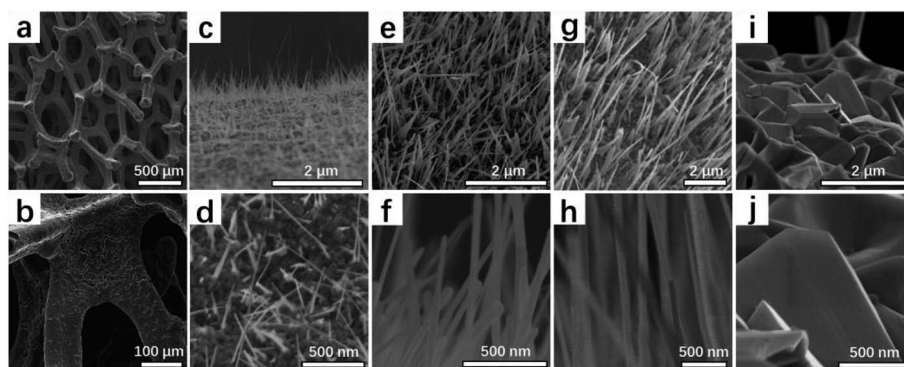


Fig. 1 SEM images of (a and b) Cu foam, (c and d) CuO-400, (e and f) CuO-500, (g and h) CuO-600, (i and j) CuO-700.



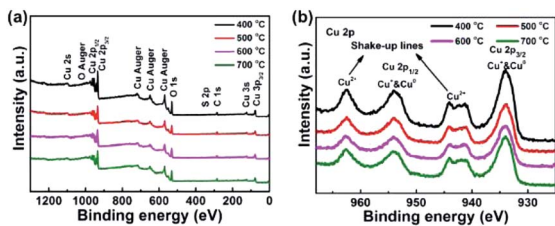


Fig. 3 XPS survey of CuO-*n* samples (a). Cu 2p scans of CuO-*n* (b).

74.2° were attributed to the Cu<sub>2</sub>O (JCPDS PDF#73-2076). The peaks locate at 2θ value of 32.7°, 35.7°, 38.9°, 48.9°, 53.7°, 58.4°, 66.5° and 68.2° correspond to the CuO (JCPDS PDF#80-1917). It was obvious to observe that the CuO-*n* were a mixture of Cu<sub>2</sub>O, CuO and metal Cu skeleton. Moreover, the Cu characterized peaks were disappeared and the Cu<sub>2</sub>O characterized peaks were reduced along with the temperature increasing, which were in accordance with the two steps growth mechanism of CuO NWs: the first one is forming of a Cu<sub>2</sub>O layer on the surface of copper, and then CuO NWs were subsequently grown on the Cu<sub>2</sub>O layer.<sup>44–46</sup>

The chemical composition and electronic structure of the CuO NWs were investigated by XPS. Fig. 3 depicts a high sensitivity scan with the presence of Cu and O elements. No other obvious impurities were found in the spectrum expect low-intensity peak of carbon, which might result from the surface contamination. The Cu 2p peak of CuO nanostructures was illustrated in detail in Fig. 2b. The Cu 2p<sub>3/2</sub> lies at 933.9 eV with a shake-up satellite at about 944 eV and Cu 2p<sub>1/2</sub> lies at 953.5 eV with a satellite at about 962.4 eV, which was in good agreement with previously reported.<sup>45,47</sup> The bonding energy gap between Cu 2p<sub>1/2</sub> and Cu 2p<sub>3/2</sub> was about 20 eV, which was in agreement with the standard spectrum of CuO. The O 1s peak for CuO and Cu<sub>2</sub>O was at 530 eV and Cu<sub>2</sub>O was at 531.8 eV (Fig. S1†), respectively.

The catalytic activities of various fabricated CuO-*n* samples were examined in the click reaction of phenylacetylene (1a) and benzyl azide (2a) in H<sub>2</sub>O at room temperature without using any additional supports and bases (Table 1). The reactions using CuO-*n* catalysts with calcination temperature at 400 °C and 500 °C (CuO-400 and CuO-500) gave moderate yields of the corresponding triazole 3a (entries 1 and 2). Surprisingly, the use of CuO-600 afforded 3a in almost quantitative yield (entry 3). The reaction using CuO-700 as catalyst, resulted in a dramatically decreased yield of 3a (entry 4). However, Cu foam was inactive as a catalyst in current click reaction system (entry 5). These results indicated that the annealing temperature has a strong influence on catalytic activity in the click reaction. The remarkable difference catalytic activities are possibly ascribed to the different morphology, density and surface component of CuO NWs. Although, it can be found that the CuO component is increased along with the temperature increasing in our XRD results. It is hard to say which kind of Cu species (Cu<sub>2</sub>O and CuO) mainly affect the catalytic activity in current stage, due to the fact that both the morphology and density of the CuO NWs are also influential factors. Can be ascribed to the formation

Table 1 Click reaction under different conditions<sup>a</sup>

Entry	Cat.	Solvent	Yield <sup>b</sup> (%)
1	CuO-400	H <sub>2</sub> O	68
2	CuO-500	H <sub>2</sub> O	83
3	CuO-600	H <sub>2</sub> O	92
4	CuO-700	H <sub>2</sub> O	30
5	Cu foam	H <sub>2</sub> O	18
6	CuO-600	H <sub>2</sub> O : <i>t</i> -BuOH	99
7	CuO-600	Toluene	93
8	CuO-600	Hexane	89
9	CuO-600	THF	91

<sup>a</sup> Reaction conditions: phenylacetylene 51 mg (0.5 mmol) and benzyl azide 67 mg (0.5 mmol), cat. (5 mol%), and in 1 ml solvent at room temperature. <sup>b</sup> Isolated yield.

morphology of the CuO NWs on the Cu foam. In order to determine the solvent system most suitable for the catalyst, several experiments were conducted. Quantitative yield was obtained with a solvent mixture of *t*-BuOH and H<sub>2</sub>O (2 : 1) (entry 6). The reactions were carried out in different solvents including toluene, hexane and THF, no better results were obtained compared with the mixture solvent of *t*-BuOH and H<sub>2</sub>O. These results indicated that solubility and hygroscopic properties are all important factors for CuO-600 catalysis of click reactions.<sup>48</sup>

The scope extension of the protocol to other alkynes and benzyl azide was also investigated under the previously optimized reaction conditions (Table 2). Phenyl acetylenes with electron-donating and electron-withdrawing groups such as 1-ethynyl-4-methylbenzene, 1-ethynyl-4-methoxybenzene and 1-chloro-4-ethynylbenzene reacted readily with benzyl azide. The corresponding triazoles 3b–3d were obtained in high yields (entries 1–3). Heteroaromatic alkynes also gave the expected adducts 3e and 3f as single regioisomers in high yields (entries 4 and 5). Hydroxy-substituted alkynes such as propargyl alcohol and pent-4-yn-1-ol also gave the expected adducts (1-benzyltriazol-4-yl) methanol 1g and 3-(1-benzyl-1*H*-1,2,3-triazol-4-yl)propan-1-ol 1h as single regioisomers in good to high yields (entries 6 and 7). While acetylenes conjugated with an ester group such as phenyl propargyl ether and aliphatic alkynes such as hex-1-yne and ethynylcyclohexane react with benzyl azide produced the corresponding product with excellent yields (entries 8–10). The reaction with alkynes containing electron-withdrawing substituents and trimethyl silanes gave high yields (entries 11 and 12). These results illustrated that not only aromatic and heteroaromatic alkynes but also alkylalkynes were catalyzed regioselectively, affording triazoles in excellent yields.

Under neat conditions, the catalytic loading can be decreased to 1 mol% without any significant influence on the reaction efficiency on the reaction temperature at 65 °C. As known to all, the CuO NWs are formed on the surface of the Cu surface and the role of Cu foam is to support the CuO NWs





**Table 2** Click reaction of benzyl azide with terminal alkynes in the presence of CuO-600<sup>a</sup>

Entry	Alkyne	Product	Yield <sup>b</sup> (%)
	$R^1-C\equiv C + Ph-CH_2-N_3$ (1 + 2a)	$Ph-CH_2-N=N-C(R^1)=C-Ph$ (3)	
1			99
2			93
3			98
4			95
5			99
6			94
7			96
8			99
9			89
10			90
11			98
12			88


<sup>a</sup> Reaction conditions: acetylene (0.5 mmol) and benzyl azide 67 mg (0.5 mmol), cat. (5 mol%), and in 1 ml H<sub>2</sub>O : *t*-BuOH (2 : 1) at room temperature. <sup>b</sup> Isolated yield.

catalytic species rather than the click reaction catalyst eqn (1). Hence, we picked off the CuO NWs by ultrasonic in ethanol solution, finding that no more than 20 wt% of the CuO NWs were existed in CuO-600 catalyst. The TON value for the CuO-

600 can be reached as high as 495 in current click reaction system. In comparison with other Cu catalysts reported recently (Table S1†), it is obvious that the CuO-600 catalyst demonstrates superior or comparable catalytic activity. It is worthy to mention that, the recyclability, separation and fabrication of CuO-600 are much more advantageous than these Cu catalysts for practical applications. Moreover, the CuO-600 catalyst demonstrated to be very efficient in the multi-component 1,3-dipolar cycloaddition of phenyl acetylene and benzyl azide yielded *in situ* from sodium azide and benzyl bromide, affording 1,2,3-triazoles 3a in excellent yield eqn (2).




The reusability is the most important feature of a heterogeneous catalyst, which is superior to a homogenous one. First, to confirm the reaction indeed catalysed by CuO-600 rather than by homogenous CuO species, we have carried out the following leaching experiments as shown in eqn (3). After the catalytic click reaction of 1a and 2a was carried out for 4 h under the standard conditions, the CuO-600 catalyst was removed from the vessel by tweezers with 3a produced in 55% yield at this time. No further reaction were took place after removing the catalyst, the CuO-600 catalyst was then put back into the mixture. As a result, the click reaction was restarted, and production 3a was obtained in 99% yield in 8 h. To assess recyclability of CuO-600 catalyst, multiple phenyl acetylene 1a and benzyl azide 1b click reactions were carried out, the recovery of the heterogeneous catalyst was carried out by tweezers for the separation of the catalyst from the reaction mixture. It was found that the catalytic activity was slightly reduced after the catalyst repetition four times at room temperature. The yield of 3a can be improved by increasing the reaction temperature to 45 °C. When the reaction temperature enhanced to 65 °C, the catalyst can be further recycled four times with producing 3a excellent yield every time (Fig. 4a). After reaction, the catalyst was again examined by SEM, and the image indicated that the CuO NWs were covered by some organic compounds and some

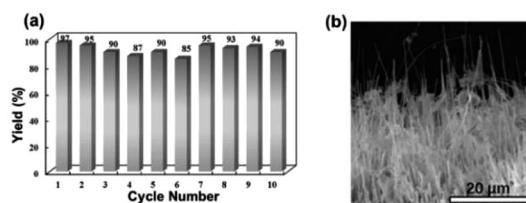

**Fig. 4** The yields for 10 cycles of CuO-600 catalysed click reaction (a), and SEM image of Pd-3 catalyst after 10 cycles (b).



of NWs were broke (Fig. 4b). However, the CuO NWs crystal structure were not changed dramatically as shown in Fig. S3,† which revealed that the CuO NWs was not transformed after the recycle test.

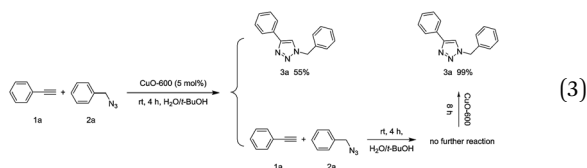

## Conclusions

In summary, CuO NWs can be synthesized by thermal oxidation of 3D Cu foam in air at different temperatures. Among all of the as-prepared catalysts, CuO-600 exhibits superior catalytic activity for 1,3-dipolar cycloaddition of phenyl acetylene and benzyl azide without using any additional supports and bases compared with CuO-400, CuO-500 and CuO-700 catalysts. A wide range of functional groups on terminal alkyne were tolerated, affording the corresponding substituted 1,2,3-triazole in good to high yields with a sole selectivity. Moreover, leaching experiment revealed that the click reaction occurred by heterogeneous way, and the CuO-600 catalyst can be effective reused nine times. Further work is in progress to extend such kind of catalyst for other applications.

## Acknowledgements

We gratefully thank for the National Natural Science Foundation of China (No. 21576289), the Science Foundation of China University of Petroleum, Beijing (No. 2462015YQ0306, 2462016YJRC027, 2462014QZDX01 and C201603), Thousand Talents Program and National High-tech R&D Program of China (863 Program, No. 2015AA034603).

## References

- R. Manetsch, A. Krasiski, Z. Radi, J. Raushel, P. Taylor, K. B. Sharpless and H. C. Kolb, *J. Am. Chem. Soc.*, 2004, **126**, 12809–12818.
- G. C. Tron, T. Pirali, R. A. Billington, P. L. Canonico, G. Orba and A. A. Genazzani, *Med. Res. Rev.*, 2008, **28**, 278–308.
- Y. M. A. Yamada, A. hno, T. Sato and Y. Uozumi, *Chem.-Eur. J.*, 2015, **21**, 17269–17273.
- H. Nandivada, X. W. Jiang and J. Lahann, *Adv. Mater.*, 2007, **19**, 2197–2208.
- P. Wu, A. K. Feldman, A. K. Nugent, C. J. Hawker, A. Scheel, B. Voit, J. Pyun, J. M. J. Fréchet, K. B. Sharpless and V. V. Fokin, *Angew. Chem., Int. Ed.*, 2004, **43**, 3928–3932.
- V. Aucagne, K. D. Hanni, D. A. Leigh, P. J. Lusby and D. B. alker, *J. Am. Chem. Soc.*, 2006, **128**, 2186–2187.
- D. Astruc, R. Ciganda, C. Deraedt, S. atard, L. Liang, N. Li, C. Ornelas, A. Rapakousiou, J. Ruiz, D. Wang, Y. Wang and P. Zhao, *Synlett*, 2015, **26**, 1437–1449.
- D. Huang, P. Zhao and D. Astruc, *Coord. Chem. Rev.*, 2014, **272**, 145–165.
- F. Alonso, Y. Moglie and G. Radivoy, *Acc. Chem. Res.*, 2015, **48**, 2516–2528.
- G. P. Ellis and T. M. Romney Alexandar, *Chem. Rev.*, 1987, **87**, 779–794.
- K. Mori, K. Yamaguchi, T. Mizugaki, K. Ebitani and K. Kaneda, *Chem. Commun.*, 2001, 461–462.
- K. Yamaguchi and N. Mizuno, *Angew. Chem., Int. Ed.*, 2003, **42**, 1480–1483.
- M. Kotani, T. Koike, K. Yamaguchi and N. Mizuno, *Green Chem.*, 2006, **8**, 735–741.
- F. Li, J. Chen, Q. Zhang and Y. Wang, *Green Chem.*, 2008, **10**, 553–562.
- Y. Zhang, K. Xu, X. Chen, T. Hu, Y. Yu, J. Zhang and J. Hung, *Catal. Commun.*, 2010, **11**, 951–954.
- M. L. Mihailovic, A. Stojiljkovic and V. Andrewjevic, *Tetrahedron Lett.*, 1965, **6**, 461–464.
- T. Kajimoto, H. Takahashi and J. Tsuji, *J. Org. Chem.*, 1976, **41**, 1389–1393.
- P. Capdevielle, A. Lavigne, D. Sparfel, J. Baranne-Lafont, K. C. Ngyuen and M. Maumy, *Tetrahedron Lett.*, 1990, **31**, 3305–3308.
- R. Tang, S. E. Diamond, N. Neary and F. Marks, *J. Chem. Soc., Chem. Commun.*, 1978, 562.
- F. Porta, C. Crotti and S. Cennini, *J. Mol. Catal.*, 1989, **50**, 333–341.
- Y. Maeda, T. Nishimura and S. Uemura, *Bull. Chem. Soc. Jpn.*, 2003, **76**, 2399–2403.
- V. V. Rostovtsev, L. G. Green, V. V. Fokin and K. B. Sharpless, *Angew. Chem.*, 2002, **114**, 2708–2711.
- C. W. Tornøe, C. Christensen and M. Meldal, *J. Org. Chem.*, 2002, **67**, 3057–3062.
- M. Gholinejad and N. Jeddi, *ACS Sustainable Chem. Eng.*, 2014, **2**, 2658–2665.
- S. Mohammed, A. K. Padala, B. A. Dar, B. Singh, B. Sreedhar, R. A. Vishwakarma and S. Bharate, *Tetrahedron*, 2012, **68**, 8156–8162.
- B. S. P. Anil Kumar, K. Harsha Vardhan Reddy, K. Karnakar, G. Satish and Y. V. D. Nageswar, *Tetrahedron Lett.*, 2015, **56**, 1968–1972.
- B. B. Lai, Z. P. Huang, Z. F. Jia, R. X. Bai and Y. L. Gu, *Catal. Sci. Technol.*, 2016, **6**, 1810–1820.
- A. S. Nia, S. Ran, D. Döhler, X. Noifalisse, A. Belfiore and W. H. Binder, *Chem. Commun.*, 2014, **50**, 15374–15377.
- T. N. Jin, M. Yan, Menggenbateer, T. Minato, M. Bao and Y. Yamamoto, *Adv. Synth. Catal.*, 2011, **353**, 3095–3100.
- T. N. Jin, M. Yan and Y. Yamamoto, *ChemCatChem*, 2012, **4**, 1217–1229.
- G. Avgouropoulos, T. Ioannides and H. Matralis, *Appl. Catal., B*, 2005, **56**, 87–93.
- K. T. Liao, P. Shimpi and P. X. Gao, *J. Mater. Chem.*, 2011, **21**, 9564–9569.
- G. Avgouropoulos and T. Ioannides, *Chem. Eng. J.*, 2011, **176**, 14–21.
- A. Aslani and V. Oroojpour, *Phys. B*, 2011, **406**, 144–149.



- 35 P. Shao, S. Deng, J. Chen and N. Xu, *Chin. Sci. Bull.*, 2011, **56**, 906–911.
- 36 J. Huang, Y. Zhu, X. Yang, W. Chen, Y. Zhou and C. Li, *Nanoscale*, 2015, **7**, 559–569.
- 37 P. J. Ni, Y. J. Sun, Y. Shi, H. C. Dai, J. T. Hu, Y. L. Wang and Z. Li, *RSC Adv.*, 2014, **4**, 28842–28847.
- 38 L. Q. Zhang, Z. F. Gao, C. Liu, L. Ren, Z. Q. Tu, R. Liu, F. Yang, Y. H. Zhang, Z. Z. Ye, Y. F. Li and L. S. Cui, *RSC Adv.*, 2014, **4**, 47455–47460.
- 39 C. K. Xu, Y. K. Liu, G. D. Xu and G. H. Wang, *Mater. Res. Bull.*, 2002, **37**, 2365–2372.
- 40 H. M. Xiao, S. Y. Fu, L. P. Zhu, Y. Q. Li and G. Yang, *Eur. J. Inorg. Chem.*, 2007, **2007**, 1966–1971.
- 41 X. F. Wu, H. Bai, J. X. Zhang, F. E. Chen and G. Q. Shi, *J. Phys. Chem. B*, 2005, **109**, 22836–22842.
- 42 H. Wu, D. D. Lin and W. Pan, *Appl. Phys. Lett.*, 2006, **89**, 133125.
- 43 A. A. Umar and M. Oyama, *Cryst. Growth Des.*, 2007, **7**, 2404–2409.
- 44 X. C. Jiang, T. Herricks and Y. N. Xia, *Nano Lett.*, 2002, **2**, 1333–1338.
- 45 M. A. Dar, S. H. Nam, Y. S. Kim and W. B. Kim, *J. Solid State Electrochem.*, 2010, **14**, 1719–1726.
- 46 J. T. Chen, F. Zhang, J. Wang, G. A. Zhang, B. B. Miao, X. Y. Fan, D. Yan and P. X. Yan, *J. Alloys Compd.*, 2008, **454**, 268–273.
- 47 D. Tahir and S. Tougaard, *J. Phys.: Condens. Matter*, 2012, **24**, 175002.
- 48 J. Y. Kim, J. C. Park, H. Kang, H. Song and K. H. Park, *Chem. Commun.*, 2010, **46**, 439–441.

