

Cite this: *RSC Adv.*, 2017, 7, 16057

Impacts of inorganic draw solutes on the performance of thin-film composite forward osmosis membrane in a microfiltration assisted anaerobic osmotic membrane bioreactor†

Taozhan Hu, Xinhua Wang,* Chen Wang, Xiufen Li* and Yueping Ren

The influences of inorganic draw solutes on the performance of the thin-film composite forward osmosis (TFC–FO) membrane in microfiltration (MF) assisted anaerobic osmotic membrane bioreactors (AnMF–OMBRs) were investigated in this study. The results indicated that compared to sodium chloride (NaCl) at the same osmotic pressure, magnesium chloride (MgCl₂) led to a higher flux decline of the TFC–FO membrane, induced by more severe membrane fouling. In addition, the NaCl and MgCl₂ had no impacts on the rejection for organic matters by the TFC–FO membrane. However, the NH₄⁺–N rejection of TFC–FO membrane was neglected in the AnMF–OMBR with NaCl as draw solute, while it was enhanced to a range of 57.5–87.6% for the draw solute MgCl₂. The different NH₄⁺–N rejection and membrane fouling of TFC–FO membrane with draw solutes NaCl and MgCl₂ could be attributed to the Donnan potential. As for NaCl, more Na⁺ diffused into the mixed liquor resulting in NH₄⁺–N passing through the TFC–FO membrane to the draw solution for keeping a charge balance. With regard to MgCl₂, more Cl[–] passing through the FO membrane to the mixed liquor led to an accumulation of NH₄⁺–N in the reactor. Moreover, Mg²⁺ passing from the draw solution to the mixed liquor enhanced the biofouling on the active layer of the FO membrane, and in the meanwhile more anions passing to the draw solution aggravated the inorganic fouling of the support layer.

Received 6th February 2017
Accepted 7th March 2017

DOI: 10.1039/c7ra01524k

rsc.li/rsc-advances

1. Introduction

Recently, a novel concept of an anaerobic osmotic membrane bioreactor (AnOMBR) has been proposed for treating low-strength wastewater.^{1–3} In the AnOMBR, a forward osmosis (FO) membrane was applied to retain the anaerobic biomass instead of the microfiltration (MF) membrane commonly used in traditional anaerobic membrane bioreactors (AnMBRs). Compared to the MF membrane, the FO membrane has a better retention for organic matter, especially low molecular weight substances, nitrogen and phosphorus, which cannot be retained by the MF membrane. In addition, the fouling of the FO membrane is lower when applying osmotic pressure instead of hydraulic pressure as the driving force and operating at mild flux conditions.^{4–6} Based on the above advantages of the FO membrane over the MF membrane, AnOMBRs have better contaminant removal and effluent water quality than conventional AnMBRs.^{1–3} Nevertheless, there are still some drawbacks

associated with the AnOMBRs such as the salinity build-up and the destruction of the FO membrane.

Salt accumulation is a common phenomenon in osmotic membrane bioreactors (OMBRs) owing to the high rejection of FO membrane for solutes and the reverse solutes transport from draw solution.^{7–15} The high salinity environment in OMBRs resulted from salt accumulation not only causes a reduction of water flux but also affects the microbial activity.^{7–15} The same problems induced by the salinity build-up have also been observed in the studies on AnOMBRs.^{1,2} In the AnOMBRs, salt accumulation was commonly alleviated by periodical supernatant discharge when the salinity reached to about 20 mS cm^{–1}.^{1,2} However, this easy controlling method can not avoid the increase of salinity in one cycle of AnOMBRs. In this case, Wang *et al.*¹⁶ developed a novel MF-assisted AnOMBR (AnMF–OMBR) for controlling salt accumulation by discharging the solutes from the MF membrane.¹⁶ The results demonstrated that the salinity was effectively controlled in a low range of 2.5–4.0 mS cm^{–1}, which enabled the AnMF–OMBR achieve a long-term continuous operation and a higher methane production.

Previous studies on the AnOMBRs also indicated the cellulose triacetate (CTA) FO membrane with a low tolerance to both the high temperature and the biological degradation, hence the unstability of CTA membrane was difficult to keep a long time

Jiangsu Key Laboratory of Anaerobic Biotechnology, School of Environmental and Civil Engineering, Jiangnan University, Wuxi 214122, P. R. China. E-mail: xhwang@jiangnan.edu.cn; xfli@jiangnan.edu.cn; Tel: +86-510-85326516

† Electronic supplementary information (ESI) available. See DOI: 10.1039/c7ra01524k



continuous operation.¹ Apart from the CTA-FO membrane, thin film composite polyamide (TFC) membrane is another commercial FO membrane commonly used in the FO process.^{7,17} Compared with the CTA-FO membrane, TFC-FO membrane has higher water flux, lower reverse salt transport and better resistance to hydrolysis and biological degradation.^{18,19} Based on these facts, application of the TFC-FO membrane instead of the CTA-FO membrane might be a feasible method for preventing the FO membrane from hydrolysis and biological degradation in the AnOMBRs. Until now, there are no studies on the AnOMBRs used the TFC-FO membrane.

Draw solution is a significant part of FO process because it can significantly affect the performance of the FO membrane.^{20–24} According to previous studies, inorganic salts especially NaCl and MgCl₂ were the most commonly used draw solutes in OMBR studies.^{4,5,25,26} Thus, the objective of this study is to evaluate the performance of TFC-FO membrane in the AnMF-OMBR with the draw solutes of NaCl and MgCl₂. This study may provide a new insight into the impacts of inorganic draw solutes on the performance of FO membrane and thus enhancing their applications in OMBRs for wastewater treatment.

2. Materials and methods

2.1 Experimental set-up

In this study, two identical laboratory-scale AnMF-OMBRs were operated in parallel. As shown in Fig. 1, the effective volume of each reactor was 4.98 L, and both an FO and an MF modules (each with an effective area of 0.025 m²) were immersed in the anaerobic sludge. The MF membrane (polyvinylidene fluoride (PVDF), Zizheng Environment Inc., China) with a mean pore size of 0.20 μm was operated under the mode of stable flux, and its water flux was controlled by a peristaltic pump. The TFC-FO membrane (supplied by Hydration Technologies Inc.) had an orientation of active layer facing the mixed liquors. Produced biogas was recycled with a recirculation rate of 2 L min^{−1} for alleviating the membrane fouling and mixing the anaerobic biomass.

The reactors were operated with the same operating conditions except for the draw solute. One reactor applied NaCl as the draw solute (called as NaCl-reactor), while MgCl₂ was used in the other one (called as MgCl₂-reactor). In order to keep the

draw solution at the same osmotic pressure (calculated by <http://www.lenntech.com>), the concentrations of NaCl and MgCl₂ solutions were kept at 0.5 and 0.36 M, respectively. The salinity of the draw solutions was kept stable through a conductivity controller equipped with 5 M NaCl and 3.6 M MgCl₂ solutions, respectively. The draw solutions were circulated with a flow rate of 0.4 L min^{−1} in both reactors. Each reactor was operated at the temperature of 25 ± 0.5 °C and at the sludge retention time (SRT) of 90 days. The hydraulic retention time (HRT) of both reactors (in the range of 12.5–90 h) varied with the flux changes of MF and FO membranes. The synthetic domestic wastewater was used as the influent with the ammonia nitrogen (NH₄⁺-N), chemical oxygen demand (COD), total organic carbon (TOC), total phosphorus (TP) and total nitrogen (TN) concentrations of 29.0 ± 0.99, 366.7 ± 5.3, 152.9 ± 4.8, 3.35 ± 0.16 and 35.2 ± 1.3 mg L^{−1}, respectively. The composition of synthetic wastewater has been listed in previous studies.^{27,28} The seeded sludge in both reactors was collected from a local municipal wastewater treatment plant (Taihu Xincheng WWTP, Wuxi, China) after cultivating approximately 60 days at the temperature of 25 ± 0.5 °C in a fermentation flask. The initial sludge concentration in both reactors was controlled at about 3.8 and 2.8 g L^{−1} for mixed liquor suspended solids (MLSS) and mixed liquor volatile suspended solids (MLVSS), respectively.

2.2 Analytical methods

COD, NH₄⁺-N, TN, TP, MLSS and MLVSS were conducted by the standard methods,²⁹ and the TOC was determined by a TOC analyzer (TOC-Vcsh, Shimadzu, Japan). All the above analyses were conducted at least 3 times, and their mean values ± standard deviations were reported.

The fouled FO membrane modules were collected from both reactors at the end of their operations, and then cut into some pieces for scanning electron microscopy (SEM), confocal laser scanning microscopy (CLSM) and energy diffusive X-ray (EDX) analyses. The specific methods of SEM, EDX and CLSM analyses could be found in previous literature.^{12,13,17,30}

3. Results and discussion

3.1 Impacts of draw solutes on water flux and salinity

Changes of FO flux and the conductivity of the mixed liquors in both reactors are illustrated in Fig. 2. It could be observed that the salinity was kept at a low level of about 3 mS cm^{−1} in both reactors with the help of MF membrane. Compared with the AnOMBR used NaCl as the draw solute,¹ the salinity obtained in this study was about one magnitude lower, which was due to the enhanced salt leakage through the MF membrane.^{9,13} In fact, if the MF membrane is not applied for discharging solutes, the salinity will be much higher in the NaCl-reactor compared to the MgCl₂-reactor owing to the more severe reverse transport of NaCl compared to MgCl₂.³¹ It could be demonstrated by a larger MF membrane flux (see Fig. S1†) needed for discharging solutes from the NaCl-reactor in order to achieve a similar salinity environment in the MgCl₂-reactor.

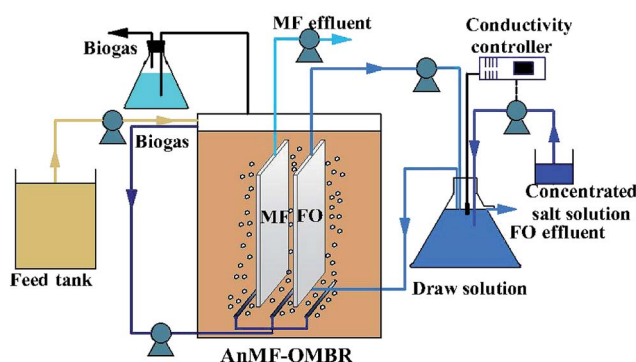


Fig. 1 Schematic diagram of the AnMF-OMBR system.



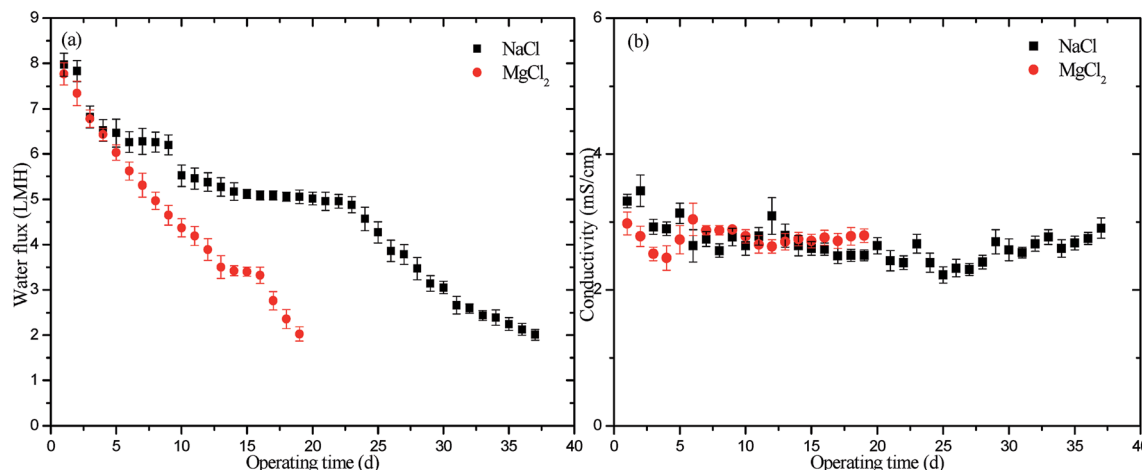


Fig. 2 Variations of FO water flux (a) and the conductivity of the mixed liquors (b) in the AnMF-OMBRs with different draw solutes.

With regard to the changes of the FO membrane flux, there were significant differences between NaCl-reactor and MgCl_2 -reactor. Compared to the NaCl-reactor, the flux drop of FO membrane was more serious in the MgCl_2 -reactor. The more severe flux decline directly led to a shorter operating time of the MgCl_2 -reactor (from 7.77 LMH to 2.06 LMH in 19 days) compared with the NaCl-reactor (from 7.99 LMH to 2.02 LMH in 37 days). According to previous studies, the flux drop of FO membrane in the OMBRs can be attributed to both membrane fouling and salt accumulation.^{8,12,13} Considering the similar salinity achieved in both reactors, the larger flux drop of FO membrane in the MgCl_2 -reactor indicated a presence of more serious membrane fouling.

3.2 Impacts of draw solutes on contaminants rejection

From Fig. S2,[†] regardless of the draw solutes, both reactors achieved a high TOC removal, *i.e.*, the TOC removal efficiencies calculated from the FO permeate were about 98.0% and 97.7% for NaCl-reactor and MgCl_2 -reactor, respectively. The high TOC removal in current study was consistent with conventional AnOMBRs treating low-strength wastewater.^{1,2} However, compared to the COD concentration in sludge supernatant within the range of 100 to 250 mg L^{-1} in AnOMBRs,^{1,2} it was lower and more stable in the AnMF-OMBR owing to part of COD passing through MF membrane.

As shown in Fig. 3, $\text{NH}_4^+\text{-N}$ concentrations in sludge supernatant, MF and FO permeates accounted for more than 90% of TN concentrations in both reactors due to the activity of anaerobes in the hydrolysis phase, which was in agreement with previous researches on the AnOMBRs.^{1,2} Thus, we just focused on the variations of $\text{NH}_4^+\text{-N}$ concentrations in both reactors. It could be found from Fig. 3 that different draw solutes exhibited much different $\text{NH}_4^+\text{-N}$ rejection of TFC-FO membrane. When NaCl was used as the draw solute, the $\text{NH}_4^+\text{-N}$ concentration in the FO permeate was much larger than that in the sludge supernatant, indicating that the TFC-FO membrane did not have any $\text{NH}_4^+\text{-N}$ rejection even though the diffusion rate of $\text{NH}_4^+\text{-N}$ larger than the water. It was much different from the CTA-FO membrane with a $\text{NH}_4^+\text{-N}$ rejection of 62.7–81.2% in AnOMBRs applied

NaCl as draw solute.^{1,2} However, the TFC-FO membrane had a $\text{NH}_4^+\text{-N}$ rejection of about 57.5–87.6% in the MgCl_2 -reactor. These results implied that the $\text{NH}_4^+\text{-N}$ rejection of TFC-FO membrane was significantly influenced by the draw solutes. Owing to the different $\text{NH}_4^+\text{-N}$ rejection of TFC-FO membranes in both reactors, the $\text{NH}_4^+\text{-N}$ concentration in the sludge supernatant was dramatically different between the two reactors. With regard to the NaCl-reactor, the $\text{NH}_4^+\text{-N}$ concentration in the supernatant was less than that in the influent, while it was accumulated in the supernatant in the MgCl_2 -reactor.

The TP concentration of the FO permeate in both reactors (see Fig. S3[†]) was below 0.5 mg L^{-1} owing to the excellent rejection of TFC membrane. The similarly high TP removal was also observed in AnOMBRs with the CTA-FO membrane.^{1,2} It is interesting to note that the TP concentration of sludge supernatant in the NaCl-reactor was less compared to the MgCl_2 -reactor. As discussed in Section 3.1, in order to maintain a stable salinity in the AnMF-OMBR, the water flux of MF membrane was larger in the NaCl-reactor owing to the higher reverse salt transport of NaCl. Thus, the lower TP concentration of sludge supernatant in the NaCl-reactor could be attributed to the larger flux of MF membrane (see Fig. S1[†]) based on the fact that partly TP can pass through the MF membrane.

3.3 Impacts of draw solutes on membrane fouling

In order to explain the impacts of inorganic draw solutes on FO membrane fouling, the membrane fouling behaviors in both reactors were further analyzed. From Fig. 4, membrane fouling could be clearly observed on both the active layer (AL) and support layer (SL) of FO membranes after the operation of both reactors. However, there were significant differences in the morphology of the AL and SL between NaCl-reactor and MgCl_2 -reactor. From EDX results (Fig. S4[†]), there were no significant differences in composition of elements on the fouled FO membranes in both reactors except for the existence of Mg in the MgCl_2 -reactor. In addition, it could be observed from Fig. 5 that the biofoulants almost could not be detected in the SL of the fouled FO membranes in both reactors, which was consisted



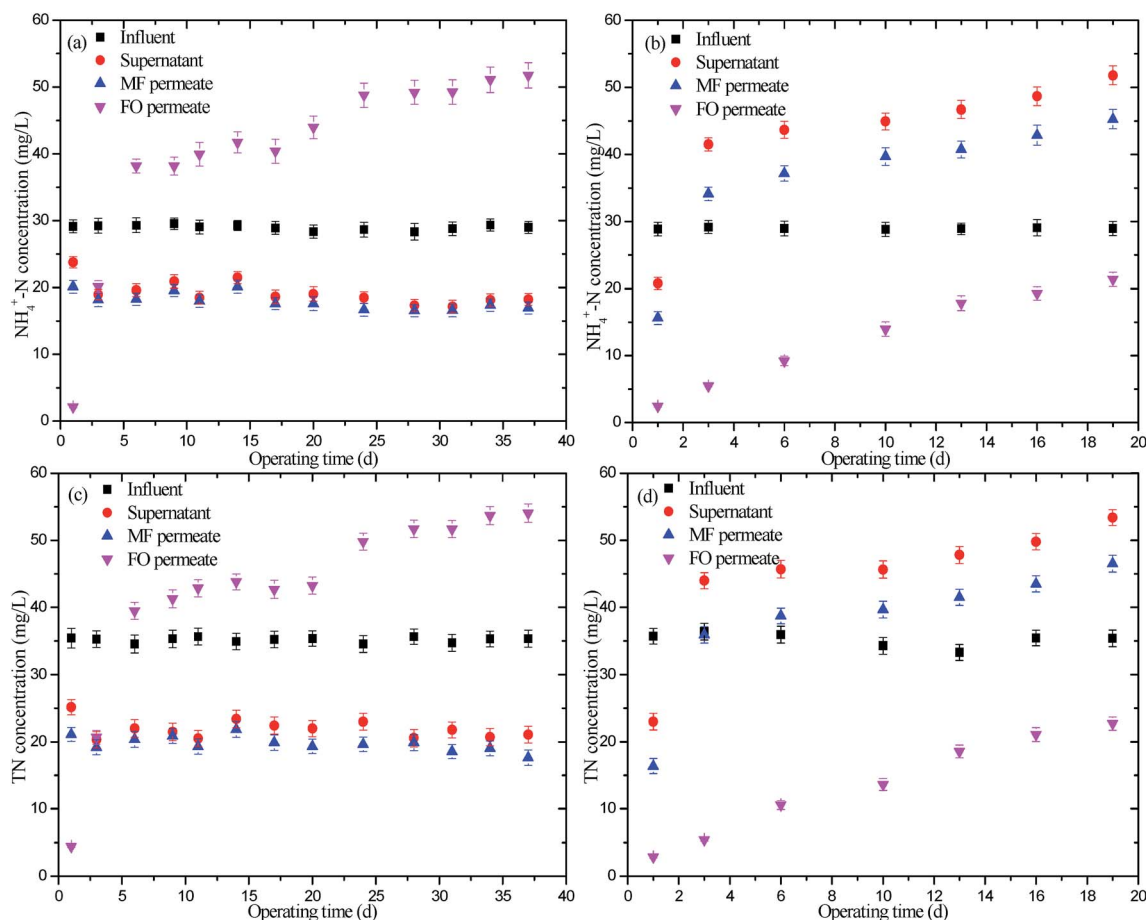


Fig. 3 Variations of $\text{NH}_4^+\text{-N}$ and TN concentrations in the influent, sludge supernatant, MF and FO permeates. (a) and (b) $\text{NH}_4^+\text{-N}$ concentrations in NaCl-reactor and MgCl_2 -reactor, respectively; (c) and (d) TN concentrations in NaCl-reactor and MgCl_2 -reactor, respectively.

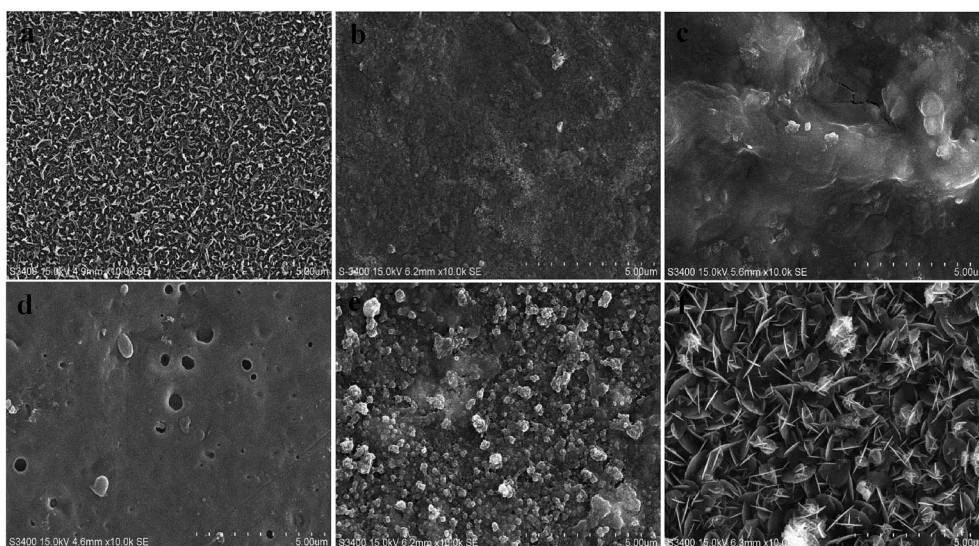


Fig. 4 SEM images of TFC FO membranes. (a) AL of the virgin FO membrane; (b) AL of the fouled FO membrane in the NaCl-reactor; (c) AL of the fouled FO membrane in the MgCl_2 -reactor; (d) SL of the virgin FO membrane; (e) SL of the fouled FO membrane in the NaCl-reactor; (f) SL of the fouled FO membrane in the MgCl_2 -reactor.



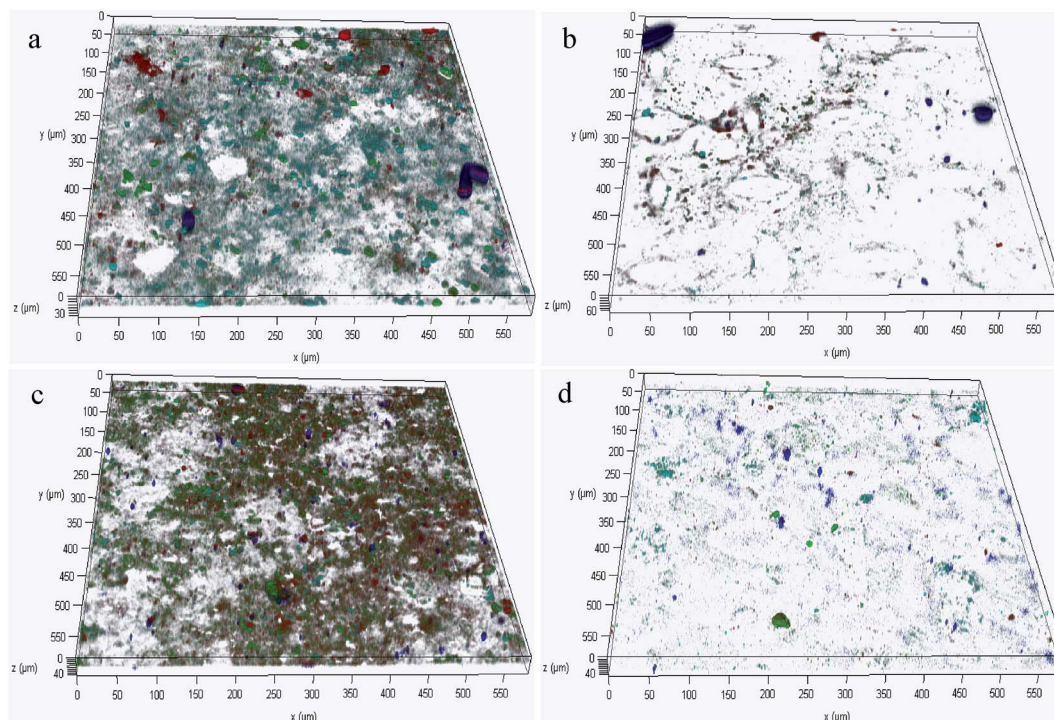


Fig. 5 Integrated CLSM images of polysaccharides, proteins and total cells in the FO biofouling layer. (a) and (b) AL and SL of the fouled FO membrane in the NaCl-reactor, respectively; (c) and (d) AL and SL of the fouled FO membrane in the MgCl_2 -reactor, respectively.

with the EDX results (no element of N) of the SL of fouled FO membranes, while the biofouling was more severe in the AL of FO membranes in both reactors. It might be implied that the inorganic fouling was the major fouling in the SL while the biofouling played a significant role in the AL fouling of the AnOMBRs applied inorganic salts as the draw solutes. This phenomenon of different types of foulants in AL and SL might be attributed to the AL facing with the activated sludge full of biofoulants and the SL contacting with the inorganic draw solutions. Moreover, compared with the fouling layer on the AL in the NaCl-reactor, it was much thicker in the MgCl_2 -reactor (40 versus 30 μm). It indicated that more serious biofouling existed on the AL when MgCl_2 was used as draw solute, which might be due to the presence of Mg^{2+} on the AL of FO membrane in the MgCl_2 -reactor based on the fact that Ca^{2+} and Mg^{2+} can enhance the biofouling due to their cationic bridges with extracellular polymeric substances (EPS).^{17,32,33} If further analyzing the distributions of polysaccharides, proteins and microorganisms on the AL in both reactors (Fig. S5†), it could be found that the microorganisms and proteins were much more on the AL in the MgCl_2 -reactor, suggesting that Mg^{2+} was more prone to enhance the deposition of microorganisms and proteins on the surface of FO membrane in the AnOMBRs.

It should be pointed out that compared with the CTA-FO membrane in AnOMBRs with the inorganic draw solute,² the TFC-FO membrane had a more severe fouling in this study based on the fact that the fouling layer of CTA-FO membrane could be easily removed just through the tap water while physical cleaning could not recover the water flux of TFC-FO

membrane. However, not like the hydrolysis and biological degradation of CTA-FO membrane in AnOMBRs, there are no damages of TFC-FO membrane in current study. Thus, TFC-FO membrane might be more suitable for the AnOMBRs due to its better resistance to hydrolysis and biological degradation.

3.4 Implications

The different inorganic draw solutes showed much different performance of TFC-FO membrane including NH_4^+ -N rejection and fouling behaviors in the AnMF-OMBR. It might be explained by the Donnan potential. From previous literature,^{34–37} TFC FO membrane has a good rejection performance of divalent cations but a worse rejection for monovalent ions, which resulted in the existence of Donnan equilibrium in current study. As shown in Fig. 6, when NaCl was used as the draw solute, Na^+ and Cl^- would diffuse from the draw solution to feed solution due to their high concentrations. Owing to the larger diffusion coefficient of Na^+ ,^{38–41} more Na^+ diffused into feed solution and thus resulting in a charge imbalance between both sides, which eventually led to more cations diffused from feed solution to draw solution for keeping charge at a balance level. Considering the excellent rejection of TFC membrane for divalent ions, NH_4^+ -N in the mixed liquor would pass through the membrane to the draw solution. Thus, the larger NH_4^+ -N concentration in the draw solution occurred in the AnMF-OMBR with NaCl as draw solute. However, when the draw solute was changed into MgCl_2 , the diffusion rate of Mg^{2+} was lower than Cl^- due to the high rejection of TFC membrane for Mg^{2+} .³⁸ In this case, more Cl^- passed through the TFC membrane to the



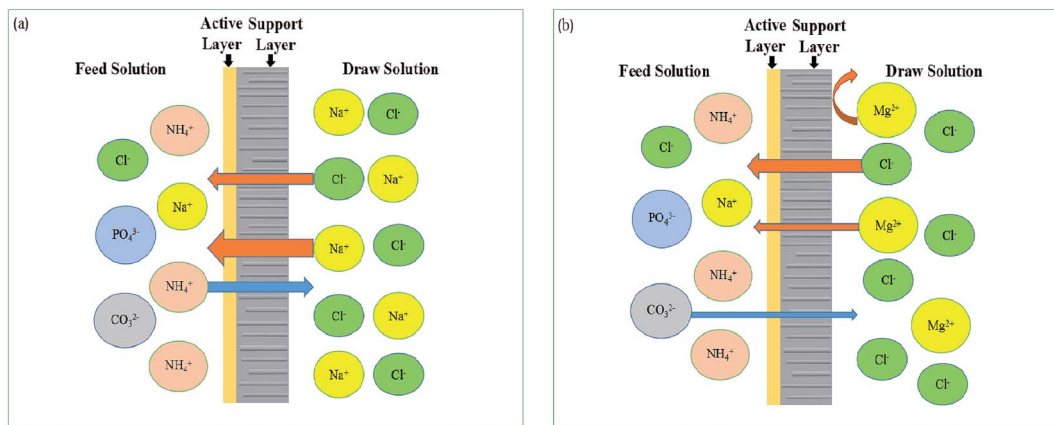


Fig. 6 Schematic diagram of Donnan equilibrium in the TFC FO membrane used NaCl (a) and MgCl_2 (b) as the draw solutes.

mixed liquor, which resulted in not cations but anions prone to permeate to the draw solution. It finally led to an accumulation of $\text{NH}_4^+\text{-N}$ in the mixed liquor and a decrease in the draw solution. Furthermore, Mg^{2+} passed to the mixed liquor enhanced the biofouling in AL, and in the meanwhile more anions through the FO membrane to the draw solution aggravated the inorganic fouling of SL.

4. Conclusion

In the AnMF-OMBR, the TFC-FO membrane had excellent rejections for organic matters and phosphorus regardless of the applied inorganic draw solutes. However, owing to the Donnan equilibrium, the draw solutes of NaCl and MgCl_2 resulted in significantly different performance of TFC-FO membrane on the $\text{NH}_4^+\text{-N}$ rejection and membrane fouling in the AnMF-OMBR. When NaCl was used as the draw solute, the TFC-FO membrane did not have any $\text{NH}_4^+\text{-N}$ rejection in the AnMF-OMBR, while the $\text{NH}_4^+\text{-N}$ rejection of TFC-FO membrane was enhanced to a range of 57.5–87.6% with the draw solute of MgCl_2 . However, compared to NaCl, MgCl_2 led to a more severe flux drop of TFC membrane, which could be attributed to the Mg^{2+} -enhanced biofouling and inorganic fouling in the AL and SL, respectively.

Acknowledgements

This work was supported by the National Natural Science Foundation of China [grant number 51578265]; the Fundamental Research Funds for the Central Universities [grant number JUSRP 51728A]; and Jiangsu Cooperative Innovation Center of Technology and Material of Water Treatment.

References

- 1 L. Chen, Y. S. Gu, C. Q. Cao, J. Zhang, J. W. Ng and C. Y. Tang, *Water Res.*, 2014, **50**, 114–123.
- 2 Y. S. Gu, L. Chen, J. W. Ng, C. Lee, V. W. C. Chang and C. Y. Tang, *J. Membr. Sci.*, 2015, **490**, 197–208.
- 3 M. K. Y. Tang and H. Y. Ng, *Water Sci. Technol.*, 2014, **69**, 2036–2042.
- 4 K. Lutchmiah, A. R. D. Verliefd, K. Roest, L. C. Rietveld and E. R. Cornelissen, *Water Res.*, 2014, **58**, 179–197.
- 5 X. H. Wang, V. W. C. Chang and C. Y. Y. Tang, *J. Membr. Sci.*, 2016, **504**, 113–132.
- 6 A. Zirehpour, A. Rahimpour, S. Khoshlhal, M. D. Firouzjaei and A. A. Ghoreyshi, *RSC Adv.*, 2016, **6**, 70174–70185.
- 7 A. J. Zhou, H. Y. Luo, Q. Wang, L. Chen, T. C. Zhang and T. Tao, *RSC Adv.*, 2015, **5**, 15359–15365.
- 8 A. Achilli, T. Y. Cath, E. A. Marchand and A. E. Childress, *Desalination*, 2009, **239**, 10–21.
- 9 R. W. Holloway, J. Ragnery, L. D. Nghiem and T. Y. Cath, *Environ. Sci. Technol.*, 2014, **48**, 10859–10868.
- 10 W. C. L. Lay, Q. Y. Zhang, J. S. Zhang, D. McDougald, C. Y. Tang, R. Wang, Y. Liu and A. G. Fane, *Desalination*, 2011, **283**, 123–130.
- 11 G. L. Qiu and Y. P. Ting, *Bioresour. Technol.*, 2013, **150**, 287–297.
- 12 X. H. Wang, Y. Chen, B. Yuan, X. F. Li and Y. P. Ren, *Bioresour. Technol.*, 2014, **161**, 340–347.
- 13 X. H. Wang, B. Yuan, Y. Chen, X. F. Li and Y. P. Ren, *Bioresour. Technol.*, 2014, **167**, 116–123.
- 14 J. M. Liu, X. H. Wang, Z. W. Wang, Y. Q. Lu, X. F. Li and Y. P. Ren, *Water Res.*, 2017, **110**, 74–82.
- 15 X. H. Wang, Y. X. Zhao, X. F. Li and Y. P. Ren, *Chem. Eng. J.*, 2017, **313**, 171–178.
- 16 X. H. Wang, C. Wang, C. Y. Y. Tang, T. Z. Hu, X. F. Li and Y. P. Ren, *J. Membr. Sci.*, 2017, **527**, 1–7.
- 17 X. H. Wang, Y. X. Zhao, B. Yuan, Z. W. Wang, X. F. Li and Y. P. Ren, *Bioresour. Technol.*, 2016, **202**, 50–58.
- 18 G. M. Geise, H. S. Lee, D. J. Miller, B. D. Freeman, J. E. McGrath and D. R. Paul, *J. Polym. Sci., Part B: Polym. Phys.*, 2010, **48**, 1685–1718.
- 19 Y. S. Gu, Y. N. Wang, J. Wei and C. Y. Y. Tang, *Water Res.*, 2013, **47**, 1867–1874.
- 20 W. H. Luo, F. I. Hai, W. E. Price and L. D. Nghiem, *Sep. Purif. Technol.*, 2015, **145**, 56–62.
- 21 W. H. Luo, F. I. Hai, W. E. Price, W. S. Guo, H. H. Ngo, K. Yamamoto and L. D. Nghiem, *Bioresour. Technol.*, 2014, **167**, 539–546.



- 22 Q. H. She, X. Jin, Q. H. Li and C. Y. Tang, *Water Res.*, 2012, **46**, 2478–2486.
- 23 Y. N. Wang, E. Järvelä, J. Wei, M. Zhang, H. Kyllönen, R. Wang and C. Y. Tang, *Desalination*, 2016, **377**, 1–10.
- 24 S. Zou, Y. S. Gu, D. Z. Xiao and C. Y. Tang, *J. Membr. Sci.*, 2011, **366**, 356–362.
- 25 Q. C. Ge, M. M. Ling and T. S. Chuang, *J. Membr. Sci.*, 2013, **442**, 225–237.
- 26 S. F. Zhao, L. Zou, C. Y. Tang and D. Mulcahy, *J. Membr. Sci.*, 2012, **396**, 1–21.
- 27 K. Chen, X. H. Wang, X. F. Li, J. J. Qian and X. L. Xiao, *Sep. Purif. Technol.*, 2011, **82**, 148–155.
- 28 X. H. Wang, J. J. Qian, X. F. Li, K. Chen, Y. P. Ren and Z. Z. Hua, *Desalination*, 2012, **296**, 24–29.
- 29 APHA, *Standard Methods for the Examination of Water and Wastewater*, American Public Health Association/American Water Works Association/Water Environment Federation, Washington, DC, 22nd edn, 2012.
- 30 B. Yuan, X. H. Wang, C. Y. Tang, X. F. Li and G. H. Yu, *Water Res.*, 2015, **75**, 188–200.
- 31 Y. P. Devia, T. Imai, T. Higuchi, A. Kanno, K. Yamamoto, M. Sekine and T. V. Le, *J. Water Resour. Prot.*, 2015, **7**, 730–740.
- 32 Y. H. Mo, K. Xiao, Y. X. Shen and X. Huang, *Sep. Purif. Technol.*, 2011, **82**, 121–127.
- 33 D. L. Hu, Z. Zhou, T. H. Niu, H. J. Wei, W. X. Dou, L. M. Jiang and Y. Lv, *Sep. Purif. Technol.*, 2017, **172**, 357–365.
- 34 J. Wei, C. Qiu, C. Y. Y. Tang, R. Wang and A. G. Fane, *J. Membr. Sci.*, 2011, **372**, 292–302.
- 35 N. Y. Yip, A. Tiraferri, W. A. Phillip, J. D. Schiffman and M. Elimelech, *Environ. Sci. Technol.*, 2010, **44**, 3812–3818.
- 36 H. Xie, T. Saito and M. A. Hickner, *Langmuir*, 2011, **27**, 4721–4727.
- 37 D. X. Hou, L. Lu and Z. Y. J. Ren, *Water Res.*, 2016, **98**, 183–189.
- 38 X. L. Lu, C. Boo, J. Ma and M. Elimelech, *Environ. Sci. Technol.*, 2014, **48**, 14369–14376.
- 39 L. X. Bian, Y. Y. Fang and X. L. Wang, *Membranes*, 2014, **4**, 275–286.
- 40 B. D. Coday, D. M. Heil, P. Xu and T. Y. Cath, *Environ. Sci. Technol.*, 2013, **47**, 2386–2393.
- 41 Y. H. Li and S. Gregory, *Geochim. Cosmochim. Acta*, 1974, **38**, 703–714.

