



Cite this: *RSC Adv.*, 2017, 7, 33986

# Durable, self-healing, superhydrophobic fabrics from fluorine-free, waterborne, polydopamine/alkyl silane coatings†

Hongxia Wang,<sup>\*a</sup> Hua Zhou,<sup>a</sup> Shuai Liu,<sup>b</sup> Hao Shao,<sup>a</sup> Sida Fu,<sup>a</sup> Gregory C. Rutledge<sup>c</sup> and Tong Lin<sup>ID</sup><sup>\*a</sup>

Superhydrophobic fabrics have diverse applications in both textile and non-textile fields. Most of the waterborne materials for superhydrophobic treatment of fabrics use fluoro-containing substances, which have potential issues with bio-accumulation in both the human body and animals. Fluorine-free waterborne coatings are highly desirable for superhydrophobic treatment. In this study, we have prepared a fully waterborne coating solution through dispersion of an alkyl silane (hexadecyl trimethoxysilane) in an aqueous dopamine solution. After applying to fabrics through a wet-chemical process, the coating made the fabrics have a superhydrophobic surface with a water contact angle and a sliding angle of 163° and 8.6°, respectively. The treated fabrics are durable enough to withstand multiple washing. The coating is self-healable against acid/base etching and plasma damage. Such a fluorine-free, durable coating may be useful for the development of various superhydrophobic fabric products.

Received 1st May 2017  
Accepted 22nd June 2017

DOI: 10.1039/c7ra04863g

rsc.li/rsc-advances

## 1. Introduction

Superhydrophobic fabrics have potential applications in a number of areas including personal protection, anti-contamination, oil–water separation, anti-ice, anti-adhesion and functional sportswear.<sup>1–18</sup> Many methods have been developed to prepare superhydrophobic fabrics. Most of the superhydrophobic fabrics are prepared using fluorine containing substances through a coating process.<sup>19–24</sup> However, some fluorine-containing substances used for superhydrophobic treatment have issues with bio-accumulation. For example, perfluorooctane sulfonate (PFOS) and perfluorooctanoic acid (PFOA) of carbon chains greater than six are difficult to be degraded within the human body and thus could cause health issues. They have been restricted for applications in fabric finishing. Therefore, fluorine-free materials are more desirable.

Fluorine-free superhydrophobic treatments have been reported by several groups.<sup>25</sup> For examples, one-step coating treatments were reported by using different solution systems such as polystyrene solution containing hydrophobic SiO<sub>2</sub> nanoparticles and mercaptopropyltrimethoxy silane,<sup>26</sup>

polydimethylsiloxane (PDMS) solution containing onion-like carbon microspheres,<sup>27</sup> and PDMS containing graphene oxide.<sup>28</sup> Two-step treatment methods were also reported, such as forming a rough surface using ormosil<sup>29</sup> or silica nanoparticles,<sup>30</sup> followed by lowering the surface free energy using PDMS or stearic acid/perfluorodecyltrichlorosilane, respectively. However, most of the works involved solutions in organic solvent, which not only causes issues to the environment but also increases the cost. Superhydrophobic fabrics prepared by a fluorine-free waterborne solution or not using any solvent are highly desirable. Recently, superhydrophobic fabrics prepared by multicycle self-assembly or multi-step spraying using aqueous solutions have been reported.<sup>31,32</sup>

Dopamine (DA) is a biological neurotransmitter widely found in living organisms.<sup>33</sup> In aqueous solution, dopamine can polymerize spontaneously into polydopamine (PDA), and the polymerization products show good adhesion on solid substances.<sup>34,35</sup> Recently, using DA to prepare superhydrophobic surfaces has been reported. However, most of the methods involved a multiple step process, to deposit PDA on a solid substrate in an alkaline condition followed by hydrophobization treatment with a fluorine-containing chemical.<sup>36–40</sup> Some fabric materials, such as wool and polyester, tend to hydrolyze in an alkaline condition,<sup>41</sup> and the hydrolysis of the fiber surface could result in poor bonding between the overlay coating and the fiber substrate, hence lowering the coating durability.

In this study, we show that co-deposition of dopamine with an alkyl silane, hexadecyl trimethoxysilane (HDTMS), in neutral

<sup>a</sup>Institute for Frontier Materials, Deakin University, Geelong, VIC3216, Australia. E-mail: tong.lin@deakin.edu.au; Hong.wang@deakin.edu.au

<sup>b</sup>School of Mechanical and Electric Engineering, Soochow University, 215000, China

<sup>c</sup>Department of Chemical Engineering, Massachusetts Institute of Technology, Cambridge, MA 02139, USA

† Electronic supplementary information (ESI) available: Photos, figures, SEM, FTIR, data colour, XPS. See DOI: 10.1039/c7ra04863g



aqueous solution renders fabrics with a durable superhydrophobic surface. The treated fabrics have a water contact angle as high as  $163^\circ$  and sliding angle as low as  $8.6^\circ$ . It has high washing durability that can withstand over 20 cycles of AATCC standard washing without losing the superhydrophobicity. The coating is self-healable against chemical damages such as plasma treatment and etching in acid (pH = 1) or alkali (pH = 14) solution. Such a novel fluorine-free coating may be useful for development of safe, durable superhydrophobic fabric products.

## 2. Experimental section

### 2.1 Materials

Dopamine hydrochloride (3-hydroxytyramine hydrochloride,  $C_8H_{11}NO_2 \cdot HCl$ ) and hexadecyl trimethoxysilane (HDTMS, Dynasylan 9116) were obtained from Aldrich. Commercial cotton fabric (plain weave,  $165 \text{ g m}^{-2}$ , thickness =  $460 \mu\text{m}$ ), polyester fabric (plain weave,  $168 \text{ g m}^{-2}$ , thickness =  $520 \mu\text{m}$ ) and wool fabric (plain weave,  $190 \text{ g m}^{-2}$ , thickness =  $540 \mu\text{m}$ ) were purchased from the local supermarket. The fabrics were pre-cleaned with isopropyl alcohol to remove grease and possible dusts from the fabric substrates, without desizing, scouring and bleaching. The treatment did not influence the chemical and physical properties of the fabrics.

### 2.2 Synthesis of coating solution

Dopamine hydrochloride (0.1 g) was dissolved in deionized water (10 mL) to get a homogeneous solution. HDTMS (0.18 g, molar ratio of dopamine/HDTMS is 1 : 1) was then added to the DA solution. The mixture was stirred at  $50^\circ\text{C}$  until the HDTMS completely dispersed in the solution (about 12 h). The final brown solution was ready for coating treatment. The fabrics used in this work may have had some kind of finishes and they may not have been removed by the isopropyl alcohol treatment.

### 2.3 Coating treatment

A dip coating technique was employed to apply the coating solution onto fabrics. In brief, a fabric sample was immersed in the coating solution for 15 min at  $50^\circ\text{C}$ . After drying at  $140^\circ\text{C}$  for 1 hour, the coated fabric was rinsed twice with water to remove the side products and finally dried at ambient condition. After coating, the fabric turned from white to tint brown.

### 2.4 Characterizations

Electron microscopic images were taken on a scanning electron microscope (SEM; Leo 1530, Gemini/Zeiss, Oberkochen). Atomic force microscopy (AFM; Cypher, Asylum Research) was used to measure surface roughness. Fourier Transform Infrared (FTIR) spectra were obtained on an FTIR spectrophotometer (Bruker Optics, Ettlingen). X-ray photoelectron spectroscopy (XPS) was measured on a VG ESCALAB 220-iXL spectrometer with a monochromated Al  $K\alpha$  source ( $1486.6 \text{ eV}$ ) using samples of approximately  $3 \text{ mm}^2$  in size. The X-ray beam incidence angle was  $0^\circ$  with respect to the surface normal, which corresponds to a sampling depth of  $\sim 10 \text{ nm}$ . The obtained XPS spectra were

analyzed by the XPSPEAK41 software (Shanghai, China). Contact angles were measured using a commercial contact angle meter (KSV CAM101 Instruments Ltd). Water droplets for the contact angle measurement were  $3 \mu\text{L}$  in volume. The size of dopamine/HDTMS particles was tested by using dynamic light scattering (DLS) (Zetasizer, Nano ZS, 90, Malvern). Color difference was measured using a Datacolor 600<sup>TM</sup> spectrophotometer (Datacolor company, USA). The test conditions were: illuminant D65,  $10^\circ$  standard observer, and specular component included.

### 2.5 Durability test

Washing durability was evaluated in reference of the washing method specified in the AATCC (American Association of Textile Chemists and Colorists) Test Method 61-2006 test no. 2A. The test was performed using a standard laundering machine (MODEL H-240, no. 4361, RAPID LABORTEX CO., LTD. Taiwan) equipped with 500 mL ( $75 \text{ mm} \times 75 \text{ mm}$ ) stainless-steel lever-lock canisters. The fabric sample (size,  $50 \text{ mm} \times 150 \text{ mm}$ ) was laundered in a 150 mL aqueous solution containing 0.15% (w/w) AATCC standard reference detergent WOB and 50 stainless steel balls. During laundering, the temperature was controlled at  $49^\circ\text{C}$ , and the stirring speed was  $40 \pm 2 \text{ rpm}$ . After 45 minutes of laundering, the laundered sample was rinsed with tap water, and then dried at room temperature without spinning. The contact angle and sliding angle were then measured. The abrasion resistance was tested using the Martindale method, according to Australian Standard AS 2001.2.25-2006 (similar to ASTM D4966). The test was performed under a commercial Martindale abrasion tester (I. D. M Instrument Design & Maintenance). The fabric sample was mounted on the dynamic disk which tightly contacted with the abradant underneath. The abradant was mounted on the motionless disk. Pressure was applied by adding weight of standard mass onto the upper shaft. During testing, the dynamic disk rotated, and in the meanwhile the whole dynamic disk moved across the different area of the abradant surface.

### 2.6 Self-healing tests

Three methods were employed to deliberately damage the coating on the fabrics: air plasma treatment, immersing in an aqueous  $\text{H}_2\text{SO}_4$  solution (pH = 1), and immersing in an aqueous KOH solution (pH = 14). For plasma treatment, the treated fabrics were subjected to a vacuum plasma treatment (gas source: air) for 30 seconds. Such plasma treatment can make the surface completely hydrophilic (contact angle  $0^\circ$ ). For acid/base immersion, the treated fabric was immersed in the acid/base solution for 10 min at room temperature, and then rinsed with deionized water, and dried naturally at room temperature. The fabric after this treatment turned hydrophilic. After those damages, the treated fabrics were heated at  $140^\circ\text{C}$  for 10 minutes. The one that can restore the superhydrophobicity, which is confirmed by contact angle, has a self-healing property.



### 3. Results and discussion

Fig. 1a shows the chemical structure of the coating materials and the procedure for coating treatment. The coating solution was prepared by dispersing HDTMS in an aqueous dopamine (DA) solution in neutral condition. At the initial stage of mixing, the HDTMS suspended on the top of the aqueous solution to form a separate layer due to the insoluble nature in water. During mechanical stirring, the HDTMS dispersed gradually in the solution with time, and meanwhile the solution turned brown. After 12 hours of stirring, HDTMS dispersed completely in the solution and the solution became dark brown (Fig. 1b). During the process of mixing and dispersion, the solution maintained the pH at 7.0.

It is known that HDTMS is insoluble in water and it has a very low hydrolysis rate in neutral aqueous solution. The presence of dopamine in the solution improved the dispersing ability of HDTMS. This is because dopamine self-polymerizes to form PDA particles, which functioned as a carrier to adsorb HDTMS. The size of PDA/HDTMS particles was measured using a dynamic light scattering (DLS) method (see measurement result in the ESI†). Fig. 1c shows the average size of the particles formed in the aqueous solution. The average particle size increased with increasing the mixing time. After 12 hours, the average particle size was 160 nm. Under TEM, the PDA/HDTMS particles showed a round shape (Fig. 1d). In contrast, the PDA formed in the same condition without HDTMS was 80 nm. Apparently, dopamine in the solution improves the dispersing ability of HDTMS in neutral aqueous solution. PDA forms

nanoparticles in water, which have large surface energy. HDTMS can be adsorbed by PDA particles during the particle formation. Further polymerization of DA could also immobilize the HDTMS through the reaction between dopamine and hydrolyzed HDTMS through hydroxyl group. The coating solution was stable at room temperature for up to one week. Longer storage time (*e.g.* two weeks) led to participation of the black particles.

When the coating solution was applied onto cotton fabric, the fabric turned superhydrophobic. Fig. 1e shows a photo of blue-dyed water on the coated cotton fabric. The coated fabric had a water contact angle (CA) as high as  $163^\circ$  and a sliding angle (SA) of  $8.6^\circ$ . Water drop stayed stability on the fabric surface for long time. The fabric was oleophilic with a CA of  $0^\circ$  to cooking oil (surface tension =  $32 \text{ mN m}^{-1}$ ). The coated fabric is repellent to coffee, milk, cherry juice and red wine (see the ESI†).

For comparison, we also treated cotton fabric (with CA of  $0^\circ$  for untreated fabrics) with an aqueous solution containing either dopamine or HDTMS. In the same concentration and stirring condition, the fabric treated by the dopamine-containing solution without HDTMS had a hydrophilic surface with a CA of zero degree to water (see the ESI†). When fabric was treated by a HDTMS–water suspension without DA, a hydrophilic surface still resulted with CA of  $0^\circ$  (see ESI†), which is different from previous reports where solid surfaces after treatment with HDTMS–ethanol become hydrophobic.<sup>42,43</sup> The unusual result from our experiment was attributable to the solvent water, which phase-separates from HDTMS and prevents the HDTMS molecules from spreading on the fiber substrate. To

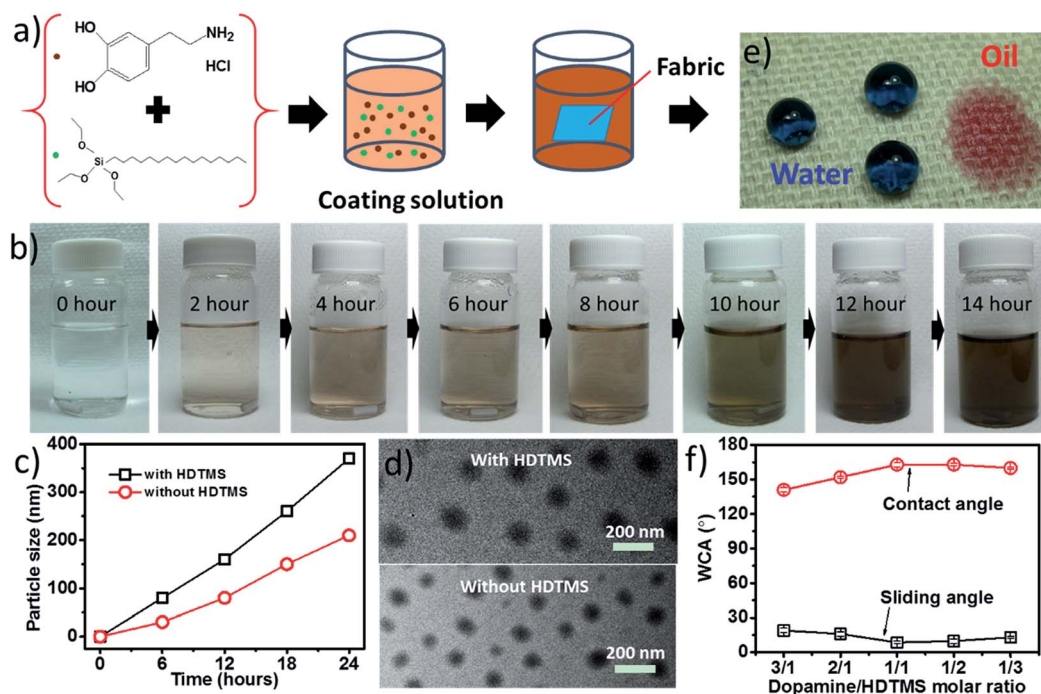


Fig. 1 (a) Chemical structure of dopamine and HDTMS, and coating procedure; (b) mixture of dopamine and HDTMS in water at different reaction times; (c) PDA particle size change with time; (d) TEM image of the dopamine/HDTMS particles; (e) water and cooking oil on the coated cotton fabric; (f) the effect of dopamine/HDTMS molar ratio on the water contact angle and sliding angle of the HDTMS/water coated cotton fabric.



verify this explanation, we did a similar experiment but used ethanol as solvent. As expected, the fabric after treatment with HDTMS–ethanol mixture showed a hydrophobic surface.

It was noted that the DA/HDTMS molar ratio in the coating solution affected the hydrophobicity of the coated fabrics. Fig. 1f shows the effect of DA/HDTMS molar ratio on water CA and SA of the coated fabrics. When DA/HDTMS was 3 : 1 (mol mol<sup>-1</sup>), the CA was below 150° and SA above 20°. When the molar ratio was changed to 2 : 1 (mol mol<sup>-1</sup>), the CA increased to 152°, and SA reduced to 15°. The best repellency result (CA = 163°, and SA = 8.6°) was found on the fabric treated by the solution of DA/HDTMS of 1 : 1 (mol mol<sup>-1</sup>). However, when the DA/HDTMS ratio was 1 : 3 (mol mol<sup>-1</sup>), the repellency was slightly decreased. These results can be explained by the effect of the two components on the surface energy and roughness. It is known that the superhydrophobicity is affected by surface energy and roughness. PDA is hydrophilic whereas HDTMS can form a hydrophobic surface. Changing the molecular ratio of DA/HDTMS could lead to change of these two factors. Increasing the HDTMS portion would reduce the surface energy. However, the roughness could be reduced if the HDTMS portion is high enough, because the extra silane fills the inter-particle gap. A similar result was also reported on other coating systems.<sup>44</sup> Therefore, in the later experiments, we chose the DA/HDTMS ratio of 1 : 1 (mol mol<sup>-1</sup>) for all coating treatments.

Fig. 2a and b show SEM images of the cotton fabric before and after coating treatment with dopamine/HDTMS. The coated

fiber was slightly increased in roughness. AFM imaging confirmed the surface roughness increased after treatment, with the root mean square (RMS) roughness increasing from 9.0 nm to 17.3 nm (Fig. 2c and d). In some fiber surfaces, the small particles aggregated to larger particles which look like loosely adhered to the fiber surface, this does not have a large influence on the superhydrophobicity. The coating thickness was measured by cross-sectional TEM imaging, being approximately 150 nm (Fig. 2e).

The chemical composition of the cotton fabrics before and after DA/HDTMS coating treatment was examined by FTIR and XPS spectra. After dopamine/HDTMS coating, the weak peaks at 1614 cm<sup>-1</sup> and 1560 cm<sup>-1</sup> appeared in the FTIR spectra (ESI†), which were ascribed to the overlap of the C=C resonance vibrations in the aromatic rings and in-plane vibration mode of the N–H and C–N bonds, respectively.<sup>45–48</sup> The occurrence of vibration bands at 810 cm<sup>-1</sup>, 1430 cm<sup>-1</sup>, 2855 cm<sup>-1</sup> and 2929 cm<sup>-1</sup> was assigned to the Si–C stretching, –CH<sub>2</sub>– bending, –CH<sub>2</sub>– stretching and CH<sub>3</sub>– stretching of HDTMS.<sup>49,50</sup> The region of 1028 cm<sup>-1</sup> was attributed to the asymmetric stretching vibration of Si–O–Si bonds.<sup>51</sup> Fig. 2f shows the XPS survey spectra of the cotton fabrics. The presence of a weak N 1s peak, Si 1s peak and Si 2p peak confirmed that PDA and HDTMS were successfully coated on the fiber surface.<sup>52</sup>

Durability is an important requirement for superhydrophobic fabrics. The washing durability of the treated fabric was examined by reference of the washing method specified in the AATCC (American Association of Textile Chemists and Colorists) Test Method 61-2006 test no. 2A. For the PDA/HDTMS coated fabrics, the superhydrophobicity maintained even after 20 cycles of AATCC standard washing. The fabric still maintained superhydrophobicity with a water CA of 150° and a sliding angle of 15.6°. Such 20 cycles of accelerated ageing test was equivalent of 100 cycles of home laundries.<sup>21</sup> The SEM image confirmed that the coated fabric after multiple cycles of laundering had little change in surface morphology, though led to the loss of certain particles from the fiber surface (see the ESI†). The fabric shows high hydrophobicity as long as the fabric surface was covered with PDA/HDTMS. After repeated washing, the XPS spectra (Fig. 2f) show that the intensity of C, O, and Si reduced, confirming the partial loss of the coating materials from the fiber surface.

The abrasion durability was evaluated by the Martindale method using untreated fabric to simulate actual damage. On cotton fabric, the coating can withstand 500 abrasion cycles without losing its superhydrophobicity. Further increasing the abrasion cycles resulted in decrease of water repellency. However, after 4000 abrasion cycles, the fabric was still hydrophobic with water CA above 90° (see the ESI†).

It was interesting to note that after being coated with PDA/HDTMS the fabric showed a self-healing ability to recover superhydrophobicity after being damaged by acid/alkali etching or oxygen plasma. When the PDA/HDTMS coated fabric was immersed in an acidic solution (e.g. pH < 4) for 10 minutes, rinsed with deionized water, and then dried at room temperature, it turned hydrophilic (CA = 0°) (Fig. 3a). After heating the sample at 140 °C for 10 min, however, the acid etched fabric

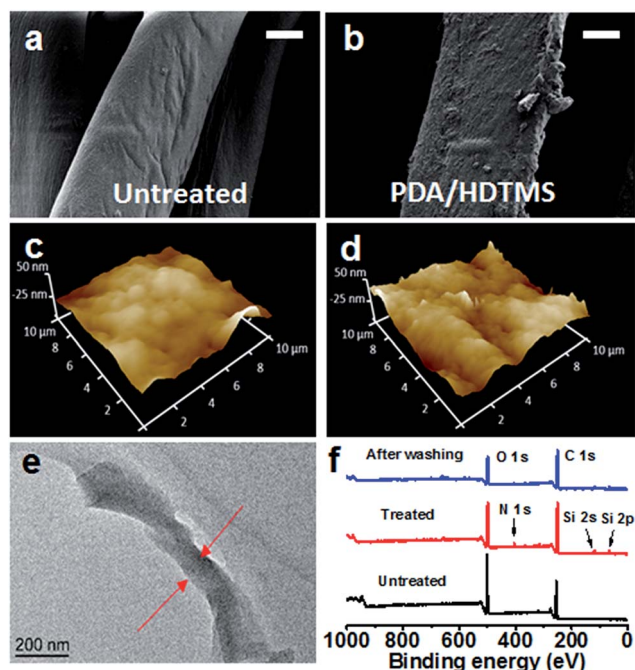


Fig. 2 SEM images of cotton fabrics (a) untreated, (b) treated with PDA/HDTMS (scale bar: 10 μm); (c) & (d) AFM images of the corresponding cotton fibers; (e) cross-sectional TEM image of the thickness of the dopamine/HDTMS coating; (f) XPS wide-scan spectra of cotton surface before and after coated with dopamine/HDTMS, and after washing test.



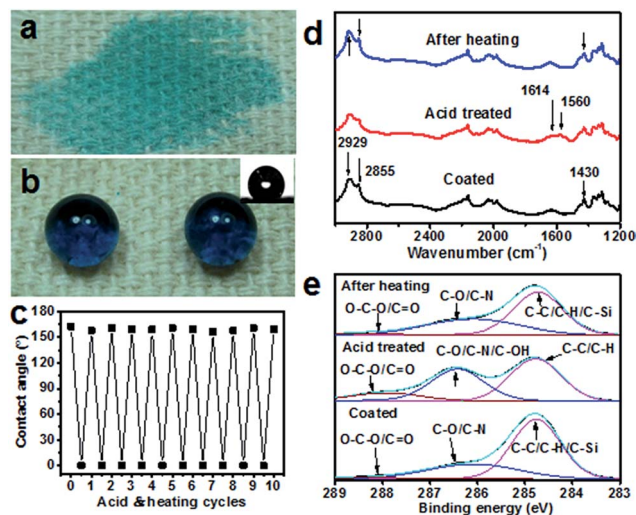


Fig. 3 Photos of water droplets on fabrics (a) after acid treatment and (b) after acid and heat treatment; (c) water contact angle change of the coated fabric after the ten cycles of acid and heat treatment; (d) FTIR spectra of cotton fabrics after dopamine/HDTMS coating, acid treatment and after heat treatment; (e) XPS high resolution C 1s spectra of dopamine/HDTMS treated cotton surface before and after acid treatment and then heat treatment.

restored the water-repellency with a CA increasing to  $154^\circ$  (Fig. 3b). Such a self-healing property was repeatable and can work for at least 30 cycles.

To find out the source of the CA change during acid etching and heating treatment, we examined the surface topology and chemistry. The acid etching and heating showed little effect on the surface morphology of the coated fibers (see the SEM images in ESI†). After etched in the acid solution, the peaks at  $1430\text{ cm}^{-1}$ ,  $2929\text{ cm}^{-1}$  and  $2855\text{ cm}^{-1}$  in the FTIR spectra decreased in intensity (Fig. 3d). After heating treatment, the peaks at  $1430\text{ cm}^{-1}$ ,  $2928$  and  $2855\text{ cm}^{-1}$  re-emerged. These results indicate that the acid treatment leads to increase of the PDA composition on the coating surface. The XPS high resolution C 1s spectra showed that the C–O/C–OH and O–C–O/C=O peaks increased, whereas the C–C/C–H/C–Si peak decreased after acid treatment (Fig. 3e), confirming the loss of HDTMS on the coating surface. After heating treatment, an opposite trend appeared for the C–C/C–H/C–Si, C–O/C–N/C–OH and O–C–O/C=O peaks, the reduced carbonyl group was assumedly due to the migration of HDTMS to the surface as indicated by the increase in Si content (see Table S2 in the ESI†). The increased HDTMS content on the coating surface would lead to reduction in surface energy, which could be the main reason leading to restoring the superhydrophobicity.

Apart from self-healing against acid etching, the coated fabric also showed a similar self-healing feature against etching in an alkaline solution (*e.g.*  $\text{pH} > 12$ ) and air plasma treatment (see ESI†). The alkali treatment showed almost no effect on the surface morphology of the coated fibers, and its effect on surface chemistry in a similar way to the acid etching (see the ESI†). For plasma treatment, the treated surface still maintained a rough surface, except that oxygen-containing polar

groups were introduced into the coating surface layer, and the heating treatment led to disappearance of these groups (see the ESI†).

In our previous papers,<sup>22</sup> we have already reported some liquid repellent fabrics with self-healing property against plasma treatment. The self-healing was explained by the lowering the surface energy due to the rotation or migration of low surface energy substrates onto the surface where the surface free energy was increased due to the introduction of oxygen-containing high polar groups. However, superhydrophobic surface with self-healing ability against acid/alkali etching has not been reported in research literature. As far as we know, our PDA/HDTMS coated self-healing superhydrophobic fabrics represent the first of their type.

According to our experiment results, we proposed the mechanism of the coating formation and self-healing against acid/base/plasma etching, as illustrated in Fig. 4. Dopamine molecules oxidated to form dopamine quinone, and they then formed 5, 6-dihydroxyindole and 5, 6-indolequinone; 5, 6-dihydroxyindole and 5, 6-indolequinone could undergo reactions at the positions of 2, 3, 4, and 7, leading to multiple isomers and even oligomers (Fig. 4a).<sup>53</sup> When HDTMS is added to the solution, its hydrolysis led to reaction of silanol with dopamine through hydroxyl groups. The unhydrolyzed HDTMS can be adsorbed on the PDA particles. As a result, the HDTMS molecules are trapped in the PDA and also adsorbed on the particle surface.

When fabric substrate is immersed in the solution, the above reactions also take place on the fiber surfaces. It is known that polydopamine can bond to almost all the solid surface through hydrogen bond, chelate action, ionic bond, covalent bond and physical interactions.<sup>54</sup> The formation of a thin layer of polydopamine increases the affinity to polydopamine particles. When PDA particles deposit on the PDA coated fiber substrate, further reaction with dopamine facilitates to bridge the PDA particles with the PDA coating layer (see the illustration in Fig. 4b), therefore enhancing the adhesion.

Here, it should be pointed out that the deposition of PDA particles on fiber surface leads to increase in surface roughness. PDA is hydrophilic. PDA only cannot form a hydrophobic coating. When HDTMS is added to PDA, the long alkyl chain brought by the HDTMS molecule largely reduces the surface free energy, leading to superhydrophobic surfaces.

When the coated fabric was subjected to an oxygen plasma, high polarity groups (*e.g.* hydroxyl groups, carbonyl groups and carboxyl groups) were introduced on to the coating surface, which largely reduced the surface free energy (Fig. 4c). When being heated, the molecules in the coating layers increase the mobility. The chain twist and migration allow the low surface energy chains to expose to the surface, which reduces the surface free energy, hence restoring the superhydrophobicity. For the acid and base treatment, in one option, the silane molecules could be removed from the coating surface. This leads to increase in the PDA, turning the surface hydrophilic. Upon heating, however, the HDTMS molecules trapped in the PDA migrate to surface, reducing the surface free energy. The acid and base treatment could also lead to breakage of crosslinked



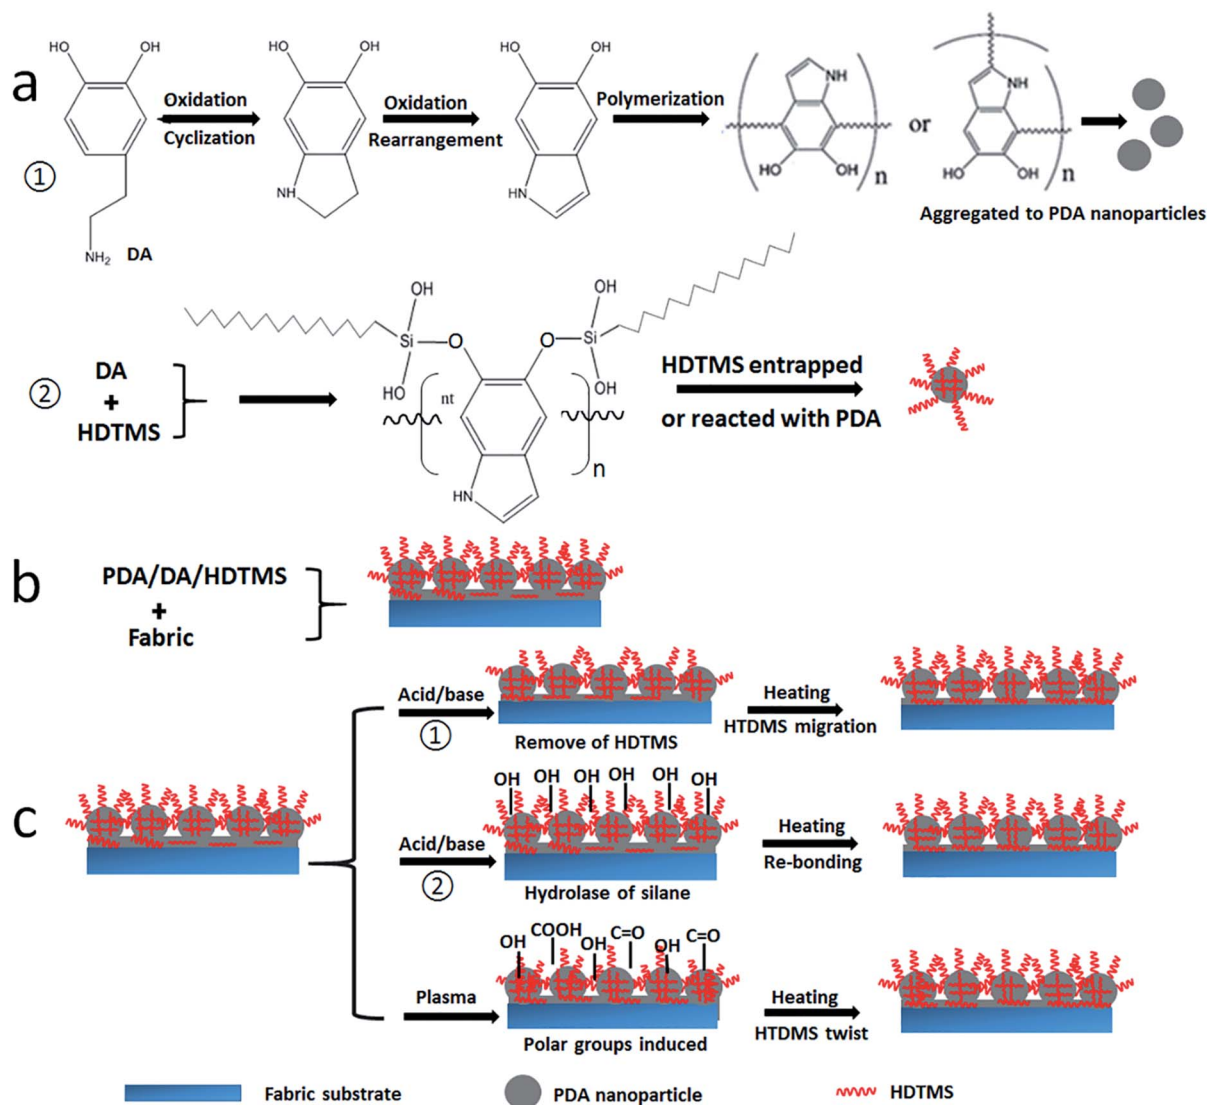


Fig. 4 Schematic diagram to illustrate coating formation and the self-healing property: (a) The reaction processes: ① from DA without HDTMS and ② DA with HDTMS; (b) the interfacial interaction between DA/PDA/HDTMS and the fabric surface; (c) schematic diagram for self-healing process.

silanes, forming hydroxyl groups and making the fabric hydrophilic. When the fabric is heated at 140 °C, the hydrolysed molecules are re-bonded, making the fabric hydrophobic. Therefore, the self-healing against acid/base etching follows a slightly different mechanism for the plasma treatment.

Coatings prepared from polydopamine are known to have a dark appearance. The polydopamine coating was brown in color (see the ESI†). To examine the effect of the PDA/HDTMS coating on fabric appearance, we used cotton fabric of different colors as substrates. Fig. 5a shows the photo of the fabrics before and after the DA/HDTMS treatment. When applied on dark color fabrics, the coating has a small effect on the fabric color. Therefore, for practical applications, the polydopamine coatings are more suitable for treatment of dark colored fabrics, such as brown, black, dark blue and dark green. Fig. 5b shows the color difference ( $\Delta E$ ) of the fabrics before and after treatment.  $\Delta E$  can be expressed by the formula:  $\Delta E =$

$[(\Delta L^*)^2 + (\Delta a^*)^2 + (\Delta b^*)^2]^{1/2}$ , where  $L^*$ ,  $a^*$ ,  $b^*$  are lightness/darkness, red or green chroma, and yellow/blue chroma, respectively. The samples no 5, 7 and 9 showed smaller  $\Delta E$  than the other samples, suggesting that the DA/HDTMS coating showed less effect on deep red, deep green and deep pink than other background colors (see the ESI†). Fig. 5c shows PDA/HDTMS coating on glass surface, which looks transparent. The transmittance spectrum, shown in Fig. 5d, indicates that the coating has a nearly 80% transmittance in the near UV and VIS region (wavelength 350–800 nm).

The DA/HDTMS coating treatment was also suitable for other types of fabrics, including wool and polyester fabrics. When commercial wool and polyester fabrics were treated by the dopamine/HDTMS solution, they both showed superhydrophobicity regardless of the original surface wettability, and the coatings had high washing durability as well (see the CA and washing results in the Table S2 in ESI†).



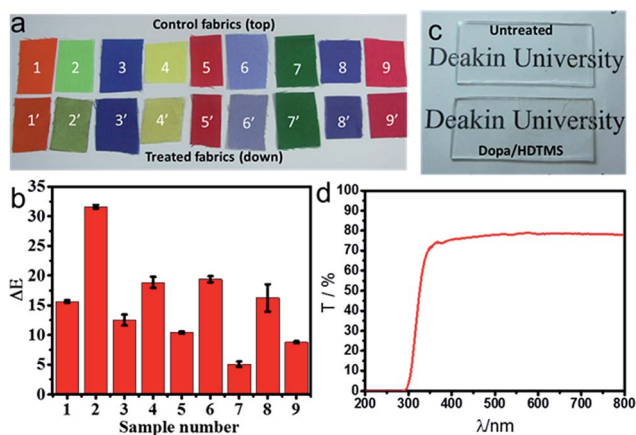


Fig. 5 Photo of (a) the control fabric and dopamine/HDTMS coated fabrics; (b) color difference  $\Delta E$  of the fabric based on the respective control; (c) photos of glass slide before and after ODTMS treatment, and (d) the corresponding transmittance spectra (100% based on glass slide transmittance).

In the previous reports, the PDA was synthesized in an aqueous solution with pH typically at 8.5.<sup>41</sup> We also prepared a coating solution at the alkaline condition (pH = 8.5), and used the solution for treatment of fabrics. In comparison with the DA/HDTMS solution synthesized in neutral condition (12 hour), the one prepared at pH = 8.5 looked darker, and the PDA/HDTMS particles formed showed a dual dispersity (size 220 nm and 780 nm), and after coating treatment, the treated fabric became uneven in color (see the ESI†). These issues were attributed to the fast polymerization of dopamine at an alkaline condition, and aggregation of the PDA particles in solution.

## 4. Conclusions

We have prepared superhydrophobic fabrics by co-deposition of dopamine with an alkyl silane in neutral aqueous solution. The treated fabric has a water contact angle as high as 163°. The fabrics show high washing durability that can withstand over 20 cycles of AATCC standard washing without losing the superhydrophobicity. The coating is self-healable, in that the superhydrophobicity can be restored by heat treatment after acid/base etching or plasma damage. The coating has a reasonably small effect on fabric color. Such fluorine-free durable coatings may be useful for development of various superhydrophobic fabric products.

## Acknowledgements

Funding support from Australian Research Council through a discovery project (ARC DP150100406) is acknowledged.

## Notes and references

1 X. Deng, L. Mammen, H. J. Butt and D. Vollmer, *Science*, 2011, **335**, 67–70.

- 2 A. Tuteja, W. Choi, M. Ma, J. M. Mabry, S. A. Mazzella, G. C. Rutledge, G. H. McKinley and R. E. Cohen, *Science*, 2007, **318**, 1618–1622.
- 3 X. M. Li, D. Reinhoudt and M. Crego-Calama, *Chem. Soc. Rev.*, 2007, **36**, 1350–1368.
- 4 F. Zhang, L. Zhao, H. Chen, S. Xu, D. G. Evans and X. Duan, *Angew. Chem., Int. Ed.*, 2008, **47**, 2466–2469.
- 5 X. Yao, Y. Song and L. Jiang, *Adv. Mater.*, 2011, **23**, 719–734.
- 6 L. Mishchenko, B. Hatton, V. Bahadur, J. A. Taylor, T. Krupenkin and J. Aizenberg, *ACS Nano*, 2010, **4**, 7699–7707.
- 7 Y. Wang, C. E. Sims, P. Marc, M. Bachman, G. Li and N. L. Allbritton, *Langmuir*, 2006, **22**, 8257–8262.
- 8 E. Galopin, G. Piret, S. Szunerits, Y. Lequette, C. Faille and R. Boukherroub, *Langmuir*, 2009, **26**, 3479–3484.
- 9 D. Quére, *Rep. Prog. Phys.*, 2005, **68**, 2495–2532.
- 10 L. Feng, Z. Zhang, Z. Mai, Y. Ma, B. Liu, L. Jiang and D. Zhu, *Angew. Chem., Int. Ed.*, 2004, **43**, 2012–2014.
- 11 H. Wang, H. Zhou, H. Niu, J. Zhang, Y. Du and T. Lin, *Adv. Mater. Interfaces*, 2015, **2**, 1400506.
- 12 A. Scardino, R. De Nys, O. Ison, W. O'Connor and P. Steinberg, *Biofouling*, 2003, **19**, 221–230.
- 13 L. D. Chambers, K. R. Stokes, F. C. Walsh and R. J. Wood, *Surf. Coat. Technol.*, 2006, **201**, 3642–3652.
- 14 H. J. Lee, *J. Mater. Sci.*, 2012, **47**, 5114–5120.
- 15 B. Mahltig and H. Böttcher, *J. Sol-Gel Sci. Technol.*, 2003, **27**, 43–52.
- 16 T. Bahners, T. Textor, K. Opwis and E. Schollmeyer, *J. Adhes. Sci. Technol.*, 2008, **22**, 285–309.
- 17 Q. Truong and E. Wilusz, *Smart Textiles for Protection*, 2012.
- 18 P. Gibson, *Text. Res. J.*, 1993, **63**, 749–764.
- 19 Y. Li, L. Li and J. Sun, *Angew. Chem.*, 2010, **122**, 6265; *Angew. Chem., Int. Ed.*, 2010, **49**, 6129–6133.
- 20 J. D. Samuel, S. Jeyaprakash and J. Ruehe, *Langmuir*, 2004, **20**, 10080–10085.
- 21 H. Wang, Y. Xue, J. Ding, L. Feng, X. Wang and T. Lin, *Angew. Chem., Int. Ed.*, 2011, **50**, 11433–11436.
- 22 H. Zhou, H. Wang, H. Niu, A. Gestos and T. Lin, *Adv. Funct. Mater.*, 2013, **23**, 1664–1670.
- 23 H. Wang, H. Zhou, A. Gestos, J. Fang and T. Lin, *ACS Appl. Mater. Interfaces*, 2013, **5**, 10221–10226.
- 24 H. Zhou, H. Wang, H. Niu, J. Fang, Y. Zhao and T. Lin, *Adv. Mater. Interfaces*, 2015, **2**, 1400559.
- 25 Y. Liu, Z. Liu, Y. Liu, H. Hu, Y. Li, P. Yan, B. Yu and F. Zhou, *Small*, 2015, **11**, 426–431.
- 26 X. Zhang, T. Geng, Y. Guo, Z. Zhang and P. Zhang, *Chem. Eng. J.*, 2013, **231**, 414–419.
- 27 H. Hu, L. Gao, C. Chen and Q. Chen, *Environ. Sci. Technol.*, 2014, **48**, 2928–2933.
- 28 H. Yan, H. Zhou, Q. Ye, X. Wang, C. M. Cho, A. Y. X. Tan and J. Xu, *RSC Adv.*, 2016, **6**, 66834–66840.
- 29 C. Cao, M. Ge, J. Huang, S. Li, S. Deng, S. Zhang, Z. Chen, K. Zhang and S. Salem, *J. Mater. Chem. A*, 2016, **4**, 12179–12187.
- 30 C. Xue, S. Jia, J. Zhang, L. Tian, H. Z. Chen and M. Wang, *Sci. Technol. Adv. Mater.*, 2008, **9**, 035008.



- 31 M. Wu, N. An, Y. Li and J. Sun, *Langmuir*, 2016, **32**, 12361–12369.
- 32 Q. Zeng, C. Ding, Q. Li, W. Yuan, Y. Peng, J. Hu and K. Zhang, *RSC Adv.*, 2017, **7**, 8443–8452.
- 33 H. Lee, S. M. Dellatore, W. M. Miller and P. B. Messersmith, *Science*, 2007, **318**, 426–430.
- 34 B. P. Lee, J. L. Dalsin and P. B. Messersmith, *Biomacromolecules*, 2002, **3**, 1038–1047.
- 35 B. P. Lee, C.-Y. Chao, F. N. Nunalee, E. Motan, K. R. Shull and P. B. Messersmith, *Macromolecules*, 2006, **39**, 1740–1748.
- 36 Y. Liu, K. Ai and L. Lu, *Chem. Rev.*, 2014, **114**, 5057–5115.
- 37 E. Herlinger, R. F. Jameson and W. Linert, *J. Chem. Soc.*, 1995, **2**, 259–263.
- 38 L. A. Burzio and J. H. Waite, *Biochemistry*, 2000, **39**, 11147–11153.
- 39 Y. Li, M. Liu, C. Xiang, Q. Xie and S. Yao, *Thin Solid Films*, 2006, **497**, 270–278.
- 40 F. Bernsmann, V. Ball, F. Addiego, A. Ponche, M. Michel, J. J. D. A. Gracio, V. Toniazzo and D. Ruch, *Langmuir*, 2011, **27**, 2819–2825.
- 41 Y. Liu, Y. Liu, H. Hu, Z. Liu, X. Pei, B. Yu, P. Yan and F. Zhou, *J. Phys. Chem. C*, 2015, **119**, 7109–7114.
- 42 J. Liu, W. Huang, Y. Xing, R. Li and J. Dai, *J. Sol-Gel Sci. Technol.*, 2011, **58**, 18–23.
- 43 M. Shateri-Khalilabad and M. Yazdanshenas, *Cellulose*, 2013, **20**, 3039–3051.
- 44 C. Zeng, H. Wang, H. Zhou and T. Lin, *RSC Adv.*, 2015, **5**, 61044–61050.
- 45 B. Prasad, A. Srivastava and M. Tiwari, *J. Colloid Interface Sci.*, 2013, **396**, 234–241.
- 46 M. Martin, P. Salazar, R. Villalonga, S. Campuzano, J. Pingarron and J. Gonzalez-Mora, *J. Phys. Chem. B*, 2014, **2**, 739.
- 47 J. Qiu, W. Zhou, J. Guo, R. Wang and R. Liang, *Anal. Biochem.*, 2009, **385**, 264–269.
- 48 S. Pande, S. Jana, A. Sinha, S. Sarkar, M. Basu, M. Pradhan, A. Pal, J. Chowdhury and T. Pal, *J. Phys. Chem. C*, 2009, **113**, 6989–7002.
- 49 J. H. Yim, V. Rodriguez, A. A. Williams and J. K. Hirvonen, *Surf. Coat. Technol.*, 2013, **234**, 21–32.
- 50 I. Woodward, W. C. E. Schofield, V. Roucoules and J. P. S. Badyal, *Langmuir*, 2003, **19**, 3432–3438.
- 51 X. Wang, S. Xu, Y. Tan, J. Du and J. Wang, *Carbohydr. Polym.*, 2016, **140**, 188–194.
- 52 Y. Li, Q. Chen, M. Yi, X. Zhou, X. Wang, Q. Cai and X. Yang, *Appl. Surf. Sci.*, 2013, **274**, 248–254.
- 53 F. Bernsmann, V. Ball, F. Addiego, A. Ponche, M. Michel, J. J. D. A. Gracio, V. Toniazzo and D. Ruch, *Langmuir*, 2011, **27**, 2819–2825.
- 54 D. Chai, Z. Xie, Y. Wang, L. Liu and Y. J. Yum, *ACS Appl. Mater. Interfaces*, 2014, **6**, 17974–17984.

