

Cite this: *RSC Adv.*, 2017, 7, 48083

Green synthesis of mesoporous anatase TiO₂ nanoparticles and their photocatalytic activities

Sunderishwary S. Muniandy,^a Noor Haida Mohd Kaus,^b Zhong-Tao Jiang,^c Mohammednoor Altarawneh^{b,c} and Hooi Ling Lee^{*,a}

Titanium dioxide (TiO₂) materials have been the focus of many promising applications due to their low-cost, availability and biocompatible properties. In this study, mesoporous anatase TiO₂ nanoparticles were synthesised using a green chemistry approach. This visible-light active photocatalyst was prepared *via* a simple and solvent free precipitation method at low temperatures using titanium tetraisopropoxide (TTIP) as a precursor and soluble starch as the template. The effect of initial solution pH and concentration of TTIP on surface morphology and photocatalytic activities of TiO₂ nanoparticles were evaluated. Based on the results obtained, the TiO₂ nanocatalyst prepared using 0.01 mol of TTIP under basic conditions revealed the best photocatalytic activity. The as-synthesised nanoparticles were further characterised using X-ray powder diffraction (XRD), scanning electron microscopy (SEM) and nitrogen adsorption analysis (NAA). The XRD spectrum confirmed that the catalyst was composed of anatase tetragonal TiO₂ phase. The Brunauer–Emmett–Teller (BET) surface area of 81.59 m² g⁻¹ proved the presence of mesopores (average pore size = 8.7 nm) which partially contributed to and catalysed the photodegradation process of methylene blue (MB) solution under sunlight. The effects of various parameters such as initial dye concentration, catalyst dosage and recyclability of the catalyst were evaluated to determine the best conditions. Results obtained suggest that TiO₂ nanoparticles synthesised through the green chemistry approach under optimum conditions exhibited an effective photodegradation process of MB solution under sunlight.

Received 25th July 2017
Accepted 6th October 2017

DOI: 10.1039/c7ra08187a

rsc.li/rsc-advances

1 Introduction

Titanium dioxide (TiO₂) is one of the most extensively studied materials due to its harmless nature and good chemical and thermal stability.¹ Titanium dioxide possesses high potential because of its availability and low cost. It is a binary metal oxide that exists in three different polymorphs; namely anatase, rutile and brookite. These polymorphs exhibit different bandgap energies with rutile TiO₂ (3.0 eV), anatase TiO₂ (3.2 eV) and brookite TiO₂ (~3.2 eV). In past decades, TiO₂ has received great attention for applications such as self-cleaning, solar cells, gas sensors,² anti-fogging, deodorisation and waste water remediation due to its superhydrophilic property.³ Among these applications, photocatalysis is considered to be the most practical due to its usage of sunlight to decompose organic pollutants.^{4,5} The mechanism involved in photocatalysis reaction exerted by semiconductors,^{6–8} mainly discussed the formation

of free electrons and holes in the conduction and valance band region as explained in the literature.^{2,10,20,21}

Many methods such as sol gel route,^{9,10} hydrothermal,¹¹ polyol synthesis,¹² and precipitation¹³ had been reported in the synthesis of TiO₂ nanoparticles (NPs). Among these methods, the sol-gel technique employed a low temperature process. However, the end product would contain high carbon content when organic reagents are used during the experiments. Hydrothermal methods have been used to synthesise metal oxides directly from solution but most of the earlier studies done on synthesis of TiO₂ NPs using a hydrothermal method required high temperatures which resulted in the formation of polydispersed powders.¹² The polyol process is the most well-known method among the production of metal oxides. Even though this process is able to control various particles property, it employs large amount of polyhydroxy alcohol (solvent) which makes this synthetic route environmentally unfavourable and unsafe. Up to this point in time, very little work has been reported on the synthesis of TiO₂ NPs under the precipitation process using the green chemistry approach.

Green chemistry denotes the implementation of chemical processes and products to reduce the use of substances hazardous towards human and the environment.¹⁴ Non-toxic solvents, closed reactors, and harmless waste production are

^aNanomaterials Research Group, School of Chemical Sciences, Universiti Sains Malaysia, Penang, Malaysia. E-mail: hlee@usm.my^bNano Hybrid Materials Group, School of Chemical Sciences, Universiti Sains Malaysia, Penang, Malaysia^cSurface Analysis and Materials Engineering Research Group, School of Engineering & Information Technology, Murdoch University, Murdoch, WA 6150, Australia

normally the factors used in order to reduce the impact on environment by easing waste disposal. Thus, a method can be recognised as a green technique if any previous method was altered according to the twelve principles of the 'Green Chemistry Principles'.¹⁵ Designing a method, according to green chemistry principles, results in an economical, safer, non-toxic and simpler route of synthesis. Therefore, green synthesis of NPs is considered an improved approach as it is environmentally friendly, sustainable, and relatively reproducible and the end products are often more stable.¹⁶

In this article, the focus is on developing a green technique adopting the fast precipitation method at a low temperature to synthesise TiO₂ Nanoparticles (NPs) using titanium tetraisopropoxide as the source of titanium, water as solvent and starch as template. It is postulated that this modified method minimises the impact on the safety of living organism and the environment. The effects of the pH and concentration of the precursor on TiO₂ NPs and their potential on self-cleaning application were also explored.

2 Experimental

2.1 Materials

Titanium(IV) tetraisopropoxide, TTIP $\geq 97\%$ purity (Sigma-Aldrich, Co., USA), soluble starch (System), ammonium hydroxide, NH₄OH (Fluka Analyticals, Sigma-Aldrich, Co., Germany), purchased pure anatase, $\geq 99\%$ (Sigma-Aldrich, Co., USA), methylene blue, MB (QREC, Grade AR, (Asia) Sdn. Bhd, Malaysia). All reagents were used as purchased and without further purification.

2.2 Synthesis of TiO₂ nanoparticles

The TiO₂ NP was synthesised based on the ZnO synthesis work by Zhang and the co-workers¹⁶ with some modifications. In a typical procedure, soluble starch was dissolved in 150 mL of boiling distilled water. Then, 0.01 mol of titanium tetraisopropoxide (TTIP) was added into the starch solution under stirring for 5 min at 85 °C. Yellow solution with white precipitates were formed after adjusting the pH of solution to basic (pH 9.0)/neutral (pH 7.0)/acidic (pH 5.0) by slowly adding ammonium hydroxide (NH₄(OH)) solution with constant stirring for 30 min. The resulting precipitate was centrifuged at 8500 rpm for 10 min, followed by several cycles of washing with distilled water and finally dried in an oven at 50 °C. The dried as-obtained powder was further calcined in air at 500 °C for 2 h to obtain TiO₂ nanoparticles (NPs).

2.3 Characterisations of TiO₂ nanoparticles

The crystallinity and phase purity of the synthesised photocatalyst was analysed by powder X-ray diffraction (XRD) (PW 3040/60 X'PERT PRO, PANalytical) using CuK α (1.541 Å) radiation in the range $2\theta = 10\text{--}90^\circ$. The specific surface area and pore size distribution studies were measured by nitrogen adsorption isotherms using a N₂ adsorption analyser (NAA) (Micromeritics ASAP 2020 Surface Adsorption Porosimeter (SAP)). The Brunauer–Emmett–Teller (BET) and Barrett–Joyner–Halenda (BJH)

models were used to estimate the surface area and pore size of the TiO₂ NPs. The TiO₂ NPs was further characterised by field emission scanning electron microscope (FESEM) (Leo Supra 50 VP Field Emission SEM) to determine its surface morphology. An acceleration electron voltage of 10 kV voltage was applied to obtain the FESEM images. Further analysis was carried out using high-resolution transmission electron microscopy (HRTEM) (TECNAI G2 20 S-TWIN, FEI) at 200 kV. X-ray photoelectron spectroscopy (XPS) was carried out using high resolution X-ray photoelectron spectroscopy Axis – Ultra DLD, XPS, Kratos with monochromatic AlK α (1486.6 eV), X-ray radiation (15 kV and 10 mA) and equipped with a hemispherical analyser which operated at 150 W. All the reported binding energy (BE) data were calibrated using the C 1s from C–H at 284.6 eV. Curve fitting was accomplished using CASAXPS (version 2.3.17) and a GL (30) Gaussian (70%)–Lorentzian (30%) profile, and the standard Shirley background was used for fitting the components.

2.4 Evaluation of photocatalytic activities

The photocatalytic activities of the TiO₂ NPs obtained were evaluated *via* the photocatalytic oxidation of methylene blue (MB) under sunlight irradiation. Prior to irradiation, 0.1 g of calcined TiO₂ NPs was dispersed in 200 mL MB (6 mg L⁻¹) and the solution was magnetically stirred for one hour in darkness to reach adsorption equilibrium. The MB solution with photocatalyst was exposed to sunlight (75–120 kLux) for two hours. During irradiation, 10 mL of the mixture was collected and centrifuged for every 15 min. The degradation efficiency of MB solution was analysed using UV-vis spectrometer (LAMBDA 25 UV/Vis Systems). Peaks were observed to be present between 600 to 700 nm. The conversion of MB solution can be calculated using the following equation:

$$R = \frac{(C_0 - C_t)}{C_0} \times 100\% \quad (1)$$

where C_0 represents the initial concentration of MB solution and C_t signifies concentration of MB solution during irradiation.

3 Results and discussion

3.1 XRD analysis

Fig. 1 illustrates the powder X-ray diffraction (XRD) pattern of synthesised TiO₂ NPs under different conditions. The sharp peaks obtained at 2θ values 25.3, 37.9, 48.4, 53.9, 55.3, 62.7, 70.1, 74.0 and 82.4 (PDF 98-005-9309) were equivalent to the planes (101), (004), (200), (105), (211), (204), (116), (215) and (303), indicated tetragonal structure of anatase TiO₂ nanoparticles. However, for TiO₂ NPs synthesised under acidic condition (pH 5), a weak diffraction peak at $2\theta = 31^\circ$ (PDF 98-010-5395) due to (121) face of brookite phase with orthorhombic crystalline structure was observed. Besides, for uncalcined TiO₂ powder, a very broad peak around 25.5° was attributed to the characteristic diffraction peak of the amorphous state of TiO₂. Once the as-prepared TiO₂ powder was calcined, the intensity of



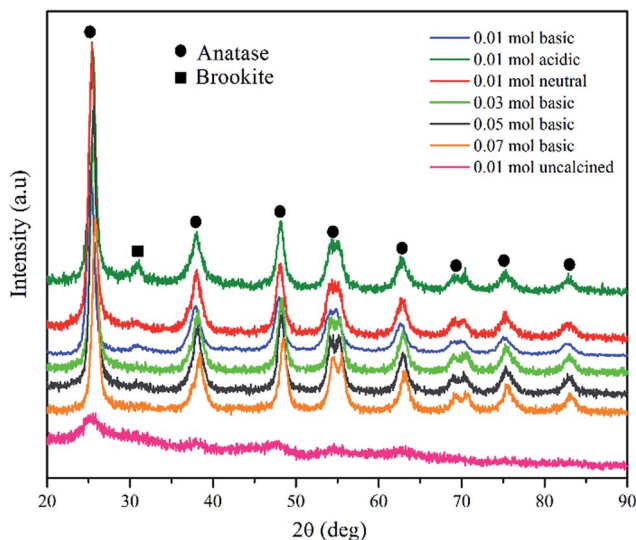


Fig. 1 X-ray patterns of TiO_2 NPs synthesised under different initial pH and concentration of TTIP.

XRD peaks became visible confirming that the TiO_2 powder underwent a calcination process. This confirms the occurrence of a transition from amorphous to crystalline anatase phase.

The average crystallite size, d -spacing, full-width at half maximum (FWHM) were determined using Rietveld refinement (Highscore Expert software). The influence of the concentration of TTIP and pH of initial solution on the crystallite sizes of the TiO_2 samples were listed in Table 1. The results show that with increasing TTIP concentration and reduction in the initial solution pH, the FWHM of the diffraction peak decreases and become narrower suggesting that the average crystallite size has become bigger correspondingly. This indicates that the enhancement of the crystallinity, stems from the increment of the crystalline volume ratio due to the size enlargement of the nuclei.¹⁷

3.2 N_2 adsorption and desorption analysis

The N_2 adsorption–desorption isotherms of the as-obtained TiO_2 NPs synthesised using different concentration of TTIP and initial solution pH are displayed in Fig. 2(a). Except for purchased pure anatase powder, all the curves exhibited the Type IV isotherm with H3 hysteresis loop of steep condensation

Table 1 Crystallographic parameters calculated by Rietveld refinement for TiO_2 NPs synthesised under various conditions. GOF: Goodness of Fit

| Samples | 2θ (degree) | d -spacing | FWHM | Crystallite size (nm) | GOF |
|------------------|-----------------------|--------------|-------|--------------------------|------|
| 0.01 mol basic | 25.4 | 3.49 | 0.980 | 8.9 | 1.90 |
| 0.01 mol neutral | 25.3 | 3.52 | 0.969 | 11.6 | 1.89 |
| 0.01 mol acidic | 25.5 | 3.49 | 0.831 | 12.2 | 1.26 |
| 0.03 mol basic | 25.6 | 3.47 | 0.907 | 14.2 | 1.89 |
| 0.05 mol basic | 25.7 | 3.48 | 0.839 | 14.3 | 1.46 |
| 0.07 mol basic | 25.9 | 3.44 | 0.824 | 15.1 | 1.99 |

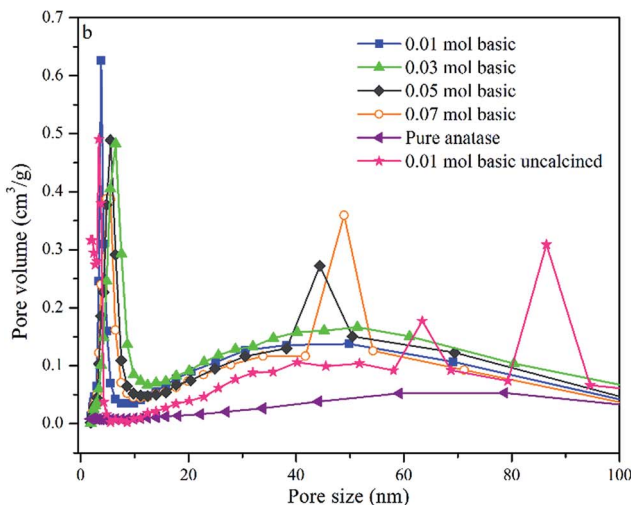
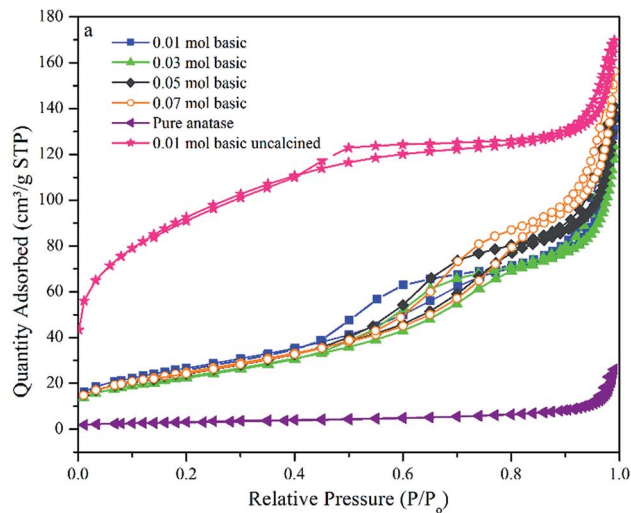


Fig. 2 (a) N_2 adsorption/desorption isotherm and (b) BJH pore size distribution TiO_2 NPs synthesised under different initial pH and concentration of TTIP.

at $P/P_0 = 0.4$ – 0.6 , indicating existence of small mesopores. Isotherms with type H3 hysteresis loop suggest the presence of irregular long, slit-like narrow pores according to IUPAC classification. However, the condensation steep shifted to high relative pressure $P/P_0 = 0.9$ – 1.0 , suggesting the occurrence of macropores.¹⁶ The Barrett–Joyner–Halenda (BJH) pore size distribution for all synthesised samples as shown in Fig. 2(b), displayed the bimodal pore size distribution. As-prepared TiO_2 NPs (0.01 mol TTIP, pH 9) without calcination has the lowest average pore diameter of 3.4 nm with narrow distribution. This narrow pore size distribution remained with a slight increase in pore size (3.7 nm) after underwent calcination process. When the concentration of TTIP increased to 0.03 mol, 0.05 mol and 0.07 mol, the mean pore size increased to 4.8 nm, 5.5 nm and 6.5 nm, respectively with a broadened pore size distribution.

It is also interesting to note that Brunauer–Emmett–Teller (BET) specific surface area also changed with the amount of precursor used as shown in Table 2. It was observed that,



Table 2 Textural parameters and Langmuir–Hinselwood first-order constants for the degradation of MB by mesoporous TiO₂ NPs samples prepared with different concentration of TTIP and pH of initial solution

| Concentration of precursor TTIP (mol) | Initial solution pH | BET (m ² g ⁻¹) | Crystallite size (nm) | <i>k</i> (min ⁻¹) | <i>R</i> ² |
|---------------------------------------|---------------------|---------------------------------------|-----------------------|-------------------------------|-----------------------|
| Pure anatase powder | — | 10.4 | — | 0.079 | 0.997 |
| 0.01 | 9.0 | 87.2 | 8.9 | 0.169 | 0.996 |
| 0.01 | 7.0 | 81.6 | 11.6 | 0.048 | 0.976 |
| 0.01 | 5.0 | 72.9 | 12.2 | 0.036 | 0.979 |
| 0.03 | 9.0 | 80.8 | 14.2 | 0.028 | 0.984 |
| 0.05 | 9.0 | 80.1 | 14.3 | 0.016 | 0.980 |
| 0.07 | 9.0 | 78.5 | 15.1 | 0.015 | 0.977 |

surface area changed from 87.2 to 78.5 m² g⁻¹, which indicates that the increase in concentration of precursor decreases the surface area and subsequently resulting in an increase of the particle size of the samples. Moreover, the surface area of uncalcined TiO₂ was decreased from 309.7 to 87.2 m² g⁻¹ when the sample was introduced with high heating treatment. This is an indication of removal of organic template (starch) resulting in enlargement of pore size, which led to the decrease in surface area.^{18,19} Also, it was verified that all the synthesised samples revealed higher BET surface area as compared to pure anatase nanopowder (10.4 m² g⁻¹).

3.3 UV-visible diffuse reflectance spectroscopy

The absorption spectra of all TiO₂ NPs synthesised samples using various concentrations of TTIP and different initial solution pH are shown in Fig. 3(a). A significant red shift in the band gap of TiO₂ NPs synthesised using 0.01 mol TTIP under basic condition were observed from the variation of $(\alpha h\nu)^2$ with photon energy ($h\nu$) compared to other samples. The extrapolated line drawn (Fig. 3(b)) for pure anatase and synthesised TiO₂ NPs corresponds to the bandgap of 3.20 eV and 3.00 eV, respectively. This suggests that the optical bandgap of the TiO₂ NPs has been reduced substantially compared to purchased pure anatase. In addition, e⁻ and h⁺ pairs can be generated, even though the particle is irradiated with longer wavelength-visible light.

Also, as shown in Fig. 3(a), the bandgaps of pure anatase, 0.01 mol (basic), 0.01 mol (neutral), 0.01 mol (acidic), 0.03 mol, 0.05 mol, 0.07 mol were determined to be 3.20, 3.00, 3.03, 3.07, 3.05, 3.07, and 3.07 eV, respectively. Therefore, by increasing the initial pH solution to basic the bandgaps of the products decreases accordingly. The decrease of bandgap could be due to the localized gap states induced by Ti³⁺ self-doping. This result also indicates that the concentration of Ti³⁺ in the TiO₂ products increased with increasing pH of initial solution (basic).³⁷ The existence of defects in the self-doped TiO₂ samples can further be confirmed by XPS analysis later.

3.4 Structures and morphologies

Fig. 4 displays the FESEM images of synthesised TiO₂ NPs under different concentration of TTIP and initial solution pH. FESEM image of Fig. 4(a) belongs to uncalcined TiO₂ sample where the particles are large and agglomerated. All samples exhibited

irregular spherical structures with rougher surfaces after the calcination process because calcination would enhance porous morphology for the as-synthesised TiO₂ NPs. From Fig. 4(b)–(d), it was observed that the particle size decreased as the pH of

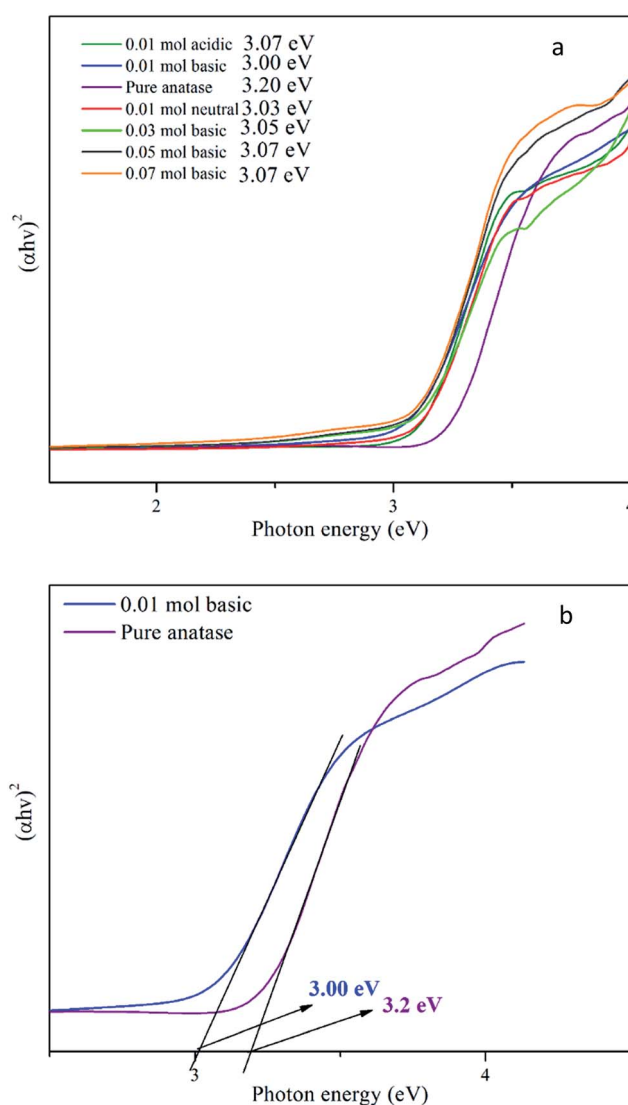


Fig. 3 (a) Bandgap of TiO₂ NPs synthesised using various concentration of TTIP and initial pH solution (b) compared bandgap spectra of synthesised sample and pure anatase.



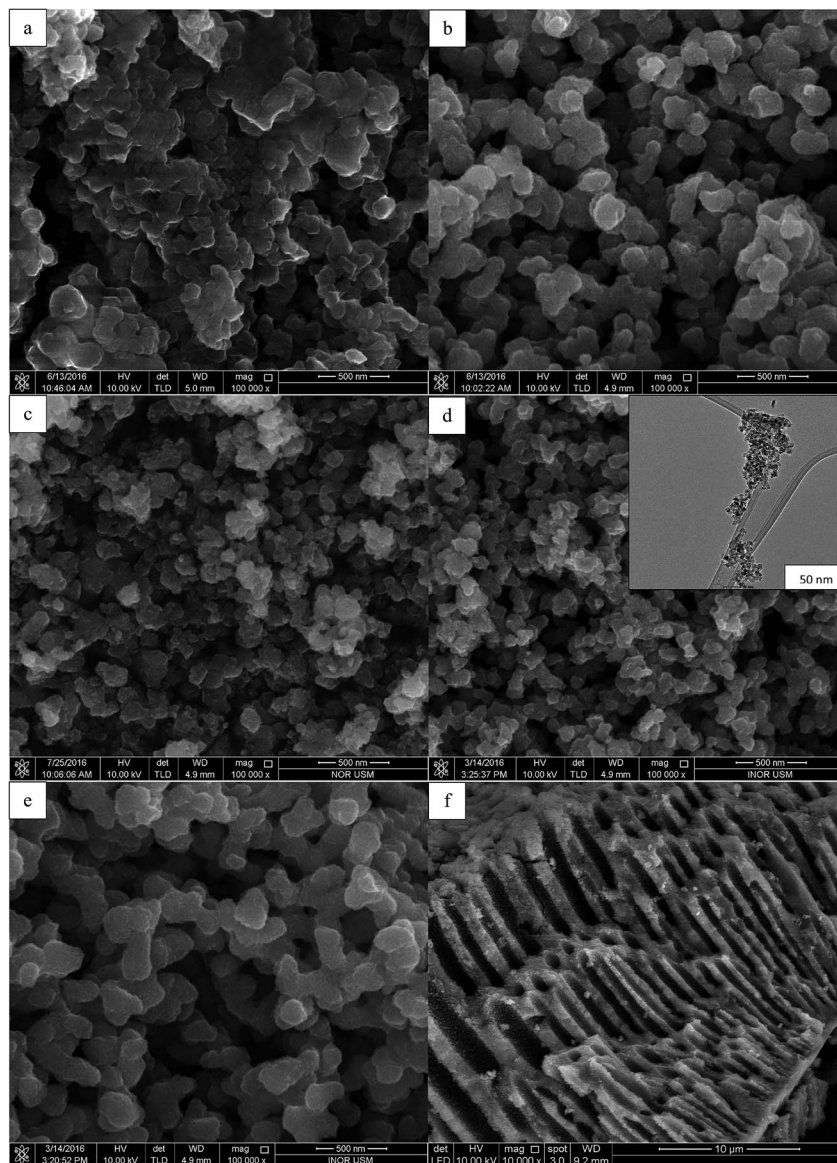


Fig. 4 FESEM micrographs (100 000 \times) of the TiO₂ NPs synthesised using (a) uncalcined TiO₂, (b) 0.01 mol TTIP, pH 5, (c) 0.01 mol TTIP, pH 7, (d) 0.01 mol TTIP, pH 9, insert: HRTEM image, (e) 0.07 mol TTIP pH 9, (f) pore channels of TiO₂ NPs (10 000 \times).

initial solution increased. Fig. 4(b) shows the morphology of sample synthesised using 0.01 mol TTIP under acidic condition (pH 5) has particle size of 99.2 ± 6.7 nm. When the pH of initial solution further increased to basic (pH 9), the particle size reduced drastically to 64.19 ± 2.6 nm. This is further confirmed with the HRTEM image (insert of Fig. 4(d)) which indicated that the size of synthesised TiO₂ NPs is in the nano range (20–70 nm). On the other hand, enlargement of particle size can be observed in Fig. 4(e) as the concentration of precursor was increased to 0.07 mol with diameter 80.20 ± 3.3 nm. This is due to enhanced coagulation and sintering resulting from the large concentration of TiO₂ nuclei generated at high TTIP precursor concentrations.^{20,21}

Besides, the high-resolution SEM images could also give information on the meso or macroscopic properties. Fig. 4(f) demonstrates the extension of the irregular parallel-arranged

long macro and mesoscopic channels through the material from the side view of the sample. Such open ended tube like channels could serve as ideal transport routes for introducing liquid phase into the interior of the framework of TiO₂.^{18–21}

3.5 Possible formation mechanism of mesoporous TiO₂


Although the exact formation mechanism of the mesoporous TiO₂ particles is not very clear, it is postulated that the soluble starch plays a key role in the formation of the mesoporous structures. Since starch is a polysaccharide carbohydrate, it can solubilise well in the boiling water. A dense formed when the starch granules swelled and burst, and the smaller amylose molecules started leaching out of the granules. Nucleation and initial crystal growth starts to take place when the precursor (Ti⁴⁺) diffuse and form complexes with amylose molecules near




the interspaces between swollen starch microspheres. In most cases, the van der Waals interactions between the surface molecules of the nanocrystallites represent the driving force for self-assembly, and then TiO₂ can be assembled to form compact uniform nanoparticles around the inflated starch granules. After calcination at 500 °C for two hours, the swollen starch gel granule template was removed leaving mesoporous structures around the TiO₂ particles as illustrated in Scheme 1.^{16,22}

Meanwhile, the reactions for the formation of anatase TiO₂ NPs are predicted as below:²³


Hydrolysis:



Condensation:



Crystallisation *via* calcination:



where x = number of water molecules.

TiO₂ nanoparticles were formed when titanium isopropoxides underwent hydrolysis and condensation. Initially, the hydrolysis process of titanium isopropoxides in an aqueous media occurred and titanium hydroxides (Ti(OH)₄) was formed as an intermediate as shown in eqn (2). Ti(OH)₄ is usually not stable and hence, it would go through the condensation process to produce amorphous hydrous oxide precipitates (TiO₂ · xH₂O) as stated in eqn (3). The formed TiO₂ · xH₂O precipitates were then subjected to the calcination process at 500 °C to remove the water molecules to form the anatase crystalline TiO₂ NPs (eqn (4)) which were confirmed in the XRD pattern earlier.


3.6 XPS analysis

XPS analysis was further performed to investigate the chemical states of Ti and O in the synthesised TiO₂ NPs. The XPS spectrum Ti, O and C element without any impurities for TiO₂ NPs is shown in Fig. 4. The XPS spectra of Ti 2p and O 1s in Fig. 5(a) and (b) confirmed the chemical compositions of TiO₂. For the Ti 2p spectra, two primary peaks are attributed to the characteristic Ti 2p_{1/2} and Ti 2p_{3/2} peaks of Ti⁴⁺. The symmetric curve

with a binding energy located at 458.7 and 464.3 eV is in agreement with that of Ti⁴⁺ 2p_{3/2} and Ti⁴⁺ 2p_{1/2} in TiO₂, respectively.²⁴

Besides, the Ti 2p peaks were deconvoluted into another two peaks: Ti³⁺ 2p_{3/2} at 457.9 eV and Ti³⁺ 2p_{1/2} at 463.3 eV which can be claimed as self-doped TiO₂ with the presence of Ti³⁺. Zhou *et al.*²⁵ and Mai W. *et al.*²⁶ reported that TiO₂ surface defects (Ti³⁺) played a significant role as they are active sites for oxygen adsorption and for trapping the electron to prevent the recombination of electrons and holes. In addition, surface Ti³⁺ sites also reduced the bandgap of TiO₂ NPs and provided the unique activity and selectivity in the target reactions at relatively high wavelengths. Ti⁴⁺ reduction to Ti³⁺ is usually accompanied by vacuum annealing or thermal treatment (calcination). Self-doped TiO₂ can also be generated by the carbon formed from pyrolysis of titanil organic compounds. In the calcination process, Ti⁴⁺ ions accept electrons from these reducing gases or lattice oxygens which are usually removed from stoichiometric TiO₂. At low temperature (300 °C), hydrogen interacted physically with adsorbed oxygen on the surface of TiO₂. When the thermal temperature was raised higher than 300 °C, electrons were transferred from the H atoms to the O atoms in the lattice of TiO₂. Then, the oxygen vacancies were formed when the O atom left with the H atom in the form of H₂O. The interface between H₂ and TiO₂ progressed more significantly as the calcination temperature increased up to 450 °C, in which the electrons transferred from oxygen vacancies to Ti⁴⁺ ions, and then Ti³⁺ ions were formed. In this study, the synthesised TiO₂ NPs was calcined at 500 °C, hence, more Ti³⁺ ions were produced rather than formation of oxygen vacancies (where the oxygen vacancy XPS peaks invisible in the result obtained). Meanwhile, the possible mechanism for the reduction reaction caused by the pyrolysis of titanil organic compounds is that the carbon from organic component carbonizing could reduce Ti⁴⁺ to Ti³⁺ at high temperature. Basically, the reduction process of Ti⁴⁺ to Ti³⁺ takes place due to the reduction by electron donors such as H₂, C, or lattice oxygen in TiO₂.²⁵ In the O 1s spectrum, only two peaks at binding energies 529.3 eV, and 530.2 eV are observed which are attributed to lattice oxygen and surface adsorbed OH group.²⁷

The C 1s spectrum (Fig. 5(c)) includes a strong peak at 284.6 eV and a shoulder at 288.0 eV. These features correspond to two forms of carbon species in the sample. The peak at

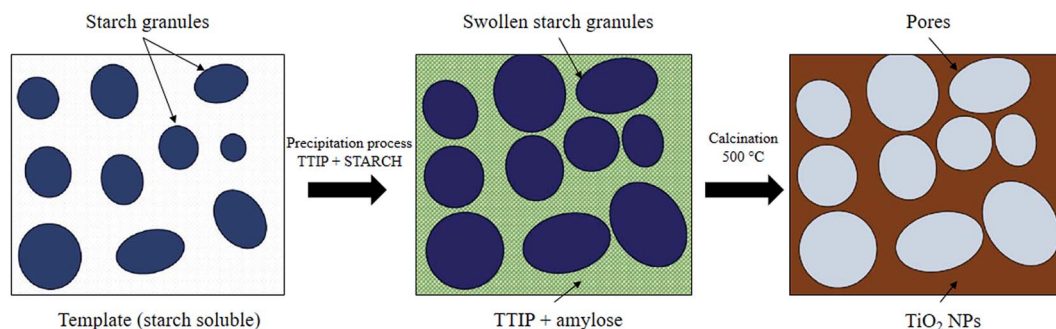

Scheme 1 Possible formation of pores in TiO₂ NPs.



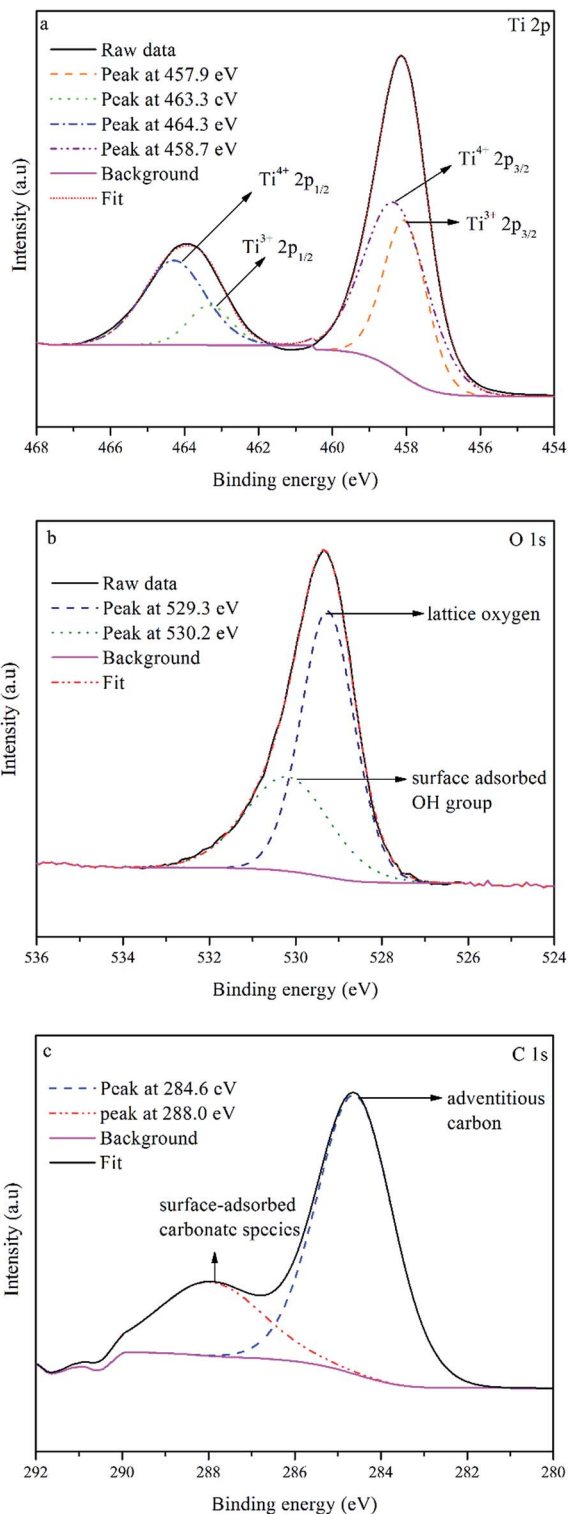


Fig. 5 High-resolution XPS spectra of (a) Ti 2p, (b) O 1s and (c) C 1s of synthesised TiO₂ NPs using 0.01 mol TTIP under basic condition.

284.6 eV on the XPS spectra is associated with elemental carbon from organic impurities in the environment that were adsorbed onto the surface of TiO₂ and the peak at 288.0 eV is associated with surface-adsorbed carbonate species resulting from carbon residues on the surface of TiO₂.²⁸ Besides, it is also proven that

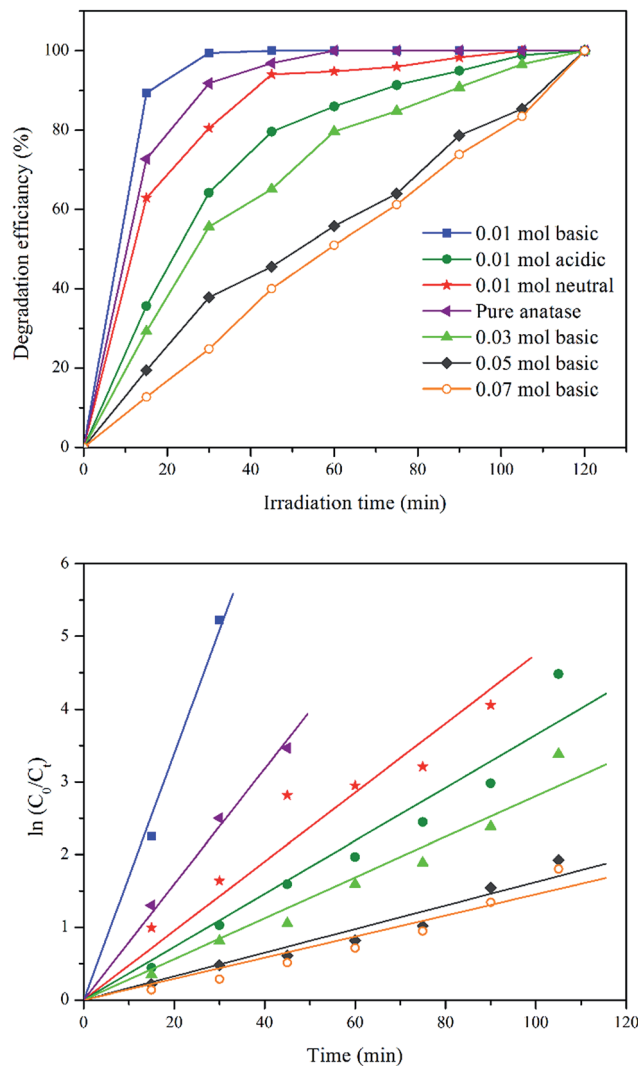


Fig. 6 Degradation efficiency and first-order kinetics for TiO₂ NPs synthesised using different TTIP concentration and initial solution pH.

TiO₂ NPs synthesised showed no carbon doped material originated from the starch, since peak 282.0 eV which assigned to Ti-C bond is absent in the obtained XPS spectrum. Thus, from the XPS result, self-doped TiO₂ NPs is the possible factor that the photocatalytic activity occurred near to visible range than at UV range.

3.7 Photocatalytic activity and kinetic studies of TiO₂ NPs

3.7.1 Effect of TTIP concentration and initial solution pH.

The photodegradation of methylene blue (MB) dye was used in order to demonstrate their potential environmental application. Fig. 6 shows the degradation rate and the pseudo-first order rate constants of the photocatalyst system were estimated from the slopes of linear plots $\ln(C_0/C_t)$ versus time. The reaction rate constants (k) were calculated according to the Langmuir-Hinshelwood first order rate model which is generally used for photocatalytic degradation process when the initial concentration of pollutant is low,



$$\ln\left(\frac{C_0}{C_t}\right) = kt \quad (5)$$

where C_0 and C_t are the concentrations of MB aqueous solution at irradiation times of 0 and t min, respectively.

According to Table 2, the activity of the synthesised TiO₂ photocatalyst decreased in order 0.01 mol basic > purchased pure anatase > 0.01 mol neutral > 0.01 mol acidic > 0.03 mol basic > 0.05 mol basic > 0.07 mol basic. The photoreactivity experiments have shown that MB photodegradation depends on the particle size of the TiO₂ powders. Since the concentration of TTIP increased from 0.01 mol to 0.07 mol and the initial solution pH reduced from 9.0 (basic) to 5.0 (acidic), the degradation rate reduced from 0.169 to 0.015 min⁻¹ and from 0.169 to 0.036 min⁻¹, respectively. These results suggest that as we increased the concentration of TTIP and reduced the initial solution pH, incomplete nucleation occurred due to supersaturation of solution which led to the increase in particle size and hence, decrease in the specific surface area of as-synthesised powder, indirectly reducing the photocatalytic degradation efficiency of MB solution. Besides, an increase in crystallite size of synthesised TiO₂ NPs under various concentrations of TTIP and initial solution pH (obtained from XRD data), reduces the photocatalytic activity.^{18,29}

3.7.2 Effect of catalyst dosage. In order to study the effect of catalyst dosage on degradation kinetics of MB solution, different amounts of TiO₂ NPs (0.05, 0.10, 0.20 or 0.40 g) synthesised using 0.01 mol TTIP under basic condition were employed (shown in Fig. 7). The regression correlation coefficients (Langmuir–Hinselwood constant; R^2), together with the calculated kinetics data of the photodegradation of MB, are given in Table 3. The result demonstrated that degradation rate decreased from 0.169 to 0.069 min⁻¹ as the catalyst loading into MB solution increased from 0.1 to 0.4 g. This means that the relative efficiency of the catalyst is lowered and a limiting rate is achieved when high amounts of TiO₂ NPs are used. One possible explanation for such behaviour is that when the photocatalyst amount surpassed 0.1 g, part of the catalyst surface probably became unavailable for photon absorption and dye adsorption under such conditions or deactivation of activated molecules by collision with ground state molecules may occur at higher catalyst loading and thus, bringing little stimulation to catalytic reaction.^{30,31} However, the catalyst dosage was further decreased to 0.05 g to determine its degradation efficiency. It is clear that the rate of degradation decrease proportionally with the decrease in the amount of the catalyst. This due to the available number of photocatalyst active sites can be insufficient for adsorption to a greater number of dyes.

3.7.3 Effect of initial dye concentration. Fig. 8 shows the degradation rate of dye measured under different concentrations of dye MB solution (6, 10, 20 and 40 ppm) with optimum catalyst loading (0.1 g TiO₂ NPs). The regression correlation coefficients (R^2) were obtained and the kinetics data of the photodegradation of MB were calculated and given in Table 4. The possible explanation for this behaviour is that as the initial concentration of the dye increases, the formation of intermediates increased during the course of reaction. Hence,

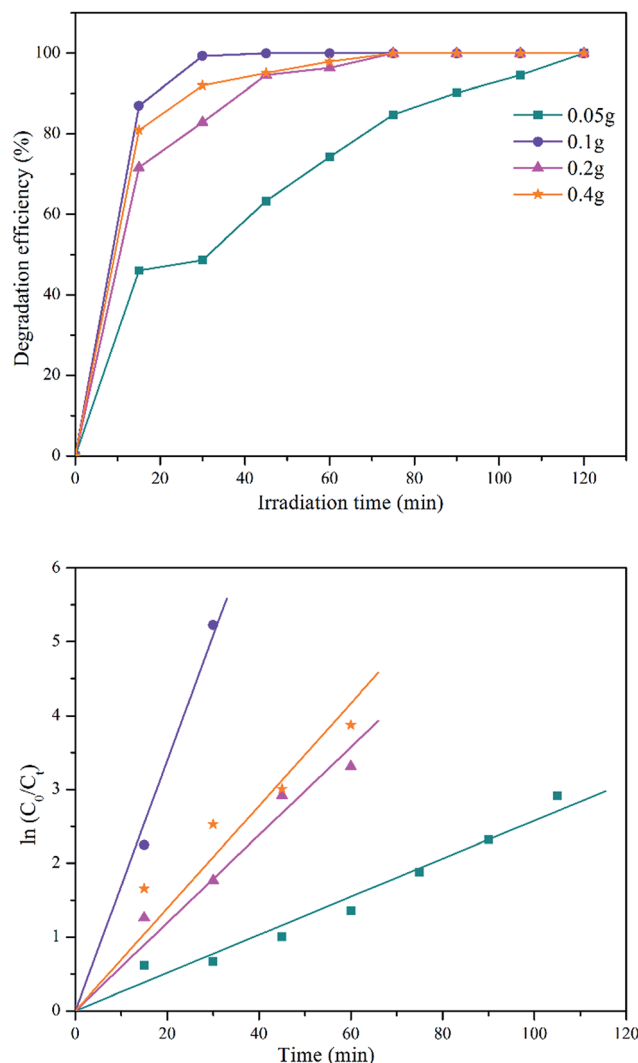


Fig. 7 Effect of catalyst dosage plot of MB removal percentage against irradiation time using different catalyst dosage and its first-order kinetic plots.

competition starts between the intermediates and the dye molecules for surface active sites of TiO₂ NPs leading to restriction of light penetration to the surface of the catalyst. This phenomenon indirectly reduces the degradation rate of MB solution at high concentration. Besides, the active sites of photocatalyst will be completely occupied by the dye molecules leading to the decrease in the generation of OH radicals and thus, inhibit the degradation process from occurring between

Table 3 First-order constants for the photodegradation of MB solution at different catalyst dosage

| Catalyst dosage (g) | k (min ⁻¹) | R^2 |
|---------------------|--------------------------|--------|
| 0.05 | 0.026 | 0.9870 |
| 0.1 | 0.169 | 0.9967 |
| 0.2 | 0.059 | 0.9860 |
| 0.4 | 0.069 | 0.9757 |



dye molecules and TiO₂ NPs.^{28,32,33} TiO₂ NP synthesised in present work has two folds better photocatalytic activity compared to the ZnO synthesised by Zhang and his co-workers.¹⁶ ZnO acquired 240 min to degrade 5 mg L⁻¹ of rhodamine B (RhB). Meanwhile, TiO₂ NPs synthesised using similar method as ZnO could degrade 6 mg L⁻¹ of MB solution in 45 minutes. Besides, several studies showed that the rate of degradation of methylene blue (low concentration: <10 ppm) is very low compared to photocatalytic activity of TiO₂ NPs in this study.^{18–20,28,30,34}

3.7.4 Regeneration and reusability of TiO₂ NPs. Ten cycles of photocatalytic activities were carried out to evaluate the stability of TiO₂ NPs (Fig. 9) after regeneration process. For each new cycle, the synthesised photocatalyst was washed in boiling distilled water for 15 min and oven dried overnight at 100 °C. After 10 cycles, the degradation efficiency of MB reduced only about 13.3% from 100% to 86.7%. The results revealed that the photocatalytic activity of TiO₂ NPs photocatalyst has a good

Table 4 Kinetic constants for the photodegradation of MB solution at different initial dye concentration

| Initial dye concentration (ppm) | k (min ⁻¹) | R^2 |
|---------------------------------|--------------------------|--------|
| 6 | 0.169 | 0.9967 |
| 10 | 0.046 | 0.9934 |
| 20 | 0.028 | 0.9757 |
| 40 | 0.009 | 0.9765 |

repeatability. The high stability of TiO₂ NPs in powder form generates a high photocatalytic activity, makes its separation from reaction solution quite difficult. The reduction in the degradation efficiency after 10 catalytic cycles, can be explained by the material loss during the recovering procedure because of the difficulty to avoid any loss of catalyst materials during the washing and filtration process.^{32–35}

After ten cycles of reusability test, TiO₂ NPs were analysed using XRD and FESEM to determine its phase, porosity and morphology stability. Fig. 10 showed XRD spectra of recycled TiO₂ NPs for ten times and freshly synthesised TiO₂ NPs. Based on the Fig. 10, synthesised TiO₂ NPs remained same as in anatase phase after ten washings. As it can be seen, the intensity of the peak belongs to anatase phase $2\theta = 25.6^\circ$ increased due to the heat treatment introduced after washing process for every cycle for overnight. Generally, heat treatment at high temperature could induce the crystallinity and phase transition of metal oxides.^{36,37} In this case, only increase in crystallinity was observed as the temperature used for each cycle was 100 °C. FESEM was used to analyse the surface morphology and porosity of TiO₂ NPs after ten recycles. Fig. 11(a–c) showed the ordered TiO₂ porous structures at different magnifications after 10 cycles of photocatalytic activities. The reused TiO₂ NPs still exhibited irregular parallel-arrayed long macro and mesoscopic channels through the material from the side view of the sample. No changes were observed on the walls of the TiO₂ NPs since

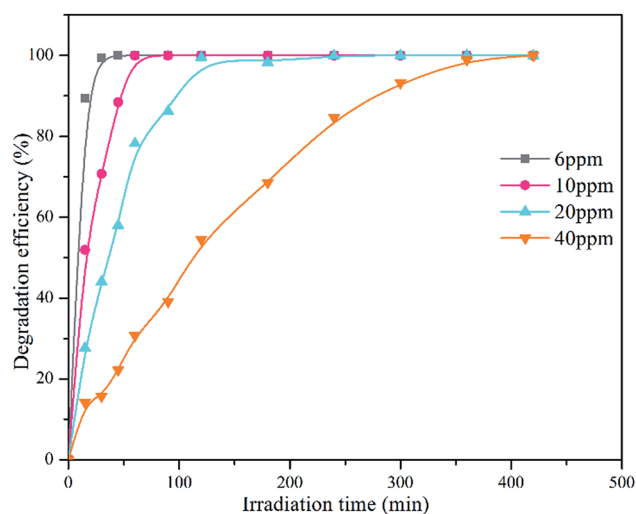


Fig. 8 Degradation efficiency of different initial concentration of MB solution and its first-order kinetic model plot.

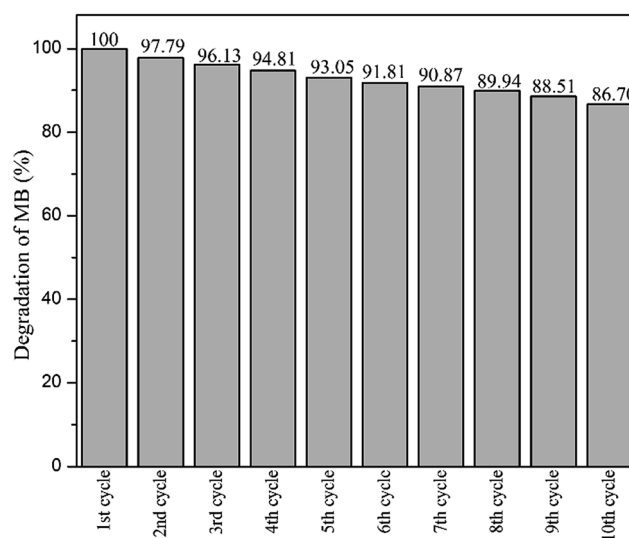


Fig. 9 Reusability test of synthesised TiO₂ NPs.



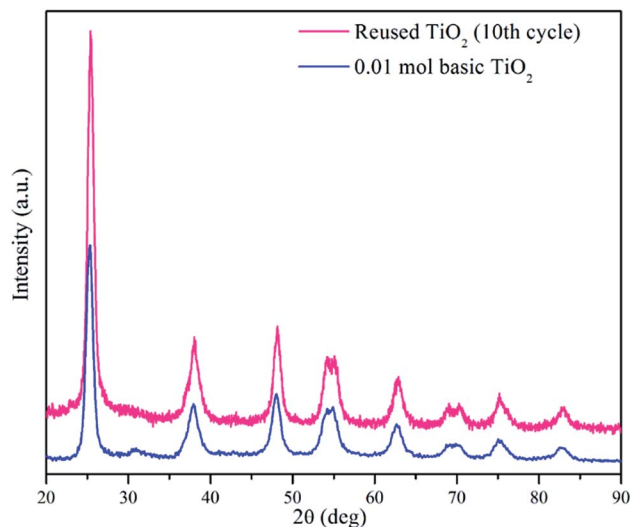


Fig. 10 XRD spectra of TiO_2 NPs after ten recycles.

TiO_2 surface was composed of pores. Besides, the particle size of recycled of TiO_2 NPs increased slightly to 68.83 ± 4.4 nm compared to the freshly synthesised TiO_2 NPs (64.19 ± 2.6 nm). The slight increase in particle size might cause by the heating process in overnight during every cycle.³⁸ Hence, we can conclude that the reusability test using boiling water in the washing process does not affect the stability of the TiO_2

NPs in term of morphology, phase and porosity of the metal oxide.

3.8 Photocatalytic reaction mechanism of Ti^{3+} surface defects

TiO_2 with surface defects enhances the photocatalytic activity by introducing a local state at the bottom of the conduction band (CB) in the range of 0.75 eV–1.18 eV so that it extends the photoresponse of TiO_2 from UV to visible light region. As a kind of defect, Ti^{3+} acts as an electron trap and results in the reduction of an electron hole pair recombination rate, thereby the subsequent reactions caused by the electrons and holes were dramatically improved.³⁹ In this case, electrons donors reacted with holes. The electron can be trapped by Ti^{4+} to generate an isolated Ti^{3+} ion as shown in eqn (6). In the presence of O_2 , the Ti^{3+} sites easily react with O_2 , leading to the formation of radicals such as $\cdot\text{O}_2^-$, $\text{HO}_2\cdot$, and $\cdot\text{OH}$ as shown in eqn (7) and (8). These $\cdot\text{OH}$ and $\text{O}_2^{\cdot-}$ species are able to degrade the MB molecules in solution. These $\cdot\text{OH}$ and $\text{O}_2^{\cdot-}$ species are able to assist in the degradation of the MB molecules in solution. $\cdot\text{OH}$ species reacts with H^+ ion to produce hydrogen peroxide (H_2O_2) as stated in eqn (9). The H_2O_2 is then reacted with the electron (e_{cb}^-) from TiO_2 and subsequently increases the concentration of $\cdot\text{OH}$ radical to enhance the degradation process as shown in eqn (10).

Meanwhile, the photogenerated holes due to transition of electron from valance band (VB) to the local state by Ti^{3+} have


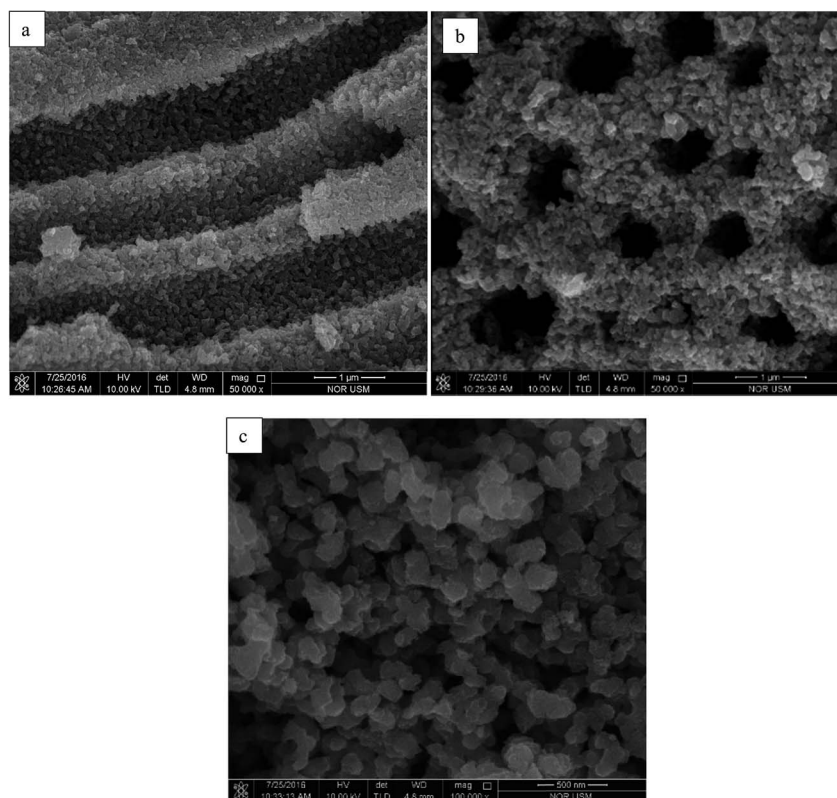


Fig. 11 FESEM micrographs of recycled TiO_2 NPs (a) pore channels of TiO_2 NPs, (b) pores on the surface of TiO_2 after 10 cycles and (c) magnified TiO_2 NPs.



strong oxidation ability and can directly degrade MB to produce less harmful products such as water and carbon dioxide.^{40,41} The charge transfer processes occurred in TiO₂ with surface defect may be as follows:^{38–41}



4 Conclusions

This study outlined the development of TiO₂ nanoparticles *via* green technique. Active mesoporous anatase TiO₂ NPs with small crystallite size (9 nm) was successfully synthesised using titanium tetraisopropoxide (TTIP) as the precursor, water as the solvent, and starch as the template using a low temperature precipitation method. The photocatalytic activities of prepared TiO₂ photocatalyst were evaluated using methylene blue (MB) aqueous solution at 6 ppm. The results clearly indicated that the sample synthesised using 0.01 mol TTIP under basic condition has smaller particle sizes (64.19 ± 2.6 nm) and higher specific area ($87.2 \text{ m}^2 \text{ g}^{-1}$) which contributed to better photocatalytic performance. XPS analysis indicates that TiO₂ NPs is active at near to visible range than the UV range is highly attributed to self-doped (Ti³⁺) of TiO₂ than the carbon-doped from starch employed in this green method. It was found that degradation kinetics of MB fitted the Langmuir–Hinselwood first order kinetics. The rate of photodegradation of MB solution decreased when the concentration of precursor increased and the initial pH of solution decreased. The optimum condition for photodegradation of MB solution at 6 or 10 ppm MB solution is by using 0.1 g TiO₂ NPs synthesised using 0.01 mol TTIP under basic condition. Besides, synthesised TiO₂ NPs revealed high stability against photodegradation process as it can be recycled up to 10 cycles. The method developed in this work is fast and environmentally friendly for the preparation of mesoporous TiO₂ NPs powders with good photocatalytic activities.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

This work was financially supported by the USM Research University Individual Grant (RUI: 1001/PKimia/811265).

Notes and references

1 Y. Ju, M. Wang, Y. Wang, S. Wang and C. Fu, Electrical properties of amorphous titanium oxide thin films for

- bolometric Application, *Adv. Condens. Matter Phys.*, 2013, 100.
- 2 S. Qiu and S. J. Kalita, Synthesis, processing and characterization of nanocrystalline titanium dioxide, *Mater. Sci. Eng., A*, 2006, 327, 435–436.
- 3 W. A. Daoud and W. S. Tung, Self-cleaning fibers *via* nanotechnology – a virtual reality, *J. Mater. Chem.*, 2011, 21, 7858–7869.
- 4 D. Tang and G. Zhang, Ultrasonic-assistant fabrication of cocoon-like Ag/AgFeO₂ nanocatalyst with excellent plasmon enhanced visible-light photocatalytic activity, *Ultrason. Sonochem.*, 2017, 37, 208–215.
- 5 Z. Wan, G. Zhang, X. Wu and S. Yin, Novel visible-light-driven Z-scheme Bi₁₂GeO₂₀/g-C₃N₄ photocatalyst: oxygen-induced pathway of organic pollutants degradation and proton assisted electron transfer mechanism of Cr(vi) reduction, *Appl. Catal., B*, 2017, 207, 17–26.
- 6 M. Pelaez, N. T. Nolan, S. C. Pillai, M. K. Seery, P. Falaras, A. G. Kontos, *et al.*, A review on the visible light active titanium dioxide photocatalysts for environmental applications, *Appl. Catal., B*, 2012, 125, 3331–3349.
- 7 D. Wu, M. Long, J. Zhou, W. Cai, X. Zhu, C. Chen, *et al.*, Synthesis and characterization of self-cleaning cotton fabrics modified by TiO₂ through a facile approach, *Surf. Coat. Technol.*, 2009, 203, 3728–3733.
- 8 M. Montazer and E. Pakdel, Functionality of nano titanium dioxide on textiles with future aspects: focus on wool, *J. Photochem. Photobiol., C*, 2011, 12, 293–303.
- 9 C. Colleoni, M. R. Massafra and G. Rosace, Photocatalytic properties and optical characterization of cotton fabric coated *via* sol-gel with non-crystalline TiO₂ modified with poly(ethylene glycol), *Surf. Coat. Technol.*, 2012, 207, 79–88.
- 10 K. Kądzioła, I. Piwoński, A. Kisielewska, D. Szczukocki, B. Krawczyk and J. Sielski, The photoactivity of titanium dioxide coatings with silver nanoparticles prepared by sol-gel and reactive magnetron sputtering methods – comparative studies, *Appl. Surf. Sci.*, 2014, 288, 503–512.
- 11 Z. Tan, K. Sato and S. Ohara, Synthesis of layered nanostructured TiO₂ by hydrothermal method, *Adv. Powder Technol.*, 2014, 26, 296–302.
- 12 S. K. Tripathy, T. Sahoo, M. Mohapatra, S. Anand and Y. T. Yu, Polyol-assisted synthesis of TiO₂ nanoparticles in a semi-aqueous solvent, *J. Phys. Chem. Solids*, 2009, 70, 147–152.
- 13 J. Morales, A. Maldonado and M. D. L. Olvera, Synthesis and characterization of nanostructured TiO₂ anatase-phase powders obtained by the homogeneous precipitation method, *10th International Conference on Electrical Engineering, Computing Science and Automatic Control (CCE)*, Mexico City, 30 September–4 October 2013, pp. 391–394.
- 14 M. N. Nadagouda, Green synthesis of nanocrystals and nanocomposites, *Mod. Aspects Bulk Cryst. Thin Film Prep.*, 2012, 395–412.
- 15 A. K. Maratha, Green technique-solvent free synthesis and its advantages, *Int. J. Res. Ayurveda Pharm.*, 2011, 2, 1079–1086.



- 16 G. Zhang, X. Shen and Y. Yang, Facile synthesis of monodisperse porous ZnO spheres by a soluble starch-assisted method and their photocatalytic activity, *J. Phys. Chem. C*, 2011, **115**, 7145–7152.
- 17 M. Gharagozlou, Influence of calcination temperature on structural and magnetic properties of nanocomposites formed by Co-ferrite dispersed in sol-gel silica matrix using tetrakis (2-hydroxyethyl) orthosilicate as precursor, *Chem. Cent. J.*, 2011, **5**, 19.
- 18 D. Zhang and G. Li, Al₂O₃-enhanced Macro/Mesoporous Fe/TiO₂ for Breaking Down Nitric Oxide, *Chem., Emiss. Control, Radioact. Pollut. Indoor Air Qual.*, 2014, **2011**, 2–14.
- 19 E. Y. Kim, D. S. Kim and B. T. Ahn, Synthesis of mesoporous TiO₂ and Its application to photocatalytic activation of Methylene Blue and *E. coli*, *Bull. Korean Chem. Soc.*, 2009, **30**, 193–196.
- 20 X. Wang, J. C. Yu, C. Ho, Y. Hou and X. Fu, Photocatalytic activity of a hierarchically macro/mesoporous titania, *Langmuir*, 2005, **21**, 2552–2559.
- 21 C. S. Kim, K. Nakaso, B. Xia, K. Okuyama and M. Shimada, A new observation on the phase transformation of TiO₂ nanoparticles produced by a CVD method, *Aerosol Sci. Technol.*, 2005, **39**, 104–112.
- 22 L. Q. Tang, W. Ni, H. Y. Zhao, Q. Xu and J. X. Jiao, Preparation of macroporous TiO₂ by starch microspheres template with assistance of supercritical CO₂, *BioResources*, 2009, **4**, 38–48.
- 23 S. Mahshid, Synthesis of TiO₂ nanoparticles by hydrolysis and peptization of titanium isopropoxide solution, *J. Mater. Process. Technol.*, 2007, **189**, 296–300.
- 24 B. Bharti, S. Kumar, H.-N. Lee and R. Kumar, Formation of oxygen vacancies and Ti³⁺ state in TiO₂ thin film and enhanced optical properties by air plasma treatment, *Sci. Rep.*, 2016, **6**, 1–12.
- 25 Y. Zhou, C. Chen, N. Wang, Y. Li and H. Ding, Stable Ti³⁺ self-doped Anatase-Rutile mixed TiO₂ with enhanced visible light utilization and durability, *J. Phys. Chem. C*, 2016, **11**, 6116–6124.
- 26 W. Mai, F. Wen, D. Xie, Y. Leng and Z. Mu, Structure and composition study of carbon-doped titanium oxide film combined with first principles, *J. Adv. Ceram.*, 2014, **1**, 49–55.
- 27 L. XiongBin, J. L. Li, B. Yang and Y. Yu, Ti³⁺ in the surface of titanium dioxide: Generation, properties and photocatalytic application, *J. Nanomater.*, 2012, 1–12.
- 28 K. Li, Z. Huang, X. Zeng, B. Huang, S. Gao and J. Lu, Synergetic Effect of Ti³⁺ and Oxygen Doping on Enhancing Photoelectrochemical and Photocatalytic Properties of TiO₂/g-C₃N₄ Heterojunctions, *ACS Appl. Mater. Interfaces*, 2017, **9**(13), 11577–11586.
- 29 M. D. G. de Luna, J. C. Lin Te, M. J. N. Gotostos and M. C. Lu, Photocatalytic oxidation of acetaminophen using carbon self-doped titanium dioxide, *Sustainable Environ. Res.*, 2016, **4**, 161–167.
- 30 A. Zyoud, A. Zu'bi, M. H. S. Helal, D. Park, G. Campet and H. S. Hilal, Optimizing photo-mineralization of aqueous methyl orange by nano-ZnO catalyst under simulated natural conditions, *J. Environ. Health Sci. Eng.*, 2015, **13**, 46.
- 31 S. K. Kavitha and P. N. Palanisamy, Photocatalytic and Sonophotocatalytic Degradation of Reactive Red 120 using Dye Sensitized TiO₂ under Visible Light, *J. Eng. Technol.*, 2011, 1–6.
- 32 R. J. Tayade, T. S. Natarajan and H. C. Bajaj, Photocatalytic degradation of Methylene Blue dye using ultraviolet light emitting diodes, *Ind. Eng. Chem. Res.*, 2009, **48**, 10262–10267.
- 33 U. G. Akpan and B. H. Hameed, Parameters affecting the photocatalytic degradation of dyes using TiO₂-based photocatalysts: A review, *J. Hazard. Mater.*, 2009, **170**, 520–529.
- 34 M. A. M. Salleh, D. K. Mahmoud, W. A. W. A. Karim and A. Idris, Cationic and anionic dye adsorption by agricultural solid wastes: A comprehensive review, *Desalination*, 2011, **280**, 1–13.
- 35 C. Randorn, J. T. S. Irvine and P. Robertson, Synthesis of visible-light-activated yellow amorphous TiO₂ photocatalyst, *Int. J. Photoenergy*, 2008, 1–6.
- 36 S. M. Lam, J. C. Sin and A. R. Mohamed, Parameter effect on photocatalytic degradation of phenol using TiO₂-P25/activated carbon (AC), *Korean J. Chem. Eng.*, 2010, **27**, 1109–1116.
- 37 Y. Chen and D. D. Dionysiou, Effect of calcination temperature on the photocatalytic activity and adhesion of TiO₂ films prepared by the P-25 powder-modified sol-gel method, *J. Mol. Catal. A: Chem.*, 2006, **244**, 73–82.
- 38 M. M. Khan, S. A. Ansari, D. Pradhan, M. O. Ansari, D. H. Han, J. Lee, *et al.*, Band gap engineered TiO₂ nanoparticles for visible light induced photoelectrochemical and photocatalytic studies, *J. Mater. Chem. A*, 2014, **2**, 637–644.
- 39 H. Lin, C. P. Huang, W. Li, C. Ni, S. I. Shah and Y. H. Tseng, Size dependency of nanocrystalline TiO₂ on its optical property and photocatalytic reactivity exemplified by 2-chlorophenol, *Appl. Catal., B*, 2006, **68**, 1–11.
- 40 L. B. Xiong, J. L. Li, B. Yang and Y. Yu, Ti³⁺ in the surface of titanium dioxide: Generation, properties and photocatalytic application, *J. Nanomater.*, 2012, 1–13.
- 41 L. Ma, I. Jia, X. Guo and L. Xiang, Current status and perspective of rare earth catalytic materials and catalysis, *Chin. J. Catal.*, 2014, **35**, 108–119.

