



Cite this: *RSC Adv.*, 2017, 7, 44874

A corn-inspired structure design for an iron oxide fiber/reduced graphene oxide composite as a high-performance anode material for Li-ion batteries†

Jianxin Cai,^a Pengfei Zhao,^a Zhipeng Li,^a Wei Li,^a Jing Zhong,^c Ji Yu^b and Zhenyu Yang^{id}*^b

In this paper, we successfully synthesized iron oxide (Fe₂O₃) fiber/reduced graphene oxide (rGO) composites with a "corn" structure by an electrospinning technique assisted by annealing treatment and a far infrared reduction process. The special structure consists of Fe₂O₃ fibers as the "corn cob" completely protected by multilayer rGO as the "sepal". Natural void space between the Fe₂O₃ fibers and rGO allows for the expansion of Fe₂O₃ upon lithiation; the good surface area and unblocked channels in the Fe₂O₃ fiber facilitates fast diffusion of Li⁺. An electrode with such structure shows excellent capacity (1085.2 mA h g⁻¹ at 0.1 A g⁻¹), and cycle life (407.8 mA h g⁻¹ at 5 A g⁻¹ for 1500 cycles with good coulombic efficiency). This is the longest cycle life for Fe₂O₃-based anode materials with excellent rate capability (e.g., >400 mA h g⁻¹ at 5 A h g⁻¹). In addition to Fe₂O₃, this "corn" structure can also be applied to other high capacity anode materials for next generation Li-ion batteries to improve cycle life and coulombic efficiency.

Received 10th August 2017
Accepted 14th September 2017

DOI: 10.1039/c7ra08846a

rsc.li/rsc-advances

1. Introduction

Recently, lithium-ion batteries (LIBs) have attracted much attention due to the rapid development of portable electronic devices, electric vehicles (EVs), and hybrid electric vehicles (HEVs).^{1–3} At present, most commonly used anode materials for commercial LIBs are based on graphite. However, graphite suffers from an inherently low theoretical charge storage capacity (372 mA h g⁻¹) and often operates at significantly low rates (typically, <1C) that in turn limits the achievable power densities.^{4,5} Therefore, the design and synthesis of new anode materials is necessary to offer the promise of high performance lithium-ion batteries with high efficiency, great energy density and long-lasting duration to meet various energy storage demands. For the purpose, nanostructure transition metal oxides have received great interest in lithium-ion batteries, and scientists have made great efforts to explore alternative anode materials with high capacity from them, such as SnO₂, FeO_x, CoO_x, MnO_x, CoFe₂O₄, and Co₃V₂O₈.^{6–13} Among these anode materials investigated for LIBs, Fe₂O₃ have been widely studied

as anode materials due to their high theoretical capacity value (1070 mA h g⁻¹), low cost, natural abundance, nontoxicity and the highest electrical conductivity (~2 × 10⁻⁴ S m⁻¹) than other metal oxides.^{14–16}

However, it remains great challenges in the application of Fe₂O₃ to commercial LIBs, especially the obstacles of poor cycling stability and inferior rate capability. The large volume expansion and severe collapse occurs in the host matrix of Fe₂O₃ during the cycling processes give rise to pulverization, which results in the breakdown of electrical connection of these anode materials from current collectors and rapid capacity fading upon cycling. To overcome these drawbacks, several strategies have been employed such as Fe₂O₃ nanotubes, nanorods/rGO, nanoropes/rGO, hollow nanobarrels, hollow nanoparticles/rGO, hollow spheres, and hollow-structured tubular nanostructures.^{17–28} Chaudhari *et al.*²⁶ reported a hollow-structured α-Fe₂O₃ nanofibers electrode with a reversible capacity of 1293 mA h g⁻¹ at a current density of 60 mA g⁻¹. Fe₂O₃ hollow nanoparticles/N-doped graphene aerogels were prepared by Liu *et al.*,²⁷ and the graphene/Fe₂O₃ aerogels exhibit high rate capability and excellent cyclic stability (729 mA h g⁻¹ at 0.1 A g⁻¹ for 300 cycles). Zhu *et al.*²⁸ reported the graphene oxide/Fe₂O₃ composite exhibiting 1027 mA h g⁻¹ at a current density of 100 mA h g⁻¹ after 50 cycles. These results suggested that incorporating nanoscale iron oxide into rGO has a great beneficial impact on the electrochemical performance of Li-ion batteries.

More recently, some core-shell nanostructure materials, which was originally used in semiconductors, have been

^aSchool of Resources Environmental and Chemical Engineering, Nanchang University, No.999, Xuefu Road, Nanchang, Jiangxi, China. E-mail: zzyang@ncu.edu.cn; Tel: +86-791-83969514

^bSchool of Chemistry, Nanchang University, No.999, Xuefu Road, Nanchang, Jiangxi, China

^cSchool of Civil Engineering, Harbin Institute of Technology, Heilongjiang 150090, P. R. China

† Electronic supplementary information (ESI) available. See DOI: 10.1039/c7ra08846a



imported to the field of Li-ion batteries. Some efforts were made to investigate Li-ion battery materials with core-shell nanostructure,^{29–33} such as Si, alloys, and transition metal oxides with carbon shells, and graphene was also introduced as a shell material. For example, Yang *et al.* have been fabricated graphene-wrapped metal oxides particles by electrostatic self-assembly. This unique core-shell structure has suppressed the aggregation of oxide nanoparticles, accommodated the volume change during the discharge-charge processes, and kept the high electrical conductivity of the electrode. The obtained graphene-wrapped Co_3O_4 hybrids delivered very high reversible capacity of about 1100 mA h g^{-1} in the initial 10 cycles and 1000 mA h g^{-1} after 130 cycles at 74 mA g^{-1} . However, further exploration and rational fabrication of iron oxide composite electrode materials with high-rate performance and long cycle life will have a significant impact on its practical utilization in Li-ion batteries.

Herein, we fabricated a novel core-shell structure Fe_2O_3 fiber/rGO anode materials by electrostatic self-assembly and the negatively charged graphene layers were wrapped on the positively charged Fe_2O_3 nanofiber. As shown in Fig. 1, the core-shell structure of Fe_2O_3 fiber/rGO composite is very similar with that of corn; Fe_2O_3 nanofiber can be regarded as the “corn cob”, and the wrapping multilayer reduced graphene oxide as the “sepal”. This unique composite with corn-like structure has several advantages for LIB anodes. First, the rGO layers are a stable framework, and the void space between the Fe_2O_3 fiber and the rGO layers allows for the Fe_2O_3 to expand upon lithiation. Second, the rGO layers prevent the electrolyte from reaching the Fe_2O_3 surface inside the rGO layers completely, and lithiation of the Fe_2O_3 occurs by Li diffusion through the rGO into the Fe_2O_3 fiber. Third, the rGO layers are both electronically and ionically conducting, which allows for good kinetics in Fe_2O_3 fiber/rGO anode. Due to the cohesiveness and good conductivity of rGO, Fe_2O_3 /rGO anode is applied for LIBs without binder and conductive agent as dopant. As a result, the synergistic effect between rGO and Fe_2O_3 fiber could reduce the initial capacity loss as well as improve the high rate capability ($1085.2 \text{ mA h g}^{-1}$ at 0.1 A g^{-1}) and cyclability ($407.8 \text{ mA h g}^{-1}$ at 5 A g^{-1} for 1500 cycles). This is the longest cycle life for the

Fe_2O_3 -based anode materials with excellent rate capability (*e.g.*, $>400 \text{ mA h g}^{-1}$ at 5 A h g^{-1}).

2. Experimental section

2.1 Preparation of Fe_2O_3 fibers

Fe_2O_3 fibers were synthesized by electrospinning technique assisted with anneal treatment. In a typical experiment, 2.4 g poly(vinyl pyrrolidone) (PVP, $M_w = 1\,300\,000$, Sigma) was dissolved in 15 ml *N,N*-dimethylformamide (DMF, AR, Sigma) and 15 ml ethanol solution, magnetic stirring for 3 h. Then, 2.4, 4.8, or 7.2 g ferric chloride (AR, Aladdin, China) was added to the solution and then vigorous stirring for 2 h, and FeCl_3 concentrations to the whole solution are 6, 12 and 18 wt%, respectively. The as-prepared samples were designated as PVP/ FeCl_3 (I), PVP/ FeCl_3 (II) and PVP/ FeCl_3 (III), respectively. Next, the precursor solution was loaded into a plastic syringe that was equipped with a stainless steel needle of 0.8 mm in diameter and electrospun at a DC voltage of 15 kV and a flow rate of 0.6 ml h^{-1} . The electrospun fibers were collected on aluminum foil and the distance between the needle and collector was 15 cm. The as-electrospun PVP/ FeCl_3 composite fibers were placed in a vacuum oven for 12 h at room temperature in order to remove the solvent residuals, and calcined for 3 h in air at $600 \text{ }^\circ\text{C}$ (the heating rate, $1 \text{ }^\circ\text{C min}^{-1}$) in a tube furnace, respectively. Finally the Fe_2O_3 fibers obtained were designated as Fe_2O_3 (I), Fe_2O_3 (II) and Fe_2O_3 (III), respectively.

2.2 Preparation of Fe_2O_3 /rGO composites

Graphene oxide was synthesized from natural graphite by a modified Hummers method described in detail previously.³⁴ To prepare Fe_2O_3 /rGO composites, a homogeneous suspension of graphene oxide (GO) and Fe_2O_3 fibers was carefully prepared. A total of 20 ml of alcoholic GO (1 mg ml^{-1}) was sonicated for 30 min to form a stable solution. Subsequently, 0.01 g Fe_2O_3 fibers was mixed with alcoholic GO and sonicated for another 30 min to form a homogeneous dispersion. Standing for 24 h, the Fe_2O_3 /GO composites were collected by centrifugation. The collecting solid was dried for 24 h by vacuum at $60 \text{ }^\circ\text{C}$. Finally, the Fe_2O_3 /GO composites were put in home-use


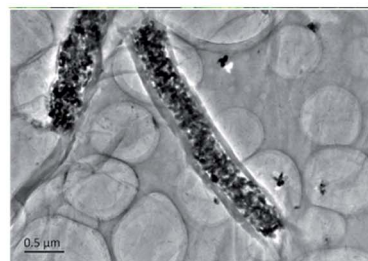


Fig. 1 Schematic of the materials design.

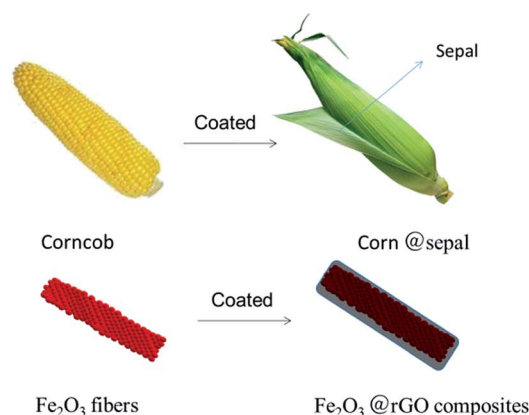

convection oven and irradiated by far infrared light for 5 min, in which the mixture color changed from bright red to dark red. Then Fe₂O₃ (I)/rGO, Fe₂O₃ (II)/rGO and Fe₂O₃ (III)/rGO Fe₂O₃/rGO composites were obtained.

2.3 Characterization

The morphology and diameter of samples were characterized using scanning electron microscope (SEM, FEI Quanta200F) and transmission electron microscope (TEM, FEI Tecnai G2 F20, 200 kV). The crystalline structural characterization of the all samples was carried out by X-ray diffraction (XRD) using a diffractometer (Bruker D8 Focus X-ray diffractometer), and the diffraction patterns were recorded at room temperature in the 2θ range between 5° and 80°. The chemical structure of fibers was conducted with a Fourier transform infrared (FT-IR) reflection spectroscopy (NICOLET 380, Wisconsin, USA). Weight loss behavior was tested by thermogravimetric (TG) analysis (TGA/DSC 3+, Mettler Toledo, Zurich, Switzerland) (air, 10 °C min⁻¹).

2.4 Electrochemical performance evaluation

The electrochemical performance of the Fe₂O₃ fibers and Fe₂O₃/rGO composites were analyzed by constructing a 2025-type coin cell. The active material and a certain amount of EtOH were mixed to prepare slurry, and the resulting slurry was attached onto copper foils. The anodes were dried in a vacuum furnace at 65 °C for 24 h. The mass loading of active materials per electrode is about 0.4 mg cm⁻², in which the mass of Fe₂O₃/rGO composites for the working electrodes was obtained by a Sartorius scale (0.01 mg) and the area of copper sheets were about 2 cm². The cells were assembled in a high purity argon atmosphere inside a glove box (Mbraun lab Master130, Germany). Lithium ribbon (0.3 mm thick) was used as the counter electrode and Celgard® 2325 was used as the separator and the

electrolyte was a solution of 1 M LiPF₆ dissolved in a mixture of ethylene carbonate (EC) : dimethyl carbonate (DMC) (1 : 1 vol%). Cyclic voltammetry (CV) measurements and electrochemical impedance spectroscopy (EIS) were performed using electrochemical workstation (PARSTAT 2273, Princeton, USA) at 0.1 mV s⁻¹ scan rate between 0.0 and 3.0 V. Charge and discharge were conducted using an a multi-channel battery test system (NEWARE, Shenzhen, China) at several different current densities between cutoff potentials of 0.02 and 3.00 V. The capacities were calculated on the basis of the weight of Fe₂O₃ fibers or Fe₂O₃/rGO composites.

3. Results and discussion

The fabrication process of the flexible Fe₂O₃ fiber/rGO composite is illustrated in Fig. 2 and S1 (ESI†). Typically, a homogeneous viscous solutions with FeCl₃ dissolved in poly(vinyl pyrrolidone) was electrospun into fibers, following with annealing process at 600 °C in air. Then, the Fe₂O₃ fibers were sonicated with alcoholic GO solution and formed a homogeneous dispersion; during the process, the negatively charged graphene oxide was uniformly wrapped on positively charged Fe₂O₃ nanofiber. In the next step, the Fe₂O₃/GO composites were collected by centrifugalization. Finally, the Fe₂O₃/GO composites was reduced to Fe₂O₃/rGO by the thermal decomposition of graphene oxide (GO) in air at a relatively low temperature of ~200 °C in under 5 minutes through far infrared (FIR) irradiation *via* a home-used convection oven.

To understand the influence of FeCl₃ concentration on the PVP/FeCl₃ fibers, three different weights PVP to FeCl₃ in DMF solution (FeCl₃ contents of 6, 12 and 18 wt%, respectively) were applied by electrospinning processes. The as-prepared fibers were designated as PVP/FeCl₃ (I), PVP/FeCl₃ (II) and PVP/FeCl₃ (III), respectively. Fig. 3 shows the SEM images of PVP/FeCl₃

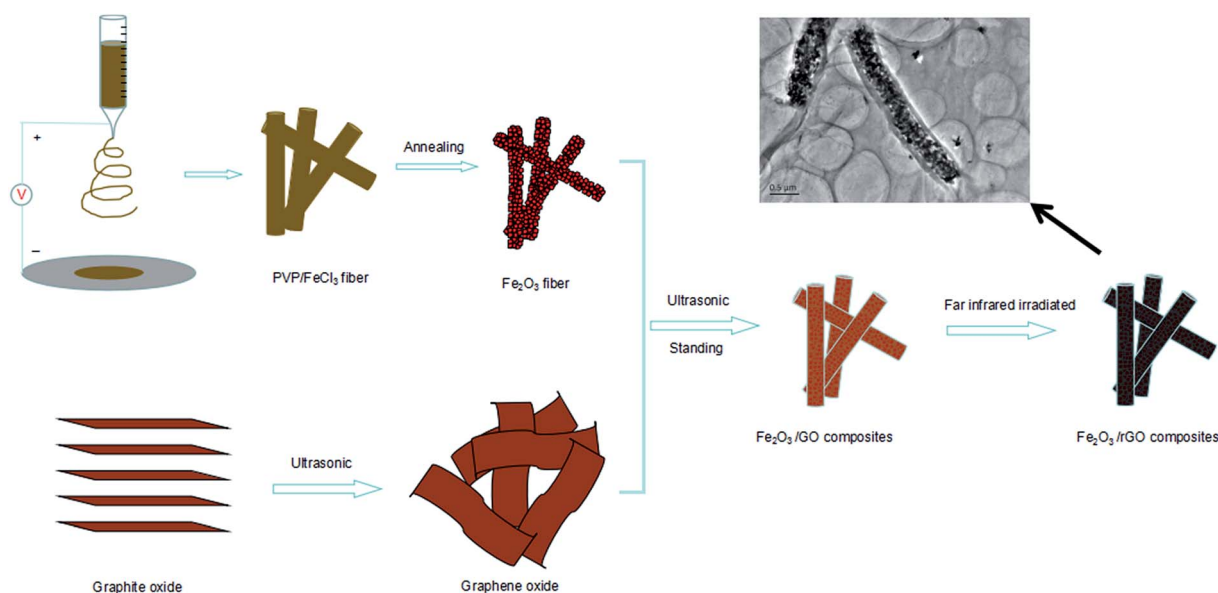


Fig. 2 Schematic diagram for the fabrication of Fe₂O₃/rGO composites.



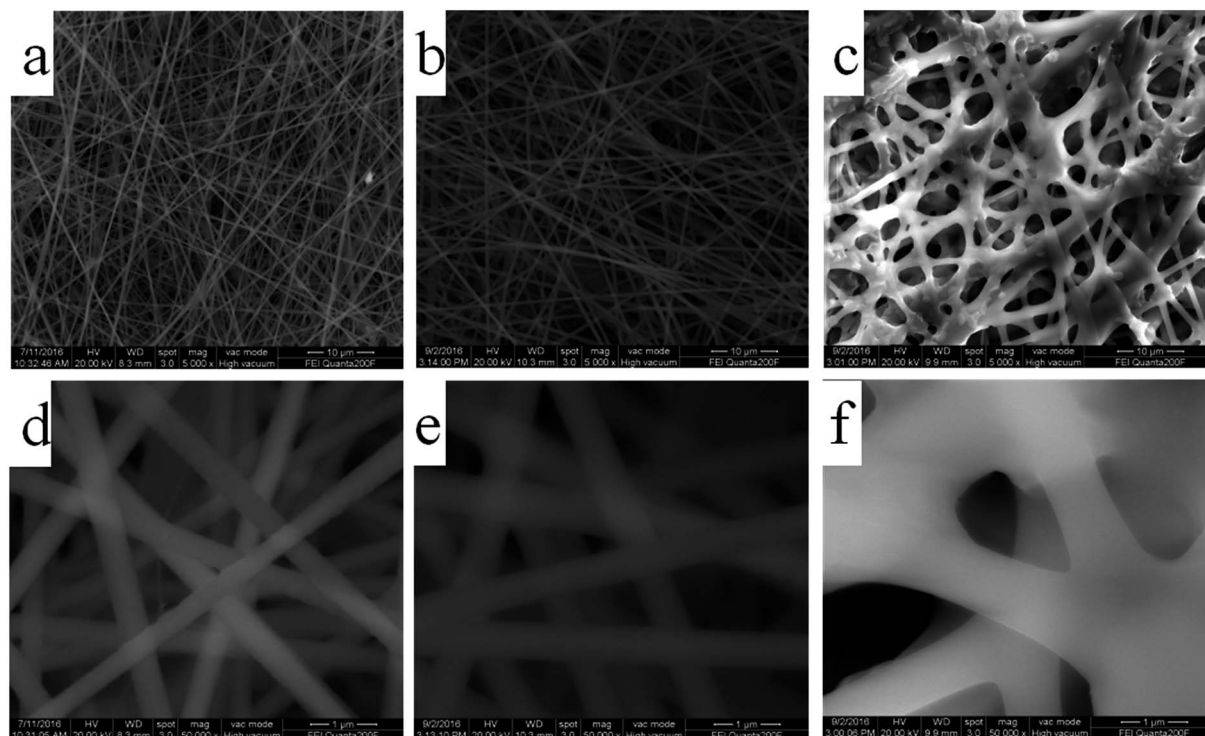


Fig. 3 SEM images of (a and d) PVP/FeCl₃ (I), (b and e) PVP/FeCl₃ (II) and (c and f) PVP/FeCl₃ (III).

fibers with different FeCl₃ contents. All electrospinning PVP/FeCl₃ fibers are straight and exhibit an interconnected pore structure and homogeneously distributed diameters. The fiber diameter increases from ~400 nm to ~1500 nm with the increasing of the contents of FeCl₃ increased from 6 to 18 wt%. However, PVP/FeCl₃ (III) shows junction between single fiber and the larger size. This phenomenon can be explained that the fibers have a lower viscosity at higher concentration of FeCl₃ which results in the junctions morphology.³⁵

To obtain the α -Fe₂O₃ fibers with good crystallinity, the FTIR spectra and X-ray diffraction spectra have been analyzed by calcining under different temperatures. Fig. 4a shows the FTIR spectra of the PVP/FeCl₃ fibers and calcined in air at 200–800 °C for 3 h. There are two peaks appearing at 463 and 551 cm⁻¹ which are assigned to the Fe–O vibration of the Fe₂O₃ fibers from 400 to 800 °C. Due to the decomposition of PVP, the peaks at about 1621 cm⁻¹ and 3369 cm⁻¹, corresponding to –N–C(=O)–, –O–H, respectively, disappear upon calcination at 600 °C, which indicates the formation of pure Fe₂O₃. Fig. 4b shows the X-ray diffraction patterns of the PVP/FeCl₃ fibers calcined in air at 200–800 °C for 3 h. The observed diffraction peaks at 2θ (°) = 24.14, 33.16, 35.62, 40.86, 49.46, 54.07, 57.61, 62.43, 63.99, 71.96 and 75.45 correspond to the planes of (012), (104), (110), (113), (024), (116), (018), (214), (300), (1010) and (220), respectively, which all match with the rhombohedral phase of α -Fe₂O₃ (JCPDS 33-0664).^{26,27} The sharp diffraction peaks clearly indicate the good crystallinity of the α -Fe₂O₃ phase. The diffraction peaks of the Fe₂O₃ fibers were observed above 400 °C in sintering processes, and enhanced upon calcinations at 600 °C, which was in accordance with the FTIR results.

Fig. 5 show the SEM and TEM images of Fe₂O₃ (I), Fe₂O₃ (II) and Fe₂O₃ (III) after heat treatment at 600 °C. As can be seen from the figures, the average diameter of these fibers greatly shrank because of the weight loss resulting from the removal of PVP after heat treatment. The average diameters of Fe₂O₃ (I), Fe₂O₃ (II) and Fe₂O₃ (III) fibers were found to be approximately 200, 400, 800 nm, respectively. It is obvious in Fig. 5 that corn-cob-like fibers were formed through the above approach and their surface became rough and porous due to some decomposition of the organic components.

Based on these Fe₂O₃ fibers obtained, the Fe₂O₃/rGO composites have been prepared after a far infrared (FIR) irradiation process. To prove the reduction effect of GO in the composite, the Raman spectrum of the Fe₂O₃/rGO samples before and after reduction was shown in Fig. S2.† It is found that two broad peaks locate at 1345 and 1589 cm⁻¹, which correspond to the A_{1g} vibration mode of the disordered carbon (D-bond) and the E_{2g} vibration mode of the ordered graphitic carbon (G-bond), respectively. The intensity ratio value of I_D/I_G for the samples increase from 0.92 to 0.97, which shows the graphene oxide has been reduced to rGO by far infrared irradiation reduction process. The higher I_D/I_G value indicates more defects and edges in the reduced graphene structure which may results in more porous structure. Interestingly, the D peaks of in the nanocomposites show the slightly red-shift, revealing the stronger interactions between Fe₂O₃ nanofiber and graphene after reduction process. This phenomenon usually derives from the dielectric confinement effect of transition metal oxide on graphene.^{36,37} Further, X-ray photoelectron spectroscopy (XPS) measurements also provide direct evidence of the reduction of



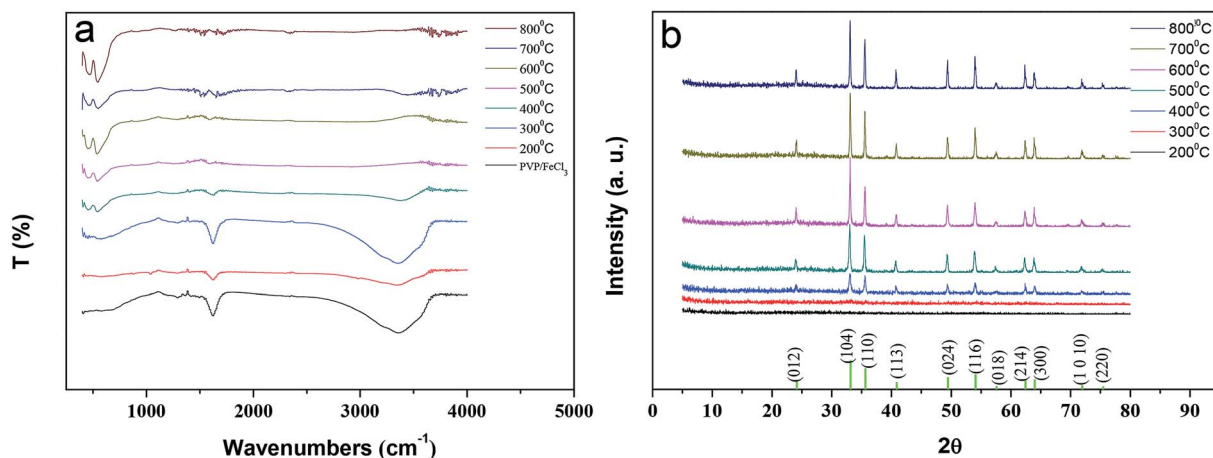


Fig. 4 (a) FTIR spectra of PVP/FeCl₃ (II) fibers and calcined in air at 200–800 °C; (b) X-ray diffraction patterns of the PVP/FeCl₃ (II) fibers calcined in air at 200–800 °C for 3 h.

GO under FIR irradiation and chemical state of Fe₂O₃ in composites, as shown in Fig. S3.† The survey scan spectrum displays the peaks of iron, oxygen and carbon, showing a high purity of as-prepared Fe₂O₃/rGO composites. The C 1s XPS spectra of Fe₂O₃/rGO composites indicates that, for Fe₂O₃/GO samples, four different peaks centered at 285.0, 286.8, and 288.1 eV were observed, corresponding to the presence of C–C/C=C in aromatic rings, C–O (epoxy and alkoxy), C=O groups, respectively. After FIR irradiation reduction treatment, the intensities of all the C 1s peaks of the carbons binding to

oxygen, decrease obviously. It suggests that the GO have been reduced to rGO in a certain degree. And for the XPS spectra of the Fe 2p for Fe₂O₃/GO composites, binding energies of Fe 2p_{3/2} and Fe 2p_{1/2} are 711.4 eV and 724.9 eV respectively for Fe₂O₃/GO composites before and after reduction, in good agreement with crystalline Fe₂O₃. The satellite peak locating at 719.9 eV between the Fe 2p_{3/2} and 2p_{1/2} peaks was assigned to its purely trivalent nature, implying that the oxidation state of Fe element in the composites were of Fe³⁺ only.³⁸ Furthermore, the weight content of reduced graphene oxide can be obtained by comparing with

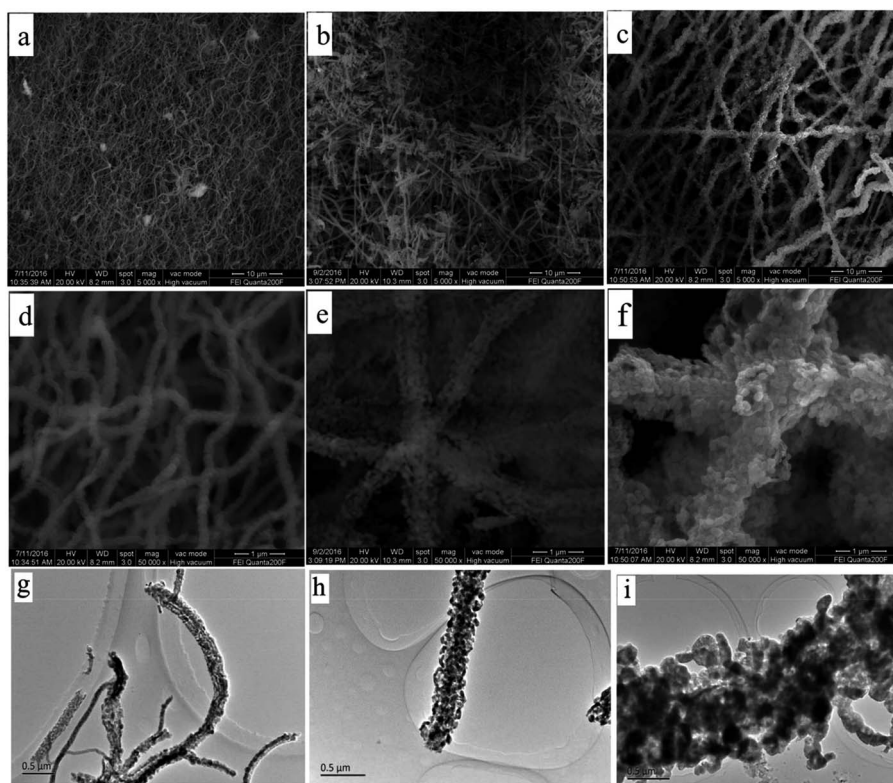


Fig. 5 SEM and TEM images of (a, d and g) Fe₂O₃ (I), (b, e and h) Fe₂O₃ (II) and (c, f and i) Fe₂O₃ (III).



the thermal weight loss behaviors between pure Fe_2O_3 fibers and $\text{Fe}_2\text{O}_3/\text{rGO}$ composites, as shown in Fig. S4.† For the sample of Fe_2O_3 fibers, it can be seen that the weight losses could be attributed to the evaporation of moisture and crystal water below 200 °C in the curves. With the temperature increasing, there is no weight loss for the sample of pure Fe_2O_3 fibers, which shows that Fe_2O_3 crystalline phase has good thermal stability. Instead, there are significant weight loss above 200 °C in the curve for the samples of Fe_2O_3 fibers/rGO composites: the weight loss between 200 to 300 °C corresponds to the further reduction process of reduced graphene oxide; the weight loss between 300 °C and 500 °C could be attributed to the complete combustion of graphene; and no further weight loss above 500 °C indicated the pure Fe_2O_3 . Therefore, the weight percentage of Fe_2O_3 in the composite samples can be estimated by about 50%.

To further investigate the morphological structure of the as-prepared $\text{Fe}_2\text{O}_3/\text{rGO}$ composites, the SEM and TEM images were shown in Fig. 6. A typical morphology of $\text{Fe}_2\text{O}_3/\text{rGO}$ hybrid fibers and porous structure have been clearly observed in Fig. 6a and b. The elemental mapping (Fig. 6c) showed that the $\text{Fe}_2\text{O}_3/\text{rGO}$ composites were uniformly distributed with carbon, oxygen, and iron. Fig. 6d demonstrates Fe_2O_3 fiber was uniformly coated by graphene oxide, which looks like a corn, even *via* a reduction of far infrared light irradiation (Fig. 6e). It is obvious that the surface of $\text{Fe}_2\text{O}_3/\text{rGO}$ composites has

a smooth film, which indicates Fe_2O_3 was coated in the rGO sheets. This phenomenon can be explained as follows: the oxygen-containing functional groups (hydroxyl, carbonyl and carboxyl groups) on the GO make it negatively-charged and they can act as anchor sites that interact strongly with the covered species;³⁹ when treating the mix solution of negatively charged GO and positively charged Fe_2O_3 fibers with ultrasound, the positively-charged Fe_2O_3 fiber may be absorbed on the negatively-charged surface of GO, which may promote the coating of Fe_2O_3 fibers by GO. A regular diffraction spot ring is observed from the selected-area electron diffraction (SAED) pattern (Fig. 6d and e, inset). The SAED pattern of rGO (Fig. 6d) shows the ring pattern obviously, and Fig. 6e shows the typical hexagonally ordered lattice of carbon in graphene, which indicated the $\text{Fe}_2\text{O}_3/\text{GO}$ was transformed into $\text{Fe}_2\text{O}_3/\text{rGO}$ completely. In addition, the reduction effect is also confirmed by XRD patterns (Fig. 6f). As shown in Fig. 6f, the sharp X-ray diffraction peak of GO (at $2\theta \approx 10^\circ$) appears in $\text{Fe}_2\text{O}_3/\text{GO}$ composites before far infrared irradiation, and after far infrared irradiation, the composites obtained appear the new diffraction peak of rGO (at $2\theta \approx 24^\circ$) and disappear the peak of GO (at $2\theta \approx 10^\circ$), indicating the $\text{Fe}_2\text{O}_3/\text{GO}$ was transformed into $\text{Fe}_2\text{O}_3/\text{rGO}$ completely. In the meantime, crystallized $\alpha\text{-Fe}_2\text{O}_3$ and graphene layers are also confirmed by XRD patterns (Fig. 6f) and HRTEM (Fig. S5†). As estimated by the HRTEM images, the lattices with a lattice fringe spacing of 0.22 nm are indexed to

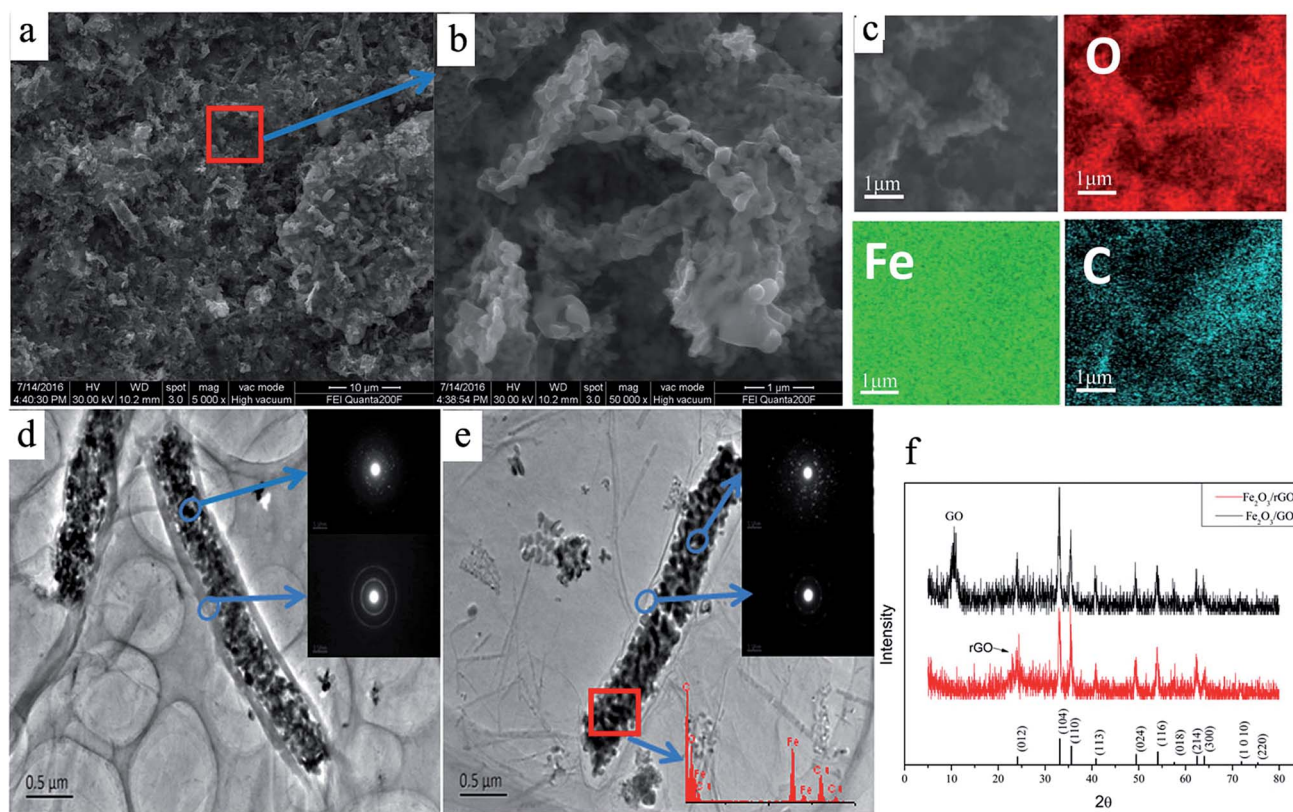


Fig. 6 (a and b) SEM images and (c) element mapping patterns of $\text{Fe}_2\text{O}_3/\text{rGO}$ composites; (d and e) TEM and SAED images of $\text{Fe}_2\text{O}_3/\text{GO}$ composites and $\text{Fe}_2\text{O}_3/\text{rGO}$ composites; (f) X-ray diffraction patterns of the $\text{Fe}_2\text{O}_3/\text{GO}$ composites and $\text{Fe}_2\text{O}_3/\text{rGO}$ composites after far infrared light irradiation.



the (113) plane of α - Fe_2O_3 , and the thickness of rGO layer is about 3 nm.

Subsequently, the porous characteristics of the Fe_2O_3 fiber/rGO composite were investigated by the nitrogen isothermal adsorption–desorption measurement. As displayed in Fig. S6,[†] the pore size distribution of the Fe_2O_3 fiber/rGO composite is almost consistent with pure Fe_2O_3 nanofiber, which give the evidence that the inside channels in Fe_2O_3 fiber remained unblocked after graphene sheets wrapping. The BET specific surface area of Fe_2O_3 fiber/rGO composites was estimated as $150.9 \text{ m}^2 \text{ g}^{-1}$ from the result of nitrogen adsorption data, and a more than 43% increase in specific surface area is found by comparing with pure Fe_2O_3 nanofiber. The major increase of the specific surface area can be attributed to the wrapped graphene nanosheets with relatively high specific surface area. It indicates that the graphene sheets working as a robust support can effectively suppress the self-aggregation of Fe_2O_3 nanofiber and thus further maintain the surface area of the Fe_2O_3 fiber/rGO material. At the same time, the synergistic effect of the unblocked channels and good surface area in the Fe_2O_3 fiber/rGO composite will facilitate fast diffusion of Li^+ when large area of active sites was provided for the lithiation and delithiation reactions.

Therefore, the as-prepared “corn” structure materials of Fe_2O_3 fiber/rGO composites with Fe_2O_3 fiber as the “corn cob” and multilayer reduced graphene oxide as the “sepal” will be expected to relieve the pulverization originated from the large volume change during the charge/discharge cycles, and further improve the electronic conductivity of Fe_2O_3 composites electrode, which contribute to high rate capability, and superior cyclability as Li-ion anode.

To investigate the possibility of the Fe_2O_3 /rGO composites used as advanced anode materials, the coin-type Li half-cells has been assembled and their electrochemical performance were studied. The initial cyclic voltammetry (CV) curves at a scan rate of 0.1 mV s^{-1} for the first five cycles were shown in Fig. 7a. In the first scan, irreversible reduction peaks were observed at 1.57, 0.90 and 0.60–0.75 V for the Fe_2O_3 /rGO, respectively. The irreversible peak of 1.57 V is attributed to the lithium intercalation into Fe_2O_3 fiber: $\text{Fe}_2\text{O}_3 + x\text{Li}^+ + xe^- \rightarrow \text{Li}_x\text{Fe}_2\text{O}_3$, disappearing at subsequent cycles. The cathodic peak of 0.90 V was ascribed to the phenomenon that hexagonal $\text{Li}_x\text{Fe}_2\text{O}_3$ is transformed to cubic $\text{Li}_2\text{Fe}_2\text{O}_3$: $\text{Li}_x\text{Fe}_2\text{O}_3 + (2-x)\text{Li}^+ + (2-x)e^- \rightarrow \text{Li}_2\text{Fe}_2\text{O}_3$. The strongest peak of (0.60–0.75 V) corresponds to the stepwise reduction of Fe^{3+} to Fe^{2+} and Fe^0 and the formation of the SEI layer:⁴⁰ $\text{Li}_2\text{Fe}_2\text{O}_3 + 4\text{Li}^+ + 4e^- \leftrightarrow 2\text{Fe}^0 + 3\text{Li}_2\text{O}$. The disappearance of the strongest peak in the subsequent cycle was due to the irreversible reactions induced by the formation of an SEI layer on the electrode in the first cycle. At the same time, the peaks at 1.57 V and 0.90 V disappeared indicating that lithium insertion and phase transformation from $\text{Li}_x\text{Fe}_2\text{O}_3$ to $\text{Li}_2\text{Fe}_2\text{O}_3$ are irreversible.⁴¹ On the other hand, the two anodic peaks at 1.64 and 1.86 V in the first scan corresponded to the oxidation process of Fe^0 to Fe^{2+} and Fe^{3+} .⁴² The broad peak appear in the subsequent cycles and their intensities remains almost the same, as observed from anodic curves, indicating enhanced stability during lithiation and delithiation processes.

Fig. 7b shows the charge–discharge curves of the Fe_2O_3 (I)/rGO composites anode at various cycles, which were tested at a current rate of 100 mA g^{-1} within a voltage range of 0.02–3.0 V. It is found that the Fe_2O_3 (I)/rGO composite electrode exhibits discharge and charge plateaus at ~ 0.9 – 0.8 V and ~ 1.5 – 1.9 V

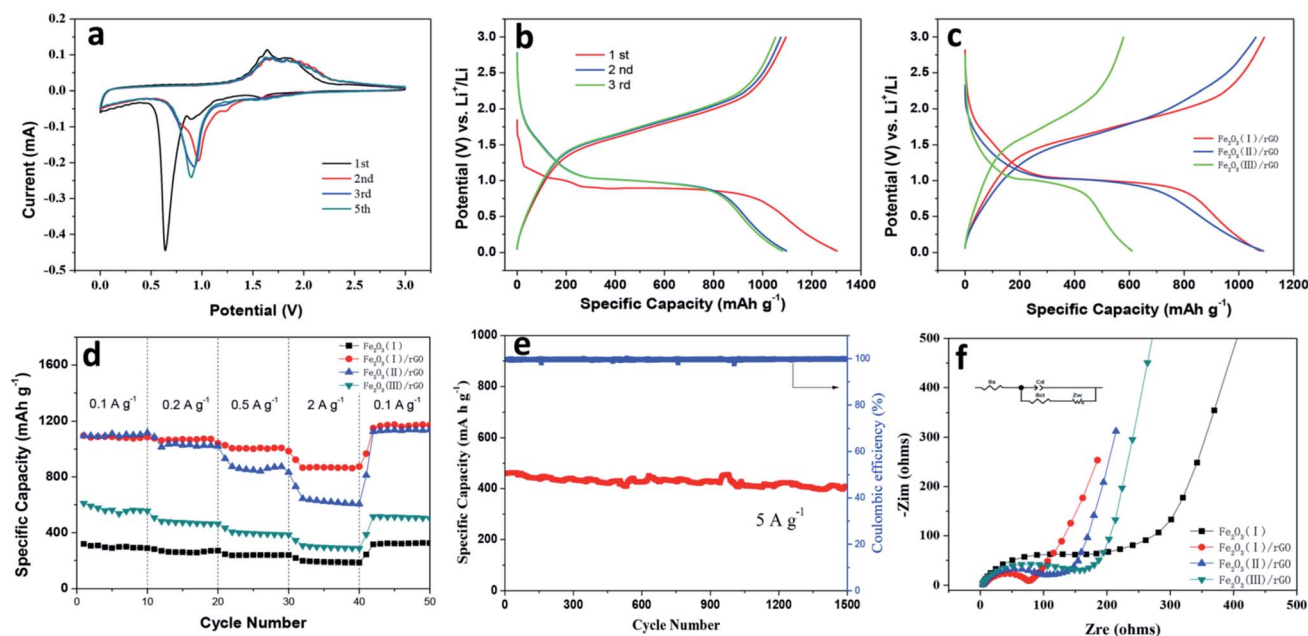


Fig. 7 (a) CV curves of Fe_2O_3 (I)/rGO composites at 0.1 mV s^{-1} ; (b) Initial discharge–charge curves of Fe_2O_3 (I)/rGO composites at 0.1 A g^{-1} ; (c) second-cycle discharge and charge curves of the Fe_2O_3 (I)/rGO, Fe_2O_3 (II)/rGO and Fe_2O_3 (III)/rGO composites at 0.1 A g^{-1} ; (d) Rate performance of Fe_2O_3 (I) fiber, Fe_2O_3 (I)/rGO, Fe_2O_3 (II)/rGO and Fe_2O_3 (III)/rGO composites; (e) long term cycling performance and coulombic efficiency of Fe_2O_3 (I)/rGO composites at 5 A g^{-1} ; (f) electrochemical impedance spectroscopy of the different electrodes.



that are typical for Fe_2O_3 based materials, which is in agreement with the charge–discharge process as shown in Fig. 7a. It is also observed that the initial charge and discharge capacities are around 1095.3 and 1303.7 mA h g^{-1} , and the initial coulombic efficiencies are 84%. In the second and third cycles, although the discharge capacities decrease gradually to about 1098.8 and 1081.6 mA h g^{-1} , the coulombic efficiencies are all above 97%. Furthermore, the typical second discharge–charge curves of the Fe_2O_3 (I)/rGO, Fe_2O_3 (II)/rGO and Fe_2O_3 (III)/rGO composites at a current rate of 100 mA g^{-1} within a voltage range of 0.02–3.0 V are shown in Fig. 7c. The discharge capacity of the Fe_2O_3 (I)/rGO, Fe_2O_3 (II)/rGO and Fe_2O_3 (III)/rGO composite was 1093.6, 1062.3 and 578.7 mA h g^{-1} , respectively. From the comparison, the Fe_2O_3 (I)/rGO with a smallest diameter show obvious improved specific capacity and higher Fe_2O_3 utilization.

To compare the nobility of Fe_2O_3 /rGO composites of electrochemical characteristics, the rate capabilities of Fe_2O_3 /rGO composites of Fe_2O_3 (I)/rGO, Fe_2O_3 (II)/rGO and Fe_2O_3 (III)/rGO and Fe_2O_3 fibers as anodes were examined at the various current densities of 0.1, 0.2, 0.5, 2 and 0.1 A g^{-1} (Fig. 7d). The Fe_2O_3 (III)/rGO electrode exhibited the lowest rate capability for three samples, significantly decreasing from 610.5 mA h g^{-1} at 0.1 A g^{-1} to 287.9 mA h g^{-1} at 2 A g^{-1} . By contrast, the Fe_2O_3 (I)/rGO electrode exhibited a more stable cyclic performance than others at high current rates and delivered capacities of 1085.2, 1065.1, 974.5, 866.1, and 1170.9 mA h g^{-1} at 0.1, 0.2, 0.5, 2 and 0.1 A g^{-1} , respectively.

Then, the cyclic stability of the Fe_2O_3 (I)/rGO was investigated as shown in Fig. 7e. It were cycled under an high current density of 5 A g^{-1} , and the Fe_2O_3 /rGO composites show high stability with a specific capacity of 407.8 mA h g^{-1} after 1500 cycles compared to the Fe_2O_3 at the same test conditions and

the excellent coulombic efficiency of higher than 99%. Most notably, the cyclability and rate performance of Fe_2O_3 /rGO are better than most of the lately reported Fe_2O_3 -based anode materials, such as porous Fe_2O_3 nanotubes,¹¹ nanoropes,¹³ hollow nanobarrels/rGO¹⁴ and hollow nanoparticles/rGO.¹⁵

In order to understand the fast ion transport in the composite electrodes, electrochemical impedance spectroscopy (EIS) measurements were conducted on the fresh cell with Fe_2O_3 (I) fiber, Fe_2O_3 (I)/rGO, Fe_2O_3 (II)/rGO and Fe_2O_3 (III)/rGO composite electrodes (Fig. 7f). The Nyquist plot shows a depressed semicircle, which generally describes two components: charge transfer resistance⁴³ and interfacial resistance.⁴⁴ The straight line in the low frequency region is the Warburg constant, which is assigned to the diffusion and transport of the Li^+ ion from the electrolyte to the surface of the electrode. The electrochemical system can be simply modeled by a Randles equivalent circuit, where R_s is the ohmic resistance, C_d is the double-layer capacitance, R_{ct} is the charge transfer resistance, and Z_w is the Warburg impedance describing the solid-state diffusion of Li^+ in Fe_2O_3 .⁴⁵ The resistance of the depressed semicircle of Fe_2O_3 (I)/rGO is lower than that of Fe_2O_3 (II)/rGO and Fe_2O_3 (III)/rGO, which is 78, 118 and 163 Ω , respectively. It suggests that the Fe_2O_3 (I)/rGO composite have a much lower electrolyte resistance and charge transfer resistance than other samples. These results confirm that such special structure for the Fe_2O_3 (I)/rGO composites with Fe_2O_3 fiber as the “corn-cob” and multilayer reduced graphene oxide as the “sepal” is beneficial to further reduce the electronic conductivity of composites. Also, the low impedance can be attributed to higher surface area, uniform Fe_2O_3 nanofiber distribution in graphene layer, and better electrolyte wettability associated with porous structure of the Fe_2O_3 /rGO composite material.

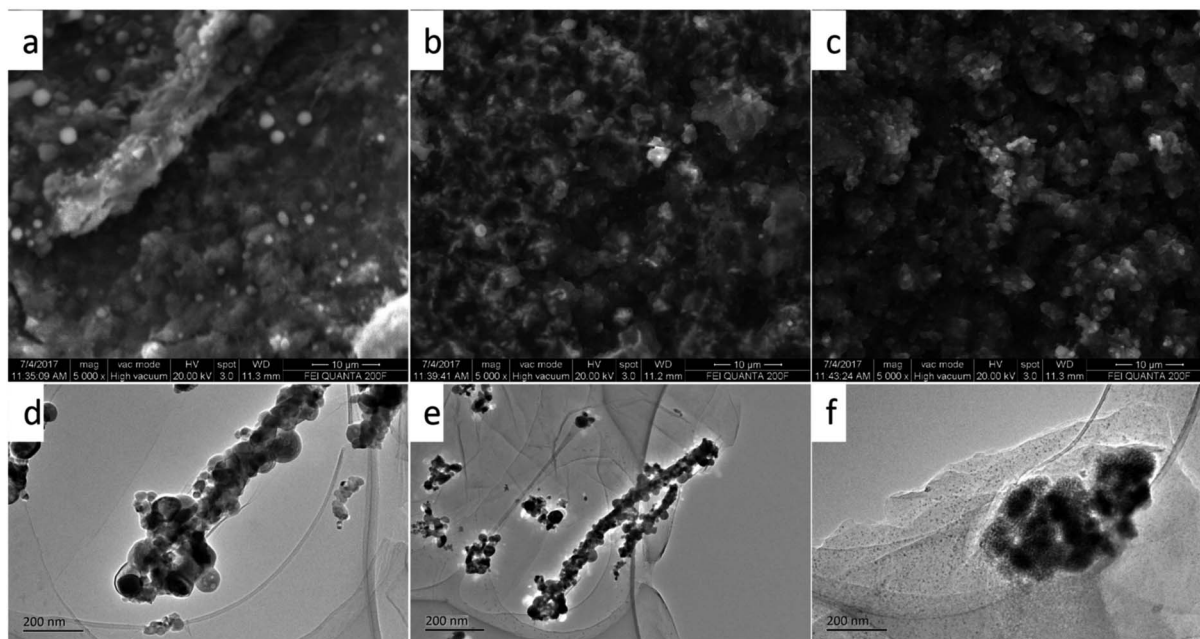


Fig. 8 The SEM (a–c) and TEM (d–f) images of Fe_2O_3 /rGO composites after different cycles: (a and d), 100 cycles; (b and e), 500 cycles; (c and f), 1000 cycles.



Finally, to further understand the excellent rate and long cycle performance of the Fe₂O₃/rGO composite electrodes based on above results, the structural and morphological evolution of the electrodes were measured by SEM and TEM, respectively in different cycle stages: 100th cycle, 500th cycle and 1000th cycle. As shown in Fig. 8(a and d) and (b and e), it is found that the film electrodes have maintained the fiber morphology before 500 cycles though some Fe₂O₃/rGO composite fiber have fractured and some fiber diameters get thin during the discharge-charge process from 100 to 500 cycles. At the 1000th cycle, the nanowires are intermixed with each other and begun to get together (Fig. 8c and f), but these Fe₂O₃ nanoparticles are still homogeneously distributed on the graphene sheets, which maintains the reversible the high specific capacity of the electrode material. In the meantime, the electrochemical impedance spectroscopy (EIS) measurements after initial, 500, and 1000 cycles have also confirmed the stability of Fe₂O₃/rGO composite electrode (Fig. S7†). The charge transfer resistance of the Fe₂O₃ (I)/rGO composite anode are 78, 101 and 195 Ω, respectively. It suggests that the Fe₂O₃ (I)/rGO composite have low charge transfer resistances, though the values become larger with the cycle number for initial to 1000 cycles gradually. The low charge transfer can be derived from the Fe₂O₃ nanofibers or nanoparticles encapsulated in the high conductive graphen network.^{46,47} In short, the aforementioned factors of as-prepared Fe₂O₃ fiber/rGO composites translate to greater accessibility to active sites for the lithium ions, shorter diffusion distances and quicker lithium ion diffusion, thereby explaining the significantly better rate capability and excellent cycling performance of the Fe₂O₃ fiber/rGO composite electrodes.

4. Conclusions

In summary, we have designed and fabricated a “corn” structure for a scalable and electrochemically stable Fe₂O₃/rGO electrode. The fabrication process is carried out by an electrospinning technique assisted with anneal treatment and far infrared reduction process. The “corn” structure consists of Fe₂O₃ fibers completely protected by multilayer rGO. Natural void space between the Fe₂O₃ fibers and rGO allows for the expansion of Fe₂O₃; and the good surface area and unblocked channels in the Fe₂O₃ fiber facilitates fast diffusion of Li⁺. Interestingly, this electrode shows excellent capacity (1085.2 mA h g⁻¹ at 0.1 A g⁻¹), long cycle life (407.8 mA h g⁻¹ at 5 A g⁻¹ for 1500 cycles), and high coulombic efficiency (99%). In addition to Fe₂O₃, this “corn” structure can also be applied to other high capacity anode materials for next generation Li-ion batteries to improve cycle life and coulombic efficiency.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

This work is financial supported by the National Natural Science Foundation of China (No. 21263016, 21363015, 51662029) and

the Jiangxi Province Research Program of Science and Technology (No. 2011BBE50022).

References

- Z. Fan, B. Wang and S. Ding, A NiCo₂O₄ nanosheet-mesoporous carbon composite electrode for enhanced reversible lithium storage, *Carbon*, 2016, **99**, 633–641.
- Y. Guan, L. Yu and X. W. Lou, Formation of Onion-Like NiCo₂S₄ particles *via* sequential ion-exchange for hybrid supercapacitors, *Adv. Mater.*, 2017, **29**, 1605051–1605056.
- M. Wang, Y. Huang, X. Chen and K. Wang, Synthesis of nitrogen and sulfur co-doped graphene supported hollow ZnFe₂O₄ nanosphere composites for application in lithium-ion batteries, *J. Alloys Compd.*, 2017, **691**, 407–415.
- L. Ji, α -Fe₂O₃ nanoparticle-loaded carbon nanofibers as stable and high-capacity anodes for rechargeable lithium-ion batteries, *ACS Appl. Mater. Interfaces*, 2012, **4**(5), 2672–2679.
- J. Chen, L. N. Xu, W. Y. Li and X. L. Gou, α -Fe₂O₃ nanotubes in gas sensor and lithium-ion battery applications, *Adv. Mater.*, 2005, **17**, 582–586.
- R. Liu, W. Su, P. He, C. Shen, C. Zhang, F. Su and C.-A. Wang, Synthesis of SnO₂/Sn hybrid hollow spheres as high performance anode materials for lithium ion battery, *J. Alloys Compd.*, 2016, **688**, 908–913.
- N. Zhang, Y. Huang, M. Zong and X. Ding, Synthesis of ZnS quantum dots and CoFe₂O₄ nanoparticles co-loaded with graphene nanosheets, *Chem. Eng. J.*, 2017, **308**, 214–221.
- J. S. Cho, Y. J. Hong and Y. C. Kang, Design and synthesis of bubble-nanorod-structured Fe₂O₃ carbon nanofibers as advanced anode material for Li-ion batteries, *ACS Nano*, 2015, **4**(9), 4025–4035.
- Z. Li, Y. Wang and M. Wu, Synthesis of nanocomposites with carbon-SnO₂ dual-shells on TiO₂ nanotubes and their application in lithium ion batteries, *J. Mater. Chem.*, 2015, **3**, 16057–16062.
- Y. Xiang, H. Wu, S. Ding and G. Gao, Quick one-pot synthesis of amorphous carbon coated cobalt-ferrite twin elliptical frustums for enhanced lithium storage capability, *J. Mater. Chem.*, 2017, **5**, 8062–8069.
- B. Dong, M. Li and C. Xiao, Tunable growth of perpendicular cobalt ferrite nanosheets on reduced graphene oxide for energy storage, *Nanotechnology*, 2017, **28**, 55401–55407.
- X. Sun, G.-P. Hao, X. Lu, L. Xi, B. Liu, W. Si, C. Ma, Q. Liu, Q. Zhang, S. Kaskel and O. G. Schmidt, High-defect hydrophilic carbon cuboids anchored with Co/CoO nanoparticles as highly efficient and ultra-stable lithium-ion battery anodes, *J. Mater. Chem. A*, 2016, **4**(26), 10166–10173.
- X. Gu, J. Yue, L. Li, H. Xue, J. Yang and X. Zhao, General synthesis of MnO_x (MnO₂, Mn₂O₃, Mn₃O₄, MnO) hierarchical microspheres as lithium-ion battery anodes, *Electrochim. Acta*, 2015, **184**, 250–256.
- C. T. Cherian, J. Sundaramurthy, M. Kalaivani, P. Ragupathy, P. S. Kumar, V. Thavasi, M. Reddy, C. H. Sow, S. G. Mhaisalkar and S. Ramakrishna, Electrospun α -Fe₂O₃



- nanorods as a stable, high capacity anode material for Li-ion batteries, *J. Mater. Chem.*, 2012, **22**, 12198–12204.
- 15 M. V. Reddy, G. V. S. Rao and B. V. R. Chowdari, Metal oxides and oxysalts as anode materials for Li ion batteries, *Chem. Rev.*, 2013, **113**, 5364–5457.
 - 16 Q. Su, D. Xie, J. Zhang, G. Du and B. Xu, *In situ* transmission electron microscopy observation of the conversion mechanism of Fe₂O₃/graphene anode during lithiation delithiation processes, *ACS Nano*, 2013, **7**, 9115–9121.
 - 17 H. Wang, *et al.*, Fabrication, formation mechanism and the application in lithium-ion battery of porous Fe₂O₃ nanotubes *via* single-spinneret electrospinning, *Electrochim. Acta*, 2015, **158**, 105–112.
 - 18 J. Jiao, *et al.*, Synthesis of well-defined Fe₃O₄ nanorods/N-doped graphene for lithium-ion batteries, *Nano Res.*, 2016, **9**(5), 1256–1266.
 - 19 S. Yan and Q. Wu, A novel structure for enhancing the sensitivity of gas sensors- α -Fe₂O₃ nanoropes containing a large amount of grain boundaries and their excellent ethanol sensing performance, *J. Mater. Chem. A*, 2015, **3**, 5982.
 - 20 K. S. Lee, *et al.*, Hollow nanobarrels of α -Fe₂O₃ on reduced graphene oxide as high-performance anode for lithium-ion batteries, *ACS Appl. Mater. Interfaces*, 2016, **8**(3), 2027–2034.
 - 21 Y. Wang, P. Mao and W. Wu, Flower-like Fe₂O₃/reduced graphene oxide composite for electrochemical energy storage, *Synth. Met.*, 2016, **222**, 198–204.
 - 22 J. Liang, C. Xiao and S. Ding, Porous Fe₂O₃ spheres coated with N-doped carbon from polydopamine as Li ion battery anode materials, *Nanotechnology*, 2016, **27**, 215403–215411.
 - 23 G. D. Park, *et al.*, Na-ion storage performances of FeSex and Fe₂O₃ hollow nanoparticles-decorated reduced graphene oxide Balls prepared by nanoscale Kirkendall diffusion Process, *Sci. Rep.*, 2016, **6**, 22432.
 - 24 T. Muraliganth, A. Vadivel Murugan and A. Manthiram, Facile synthesis of carbon-decorated single-crystalline Fe₃O₄ nanowires and their application as high performance anode in lithium ion batteries, *Chem. Commun.*, 2009, 7360–7362.
 - 25 L. Wang, *et al.*, Electrospun hollow cage-like α -Fe₂O₃ microspheres: synthesis, formation mechanism, and morphology-preserved conversion to Fe nanostructures, *CrystEngComm*, 2014, **16**, 10618.
 - 26 S. Chaudhari and M. Srinivasan, 1D hollow α -Fe₂O₃ electrospun nanofibers as high performance anode material for lithium ion batteries, *J. Mater. Chem.*, 2012, **22**, 23049–23056.
 - 27 L. Liu, *et al.*, Seaweed-derived route to Fe₂O₃ hollow nanoparticles/N-doped graphene aerogels with high lithium ion storage performance, *ACS Appl. Mater. Interfaces*, 2016, **8**(11), 7047–7053.
 - 28 X. Zhu, *et al.*, Nanostructured reduced graphene oxide/Fe₂O₃ composite as a high-performance anode material for lithium ion batteries, *ACS Nano*, 2011, **5**(4), 3333–3338.
 - 29 X. Wang, L. Fan and B. Lu, Core-shell Ge@graphene@TiO₂ nanofibers as a high-capacity and cycle-stable anode for lithium and sodium ion battery, *Adv. Funct. Mater.*, 2016, **26**, 1104–1111.
 - 30 L. Su, L. Jing and Z. Zhou, Li ion battery materials with core-shell nanostructures, *Nanoscale*, 2011, **3**, 3969–3983.
 - 31 Z. Zhang, F. Xiao and S. Wang, Functionalized carbonaceous fibers for high performance flexible all-solid-state asymmetric supercapacitors, *J. Mater. Chem. A*, 2015, **3**, 11817–11823.
 - 32 Y. Zhu, W. Liu and J. Chen, Directing silicon-graphene self-assembly as a core/shell anode for high-performance lithium-ion batteries, *Langmuir*, 2013, **29**, 744–749.
 - 33 S. Yang, X. Feng and S. Ivanovici, Fabrication of graphene-encapsulated oxide nanoparticles: towards high-performance anode materials for lithium storage, *Angew. Chem., Int. Ed.*, 2016, **49**, 8408–8411.
 - 34 F. Xiang, *et al.*, Scalable and rapid Far Infrared reduction of graphene oxide for high performance lithium ion batteries, *Energy Storage Mater.*, 2015, **1**, 9–16.
 - 35 Y. Zhu, *et al.*, Preparation of superhydrophilic α -Fe₂O₃ nanofibers with tunable magnetic properties, *Thin Solid Films*, 2006, **510**(1/2), 271–274.
 - 36 Y. Xiao, X. Li, J. Zai and X. Qian, CoFe₂O₄ graphene nanocomposites synthesized through an ultrasonic method with enhanced performance as anode materials for Li-ion batteries, *Nano-Micro Lett.*, 2014, **6**, 307–315.
 - 37 Y. Xiao, J. Zai, B. Tian and X. Qian, Formation of NiFe₂O₄/expanded graphite nanocomposites with superior lithium storage properties, *Nano-Micro Lett.*, 2017, **9**, 34.
 - 38 C. Wu, H. Zhang and Y. X. Wu, Synthesis and characterization of Fe@Fe₂O₃ core-shell nanoparticles/graphene anode material for lithium-ion batteries, *Electrochim. Acta*, 2014, **134**, 18–27.
 - 39 T. Hu, *et al.*, Trimethylamine sensing properties of graphene quantum dots/ α -Fe₂O₃ composites, *J. Solid State Chem.*, 2016, **237**, 284–291.
 - 40 Y. Zou, J. Kan and Y. Wang, Fe₂O₃-graphene rice-on-sheet nanocomposite for high and fast lithium ion storage, *J. Phys. Chem. C*, 2011, **115**, 20747–20753.
 - 41 J. Morales, L. Sanchez, F. Martin, *et al.*, Synthesis and characterization of nanometric iron and iron-titanium oxides by mechanical milling: electrochemical properties as anodic materials in lithium cells, *J. Electrochem. Soc.*, 2005, **152**, A1748.
 - 42 G. Zhou, D.-W. Wang, P.-X. Hou, W. Li, N. Li, C. Liu, F. Li and H.-M. Cheng, A nanosized Fe₂O₃ decorated single-walled carbon nanotube membrane as a high-performance flexible anode for lithium ion batteries, *J. Mater. Chem.*, 2012, **22**, 17942–17946.
 - 43 K. Xu, S. Zhang and R. Jow, Electrochemical Impedance Study of Graphite/Electrolyte Interface Formed in LiBOB/PC Electrolyte, *J. Power Sources*, 2005, **143**, 197–202.
 - 44 Y. Zhang, C.-Y. Wang and X. Tang, Cycling Degradation of an Automotive LiFePO₄ Lithium-Ion Battery, *J. Power Sources*, 2011, **196**, 1513–1520.
 - 45 A. J. Bard and L. R. Faulkner, *Electrochemical Methods: Fundamentals and Applications*, Wiley, New York, 2nd edn, 2001.
 - 46 X. Li, J. Zai, S. Xiang and X. Qian, Regeneration of metal sulfides in the delithiation process: the key to cyclic stability, *Adv. Energy Mater.*, 2016, **6**, 1601056.
 - 47 X. Liu, J. Zai, Z. Ma and X. Qian, Na₂Ge₄O₉ nanoparticles encapsulated in 3D carbon networks with long-term stability and superior rate capability in lithium ion batteries, *J. Mater. Chem. A*, 2016, **4**, 10552–10557.

