

Cite this: *RSC Adv.*, 2017, 7, 48208

Ultra-deep oxidative desulfurization of fuel with H_2O_2 catalyzed by molybdenum oxide supported on alumina modified by Ca^{2+} †

Wei Jin,^{ID} Yongsheng Tian,^{ID} Guanghui Wang,* Danlin Zeng,^{ID} Qian Xu and Jiawei Cui

A highly active catalyst of molybdenum oxide supported on mesoporous alumina modified by Ca^{2+} was synthesized by an *in situ* method and applied in the catalytic oxidative desulfurization (CODS) system. This catalyst was characterized by FT-IR, XRD, BET and XPS. The influences of $m(\text{catalyst})/m(\text{model oil})$, $V(\text{H}_2\text{O}_2)/V(\text{model oil})$, reaction temperature and reaction time on oxidative desulfurization of 4,6-dimethyldibenzothiophene (4,6-DMDBT), dibenzothiophene (DBT) and benzothiophene (BT) were investigated. This catalyst has high desulfurization activity in the removal of organic sulfides under mild conditions. The catalytic oxidation reactivity of sulfur-containing compounds is in the order of $\text{DBT} > 4,6\text{-DMDBT} > \text{BT}$. The kinetic studies reveal that the oxidative desulfurization of the organic sulfides can present a pseudo first-order kinetic process, and the apparent activation energies of 4,6-DMDBT, DBT and BT are $34.67 \text{ kJ mol}^{-1}$, $33.01 \text{ kJ mol}^{-1}$ and $40.16 \text{ kJ mol}^{-1}$, respectively. The recycling experiments indicate that 4,6-DMDBT, DBT and BT removal can still reach 90.0%, 89.9% and 87.3% after eight cycles.

Received 11th August 2017
Accepted 9th October 2017

DOI: 10.1039/c7ra08900g

rsc.li/rsc-advances

1. Introduction

Nowadays, manufacturing of ultra-low sulfur fuels has caused worldwide research general concern.^{1,2} Sulfur oxides and sulfate particulates are produced in the combustion process of the sulfur organic compounds in fuel oil, which comes amid fears, creating environmental pollution such as acid rain.³ Explosion engines are also etched because of these sulfur organic compounds in fuel oil.⁴ Furthermore, these hazardous substances produced from the sulfur organic compounds in fuel oil also play an important role in contaminating the catalysts for tail gas treatment in catalytic converters.⁵ Thus, the oil refinery industry is facing more stringent environmental regulations and laws all over the world. In order to meet the requirements of environmental protection, various of desulfurization methods were developed.

Conventionally, hydrodesulfurization (HDS) is the most important technology for removal of the sulfur compounds from fuel oil in the oil refinery industry. However, HDS process usually needs harsh reaction conditions including high temperatures, high pressures and huge amounts of hydrogen. HDS is high efficiency in removing of thiols, sulfides, disulfides, and some thiophenic compounds, but it is hard to remove the

refractory sulfur compounds such as 4,6-dimethyldibenzothiophene (4,6-DMDBT), dibenzothiophene (DBT) and benzothiophene (BT).^{6–9} In order to solve these problems in hydrodesulfurization process, some other supplementary desulfurization methods were researched extensively, such as oxidative desulfurization (ODS),¹⁰ adsorption desulfurization,¹¹ alkylation desulfurization,¹² biodesulfurization¹³ and so on. ODS is considered to be a promising method for ultra-deep desulfurization under mild conditions because it is efficient and economical.¹⁴ In ODS, non-polar organic sulfides are oxidized by oxidizing agent to their homologous sulfones under catalysts and then remove it by rectification, extraction, adsorption or other separation operation.¹⁵

In recent years, various oxidizing agents such as oxygen,¹⁶ ozone,¹⁷ hydrogen peroxide,¹⁸ cumene hydroperoxide (CHP),¹⁹ tertiary butyl hydroperoxide (*t*-BuOOH)²⁰ have been used for the oxidative desulfurization. However, hydrogen peroxide is more popular than the other oxidants due to the environmental friendliness, safety, high oxidation capacity and high selectivity. A number of homogenous and heterogeneous catalysts are developed in diverse ODS systems in order to increase the oxidation activity of the oxidizing agent, for example, sodium bicarbonate,²¹ organic acids,²² polyoxometalates,²³ molecular sieve,²⁴ molybdenum oxide²⁵ and so on. Among these, molybdenum oxide have been extensively researched and employed because of its good performance in the CODS system. Such as, Jia and coworkers²⁶ reported an efficient oxidative desulfurization with MoO_3 as the active phase and H_2O_2 as oxidant under mild and solvent free conditions. García-Gutiérrez and

Hubei Key Laboratory of Coal Conversion and New Carbon Material, School of Chemistry and Chemical Engineering, Wuhan University of Science and Technology, Wuhan 430081, Hubei, China. E-mail: wangguanghui@wust.edu.cn

† Electronic supplementary information (ESI) available: Additional experimental details. See DOI: 10.1039/c7ra08900g



coworkers¹ reported that $\text{Mo}/\gamma\text{Al}_2\text{O}_3$ as the catalyst and H_2O_2 as oxidant in the CODS. The sulfur level of diesel fuel can be reduced from about 320 to less than 10 ppmw at 60 °C under atmospheric pressure. Meanwhile, the catalyst support also shows great effects on catalytic oxidative desulfurization. Silica,²⁷ titanium dioxide,²⁸ active carbon²⁹ and alumina (Al_2O_3)³⁰ as the catalyst supports have been widely investigated. From the perspective of application, Al_2O_3 has received much attention in both academia and industry community because of its good mechanical properties, adjustable pore structure and high resistance to attrition. Such as, Wang *et al.*³¹ used *t*-BuOOH as oxidant in DBT ODS in a flow-type fixed-bed reactor. They found that Al_2O_3 as catalyst supports showed higher catalytic activity than those supported on TiO_2 and SiO_2 . Al_2O_3 is also easy to synthesize and a cheap material compared to other supports. The study found that the introduction of different kinds of promoters can adjust surface acidity and pore structure in a wide range and increase the activity and selectivity of the catalysts. Lanthanides and transition metal elements are the common promoters of catalysts in the oxidation desulfurization system. There are many reports about them. For instance, Zhang and coworkers³² synthesized the catalyst $\text{MoO}_3/\text{SiO}_2$ with the modification of La^{3+} and applied it in the catalytic oxidative desulfurization system. Yan and coworkers³³ reported that mesoporous HPW/ SiO_2 modified with Ag species was used as the catalyst for the oxidative desulfurization of both model and real diesel oils. However, there are few studies about alkali-earth metal elements as the promoters of catalysts in the oxidation desulfurization system.

In this work, molybdenum oxide was loaded on the mesoporous alumina by *in situ* synthesis method using the alkali-earth metal Ca^{2+} as the promoter. The catalytic reaction conditions $m(\text{catalyst})/m(\text{model oil})$, $V(\text{H}_2\text{O}_2)/V(\text{model oil})$, reaction temperature and reaction time, kinetic studies of the catalytic oxidation and reuse of the catalyst were investigated in the oxidative desulfurization of the model fuel oil. The results indicated that the mesoporous alumina loaded MoO_3 materials of Ca^{2+} modified exhibited a high catalytic activity in the oxidation desulfurization system of 4,6-DMDBT, DBT and BT model fuel oil.

2. Experimental

2.1. Materials

All chemicals including ammonium molybdate, aluminium chloride, polyethylene oxide–polypropylene oxide–polyethylene oxide (F127), methanol, ethanol, ammonia, calcium nitrate, 4,6-dimethyldibenzothiophene (4,6-DMDBT), dibenzothiophene (DBT), benzothiophene (BT), *n*-octane, hydrogen peroxide (H_2O_2 , 30% wt), were purchased from Sinopharm Chemical Reagent Co., Ltd.

2.2. Catalyst preparation

For the preparation of the catalysts, 3.17 g AlCl_3 , 0.67 g ammonium molybdate and 0.056 g calcium nitrate were firstly dissolved respectively in 5.0 ml deionized water to spare. Then 0.38 g F127 was added into a 62.0 ml mixed solution of deionized water, ethanol and ammonia ($V(\text{deionized}$

water) : $V(\text{ethanol})$: $V(\text{ammonia}) = 20 : 10 : 1$) in a 100 ml three-neck flask. After that, AlCl_3 , ammonium molybdate, and calcium nitrate were dropwise added in turn every 10 minutes and stirred at 1000 rpm. Next the mixture was continuously stirred for 1 h before aging for 4 h at room temperature, subsequently separated by filtration, thoroughly washed with deionized water and dried in a vacuum oven at 105 °C. Finally, the dried samples were calcined at 540 °C for 12 h and labeled as $\text{Ca}/\text{MoO}_3/\text{Al}_2\text{O}_3$ ($n(\text{Mo})/n(\text{Al}) = 16.7\%$, $n(\text{Ca})/n(\text{Mo}) = 6.1\%$). The control group catalyst was prepared without calcium nitrate according to the above method and labeled as $\text{MoO}_3/\text{Al}_2\text{O}_3$.

2.3. Characterization of the samples

FT-IR spectra ($4000\text{--}500\text{ cm}^{-1}$) were recorded at room temperature on a Bruker VERTEX 70 FT-IR spectrometer using KBr in the ratio of 1 : 200. The X-ray diffraction (XRD) patterns were recorded on a Phillips Xpert Pro powder diffraction system using $\text{Cu K}\alpha$ radiation with a Ni filter over the range $10^\circ \leq 2\theta \leq 90^\circ$. The pore structure of the catalysts were obtained from N_2 adsorption isotherms which were obtained at -195.8°C in the relative pressure range of 0.001–1 with a Quantachrome instrument for Quadrasorb SI. The X-ray photoelectron spectrum (XPS) measurements were performed with a Multilab 2000 X-ray photoelectron spectrometer (VG, UK) (see ESI†).

2.4. Catalytic oxidative desulfurization

The model fuel was prepared by dissolving a certain amount of 4,6-DMDBT, DBT and BT in *n*-octane to get the solution with a sulfur content of $400\text{ }\mu\text{g g}^{-1}$ respectively. The catalytic oxidation reaction was performed in a three necked glass flask with a condenser, stirrer and thermometer. In these experiments, 10.0 ml of the model fuel oil and a certain amount of catalyst were put into the reactor, which were placed in a water bath at a constant temperature. When the reaction mixture was heated to the set temperature, a certain amount of hydrogen peroxide was added into the mixture, and the reaction was kept at the set temperature under stirring at 1000 rpm for a certain time. Then the mixture was rapidly cooled down to room temperature and separated by centrifugation. The reaction products were analyzed by GC-FID equipped with a HP-5 capillary column.

3. Results and discussion

3.1. Oxidative desulfurization of the model fuel oil

In order to verify the CODS activity, the catalytic oxidative desulfurization of the 4,6-DMDBT, DBT and BT model fuel oil was performed with the catalyst $\text{Ca}/\text{MoO}_3/\text{Al}_2\text{O}_3$. The effect of mass ratio of catalyst/model oil on 4,6-DMDBT, DBT and BT removal rate of the 10 ml model oil was shown in Fig. 1. Clearly, with the increase of catalyst amount, the oxidative removals of 4,6-DMDBT, DBT and BT increased gradually and then reached a plateau. When $m(\text{catalyst})/m(\text{model oil})$ reached 0.56% for 4,6-DMDBT or DBT (and 0.70% for BT), the removal rate of the sulfur compound was close to 100.0%. The conversion of 4,6-DMDBT or DBT was higher than that of BT with the same amount of catalyst.



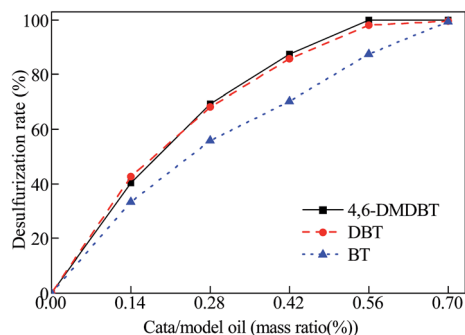


Fig. 1 Effect of catalyst/model oil on 4,6-DMDBT, DBT and BT removal. Reaction conditions for 4,6-DMDBT removal: $V(H_2O_2)/V(model\ oil) = 0.20\%$, $55\ ^\circ C$, 10 min; reaction conditions for DBT removal: $V(H_2O_2)/V(model\ oil) = 0.20\%$, $55\ ^\circ C$, 8 min; reaction conditions for BT removal: $V(H_2O_2)/V(model\ oil) = 0.20\%$, $55\ ^\circ C$, 16 min.

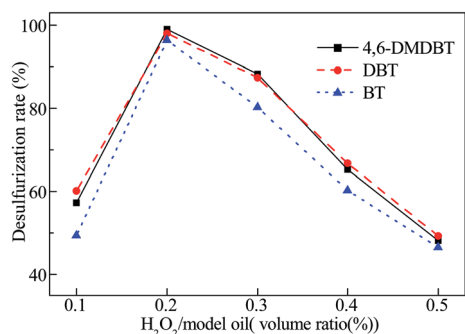


Fig. 2 Effect of H_2O_2 /model oil on 4,6-DMDBT, DBT and BT removal. Reaction conditions for 4,6-DMDBT removal: $m(catalyst)/m(model\ oil) = 0.56\%$, $55\ ^\circ C$, 10 min; reaction conditions for DBT removal: $m(catalyst)/m(model\ oil) = 0.56\%$, $55\ ^\circ C$, 8 min; reaction conditions for BT removal: $m(catalyst)/m(model\ oil) = 0.70\%$, $55\ ^\circ C$, 16 min.

The effect of volume ratio of H_2O_2 /model oil on 4,6-DMDBT, DBT and BT removal rate of the 10 ml model oil is shown in Fig. 2. When $V(H_2O_2)/V(model\ oil)$ reached 0.2% ($n(O/S) = 2.3$), the removal rate of 4,6-DMDBT, DBT and BT was close to 100.0%. However, when $V(H_2O_2)/V(model\ oil)$ got up to more than 0.2%, the removal rate of 4,6-DMDBT, DBT and BT decreased significantly. It is probably because excess H_2O_2 caused a side reaction catalyzed by Mo and produced excess H_2O . On the one hand, the side reaction occupied the active center and increased the consumption of H_2O_2 .³⁴ On the other hand, a percentage of the hydrophilic catalyst was transferred to the water phase, thus reducing the catalyst dispersed in the oil phase.³⁴ This resulted the reduction of the desulfurization rate.

The effect of reaction temperature and reaction time on 4,6-DMDBT, DBT and BT removal rate of the 10 ml model oil is shown in Fig. 3. The experimental results show that both enhancing reaction temperature and prolonging reaction time are advantageous to the removal rate of model fuel oil. The higher reaction temperature improved the performance of catalyst greatly, because the higher temperature aggravated the molecules thermal motion, meanwhile the formation quantity

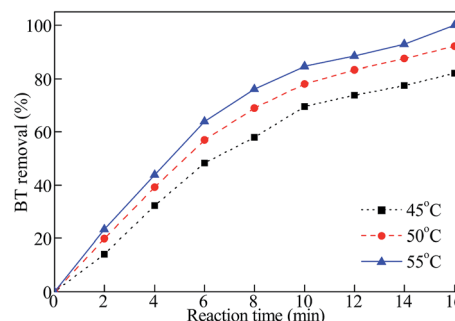
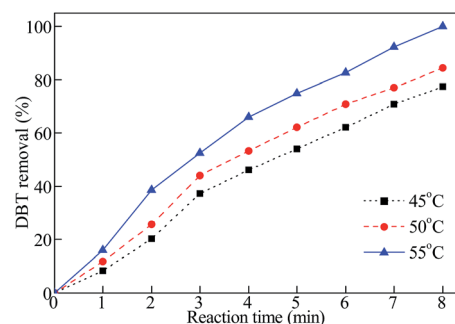
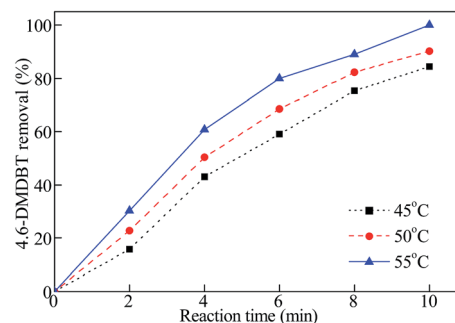


Fig. 3 Effect of reaction time on 4,6-DMDBT, DBT and BT removal. Reaction conditions for 4,6-DMDBT removal: $m(catalyst)/m(model\ oil) = 0.56\%$, $V(H_2O_2)/V(model\ oil) = 0.20\%$; reaction conditions for DBT removal: $m(catalyst)/m(model\ oil) = 0.56\%$, $V(H_2O_2)/V(model\ oil) = 0.20\%$; reaction conditions for BT removal: $m(catalyst)/m(model\ oil) = 0.70\%$, $V(H_2O_2)/V(model\ oil) = 0.20\%$.

of the metallic peroxide species which were produced by the hydrogen peroxide and molybdenum oxide in the catalyst in a unit time increased with increasing of reaction temperature.³⁵ At $55\ ^\circ C$, the oxidative removal rate of 4,6-DMDBT, DBT and BT were close to 100.0% only in 10 min, 8 min and 16 min, respectively. Meanwhile, under the same reaction conditions, the oxidative removal rate of 4,6-DMDBT, DBT and BT catalyzed with MoO_3/Al_2O_3 were 64.4%, 68.3%, 53.9%, respectively. This showed that the desulfurization rate of 4,6-DMDBT, DBT and BT catalyzed with $Ca/MoO_3/Al_2O_3$ was higher than with MoO_3/Al_2O_3 under the same conditions. The results indicated that oxidation reactivities of these sulfur compounds decreased in the order of $DBT > 4,6-DMDBT > BT$ under the same reaction conditions. This was because of the lower electron density of the sulfur atom on BT (5.739). As calculated by Otsuki *et al.*³⁶ The electron densities on sulfur atoms are 5.760 for 4,6-DMDBT and



Table 1 Reaction rate constant (k) and correlation coefficient (R^2) for oxidation reaction of 4,6-DMDBT, DBT and BT at different temperatures

Sample	t ($^{\circ}\text{C}$)	k (min^{-1})	R^2
DBT	45	0.201	0.981
DBT	50	0.247	0.985
DBT	55	0.294	0.992
BT	45	0.119	0.989
BT	50	0.154	0.993
BT	55	0.190	0.989
4,6-DMDBT	45	0.189	0.977
4,6-DMDBT	50	0.235	0.981
4,6-DMDBT	55	0.283	0.987

5.758 for DBT. Therefore, it was clearly demonstrated that 4,6-DMDBT and DBT can be oxidized more easily than that of BT. The electron density of the sulfur atom on 4,6-DMDBT is higher than that of DBT, however, 4,6-DMDBT has two methyl groups, as well as the higher steric hindrance. As a result, the reactivity of DBT was higher than that of 4,6-DMDBT. When catalyzed by $\text{Ca}/\text{MoO}_3/\text{Al}_2\text{O}_3$, the oxidative removal rate of DBT was close to 100.0% under 55 $^{\circ}\text{C}$ after 8 min. Chang and coworkers³⁷ reported that oxidation of dibenzothiophene with CHP on $\text{MoO}_3/\text{SiO}_2$ modified with alkaline earth metals. The DBT conversions on $\text{MoO}_3/\text{Ca}-\text{SiO}_2$ catalysts was the highest (95%) at 60 $^{\circ}\text{C}$, 4 h and O/S molar ratio 3.0. It shows that the catalyst $\text{Ca}/\text{MoO}_3/\text{Al}_2\text{O}_3$ prepared in this research has higher activity than other catalysts in ODS.

3.2. Apparent activation energy and reaction rate constant

The reaction rates determined at different temperatures were summarized in Table 1. The apparent activation energies for the CODS reactions (Fig. 4) were calculated by the Arrhenius equation. The results indicated that the CODS reactions fitted pseudo first order reaction kinetics. As can be seen from Fig. 4, the activation energies of 4,6-DMDBT, DBT and BT oxidation reactions were 34.67 kJ mol^{-1} , 33.01 kJ mol^{-1} and 40.16 kJ mol^{-1} , respectively. The activation energies of DBT and 4,6-DMDBT are lower than that of BT, which proves the easier oxidation of DBT and 4,6-DMDBT. M. A. Safa and coworkers⁴

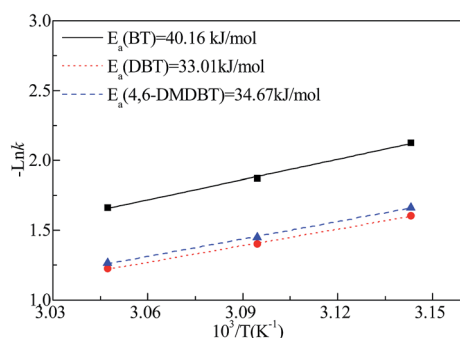


Fig. 4 Arrhenius activation energies for 4,6-DMDBT, DBT and BT oxidation.

reported that the apparent activation energy of DBT in the $\text{MoO}_3/\text{Al}_2\text{O}_3$ -CHP catalytic system was 67.5 kJ mol^{-1} . The experiment and comparison results indicate that the mesoporous $\text{Ca}/\text{MoO}_3/\text{Al}_2\text{O}_3$ - H_2O_2 catalytic system in the present work displays the higher catalytic activity.

3.3. Analysis of oxidation product

For analysis the oxidation product, GC-MS was used to research the 4,6-DMDBT, DBT and BT oxidation reaction process catalyzed by $\text{Ca}/\text{MoO}_3/\text{Al}_2\text{O}_3$. After the oxidation reaction, the oil phase and the solid catalyst were separated by centrifugation. After that the catalyst was extracted by methanol. In the end, the methanol phase were analyzed by GC-MS. Fig. 5 shows that MS spectra of oxidized product of 4,6-DMDBT, DBT and BT. The peak observed in the MS spectra at $m/z = 244.2$, 216.0 and 166.1 were belonged to the molecular ion peak of 4,6-dimethyldibenzothiophene sulfone (4,6-DMDBTO₂), dibenzothiophene sulfone (DBTO₂) and benzothiophene sulfone (BTO₂). By comparison with standard NIST data, 4,6-DMDBT, DBT and BT

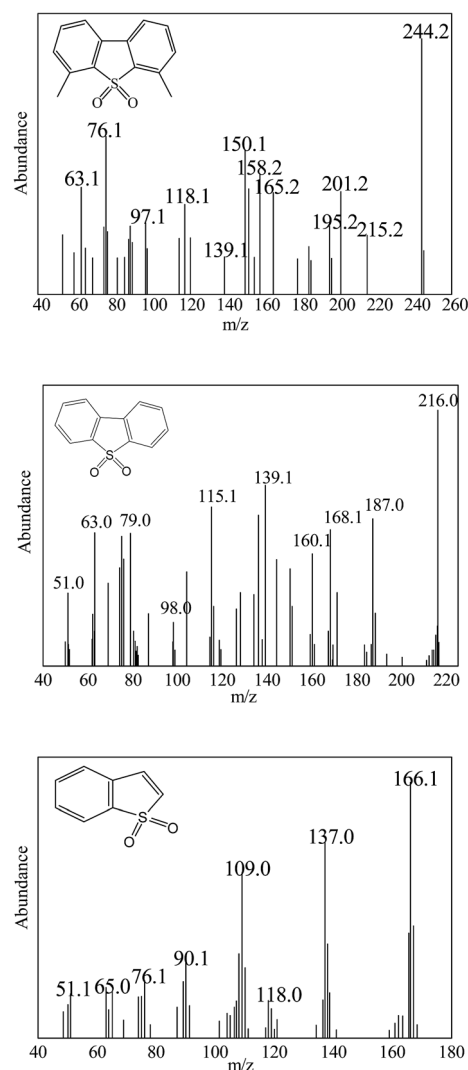


Fig. 5 MS spectra of oxidized product of 4,6-DMDBT, DBT and BT.



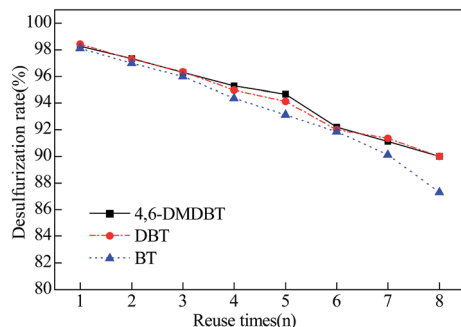


Fig. 6 Effect of reuse times on the oxidative desulfurization rate of 4,6-DMDBT, DBT and BT.

were oxidized to corresponding sulfone 4,6-DMDBTO₂, DBTO₂ and BTO₂ can be authenticated. Meanwhile, no sulfur and sulfone compounds were detected in oil phase by GC-MS. The experimental result indicated that the oxidation product of 4,6-DMDBT, DBT and BT were 4,6-DMDBTO₂, DBTO₂ and BTO₂, which were adsorbed by the solid catalyst because of its highly polar nature.

3.4. Reuse cycles of the catalysts

After each CODS run, the catalyst Ca/MoO₃/Al₂O₃ could be separated by centrifugation. The filter was washed with methanol and then dried at 105 °C in a vacuum drying oven for 12 h. Then the catalyst was charged again with the same volumes of fresh H₂O₂ solution and model oil for the next cycle. The stability of catalytic system after regeneration was shown in Fig. 6, indicating that Ca/MoO₃/Al₂O₃ has a good recycling performance in the CODS process. After eight recycling, the conversion rates of 4,6-DMDBT, DBT and BT decreased to 90.0%, 89.9% and 87.3%. At the same time, the Mo content in the catalysts before and after the oxidation reaction decreased from 29.4% to 28.3% by ICP-AES. Such a result indicated that weak leaching of MoO₃ occurs throughout the CODS process, which resulted in a slight decrease in the desulfurization activity after reused eight times of the catalyst.

4. Conclusion

An amorphous Ca/MoO₃/Al₂O₃ has been prepared and utilized with H₂O₂ in the CODS system. The advantages of the mesoporous material are low produce cost and simple operation process. The Ca/MoO₃/Al₂O₃ catalyst exhibited higher desulfurization activity for the oxidation of 4,6-DMDBT, DBT and BT under mild conditions. And the catalytic oxidation activity of the sulfur-containing compounds occurred in the following order: DBT > 4,6-DMDBT > BT. The kinetic studies indicated that the oxidative desulfurization of 4,6-DMDBT, DBT and BT was pseudo-first-order reaction. The activation energies of 4,6-DMDBT, DBT and BT were 34.67 kJ mol⁻¹, 33.01 kJ mol⁻¹ and 40.16 kJ mol⁻¹, respectively. GC-MS analysis demonstrated that 4,6-DMDBTO₂, DBTO₂ and BTO₂ were the only products of 4,6-DMDBT, DBT and BT oxidation, which were adsorbed by the

catalyst. The recycling experiments of Ca/MoO₃/Al₂O₃ indicated that 4,6-DMDBT, DBT and BT removal still reached 90.0%, 89.9% and 87.3% after 8 cycles.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

This work was financially supported by the National Natural Science Foundation (No. 21473126).

References

- 1 J. L. García-Gutiérrez, G. A. Fuentes, M. E. Hernández-Terán, *et al.*, *Appl. Catal.*, A, 2008, **334**(1–2), 366–373.
- 2 C. Zou, P. Zhao, J. Ge, *et al.*, *Fuel*, 2013, **104**, 635–640.
- 3 J. M. Campos-Martin, M. C. Capel-Sanchez, P. Perez-Presas, *et al.*, *J. Chem. Technol. Biotechnol.*, 2010, **85**(7), 879–890.
- 4 M. A. Safa and X. Ma, *Fuel*, 2016, **171**, 238–246.
- 5 A. Stanislaus, A. Marafi and M. S. Rana, *Catal. Today*, 2010, **153**(1–2), 1–68.
- 6 R. M. Casagrande, W. K. Meerbott, A. F. Sartor, *et al.*, *Ind. Eng. Chem.*, 1955, **47**(4), 744–749.
- 7 W. Lai, Z. Chen, J. Zhu, *et al.*, *Nanoscale*, 2016, **8**(6), 3823.
- 8 L. Wang, Y. Wang, Y. Liu, *et al.*, *Microporous Mesoporous Mater.*, 2008, **113**(1–3), 435–444.
- 9 L. Yang, X. Li, A. Wang, *et al.*, *J. Catal.*, 2015, **330**, 330–343.
- 10 S. Otsuki, T. Nonaka, N. Takashima, *et al.*, *Energy Fuels*, 2015, **14**(6), 750–753.
- 11 K. S. Triantafyllidis and E. A. Deliyanni, *Chem. Eng. J.*, 2014, **236**(2), 406–414.
- 12 W. Rong, J. Wan, Y. Li, *et al.*, *Fuel*, 2015, **143**, 504–511.
- 13 M. Agarwal, P. K. Dikshit, J. B. Bhasarkar, *et al.*, *Chem. Eng. J.*, 2016, **295**, 254–267.
- 14 A. W. Bhutto, R. Abro, S. Gao, *et al.*, *J. Taiwan Inst. Chem. Eng.*, 2016, **62**, 84–97.
- 15 I. V. Babich and J. A. Moulijn, *Fuel*, 2003, **82**(6), 607–631.
- 16 S. Murata, K. Murata, A. Koh Kidena, *et al.*, *Energy Fuels*, 2004, **18**(1), 116–121.
- 17 J. Wang, D. Zhao and K. Li, *Energy Fuels*, 2010, **24**(4), 2527–2529.
- 18 G. Yu, S. Lu, H. Chen, *et al.*, *Energy Fuels*, 2005, **19**(2), 447–452.
- 19 X. Han, A. Wang, X. Wang, *et al.*, *Catal. Commun.*, 2013, **42**(23), 6–9.
- 20 N. A. W. M. Wan, A. W. A. B. Wan, R. Ali, *et al.*, *Clean Technol. Environ. Policy*, 2015, **17**(6), 1487–1497.
- 21 A. D. Bokare and W. Choi, *J. Hazard. Mater.*, 2016, **304**, 313–319.
- 22 D. Bunthid, P. Prasassarakich and N. Hinchiranan, *Fuel*, 2010, **89**(9), 2617–2622.
- 23 W. Trakarnpruk and K. Rujiraworawut, *Fuel Process. Technol.*, 2009, **90**(3), 411–414.
- 24 Q. Du, Y. Guo, H. Duan, *et al.*, *Fuel*, 2017, **188**, 232–238.



- 25 J. L. García-Gutiérrez, G. A. Fuentes, M. E. Hernández-Terán, *et al.*, *Appl. Catal., A*, 2006, **305**(1), 15–20.
- 26 Y. Jia, G. Li and G. Ning, *Fuel Process. Technol.*, 2011, **92**(1), 106–111.
- 27 P. Yang, S. Zhou, Y. Du, *et al.*, *RSC Adv.*, 2016, **6**(59), 53860–53866.
- 28 X. Wang, F. Li, J. Liu, *et al.*, *Energy Fuels*, 2012, **26**(11), 6777–6782.
- 29 K. G. Haw, A. W. A. B. Wan, R. Ali, *et al.*, *Fuel Process. Technol.*, 2010, **91**(9), 1105–1112.
- 30 Y. Tian, Y. Yao, Y. Zhi, *et al.*, *Energy Fuels*, 2015, **29**(2), 150126070926009.
- 31 D. Wang, E. W. Qian, H. Amano, *et al.*, *Appl. Catal., A*, 2003, **253**(1), 91–99.
- 32 Y. Zhang, J. Qiu, G. Wang, *et al.*, *Mater. Rev.*, 2013, **27**, 75–79.
- 33 X. M. Yan, S. U. Gao-Shen and L. Xiong, *J. Fuel Chem. Technol.*, 2009, **37**(3), 318–323.
- 34 Y. Tian, G. Wang, J. Long, *et al.*, *Chin. J. Catal.*, 2016, **37**(12), 2098–2105.
- 35 J. Qiu, G. Wang, Y. Zhang, *et al.*, *Fuel*, 2015, **147**, 195–202.
- 36 S. Otsuki, T. Nonaka, N. Takashima, *et al.*, *Energy Fuels*, 2000, **14**(6), 750–753.
- 37 J. Chang, A. Wang, J. Liu, *et al.*, *Catal. Today*, 2010, **149**(1), 122–126.

