

Cite this: *RSC Adv.*, 2017, 7, 48894

Construction of stable core–shell imprinted Ag-(poly-*o*-phenylenediamine)/CoFe₂O₄ photocatalyst endowed with the specific recognition capability for selective photodegradation of ciprofloxacin†

Ziyang Lu,^{ab} Zehui Yu,^a Jinbo Dong,^c Minshan Song,^d Yang Liu,^e Xinlin Liu,^f Di Fan,^c Zhongfei Ma,^a Yongsheng Yan^{ib}*^b and Pengwei Huo^{*b}

A stable core–shell imprinted Ag-(poly-*o*-phenylenediamine)/CoFe₂O₄ (imprinted Ag-POPDP/CoFe₂O₄) was synthesized *via* the surface imprinting technique. Ag-POPDP was introduced into an imprinted layer, which significantly enhanced the photocatalytic activity. Meanwhile, due to the existence of imprinted cavities in the imprinted layer, the imprinted Ag-POPDP/CoFe₂O₄ exhibited the superior specific recognition capability for selective photodegradation of ciprofloxacin (CIP). This work puts forward a novel design idea for synthesizing imprinted photocatalysts.

Received 4th September 2017
Accepted 6th October 2017

DOI: 10.1039/c7ra09835a

rsc.li/rsc-advances

Introduction

In recent years, the development of industrialization has also been accompanied by increasingly serious environmental problems, especially water pollution.^{1–5} Currently, due to the large usage of ciprofloxacin (CIP, one of the most common antibiotics), the harm caused by CIP residues to the ecological environment and human health is causing widespread concern.^{6–9} Therefore, finding a simple, quick and effective method to remove CIP residues from the water environment is of great importance.^{10–13} In this context, photocatalysis, as a green technology which uses light energy and degrades pollutants to non-toxic harmless substances, has aroused great interest among many researchers.^{14–18}

Recently, TiO₂, CdS, ZnO and other materials have been extensively studied and widely used as photocatalysts.^{19–23} They each have their respective advantages; however, their common shortcomings are also evident, such as poor selectivity, namely,

these common photocatalysts cannot selectively remove specific pollutants in the presence of other pollutants.^{24–27} This inherent defect greatly limits their functional application. In order to overcome the above defect, the surface imprinting technique is widely used to improve the selectivity. Surface imprinting is an effective approach for synthesizing materials with the specific recognition capability towards the target molecule.^{28–34}

Nevertheless, when these common photocatalysts are coated with an imprinted layer, although the selectivity will increase, the photocatalytic activity will greatly decrease due to the coating of the imprinted layer. Therefore, to improve selectivity without reducing photocatalytic activity is a major challenge. Based on the above considerations, we have found that poly-*o*-phenylenediamine (POPDP, a typical conductive polymer)^{35–37} can not only be used in the same way as the functional monomer for synthesizing the imprinted layer, but also possesses good photocatalytic activity. More importantly, the introduction of POPDP into the imprinted layer can effectively avoid the decrease of photocatalytic activity resulting from the coating of an imprinted layer on common photocatalysts. Moreover, in order to further enhance the photocatalytic activity, silver (Ag)^{38–42} can be loaded onto the POPDP, in order to aid the transfer of photo-generated electrons from POPDP. In brief, the introduction of Ag-POPDP into the imprinted layer not only improves the selectivity, but also improves the photocatalytic activity.

On the other hand, the poor recycling capacity of the above imprinted material severely restricts its development and application.^{43–45} CoFe₂O₄, as a widely used magnetic material, can be easily collected using a magnet without additional centrifugation or filtration and maintains a very good

^aSchool of the Environment and Safety Engineering, Jiangsu University, Jiangsu, Zhenjiang 212013, PR China

^bSchool of Chemistry & Chemical Engineering, Jiangsu University, Jiangsu, Zhenjiang 212013, PR China. E-mail: luziyang126@126.com; huopw@mail.ujs.edu.cn

^cZhenjiang Water Corporation, Jiangsu, Zhenjiang 212003, PR China

^dSchool of Mathematics and Physics, Jiangsu University of Science and Technology, Jiangsu, Zhenjiang 212003, PR China

^eKey Laboratory of Functional Materials Physics and Chemistry of the Ministry of Education, Jilin Normal University, Jilin, Changchun 130103, PR China

^fSchool of Energy and Power Engineering, Jiangsu University, Jiangsu, Zhenjiang 212013, PR China

† Electronic supplementary information (ESI) available. See DOI: 10.1039/c7ra09835a



recyclability.^{46–51} CoFe_2O_4 can be used not only as a carrier to improve the specific surface area of composite materials, but also can reduce the costs to improve the economic viability of composite materials.

Therefore, in this work, a stable core-shell imprinted Ag-(poly-*o*-phenylenediamine)/ CoFe_2O_4 photocatalyst (imprinted Ag-POPDP/ CoFe_2O_4) was synthesized, based on CoFe_2O_4 as the carrier, *via* the surface imprinting technique. A series of characterizations were performed and influential factors were investigated to confirm the composition, structure, morphology and performance. The material properties in terms of adsorption, photocatalysis, selectivity, mechanism and reproducibility were also experimentally investigated.

Experimental section

Materials

Ferric chloride hydrate ($\text{FeCl}_3 \cdot 6\text{H}_2\text{O}$, A.R.), cobalt chloride hexahydrate ($\text{CoCl}_2 \cdot 6\text{H}_2\text{O}$, A.R.), ammonium acetate (A.R.), *o*-phenylenediamine (OPD, A.R.), trimethylpropane trimethacrylate (TRIM, A.R.) *tert*-butyl alcohol (*t*-BuOH, A.R.), triethanolamine (TEOA, A.R.) and benzoquinone (BQ, A.R.) were supplied by Aladdin Chemistry Co., Ltd. 2,2'-Azobis(2,4-dimethylvaleronitrile) (97%) was supplied by J&K Scientific Ltd. Ciprofloxacin (CIP, 99%) and tetracycline (TC, 99%) were purchased from National Institutes for Food and Drug Control. Trichloromethane (A.R.), sodium borohydride (NaBH_4 , A.R.), ethylene glycol (A.R.), ammonium persulfate (A.R.), methanol (A.R.), anhydrous ethanol (A.R.), silver nitrate (AgNO_3 , A.R.) and dimethyl sulfoxide (DMSO, A.R.) were all purchased from Sinopharm Chemical Reagent Co., Ltd. Nitrogen (N_2) was supplied by INHONG GAS. Deionized water was used throughout this work.

Synthesis

Synthesis of CoFe_2O_4 . CoFe_2O_4 was synthesized as follows: 4 mmol of $\text{FeCl}_3 \cdot 6\text{H}_2\text{O}$ and 2 mmol of $\text{CoCl}_2 \cdot 6\text{H}_2\text{O}$ were dissolved in 70 mL of ethylene glycol. After a clear solution was formed, 30 mL of ammonium acetate was added into the above mixed solution with mechanical agitation for 30 min at 30 °C. Afterwards, the mixed solution was transferred into a Teflon-lined stainless steel autoclave and sealed to heat at 210 °C. After reacting for 48 h, the autoclave was cooled to room temperature. Subsequently, the solid product was washed with deionized water and anhydrous ethanol several times. Finally, after drying under vacuum at 50 °C, CoFe_2O_4 was obtained.

Synthesis of Ag-POPDP. Briefly, 0.02 mol of OPD was dissolved in 30 mL of trichloromethane, which was marked as Sol. A. Meanwhile, 0.01 mol of ammonium persulfate was dissolved in 30 mL of deionized water. Then, the ammonium persulfate solution was slowly added into Sol. A. After the mixed solution was left to stand for 24 h, the product was washed with methanol and anhydrous ethanol several times. Finally, after drying under vacuum at 50 °C, poly-*o*-phenylenediamine (POPDP) was obtained. In the following step, Ag-POPDP was synthesized as follows: 1.45 g of POPDP was added into 320 mL of 0.025 mol L^{-1}

AgNO_3 solution with mechanical agitation for 60 min at 30 °C. Afterwards, 380 mL of 0.025 mol L^{-1} NaBH_4 solution was added into the above mixed solution drop by drop. After reacting for 90 min under mechanical agitation, the product was washed with deionized water several times and then dried under vacuum at 50 °C. In consequence, Ag-POPDP was obtained.


Synthesis of imprinted Ag-POPDP/ CoFe_2O_4 . Imprinted Ag-POPDP/ CoFe_2O_4 was synthesized *via* the surface imprinting technique, by the following specific process: 0.5 g of CoFe_2O_4 and a certain amount of Ag-POPDP were added into 50 mL of DMSO. After reacting for 60 min under magnetic stirring at 30 °C, 0.05 g of ciprofloxacin (CIP) was added into this solution, and the reaction was continued for another 60 min under magnetic stirring at 30 °C. Subsequently, 0.5 mL of TRIM and 0.005 g of 2,2'-azobis(2,4-dimethylvaleronitrile) were both added into the above mixed solution. Then, the polymerization reaction was carried out in a microwave synthesizer (XH-300UL, Beijing XiangHu Science and Technology Development Co., Ltd) at 600 W and 40 °C under a N_2 atmosphere. After reacting for a period of time, the product was washed with deionized water and anhydrous ethanol several times. Afterwards, the molecular template (CIP) was removed by adding 200 mL deionized water into the above solution under simulated sunlight irradiation (250 W xenon lamp) for 3 h with magnetic agitation at 30 °C under an air atmosphere. Finally, the solid product was washed with deionized water and anhydrous ethanol several times. After drying under vacuum at 50 °C, imprinted Ag-POPDP/ CoFe_2O_4 was obtained. The general scheme of the synthesis approach is shown in Scheme 1.

Synthesis of non-imprinted Ag-POPDP/ CoFe_2O_4 . The synthesis process of non-imprinted Ag-POPDP/ CoFe_2O_4 was consistent with that of imprinted Ag-POPDP/ CoFe_2O_4 , but without the addition and removal process of CIP.

Characterization

Fourier-transformed infrared (FT-IR) spectra of the samples were recorded on a Nicolet Nexus 470 FT-IR (Thermo Nicolet Co., USA) with 2.0 cm^{-1} resolution in the range 400–4000 cm^{-1} , using KBr pellets. X-ray photoelectron spectroscopy (XPS) was measured with a PHI5300 spectrometer using an Al $K\alpha$ (12.5 kV) X-ray source. XRD patterns were obtained with a D8 ADVANCE X-ray diffractometer (Bruker AXS Co., Germany). The morphology was observed by a JEM-2010 transmission electron microscope (TEM, Japan) and a JSM-7001F scanning electron microscope (SEM, Japan) equipped with energy dispersive spectroscopy analysis (EDS). UV-vis diffuse reflectance spectra (UV-vis DRS) were obtained for the dry-pressed disk samples using a 2450 spectrometer (Shimadzu Co., Japan) equipped with the integrated sphere accessory for diffuse reflectance spectra, using BaSO_4 as the reflectance sample. The specific surface area, pore volume and average pore diameter of the samples were measured by using a NOVA 4000e high speed automated surface area and pore size analyzer (Quantachrome Co., USA). Magnetic measurement was carried out using a vibrating sample magnetometer (VSM) (7300, Lakeshore) under a magnetic field up to 10 kOe. The photoluminescence (PL)



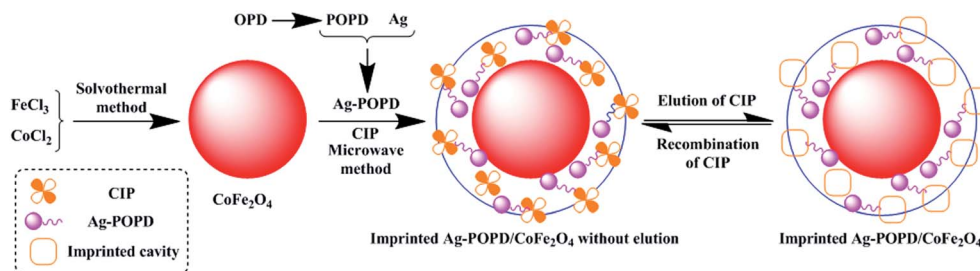

Scheme 1 General scheme of the synthesis approach.

spectra of different samples were investigated by utilizing a fluorescence spectrophotometer (Cary Eclipse Spectrophotometer, VARIAN, USA) equipped with a xenon lamp as the excitation source at room temperature with an excitation wavelength of 253 nm.

Experiments of adsorption, photocatalysis, selectivity, mechanism and reproducibility

The adsorption experiment was carried out with magnetic stirring (600 rpm) at 25 °C in the dark. Briefly, 0.1 g of sample was added into 100 mL of 10 mg L⁻¹ CIP solution. Subsequently, the sample analysis was carried out at intervals of 10 min. After 60 min in the dark, the solid sample was isolated using a magnet, and the concentration was measured with a UV-vis spectrophotometer 2450 (Shimadzu Co., Japan). The adsorption capacity (Q) was calculated by using the formula:

$$Q = \frac{(C_0 - C) \times V}{m} \quad (1)$$

where C_0 was the initial concentration of CIP, C was the concentration of CIP after adsorption, V was the volume of the CIP solution, and m was the mass of the sample.

The photocatalytic experiment was carried out at 25 °C with magnetic stirring (600 rpm) under an air atmosphere (the aeration rate was 2 mL min⁻¹) and simulated sunlight irradiation provided by a 250 W xenon lamp (the illuminance reached 1.8×10^5 lux). Briefly, 0.1 g of sample was added into 100 mL of 10 mg L⁻¹ CIP solution. After reaching the desired adsorption time in the dark, the initial concentration was determined. Subsequently, the sample analysis was carried out at intervals of 15 min. After exposure to simulated sunlight irradiation for 60 min, the concentration was measured with the UV-vis spectrophotometer 2450. The photodegradation degree was calculated by using the formula:

$$\text{Photodegradation degree} = 1 - \frac{C}{C_0} \times 100\% \quad (2)$$

where C_0 was the initial concentration of CIP after adsorption and C was the concentration of CIP after photodegradation reaction.

The selectivity experiment was carried out in accordance with the photocatalytic experiment, but during the reaction process, 0.1 g of sample was added into 100 mL of 20 mg L⁻¹ tetracycline (TC) solution, and the concentration was likewise

measured with the UV-vis spectrophotometer 2450. The selectivity coefficient ($k_{\text{selectivity}}$) was calculated by using the following formulas:

For the imprinted sample:

$$k_{\text{imprinted}} = \frac{\text{photodegradation degree (CIP)}}{\text{photodegradation degree (TC)}} \quad (3)$$

For other samples:

$$k_{\text{others}} = \frac{\text{photodegradation degree (CIP)}}{\text{photodegradation degree (TC)}} \quad (4)$$

For the selectivity coefficient:

$$k_{\text{selectivity}} = \frac{k_{\text{imprinted}}}{k_{\text{others}}} \quad (5)$$

In order to investigate the dominant reactive oxygen species and mechanism of degradation of CIP with the imprinted Ag-POPd/CoFe₂O₄, the corresponding experiments were also carried out in accordance with the above photocatalytic experiment, but with the following difference: at the beginning of the photocatalytic reaction, various quenchers (1 mmol) were added into the CIP solution, including *tert*-butyl alcohol (*t*-BuOH), triethanolamine (TEOA) and benzoquinone (BQ).

The reproducibility of the imprinted Ag-POPd/CoFe₂O₄ was investigated as follows: after the first photocatalytic reaction, the sample was isolated by a magnet and sonicated with anhydrous ethanol for 1 h to remove the residual CIP and by-products. After the product was washed with deionized water and dried, it was used to perform another photocatalytic reaction. The above procedure was repeated five times to confirm the reproducibility of the imprinted Ag-POPd/CoFe₂O₄.

Results and discussion

Characterization

The first task was to record the XRD patterns of different samples, which are shown in Fig. S2.† As can be clearly seen in Fig. S2a,† the XRD pattern matched the face-centered cubic structure of Ag (JCPDS standard card 65-2871): the diffraction peaks observed at $2\theta = 38.1^\circ$, 44.3° , 64.4° and 77.4° corresponded to the indexes (111), (200), (220) and (311) for Ag,^{52,53} which indicated that Ag had been successfully loaded on POPd.



Meanwhile, in Fig. S2b,[†] the diffraction peaks appearing at 2θ values of 30.1° , 35.4° , 37.1° , 43.1° , 53.4° , 56.9° , 62.5° , 70.9° , 73.9° and 74.9° correspond to the indexes (220), (311), (222), (400), (422), (511), (440), (620), (533) and (622) of the cubic CoFe_2O_4 with a spinel structure, and closely match the JCPDS standard card 22-1086 data file.^{46,48,54} In addition, the XRD patterns of imprinted Ag-POPDP/ CoFe_2O_4 and non-imprinted Ag-POPDP/ CoFe_2O_4 not only possessed all the characteristic diffraction peaks of CoFe_2O_4 , but also a strong and unambiguous diffraction peak of Ag, while no other diffraction peaks were observed in these two patterns. The results indicated that the crystalline structures of CoFe_2O_4 and Ag were not changed during coating of the outer layer.

In order to further confirm the elemental composition of imprinted Ag-POPDP/ CoFe_2O_4 , XPS spectra were recorded, as shown in Fig. 1. It could be clearly seen that the C 1s pattern showed a dominant peak at 283.75 eV, accompanied by two minor peaks at 285.31 eV and 286.53 eV, which were assigned to C=C, C-O and -COO groups, respectively.³⁶ The four component peaks of N 1s were attributed to pyridinic N (398.71 eV), nitrile N or imine N (399.41 eV), pyrrolic N (400.41 eV) and graphitic N (401.31 eV).^{35,36} The peaks at 530.2 eV, 531.2 eV, 532.2 eV and 534.2 eV were assigned to adsorbed oxygen, =C=O/C-O-C-, -O-C=O and -N-O-, respectively.^{35,36} All the above peaks confirmed that POPD was successfully synthesized. Furthermore, Ag 3d_{5/2} (368.69 eV) and Ag 3d_{3/2} (374.79 eV) were observed in the sample, indicating that the as-prepared sample possessed Ag.⁵⁴ Moreover, the peaks at 779.64 eV (with a satellite peak at 784.83 eV) and at 798.61 eV (with a satellite peak at 804.23 eV) correspond to Co 2p_{3/2} and Co 2p_{1/2}, respectively, and

are the characteristic peaks of Co^{2+} .⁵⁴ At the same time, Fe 2p_{3/2} (711.29 eV) and Fe 2p_{1/2} (723.49 eV) were observed in the sample.⁵⁴ The presence of Co 2p_{3/2}, Co 2p_{1/2}, Fe 2p_{3/2} and Fe 2p_{1/2} indicated that CoFe_2O_4 was present in the as-prepared sample. Therefore, all the above results confirmed that the imprinted Ag-POPDP/ CoFe_2O_4 was successfully synthesized.

Fig. 2 presents the FT-IR spectra of CoFe_2O_4 and imprinted Ag-POPDP/ CoFe_2O_4 , which were recorded to further verify the formation of imprinted Ag-POPDP/ CoFe_2O_4 . Compared with CoFe_2O_4 , due to the formation of the imprinted layer and the introduction of POPD, some additional absorption peaks (1668 cm^{-1} , 1523 cm^{-1} , 1481 cm^{-1} , 1384 cm^{-1} , 1295 cm^{-1} , 1189 cm^{-1} , 949 cm^{-1} and 893 cm^{-1}) were observed in imprinted Ag-POPDP/ CoFe_2O_4 . The absorption peak at 1668 cm^{-1} was attributed to the stretching vibration of C=O,¹⁶ the absorption peak of C=C was observed at 1523 cm^{-1} ,⁵⁵ the absorption peak at 1481 cm^{-1} was assigned to the skeleton vibration peaks of the benzene ring,¹⁶ the absorption peaks of C-N-C were observed at 1384 cm^{-1} and 1295 cm^{-1} ,⁵⁵ the absorption peak of C-C was observed at 1189 cm^{-1} ,⁵⁵ and the absorption peaks of C-H were observed at 949 cm^{-1} and 893 cm^{-1} . All the above absorption peaks indicated that POPD and the imprinted layer were successfully formed in imprinted Ag-POPDP/ CoFe_2O_4 , and the imprinted Ag-POPDP/ CoFe_2O_4 had been successfully synthesized.

TEM images, SEM images and EDS spectra of CoFe_2O_4 and imprinted Ag-POPDP/ CoFe_2O_4 are shown in Fig. 3 and S3.[†] Fig. 3a and c display that CoFe_2O_4 possessed a good spherical structure with an average diameter of approximately 500 nm. The presence of the elements O, Fe and Co, as indicated in Fig. S3a,[†] confirmed again that CoFe_2O_4 had been successfully synthesized. Compared with Fig. 3a, a surface coating layer can be clearly observed in Fig. 3b, which indicates that the surface imprinted layer had been successfully coated on the surface of CoFe_2O_4 . It can be clearly seen from Fig. 3b and d that after coating the surface imprinted layer, the imprinted Ag-POPDP/ CoFe_2O_4 still possessed good spherical and core-shell structure,

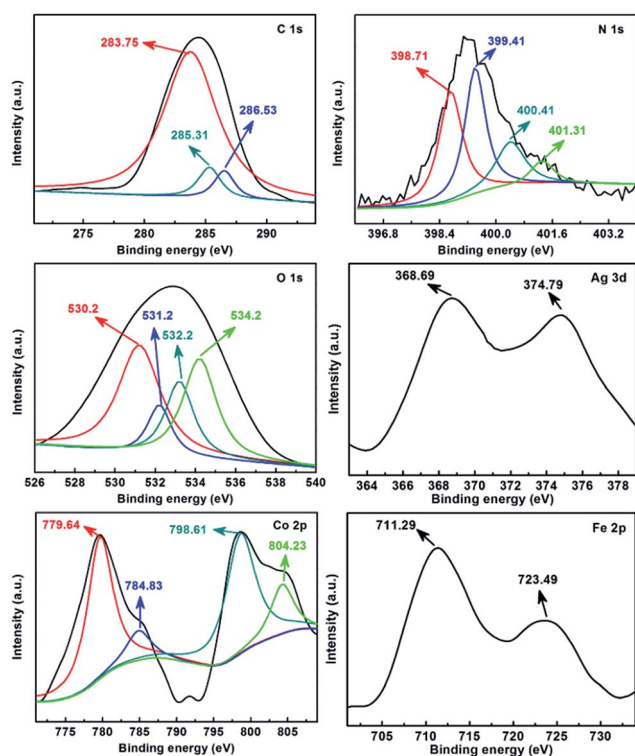


Fig. 1 XPS spectra of imprinted Ag-POPDP/ CoFe_2O_4 .

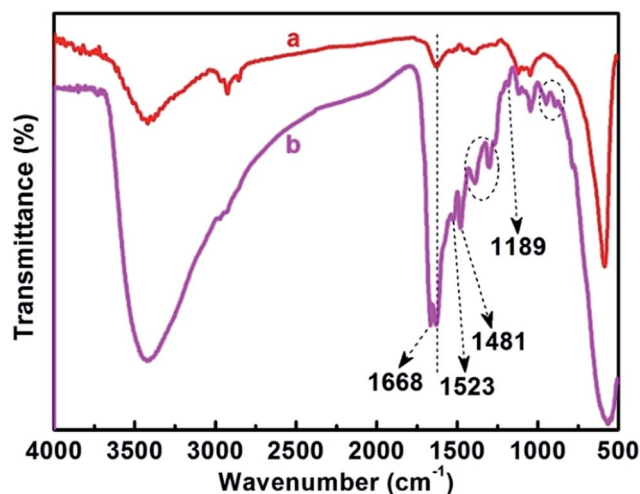


Fig. 2 FT-IR spectra of different samples ((a) CoFe_2O_4 and (b) imprinted Ag-POPDP/ CoFe_2O_4).



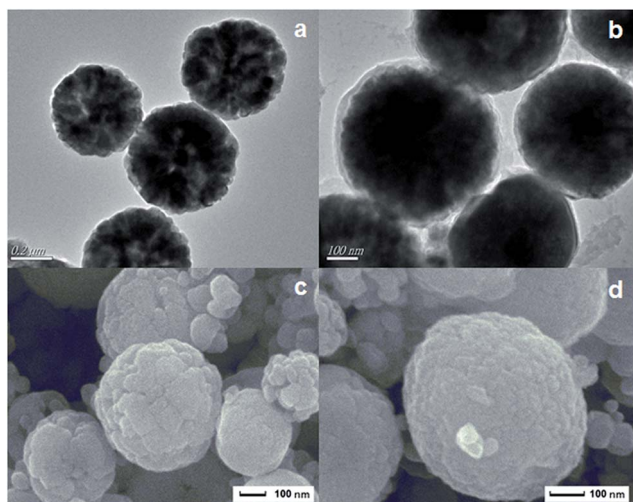


Fig. 3 TEM images and SEM images of CoFe_2O_4 (a and c) and imprinted Ag-POPd/ CoFe_2O_4 (b and d).

and the average diameter was approximately 530 nm. Furthermore, compared with Fig. S3a,[†] the additional elements C and Ag are observed in Fig. S3b,[†] which verifies again that Ag-POPd and the imprinted layer were both present in the imprinted Ag-POPd/ CoFe_2O_4 .

In order to further confirm that the imprinted cavities were indeed present in the imprinted layer, N_2 adsorption-desorption experiments were carried out. As shown in Fig. 4, it could be clearly seen that the N_2 adsorption-desorption isotherm of imprinted Ag-POPd/ CoFe_2O_4 displayed the type IV behavior with distinct hysteresis loops consistent with the H1 type, demonstrating that the imprinted Ag-POPd/ CoFe_2O_4 possessed a mesoporous structure.^{56,57} The BET specific surface area reached $199.09 \text{ m}^2 \text{ g}^{-1}$ and the average pore diameter obtained from the Barrett-Joyner-Halenda (BJH) method was 2.61 nm. Furthermore, as shown in Fig. S4,[†] compared with imprinted Ag-POPd/ CoFe_2O_4 , the non-imprinted Ag-POPd/ CoFe_2O_4

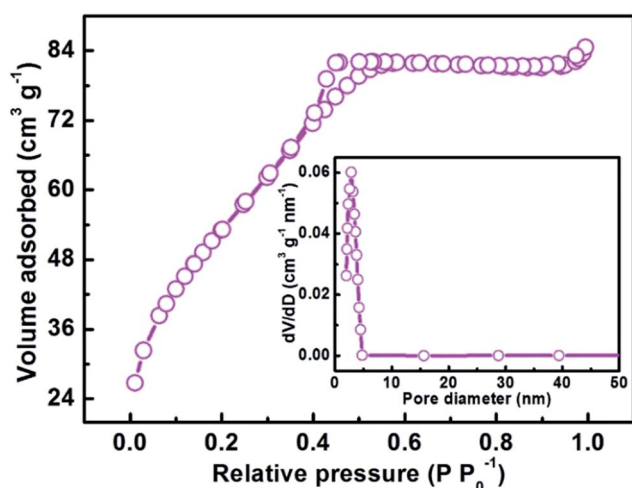


Fig. 4 N_2 adsorption-desorption isotherm and corresponding pore size distribution curve (inset) of the imprinted Ag-POPd/ CoFe_2O_4 .

possessed a very small BET specific surface area ($9.47 \text{ m}^2 \text{ g}^{-1}$) and a large average pore diameter (28.93 nm), due to the fact that no imprinted cavities were present in the non-imprinted Ag-POPd/ CoFe_2O_4 . Therefore, the N_2 adsorption-desorption experiments conclusively proved that imprinted cavities were formed in the imprinted layer of imprinted Ag-POPd/ CoFe_2O_4 .

Fig. 5 and S5[†] show the UV-vis DRS spectra and the magnetization patterns at room temperature of CoFe_2O_4 and imprinted Ag-POPd/ CoFe_2O_4 . As shown in Fig. 5, after coating the imprinted layer and introducing Ag-POPd, imprinted Ag-POPd/ CoFe_2O_4 exhibited good absorption across a wide range of light wavelengths, which indicated that the imprinted Ag-POPd/ CoFe_2O_4 had a favorable response to light. Moreover, Fig. S5[†] shows that the magnetic saturation (M_s) value of CoFe_2O_4 was 69.08 emu g^{-1} , which represents distinct magnetism. Moreover, even after coating the imprinted layer, the magnetic saturation (M_s) value of imprinted Ag-POPd/ CoFe_2O_4 was 65.82 emu g^{-1} , which showed that the distinct magnetism was not significantly reduced. From the photograph (inset in Fig. 5), it could be clearly observed that the imprinted Ag-POPd/ CoFe_2O_4 could be easily separated by a magnet, indicating that the imprinted Ag-POPd/ CoFe_2O_4 indeed possessed good magnetic separation performance.

Adsorption, photocatalytic activity, selectivity and reproducibility

As shown in Fig. 6, the adsorption performance of different samples was investigated. For the first 30 min of adsorption, the adsorption capacity of CoFe_2O_4 , Ag-POPd, imprinted Ag-POPd/ CoFe_2O_4 and non-imprinted Ag-POPd/ CoFe_2O_4 increased significantly. After 30 min of adsorption, the reaction process, which followed the order of adsorption-desorption-adsorption, reached the equilibrium adsorption state for photocatalysis. At this time, the value of the adsorption capacity of CoFe_2O_4 , Ag-POPd, imprinted Ag-POPd/ CoFe_2O_4 and non-imprinted Ag-

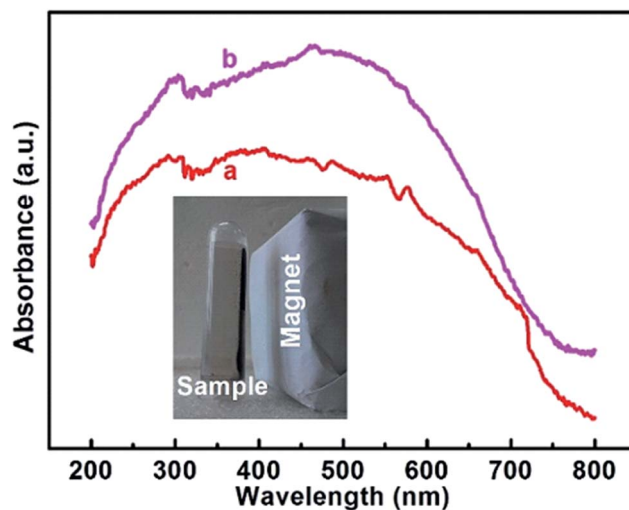


Fig. 5 UV-vis DRS spectra of CoFe_2O_4 (a) and imprinted Ag-POPd/ CoFe_2O_4 (b) (inset is the photograph of the imprinted Ag-POPd/ CoFe_2O_4 separated from solution under a magnet).



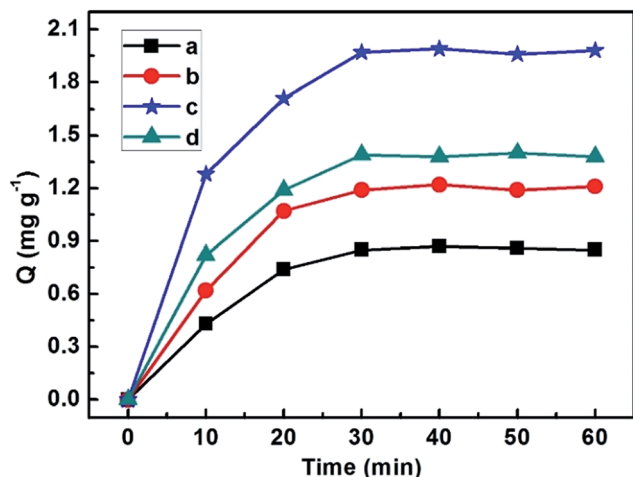


Fig. 6 Adsorption capacities of different samples ((a) CoFe₂O₄, (b) Ag-POP, (c) imprinted Ag-POP/CoFe₂O₄ and (d) non-imprinted Ag-POP/CoFe₂O₄).

POP/CoFe₂O₄ fluctuated around 0.85 mg g⁻¹, 1.21 mg g⁻¹, 1.98 mg g⁻¹ and 1.38 mg g⁻¹, respectively. The above results indicated that compared with CoFe₂O₄, Ag-POP and non-imprinted Ag-POP/CoFe₂O₄, imprinted Ag-POP/CoFe₂O₄ exhibited the highest adsorption performance, because of the existence of a large number of imprinted cavities in the imprinted layer of imprinted Ag-POP/CoFe₂O₄, which had a strong specific recognition capability for selective adsorption of CIP. Therefore, in the following experiments, 30 min was chosen as the desired adsorption time.

In order to achieve a better photocatalytic activity, the influences of different additive doses of Ag-POP and different microwave polymerization times on the photocatalytic activity of the imprinted Ag-POP/CoFe₂O₄ were investigated, as shown in Fig. 7. In Fig. 7A, when the additive dose of Ag-POP was 0.1 g, the imprinted Ag-POP/CoFe₂O₄ possessed the highest photocatalytic activity (94.38%). When the additive dose of Ag-POP was lower than 0.1 g, the content of Ag-POP was below the optimum value, resulting in lower photocatalytic activity. Meanwhile, when the additive dose of Ag-POP was

higher than 0.1 g, the excessive Ag-POP led to a lower density of imprinted cavities in the imprinted layer. Thus, the distribution of imprinted cavities on the surface became less dense, which in turn led to a decrease in photocatalytic activity. Hence 0.1 g was the optimum additive dose of Ag-POP. Furthermore, as shown in Fig. 7B, the optimum microwave polymerization time was 60 min: under these conditions, the photodegradation degree reached 94.38%. When the microwave polymerization time was lower than 60 min, the polymerization was not complete, namely, the imprinted layer had not been fully formed, resulting in low photocatalytic activity. Meanwhile, when the microwave polymerization time was higher than 60 min, the degree of microwave polymerization was too high: on one hand, the imprinted layer became thicker, and the distribution of imprinted cavities on the surface became less dense, while on the other hand, the bonding became more stable, which was detrimental to the removal and re-binding of CIP. The above two factors both led to low photocatalytic activity. Therefore, in the following experiments, 0.1 g was chosen as the additive dose of Ag-POP, and 60 min was chosen as the microwave polymerization time.

The selectivity of different samples was investigated by comparing the photodegradation degree for degradation of CIP and TC, as displayed in Fig. 8. It could be clearly seen that the photocatalytic activity of CoFe₂O₄ was very low, possibly implying that degradation mainly relied on the adsorption and self-degradation of CIP and TC. Furthermore, for photodegradation of CIP, imprinted Ag-POP/CoFe₂O₄ possessed a large number of imprinted cavities in the imprinted layer and these imprinted cavities had strong affinity to CIP, enabling them to specifically recognize and selectively photodegrade CIP. Hence, imprinted Ag-POP/CoFe₂O₄ achieved the highest photodegradation degree (94.38%) in 90 min under simulated sunlight irradiation, which was approximately 5.47 times that of CoFe₂O₄, 1.34 times that of Ag-POP and 1.29 times that of non-imprinted Ag-POP/CoFe₂O₄. On the other hand, because of the relatively large structural difference between CIP and TC, the imprinted cavities could not efficiently specifically recognize TC. Therefore, for photodegradation of TC, compared with Ag-POP and non-imprinted Ag-POP/CoFe₂O₄, imprinted Ag-

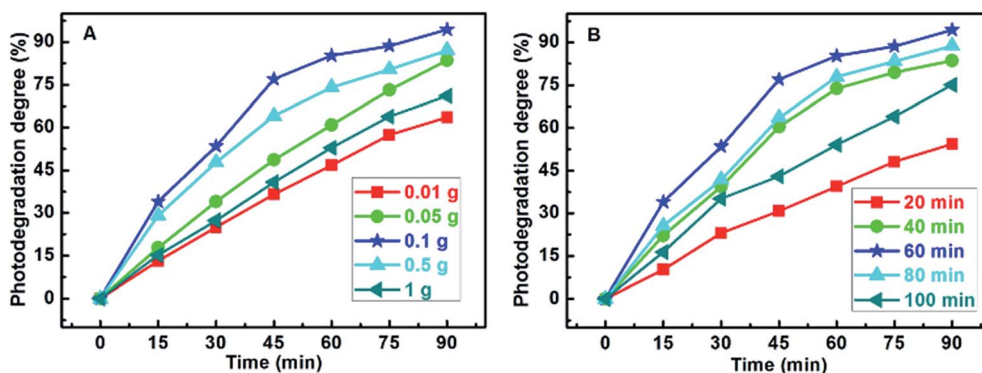


Fig. 7 Influence of different additive doses of Ag-POP (A) and influence of different microwave polymerization times (B) on photocatalytic activity of the imprinted Ag-POP/CoFe₂O₄.



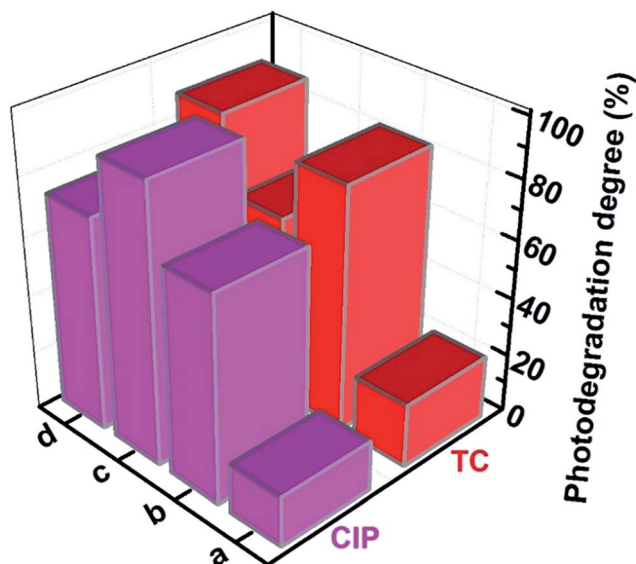


Fig. 8 Selectivity for degradation of different pollutants with different samples under simulated sunlight irradiation for 90 min ((a) CoFe_2O_4 , (b) Ag-POPD, (c) imprinted Ag-POPD/ CoFe_2O_4 and (d) non-imprinted Ag-POPD/ CoFe_2O_4).

POPD/ CoFe_2O_4 achieved a relatively poor photodegradation degree (62.75%) in 90 min under simulated sunlight irradiation.

In addition, Table 1 presents the detailed photodegradation degrees and coefficients of selectivity of the different photocatalysts. The coefficient of selectivity ($k_{\text{selectivity}}$) of imprinted Ag-POPD/ CoFe_2O_4 relative to CoFe_2O_4 , Ag-POPD and non-imprinted Ag-POPD/ CoFe_2O_4 was 1.88, 1.79 and 1.83, respectively. These values of $k_{\text{selectivity}}$ indicated that imprinted Ag-POPD/ CoFe_2O_4 was highly selective for the structure of CIP as a result of the imprinted cavities, which could selectively photodegrade CIP in the presence of TC. Therefore, all the above results demonstrated that imprinted Ag-POPD/ CoFe_2O_4 not only had high photocatalytic efficiency, but also possessed the specific recognition capability for selective photodegradation of CIP.

The reproducibility of imprinted Ag-POPD/ CoFe_2O_4 was investigated by performing 5 cycles of use, as shown in Fig. S6.† It could be clearly seen that the imprinted Ag-POPD/ CoFe_2O_4 could be used for at least 5 cycles with little loss of

photocatalytic activity, demonstrating that the imprinted Ag-POPD/ CoFe_2O_4 had good photocatalytic stability and reproducibility. Furthermore, Fig. S6B† shows that the XRD pattern of the sample after 5 cycles was nearly the same as that of the initial sample, demonstrating that the crystalline structure of imprinted Ag-POPD/ CoFe_2O_4 was not changed during the photocatalytic reaction. In addition, the photoluminescence (PL) spectra^{58,59} were further investigated to confirm the reproducibility, as shown in Fig. S7.† It could be easily observed that the spectrum of imprinted Ag-POPD/ CoFe_2O_4 was almost unchanged after 5 cycles, demonstrating that the as-prepared imprinted Ag-POPD/ CoFe_2O_4 had good photocatalytic stability and reproducibility.

Dominant reactive oxygen species and mechanism

In order to investigate the photocatalytic mechanism of degradation of CIP with the imprinted Ag-POPD/ CoFe_2O_4 , photocatalytic experiments were performed in which TEOA, *t*-BuOH or BQ were used as quenchers for h^+ , $\cdot\text{OH}$, and $\cdot\text{O}_2^-$, respectively. The results are shown in Fig. 9. When *t*-BuOH and BQ were added into the CIP solution, the photodegradation degree was reduced to 79.29% and 64.88%, respectively, compared with that without quencher (94.38%), which indicated that *t*-BuOH and BQ had little effect on the photocatalytic activity of

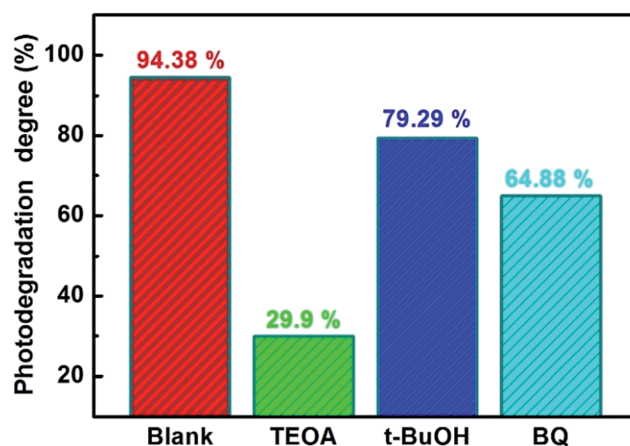


Fig. 9 Photodegradation degrees for degradation of CIP with the imprinted Ag-POPD/ CoFe_2O_4 in the presence of different quenchers under simulated sunlight irradiation for 90 min.

Table 1 Photodegradation degrees and coefficients of selectivity with different photocatalysts under simulated sunlight irradiation for 90 min

Photocatalysts	Antibiotic solution	Photodegradation degrees (%)	$k_{\text{imprinted}}$	k_{others}	$k_{\text{selectivity}}$
CoFe_2O_4	CIP	17.25	—	0.8	1.88
	TC	21.68			
Ag-POPD	CIP	70.41	—	0.84	1.79
	TC	83.61			
Imprinted Ag-POPD/ CoFe_2O_4	CIP	94.38	1.5	—	—
	TC	62.75			
Non-imprinted Ag-POPD/ CoFe_2O_4	CIP	73	—	0.82	1.83
	TC	88.61			



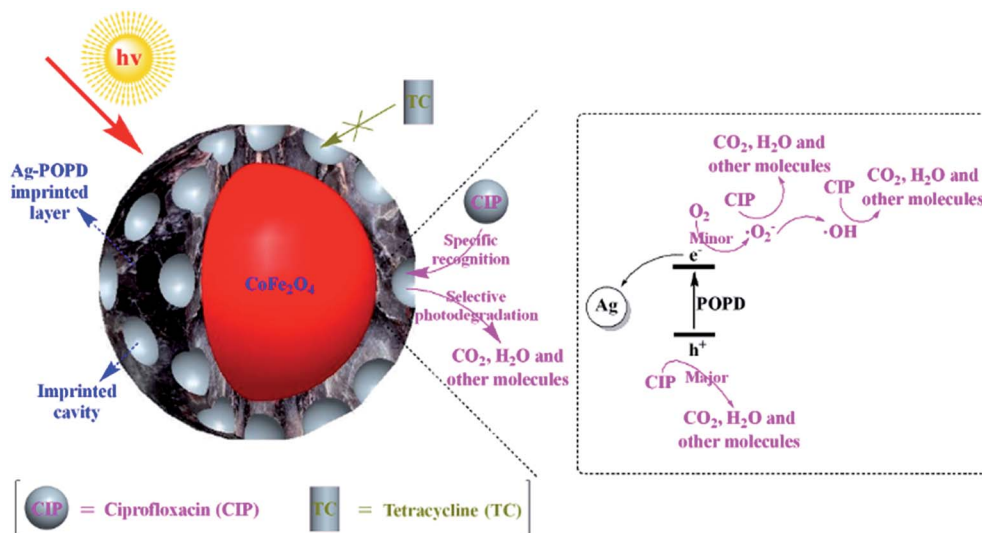


Fig. 10 Proposed selective photocatalytic mechanism of the imprinted Ag-POPd/CoFe₂O₄.

imprinted Ag-POPd/CoFe₂O₄. In contrast, when TEOA was added into the CIP solution, the photodegradation degree was heavily reduced to only 29.9%, indicating that TEOA exerted a significant effect on the photocatalytic activity of imprinted Ag-POPd/CoFe₂O₄. Therefore, in this photocatalytic reaction, h^+ was the main oxidative species, O_2^- was the secondary oxidative species, while $\cdot OH$ only played a small role. Based on the above results, we note that if h^+ had reacted with H₂O or OH⁻ to form $\cdot OH$ in large amounts, $\cdot OH$ would have played a greater role. Hence, we draw the interesting conclusion that $\cdot OH$ was not formed in large amounts by the reaction of h^+ and H₂O/OH⁻.

Combining all the above results, the selective photocatalytic mechanism of imprinted Ag-POPd/CoFe₂O₄ was proposed, as displayed in Fig. 10. Briefly, when imprinted Ag-POPd/CoFe₂O₄ was exposed to simulated sunlight, electrons (e^-) and holes (h^+) were generated in the LUMO energy level and the HOMO energy level of POPd. Afterwards, the majority of e^- in the LUMO energy level of POPd transferred to Ag, while the remaining minority of e^- in the LUMO energy level of POPd were captured by dissolved O₂ to generate superoxide radicals (O_2^-), which further generated hydroxyl radicals ($\cdot OH$). The O_2^- and $\cdot OH$ that originated from O₂ played only a minor role in the photocatalytic reaction. Meanwhile, the h^+ could directly oxidize CIP to generate CO₂, H₂O and other molecules. In addition, CIP could be specifically recognized by the imprinted cavities in the imprinted layer, but TC could not. Therefore, the specific recognition and selective photodegradation of CIP was realized through the imprinted cavities.

Conclusions

In brief, based on CoFe₂O₄ as the carrier, an imprinted Ag-POPd/CoFe₂O₄ was synthesized *via* the surface imprinting technique, and possessed a spherical core-shell structure, strong response to light, good magnetic separation

performance and good reproducibility. Moreover, when the additive dose of Ag-POPd was 0.1 g and the microwave polymerization time was 60 min, the imprinted Ag-POPd/CoFe₂O₄ achieved the highest photodegradation degree (94.38%) for degradation of CIP in 90 min under simulated sunlight irradiation. Furthermore, Ag-POPd was introduced into the imprinted layer, which significantly enhanced the photocatalytic activity; meanwhile, due to the existence of imprinted cavities in the imprinted layer, the imprinted Ag-POPd/CoFe₂O₄ exhibited a superior specific recognition capability for selective photodegradation of CIP. In addition, in this photocatalytic reaction, h^+ was the main oxidative species, O_2^- was the secondary oxidative species, while $\cdot OH$ only played a small role.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

This work was financially supported by the National Natural Science Foundation of China (No. 21607062), the Natural Science Foundation of Jiangsu Province (No. BK20160494, BK20140532 and BK20150536), the China Postdoctoral Science Foundation (No. 2016M600378 and 2017T100333), the Social Development Project of Key Research Program of Zhenjiang (No. SH2016018), the Youth Talent Development Program of Jiangsu University and Jiangsu Collaborative Innovation Center of Technology and Material of Water Treatment.

References

- 1 C. Santhosh, V. Velmurugan, G. Jacob, S. K. Jeong, A. N. Grace and A. Bhatnagar, *Chem. Eng. J.*, 2016, **306**, 1116–1137.



- 2 Z. Zhu, X. Tang, S. Kang, P. W. Huo, M. S. Song, W. D. Shi, Z. Y. Lu and Y. S. Yan, *J. Phys. Chem. C*, 2016, **120**, 27250–27258.
- 3 K. H. Chu, Y. A. J. Al-Hamadani, C. M. Park, G. Lee, M. Jang, A. Jang, N. Her, A. Son and Y. Yoon, *Chem. Eng. J.*, 2017, **327**, 629–647.
- 4 Z. Y. Lu, P. W. Huo, Y. Y. Luo, X. L. Liu, D. Wu, X. Gao, C. X. Li and Y. S. Yan, *J. Mol. Catal. A: Chem.*, 2013, **378**, 91–98.
- 5 G. G. Liu, K. Han, H. Q. Ye, C. Y. Zhu, Y. P. Gao, Y. Liu and Y. H. Zhou, *Chem. Eng. J.*, 2017, **320**, 74–80.
- 6 A. R. Silva, P. M. Martins, S. Teixeira, S. A. C. Carabineiro, K. Kuehn, G. Cuniberti, M. M. Alves, S. Lanceros-Mendez and L. Pereira, *RSC Adv.*, 2016, **6**, 95494–95503.
- 7 Z. Y. Lu, Z. Zhu, D. D. Wang, Z. F. Ma, W. D. Shi, Y. S. Yan, X. X. Zhao, H. J. Dong, L. Yang and Z. F. Hua, *Catal. Sci. Technol.*, 2016, **6**, 1367–1377.
- 8 B. X. Liu, Y. K. Huang, Q. Shen, X. Zhu, Y. Q. Hao, P. Qu and M. T. Xu, *RSC Adv.*, 2016, **6**, 100743–100747.
- 9 S. Martin, A. Shchukarev, K. Hanna and J. Boily, *Environ. Sci. Technol.*, 2015, **49**, 12197–12205.
- 10 Z. W. Zhao, J. H. Zhao and C. Yang, *Chem. Eng. J.*, 2017, **327**, 481–489.
- 11 Z. Y. Lu, X. X. Zhao, Z. Zhu, Y. S. Yan, W. D. Shi, H. J. Dong, Z. F. Ma, N. L. Gao, Y. S. Wang and H. Huang, *Chem.–Eur. J.*, 2015, **21**, 18528–18533.
- 12 M. F. Li, Y. G. Liu, S. B. Liu, D. Shu, G. M. Zeng, X. J. Hu, X. F. Tan, L. H. Jiang, Z. L. Yan and X. X. Cai, *Chem. Eng. J.*, 2017, **319**, 219–228.
- 13 A. Hassani, A. Khataee and S. Karaca, *J. Mol. Catal. A: Chem.*, 2015, **409**, 149–161.
- 14 C. Bojer, J. Schöbel, T. Martin, M. Ertl, H. Schmalz and J. Breu, *Appl. Catal., B*, 2017, **204**, 561–565.
- 15 X. B. Yang, J. Chen, H. X. Lai, J. P. Hu, M. Fang and X. T. Luo, *RSC Adv.*, 2017, **7**, 38519–38525.
- 16 Z. Y. Lu, Y. Y. Luo, M. He, P. W. Huo, T. T. Chen, W. D. Shi, Y. S. Yan, J. M. Pan, Z. F. Ma and S. Y. Yang, *RSC Adv.*, 2013, **3**, 18373–18382.
- 17 G. Z. Yuan, C. F. Hsia, Z. W. Lin, C. Chiang, Y. W. Chiang and M. H. Huang, *Chem.–Eur. J.*, 2016, **22**, 12548–12556.
- 18 Y. Y. Shao, W. D. Ye, C. Y. Sun, C. L. Liu and Q. Wang, *RSC Adv.*, 2017, **7**, 39089–39095.
- 19 Y. Xu, Z. C. Fu, S. Cao, Y. Chen and W. F. Fu, *Catal. Sci. Technol.*, 2017, **7**, 587–595.
- 20 Z. Y. Lu, W. C. Zhou, P. W. Huo, Y. Y. Luo, M. He, J. M. Pan, C. X. Li and Y. S. Yan, *Chem. Eng. J.*, 2013, **217**, 398–406.
- 21 S. N. Liu, M. Zheng, R. Chen and Z. S. Wang, *RSC Adv.*, 2017, **7**, 31230–31238.
- 22 Z. Zhu, X. Tang, C. C. Ma, M. S. Song, N. L. Gao, Y. S. Wang, P. W. Huo, Z. Y. Lu and Y. S. Yan, *Appl. Surf. Sci.*, 2016, **387**, 366–374.
- 23 H. W. Bai, Z. Y. Liu, L. Liu and D. D. Sun, *Chem.–Eur. J.*, 2013, **19**, 3061–3070.
- 24 Y. N. Zhang, W. G. Dai, Y. Z. Wen and G. H. Zhao, *Appl. Catal., B*, 2017, **212**, 185–192.
- 25 Z. Y. Lu, X. X. Zhao, Z. Zhu, M. S. Song, N. L. Gao, Y. S. Wang, Z. F. Ma, W. D. Shi, Y. S. Yan and H. J. Dong, *Catal. Sci. Technol.*, 2016, **6**, 6513–6524.
- 26 C. Lai, M. M. Wang, G. M. Zeng, Y. G. Liu, D. L. Huang, C. Zhang, R. Z. Wang, P. Xu, M. Cheng, C. Huang, H. P. Wu and L. Qin, *Appl. Surf. Sci.*, 2016, **390**, 368–376.
- 27 Y. Y. Wu, Y. M. Dong, X. F. Xia, X. Liu and H. X. Li, *Appl. Surf. Sci.*, 2016, **364**, 829–836.
- 28 L. X. Chen, X. Y. Wang, W. H. Lu, X. Q. Wu and J. H. Li, *Chem. Soc. Rev.*, 2016, **45**, 2137–2211.
- 29 R. N. Liang, J. W. Ding, S. S. Gao and W. Qin, *Angew. Chem., Int. Ed.*, 2017, **56**, 6833–6837.
- 30 Z. Y. Lu, F. Chen, M. He, M. S. Song, Z. F. Ma, W. D. Shi, Y. S. Yan, J. Z. Lan, F. Li and P. Xiao, *Chem. Eng. J.*, 2014, **249**, 15–26.
- 31 X. T. Shen, L. H. Zhu, G. X. Liu, H. W. Yu and H. Q. Tang, *Environ. Sci. Technol.*, 2008, **42**, 1687–1692.
- 32 R. Yang, Y. X. Liu, X. Y. Yan, S. M. Liu and H. S. Zheng, *J. Mater. Chem. A*, 2016, **4**, 9807–9815.
- 33 S. J. Li, S. S. Cao, M. J. Whitcombe and S. A. Piletsky, *Prog. Polym. Sci.*, 2014, **39**, 145–163.
- 34 Z. Zhu, Y. Yu, H. Huang, X. Yao, H. J. Dong, Z. Liu, Y. S. Yan, C. X. Li and P. W. Huo, *Catal. Sci. Technol.*, 2017, **7**, 4092–4104.
- 35 H. Zhu, X. L. Wang, X. X. Liu and X. R. Yang, *Adv. Mater.*, 2012, **24**, 6524–6529.
- 36 C. Q. Yuan, X. H. Liu, M. Y. Jia, Z. X. Luo and J. N. Yao, *J. Mater. Chem. A*, 2015, **3**, 3409–3415.
- 37 M. R. Huang, Q. Y. Peng and X. G. Li, *Chem.–Eur. J.*, 2006, **12**, 4341–4350.
- 38 A. J. Cheah, W. S. Chiu, P. S. Khiew, H. Nakajima, T. Saisopa, P. Songsiriritthigul, S. Radiman and M. A. A. Hamid, *Catal. Sci. Technol.*, 2015, **5**, 4133–4143.
- 39 A. Meng, J. Xing, Z. J. Li, Q. Wei and Q. D. Li, *J. Mol. Catal. A: Chem.*, 2016, **411**, 290–298.
- 40 J. Jiang, H. Li and L. Z. Zhang, *Chem.–Eur. J.*, 2012, **18**, 6360–6369.
- 41 W. Zhang, L. Zhou and H. P. Deng, *J. Mol. Catal. A: Chem.*, 2016, **423**, 270–276.
- 42 K. Yuan, L. Chen and Y. W. Chen, *Chem.–Eur. J.*, 2015, **21**, 11899–11906.
- 43 C. Boitard, A. Rollet, C. Ménager and N. Griffete, *Chem. Commun.*, 2017, **53**, 8846–8849.
- 44 Y. S. Wang, Z. Y. Lu, Z. Zhu, X. X. Zhao, N. L. Gao, D. D. Wang, Z. F. Hua, Y. S. Yan, P. W. Huo and M. S. Song, *RSC Adv.*, 2016, **6**, 51877–51887.
- 45 R. Z. Wang, D. L. Huang, Y. G. Liu, Z. W. Peng, G. M. Zeng, C. Lai, P. Xu, C. Huang, C. Zhang and X. M. Gong, *RSC Adv.*, 2016, **6**, 106201–106210.
- 46 X. L. Li, H. J. Lu, Y. Zhang and F. He, *Chem. Eng. J.*, 2017, **316**, 893–902.
- 47 J. H. Tong, L. L. Bo, Z. Li, Z. Q. Lei and C. G. Xia, *J. Mol. Catal. A: Chem.*, 2009, **307**, 58–63.
- 48 Z. Y. Lu, M. He, L. L. Yang, Z. F. Ma, L. Yang, D. D. Wang, Y. S. Yan, W. D. Shi, Y. Liu and Z. F. Hua, *RSC Adv.*, 2015, **5**, 47820–47829.
- 49 K. F. Ortega, S. Anke, S. Salamon, F. Özcan, J. Heese, C. Andronesco, J. Landers, H. Wende, W. Schuhmann, M. Muhler, T. Lunkenbein and M. Behrens, *Chem.–Eur. J.*, 2017, **23**, 12443–12449.



- 50 K. K. Senapati, C. Borgohain and P. Phukan, *Catal. Sci. Technol.*, 2012, **2**, 2361–2366.
- 51 X. X. Pan, L. Q. Yan, C. G. Li, R. J. Qu and Z. Y. Wang, *Chem. Eng. J.*, 2017, **326**, 1197–1209.
- 52 H. H. Ji, L. Lyu, L. L. Zhang, X. Q. An and C. Hu, *Appl. Catal., B*, 2016, **199**, 230–240.
- 53 Q. Wu, G. E. Chen, W. G. Sun, Z. L. Xu, Y. F. Kong, X. P. Zheng and S. J. Xu, *Chem. Eng. J.*, 2017, **313**, 450–460.
- 54 L. Q. Jing, Y. G. Xu, S. Q. Huang, M. Xie, M. Q. He, H. Xu, H. M. Li and Q. Zhang, *Appl. Catal., B*, 2016, **199**, 11–22.
- 55 X. G. Li, M. R. Huang and W. Duan, *Chem. Rev.*, 2002, **102**, 2925–3030.
- 56 P. F. Zhang, L. Wang, S. Z. Yang, J. A. Schott, X. F. Liu, S. M. Mahurin, C. L. Huang, Y. Zhang, P. F. Fulvio, M. F. Chisholm and S. Dai, *Nat. Commun.*, 2017, **8**, 15020.
- 57 Y. W. Jiang, J. L. Carvalho-de-Souza, R. C. S. Wong, Z. Q. Luo, D. Isheim, X. B. Zuo, A. W. Nicholls, I. W. Jung, J. P. Yue, D. J. Liu, Y. C. Wang, V. D. Andrade, X. H. Xiao, L. Navrazhnykh, D. E. Weiss, X. Y. Wu, D. N. Seidman, F. Bezanilla and B. Z. Tian, *Nat. Mater.*, 2016, **15**, 1023–1030.
- 58 G. T. Pan, C. M. Huang, P. Y. Peng and T. C. K. Yang, *Catal. Today*, 2011, **164**, 377–383.
- 59 W. S. Chang, Y. C. M. Li, T. W. Chung, Y. S. Lin and C. M. Huang, *Appl. Catal., A*, 2011, **407**, 224–230.

