

Cite this: *RSC Adv.*, 2017, 7, 50693

Visible light-induced photocatalytic degradation of gas-phase acetaldehyde with platinum/reduced titanium oxide-loaded carbon paper†

Soonhyun Kim, *^a Minsun Kim,^a Ha-Young Lee^b and Jong-Sung Yu *^b

Visible light-induced degradation of gas-phase acetaldehyde (CH_3CHO) is investigated using O-deficient reduced TiO_{2-x} -loaded carbon paper. The carbon paper is synthesized by the pyrolysis of a filter paper, and the reduced TiO_{2-x} is prepared by the magnesiothermic reduction of commercial anatase TiO_2 . The surface areas of the non-carbonized filter paper and carbon papers obtained by carbonization at 400, 600, 800, and 1000 °C are 4.31 $\text{m}^2 \text{g}^{-1}$, 13.57 $\text{m}^2 \text{g}^{-1}$, 466.81 $\text{m}^2 \text{g}^{-1}$, 461.60 $\text{m}^2 \text{g}^{-1}$, and 26.28 $\text{m}^2 \text{g}^{-1}$, respectively. Although the as-prepared carbon papers possess much lower specific surface areas than that of commercial activated carbon (2200 $\text{m}^2 \text{g}^{-1}$), the carbon papers show better adsorption capabilities. The O-deficient reduced TiO_{2-x} samples exhibit strong visible-light absorption, and the reduced TiO_{2-x} -loaded carbon papers induce rapid degradation of CH_3CHO and simultaneous generation of CO_2 in both closed-circulation and continuous-flow modes under visible light irradiation ($\lambda > 420 \text{ nm}$), attributed to the efficient adsorption of gas-phase CH_3CHO by the carbon paper and the rapid and complete degradation of CH_3CHO to CO_2 by the active reduced TiO_{2-x} . This strongly suggests that the reduced TiO_{2-x} -loaded carbon paper is an efficient composite photocatalyst for the visible light-induced photocatalytic degradation of gas-phase CH_3CHO .

Received 29th September 2017
Accepted 21st October 2017

DOI: 10.1039/c7ra10778a

rsc.li/rsc-advances

1. Introduction

TiO_2 photocatalysis has been extensively studied in applications for air and water purification.^{1–5} Photocatalytic reactions are initiated by the absorption of ultraviolet (UV) photons, which concurrently generate conduction-band (CB) electrons and valence-band (VB) holes in the TiO_2 lattice. The VB holes are strong oxidants and react with surface $-\text{OH}$ groups to produce $\cdot\text{OH}$ radicals. The remediation power of TiO_2 photocatalysts is largely attributed to the strong oxidation potential of these $\cdot\text{OH}$ radicals. However, the wide band gap of TiO_2 limits the range of solar light wavelengths that can be utilized for catalysis. Several strategies have been investigated to enhance the solar light absorption of TiO_2 , including metal and non-metal doping,^{6–8} coupling of low-band gap materials,^{9,10} and dye sensitization.^{11,12}

Many researchers focus on the photooxidation of gas-phase acetaldehyde (CH_3CHO), a prevalent volatile organic

compound that causes sick-house syndrome.^{13–15} The complete degradation of gas-phase CH_3CHO to CO_2 can be achieved with TiO_2 or Au-loaded TiO_2 under UV irradiation.^{16,17} Recently, the visible light-induced photocatalytic removal of gas-phase CH_3CHO was also investigated using visible light-responsive modified photocatalysts including zeolite/ WO_3 -Pt hybrids,¹⁸ Mn^{4+} -doped TiO_2 ,¹⁹ and N-doped TiO_2 .²⁰

For air purification, photocatalysts immobilized on support materials are usually employed. The surface area and activity of the catalyst are often reduced by immobilization. Therefore, support materials with high surface areas are preferred for photocatalyst immobilization. The composite materials generated can show synergetic effects on adsorption and photocatalysis.²¹ Activated carbon is one such commonly used support material;^{22–24} it has a high surface area that can enhance adsorption and photocatalytic activity. Previously, we prepared TiO_2 -embedded carbon nanofibers (CNFs) and core-shell-structured CNF- TiO_2 nanotubes for the photocatalytic oxidation of gaseous CH_3CHO .^{25,26} CNF mats prepared by electrospinning and subsequent carbonization did not adsorb gas-phase CH_3CHO , but the convenient application of CNF mats suggests that mats with improved adsorption of gas-phase CH_3CHO could be widely used.

Recently, O-deficient black or reduced TiO_{2-x} samples have attracted great attention as new photocatalysts for light-induced water splitting towards H_2 production.²⁷ The reduction of TiO_2 generates many surface defects, Ti^{3+} species, and O vacancies,

^aSmart Textile Convergence Research Group, Daegu Gyeongbuk Institute of Science and Technology (DGIST), Daegu, 42988, Republic of Korea. E-mail: sh2358@dgist.ac.kr; Fax: +82-53-785-3439; Tel: +82-53-785-3410

^bDepartment Energy Science and Engineering, Daegu Gyeongbuk Institute of Science and Technology (DGIST), Daegu, 42988, Republic of Korea. E-mail: jsyu@dgist.ac.kr; Fax: +82-53-785-6409; Tel: +82-53-785-6443

† Electronic supplementary information (ESI) available: N_2 absorption-desorption isotherms and thermal decomposition curves of synthesized materials. See DOI: 10.1039/c7ra10778a

which contribute to improved light absorption.^{28,29} We also investigated a new approach for a defect-induced TiO_{2-x} solar photocatalyst for H_2 production from water and CO_2 reduction to fuel.^{30,31} However, the approach has not yet been applied to the degradation of environmental pollutants.

In this study, carbon paper was synthesized by the simple pyrolysis of a filter paper, and O-deficient reduced TiO_{2-x} was prepared by the magnesiothermic reduction of commercial anatase TiO_2 . Then, Pt-deposited reduced TiO_{2-x} (Pt/rT) nanoparticles were loaded on the as-prepared carbon papers. The physicochemical properties of the Pt@reduced TiO_{2-x} -loaded carbon paper (Pt/rT-FPC) were measured. The adsorption of gas-phase CH_3CHO by the filter paper carbon (FPC) or Pt/rT-FPC and the visible light-induced photocatalytic oxidation of adsorbed CH_3CHO over the Pt/rT-FPC were investigated.

2. Experimental details

2.1. Preparation of carbon paper from filter paper

Carbon paper was prepared from a filter paper (Hyundai Micro Co., Ltd.). The filter paper was carbonized at 400, 600, 800, or 1000 °C for 2 h under continuous-flow Ar gas. The temperature was increased at the rate of 5 °C min⁻¹. The prepared samples are hereinafter denoted as FPC-*x* where *x* indicates the carbonization temperature. For comparison, two different carbon materials of CNFs prepared by a previously reported method³² and commercial activated carbon (MSC, MSC-30, Kansai Coke and Chemicals Co., Ltd, Japan) were also used as substrates.

2.2. Synthesis of reduced TiO_{2-x} and preparation of reduced TiO_{2-x} -FPC

O-deficient reduced TiO_{2-x} was synthesized by a magnesiothermic reduction of commercial anatase TiO_2 as previously reported.^{30,31} A 4 g sample of commercial anatase TiO_2 (CT, particle size <25 nm, Sigma Aldrich) was mixed with the desired amount of Mg powder. The mixed powder was placed in a tube furnace and heated at 500 °C for 8 h under flowing 5% H_2/Ar . After annealing, the Mg-treated sample was stirred in 2.0 M HCl solution for 1 day and then washed with distilled water and ethanol to remove MgO and other Mg impurities. The washed Mg-free reduced TiO_{2-x} samples were dried at 80 °C. Different reduced samples prepared with 0.5 and 0.75 molar ratios of Mg per molar amount of CT are denoted as rT-0.5 and rT-0.75, respectively. For comparison, a commercial photocatalyst of P25 TiO_2 (P25, Aeroxide) was also used.

Pt/rT photocatalysts were synthesized through the well-documented photodeposition method.³³ The reduced TiO_{2-x} photocatalyst (0.5 g L⁻¹) was dispersed in 10 vol% methanol, and a proper amount of *x* mole chloroplatinic acid hexahydrate solution was added dropwise to this dispersion under vigorous stirring for 30 min. The Pt : photocatalyst weight ratio was 0.005 : 1. The suspension was illuminated with UV light (300 W Xe arc lamp, Newport) through a 10 cm infrared (IR) water filter and a UV cutoff filter ($\lambda > 295$ nm) for 30 min. The suspension was filtered using 0.45 μm polytetrafluoroethylene (PTFE) filters

(Millipore), washed with methanol solution, and dried at 80 °C in an oven to obtain Pt/rT. The photocatalyst was then loaded on the FPC. A 5 mL suspension of photocatalyst in distilled water was pipetted onto the center of each FPC specimen. After the dispersion of the suspension, the FPC was dried at 80 °C in an oven. The mass of the photocatalyst (Pt/rT-FPC or Pt/rT) in the sample holder was approximately 10 mg for each loading.

2.3. Characterizations

Surface morphology images were obtained using a field-emission scanning electron microscope (FE-SEM, Hitachi S4-8020, Japan). Transmission electron micrographs were obtained on a high-resolution transmission electron microscope (HR-TEM, Hitachi HF-3300, Japan). X-ray diffraction (XRD) patterns were obtained with an X-ray diffractometer (Panalytical, Empyrean, 40 kV, 30 mA) using Cu K α_1 radiation ($\lambda = 0.154178$ nm) and a quartz monochromator. Raman spectra of the samples were analyzed by a Raman spectrophotometer (Thermo Scientific, Nicolet Almega XR) in the wavenumber range of ~100 to 4000 cm⁻¹ using a 532 nm laser. The Brunauer–Emmett–Teller (BET) surface areas were determined from the N_2 adsorption–desorption isotherms obtained at 77 K (ASAP 2020 Micromeritics). The surface compositions were measured by X-ray photoelectron spectroscopy (XPS, Thermo Scientific, Escalab 250Xi) using the Mg-K α line (1253.6 eV) as the excitation source. The light absorption was analyzed by UV-visible diffuse reflectance spectroscopy (DRS) using a Cary series spectroscope (Cary 5000, Agilent Technologies).

2.4. Visible light-induced gas-phase CH_3CHO oxidation

Photocatalytic oxidation experiments were performed by two different methods of closed-circulation mode and continuous-flow mode. In closed-circulation mode, the photocatalytic oxidation of gaseous CH_3CHO was determined in a closed circulating stainless steel reactor with a volume of 150 cm³ that could be divided into two parts (upper and lower) by a control valve, similar to the reactor in a previously reported experiment.²⁵ The gases used were CH_3CHO (300 ppmv N_2) as a CH_3CHO standard, O_2 (99.9999%), and Ar (99.9999%) as the carrier gas. The concentrations of CH_3CHO and O_2 were 80 ppmv and 20%, respectively. A sample of reduced TiO_{2-x} -loaded FPC was placed in the lower reactor. Each sample weighed approximately 15 mg. The mixed gas passed through the empty upper reactor, and the concentration of CH_3CHO in the exit stream was monitored until it reached a constant value. The gas was then circulated in the reactor by the pump. Next, the circulated gas was passed through the lower reactor by using the valve to make contact with the surface of the sample in the lower reactor. After adsorption equilibrium with the surface of the sample was established in the dark, the sample was illuminated with UV light (150 W Xe arc lamp, Abet Technologies). The distance between the sample and the lamp was 15 cm, and a cut-off filter ($\lambda > 295$ nm for UV irradiation or $\lambda > 420$ nm for visible irradiation) was used. The removal of CH_3CHO was monitored using a gas chromatograph (GC, HP6890, Agilent) equipped with a Porapak Q column, a flame ionization detector



(FID), a CO₂ methanizer (Ni catalyst), and a gas-sampling valve. In the continuous-flow mode, the photocatalytic oxidation of gaseous CH₃CHO was performed in the same 150 cm³ stainless steel reactor without division. The mixed gas was fed to the reactor at the total flow rate of 100 mL min⁻¹. The concentrations of CH₃CHO and O₂ were 60 ppmv and 20%, respectively. The gas residence time in the reactor was 1.5 min. All other experimental conditions were the same as those in the closed-circulation experiments.

3. Results and discussion

3.1. Characterization of FPCs

Fig. 1 shows photographs and SEM images of the filter paper and the FPC-600. The filter paper is obviously transformed to carbon paper, as shown in Fig. 1a and c. The filter paper and the FPC-600 both contain fibers with some degree of variation in diameter. The diameters of the fibers are not strongly affected by the carbonization, but do show slight shrinkage.

Fig. 2a shows the XRD patterns of the filter paper, FPC-600, and FPC-800. The filter paper pattern exhibits two major peaks, a weak diffraction peak centered at 15.1° and a strong diffusion diffraction peak centered at 22.5°, which are consistent with previously reported results.³⁴ The FPC patterns each exhibit one broad peak centered at 23°, indicating amorphous carbon.²³ The intensities of the diffraction peaks are increased as the temperature of carbonization is increased. Fig. 2b shows the Raman spectra of the filter paper and the FPCs. The FPC spectra show two characteristic peaks centered at 1350 cm⁻¹ and 1580 cm⁻¹ corresponding to the D and G bands, respectively.³⁵ These characteristic peaks become sharper and more intense with increased carbonization temperature. The D and G bands are associated with the vibrations of sp² carbon atoms with dangling bonds; the integrated intensity ratio (I_D/I_G) corresponds to the degree of graphitization. The I_D/I_G ratios for

FPC-400, FPC-600, FPC-800, and FPC-1000 are 0.62, 0.65, 0.89, and 0.96, respectively. This implies increasing structural order in the FPC with increasing carbonization temperature, consistent with the results reported for other cellulose materials.³⁶ The XRD patterns and Raman spectra obviously demonstrate that graphitized carbon forms during carbonization, with increasing formation at higher carbonization temperatures.

The N₂ adsorption-desorption isotherms of the filter paper and FPCs are shown in Fig. S1.† The BET surface areas of the filter paper, FPC-400, FPC-600, FPC-800, and FPC-1000 were 4.31 m² g⁻¹, 13.57 m² g⁻¹, 466.81 m² g⁻¹, 461.60 m² g⁻¹, and 26.28 m² g⁻¹, respectively. The surface areas increase significantly for papers carbonized at temperatures of 400 and 800 °C, and then decrease with the increase of temperature from 800 to 1000 °C. The release of volatile compounds favors the formation of pores, which create the high surface areas of FPC-600 and FPC-800. At 1000 °C, structural ordering and merging of pores decreases the surface area of the FPC.

3.2. Gas-phase CH₃CHO adsorption on FPCs

The capability of FPCs to adsorb gaseous CH₃CHO was compared with those of commercially available activated carbon (MSC), CNF, and non-carbonized filter paper. Fig. 3a shows that the dark adsorption of gaseous CH₃CHO on filter paper and CNF does not occur at all, whereas MSC exhibits strong dark adsorption of CH₃CHO. However, FPC-800 shows better CH₃CHO adsorption than MSC does. The CH₃CHO adsorption may be influenced by the carbonization temperature. Therefore, the carbonization temperature-dependent adsorption of CH₃CHO is analyzed as shown in Fig. 3b. The FPCs, except FPC-1000, exhibit strong CH₃CHO adsorption. Fig. 3c shows the relationship between the amount of adsorbed CH₃CHO and the BET surface area. The dark adsorption capacity of CH₃CHO follows the order of FPC-600 > FPC-800 > FPC-400 ≫ MSC ≫ FPC-1000. Although the specific surface areas of FPCs are much lower than that of MSC, the adsorption capacities of FPCs, except that of FPC-1000, exceed that of MSC. The adsorption of CH₃CHO on the surfaces of the carbon materials depends on the surface chemistry as well as the microporosity.³⁷ The atomic ratio of O in the FPCs is higher than that in MSC (Fig. S3†). Therefore, enhanced adsorption of CH₃CHO appears in FPCs bearing O-containing functional groups. These results were obtained in the closed-circulation system. Similar tendencies were more clearly observed in the continuous-flow system during the photocatalytic oxidation experiments. Additionally, CH₃CHO showed no oxidation under UV irradiation on FPCs without photocatalyst.

3.3. Visible light-induced activity of reduced TiO_{2-x}

The visible light-induced photocatalytic oxidation of gas-phase CH₃CHO was further investigated using Pt/rT-FPC. Previously, reduced TiO_{2-x} exhibited high activity for the visible light-induced production of H₂ (ref. 30) and photocatalytic reduction of CO₂.³¹ In Fig. 4a, the reduced TiO_{2-x} samples clearly illustrate extended absorbance in the visible region as well as the UV region compared to that of commercial pristine TiO₂,

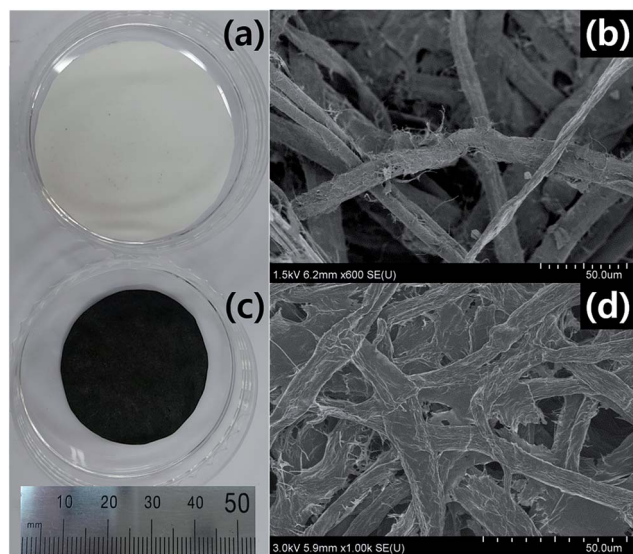


Fig. 1 Photographs and SEM images of (a, b) filter paper and (c, d) carbon paper after carbonization at 600 °C (FPC-600).



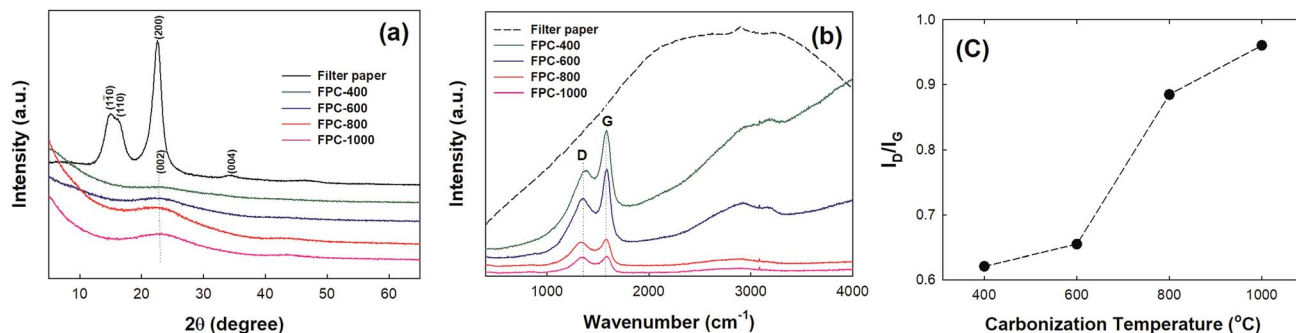


Fig. 2 (a) XRD patterns and (b) Raman spectra of filter paper and FPCs. (c) Ratio of intensity of D to G peaks in Raman spectra for carbon papers as a function of carbonization temperature.

which shows only UV-region absorption. Our previous work revealed that visible light absorption is related to the presence of Ti^{3+} .³¹ The absorption of light increases as the amount of Mg used in the reduction increases, as observed for rT-0.5 and rT-0.75; this is also reflected in the color change of the samples from white to yellow and gray for pristine TiO_2 , rT-0.5, and rT-0.75, respectively. The XRD patterns of the different samples are presented in Fig. 4b. Despite the color changes, the reduced samples still show predominantly anatase-phase TiO_2 . Although the XRD analysis indicates no major structural changes during Mg reduction, the Mg treatment probably

induces modifications on the surfaces of the reduced TiO_{2-x} particles, as reflected in the enhanced light absorption and color changes of the reduced samples. The magnesiothermic reduction of TiO_2 follows the reaction shown below. The strong reduction powder of Mg causes the pristine TiO_2 to lose the framework of O on the surface of the TiO_2 particles, generating reduced O-deficient TiO_{2-x} and MgO. The light absorption in the visible region is increased, and the color darkens because of the increased surface modification of the reduced samples with increased amounts of Mg. In the given reaction conditions, this modification occurs only on the surface of the reduced sample;

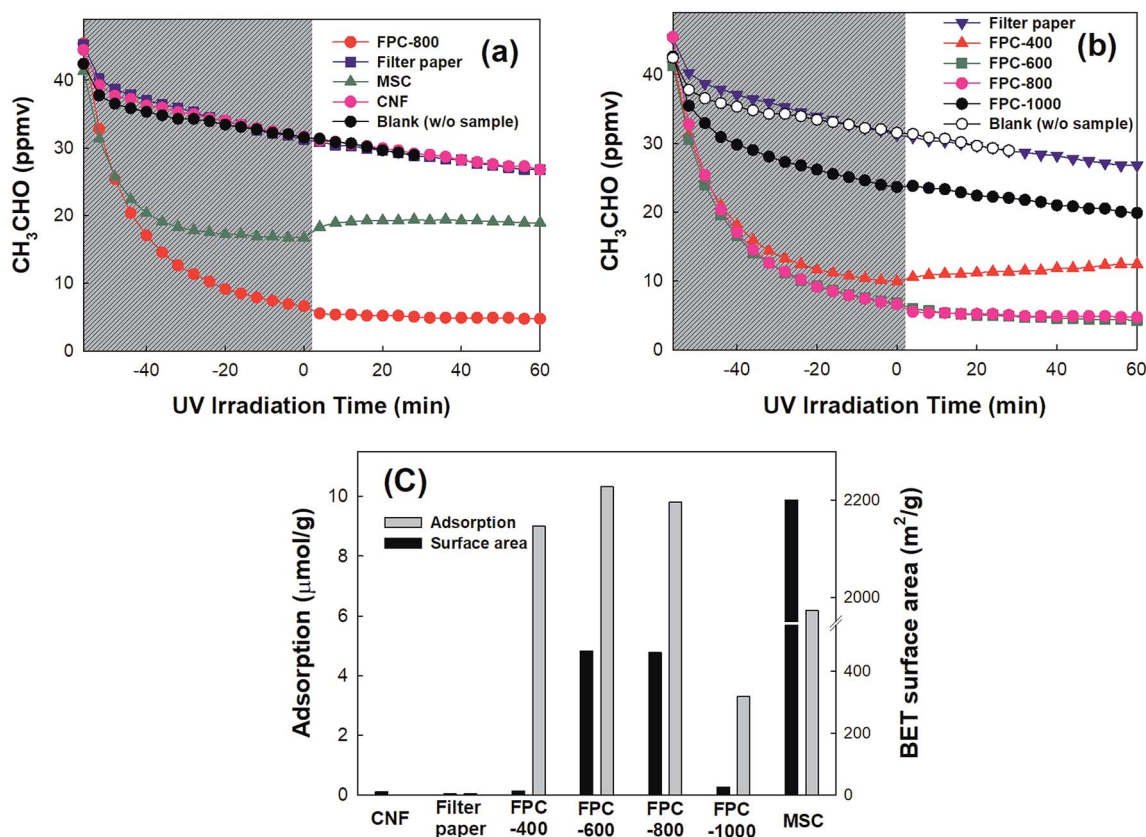


Fig. 3 (a, b) Time-profile CH_3CHO concentration on the FPC before and after UV irradiation in closed-circulation mode. (c) The relationship between the CH_3CHO adsorption capacity and BET surface area of the FPC.




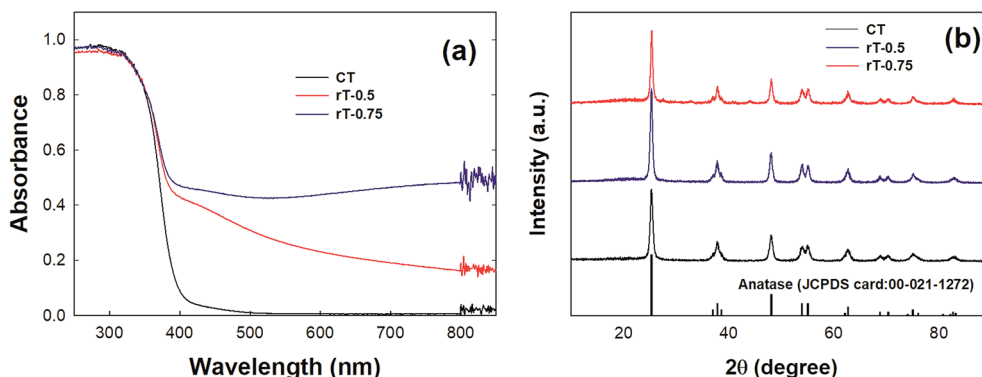


Fig. 4 (a) DRS absorbance and (b) XRD patterns of CT, rT-0.5, and rT-0.75.





thus, the inner part of the reduced sample has the anatase TiO_2 structure, as indicated by the XRD patterns in Fig. 4b.



The photocatalytic oxidation of CH_3CHO by reduced TiO_{2-x} under visible light was performed in continuous-flow mode. Fig. 5a shows the photocatalytic oxidation of CH_3CHO on reduced TiO_{2-x} and P25 TiO_2 . The dark adsorption capacities on the surfaces of the reduced TiO_{2-x} and P25 TiO_2 are much lower than those of reduced TiO_{2-x} immobilized on the FPCs. Under visible irradiation, the concentration of CH_3CHO is only

slightly reduced and CO_2 production is negligible. Under UV irradiation, however, the CH_3CHO is degraded and CO_2 immediately produced. The concentrations of CH_3CHO and CO_2 reach steady-state levels after several minutes, indicating that establishing adsorption-desorption equilibrium under UV illumination requires a long time. Meanwhile, the concentration of CO_2 on rT-0.75 is higher than that on either P25 or rT-0.5. This implies that the photocatalytic oxidation of CH_3CHO is faster on rT-0.75. The CH_3CHO degradation and the CO_2 production under UV irradiation remain almost identical throughout repeated cycling. However, although the reduced TiO_{2-x} absorbs visible light, the visible light-induced photocatalytic oxidation of CH_3CHO occurs on neither rT-0.5 nor rT-0.75. This can be attributed to the rapid recombination of the electron-hole pairs produced under visible irradiation. Therefore, Pt must be photodeposited onto the reduced TiO_{2-x} surface for the efficient separation of the photo-generated electron-hole pairs.

Fig. 6 shows HR-TEM images of Pt/P25, Pt/rT-0.5, and Pt/rT-0.75. In all cases, Pt is deposited similarly. The photocatalytic oxidation of CH_3CHO on Pt-deposited P25 and reduced TiO_{2-x} was also investigated. As shown in Fig. 5b, under visible irradiation, the CH_3CHO is degraded with simultaneous CO_2 production on Pt/rT-0.5. The concentrations of CH_3CHO and CO_2 do not reach a steady-state level because of the offsets of the adsorption and the photocatalytic oxidation of CH_3CHO . This implies that Pt deposition inhibits the recombination of charge carriers created by absorbing visible light and thereby enables visible light-induced CH_3CHO degradation. The photocatalytic reaction of CH_3CHO oxidation into CO_2 can be written as follows:



On Pt/rT-0.75, the CH_3CHO is degraded but no CO_2 is observed, which could be attributed to the production of some undetected intermediates by the visible light-induced

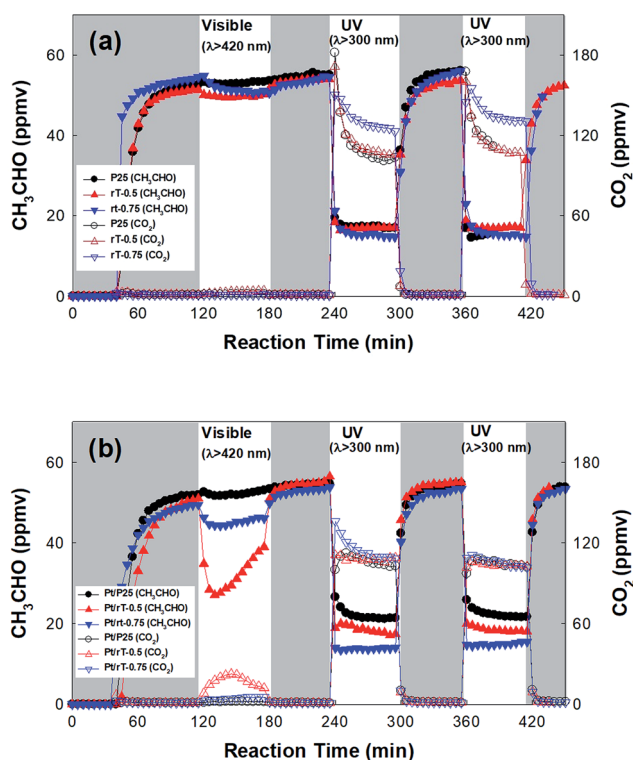


Fig. 5 Dark adsorption and photocatalytic oxidation of CH_3CHO under visible and UV irradiation on (a) bare photocatalyst and (b) Pt-deposited photocatalyst in continuous-flow mode.



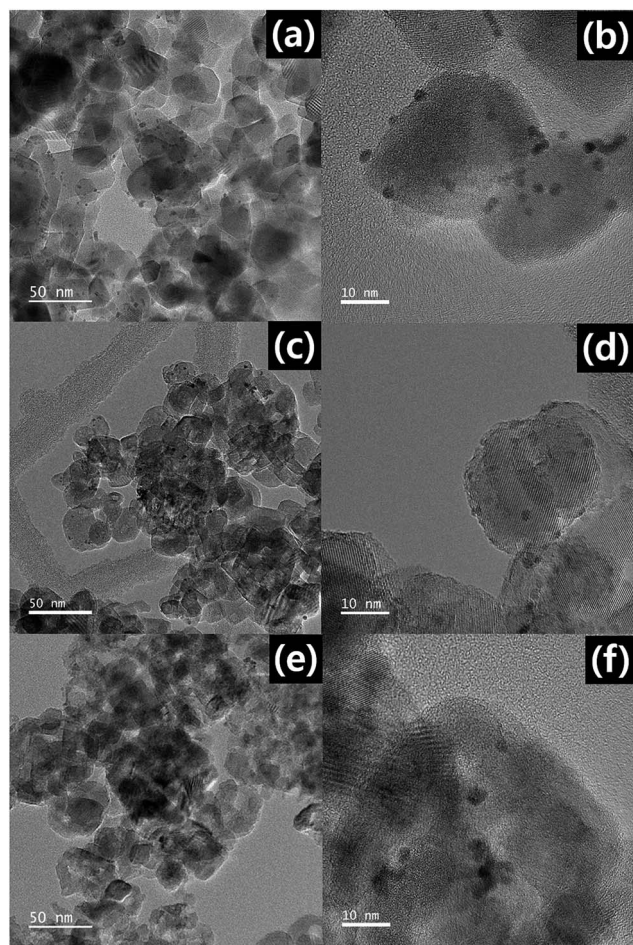


Fig. 6 High-resolution TEM images of (a, b) Pt/P25, (c, d) Pt/rT-0.5, and (e, f) Pt/rT-0.75.

degradation of CH_3CHO . Meanwhile on Pt/P25, CH_3CHO is not degraded under visible irradiation. The photocatalytic degradation rates of CH_3CHO on Pt/P25, Pt/rT-0.5, and Pt/rT-0.75 under UV irradiation are much higher than those under visible irradiation. Compared to the results obtained in the absence of Pt, the photocatalytic activities for CH_3CHO degradation under UV irradiation are not significantly enhanced. This implies that UV light-induced charge separation occurs efficiently on P25, rT-0.5, and rT-0.75, so the effect of Pt

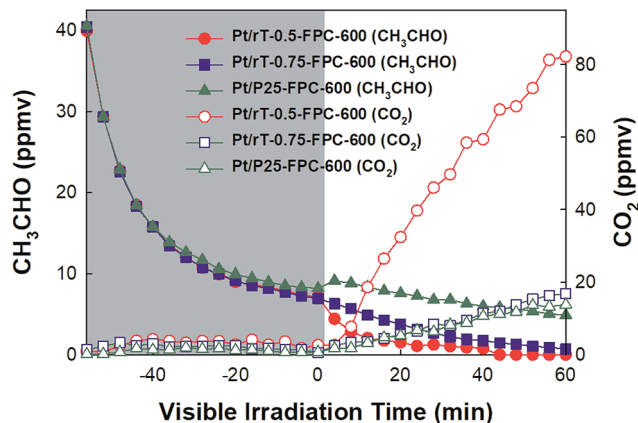


Fig. 8 Dark adsorption and photocatalytic oxidation of CH_3CHO on the Pt/P25-FPC-600, Pt/rT-0.5-FPC-600, and Pt/rT-0.75-FPC-600 under visible irradiation in closed-circulation mode.

deposition is not significant. Moreover, the CH_3CHO degradation and the CO_2 production under UV irradiation remain almost identical throughout repeated cycling, as with the results obtained in the absence of Pt.

3.4. Visible light-induced gas-phase CH_3CHO oxidation

The visible light-induced photocatalytic oxidation of gas-phase CH_3CHO using reduced TiO_{2-x} -loaded FPC was investigated. Based on the above results, we investigated visible light-induced gas-phase CH_3CHO oxidation using the Pt-deposited photocatalysts and FPC-600. We observed cross-sectional SEM images and analyzed the elemental composition of the Pt/rT-0.5 loaded on the FPC-600 by energy-dispersive X-ray spectroscopy (EDS) mapping, as shown in Fig. 7a and 8b. The Pt/rT-0.5 is well loaded and easily distinguishable on the FPC-600. The amount of Pt/rT-0.5 nanoparticles on the surface of the FPC-600 is indirectly calculated from the thermogravimetric analysis (TGA) results (Fig. S2†). Fig. S2a† shows that the decomposition of Pt/rT-0.5 loaded on FPC-600 begins at approximately 400 °C and stops at 500 °C. The weight loss of Pt/rT-0.5 loaded on the FPC-600 is approximately 47%.

Fig. 8 shows the photocatalytic oxidation of CH_3CHO on Pt/rT-0.5, Pt/rT-0.75, and Pt/P25 loaded on FPC-600 in closed-circulation mode. All cases show strong dark adsorption of

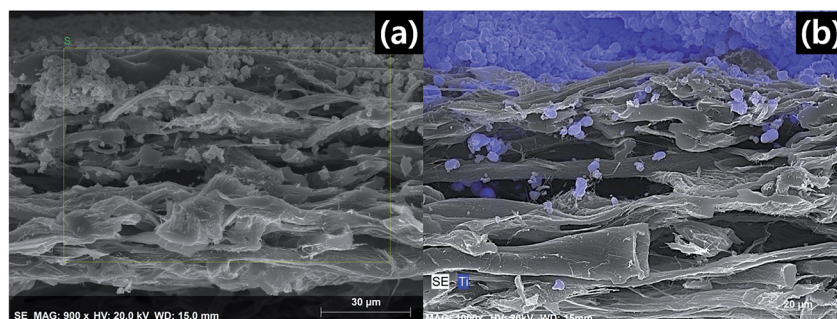


Fig. 7 Cross-sectional SEM images of Pt/rT-0.5 loaded on FPC-600.



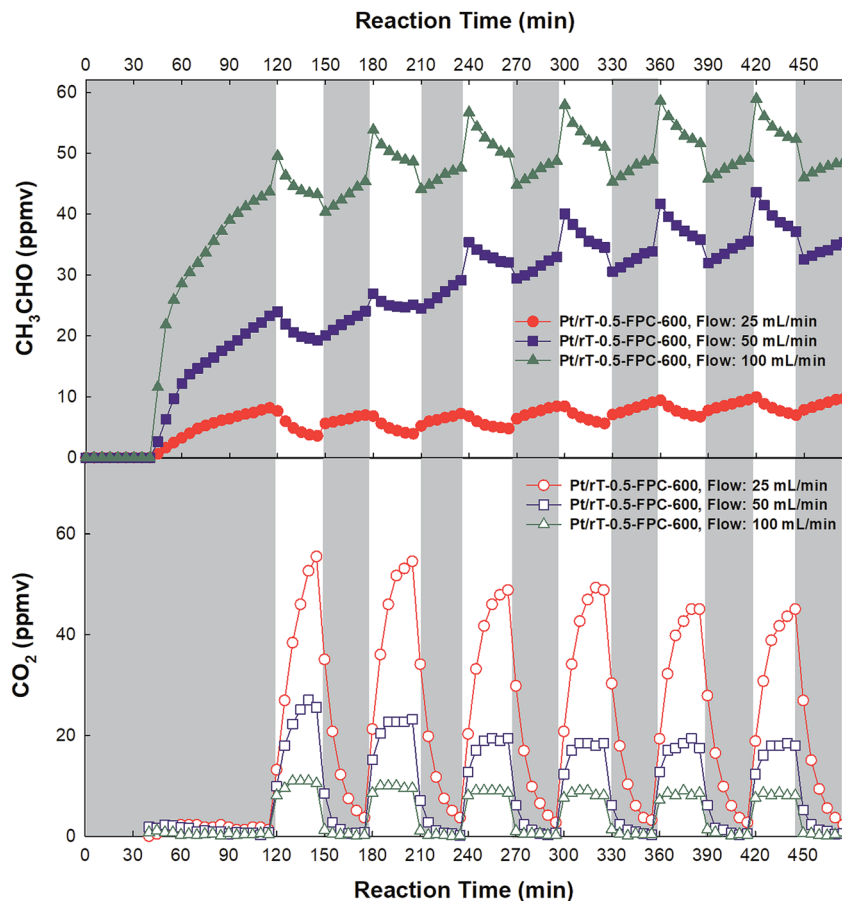


Fig. 9 Dark adsorption and photocatalytic oxidation of CH_3CHO on the Pt/rT-0.5-FPC-600 under visible irradiation in continuous-flow mode.

CH_3CHO , similar to the dark adsorption of CH_3CHO on the FPC without Pt/rT-0.5, Pt/rT-0.75, or Pt/P25. Upon visible irradiation, the Pt/rT-0.5 loaded on the FPC-600 shows rapid degradation of CH_3CHO and simultaneous generation of CO_2 . The photocatalytic oxidation of CH_3CHO on Pt/rT-0.5-FPC-600 is also performed in continuous-flow mode under repeated experiments, as shown in Fig. 9. The photocatalytic oxidation of CH_3CHO to CO_2 is strongly dependent on the flow rates of 25, 50, and 100 mL min^{-1} , which relate directly to the residence times of 6, 3, and 1.5 min, respectively. For all cases, the concentration of CH_3CHO does not reach steady-state levels within 30 min. At the highest flow rate, CO_2 production is rapidly saturated and its concentration remains constant under repeated experiments. However, at the lowest flow rate, the concentration of CO_2 does not reach a steady-state level but CO_2 production from the photocatalytic oxidation of CH_3CHO is dramatic, possibly because of the longer residence time. The photocatalytic oxidation of CH_3CHO to CO_2 was repeated up to six times. The result demonstrates the good stability of Pt/rT-0.5-FPC-600. Investigations to improve the operation conditions are needed for photocatalytic oxidation applications. Even with a small amount of Pt/rT-0.5, the photocatalytic oxidation of CH_3CHO under visible irradiation occurs in a few minutes. The FPC-600 efficiently adsorbs the CH_3CHO , and Pt/rT-0.5 rapidly and completely degrades the CH_3CHO to CO_2 , even under visible irradiation. It is also possible that some

electrons are transferred to the carbon paper, which would promote electron-hole pair separation; this implies that the carbon paper could function as an electron-transfer mediator as well as a support material.^{32,38} A schematic of the visible light-induced photocatalytic degradation of gas-phase CH_3CHO using reduced TiO_{2-x} -loaded FPC is shown in Fig. 10.

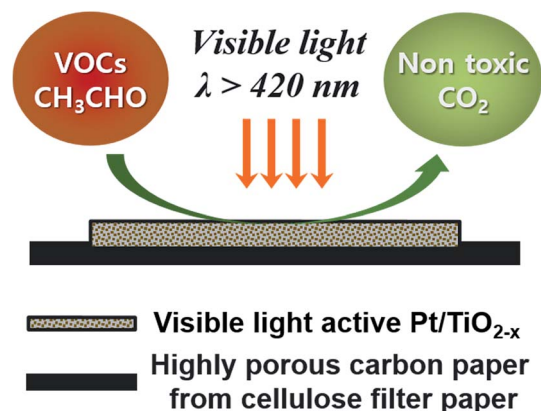


Fig. 10 Schematic of the visible light-induced photocatalytic degradation of gas-phase CH_3CHO using reduced TiO_{2-x} -loaded carbon paper.



4. Conclusion

In this work, visible light-induced gas-phase CH_3CHO degradation on Pt/reduced TiO_{2-x} -loaded FPC was examined for the first time. The FPC was synthesized by the simple pyrolysis of filter paper; its surface area was strongly affected by the carbonization temperature. Although the specific surface areas of the FPCs were much lower than that of commercial MSC, the adsorption rate and capacities of FPCs outperformed those of MSC. The O-deficient reduced TiO_{2-x} prepared by the Mg-H_2 reduction of commercial anatase TiO_2 showed increased visible light absorption; it was successfully utilized as the active material for visible light-induced photocatalysis. The reduced TiO_2 -loaded FPC showed rapid degradation of CH_3CHO and simultaneous generation of CO_2 in both closed-circulation and continuous-flow modes under visible irradiation, clearly demonstrating that the reduced TiO_{2-x} -loaded FPC described in this work is a suitable candidate for the visible light-induced photocatalytic degradation of gas-phase CH_3CHO .

Conflicts of interest

There are no conflicts of interest to declare.

Acknowledgements

This work was supported by the DGIST R&D Program of the Ministry of Science, ICT & Future Planning (17-NT-02 and 17-01-HRLA-01). This work was also supported by Basic Science Research Program, through the National Research Foundation of Korea (NRF), funded by the Ministry of Science, ICT & Future Planning (2017R1A2B4003919).

References

- M. R. Hoffmann, S. T. Martin, W. Choi and D. W. Bahnemann, *Chem. Rev.*, 1995, **95**, 69–96.
- W. Choi, J. Y. Ko, H. Park and J. S. Chung, *Appl. Catal., B*, 2001, **31**, 209–220.
- S. Kim and W. Choi, *Environ. Sci. Technol.*, 2002, **36**, 2019–2025.
- J. S. Park and W. Choi, *Chem. Lett.*, 2005, **34**, 1630–1631.
- J. Ryu and W. Choi, *Environ. Sci. Technol.*, 2008, **42**, 294–300.
- S. Kim, S.-J. Hwang and W. Choi, *J. Phys. Chem. B*, 2005, **109**, 24260–24267.
- J. W. Zheng, A. Bhattacharyya, P. Wu, Z. Chen, J. Highfield, Z. Dong and R. Xu, *J. Phys. Chem. C*, 2010, **114**, 7063–7069.
- S. Na Phattalung, S. Limpijumnong and J. Yu, *Appl. Catal., B*, 2017, **200**, 1–9.
- M. Kim, Y. K. Kim, S. K. Lim, S. Kim and S.-I. In, *Appl. Catal., B*, 2015, **166**, 423–431.
- H. Li, Z. Xia, J. Chen, L. Lei and J. Xing, *Appl. Catal., B*, 2015, **168**, 105–113.
- S. K. Choi, S. Kim, J. Ryu, S. K. Lim and H. Park, *Photochem. Photobiol. Sci.*, 2012, **11**, 1437–1444.
- P. Chowdhury, H. Goma and A. K. Ray, *Chemosphere*, 2015, **121**, 54–61.
- A. T. Hodgson, D. Beal and J. E. R. McIlvaine, *Indoor Air*, 2002, **12**, 235–242.
- Y. Odaka, H. Seto, H. Nakaoka, M. Hanazato, E. Todaka and C. Mori, *Indoor Built Environ.*, 2014, **25**, 254–261.
- I. Sopyan, M. Watanabe, S. Murasawa, K. Hashimoto and A. Fujishima, *J. Photochem. Photobiol., A*, 1996, **98**, 79–86.
- S. W. Verbruggen, K. Masschaele, E. Moortgat, T. E. Korany, B. Hauchecorne, J. A. Martens and S. Lenaerts, *Catal. Sci. Technol.*, 2012, **2**, 2311–2318.
- T. Nikawa, S.-i. Naya and H. Tada, *J. Colloid Interface Sci.*, 2015, **456**, 161–165.
- I. Jansson, K. Yoshiiri, H. Hori, F. J. García-García, S. Rojas, B. Sánchez, B. Ohtani and S. Suárez, *Appl. Catal., A*, 2016, **521**, 208–219.
- M.-V. Sofianou, M. Tassi, V. Psycharis, N. Boukos, S. Thanos, T. Vaimakis, J. Yu and C. Trapalis, *Appl. Catal., B*, 2015, **162**, 27–33.
- D. Meroni, S. Ardizzone, G. Cappelletti, C. Oliva, M. Ceotto, D. Poelman and H. Poelman, *Catal. Today*, 2011, **161**, 169–174.
- S. Wang, X. Zhang, L. Pan, F.-M. Zhao, J.-J. Zou, T. Zhang and L. Wang, *Appl. Catal., B*, 2015, **164**, 234–240.
- Y. El-Sayed and T. J. Bandosz, *Langmuir*, 2002, **18**, 3213–3218.
- W. Wei, C. Yu, Q. Zhao, X. Qian, G. Li and Y. Wan, *Appl. Catal., B*, 2014, **146**, 151–161.
- E. D. Dimotakis, M. P. Cal, J. Economy, M. J. Rood and S. M. Larson, *Environ. Sci. Technol.*, 1995, **29**, 1876–1880.
- S. Kim and S. K. Lim, *Appl. Catal., B*, 2008, **84**, 16–20.
- S. Kim, M. Kim, Y. K. Kim, S. H. Hwang and S. K. Lim, *Appl. Catal., B*, 2014, **148**, 170–176.
- X. Chen, L. Liu, P. Y. Yu and S. S. Mao, *Science*, 2011, **331**, 746–750.
- S. Hoang, S. P. Berglund, N. T. Hahn, A. J. Bard and C. B. Mullins, *J. Am. Chem. Soc.*, 2012, **134**, 3659–3662.
- S. Wang, L. Pan, J.-J. Song, W. Mi, J.-J. Zou, L. Wang and X. Zhang, *J. Am. Chem. Soc.*, 2015, **137**, 2975–2983.
- A. Sinhamahapatra, J.-P. Jeon and J.-S. Yu, *Energy Environ. Sci.*, 2015, **8**, 3539–3544.
- A. Razzaq, A. Sinhamahapatra, T.-H. Kang, C. A. Grimes, J.-S. Yu and S.-I. In, *Appl. Catal., B*, 2017, **215**, 28–35.
- Y. K. Kim, S. K. Lim, H. Park, M. R. Hoffmann and S. Kim, *Appl. Catal., B*, 2016, **196**, 216–222.
- S. K. Choi, S. Kim, S. K. Lim and H. Park, *J. Phys. Chem. C*, 2010, **114**, 16475–16480.
- K. Zhang, Q. Li, L. Zhang, J. Fang, J. Li, F. Qin, Z. Zhang and Y. Lai, *Mater. Lett.*, 2014, **121**, 198–201.
- Y. W. Zhu, S. Murali, W. W. Cai, X. S. Li, J. W. Suk, J. R. Potts and R. S. Ruoff, *Adv. Mater.*, 2010, **22**, 3907–3924.
- A. E. Lewandowska, C. Soutis, L. Savage and S. J. Eichhorn, *Compos. Sci. Technol.*, 2015, **116**, 50–57.
- Y. El-Sayed and T. J. Bandosz, *J. Colloid Interface Sci.*, 2001, **242**, 44–51.
- Y. K. Kim, M. Kim, S. H. Hwang, S. K. Lim, H. Park and S. Kim, *Int. J. Hydrogen Energy*, 2015, **40**, 136–145.

