

CrossMark  
click for updatesCite this: *Chem. Sci.*, 2017, 8, 2426

# Pairwise hydrogen addition in the selective semihydrogenation of alkynes on silica-supported Cu catalysts†

Oleg G. Salnikov,<sup>ab</sup> Hsueh-Ju Liu,<sup>c</sup> Alexey Fedorov,<sup>c</sup> Dudari B. Burueva,<sup>ab</sup>  
Kirill V. Kovtunov,<sup>\*ab</sup> Christophe Copéret<sup>c</sup> and Igor V. Koptug<sup>ab</sup>

Mechanistic insight into the semihydrogenation of 1-butyne and 2-butyne on Cu nanoparticles supported on partially dehydroxylated silica (Cu/SiO<sub>2-700</sub>) was obtained using parahydrogen. Hydrogenation of 1-butyne over Cu/SiO<sub>2-700</sub> yielded 1-butene with ≥97% selectivity. The surface modification of this catalyst with tricyclohexylphosphine (PCy<sub>3</sub>) increased the selectivity to 1-butene up to nearly 100%, although at the expense of reduced catalytic activity. Similar trends were observed in the hydrogenation of 2-butyne, where Cu/SiO<sub>2-700</sub> provided a selectivity to 2-butene in the range of 72–100% depending on the reaction conditions, while the catalyst modified with PCy<sub>3</sub> again demonstrated nearly 100% selectivity. Parahydrogen-induced polarization effects observed in hydrogenation reactions catalyzed by copper-based catalysts demonstrate the viability of pairwise hydrogen addition over these catalysts. Contribution of pairwise hydrogen addition to 1-butyne was estimated to be at least 0.2–0.6% for unmodified Cu/SiO<sub>2-700</sub> and ≥2.7% for Cu/SiO<sub>2-700</sub> modified with PCy<sub>3</sub>, highlighting the effect of surface modification with the tricyclohexylphosphine ligand.

Received 1st December 2016  
Accepted 18th December 2016

DOI: 10.1039/c6sc05276b

www.rsc.org/chemicalscience

## Introduction

Semihydrogenation of alkynes is a process used industrially to remove acetylene from ethylene streams and thus avoid poisoning downstream ethylene polymerization catalysts.<sup>1</sup> It is also an important reaction in organic chemistry applied for the stereoselective synthesis of *Z*-olefins.<sup>2</sup> Expensive Pd catalysts are currently used for alkyne semihydrogenation, both in industry and in academia (*e.g.*, the Lindlar catalyst).<sup>3</sup> Research efforts to reduce the required amounts of Pd semihydrogenation catalysts or even totally replace them with cheaper and more sustainable metals identified Cu-based catalysts as a viable alternative.<sup>4–8</sup> However, further improvement of activity and especially chemo- and stereoselectivity is necessary before Cu can replace the established Pd systems. It has been recently demonstrated by some of us that combining small silica-supported Cu nanoparticles and a phosphorus-based ligand allows one to achieve this goal.<sup>9</sup> However, a more detailed understanding of the reaction mechanism and the role of the phosphine ligand is

critically needed to aid the rational development of improved catalysts.

That said, addressing the molecular mechanisms in heterogeneous catalysis is inherently difficult because of the low abundance of catalytically relevant sites and low sensitivity of many conventional spectroscopic techniques, especially when applied to surfaces.<sup>10</sup> The latter is a long-standing problem in nuclear magnetic resonance (NMR) and magnetic resonance imaging (MRI).<sup>11</sup> One strategy to increase the sensitivity utilizes hyperpolarization of nuclear spins, which creates nuclear spin polarization beyond the thermal equilibrium.<sup>12</sup> Dynamic nuclear polarization (DNP) is a technique that exploits the transfer of polarization from electrons to nuclei.<sup>13,14</sup> DNP was successfully applied to study surfaces of solid materials,<sup>10,15,16</sup> including catalysts.<sup>17,18</sup> Another hyperpolarization technique is parahydrogen-induced polarization (PHIP), which creates non-equilibrium magnetization using a high spin order of parahydrogen (p-H<sub>2</sub>).<sup>19–21</sup> Parahydrogen itself cannot be detected by NMR because of its zero nuclear spin. However if p-H<sub>2</sub>-derived hydrogen atoms are added to an unsaturated asymmetric substrate as a pair, the corresponding NMR signals of the reaction product are enhanced because the parahydrogen-derived protons retain their spin correlation. This effect was demonstrated with homogeneous<sup>19,22</sup> and heterogeneous<sup>23–27</sup> hydrogenation catalysts, the latter of which were utilized both in the liquid<sup>25–27</sup> and in the gas<sup>23,24</sup> phases. Applied to heterogeneous catalysis, PHIP provides very valuable mechanistic<sup>28–32</sup>

<sup>a</sup>International Tomography Center, SB RAS, 3A Institutskaya St., 630090 Novosibirsk, Russia. E-mail: kovtunov@tomo.nsc.ru

<sup>b</sup>Novosibirsk State University, 2 Pirogova St., 630090 Novosibirsk, Russia

<sup>c</sup>Department of Chemistry and Applied Biosciences, ETH Zürich, Vladimir-Prelog-Weg 1-5, CH-8093 Zürich, Switzerland

† Electronic supplementary information (ESI) available: Additional NMR spectra and data on conversion, NMR signal enhancements and percentages of pairwise hydrogen addition. See DOI: 10.1039/c6sc05276b

and kinetic<sup>33</sup> insights and can be used for MRI visualization of operating catalytic reactors.<sup>34,35</sup>

Here, we use PHIP to obtain mechanistic insight into selective semihydrogenation of alkynes on promising Cu catalysts, in particular to probe whether or not the pairwise hydrogen addition route operates on these systems and how the phosphine ligand might be involved in modifying the reaction pathway and thereby the selectivity of silica-supported Cu nanoparticles.

## Experimental

Cu/SiO<sub>2-700</sub> and Cy<sub>3</sub>P-Cu/SiO<sub>2-700</sub> catalysts were prepared using the surface organometallic chemistry approach<sup>36</sup> grafting [Cu<sub>5</sub>Mes<sub>5</sub>] (Mes = mesityl) onto silica partially dehydroxylated at 700 °C (SiO<sub>2-700</sub>), followed by reduction in H<sub>2</sub> flow at 300 °C to give Cu/SiO<sub>2-700</sub>. Subsequent impregnation of this material with tricyclohexylphosphine yields the Cy<sub>3</sub>P-Cu/SiO<sub>2-700</sub> catalyst, as reported in detail elsewhere.<sup>9</sup>

Commercially available 1-butene, 1-butyne (Sigma-Aldrich, ≥99%), 2-butyne (Sigma-Aldrich, 99%) and hydrogen were used as received. For the PHIP experiments, hydrogen gas was enriched with parahydrogen to 50% by passing it through a layer of FeO(OH) maintained at liquid nitrogen temperature (77 K). The 1 : 4 mixtures of 1-butene/p-H<sub>2</sub> and 1-butyne/p-H<sub>2</sub> or a 1 : 11 : 5 mixture of 2-butyne/p-H<sub>2</sub>/He were used in the hydrogenation experiments.

Catalysts (20–105 mg) were loaded in the 1/4" outer diameter (OD) stainless steel reactor between two pieces of fiberglass tissue in an argon-filled glove box. The reactor was then sealed with two Swagelok valves inside the glove box. All lines between the tank with the gas mixture and the reactor were preliminarily evacuated. The reactor was heated in a tubular furnace; the temperature was varied from 150 to 550 °C. The reaction gas mixture was supplied to the reactor and then to the NMR tube placed inside an NMR spectrometer through a 1/16" OD PTFE capillary. All hydrogenation reactions were carried out at atmospheric pressure. The gas flow rate was controlled using an Aalborg rotameter. <sup>1</sup>H NMR spectra of the reaction mixtures in the gas phase were acquired using a 300 MHz Bruker AV 300 NMR spectrometer using a single  $\pi/2$  radiofrequency pulse.

## Results and discussion

The Cu/SiO<sub>2-700</sub> catalyst was prepared using the surface organometallic chemistry approach<sup>36</sup> by grafting [Cu<sub>5</sub>Mes<sub>5</sub>] onto SiO<sub>2-700</sub>, followed by reduction in H<sub>2</sub> flow at 300 °C.<sup>9</sup> This synthetic protocol provided silica-supported Cu(0) nanoparticles with an average size in the range 1.9 ± 0.3 nm, as determined by high-angle annular dark field scanning transmission microscopy after the sample was slowly exposed to air.<sup>9</sup> Treatment of Cu/SiO<sub>2-700</sub> with PCy<sub>3</sub> afforded a surface-modified catalyst (Cy<sub>3</sub>P-Cu/SiO<sub>2-700</sub>) with enhanced selectivity in alkyne batch semihydrogenation.<sup>9</sup> Both catalysts were then used in the PHIP experiments with 1-butyne, 1-butene or 2-butyne.

The Cu/SiO<sub>2-700</sub> catalyst showed modest to fair activity in 1-butyne hydrogenation at 350–550 °C, with overall conversions

in the 37–81% range, depending on the gas flow rate and temperature (see Table 1), with no significant activity below 300 °C. High selectivity toward 1-butene (≥97%) was always observed (Table 1). Even though hydrogen adsorption on the Cu surface is dissociative,<sup>37,38</sup> PHIP effects were detected in <sup>1</sup>H NMR spectra not only for vinylic protons of 1-butene but also for protons of its ethyl moiety as a result of spontaneous transfer of polarization in the Earth's magnetic field (Fig. 1b and c).<sup>39</sup> The observed signal enhancements (SE) at 7.1 T magnetic field were 25–90 for the CH and 13–60 for the CH<sub>2</sub> groups of 1-butene, corresponding to 0.2–0.6% and 0.1–0.4% lower boundary estimates for the percentages of pairwise hydrogen addition ( $\phi_p$ ). These values are typical for supported metal catalysts,<sup>24</sup> and it should be emphasized that the actual contribution of pairwise hydrogen addition is likely higher due to the partial loss of polarization associated with relaxation effects and incomplete adiabaticity of gas transfer into a 7.1 T field.<sup>40</sup> The difference in the estimated percentages of pairwise addition between CH and CH<sub>2</sub> groups is explained by the different nuclear spin relaxation rates of these protons.

To assess the stability of the catalyst's performance, it was cooled down to room temperature under H<sub>2</sub> atmosphere and tested in the hydrogenation of 1-butyne at 350 °C *ca.* 4.5 hours later. The activity of the catalyst decreased dramatically (1-butyne conversion decreased from 81 to 13%), however, a 4–5 fold increase in the SE and  $\phi_p$  values was observed (Table S1†), indicating that the catalyst became less active but more selective in terms of pairwise hydrogen addition.

Next, the more selective catalyst,<sup>9</sup> Cy<sub>3</sub>P-Cu/SiO<sub>2-700</sub>, was tested in the hydrogenation of 1-butyne with parahydrogen (Fig. 1d and e). Similar to Cu/SiO<sub>2-700</sub>, it showed hydrogenation activity only above 250 °C (Table S2†). Cy<sub>3</sub>P-Cu/SiO<sub>2-700</sub> was significantly less active than Cu/SiO<sub>2-700</sub> with conversion below 10%. However, it provided higher PHIP enhancements of the 1-butene NMR signals (*ca.* 3–6 fold compared to Cu/SiO<sub>2-700</sub>), and therefore is more prone to pairwise hydrogen addition, assuming that the presence of the ligand does not change the spin relaxation rates significantly. The maximum signal enhancement values were no less than 370 and the maximum contributions of pairwise hydrogen addition were no less than 2.7%, as observed at 350 °C and a 6.5 mL s<sup>-1</sup> gas flow rate (Fig. S3, Table S2†). Note that as the signals of thermally polarized 1-butene were below the noise level, the SE and  $\phi_p$  values were estimated using the signal-to-noise ratio as a reference. As was already mentioned above, losses of polarization due to relaxation and incomplete adiabaticity were not taken into account and therefore the actual SE and  $\phi_p$  values can be significantly higher.

In order to gain further insight into the mechanism of the hydrogenation of 1-butyne on these Cu-based catalysts, hydrogenation of 1-butene with parahydrogen was also carried out. The unmodified Cu/SiO<sub>2-700</sub> catalyst initially showed substantial activity in both the isomerization of 1-butene to 2-butene and hydrogenation to butane even at 150 °C (Table S4†). However, in a short time (~2–4 min) its activity decreased dramatically (Table S4†). In contrast, the catalyst performance was stable at higher temperatures (250–450 °C). As can be seen from



**Table 1** Hydrogenation of 1-butyne with parahydrogen over the Cu/SiO<sub>2-700</sub> catalyst: 1-butyne conversion (X), selectivities to different reaction products (S), signal enhancements (SE) calculated for vinyl CH and CH<sub>2</sub> protons of 1-butene, and lower estimates of percentages of pairwise hydrogen addition calculated using SE values

Temperature, °C	Flow rate, mL s <sup>-1</sup>	X, %	S <sub>1-butene</sub> , %	S <sub>2-butene</sub> , %	S <sub>butane</sub> , %	SE (CH)	SE (CH <sub>2</sub> )	φ <sub>p</sub> (CH) <sup>a</sup>	φ <sub>p</sub> (CH <sub>2</sub> ) <sup>a</sup>
350	3.8	81	98.5	1.1	0.4	25	13	0.18	0.09
350	5.1	70	98	1.5	0.6	35	29	0.25	0.21
350	6.5	37	100	0	0	88	59	0.63	0.43
450	3.8	71	99	0.8	0.1	42	42	0.31	0.31
450	5.1	62	99	0.6	0.3	67	41	0.48	0.30
450	6.5	55	97	2.0	0.9	79	49	0.57	0.35


<sup>a</sup> The losses of polarization caused by relaxation on the way from the reactor to the NMR instrument and the incomplete adiabaticity of this transfer were not taken into account. The difference in the percentages of pairwise addition between the CH and CH<sub>2</sub> groups is explained by different relaxation rates of these protons.

Table S4,<sup>†</sup> the catalyst was more active in isomerization than in hydrogenation. This activity in the hydrogenation of alkenes to alkanes agrees well with the behavior usually observed in the batch hydrogenation of alkynes, where olefins (primary products) get consumed as soon as there is no more alkyne in the reaction mixture.<sup>9,41</sup> It is worth noting that no PHIP effects were observed in the hydrogenation of 1-butene on Cu/SiO<sub>2-700</sub> (Fig. S5<sup>†</sup>). This observation is in a sharp contrast with the semihydrogenation of 1-butyne under similar reaction conditions and signifies that mechanistic pathways for the hydrogenation of alkynes and alkenes on supported Cu nanoparticles are different.

Similarly, Cy<sub>3</sub>P-Cu/SiO<sub>2-700</sub> was tested in the hydrogenation of 1-butene. The catalyst did not show any considerable activity in the isomerization or hydrogenation of 1-butene in the 150–550 °C temperature range. This result demonstrates that modification of Cu/SiO<sub>2-700</sub> with PCy<sub>3</sub> indeed makes it a very

selective catalyst toward hydrogenation of C≡C triple bonds, consistent with the high selectivity to olefins featured by Cy<sub>3</sub>P-Cu/SiO<sub>2-700</sub> in the liquid phase batch alkyne semihydrogenation.<sup>9</sup> Note, however, that Cy<sub>3</sub>P-Cu/SiO<sub>2-700</sub> shows slightly higher activity than Cu/SiO<sub>2-700</sub> in the semihydrogenation of 1-phenyl-1-propyne at 40 °C in toluene solution,<sup>9</sup> in contrast with the substantially higher activity of Cu/SiO<sub>2-700</sub> under the flow conditions utilized in this study. This difference is possibly due to the very different reaction conditions (gas vs. liquid phase and temperatures).

Since hydrogenation of terminal and internal alkynes can proceed *via* different mechanisms, Cu/SiO<sub>2-700</sub> was tested in the hydrogenation of 2-butyne with p-H<sub>2</sub>. Significant activity in the formation of 2-butene and butane was observed starting at 250 °C (see Table S6<sup>†</sup> for conversions). The catalyst was selective toward 2-butene, but also produced some amounts of butane at 250 and 350 °C. No PHIP effects were observed in 2-butyne

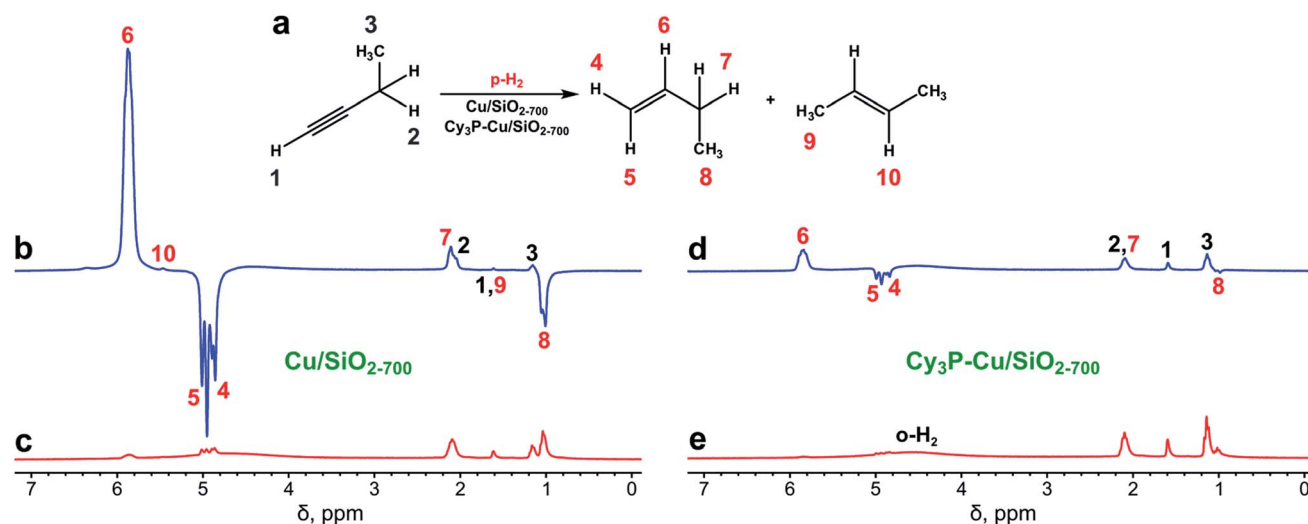


**Fig. 1** (a) Scheme of 1-butyne hydrogenation. (b and c) <sup>1</sup>H NMR spectra acquired during 1-butyne hydrogenation with parahydrogen over the Cu/SiO<sub>2-700</sub> catalyst (b) while the gas was flowing and (c) after rapid interruption of the gas flow and subsequent relaxation of nuclear spins to thermal equilibrium. (d and e) <sup>1</sup>H NMR spectra acquired during 1-butyne hydrogenation with parahydrogen over the Cy<sub>3</sub>P-Cu/SiO<sub>2-700</sub> catalyst (d) while the gas was flowing and (e) after rapid interruption of the gas flow and subsequent relaxation of nuclear spins to thermal equilibrium. All spectra were acquired with 8 signal accumulations and are presented on the same vertical scale. The reaction temperature was 450 °C, and gas flow rate was 5.1 mL s<sup>-1</sup>.



hydrogenation over the Cu/SiO<sub>2-700</sub> catalyst. Similarly, the Cy<sub>3</sub>P–Cu/SiO<sub>2-700</sub> catalyst showed significant activity above 250 °C. The catalyst was highly selective toward 2-butene (>95%) and in this case, no butane was formed (Table S7†). Then the temperature was increased to 300 °C. At the very first moment at 300 °C and a 6.5 mL s<sup>−1</sup> gas flow rate, some catalytic activity was observed in the hydrogenation of 2-butyne to 2-butene (Fig. S8,† red trace). Unfortunately, the catalyst rapidly deactivated at the reaction temperature, as evidenced by a rapid decrease in the signals of 2-butene (see Fig. S8,† blue trace) that occurred within minutes. Any PHIP effects, if present, were very small. Interestingly, hydrogenation of 2-butyne over more common heterogeneous hydrogenation catalysts such as Pd/TiO<sub>2</sub> and Rh/TiO<sub>2</sub> featured pronounced PHIP effects for 2-butene and butane (Fig. S9†).<sup>30</sup>

Thus, it was found that treatment of the Cu/SiO<sub>2-700</sub> catalyst with PCy<sub>3</sub> leads to a significant increase in selectivity toward the formation of alkenes in the flow semihydrogenation of alkynes. Moreover, the modified catalyst provided a higher intensity of PHIP effects pointing to a higher contribution of pairwise hydrogen addition with this material (Scheme 1). These results can tentatively be explained by the selective binding of the PCy<sub>3</sub> ligand to more active but unselective Cu surface sites, which in turn can impede the migration of hydrogen atoms, making pairwise addition of hydrogen more probable. A significant increase in the chemoselectivity of hydrogenation at the expense of catalytic activity confirms this hypothesis, as such an effect is typically observed with ligand-induced catalyst poisoning in heterogeneous catalysis.

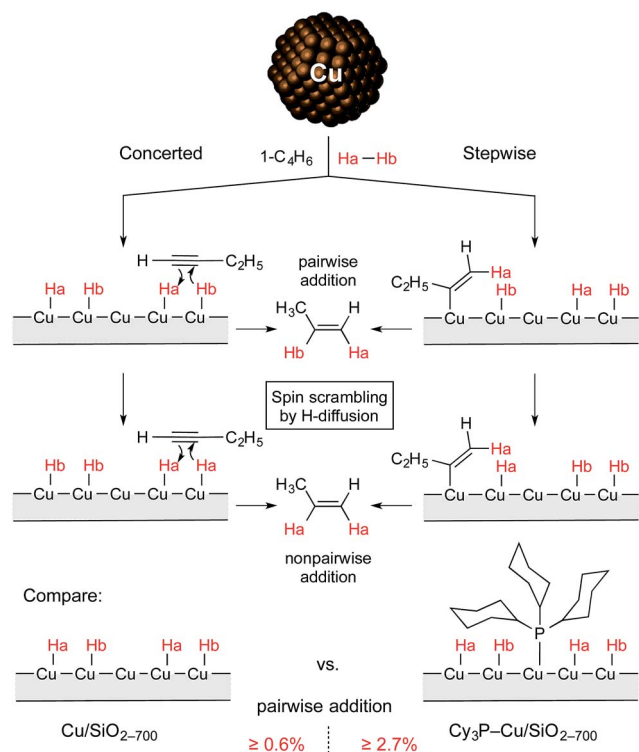

**Scheme 1** Non-pairwise and pairwise routes of hydrogen addition to 1-butyne over Cu/SiO<sub>2-700</sub> and Cy<sub>3</sub>P–Cu/SiO<sub>2-700</sub> catalysts.

## Conclusions

We reported the first study on selective semihydrogenation of alkynes with silica-supported Cu nanoparticles and parahydrogen. PHIP effects were observed for the hydrogenation of 1-butyne on Cu/SiO<sub>2-700</sub> and were very minor for the hydrogenation of 1-butene and not observed for 2-butyne hydrogenation, indicating that different mechanistic manifolds operate with these substrates. Modification of the Cu/SiO<sub>2-700</sub> catalyst with PCy<sub>3</sub> leads to an increase in the selectivity of 1-butyne hydrogenation to nearly 100% (with by-products below the detection limit of NMR), although it was found to make this catalyst significantly less active. The remarkable selectivity of Cy<sub>3</sub>P–Cu/SiO<sub>2-700</sub> also manifested in no activity in the hydrogenation of 1-butene, and no formation of butane from 2-butyne. Cy<sub>3</sub>P–Cu/SiO<sub>2-700</sub> provided no less than 2.7% pairwise hydrogen addition to 1-butyne, with the actual value likely to be higher due to polarization losses *via* relaxation. Our results demonstrate that copper-based catalysts are promising inexpensive alternatives to heterogeneous noble metal catalysts for the semihydrogenation of alkynes in the flow and the production of hyperpolarized gases.

## Acknowledgements

The ITC team thanks the Russian Science Foundation (grant 14-13-00445) for the support of the PHIP experiments, and Dr Syatoslav E. Tolstikov (ITC) for providing access to the glove box equipment. A. F. thanks the Holcim Stiftung for the Habilitation fellowship. O. G. S. acknowledges the PhD scholarship from Haldor Topsøe. The supported Cu nanoparticles were developed in a project funded by CCEM and Swiss Electric Research.

## Notes and references

- 1 S. A. Nikolaev, L. N. Zanaevskii, V. V. Smirnov, V. A. Averyanov and K. L. Zanaevskii, *Russ. Chem. Rev.*, 2009, **78**, 231–247.
- 2 W.-Y. Siau, Y. Zhang and Y. Zhao, *Top. Curr. Chem.*, 2012, **327**, 33–58.
- 3 H. Lindlar, *Helv. Chim. Acta*, 1952, **35**, 446–450.
- 4 M. R. Stambach, D. J. Thomas, D. L. Trimm and M. S. Wainwright, *Appl. Catal.*, 1990, **58**, 209–217.
- 5 J. T. Wehrli, D. J. Thomas, M. S. Wainwright and D. L. Trimm, *Appl. Catal.*, 1990, **66**, 199–208.
- 6 R. A. Koeppe, J. T. Wehrli, M. S. Wainwright, D. L. Trimm and N. W. Cant, *Appl. Catal.*, 1994, **120**, 163–177.
- 7 B. Bridier and J. Pérez-Ramírez, *J. Am. Chem. Soc.*, 2010, **132**, 4321–4327.
- 8 B. Bridier, N. López and J. Pérez-Ramírez, *J. Catal.*, 2010, **269**, 80–92.
- 9 A. Fedorov, H.-J. Liu, H.-K. Lo and C. Copéret, *J. Am. Chem. Soc.*, 2016, **138**, 16502–16507.
- 10 A. J. Rossini, A. Zagdoun, M. Lelli, A. Lesage, C. Copéret and L. Emsley, *Acc. Chem. Res.*, 2013, **46**, 1942–1951.





- 11 J.-H. Ardenkjaer-Larsen, G. S. Boebinger, A. Comment, S. Duckett, A. S. Edison, F. Engelke, C. Griesinger, R. G. Griffin, C. Hilty, H. Maeda, G. Parigi, T. Prisner, E. Ravera, J. van Bentum, S. Vega, A. Webb, C. Luchinat, H. Schwalbe and L. Frydman, *Angew. Chem., Int. Ed.*, 2015, **54**, 9162–9185.
- 12 P. Nikolaou, B. M. Goodson and E. Y. Chekmenev, *Chem. – Eur. J.*, 2015, **21**, 3156–3166.
- 13 J. H. Ardenkjær-Larsen, B. Fridlund, A. Gram, G. Hansson, L. Hansson, M. H. Lerche, R. Servin, M. Thaning and K. Golman, *Proc. Natl. Acad. Sci. U. S. A.*, 2003, **100**, 10158–10163.
- 14 J. H. Ardenkjaer-Larsen, *J. Magn. Reson.*, 2016, **264**, 3–12.
- 15 A. Lesage, M. Lelli, D. Gajan, M. A. Caporini, V. Vitzthum, P. Mieville, J. Alauzun, A. Roussey, C. Thieuleux, A. Mehdi, G. Bodenhausen, C. Copéret and L. Emsley, *J. Am. Chem. Soc.*, 2010, **132**, 15459–15461.
- 16 M. Valla, A. J. Rossini, M. Caillot, C. Chizallet, P. Raybaud, M. Digne, A. Chaumonnot, A. Lesage, L. Emsley, J. A. van Bokhoven and C. Copéret, *J. Am. Chem. Soc.*, 2015, **137**, 10710–10719.
- 17 T. Kobayashi, F. A. Perras, I. I. Slowing, A. D. Sadow and M. Pruski, *ACS Catal.*, 2015, **5**, 7055–7062.
- 18 T.-C. Ong, W.-C. Liao, V. Mougel, D. Gajan, A. Lesage, L. Emsley and C. Copéret, *Angew. Chem., Int. Ed.*, 2016, **55**, 4743–4747.
- 19 C. R. Bowers and D. P. Weitekamp, *J. Am. Chem. Soc.*, 1987, **109**, 5541–5542.
- 20 R. A. Green, R. W. Adams, S. B. Duckett, R. E. Mewis, D. C. Williamson and G. G. R. Green, *Prog. Nucl. Magn. Reson. Spectrosc.*, 2012, **67**, 1–48.
- 21 C. R. Bowers and D. P. Weitekamp, *Phys. Rev. Lett.*, 1986, **57**, 2645–2648.
- 22 L. Buljubasich, M. B. Franzoni and K. Munnemann, *Top. Curr. Chem.*, 2013, **338**, 33–74.
- 23 K. V. Kovtunov, I. E. Beck, V. I. Bukhtiyarov and I. V. Koptug, *Angew. Chem., Int. Ed.*, 2008, **47**, 1492–1495.
- 24 K. V. Kovtunov, V. V. Zhivonitko, I. V. Skovpin, D. A. Barskiy and I. V. Koptug, *Top. Curr. Chem.*, 2013, **338**, 123–180.
- 25 A. M. Balu, S. B. Duckett and R. Luque, *Dalton Trans.*, 2009, 5074–5076.
- 26 I. V. Koptug, V. V. Zhivonitko and K. V. Kovtunov, *ChemPhysChem*, 2010, **11**, 3086–3088.
- 27 K. V. Kovtunov, D. A. Barskiy, O. G. Salnikov, R. V. Shchepin, A. M. Coffey, L. M. Kovtunova, V. I. Bukhtiyarov, I. V. Koptug and E. Y. Chekmenev, *RSC Adv.*, 2016, **6**, 69728–69732.
- 28 D. B. Burueva, O. G. Salnikov, K. V. Kovtunov, A. S. Romanov, L. M. Kovtunova, A. K. Khudorozhkov, A. V. Bukhtiyarov, I. P. Prosvirin, V. I. Bukhtiyarov and I. V. Koptug, *J. Phys. Chem. C*, 2016, **120**, 13541–13548.
- 29 O. G. Salnikov, D. B. Burueva, D. A. Barskiy, G. A. Bukhtiyarova, K. V. Kovtunov and I. V. Koptug, *ChemCatChem*, 2015, **7**, 3508–3512.
- 30 O. G. Salnikov, K. V. Kovtunov, D. A. Barskiy, A. K. Khudorozhkov, E. A. Inozemtseva, I. P. Prosvirin, V. I. Bukhtiyarov and I. V. Koptug, *ACS Catal.*, 2014, **4**, 2022–2028.
- 31 R. Zhou, E. W. Zhao, W. Cheng, L. M. Neal, H. Zheng, R. E. Quiñones, H. E. Hagelin-Weaver and C. R. Bowers, *J. Am. Chem. Soc.*, 2015, **137**, 1938–1946.
- 32 R. Zhou, W. Cheng, L. M. Neal, E. W. Zhao, K. Ludden, H. E. Hagelin-Weaver and C. R. Bowers, *Phys. Chem. Chem. Phys.*, 2015, **17**, 26121–26129.
- 33 O. G. Salnikov, D. A. Barskiy, D. B. Burueva, Y. K. Gulyaeva, B. S. Balzhinimaev, K. V. Kovtunov and I. V. Koptug, *Appl. Magn. Reson.*, 2014, **45**, 1051–1061.
- 34 L.-S. Bouchard, S. R. Burt, M. S. Anwar, K. V. Kovtunov, I. V. Koptug and A. Pines, *Science*, 2008, **319**, 442–445.
- 35 V.-V. Telkki, V. V. Zhivonitko, S. Ahola, K. V. Kovtunov, J. Jokisaari and I. V. Koptug, *Angew. Chem., Int. Ed.*, 2010, **49**, 8363–8366.
- 36 C. Copéret, A. Comas-Vives, M. P. Conley, D. P. Estes, A. Fedorov, V. Mougel, H. Nagae, F. Núñez-Zarur and P. A. Zhizhko, *Chem. Rev.*, 2016, **116**, 323–421.
- 37 S. Sakong and A. Groß, *Surf. Sci.*, 2003, **525**, 107–118.
- 38 M. A. Chesters, K. J. Packer, H. E. Viner and M. A. P. Wright, *J. Phys. Chem. B*, 1997, **101**, 9995–10003.
- 39 L. T. Kuhn and J. Bargon, *Top. Curr. Chem.*, 2007, **276**, 25–68.
- 40 D. A. Barskiy, O. G. Salnikov, K. V. Kovtunov and I. V. Koptug, *J. Phys. Chem. A*, 2015, **119**, 996–1006.
- 41 P.-H. Phua, L. Lefort, J. A. F. Boogers, M. Tristany and J. G. de Vries, *Chem. Commun.*, 2009, 3747–3749.

