



Cite this: *RSC Adv.*, 2018, 8, 14369

Enhanced hydrogen evolution reaction activity of hydrogen-annealed vertical MoS₂ nanosheets†

Mengci He,^a Fanpeng Kong,^b Geping Yin,^b Zhe Lv,^c Xiudong Sun,^{ID} ^{ad} Hongyan Shi^{*ad} and Bo Gao^{ID} ^{*ad}

Molybdenum disulfide (MoS₂) is a promising electrocatalyst for hydrogen evolution reaction (HER), but only edges and S-vacancies are catalytic active sites for the HER. Therefore, it is crucial to increase edge sites and S-vacancies for enhancing the HER activity of MoS₂. Here, we report an enhanced HER activity of MoS₂ by combing vertical nanosheets and H₂ annealing. Compared to horizontal MoS₂ nanosheets, pristine vertical MoS₂ nanosheets showed better HER activity due to a larger amount of edges. H₂ annealing further enhanced the HER activity of vertical MoS₂ nanosheets remarkably. Scanning electron microscopy (SEM), X-ray photoelectron spectra (XPS) and electrochemical impedance spectroscopy (EIS) were used to elucidate the enhanced HER activity by H₂ annealing. SEM images showed that H₂ annealing roughened the MoS₂ edges, leading to more edge sites. XPS data revealed the smaller S : Mo ratio after H₂ annealing, meaning more S-vacancies. Meanwhile, EIS measurements showed that charge transfer was accelerated by H₂ annealing. These findings elaborated the H₂ annealing induced enhancement of the HER activity, which were further confirmed by the subsequent re-sulfurization experiment.

Received 6th February 2018

Accepted 11th April 2018

DOI: 10.1039/c8ra01147h

rsc.li/rsc-advances

Introduction

Because of its high efficiency, environment-friendliness and renewability, hydrogen is expected to play an important role in superseding the carbon-based fossil fuels. Sustainable, cost-effective and efficient production of hydrogen is a prerequisite for realizing hydrogen economy.^{1,2} Electrochemical catalytic hydrogen evolution reaction (HER) in acidic media is an efficient method to generate hydrogen from water splitting.² Due to the presence of an overpotential, an electrolysis voltage is always needed, which leads to a waste of electric energy. Currently, there are no materials that could compare with platinum (Pt) in terms of the activity and stability. But its commercial application is greatly limited by the high cost and scarcity.^{3,4} Therefore, it highly demands to develop other efficient non-noble-metal HER electrocatalysts with high abundance and low cost to make H₂ a competitive alternative energy source.^{5,6}

A significant breakthrough was achieved when MoS₂ was introduced as a promising and highly stable electrocatalyst for the HER.^{7–19} For decades, MoS₂ was believed to be inactive of the HER, because the basal plane exhibits a hydrogen adsorption free energy of 1.92 eV.^{20,21} Recently, density functional theory (DFT) calculations on the Mo edge of MoS₂ revealed that at 50% hydrogen coverage, it possessed a hydrogen adsorption free energy of 0.08 eV, near the optimal value of 0 eV.⁷ Soon after, it was experimentally confirmed that the edges of MoS₂ are indeed the catalytic active sites for the HER.^{9,10} These studies motivated the development of MoS₂ catalysts with a substantial fraction of further exposed edge sites, including hollow spheres,⁹ edge-exposed films,²² amorphous films,²³ defect-rich films,²⁴ nanodots²⁵ and vertically aligned nanosheets.^{8,24,26–28} Therein, vertical MoS₂ nanosheets, which have vertical channels for ion penetration and intimate contact between the active nanosheets and the random substrate, were shown to remarkably increase the density of edge sites and hence considered as an ideal geometry for improving the HER performance of MoS₂-based HER catalysts.^{9,22,29–41}

Although extensive efforts have been made to increase the number of edge sites, the overall HER activity is still limited, as generally only a small fraction of edge sites contribute to the reaction rate.^{10,42} Therefore, it is necessary and urgent to explore effective methods to increase the HER activity of inert basal plane sites in MoS₂ nanosheets. Fortunately, S-vacancies in the basal plane of MoS₂ nanosheets were recently explored and suggested to have a significant impact on the HER activity.^{10,43–45} By Ar or oxygen plasma exposure, or H₂ treatment, S-vacancies

^aInstitute of Modern Optics, Key Lab of Micro-optics and Photonic Technology of Heilongjiang Province, Key Laboratory of Micro-Nano Optoelectronic Information System, Ministry of Industry and Information Technology, Department of Physics, Harbin Institute of Technology, Harbin 150001, China. E-mail: gaobo@hit.edu.cn

^bSchool of Chemistry and Chemical Engineering, Harbin Institute of Technology, Harbin 150001, China

^cDepartment of Physics, Harbin Institute of Technology, Harbin 150080, China

^dCollaborative Innovation Center of Extreme Optics, Shanxi University, Taiyuan 03006, China. E-mail: shi.hong.yan@hit.edu.cn

† Electronic supplementary information (ESI) available: XPS data of Mo 3d region for the re-sulfurized MoS₂, calculation of onset overpotential, cathodic polarization curves of three H₂-annealed MoS₂ samples. See DOI: 10.1039/c8ra01147h



were introduced into MoS₂ nanosheets, and remarkably enhanced the HER activity.^{44,46} This method is only effective for flat MoS₂ catalysts due to the Ar and oxygen plasma's directionality and thus unsuitable for vertical nanostructures and 3D nanostructures.⁴⁷ Meanwhile, conductivity was also identified as a crucial factor for the HER activity, because a high conductivity ensures a fast charge transfer in the HER interface.^{48–51} Therefore, improving the conductivity while increasing active sites is the most promising but challenging task for optimizing the HER activity of MoS₂ nanosheets.

Herein, we report an enhanced HER activity of MoS₂ by combing vertical nanosheets and H₂ annealing. Vertical MoS₂ nanosheets were grown on glassy carbon by CVD method at 520 °C. Pristine vertical MoS₂ nanosheets with a larger amount of edges showed better HER activity than horizontal ones. H₂ annealing further enhanced the HER activity of vertical MoS₂ nanosheets. Scanning electron microscopy (SEM), X-ray photoelectron spectra (XPS) and electrochemical impedance spectroscopy (EIS) were used to elucidate the enhanced HER activity by H₂ annealing. SEM images showed that H₂ annealing roughened the MoS₂ edges, leading to more edge sites. XPS data revealed the smaller S : Mo ratio after H₂ annealing, meaning more S-vacancies. Meanwhile, EIS measurements showed that charge transfer was accelerated by H₂ annealing. These findings elaborated the H₂ annealing induced enhancement of the HER activity, which were further confirmed by the subsequent re-sulfurization experiment.

Experimental

Growth of vertical MoS₂ nanosheets by CVD method

Vertical MoS₂ nanosheets were synthesized by CVD method as shown in Fig. 1a. The vertical MoS₂ nanosheets samples were grown on glassy carbon inside a tubular furnace equipped with 22 mm diameter quartz tube. A silica boat loaded with MoO₃ powder (purity 99.95%) and glassy carbon substrate were placed one after another in the center of hot zone inside the tube furnace, and the distance between MoO₃ powder and glassy carbon substrate was ~2 cm. At the upstream of the tube, the other boat with sulfur powder (purity 99.5%) was placed outside the hot zone, which was mildly sublimated with heater band at ~120 °C. Before heating, the tube was pumped down to a base pressure of ~0.1 Pa and flushed with Ar to guarantee a favorable growth atmosphere. The furnace was then heated from room temperature to 520 °C at 50 °C min⁻¹ and kept at 520 °C for 15 min with Ar flow of 10 sccm. After growth, the furnace was opened directly for rapid cooling to the room temperature with Ar flow of 200 sccm.

Hydrogen annealing of vertical MoS₂ nanosheets

Before the hydrogen annealing experiment, high quality vertical MoS₂ nanosheets sample on glassy carbon was selected by electrochemical measurements. After putting selected MoS₂ nanosheets sample into the quartz tube at center of the furnace, the temperature of the furnace was raised up to 780 °C at 50 °C min⁻¹ with Ar flow of 50 sccm. After the temperature

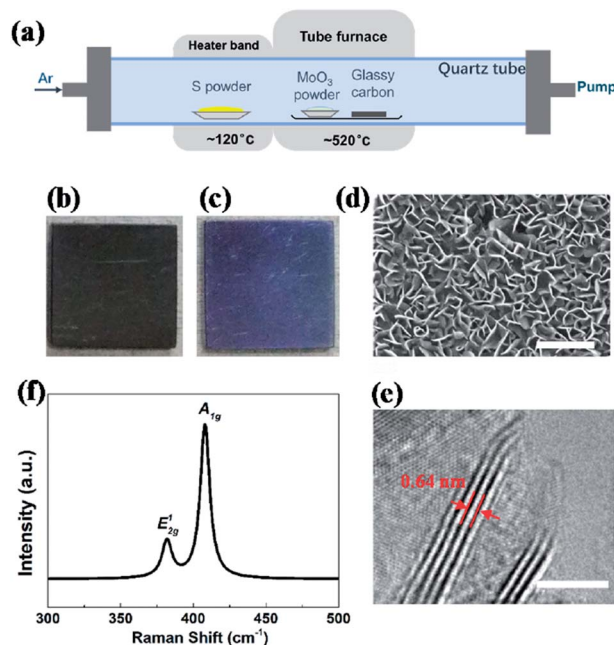


Fig. 1 (a) Schematic diagram of dual-temperature zone CVD synthesis of vertical MoS₂ nanosheets on glassy carbon. Photos of glassy carbon (b) without and (c) with vertical MoS₂ nanosheets. (d) Typical SEM image of pristine vertical MoS₂ nanosheets on glassy carbon; scale bar: 300 nm. (e) Typical HRTEM image of pristine vertical MoS₂ nanosheets on glassy carbon with perfectly vertically aligned nanosheets consisting of a few layer with an interlayer spacing of 0.64 nm; scale bar: 5 nm. (f) Raman spectra of MoS₂ nanosheets with two characteristic Raman vibration modes: in-plane vibration of molybdenum and sulfur atoms E_{2g}¹ and out-of-plane vibration of sulfur atoms A_{1g}.

reached 780 °C, Ar was immediately switched to H₂ with flow of 20 sccm, which is thought as the start point of the H₂ annealing. After a desired time (5, 10, 15, 20, 25, 30 and 35 min, respectively), H₂ was immediately switched to Ar with flow of 50 sccm and the furnace was shut off, leaving to cool down naturally. The annealing was carried out at low pressure of ~55 Pa.

Re-sulfurization of H₂-annealed MoS₂ nanosheets

The re-sulfurization was conducted following a similar process of growth experiment, except for the absence of MoO₃ and longer treatment time. H₂-annealed MoS₂ sample was placed in the center of the furnace and excessive sulfur powder was put in the center of the heater bend with temperature of ~120 °C. Before heating, the tube was pumped down to a base pressure of ~0.1 Pa and flushed with Ar to guarantee a favorable growth atmosphere. The furnace was then heated from room temperature to 520 °C at 50 °C min⁻¹ and kept at 520 °C for 30 min with Ar flow of 10 sccm. After re-sulfurization, the furnace was opened directly for rapid cooling to the room temperature with Ar flow of 200 sccm.

Structural characterization

Surface morphology and structure were characterized by SEM and high resolution transmission electron microscopy (HRTEM, Tecnai TF20) techniques, respectively. SEM characterization was



carried out on a Hitachi SU8000 instrument with an accelerating voltage of 15 kV and current of 10 μA . HRTEM samples were prepared by gently rubbing the TEM grid across the face of the MoS_2 thin film to detach nanosheets and promote their adhesive on to the lacey-carbon TEM grid. Raman spectroscopy was measured using a B&W-Tek confocal Raman microscope with a laser excitation energy of 532 nm (2.33 eV). XPS were recorded on an ESCALAB MKII using an Al K α excitation source.

Electrochemical measurements

The experiment of HER was carried out by measuring the current correlated with the water dissociation in the ambient conditions. All of the electrochemical measurements were performed in an electrochemical workstation CHI604B with a standard three-electrode configuration. The working electrode was the vertical MoS_2 nanosheets on glassy carbon. A graphite rod and an Ag/AgCl electrode were used as the counter electrode and the reference electrode, respectively. The performance of the HER was measured using linear sweep voltammetry from 0 to -0.6 V (vs. RHE) with scan rate of 5 mV s^{-1} at room temperature, which was conducted in $0.5 \text{ M H}_2\text{SO}_4$ aqueous solution. All the potentials were referenced to reversible hydrogen electrode (RHE) by the following equation: $E(V \text{ vs. RHE}) = E(V \text{ vs. Ag/AgCl}) + 0.197 \text{ V} + 0.059 \text{ pH}$. In $0.5 \text{ M H}_2\text{SO}_4$, $E(V \text{ vs. RHE}) = E(V \text{ vs. Ag/AgCl}) + 0.197 \text{ V}$. An iR correction was normally employed to compensate for any potential loss arising from the external resistance of the electrochemical system. The electrolyte resistance and capacitance of the electrocatalysts were characterized by EIS. The ac impedance is measured at overpotential of -0.3 V (vs. RHE) within the frequency range from 0.1 to 10^6 Hz with a perturbation voltage amplitude of 10 mV . Cyclic voltammetry (CV) was conducted from 0 to -0.6 V (vs. RHE) at 100 mV s^{-1} to investigate the cycling stability.

Results and discussion

Fig. 1a shows an illustration of the dual-temperature zone CVD synthesis of vertical MoS_2 nanosheets on glassy carbon. In the dual-temperature approach, heater band is isolated from the tube furnace. Therefore, the temperature of the heater band can be controlled independently from the temperature of the tube furnace. A 1 g portion of S powder was placed upstream of the gas flow in the quartz tube, right in the center of the heater band. 5 mg of MoO_3 powder and glassy carbon was put in the center of the tube furnace. The S powder was heated to 120°C in order to be evaporated by heater band. And the S vapor was carried downstream by Ar. At low pressure, S and MoO_3 vapor reacted and formed MoS_2 on glassy carbon at 520°C , which is much lower than previous study.^{22,43}

After the growth, the whole substrate turned violet from black (shown in Fig. 1b and c), indicating the formation of uniform MoS_2 nanostructures. The morphology and structure of MoS_2 were characterized by SEM and HRTEM, respectively. Fig. 1d shows the SEM image of vertical MoS_2 nanosheets on glassy carbon. It can be seen that the size of MoS_2 nanosheets is

about $100\text{--}200 \text{ nm}$. From the HRTEM image in Fig. 1e, it can be seen that the nanosheets consisted of $4\text{--}5$ layers with layer distance of 0.64 nm . Raman measurements were also performed to further confirm the presence of MoS_2 . As shown in Fig. 1f, there are two dominant Raman peaks at 382 and 408 cm^{-1} , respectively, which originate from the in-plane E_{2g}^1 and out-of-planes A_{1g} vibrational modes of MoS_2 , respectively.

The electrocatalytic HER activities were investigated in $0.5 \text{ M H}_2\text{SO}_4$ solution by linear sweep voltammetry (LSV) using a three-electrode setup at a scan rate of 5 mV s^{-1} . An iR correction was normally employed to compensate for any potential loss arising from the external resistance of the electrochemical system. Fig. 2a shows the cathodic polarization curves of glassy carbon with and without vertical MoS_2 nanosheets, which are indicated by black and orange lines, respectively. It can be seen that vertical MoS_2 nanosheets exhibited great HER activity, compared to bare glassy carbon. A variety of methodologies have been proposed to evaluate the HER activity. Here overpotential at current density of 10 mA cm^{-2} ,⁴² onset overpotential and Tafel slope were used. The overpotential for vertical MoS_2 nanosheets at current density of 10 mA cm^{-2} is 485 mV , which is lower than horizontal MoS_2 nanosheets.^{46,52} The improvement is due to more edges in the vertical MoS_2 nanosheets sample, and hence more active sites.²² Fig. 2b shows the Tafel plot of pristine vertical MoS_2 nanosheets, indicated by black dotted lines. The Tafel slope is determined by fitting the linear portion of the Tafel plot to the Tafel equation $\eta = b \log |j| + a$, where j is the current density, b is the Tafel slope. The value of 118 mV dec^{-1} was obtained from the pristine sample. The pristine MoS_2 sample exhibited the current density 1 mA cm^{-2} at the onset overpotential (301 mV), which was determined from Tafel plot as shown in Fig. S1.†

To further enhance HER activity, pristine vertical MoS_2 nanosheets were annealed in H_2 atmosphere, which has been demonstrated to be catalytically effective for horizontal MoS_2 nanosheets.⁴⁶ But the mechanism was not clear. Before H_2 annealing, the cathodic polarization curves of each vertical MoS_2 nanosheets sample were measured to assure that all pristine samples had similar HER activity (the overpotentials at current density of 10 mA cm^{-2} are shown by black squares in Fig. 2c). In the H_2 annealing experiment, the selected MoS_2 samples were placed in the center of the tube furnace set at 780°C . For time-dependent H_2 annealing, the different pristine samples were treated for $5, 10, 15, 20, 25, 30$ and 35 min , respectively. To precisely control the H_2 annealing time, 20 sccm of H_2 only flowed when the temperature reached 780°C , while 50 sccm of Ar flowed during the warming-up and cooling-down process.

Fig. 2a shows the cathodic polarization curves of pristine and H_2 -annealed vertical MoS_2 nanosheets for $5, 10, 15, 20, 25, 30$ and 35 min , respectively. It can be seen that all H_2 -annealed MoS_2 samples had a smaller onset overpotential and a smaller overpotential at current density of 10 mA cm^{-2} . Meanwhile, the onset potential and the overpotential at current density of 10 mA cm^{-2} have a relation to the annealing time. So, we plotted the overpotential at current density of 10 mA cm^{-2} as a function



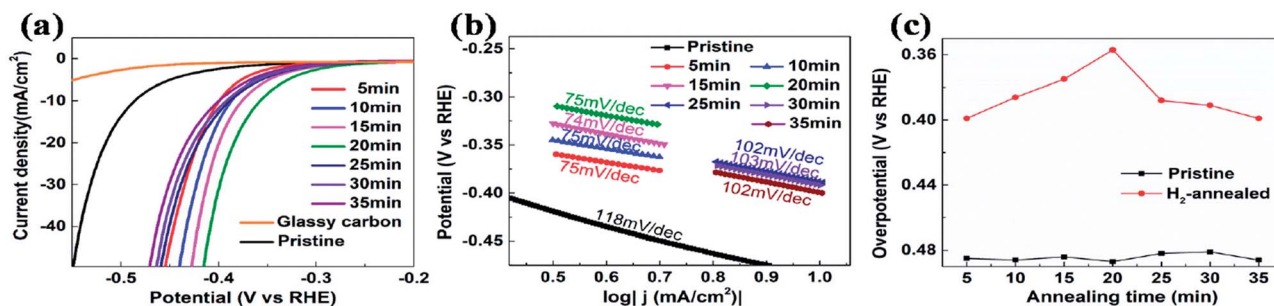


Fig. 2 (a) Cathodic polarization curves at scan rate of 5 mV s^{-1} in $0.5 \text{ M H}_2\text{SO}_4$ and corresponding (b) Tafel plots. (c) Overpotential at 10 mA cm^{-2} of pristine (black squares) and H_2 -annealed (red dots) vertical MoS_2 nanosheets versus annealing time.

of annealing time (shown by red dots in Fig. 2c). It can be seen that, as the annealing time increased to 20 min, the overpotential decreased to 357 mV from $\sim 485 \text{ mV}$ for pristine MoS_2 samples, which is reproducible (see Fig. S3 of ESI†). The overpotential was increased when further increasing the annealing time, but it was still smaller than that of pristine MoS_2 samples. The annealing time dependence of cathodic polarization curves also indicates good reproducibility of our method. Fig. 2b shows the Tafel plots of pristine and H_2 -annealed vertical MoS_2 nanosheets for 5, 10, 15, 20, 25, 30 and 35 min, respectively. It can be seen that, when annealing for 5–20 min, all samples exhibited similar Tafel slopes of $\sim 75 \text{ mV dec}^{-1}$, which are much lower than pristine samples with Tafel slopes of $\sim 118 \text{ mV dec}^{-1}$. But when further increasing the annealing time, the Tafel slopes were increased to $\sim 102 \text{ mV dec}^{-1}$. The HER results indicated that the HER activities of vertical MoS_2 nanosheets were enhanced after H_2 annealing, and was maximized with annealing time of 20 min, which showed better performance than CVD-grown vertical MoS_2 nanosheets and H_2 annealed horizontal MoS_2 in previously reported.^{22,46}

To figure out the origin of the enhanced HER activity of vertical MoS_2 nanosheets by H_2 annealing, the morphologies of H_2 -annealed samples were characterized by SEM. Fig. 3a–g

show the SEM images of H_2 -annealed vertical MoS_2 nanosheets samples for 5, 10, 15, 20, 25, 30 and 35 min at 780°C , respectively. It can be seen in Fig. 3a that, when the annealing time is 5 min, only a few vertical MoS_2 nanosheets were damaged (indicated by yellow circles), while most ones were intact. When further increasing the annealing time, the damaged MoS_2 nanosheets were fragmented into smaller nanosheets (indicated by yellow circles in Fig. 3b) and further formed aggregates (shown in Fig. 3c). After annealing for 20 min, almost all MoS_2 nanosheets were damaged (shown in Fig. 3d). When the annealing time was increased to 35 min, all nanosheets were melted and the sheet size was greatly reduced (shown in Fig. 3g). It is particularly noted in Fig. 3h that the edge of the nanosheets became rough, indicating that H_2 annealing increased the edges and hence active sites.

To fully elaborate the enhanced HER activity of vertical MoS_2 nanosheets by H_2 annealing, we also did the XPS characterization on the pristine and H_2 -annealed samples to explore the chemical states of the vertical MoS_2 nanosheets. Fig. 4 shows the XPS data of Mo 3d region for the pristine and H_2 -annealed vertical MoS_2 nanosheets for 5, 10, 15, 20, 25, 30 and 35 min, respectively. As shown in Fig. 4a, the spectrum of the pristine sample is dominated by a doublet with two sharp peaks, which

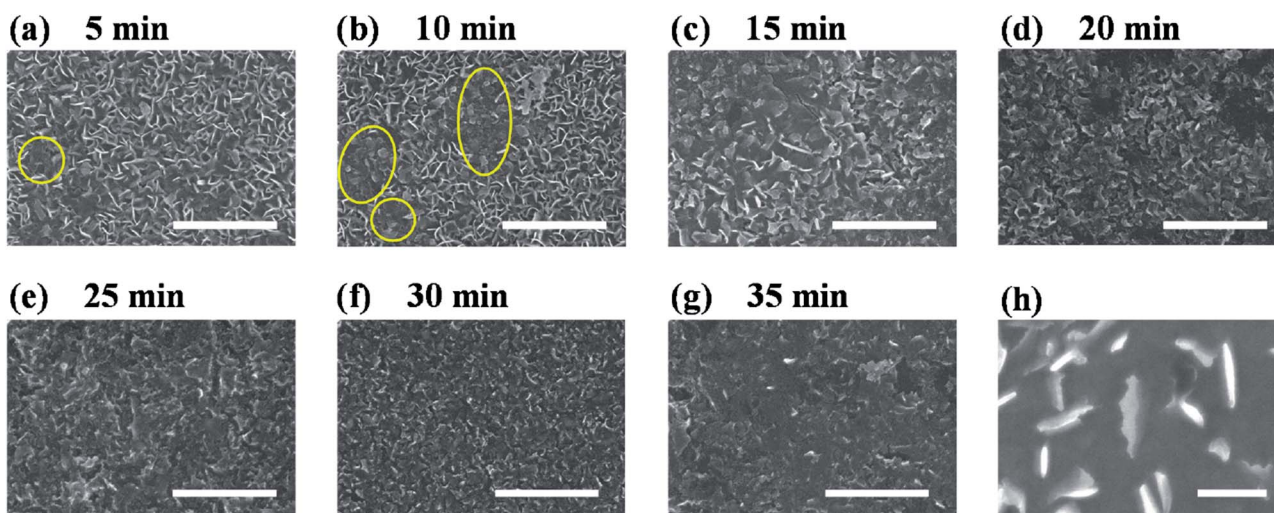


Fig. 3 (a–g) SEM images of H_2 -annealed vertical MoS_2 nanosheets for 5, 10, 15, 20, 25, 30 and 35 min, respectively; scale bar: $1 \mu\text{m}$. (h) High magnification SEM image of H_2 -annealed vertical MoS_2 nanosheets for 20 min, showing rough edges induced by H_2 annealing; scale bar: 200 nm .



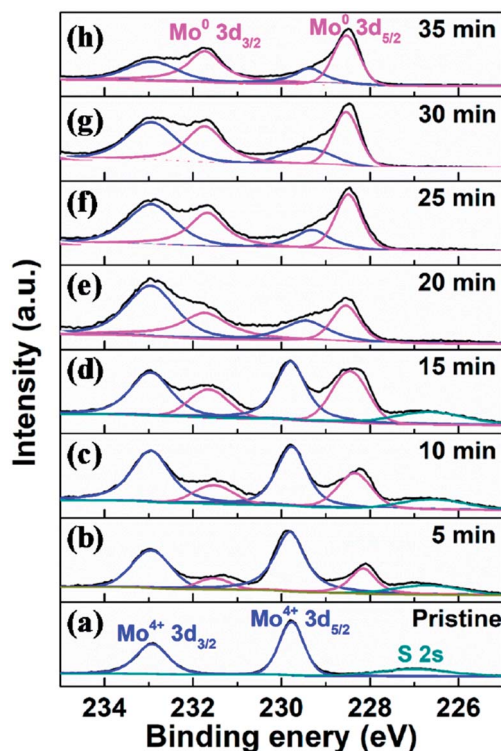


Fig. 4 XPS data of Mo 3d region for (a) pristine and H₂-annealed vertical MoS₂ nanosheets for (b) 5, (c) 10, (d) 15, (e) 20, (f) 25, (g) 30 and (h) 35 min, respectively.

are Mo 3d_{5/2} with binding energy of 229.7 eV and Mo 3d_{3/2} with binding energy of 232.9 eV. The distance between the two peaks was ~ 3.2 eV, which corresponds to the formation of MoS₂. The peak located at 226.5 eV corresponds to S 2s in MoS₂.⁵³

As shown in Fig. 4b, after H₂ annealing for 5 min, a new doublet appeared in the Mo 3d region located at a lower binding energy to that of the original Mo⁴⁺ doublet of the pristine sample. The two components of the new doublet at 228.1 and 231.5 eV, could be assigned to Mo 3d_{5/2} and Mo 3d_{3/2} of Mo⁰, respectively, as in elementary molybdenum, which was reduced from the pristine MoS₂ nanosheets by H₂ annealing. The appearance of elementary molybdenum indicates the loss of sulfur and hence the appearance of S-vacancies in H₂-annealed

MoS₂ samples. From the relative intensity between the new Mo⁰ doublet and the original Mo⁴⁺ doublet in Fig. 4b, the percentage of S-vacancies was determined to be 22.8%. As the annealing time was increased, the peak intensities of the new Mo⁰ doublet were increased, and so did the relative intensities between the new Mo⁰ doublet and the original Mo⁴⁺ doublet. It is also determined that the percentage of S-vacancies were 29.2%, 39.2%, 41.5%, 50.0%, 52.4% and 61.2% for H₂-annealing time of 10, 15, 20, 25, 30 and 35 min, respectively. As shown in Fig. 2, the maximal HER activity was found at H₂ annealing time of 20 min, corresponding to 41.5% of S-vacancies. Recent calculation showed that the optimal hydrogen adsorption free energy for HER occurred for an S-vacancy concentration that is between 12.5 and 15.62% of the surface atoms,^{44,47} which is much lower than our experiment result. It is known that besides hydrogen adsorption free energy, conductivity is also a crucial factor in HER, which we think is responsible for the high percentage of S-vacancies. Meanwhile, the intensity of the S 2s peak was gradually decreased without changing its shape and binding energy, which also suggested the production of S-vacancies in the H₂-annealed MoS₂ sample.

To further confirm that it is the S-vacancy that contributed to the enhanced HER activity of H₂-annealed vertical MoS₂ nanosheets, we re-sulfurized the H₂-annealed MoS₂ samples to repair the S-vacancies and measured the catalytic activities after the re-sulfurization. The re-sulfurization was achieved in the dual-temperature zone CVD with similar parameters to the synthesis of the vertical MoS₂ nanosheets, except for the absence of MoO₃ and longer treatment time. Fig. 5a shows the cathodic polarization curves of pristine and re-sulfurized MoS₂ samples which were previously H₂-annealed for 5, 10, 15, 20, 25, 30 and 35 min, respectively. It can be seen that, compared to H₂-annealed MoS₂ samples, both onset overpotential and overpotential at current density of 10 mA cm⁻² were increased after re-sulfurization, but smaller than pristine MoS₂ samples, which means HER activity were decreased after re-sulfurization, but still better than pristine MoS₂ samples. Since the re-sulfurization filled all S-vacancies induced by H₂ annealing (see XPS data of re-sulfurized vertical MoS₂ nanosheets in Fig. S2 of ESI[†]), the decrease of the HER activity after re-sulfurization could be attributed to the reduction of S-vacancies. For the partial recovery of HER activities compared

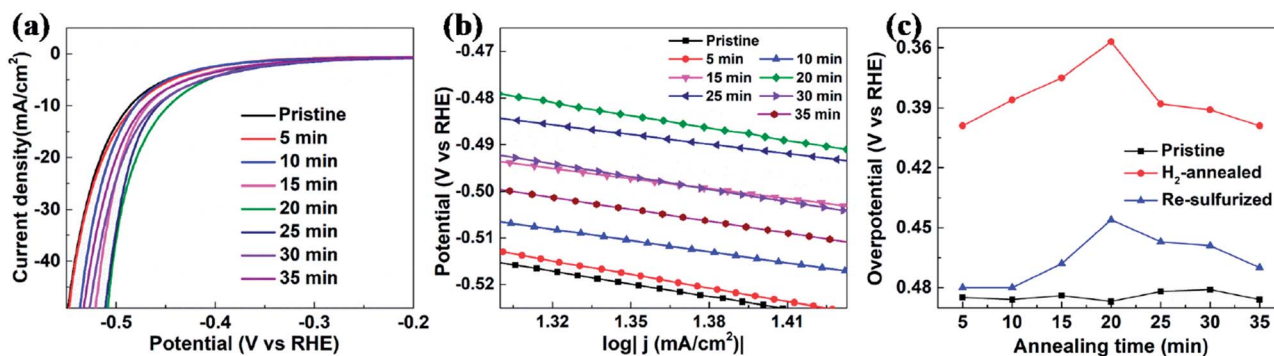


Fig. 5 (a) Cathodic polarization curves at scan rate of 5 mV s⁻¹ in 0.5 M H₂SO₄ and corresponding (b) Tafel plots. (c) Overpotential at 10 mA cm⁻² of pristine (black squares), H₂-annealed (red dots) and re-sulfurized (blue triangles) MoS₂ nanosheets versus annealing time.



to pristine MoS₂ samples, we conjecture that H₂ annealing induced rough MoS₂ edges played a role, which also could explain the dependence of the overpotential at current density of 10 mA cm⁻² as on annealing time for re-sulfurized MoS₂ samples (indicated by blue triangles in Fig. 5c).

In order to evaluate the kinetics of charge transfer in these samples, EIS measurements were carried out in a traditional three-electrode system. The diameter of the semicircle is considered to be related to charge transfer at the interface of the HER. A smaller diameter corresponds to more efficient charge transfer and smaller conductivity. Fig. 6a shows the Nyquist plots of pristine, H₂-annealed and re-sulfurized MoS₂ samples, respectively, which were collected by scanning from 0.1 to 10⁶ Hz with an overpotential of 0.3 V. H₂-annealed MoS₂ sample had a smaller semicircle diameter compared to pristine sample, indicating more efficient charge transfer after H₂ annealing. This also contributes to the enhanced HER activity of H₂-annealed MoS₂ samples. The efficient charge transfer could be attributed to the elementary Mo which has better conductivity than MoS₂, and reduced size of H₂-annealed MoS₂ nanosheets. This could explain the higher percentage of S-vacancies than previous calculation, at which the optimum HER activity was achieved.^{44,47} After re-sulfurization, the semicircle diameter of MoS₂ samples became larger, meaning slower charge transfer

than H₂-annealed MoS₂ sample. This is also considered to be responsible for the worse HER activity than H₂-annealed MoS₂ samples (shown in Fig. 5c). It is also found in Fig. 6a that the semicircle diameter of re-sulfurized MoS₂ sample was not completely recovered to that of pristine sample, indicating faster charge transfer than pristine sample, which resulted in the partial recovery of HER activity (shown in Fig. 5c). The faster charge transfer could be attributed to the reduced size of re-sulfurized MoS₂ nanosheets and hence the smaller resistance.

Long-term durability, which demonstrates the thermodynamic stability, is also an important factor to evaluate the overall performance of an electrocatalyst. We investigated the cycling stability of H₂-annealed vertical MoS₂ nanosheets sample for 20 min at 780 °C, which had the best electrocatalytic performance. The LSV scanning was performed before and after repeating cycling voltammetry treatment for 10 000 cycles in an acidic environment with a fast scan rate of 100 mV s⁻¹ in order to simulate the practical working conditions of water-splitting devices. Fig. 6b shows the cathodic polarization curves of the sample before and after the cycling treatment. It can be seen that there is a negligible change in the cathodic current. Meanwhile, the time-dependent electrochemical measurement for the sample (inset of Fig. 6b) suggests that such electrocatalyst maintained its current density for at least 8 h. Both results indicated the excellent durability of the H₂-annealed vertical MoS₂ nanosheets as an electrocatalyst.

Conclusions

We demonstrated the enhanced HER activity of MoS₂ nanosheets with vertical configuration and H₂ annealing. Vertical configuration offered more edge sites compared to horizontal MoS₂ nanosheets, and hence improved the HER activity. In addition, H₂ annealing produced a synergistic enhancement in two aspects. First, H₂ annealing roughened the edges and produced S-vacancies in the basal plane of vertical MoS₂ nanosheets, which increased the number of active sites. Second, H₂ annealing leads to the enhancement of the conductivity due to the production of elementary Mo and the decreased sheet size. Moreover, prominent electrochemical durability is also achieved. The H₂-annealed vertical MoS₂ nanosheets reported here represents a novel approach for producing highly active nanostructured MoS₂ as HER catalysts, and can be extended to other applications, such as supercapacitor and lithium-ion battery.

Conflicts of interest

The authors declare no competing financial interest.

Acknowledgements

This work was financially supported by the National Natural Science Foundation of China (No. 21203046, 21473046 and 11374074) and the New Faculty Start-up Funds from Harbin Institute of Technology.

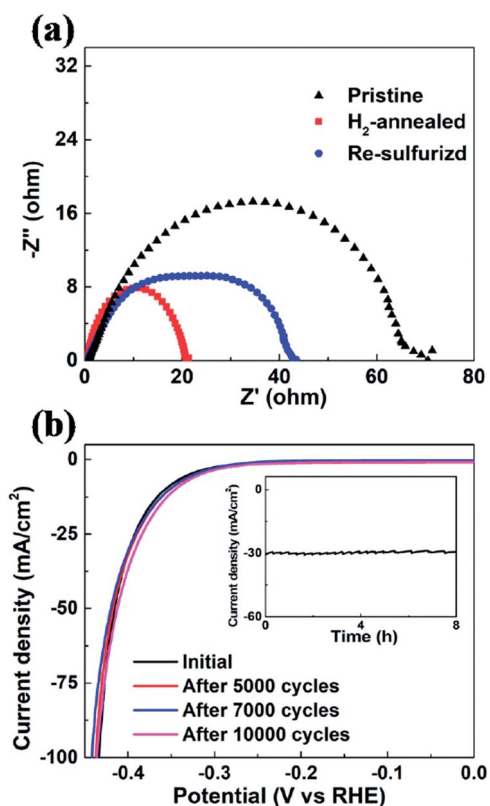


Fig. 6 (a) EIS of pristine, H₂-annealed and re-sulfurized vertical MoS₂ nanosheets. All of the spectra were collected by scanning from 0.1 to 10⁶ Hz with an overpotential of 0.3 V. (b) Cathodic polarization curves of the H₂-annealed MoS₂ for 20 min before and after 5000, 7000 and 10 000 cycles, respectively. Inset: time-dependent current density of the H₂-annealed MoS₂ for 20 min under a static overpotential of 400 mV for 8 h.



Notes and references

- 1 J. A. Turner, *Science*, 2004, **305**, 972.
- 2 K. Zeng and D. Zhang, *Prog. Energy Combust. Sci.*, 2010, **36**, 307.
- 3 K. Kwak, W. Choi, Q. Tang, M. Kim, Y. Lee, D. E. Jiang and D. Lee, *Nat. Commun.*, 2017, **8**, 14723.
- 4 J. Greeley, T. F. Jaramillo, J. Bonde, I. B. Chorkendorff and J. K. Norskov, *Nat. Mater.*, 2006, **5**, 909.
- 5 J. Xie and Y. Xie, *ChemCatChem*, 2015, **7**, 2568.
- 6 C. G. Morales-Guio, L. A. Stern and X. Hu, *Chem. Soc. Rev.*, 2014, **43**, 6555.
- 7 B. Hinnemann, P. G. Moses, J. Bonde, K. P. Jorgensen, J. H. Nielsen, S. Horch, I. Chorkendorff and J. K. Norskov, *J. Am. Chem. Soc.*, 2005, **127**, 5308.
- 8 D. Kong, H. Wang, J. J. Cha, M. Pasta, K. J. Koski, J. Yao and Y. Cui, *Nano Lett.*, 2013, **13**, 1341.
- 9 J. Kibsgaard, Z. Chen, B. N. Reinecke and T. F. Jaramillo, *Nat. Mater.*, 2012, **11**, 963.
- 10 T. F. Jaramillo, K. P. Jorgensen, J. Bonde, J. H. Nielsen, S. Horch and I. Chorkendorff, *Science*, 2007, **317**, 100.
- 11 H. Wang, Z. Lu, S. Xu, D. Kong, J. J. Cha, G. Zheng, P. C. Hsu, K. Yan, D. Bradshaw, F. B. Prinz and Y. Cui, *Proc. Natl. Acad. Sci. U. S. A.*, 2013, **110**, 19701.
- 12 J. Xie, H. Zhang, S. Li, R. Wang, X. Sun, M. Zhou, J. Zhou, X. W. Lou and Y. Xie, *Adv. Mater.*, 2013, **25**, 5807.
- 13 L. Yang, W. Zhou, J. Lu, D. Hou, Y. Ke, G. Li, Z. Tang, X. Kang and S. Chen, *Nano Energy*, 2016, **22**, 490.
- 14 W. Zhou, K. Zhou, D. Hou, X. Liu, G. Li, Y. Sang, H. Liu, L. Li and S. Chen, *ACS Appl. Mater. Interfaces*, 2014, **6**, 21534.
- 15 J. Xie, J. Zhang, S. Li, F. Grote, X. Zhang, H. Zhang, R. Wang, Y. Lei, B. Pan and Y. Xie, *J. Am. Chem. Soc.*, 2013, **135**, 17881.
- 16 W. Zhou, D. Hou, Y. Sang, S. Yao, J. Zhou, G. Li, L. Li, H. Liu and S. Chen, *J. Mater. Chem. A*, 2014, **2**, 11358.
- 17 Y. Yan, B. Xia, X. Ge, Z. Liu, J. Y. Wang and X. Wang, *ACS Appl. Mater. Interfaces*, 2013, **5**, 12794.
- 18 M. Xu, T. Liang, M. Shi and H. Chen, *Chem. Rev.*, 2013, **113**, 3766.
- 19 Z. Lu, W. Zhu, X. Yu, H. Zhang, Y. Li, X. Sun, X. Wang, H. Wang, J. Wang, J. Luo, X. Lei and L. Jiang, *Adv. Mater.*, 2014, **26**, 2683.
- 20 C. Tsai, K. Chan, J. K. Norskov and F. Abild-Pedersen, *Surf. Sci.*, 2015, **640**, 133.
- 21 H. Tributsch and J. C. Bennett, *J. Electroanal. Chem.*, 1977, **81**, 97.
- 22 S. Li, S. Wang, M. M. Salamone, A. W. Robertson, S. Nayak, H. Kim, S. C. E. Tsang, M. Pasta and J. H. Warner, *ACS Catal.*, 2017, **7**, 877.
- 23 J. Kibsgaard, T. F. Jaramillo and F. Besenbacher, *Nat. Chem.*, 2014, **6**, 248.
- 24 Y. Guo, X. Zhang, X. Zhang and T. You, *J. Mater. Chem. A*, 2015, **3**, 15927.
- 25 D. Gopalakrishnan, D. Damien and M. M. Shaijumon, *ACS Nano*, 2014, **8**, 5297.
- 26 D. J. Li, U. N. Maiti, J. Lim, D. S. Choi, W. J. Lee, Y. Oh, G. Y. Lee and S. O. Kim, *Nano Lett.*, 2014, **14**, 1228.
- 27 Y. H. Chang, C. T. Lin, T. Y. Chen, C. L. Hsu, Y. H. Lee, W. Zhang, K. H. Wei and L. J. Li, *Adv. Mater.*, 2013, **25**, 756.
- 28 Y. H. Chang, R. D. Nikam, C. T. Lin, J. K. Huang, C. C. Tseng, C. L. Hsu, C. C. Cheng, C. Y. Su, L. J. Li and D. H. Chua, *ACS Appl. Mater. Interfaces*, 2014, **6**, 17679.
- 29 Q. Feng, K. Duan, X. Ye, D. Lu, Y. Du and C. Wang, *Sens. Actuators, B*, 2014, **192**, 1.
- 30 R. R. Chianelli, M. H. Siadati, M. P. De la Rosa, G. Berhault, J. P. Wilcoxon, R. Bearden and B. L. Abrams, *Catal. Rev.*, 2006, **48**, 1.
- 31 J. N. Coleman, M. Lotya, A. O'Neill, S. D. Bergin, P. J. King, U. Khan, K. Young, A. Gaucher, S. De, R. J. Smith, I. V. Shvets, S. K. Arora, G. Stanton, H. Y. Kim, K. Lee, G. T. Kim, G. S. Duesberg, T. Hallam, J. J. Boland, J. J. Wang, J. F. Donegan, J. C. Grunlan, G. Moriarty, A. Shmeliov, R. J. Nicholls, J. M. Perkins, E. M. Grievson, K. Theuwissen, D. W. McComb, P. D. Nellist and V. Nicolosi, *Science*, 2011, **331**, 568.
- 32 Z. Lu, H. Zhang, W. Zhu, X. Yu, Y. Kuang, Z. Chang, X. Lei and X. Sun, *Chem. Commun.*, 2013, **49**, 7516.
- 33 A. J. Smith, Y.-H. Chang, K. Raidongia, T.-Y. Chen, L.-J. Li and J. Huang, *Adv. Energy Mater.*, 2014, **4**, 1400398.
- 34 H. Wang, Q. Zhang, H. Yao, Z. Liang, H. W. Lee, P. C. Hsu, G. Zheng and Y. Cui, *Nano Lett.*, 2014, **14**, 7138.
- 35 Y. Jung, J. Shen, Y. Liu, J. M. Woods, Y. Sun and J. J. Cha, *Nano Lett.*, 2014, **14**, 6842.
- 36 G. R. Bhimanapati, T. Hankins, Y. Lei, R. A. Vila, I. Fuller, M. Terrones and J. A. Robinson, *ACS Appl. Mater. Interfaces*, 2016, **8**, 22190.
- 37 J. Xie, H. Qu, J. Xin, X. Zhang, G. Cui, X. Zhang, J. Bao, B. Tang and Y. Xie, *Nano Res.*, 2017, **10**, 1178.
- 38 Y. Yan, B. Xia, N. Li, Z. Xu, A. Fisher and X. Wang, *J. Mater. Chem. A*, 2015, **3**, 131.
- 39 G. Zhou, X. Xu, J. Yu, B. Feng, Y. Zhang, J. Hu and Y. Zhou, *CrystEngComm*, 2014, **16**, 9025.
- 40 J. Xie, J. Xin, G. Cui, X. Zhang, L. Zhou, Y. Wang, W. Liu, C. Wang, M. Ning, X. Xia, Y. Zhao and B. Tang, *Inorg. Chem. Front.*, 2016, **3**, 1160.
- 41 Y. Yang, H. Fei, G. Ruan, C. Xiang and J. M. Tour, *Adv. Mater.*, 2014, **26**, 8163.
- 42 J. D. Benck, T. R. Hellstern, J. Kibsgaard, P. Chakthranont and T. F. Jaramillo, *ACS Catal.*, 2014, **4**, 3957.
- 43 Y. Yin, J. Han, Y. Zhang, X. Zhang, P. Xu, Q. Yuan, L. Samad, X. Wang, Y. Wang, Z. Zhang, P. Zhang, X. Cao, B. Song and S. Jin, *J. Am. Chem. Soc.*, 2016, **138**, 7965.
- 44 H. Li, C. Tsai, A. L. Koh, L. Cai, A. W. Contryman, A. H. Fragapane, J. Zhao, H. S. Han, H. C. Manoharan, F. Abild-Pedersen, J. K. Norskov and X. Zheng, *Nat. Mater.*, 2016, **15**, 48.
- 45 H. Li, M. Du, M. J. Mleczko, A. L. Koh, Y. Nishi, E. Pop, A. J. Bard and X. Zheng, *J. Am. Chem. Soc.*, 2016, **138**, 5123.
- 46 G. Ye, Y. Gong, J. Lin, B. Li, Y. He, S. T. Pantelides, W. Zhou, R. Vajtai and P. M. Ajayan, *Nano Lett.*, 2016, **16**, 1097.
- 47 C. Tsai, H. Li, S. Park, J. Park, H. S. Han, J. K. Norskov, X. Zheng and F. Abild-Pedersen, *Nat. Commun.*, 2017, **8**, 15113.



- 48 Y. Liang, Y. Li, H. Wang and H. Dai, *J. Am. Chem. Soc.*, 2013, **135**, 2013.
- 49 Z. S. Wu, S. Yang, Y. Sun, K. Parvez, X. Feng and K. Mullen, *J. Am. Chem. Soc.*, 2012, **134**, 9082.
- 50 L. Liao, J. Zhu, X. Bian, L. Zhu, M. D. Scanlon, H. H. Girault and B. Liu, *Adv. Funct. Mater.*, 2013, **23**, 5326.
- 51 Y. Li, H. Wang, L. Xie, Y. Liang, G. Hong and H. Dai, *J. Am. Chem. Soc.*, 2011, **133**, 7296.
- 52 Y. Yu, S. Y. Huang, Y. Li, S. N. Steinmann, W. Yang and L. Cao, *Nano Lett.*, 2014, **14**, 553.
- 53 T. Weber, J. C. Muijsers, J. H. M. C. van Wolput, C. P. J. Verhagen and J. W. Niemantsverdriet, *J. Phys. Chem.*, 1996, **100**, 14144.

