



Cite this: *RSC Adv.*, 2018, 8, 14221

Received 23rd February 2018
 Accepted 26th March 2018

DOI: 10.1039/c8ra01611a

rsc.li/rsc-advances

Ag–K/MnO₂ nanorods as highly efficient catalysts for formaldehyde oxidation at low temperature

Suhong Lu,^a Xue Wang,^{a*} Qinyu Zhu,^a Canchang Chen,^a Xuefeng Zhou,^a Fenglin Huang,^a Kelun Li,^b Lulu He,^a Yanxiong Liu^a and Fanjue Pang^a

A series of Ag–K/MnO₂ nanorods with various molar ratios of K/Ag were synthesized by a conventional wetness incipient impregnation method. The as-prepared catalysts were used for the catalytic oxidation of HCHO. The Ag–K/MnO₂ nanorods with an optimal K/Ag molar ratio of 0.9 demonstrated excellent HCHO conversion efficiency of 100% at a low temperature of 60 °C. The structures of the samples were investigated by BET, TEM, SEM, XRD, H₂-TPR, O₂-TPD and XPS. The results showed that Ag–0.9K/MnO₂-r exhibited more facile reducibility and greatly abundant surface active oxygen species, endowing it with the best catalytic activity of the studied catalysts. This work provides new insights into the development of low-cost and highly efficient catalysts for the removal of HCHO.

1 Introduction

Formaldehyde (HCHO) is commonly released from building/decorative materials and unregulated indoor smoking; it is regarded as a major pollutant.^{1,2} It has been reported that long-term exposure to indoor air containing even a few ppm of HCHO threatens human health and causes health problems, such as nasal tumors, skin irritation, allergies, and decreased concentration.^{3,4} Thus, numerous technologies have been investigated to eliminate indoor emission of HCHO to satisfy stringent environmental regulations; these techniques include adsorption,⁵ photo-catalysis,⁶ plasma technology,⁷ and thermal catalytic oxidation.⁸

In recent years, complete oxidation of HCHO over heterogeneous catalysts has been considered to be the most promising strategy for indoor HCHO removal due to its properties of high efficiency and lack of pollution. Highly effective catalysts have been prepared to reduce HCHO, such as transition metal oxides^{9–11} and supported noble metals (Pt,^{12–15} Au,¹⁶ and Pd¹⁷). Generally, transition metal oxides can achieve complete oxidation of HCHO at very high temperatures (>100 °C). In contrast, supported noble metal catalysts such as Pt/TiO₂,¹⁸ Na-Pd/TiO₂ (ref. 19) and Au/Co₃O₄–CeO₂ (ref. 20) have been proved to have excellent catalytic activity at relatively low temperatures, even room temperature. However, the high cost of the supported noble metals limits their widespread application. Therefore, it is still a challenge to develop efficient and low cost catalysts.

On the basis of current research, Ag-supported catalysts, which are much less expensive than the abovementioned noble

metals, have been demonstrated to possess efficient low-temperature catalytic activities for HCHO oxidation. For example, the price of Pt per gram for H₂PtCl₆·6H₂O is about 20 times that of Ag per gram for AgNO₃ on the Sigma-Aldrich website. It was reported that complete oxidation of HCHO was obtained over Ag/MnO_x–CeO₂ catalysts at a temperature as low as 100 °C; the catalysts were synthesized by a deposition precipitation method.²¹ Ma *et al.*²² successfully prepared Ag/CeO₂ nanospheres by a one-step hydrothermal method which could achieve complete HCHO oxidation at temperatures above 110 °C under relatively high space velocity. Huang *et al.*²³ demonstrated that Ag nanoparticles-supported hollandite-type manganese oxide nanorods exhibited good activity for HCHO oxidation; complete conversion of HCHO was obtained at 110 °C. In order to improve the activity of Ag-supported catalysts, Li *et al.*²⁴ indicated that Ag/Fe–MnO_x possesses higher catalytic activity than Ag/MnO_x due to the enhanced interaction between Ag and the support. The conversion of HCHO was 100% at 90 °C. Qu *et al.*²⁵ reported a bimetallic AgCo/APTES@MCM-41 catalyst that could achieve complete oxidation of HCHO at temperatures as low as 90 °C because of the formation of strong metal–metal interactions between Ag and Co. Bai *et al.*²⁶ demonstrated that K–Ag/Co₃O₄ displayed complete conversion of HCHO at 70 °C due to additional surface OH[–] provided by K⁺ ions. However, the performance of Ag-supported catalysts at low temperature still requires improvement in comparison with other noble metal catalysts.

Due to its remarkable oxygen storage ability, manganese oxide has attracted much attention and is regarded as an effective catalyst for the catalytic oxidation of HCHO. For example, Torres *et al.*²⁷ fabricated mesoporous MnO_x catalysts and observed their good catalytic activities for the complete oxidation of HCHO; using these catalysts, complete conversion

^aCollege of Chemistry and Chemical Engineering, Xi'an Shiyou University, Xi'an 710065, China. E-mail: lusuhong@xsyu.edu.cn

^bShaanxi Coal and Chemical Technology Institute Co., Ltd, Xi'an 710070, China



of HCHO was achieved at 145 °C. Zhou *et al.*²⁸ prepared porous cellulose-supported MnO₂ nanosheet catalysts and observed their excellent performance in the catalytic oxidation of HCHO at a temperature of 140 °C. Previous literature studies have reported that manganese oxides with various morphologies showed obvious differences in catalytic performance.²⁹ For example, flower-like manganese oxide nanospheres (α -MnO₂) outperformed other crystalline manganese oxides below 120 °C for the oxidation of HCHO.³⁰ Studying the preparation and catalysis of materials for rod-like tetragonal α -MnO₂, flower-like hexagonal ϵ -MnO₂, and dumbbell-like tetragonal β -MnO₂, Shi *et al.*³¹ discovered that the catalytic activity decreased in the order of α -MnO₂ > ϵ -MnO₂ > β -MnO₂. To the best of our knowledge, the catalytic application of Ag/MnO₂ nanorods for the catalytic oxidation of HCHO has not been reported. Moreover, it has been well acknowledged that alkali metals can serve as electronic or textural promoters for catalysis.^{19,32} The addition of alkali metals (Li, Na and K) to Pt/TiO₂ catalysts resulted in remarkable enhancements of their performance in HCHO oxidation.³³ It was further found that addition of K has an obvious enhancing effect on Ag/Co₃O₄ catalysts for HCHO oxidation.²⁶

Therefore, in this work, MnO₂ nanorods were synthesized by a hydrothermal preparation method and Ag-K/MnO₂ nanorods were prepared by a conventional wetness incipient impregnation method. These catalysts were applied for the catalytic oxidation of HCHO. The catalysts were characterized by BET, TEM, SEM, XRD, H₂-TPR and O₂-TPD. It is proposed that the abundant surface oxygen species and low-temperature reducibility enhanced the catalytic oxidation activity of the Ag-K/MnO₂ nanorods.

2 Experimental

Materials

KMnO₄, Mn₅O₄, AgNO₃ and KNO₃ (analytically pure reagents) were obtained from Sinopharm Chemical Reagent Co., Ltd. The reagents were used as received without further purification.

Preparation of catalysts

The MnO₂ nanorods were synthesized by a hydrothermal method similar to previous studies.^{31,34} 16 mmol of KMnO₄ and 6 mmol of MnSO₄ precursor were dissolved in 160 mL of deionized water and then stirred for 1 h to form a homogeneous solution. Subsequently, the mixture was transferred into a stainless steel autoclave for thermal treatment at 160 °C for 12 h. After cooling, the resulting precipitate was collected by filtration, washed with deionized water to remove any possible residual reactants and dried at 60 °C for 24 h. The acquired powder was calcined in a muffle oven at 300 °C for 4 h with a heating rate of 1 °C min⁻¹, thus affording the final MnO₂ nanorods (designed as MnO₂-r).

Ag-K/MnO₂ nanorods with different molar ratios (K/Ag = 0.5, 0.9, 1.3) were prepared by a conventional wetness incipient impregnation method, and the general steps were as follows: 1 g MnO₂-r was dispersed in 40 mL deionized water under vigorous

stirring for 30 min, and then the appropriate amounts of AgNO₃ and KNO₃ solution were added dropwise. After that, the resulting suspension was stirred at room temperature for 24 h and then evaporated at 80 °C with continuous stirring. The obtained powder was dried at 80 °C for 12 h. The amount of Ag in the final catalyst was 0.1 wt%, measured *via* ICP-AES. The as-prepared samples were thus represented as Ag-xK/MnO₂-r (x indicates the molar ratio of K/Ag). Ag/MnO₂-r was also synthesized by a similar process to that described above.

Characterization

The Ag contents of the prepared catalysts were determined by inductively coupled plasma-atomic emission spectroscopy (ICP-AES, Vista-MPX, Varian).

Nitrogen adsorption and desorption isotherms were measured at -196 °C using a Micromeritics apparatus (ASAP2020HD88). The specific surface areas were computed by applying the Brunauer-Emmett-Teller (BET) method. The pore size distribution was estimated from the desorption branch of the isotherms using the BJH model. All samples were outgassed under vacuum at 250 °C for 4 h prior to analysis.

The morphologies of the products were determined by scanning electron microscopy (SEM, America FET Quanta 600 FEG) and transmission electron microscopy (TEM, Tecnai G2 F20).

Powder X-ray diffraction (XRD) measurements of the catalysts were carried out using a Panalytical Empyrean X-ray diffractometer with Cu-K α radiation ($\lambda = 0.154\ 056\ \text{nm}$) at 40 kV and 30 mA with a scanning speed of 2° min⁻¹ from 10.0° to 80.0°.

The temperature programmed reduction (H₂-TPR) equipment consisted of a thermal conductivity detector (TCD) connected to a flow-control system and a programmed heating unit. About 50 mg of catalyst was used in each measurement. The reduction agent of 10% H₂/N₂ was introduced with a flow rate of 60 mL min⁻¹; each sample was heated to 650 °C from 40 °C at a rate of 10 °C min⁻¹.

Oxygen temperature-programmed desorption (O₂-TPD) tests were conducted using the same equipment as the H₂-TPR tests. Prior to each run, 60 mg of sample was loaded and pretreated with 21 vol% O₂/N₂ (30 mL min⁻¹) at 300 °C for 1 h, then pre-reduced in a stream of 10 vol% H₂/N₂ flow at 200 °C for 1 h with a heating rate of 10 °C min⁻¹. After cooling to 65 °C in the same flow, the adsorption of O₂ was operated in a flow of 21% O₂/N₂ at a rate of 20 mL min⁻¹ for 1 h at 65 °C. Finally, the catalyst was heated from 65 °C to 500 °C at a constant heating rate of 10 °C min⁻¹ in a flow of He (60 mL min⁻¹). The desorption of oxygen was calculated from the signal of a TCD detector.

X-ray photoelectron spectroscopy (XPS) was performed on a Thermo Scientific K-Alpha instrument using MgK α radiation (1653.6 eV) at a beam power of 250 W. The binding energy of C 1s (284.6 eV) was used as the internal standard.

Catalytic activity tests

The catalytic activity tests of the as-prepared catalysts for HCHO oxidation were performed in a fixed-bed reactor under



Table 1 Physical parameters of Ag-xK/MnO₂-r with Ag/MnO₂-r and MnO₂-r

Catalyst	S_{BET} (m ² g ⁻¹)	Pore diameter (nm)	Pore volume (cm ³ g ⁻¹)	Ag mass loading ^a (wt%)
MnO ₂ -r	102.1	12.2	0.37	—
Ag/MnO ₂ -r	71.2	15.2	0.33	0.11
Ag-0.5K/MnO ₂ -r	68.1	15.9	0.32	0.13
Ag-0.9K/MnO ₂ -r	60.8	18.1	0.30	0.10
Ag-1.3K/MnO ₂ -r	45.9	19.2	0.25	0.12

^a Calculated from the ICP data.

atmospheric pressure. Before the catalytic activity tests, the Ag-K/MnO₂ nanorods (50 mg) were pretreated with 21 vol% O₂/N₂ at 300 °C for 1 h and then cooled to 200 °C. The gas was switched to 10 vol% H₂/N₂ for 1 h at a temperature of 200 °C. After that, the temperature was cooled to 25 °C. Gaseous HCHO was generated by flowing 21% O₂/N₂ over paraformaldehyde in a thermostatic water bath. The standard feed gas containing 300 ppm of HCHO, 21% O₂ and N₂ comprising the balance was introduced into the reactor. The total flow rate was 30 mL min⁻¹ in a mass space velocity of 36 000 mL g_{cat}⁻¹ h⁻¹. The analyses of the products, such as CO and CO₂, were executed using a gas chromatograph equipped with a hydrogen flame ionization detector (FID) and Ni catalyst convertor. No carbon-containing compounds other than CO₂ in the products were detected for the tested catalysts. Thus, HCHO conversion was calculated as follows:

$$\text{HCHO conversion(\%)} = \frac{[\text{CO}_2]_{\text{out}}}{[\text{HCHO}]_{\text{in}}} \times 100$$

where [CO₂]_{out} and [HCHO]_{in} in the formula correspond to the CO₂ concentration in the products and the concentration of HCHO in the gas flow, respectively.

3 Results and discussion

N₂ adsorption and desorption

The specific surface areas, pore diameters and pore volumes of the Ag-xK/MnO₂-r samples, along with those of Ag/MnO₂-r and MnO₂-r, are listed in Table 1. Among all the samples, pure MnO₂-r possessed the highest surface area (102.1 m² g⁻¹) and pore volume (0.37 cm³ g⁻¹). However, the surface area and pore volume showed remarkable decreases after the addition of Ag and K; especially, when the molar ratio of K/Ag was 1.3, these values were 45.9 m² g⁻¹ and 0.25 cm³ g⁻¹, respectively, for Ag-1.3K/MnO₂-r. Meanwhile, the average pore diameters of these samples increased from 12.2 to 19.2 nm, which indicates that Ag and K nanoparticles formed on the surface and blocked the small pores.^{22,24}

SEM and TEM images

The morphologies of the MnO₂-r and Ag-0.9K/MnO₂-r samples were investigated using SEM (Fig. 1). It was observed that the MnO₂-r sample derived hydrothermally at 160 °C displayed a rod-like morphology, in good agreement with previous reports for MnO₂ in the literature.^{31,34} The MnO₂-r samples had

diameters of about 80 nm and lengths ranging from 2 to 5 μm. Moreover, the Ag-0.9K/MnO₂-r catalyst also demonstrated a rod-like morphology similar to that of MnO₂-r.

XRD patterns

Fig. 2 displays the XRD patterns of the as-prepared Ag-xK/MnO₂-r catalysts, Ag/MnO₂-r and MnO₂-r. It can be seen that all the samples consisted of single-phase α-MnO₂ (JCPDS PDF 44-0141). However, no feature peaks corresponding to the Ag and K species could be found in the XRD patterns; the absence of peaks related to Ag and K species probably resulted from the low loading content and high dispersion of Ag and K with small diameters.^{22,35}

H₂-TPR

Fig. 3 illustrates the H₂-TPR profiles of the pure MnO₂-r, Ag/MnO₂-r and Ag-xK/MnO₂-r samples. For the sample of pure MnO₂-r, a strong reduction peak was observed in the temperature range from 149–450 °C with an overlap peak centered at 327 °C; this can be assigned to the combined reduction of MnO₂/Mn₂O₃ to Mn₃O₄ and of Mn₃O₄ to MnO. This is similar to the observation of Li *et al.*³⁵ For Ag/MnO₂-r, a shoulder peak was centered at 306 °C and a strong broad reduction peak appeared between 324 °C and 432 °C. Obviously, the addition of Ag to MnO₂-r dramatically shifted the reduction temperatures to lower regions, indicating the occurrence of metal-support interactions between Ag and MnO₂-r. It has been reported that the reducibility of a material can be significantly improved by noble metal loading, which is often interpreted in terms of the activation and spillover of hydrogen from Ag atoms to MnO₂-r.²⁴ The H₂ spillover phenomenon showed an ability to adsorb, activate, and migrate hydrogen. Activated hydrogen on the Ag surface can readily migrate to the surface of the MnO₂-r support and participate in the reduction reaction.

Compared with the reduction features of Ag/MnO₂-r, the reduction peaks of the Ag-xK/MnO₂-r samples shifted towards lower temperatures; this shift was most noticeable for the Ag-0.9K/MnO₂-r catalyst. Moreover, without changes in its peak pattern, the reduction temperature of Ag-0.9K/MnO₂-r showed the best low-temperature reducibility, which was 14 °C and 3 °C lower than those of Ag-0.5K/MnO₂-r and Ag-1.3K/MnO₂-r, respectively. A similar enhancing effect of K addition on catalytic reducibility was studied previously. Bai *et al.*²⁶ reported that the presence of K⁺ enhanced the reducibility of K-Ag/Co₃O₄ due



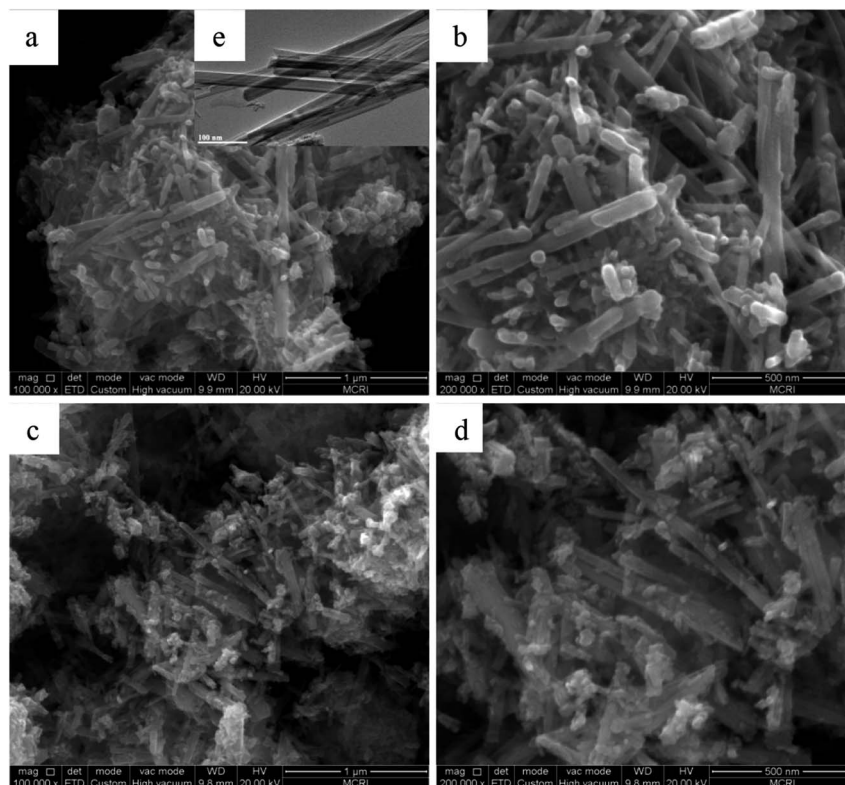


Fig. 1 SEM images of (a and b) MnO₂-r and (c and d) Ag-0.9K/MnO₂-r. TEM image of (e) MnO₂-r.

to the stronger metal-support interaction. They also found that the presence of K⁺ ions increased the number of Co³⁺ cations. Pan *et al.*³⁶ indicated that acid-treated MnO_x samples showed the best redox properties due to the higher oxidation states of the manganese ions, which appeared to be responsible for their enhanced catalytic properties in HCHO oxidation. Hence, it is reasonable to speculate that the addition of K⁺ improved the low-temperature reducibility and higher oxidation states of manganese ions of the Ag-0.9K/MnO₂-r sample in this study. The sufficient manganese cations implied that the oxygen species in the Ag-0.9K/MnO₂-r sample could be more readily activated and that they migrated and improved the catalytic performance of HCHO oxidation (see Fig. 5).³⁷

In addition, previous studies reported that catalyst reducibility is related to oxygen vacancies. Catalysts with better reducibility can yield more oxygen vacancies.^{24,38} Thus, Ag-0.9K/MnO₂-r could produce more oxygen vacancies with the assistance of K than Ag/MnO₂-r. Gas-phase oxygen molecules could be readily adsorbed in the oxygen vacancies, forming active oxygen species.^{20,39} This result is in agreement with the O₂-TPD results (see Fig. 4).

O₂-TPD

O₂-TPD experiments over the pure MnO₂-r, Ag/MnO₂-r, Ag-0.5K/MnO₂-r, Ag-0.9K/MnO₂-r and Ag-1.3K/MnO₂-r catalysts were carried out to determine the mobility of oxygen species, as

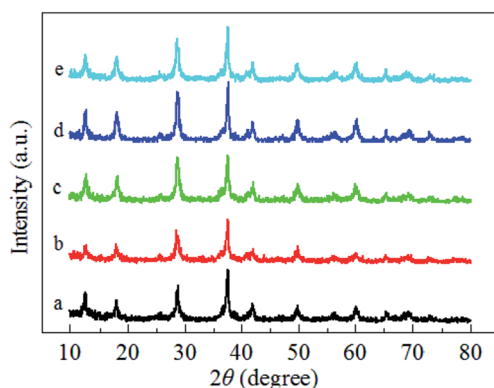


Fig. 2 XRD patterns of (a) MnO₂-r, (b) Ag/MnO₂-r, (c) Ag-0.5K/MnO₂-r, (d) Ag-0.9K/MnO₂-r and (e) Ag-1.3K/MnO₂-r.

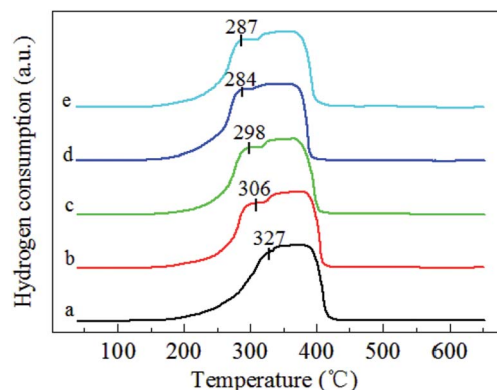


Fig. 3 H₂-TPR profiles of (a) MnO₂-r, (b) Ag/MnO₂-r, (c) Ag-0.5K/MnO₂-r, (d) Ag-0.9K/MnO₂-r and (e) Ag-1.3K/MnO₂-r.



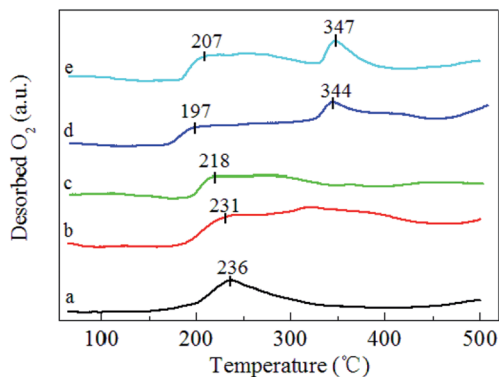


Fig. 4 O_2 -TPD profiles of (a) MnO_2 -r, (b) Ag/MnO_2 -r, (c) $Ag-0.5K/MnO_2$ -r, (d) $Ag-0.9K/MnO_2$ -r and (e) $Ag-1.3K/MnO_2$ -r.

shown in Fig. 4. According to the literature,^{40,41} the desorption oxygen species of the oxides can be generally ranked in the sequence of oxygen molecule (O_2) > oxygen molecule anion (O_2^-) > oxygen anion (O^-) > lattice oxygen (O^{2-}). The desorption of O_2 can occur at a very low temperature (<200 °C), while surface active oxygen species such as O_2^- and O^- can desorb between 200 °C and 400 °C and the lattice oxygen from MnO_2 can desorb above 400 °C.^{20,42} As shown in Fig. 4, for pure MnO_2 -r, the large peak between 150 °C and 350 °C can be assigned to O_2 , O_2^- and O^- desorption. After the introduction of Ag, significant increases of the desorption peaks in the range of 175–400 °C were noted for Ag/MnO_2 -r. Moreover, the desorption peak positions shifted to a lower temperature range. These data suggest that the presence of Ag is beneficial to produce surface active oxygen in the Ag/MnO_2 -r catalyst. Similar phenomena were observed by Huang *et al.*⁴⁰ and Ma *et al.*²² Huang *et al.*⁴⁰ observed that the formation of Ru–O–Ce in Ru/CeO₂ can remarkably increase the amount of oxygen vacancies (a reflection of the surface active oxygen). Ma *et al.*²² observed that the presence of Ag in Ag/CeO₂ nanospheres facilitates the generation of much more surface active oxygen desorption during the O_2 -TPD process.

With the addition of K, the original desorption temperature of the surface active oxygen species shifted to lower temperatures for $Ag-xK/MnO_2$ -r in comparison with those of Ag/MnO_2 -r. For example, the desorption of oxygen from the surface active oxygen species appeared at 218 °C on $Ag-0.5K/MnO_2$ -r, 197 °C on $Ag-0.9K/MnO_2$ -r and 207 °C on $Ag-1.3K/MnO_2$ -r. This indicates that the $Ag-0.9K/MnO_2$ -r catalyst most readily desorbed the surface active oxygen species. This is in good accordance with the TPR measurements (see Fig. 3). As reported,^{43,44} the oxygen desorption temperature of catalytic materials is related to their catalytic oxidation activity. Lower starting oxygen desorption temperatures may be significantly favorable for high activity in HCHO oxidation due to the abundance of active surface oxygen species that can readily participate in the catalytic oxidation reaction.⁴⁵ Here, it can be expected that $Ag-0.9K/MnO_2$ -r will possess excellent catalytic performance for HCHO oxidation at low temperature.

XPS spectra

The XPS spectra of the MnO_2 -r, Ag/MnO_2 -r and $Ag-0.9K/MnO_2$ -r samples are displayed in Fig. 5. As shown in Fig. 5A, the two peaks of binding energy around 368.0 eV and 375.0 eV can be assigned to the escape of electrons from the $3d_{5/2}$ and $3d_{3/2}$ core levels. The Ag $3d_{5/2}$ binding energies of Ag/MnO_2 -r and $Ag-0.9K/MnO_2$ -r are 368.3 eV, reflecting the metallic state. The Ag atoms of $Ag-0.9K/MnO_2$ -r have a relatively higher electronic density of states than those of Ag/MnO_2 -r, originating from the different density of states of the Ag d orbitals.⁴⁶ In the Mn 2p spectra (Fig. 5B), two obvious peaks were found. The splitting energy of the Mn 2p peak (11.8 eV) approached that of Mn^{4+} , in accord with the energy separation between Mn $2p_{3/2}$ and Mn $2p_{1/2}$ reported previously.³⁷ In comparison with MnO_2 -r, apparent upshifts of the Mn $2p_{3/2}$ and Mn $2p_{1/2}$ peaks occurred for Ag/MnO_2 -r and $Ag-0.9K/MnO_2$ -r, which indicates that the addition of K increased the number of Mn^{4+} ions. Fig. 5C displays that K 2p has two components at BE = 291.8 and 295.0 eV, which demonstrates the presence of K^+ ions.²⁶ The BE of O 1s in Fig. 5D shows two surface oxygen species by deconvolution of the O 1s spectra. A shoulder on a higher BE (532.3 eV) can be assigned to adsorbed oxygen or surface hydroxyl species, while the main peak at about 529.9 eV can be attributed to surface lattice oxygen atoms. Moreover, discernible shifts to a lower binding energy for Ag/MnO_2 -r and $Ag-0.9K/MnO_2$ -r were observed in comparison to MnO_2 -r, accounting for an increase in their negative charge.⁴⁶ It has been reported that increased surface adsorbed oxygen and hydroxyl species play crucial roles to promote catalytic activity for HCHO oxidation.^{26,46} From Fig. 5D, it can be observed that the intensity of the higher BE (531.8 eV) of the $Ag-0.9K/MnO_2$ -r catalyst is the strongest, implying that it contains more surface active oxygen. The result is in good agreement with the O_2 -TPD analysis (Fig. 4).

Catalytic activity

Formaldehyde conversion was measured as a function of reaction temperature over the $Ag-xK/MnO_2$ -r catalysts together with Ag/MnO_2 -r and pure MnO_2 -r. As shown in Fig. 6, pure MnO_2 -r afforded HCHO conversion of less than 89% in the temperature range investigated. With 0.1% Ag addition, 85.4% HCHO conversion was tested at 60 °C over Ag/MnO_2 -r. Obviously, the catalytic performance of Ag/MnO_2 -r was promoted by the presence of K^+ ions. $Ag-0.5K/MnO_2$ -r achieved 92.7% HCHO conversion at 60 °C. With increasing K^+ ion content, $Ag-0.9K/MnO_2$ -r showed the highest performance, with 100% HCHO conversion at 60 °C. The conversion of HCHO slightly decreased with further increase of the K^+ ion loading amount. 99.6% conversion of HCHO was obtained at 60 °C over $Ag-1.3K/MnO_2$ -r. The results revealed that the catalytic activity followed the decreasing order of $Ag-0.9K/MnO_2$ -r > $Ag-1.3K/MnO_2$ -r > $Ag-0.5K/MnO_2$ -r > Ag/MnO_2 -r > MnO_2 -r. The optimal molar ratio of K/Ag was 0.9. Thus, the addition of K enhanced the catalytic activity for HCHO oxidation, which is similar to Na or K-promoted catalysts.^{19,26} It is well known that the presence of K^+ ions provides surface OH^- species, which may play an important role in the catalytic oxidation of HCHO. Nie *et al.*⁴⁷



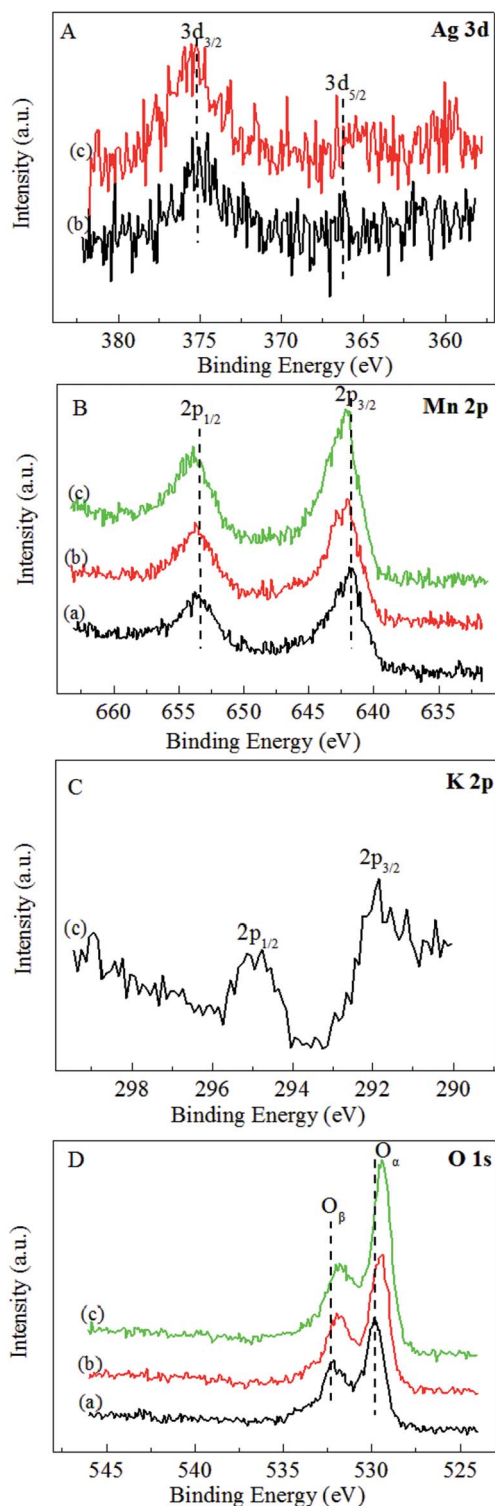


Fig. 5 XPS spectra of (a) $\text{MnO}_2\text{-r}$, (b) $\text{Ag}/\text{MnO}_2\text{-r}$ and (c) $\text{Ag-0.9K}/\text{MnO}_2\text{-r}$. (A) Ag 3d, (B) Mn 2p, (C) K 2p and (D) O 1s.

investigated the reactivity of Pt/TiO_2 catalysts with the assistance of NaOH toward HCHO oxidation; they found that the catalyst showed higher activity than that without NaOH due to the introduction of additional surface hydroxyl groups (OH^-), which can favor HCHO adsorption *via* strong hydrogen-bond

interactions between HCHO and OH^- present on TiO_2 . Bai *et al.*²⁶ prepared 3D $\text{K-Ag}/\text{Co}_3\text{O}_4$ catalyst and discovered that the addition of K^+ ions obviously promoted the catalytic performance for HCHO oxidation because of the surface OH^- species provided by K^+ ions. Yang *et al.*⁴⁸ reported that the superior performance of $\text{PtNi}(\text{OH})_x/\gamma\text{-Al}_2\text{O}_3$ could be attributed to the preferred hydroxyl-facilitated HCHO oxidation pathway through formate oxidation by the abundant associated hydroxyl groups near the Pt active sites.

The Ag-based catalysts currently being applied for HCHO oxidation are summarized in Table 2. It can be clearly seen that the $\text{Ag-0.9K}/\text{MnO}_2\text{-r}$ catalysts show the best catalytic activities at the lowest temperature.

Catalytic stability of the $0.9\text{K}/\text{MnO}_2\text{-r}$ samples is very important for HCHO decomposition; therefore, cycle and stability tests were carried out at $60\text{ }^\circ\text{C}$ for 60 h with a WHSV of $36\ 000\ \text{mL g}_{\text{cat}}^{-1}\ \text{h}^{-1}$, as displayed in Fig. 7 and 8. No noticeable decrease in the catalytic activity was found during five on/off cycles. As shown in Fig. 7, the catalytic activity of $\text{Ag-0.9K}/\text{MnO}_2\text{-r}$ showed no obvious change up to the end of the experiments, indicating the outstanding stability and efficiency of this catalyst for HCHO removal.

Generally, it is well acknowledged that the surface area, surface active oxygen species, and reducibility are crucial parameters influencing the catalytic performance of a catalyst.⁴⁹ Notably, the $\text{Ag-xK}/\text{MnO}_2\text{-r}$ samples, which have slightly smaller specific surface areas, exhibited higher catalytic activity than $\text{Ag}/\text{MnO}_2\text{-r}$; this was also mentioned in previous reports.⁵⁰ This observation implied that the specific surface area was not the decisive factor for HCHO oxidation. In addition to the specific surface area, better low-temperature reducibility and abundant surface active oxygen species are significantly beneficial for enhanced catalytic activity. In our case, by comparing the activity data and characterization results, it can be seen that there are obvious relationships of the reducibility (Fig. 3) and surface active oxygen species (Fig. 4) with the catalytic activity (Fig. 5). The decreasing order of reducibility and oxygen desorption is $\text{Ag-0.9K}/\text{MnO}_2\text{-r} > \text{Ag-1.3K}/\text{MnO}_2\text{-r} > \text{Ag-0.5K}/\text{MnO}_2\text{-r} > \text{Ag}/\text{MnO}_2\text{-r} > \text{MnO}_2\text{-r}$, which is the same as the

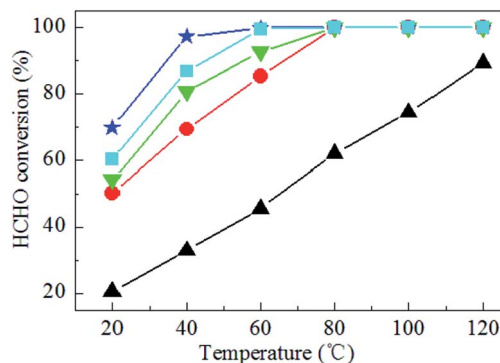


Fig. 6 HCHO conversion over (▲) $\text{MnO}_2\text{-r}$, (●) $\text{Ag}/\text{MnO}_2\text{-r}$, (▼) $\text{Ag-0.5K}/\text{MnO}_2\text{-r}$, (★) $\text{Ag-0.9K}/\text{MnO}_2\text{-r}$ and (■) $\text{Ag-1.3K}/\text{MnO}_2\text{-r}$ catalysts. Reaction conditions: 300 ppm HCHO, 21 vol% O_2 and N_2 (balance). The total flow rate and WHSV are $30\ \text{mL min}^{-1}$ and $36\ 000\ \text{mL g}_{\text{cat}}^{-1}\ \text{h}^{-1}$, respectively.



Table 2 Catalytic activities of Ag-based catalysts in the references and in this work

Catalyst	Reaction conditions	T_{100} ($^{\circ}\text{C}$)	Ref.
Ag/MnO _x -CeO ₂	580 ppm HCHO, 18% O ₂ , 30 000 mL g _{cat} ⁻¹ h ⁻¹	100	21
Ag/CeO ₂ nanosphere	810 ppm HCHO, 20% O ₂ , 84 000 h ⁻¹	110	22
Ag/Fe _{0.1} -MnO _x	230 ppm HCHO, 21% O ₂ , 30 000 mL g _{cat} ⁻¹ h ⁻¹	90	24
AgCo/APTES@MCM-41	500 ppm HCHO, 20% O ₂ , 9000 mL g _{cat} ⁻¹ h ⁻¹	90	25
3D K-Ag/Co ₃ O ₄	100 ppm HCHO, 20% O ₂ , 30 000 h ⁻¹	70	26
Ag-0.9K/MnO ₂ -r	300 ppm HCHO, 21% O ₂ , 36 000 mL g _{cat} ⁻¹ h ⁻¹	60	Herein

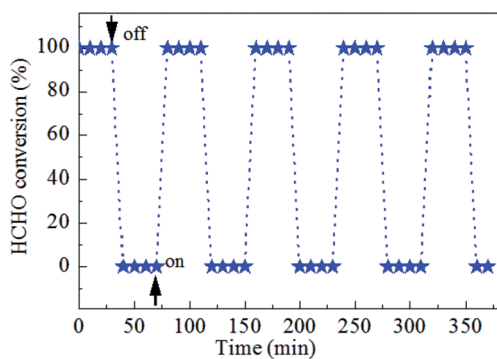


Fig. 7 Cycle test of Ag-0.9K/MnO₂-r for HCHO oxidation at 60 °C under the reaction conditions of 300 ppm HCHO, 21 vol% O₂ and N₂ (balance).

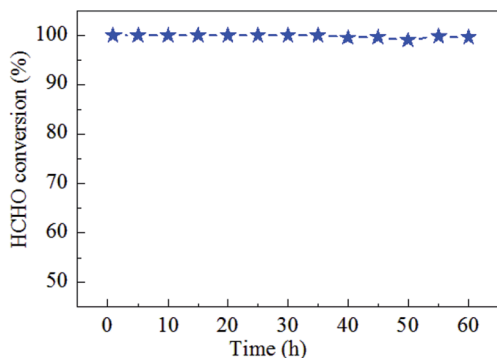


Fig. 8 Stability test of Ag-0.9K/MnO₂-r for HCHO oxidation at 60 °C with the reaction conditions of 300 ppm HCHO, 21 vol% O₂ and N₂ (balance).

sequence of the HCHO catalytic oxidation tests. Research found that the oxidation of HCHO followed a redox reaction mechanism;⁴⁶ an efficient catalyst requires good reducibility. Simultaneously, the enriched surface active oxygen species generated on the catalyst interface can take part in the reaction of HCHO at low temperature.^{20,51} It is reasonable to deduce that the good performance of the catalyst is associated with its better low-temperature reducibility and higher number of surface active oxygen species.

4 Conclusions

In summary, Ag-K/MnO₂ nanorods have been demonstrated as a new and high-performance catalyst for efficient catalytic

oxidation of HCHO. The molar ratio of K/Ag greatly influenced the catalytic activity of the Ag-K/MnO₂ nanorods, and the optimal K/Ag ratio was found to be 0.9. It was observed that Ag-0.9K/MnO₂-r presented outstanding catalytic activity; this catalyst achieved 100% HCHO conversion at a low temperature of 60 °C. The excellent performance of Ag-0.9K/MnO₂-r resulted from its facile reducibility and highly abundant surface active oxygen species. This work provides new insight into the development of low-cost and high-efficiency catalysts for low-temperature catalytic oxidation of HCHO.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

This work was sponsored financially by the Science & Technology Plan Project of Xi'an City (No. 2017081CG/RC044 (XASY006)), the Special Scientific Research of Shaanxi Educational Committee (No. 17JK0608), the College Students' Innovative Entrepreneurial Training Program of Xi'an Shiyou University (No. 201610705027 and YCS17221013) and Shaanxi Province (No. 2017107051486), and the National Nature Science Foundation of China (No. 21606177).

References

- B. Y. Bai, Q. Qiao, J. H. Li and J. M. Hao, *Chin. J. Catal.*, 2016, **37**, 102–122.
- L. H. Nie, J. G. Yu, M. Jaroniec and F. F. Tao, *Catal. Sci. Technol.*, 2016, **6**, 3649–3669.
- J. Q. Torres, S. Royer, J. P. Bellat, J. M. Giraudon and J. F. Lamonier, *ChemSusChem*, 2013, **6**, 578–592.
- H. M. Guo, M. Li, X. Liu, C. G. Meng, R. Linguerri, Y. Han and G. Chambaud, *Catal. Sci. Technol.*, 2017, **7**, 2012–2021.
- L. R. Wu, Z. Y. Qin, L. X. Zhang, T. Meng, F. Yu and J. Ma, *New J. Chem.*, 2017, **41**, 2527–2533.
- L. K. Gao, W. T. Gan, S. L. Xiao, X. X. Zhan and J. Li, *RSC Adv.*, 2015, **5**, 52985–52992.
- X. X. Feng, H. X. Liu, C. He, Z. X. Shen and T. B. Wang, *Catal. Sci. Technol.*, 2018, **8**, 936–954.
- H. B. Huang, Y. Xu, Q. Y. Feng and D. Y. C. Leung, *Catal. Sci. Technol.*, 2015, **5**, 2649–2669.
- Z. Wang, W. Z. Wang, L. Zhang and D. Jiang, *Catal. Sci. Technol.*, 2016, **6**, 3845–3853.



- 10 Z. J. Dai, X. W. Yu, C. Huang, M. Li, J. F. Su, Y. P. Guo, H. Xu and Q. F. Ke, *RSC Adv.*, 2016, **6**, 97022–97029.
- 11 Y. X. Wu, M. Ma, B. Zhang, Y. H. Gao, W. P. Lu and Y. C. Guo, *RSC Adv.*, 2016, **6**, 102127–102133.
- 12 W. Y. Cui, X. L. Yuan, P. Wu, B. Zheng, W. X. Zhang and M. J. Jia, *RSC Adv.*, 2015, **5**, 104330–104336.
- 13 J. W. Ye, B. Cheng, S. Wageh, A. A. Al-Ghamdi and J. G. Yu, *RSC Adv.*, 2016, **6**, 34280–34287.
- 14 L. H. Nie, J. Wang and J. G. Yu, *RSC Adv.*, 2017, **7**, 21389–21397.
- 15 G. J. Kim, S. M. Lee, S. C. Hong and S. S. Kim, *RSC Adv.*, 2018, **8**, 3626–3636.
- 16 G. N. Li and L. Li, *RSC Adv.*, 2015, **5**, 36428–36433.
- 17 Y. B. Li, C. B. Zhang, H. He, J. H. Zhang and M. Chen, *Catal. Sci. Technol.*, 2016, **6**, 2289–2295.
- 18 C. B. Zhang, H. He and K. Tanaka, *Appl. Catal., B*, 2006, **65**, 37–43.
- 19 C. B. Zhang, Y. B. Li, Y. F. Wang and H. He, *Environ. Sci. Technol.*, 2014, **48**, 5816–5822.
- 20 C. Y. Ma, D. H. Wang, W. J. Xue, B. J. Dou, H. L. Wang and Z. P. Hao, *Environ. Sci. Technol.*, 2011, **45**, 3628–3634.
- 21 X. F. Tang, J. L. Chen, Y. G. Li, Y. Li, Y. D. Xu and W. J. Shen, *Chem. Eng. J.*, 2006, **118**, 119–125.
- 22 L. Ma, D. S. Wang, J. H. Li, B. Y. Bai, L. X. Fu and Y. D. Li, *Appl. Catal., B*, 2014, **148–149**, 36–43.
- 23 Z. W. Huang, X. Gu, Q. Q. Cao, P. P. Hu, J. M. Hao, J. H. Li and X. F. Tang, *Angew. Chem.*, 2012, **124**, 4274–4279.
- 24 D. D. Li, G. L. Yang, P. L. Li, J. L. Wang and P. Y. Zhang, *Catal. Today*, 2016, **277**, 257–265.
- 25 Z. P. Qu, D. Chen, Y. H. Sun and Y. Wang, *Appl. Catal., A*, 2014, **487**, 100–109.
- 26 B. Y. Bai and J. H. Li, *ACS Catal.*, 2014, **4**, 2753–2762.
- 27 J. Q. Torres, J. M. Giraudon and J. F. Lamonier, *Catal. Today*, 2011, **176**, 277–280.
- 28 L. Zhou, J. H. He, J. Zhang, Z. C. He, Y. C. Hu, C. B. Zhang and H. He, *J. Phys. Chem. C*, 2011, **115**, 16873–16878.
- 29 S. C. Kim and W. G. Shim, *Appl. Catal., B*, 2010, **98**, 180–185.
- 30 L. Zhou, J. Zhang, J. H. He, Y. C. Hu and H. Tian, *Mater. Res. Bull.*, 2011, **46**, 1714–1722.
- 31 F. J. Shi, F. Wang, H. X. Dai, J. X. Dai, J. G. Deng, Y. X. Liu, G. M. Bai, K. M. Ji and C. T. Au, *Appl. Catal., A*, 2012, **433–434**, 206–213.
- 32 X. L. Zhu, M. Shen, L. L. Lobban and R. G. Mallinson, *J. Catal.*, 2011, **278**, 123–132.
- 33 C. B. Zhang, F. D. Liu, Y. P. Zhai, H. Ariga, N. Yi, Y. C. Liu, K. Asakura, M. Flytzani-Stephanopoulos and H. He, *Angew. Chem., Int. Ed.*, 2012, **51**, 9628–9632.
- 34 J. Zhou, L. F. Qin, W. Xiao, C. Zeng, N. Li, T. Lv and H. Zhu, *Appl. Catal., B*, 2017, **207**, 233–243.
- 35 J. M. Li, Z. P. Qu, Y. Qin and H. Wang, *Appl. Surf. Sci.*, 2016, **385**, 234–240.
- 36 Y. M. Pan, Z. S. Mei, Z. H. Yang, W. X. Zhang, B. Pei and H. X. Yao, *Chem. Eng. J.*, 2014, **242**, 397–403.
- 37 X. F. Tang, Y. G. Li, X. M. Huang, Y. D. Xu, H. Q. Zhu, J. G. Wang and W. J. Shen, *Appl. Catal., B*, 2006, **62**, 265–273.
- 38 Q. Y. Liu, Y. W. Bie, S. B. Qiu, Q. Zhang, J. Sainio, T. J. Wang, L. L. Ma and J. Lehtonen, *Appl. Catal., B*, 2014, **147**, 236–245.
- 39 B. C. Liu, Y. Liu, C. Y. Li, W. T. Hu, P. Jing, Q. Wang and J. Zhang, *Appl. Catal., B*, 2012, **127**, 47–58.
- 40 H. Huang, Q. G. Dai and X. Y. Wang, *Appl. Catal., B*, 2014, **158–159**, 96–105.
- 41 T. Cai, H. Huang, W. Deng, Q. G. Dai, W. Liu and X. Y. Wang, *Appl. Catal., B*, 2015, **166–167**, 393–405.
- 42 L. Xue, C. B. Zhang, H. He and Y. Teraoka, *Appl. Catal., B*, 2007, **75**, 167–174.
- 43 C. Y. Ma, Z. Mu, J. J. Li, Y. G. Jin, J. Cheng, G. Q. Lu, Z. P. Hao and S. Z. Qiao, *J. Am. Chem. Soc.*, 2010, **132**, 2608–2613.
- 44 Z. P. Hao, D. Y. Cheng, Y. Guo and Y. H. Liang, *Appl. Catal., B*, 2011, **33**, 217–222.
- 45 S. S. Sun, D. S. Mao and J. Yu, *J. Rare Earths*, 2015, **33**, 1268–1274.
- 46 P. P. Hu, Z. Amghouz, Z. W. Huang, F. Xu, Y. X. Chen and X. F. Tang, *Environ. Sci. Technol.*, 2015, **49**, 2384–2390.
- 47 L. H. Nie, J. G. Yu, X. Y. Li, B. Cheng, G. Liu and M. Jaroniec, *Environ. Sci. Technol.*, 2013, **47**, 2777–2783.
- 48 T. F. Yang, Y. Huo, Y. Liu, Z. B. Rui and H. B. Ji, *Appl. Catal., B*, 2017, **200**, 543–551.
- 49 Y. S. Xia, H. X. Dai, H. Y. Jiang, L. Zhang, J. G. Deng and Y. X. Liu, *J. Hazard. Mater.*, 2011, **186**, 84–91.
- 50 L. Qi, W. Ho, J. Wang, P. Zhang and J. Yu, *Catal. Sci. Technol.*, 2015, **5**, 2366–2377.
- 51 F. Yu, Z. Qu, X. Zhang, Q. Fu and Y. Wang, *J. Energy Chem.*, 2013, **22**, 845–852.

