



Cite this: *RSC Adv.*, 2018, 8, 16902

# Template-assisted synthesis of NiCoO<sub>2</sub> nanocages/reduced graphene oxide composites as high-performance electrodes for supercapacitors†

Xiao-Hui Guan,<sup>a</sup> Mu Li,<sup>a</sup> Hai-Zhen Zhang,<sup>a</sup> Liu Yang<sup>a</sup> and Guang-Sheng Wang<sup>a,b\*</sup>

Here we reported a coordinating etching and precipitating method to synthesize a complex binary metal oxides hollow cubic structure. A novel NiCoO<sub>2</sub>/rGO composite with a structure of NiCoO<sub>2</sub> nanocages anchored on layers of reduced graphene oxide (rGO) were synthesized *via* a simple template-assisted method and the electrochemical performance was investigated by cyclic voltammetry, galvanostatic charge–discharge and electrochemical impedance spectroscopy tests as a faradaic electrode for supercapacitors at a graphene weight ratio of 1 wt% (1%). When used as electrode materials for electrochemical capacitors, the NiCoO<sub>2</sub>/rGO composites achieved a specific capacity of 1375 F g<sup>-1</sup> at the current density of 1 A g<sup>-1</sup> and maintained 742 F g<sup>-1</sup> at 10 A g<sup>-1</sup>. After 3000 cycles, the supercapacitor based on these nanocage structures shows long-term cycling performance with a high capacity of 778 F g<sup>-1</sup> at a current density of 1 A g<sup>-1</sup>. These outstanding electrochemical performances are primarily attributed to the special morphological structure and the combination of mixed transition metal oxides and rGO, which not only maintains a high electrical conductivity for the overall electrode but also prevents the aggregation and volume expansion of electrochemical materials during the cycling processes.

Received 15th March 2018

Accepted 27th April 2018

DOI: 10.1039/c8ra02267d

[rsc.li/rsc-advances](http://rsc.li/rsc-advances)

## 1 Introduction

Electrochemical capacitors (ECs), also called supercapacitors, a new energy storage system, have great potential as next generation energy storage systems, due to their outstanding electrochemical performance including high specific capacitance, high power density, good rate capability and excellent cycling stability.<sup>1,2</sup> Supercapacitors have been successfully utilized in many fields including communication, transportation, electronics, and aviation, and have considerable application prospects.<sup>3,4</sup> Based on different energy storage mechanisms, ECs are classified into two categories: double-layer capacitors (DLC) and pseudocapacitors (PC).<sup>5,6</sup> In particular, PCs rely on reversible redox reactions between active materials and electrolyte ions to more rapidly complete the storage of energy and the release of charge.<sup>7</sup> As is well-known, the electrode material is the most important component of supercapacitors, which affects the supercapacitors' performance to a large extent. Many researchers are aiming at

producing new substances and structures to achieve better properties for supercapacitors.

Various materials, such as transition metal oxides,<sup>8</sup> metal sulfides,<sup>9</sup> metal hydroxides<sup>10</sup> and modified carbons,<sup>11</sup> have been explored for pseudocapacitor applications. Among them, nickel hydroxide is an attractive pseudocapacitive material due to its well-known electro-chemical redox activity, high specific capacitance, good rate capability and low cost.<sup>12,13</sup> Nickel hydroxide is a kind of p-type semiconductor, which can increase the internal resistance of the electrode.<sup>14</sup> To minimize the internal resistance of the electrode among nickel hydroxide, nickel substrate and electrolyte, it is suggested to incorporate some additives in the electrode. Meanwhile, cobalt oxides have special structure and surface redox reactivity.<sup>15</sup> Cobalt oxides comprise two readily accessible cation oxidation states: Co<sup>2+</sup> and Co<sup>3+</sup>, which are thermodynamically competitive under common ambient conditions, and two species of cobalt oxide are stable in the natural environment, which make them potential additive candidates for advanced materials.<sup>16</sup> One of the most promising materials based on transition metal oxides is the mixed Ni and Co oxide, which is a cheap and stable electrode material. As a novel two-dimensional single-atom-thick carbon material with a honeycomb lattice structure, graphene has attracted huge research interest in both academia and industry. Its unique structural features provide excellent mechanical, thermal and optical properties. In particular, its great theoretical specific surface area and high electronic conductivity make graphene a promising material for high-performance supercapacitors.

<sup>a</sup>School of Chemical Engineering, Northeast Electric Power University, Jilin 132000, P. R. China

<sup>b</sup>Key Laboratory of Bio-Inspired Smart Interfacial Science, Technology of Ministry of Education, School of Chemistry and Environment, Beihang University, Beijing 100191, P. R. China. E-mail: wanggsh@buaa.edu.cn

† Electronic supplementary information (ESI) available. See DOI: 10.1039/c8ra02267d



However, there are still several considerable barriers preventing graphene's effective application in supercapacitors. The foremost obstacles are serious aggregation and restacking of graphene, which not only decrease its actual specific surface area but also hinder the rapid transport of electrolyte ions. To date, there have been several reports on the synthesis and electrochemical evaluation of NiCo<sub>2</sub>O<sub>4</sub> material with various morphologies.<sup>17–20</sup> Mondal *et al.* developed rGO–NiCo<sub>2</sub>O<sub>4</sub> hollow spheres for supercapacitor application. The synthesized rGO–NiCo<sub>2</sub>O<sub>4</sub> showed a specific capacity as high as 971 F g<sup>−1</sup> at a current density of 0.5 A g<sup>−1</sup>, which is much superior to that of pristine NiCo<sub>2</sub>O<sub>4</sub> hollow spheres (416 F g<sup>−1</sup>).<sup>21</sup> Zhang *et al.* reported the synthesis method of mesoporous NiCo<sub>2</sub>O<sub>4</sub> with nanoflake@nanoneedles-like multiple hierarchical structures (NCO-MHS) and urchin-like hierarchical structures (NCO-urchin-like HSS). The performance of synthesized NiCo<sub>2</sub>O<sub>4</sub> as supercapacitor electrode materials were measured and the results demonstrated that the NCO-MHSs and NCO-urchin-like HSS exhibits higher specific capacitance of 640 F g<sup>−1</sup> and 655 F g<sup>−1</sup> at current density of 1 A g<sup>−1</sup> respectively, and capacitance retention is 99.6% and 95% after 1000 cycles at a current density of 5 A g<sup>−1</sup>.<sup>22</sup> However, few of NiCoO<sub>2</sub> materials, as another mixed Ni and Co oxide, have been reported on the synthesis and electrochemical evaluation. Especially, the study on the template-assisted synthesis of novel NiCoO<sub>2</sub>/rGO nanocage composites for supercapacitors has been rarely been reported.

Herein, we explored a general strategy for fabricating uniform nanocages of NiCo(OH)<sub>2</sub>/rGO (MHs) by templating against cubic Cu<sub>2</sub>O nanocrystals at room temperature and then obtaining homologous metal oxide (MO) porous nanocages by simple thermal treatment of the as-prepared MHs. Due to positive synergistic effects, the composites maintained a high electrical conductivity, a distinct volume change cushion, and all effective prevention of rGO's agglomeration or restacking during the charge–discharge process. The electrochemical performance of the hollow NiCo(OH)<sub>2</sub>, NiCoO<sub>2</sub>, NiCo(OH)<sub>2</sub>/rGO and NiCoO<sub>2</sub>/rGO nanocages were further researched and compared in detail based on cyclic voltammetry (CV), galvanostatic charge–discharge (GCD) and electrochemical impedance spectroscopy (EIS) techniques.

## 2 Experimental

### 2.1 Sample preparation

All of the chemical reagents used in this experiment were of analytical grade and used without further purification.

**Preparation of graphene oxides.** Graphene oxides (GO) were synthesized *via* a modified Hummers method using pristine graphite powders as raw materials. The detail procedure are shown in the ESI,<sup>†</sup> as well as the SEM of GO in Fig. S1.<sup>†</sup>

**Preparation of solid Cu<sub>2</sub>O crystals.** The synthesis of Cu<sub>2</sub>O followed Zhang's previous report<sup>23</sup> with some modification, which increased the quantity of products than Zhang's. In a typical synthesis, 6 mmol CuCl<sub>2</sub>·6H<sub>2</sub>O was dissolved in 200 mL of deionized water with magnetic stirring for 30 min to obtain transparent light green solution. Then, 20 mL NaOH aqueous solution (2 mol L<sup>−1</sup>) was dropwise added into the above solution, which turned into turbid blue-green and then dark brown. After

stirring for 1 h, 20 mL ascorbic acid solution (0.6 mol L<sup>−1</sup>) was dropwise added into the dark brown solution and a turbid red liquid gradually formed. The liquid was aged for 3 h. All of the procedure was carried out under constant stirring and heated in a water bath at 60 °C. The resulting precipitate was collected by centrifugation and decanting, followed by washing with distilled water and absolute ethanol and finally dried in vacuum at 60 °C for 12 h, and after that, the cubic nanostructures of Cu<sub>2</sub>O samples was obtained. The cubic nanostructures of Cu<sub>2</sub>O samples are shown in Fig. S2 in the ESI, as well as XRD in Fig. S3.<sup>†</sup>

**Preparation of NiCo(OH)<sub>2</sub>, NiCo(OH)<sub>2</sub>/rGO nanocages.** In a typical procedure,<sup>24</sup> a certain amount of Cu<sub>2</sub>O templates, NiCl<sub>2</sub>·2H<sub>2</sub>O and CoCl<sub>2</sub>·2H<sub>2</sub>O (Co : Ni = 3 : 2, molar ratio) were added to 120 mL of the ethanol/water mixed solvent (MS) in the presence of PVP (*M<sub>w</sub>* = 30 000). After the mixture was stirred for 10 min, a certain amount of Na<sub>2</sub>S<sub>2</sub>O<sub>3</sub> aqueous solution was dropwise added. Then the reaction was carried out at room temperature for some time until the suspension solution changed from red to the expected color. Eventually, NiCo(OH)<sub>2</sub> nanocages were fabricated respectively. As for the synthesis of NiCo(OH)<sub>2</sub>/rGO nanocages, GO of one percent (1%) is added to the above mixed solvent (MS). The cubic nanostructures of NiCo(OH)<sub>2</sub>, 1%NiCo(OH)<sub>2</sub>/rGO samples are shown in Fig. S4 in the ESI.<sup>†</sup>

**Preparation of NiCoO<sub>2</sub>, NiCoO<sub>2</sub>/rGO nanocages.** In a typical procedure,<sup>25</sup> the as-prepared NiCo(OH)<sub>2</sub> and NiCo(OH)<sub>2</sub>/rGO samples were treated with calcination under a nitrogen atmosphere at a certain temperatures for a certain time. The heating rate was kept at 1 °C min<sup>−1</sup> for each sample. After thermal treatment, NiCoO<sub>2</sub> and NiCoO<sub>2</sub>/rGO nanocages were obtained.

### 2.2 Characterization

The samples were examined by X-ray diffraction (XRD-7000), recorded using a Shimadzu X-ray powder diffractometer with Cu-K $\alpha$  radiation ( $\lambda$  = 0.15405 nm). The morphology and size of the products were obtained using scanning electron microscopy (SEM) with a JSM-6510A microscope and by sputtering with gold. The internal structures of the products were observed using a JEOL JEM-2100F microscope used for transmission electron microscopy (TEM). The elemental composition of the products was determined using energy dispersive X-ray spectroscopy (EDS; Hitachi SU8010 IXRP Systems). Thermogravimetric analysis (TG) was carried out using Switzerland Mettler-Toledo TGA/DSC1 apparatus.

### 2.3 Fabrication of the working electrode and electrochemical measurements

To prepare the working electrode with the following procedure, the as-prepared active materials, acetylene black and a polytetrafluoroethylene (PTFE) emulsion, were mixed in ethanol at a weight ratio of 8 : 1 : 1, and dispersed by ultrasonic treatment for 10 min. The slurry was coated on a nickel foam (1 × 1 cm<sup>2</sup>) current collector and then pressed at 8 MPa for 30 s and dried under vacuum at 60 °C for 12 h. Finally, the working electrode was obtained, and the mass of the active loading on the nickel foam was about 10 mg. The electrochemical properties of the active material were tested using an electrochemical workstation



by a conventional three-electrode system (a reference electrode, counter electrode and working electrode). Hg/HgO was used as the reference electrode, a platinum foil as the counter electrode and the working electrode was prepared using the active materials. All of the electrochemical measurements were carried out in a 2.0 M KOH solution on a Parstat 4000 workstation at room temperature. Based on the CV curves, the average specific capacitance of the electrodes was calculated *via* eqn (1),

$$C_s = \frac{\int_{V_0}^V I(V) dV}{mv(V - V_0)} \quad (1)$$

where  $C_s$  ( $F g^{-1}$ ),  $m$  (g),  $v$  ( $V s^{-1}$ ),  $(V - V_0)$ , and  $I(V)$  are the specific capacitance, mass of the active material, potential scan rate, potential range and current density, respectively. Based on the discharge curves, the average specific capacitance of the electrodes was calculated according to eqn (2),


$$C_s = \frac{I \times \Delta t}{\Delta V \times m} \quad (2)$$

where  $C_s$  ( $F g^{-1}$ ),  $I$  (A),  $\Delta t$  (s),  $\Delta V$  (V) and  $m$  (g) are the specific capacitance, discharge current, discharge time, potential range of discharge and mass of the active material, respectively.

## 3 Results and discussion


### 3.1 Strategy for the NiCoO<sub>2</sub>/rGO nanocages fabrication

A possible formation mechanism of NiCoO<sub>2</sub>/rGO nanocages is illustrated in Scheme 1. The formation process is illustrated as steps I, II and III in Scheme 1, and the general chemical route could be described as,



During this process, continuous dissolution of Cu<sub>2</sub>O can occur even in closed shells, proving that species such as S<sub>2</sub>O<sub>3</sub><sup>2-</sup> and the [Cu<sub>2</sub>(S<sub>2</sub>O<sub>3</sub>)<sub>x</sub>]<sup>2-2x</sup> complex can freely transport across the shells through interparticle interstitials and driven by the as-buildup concentration gradient during the etching process (occurs in both steps I and II). Meanwhile, rGO can be added to synthesise the reduced graphene oxide of homologous composites. In a further procedure, NiCoO<sub>2</sub> and NiCoO<sub>2</sub>/rGO nanocages can be readily obtained by the common thermal treatment of the as-prepared NiCo(OH)<sub>2</sub> and NiCo(OH)<sub>2</sub>/rGO, illustrated as step III in Scheme 1.

The calcination temperature of NiCo(OH)<sub>2</sub>/rGO composites can be further investigated by TGA, which was performed up to 900 °C in nitrogen with a heating rate of 10 °C min<sup>-1</sup>. As shown in Fig. S5 (ESI†), there is an initial mass loss of approximately 10% below 150 °C, which is associated with the deintercalation of surface-absorbed water. Subsequently, NiCo(OH)<sub>2</sub>/rGO composites display a dramatic mass loss at approximately 350 °C. And this fully 11% of mass loss should be attributed to the removal of ions OH<sup>-</sup>, and at this time NiCoO<sub>2</sub>/rGO composites have been prepared. After 700 °C, this fully 1% of mass loss should be attributed to the removal of carbon sketch by burning rGO, while the remainder is NiCoO<sub>2</sub>, which has a better thermal property.

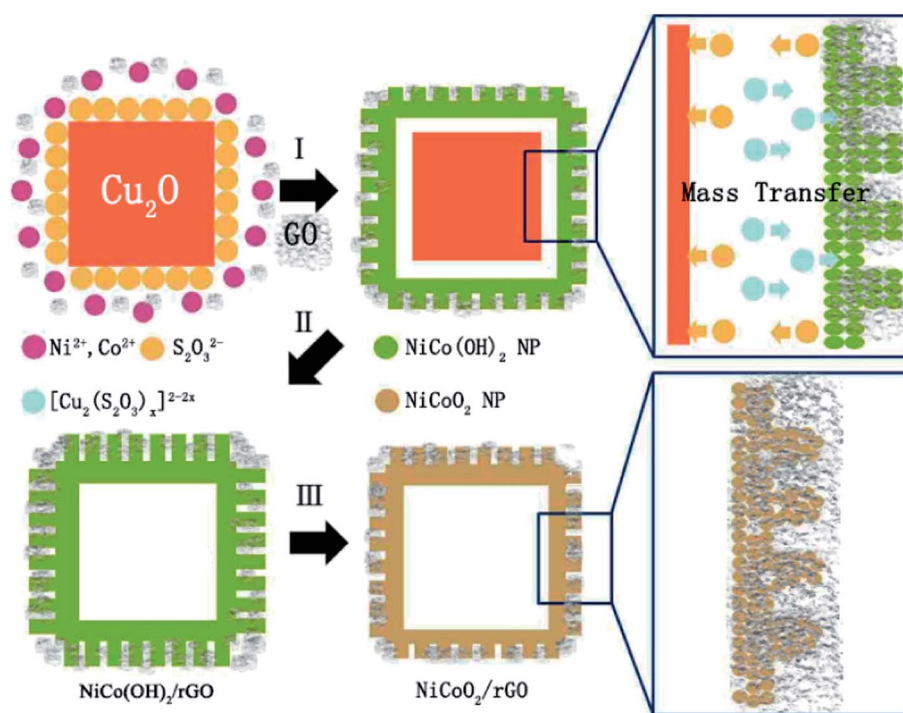

**Scheme 1** Schematic illustration of the fabrication of NiCoO<sub>2</sub>/rGO nanocages by synchronous coordinating etching of Cu<sub>2</sub>O nanocrystals and the fabrication of NiCoO<sub>2</sub> by thermal treating of relevant NiCo(OH)<sub>2</sub>/rGO. (Step I: coordinating etching and precipitating. Step II: coordinating etching; Step III: thermal treatment).



### 3.2 Characterization of structure and morphology

XRD characterizations were used to determine the crystalline structure and phase composition of the samples. As shown in Fig. 1, there are the patterns of rGO, NiCoO<sub>2</sub> and NiCoO<sub>2</sub>/rGO composites. All diffraction peaks of NiCoO<sub>2</sub> are perfectly in accordance with the standard data of cubic NiCoO<sub>2</sub> (JCPDS no. 10-0188), indicating the pure quality of the as-prepared sample.<sup>26</sup> Meanwhile, the strong and narrow diffraction peaks show that the material possesses high crystallinity. In Fig. 1, the broad diffraction peak of rGO appearing at approximately 25° corresponds to the (002) plane of grapheme.<sup>27–29</sup> And the diffraction peaks of 1% NiCoO<sub>2</sub>/rGO composites are similar to that of NiCoO<sub>2</sub>. However, this characteristic peak of rGO is not observed in the XRD pattern of 1% NiCoO<sub>2</sub>/rGO, the reason of which may be the content of rGO under the detection limit.<sup>30</sup>

In addition, XPS characterization was used to further confirm the crystal phase of the NiCoO<sub>2</sub>/rGO composites. As shown in Fig. S5 (ESI†), the survey spectrum of NiCoO<sub>2</sub>/rGO composites mainly confirms presence of carbon, oxygen, cobalt and nickel species. In Fig. 2(a), the major peak of the Ni<sub>2p</sub> XPS spectrum can be assigned to the Ni<sub>2p3/2</sub> (approximately 857.0 eV).<sup>31</sup> In Fig. 2(b), the major peak of the Co<sub>2p</sub> XPS spectrum can be assigned to the Co<sub>2p3/2</sub> (approximately 782.4 eV). The Ni<sub>2p</sub> and Co<sub>2p</sub> XPS spectra show that both the cobalt and nickel elements in the composites exist in the bivalent form, which is in accordance with results from the XRD. Moreover, the peak located at 284.6 eV is assigned to the characteristic peak of C1s, and a detailed deconvolution of the C1s spectrum is shown in Fig. 2(c).<sup>32</sup> It is noteworthy that there are two types of carbon bonds, including C–C at 284.6 eV and C–O at 286.9 eV.<sup>33</sup> The deconvoluted O<sub>1s</sub> spectrum (Fig. 2(d)) demonstrates the formation of NiCoO<sub>2</sub> at 531.7 eV, and the presence of the oxygen atoms of the relevant surface functional groups at 533.6 eV (O=C–O).<sup>34</sup> The presence of these residual oxygen-containing groups can be attributed to the partial oxidation of GO during the hydrothermal process. However, these hydrophilic groups can act as anchoring sites to enable NiCoO<sub>2</sub> to interact tightly with rGO. Moreover, these groups can enhance the wettability of the electrode, which brings a further positive effect on the compatibility between the electrode and the electrolyte.

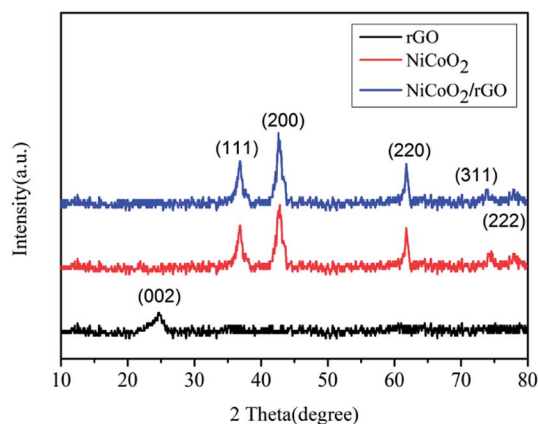


Fig. 1 XRD patterns of rGO, NiCoO<sub>2</sub> and NiCoO<sub>2</sub>/rGO composites.

Fig. 3 displays Raman spectra of pure GO and NiCoO<sub>2</sub>/rGO composites, which show that all samples contain the D and G bands due to the GO. The G band denoted as the characteristic Raman band at ~1585 cm<sup>-1</sup> resulted from the E<sub>2g</sub> phonon vibration of the carbon sp<sup>2</sup> atoms and D band at ~1365 cm<sup>-1</sup> associated with the structural disorders and defects attributed to the amorphous sp<sup>3</sup> C–C vibrations.<sup>35,36</sup> Also, the broad 2D band position around ~2700 cm<sup>-1</sup>, which is highly sensitive to stacking of grapheme sheets.<sup>37,38</sup> It can be seen that D and G band intensity varies for the as synthesized composites. Also, the ratio of intensities of the D and G bands (*I*<sub>D</sub>/*I*<sub>G</sub>) is an important parameter and gives significant information about the structural defects present in carbon materials.<sup>39</sup> The calculated *I*<sub>D</sub>/*I*<sub>G</sub> intensity ratios were 0.88 and 1.03 for pure GO and NiCoO<sub>2</sub>/rGO composites, respectively. The small value of the intensity ratio of pure GO indicates the presence of lower number of defects in as synthesized GO. However, the NiCoO<sub>2</sub>/rGO composite shows the highest defect (1.03) due to the formation of NiCoO<sub>2</sub> nanoparticles of metal oxide on the rGO.<sup>40</sup>

The morphology and microstructure of the NiCoO<sub>2</sub> and NiCoO<sub>2</sub>/rGO samples were characterized by SEM and TEM observations, shown in Fig. 4. When cube of Cu<sub>2</sub>O templates are introduced, the overall sample was dominated by the three-dimensional cubic structure of nanocages. It can be distinctly observed from the large number of nanocages and some of the broken nanocages that the nanocages are hollow and the side length of the hollow nanocages is approximately 500 nm, as shown in Fig. 4(a and b). And compared with NiCoO<sub>2</sub>, the NiCoO<sub>2</sub> nanocage in NiCoO<sub>2</sub>/rGO composites are covered by the layers of rGO (SEM images c and d in Fig. 4). The features of the cubic nanocages, including uniform dimensions, good exterior texture, and amorphous, intact, and regular shell structure, can also be clearly observed in these cubic nanocages, which can be confirmed by the TEM image in Fig. 4(e). In particular, Fig. 4(f) shows NiCoO<sub>2</sub> nanoparticles (NiCoO<sub>2</sub> NPs) in size distribution of 10–20 nm are well anchored on the layers of rGO.

### 3.3 Electrochemical performance

The electrochemical properties of NiCo(OH)<sub>2</sub>, NiCo(OH)<sub>2</sub>/rGO, NiCoO<sub>2</sub> and NiCoO<sub>2</sub>/rGO were evaluated using CV and GCD techniques. Fig. S6† shows the typical CV curves of NiCo(OH)<sub>2</sub>, NiCo(OH)<sub>2</sub>/rGO, NiCoO<sub>2</sub> and NiCoO<sub>2</sub>/rGO at different scan rates with a potential window ranging from -0.5 V to 0.7 V. From Fig. S8 (ESI†), each pair of peaks is visible in each voltammogram. In the cathodic scan, a small amount of charges would be stored in the interphase between the electrode material and electrolyte, which occurs at different peaks. In the reverse anodic scan, the stored charge would be released, which displays different peaks. When the scan rate is increased, the shapes of the curves are maintained and the peak current increases. The CV curves of all of the electrodes involving the reversible redox reactions are expected to exhibit good quasi-capacitance. Obviously, NiCoO<sub>2</sub>/rGO, the target product, shows the best electrochemical performance among them. From Fig. S10,† the capacitances of NiCoO<sub>2</sub>/rGO composites with different weight ratios of rGO (0.5%, 1%, 1.5%, and 2%) at 1 A g<sup>-1</sup> are 806, 1375, 508, and 490 F g<sup>-1</sup>, respectively. It is clear



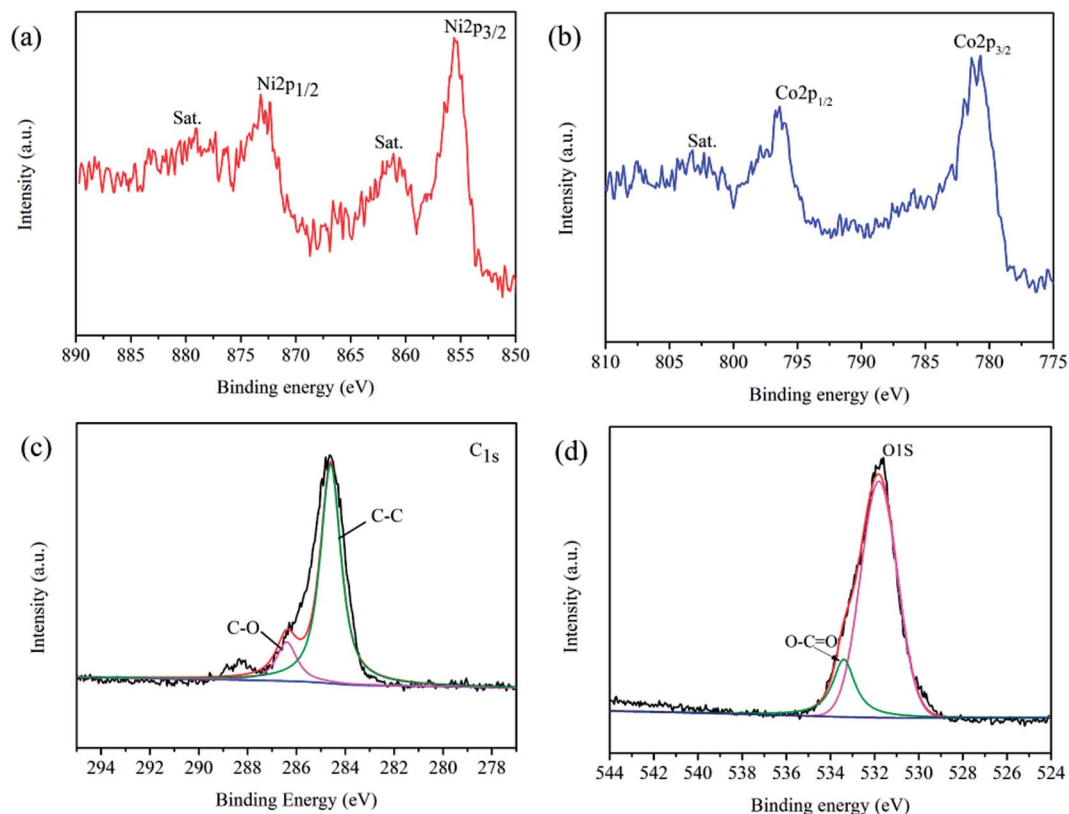


Fig. 2 XPS spectra of NiCoO<sub>2</sub>/rGO composites. (a) Ni<sub>2p</sub> spectrum; (b) Co<sub>2p</sub> spectrum; (c) C<sub>1s</sub> spectrum; (d) O<sub>1s</sub> spectrum.

that with the increasing rGO weight ratio, the specific capacitance first increased, and then decreased. The specific capacitance of the 1% NiCoO<sub>2</sub>/rGO is the highest. From Fig. 5(a), CV curves cycled at 10 mV s<sup>-1</sup> on the NiCoO<sub>2</sub>/rGO electrode shows a pair of obvious redox peaks, which differs from the CV curves of rGO and NiCoO<sub>2</sub> displaying a smaller peak area. Fig. S6(d)<sup>†</sup> shows the CV curves on the NiCoO<sub>2</sub>/rGO composite electrodes at scan rates from 1 to 20 mV s<sup>-1</sup>. The strong pairs of peaks in the CV curves indicate that the capacitive behaviors mainly attributed to faradic redox reaction. The faradic behavior is consistent with a battery-type electrode, coming from the following redox reactions,<sup>41–43</sup>



In alkaline media, NiCoO<sub>2</sub> tends to change to NiOOH and CoOOH, as such in reaction (6), which have a high electron and proton conductivity and significant voltammetric response, due

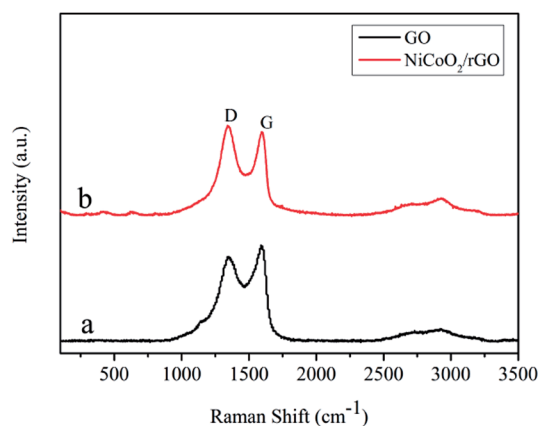


Fig. 3 Comparison of Raman spectra of these products. (a) Pure GO; (b) NiCoO<sub>2</sub>/rGO.

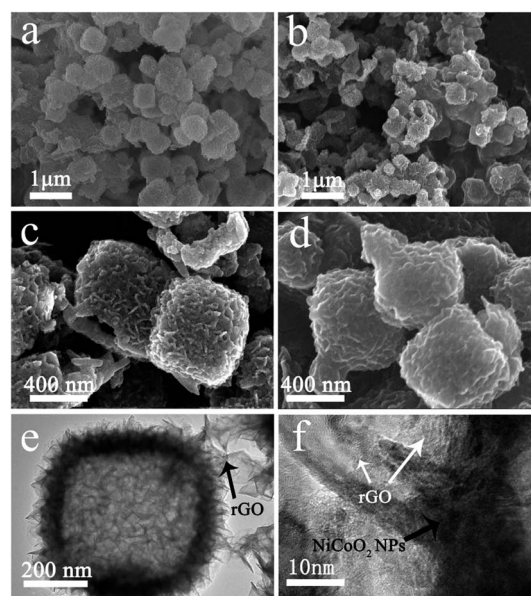


Fig. 4 SEM images (a and c) of NiCoO<sub>2</sub>, SEM images (b and d) and TEM images (e and f) of 1% NiCoO<sub>2</sub>/rGO composites.



to the combined effect of the oxygen donation from Ni and Co oxide/hydroxide.

In Fig. 5(b), the obvious plateau regions demonstrate faradic behaviors in the GCD curve of NiCoO<sub>2</sub>/rGO electrode, which is caused by redox reactions. And this also is in accordance with the CV results. In addition, GCD curves on NiCoO<sub>2</sub>/rGO composites at various current densities ranging from 1 to 10 A g<sup>-1</sup> were also employed in Fig. S7(d).† The relationship between the capacitance and the area bounded by the CV curves can be described by eqn (2).<sup>44,45</sup> According to eqn (2), the specific capacities of the NiCoO<sub>2</sub>/rGO composites are calculated at current densities of 1, 2, 5 and 10 A g<sup>-1</sup>, respectively, and the calculated capacitances of NiCoO<sub>2</sub>/rGO composites at corresponding current densities are 1375, 1271, 1022 and 742 F g<sup>-1</sup>, as shown in Fig. 5(c). And compared with NiCoO<sub>2</sub>, the specific capacities of the NiCoO<sub>2</sub>/rGO composites have an obvious improvement and show higher rate capacity and high multiplier performance, for which the reason is closely related to the combination of NiCoO<sub>2</sub> and rGO. In Fig. 5(d), it shows the cycling performance of the NiCoO<sub>2</sub>/rGO working electrodes for electrochemical energy storage at a current density of 1 A g<sup>-1</sup> between 0 V and 0.45 V, which reveals a higher initial specific capacitance for the first 300 cycles. Meanwhile, they undergo a rapid consecutive capacity reduction along with the increase in cycle number. After 300 cycles, the NiCoO<sub>2</sub>/rGO electrodes retain a capacity of 800 F g<sup>-1</sup>. The decrease of the capacitance

could be caused by mainly decreasing the electroactive sites and a slight collapse of the hollow structure when the ions were intercalated/extracted into/out of the hollow structures. From the 300th to 3000th cycle, we can see that the long-term cycling performance of the NiCoO<sub>2</sub>/rGO electrode at a current density of 1 A g<sup>-1</sup>. In particular, the NiCoO<sub>2</sub>/rGO composites show a stable cycle performance with 97% capacity retention ratios (approximately from 800 to 778 F g<sup>-1</sup>) from the 300th to 3000th cycle of charging and discharging. Even if compared with the specific capacities, the capacity retention of NiCoO<sub>2</sub>/rGO composites is still 56% at a current density of 1 A g<sup>-1</sup> (approximately from 1375 to 778 F g<sup>-1</sup>). And the good rate capability and excellent cycling stability of NiCoO<sub>2</sub>/rGO electrodes are closely related to the combination of mixed transition metal oxides and rGO. The unique hybrid architecture can maintain a high electrical conductivity for the overall electrode, which promotes a fast faradic charging and discharging process on the composites. Moreover, the aggregation and volume expansion/contraction of electrochemical materials can be effectively prevented during the cycling processes by virtue of the hybrid structure. Meanwhile, the high specific capacitance of NiCoO<sub>2</sub>/rGO electrodes is closely related to annealing in nitrogen, which makes NiCoO<sub>2</sub>/rGO possessing high crystallinity.

Electrochemical impedance spectra (EIS) measurement is also a significant aspect for quantitatively evaluating the electrical resistance of NiCoO<sub>2</sub>/rGO composites.<sup>46,47</sup> Fig. 6(a)

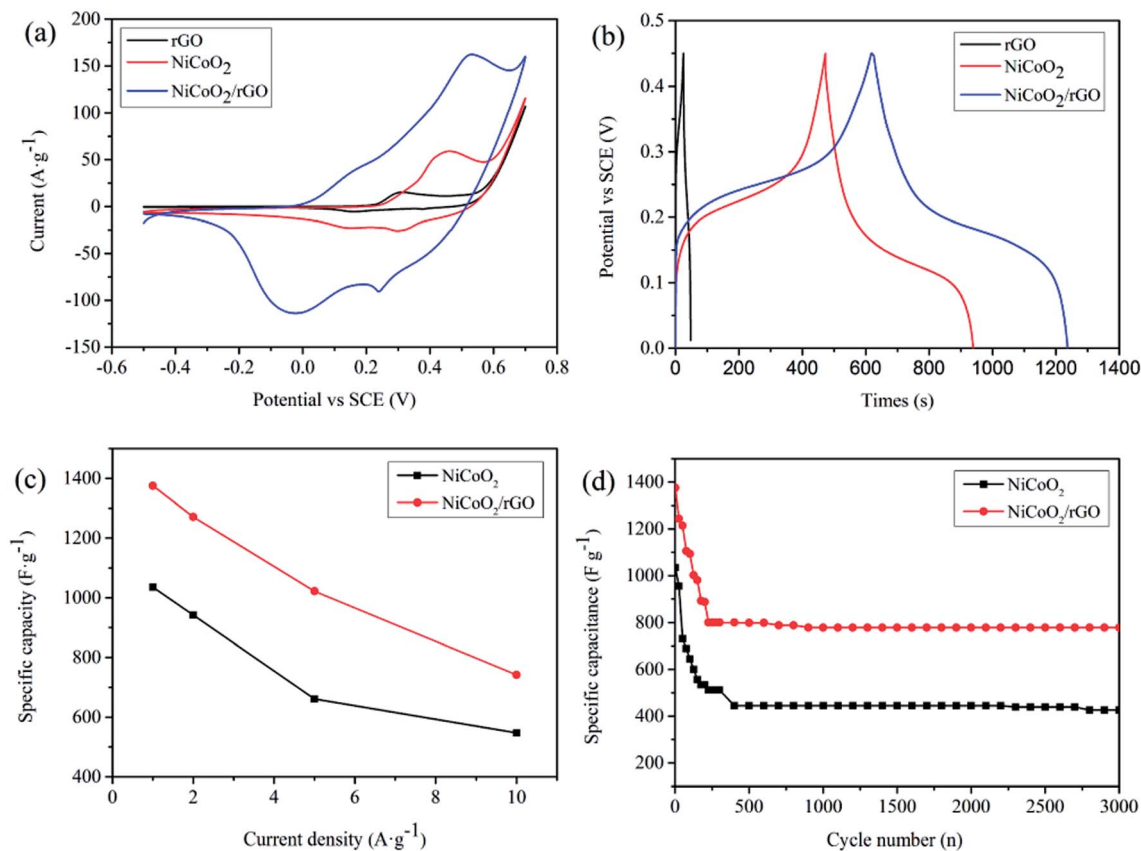


Fig. 5 (a) CV curves of rGO and 1% NiCoO<sub>2</sub>/rGO composites at a scan rate of 10 mV s<sup>-1</sup>; (b) GCD plots of rGO and 1% NiCoO<sub>2</sub>/rGO composites at a current density of 1 A g<sup>-1</sup>; (c) specific capacities of 1% NiCoO<sub>2</sub>/rGO composites at various current densities and (d) cycling performance of 1% NiCoO<sub>2</sub>/rGO composites at a current density of 1 A g<sup>-1</sup>.



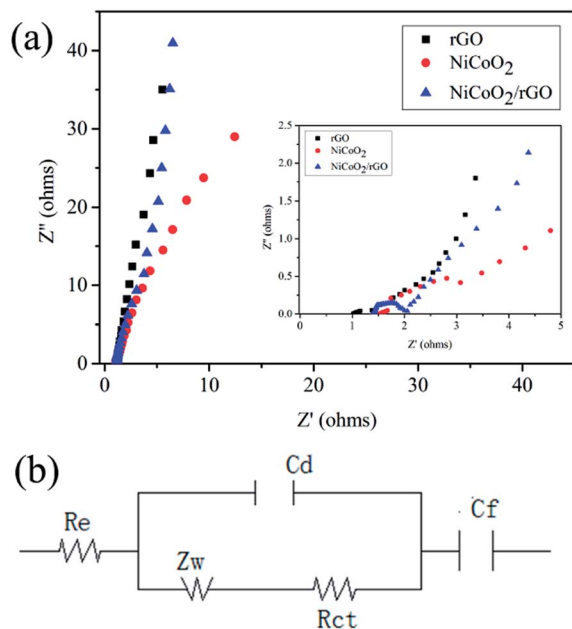


Fig. 6 EIS spectra (a) of rGO, NiCoO<sub>2</sub> and NiCoO<sub>2</sub>/rGO electrodes in the frequency range from 100 kHz to 0.01 Hz and the electrical equivalent circuit (b) used for fitting the impedance spectra of NiCoO<sub>2</sub>/rGO.

demonstrates the Nyquist plots of the rGO, NiCoO<sub>2</sub> and NiCoO<sub>2</sub>/rGO electrodes to illustrate their impedance characteristics. The Nyquist plots are composed of semicircles in the higher (left) frequency region (in the inset of Fig. 6(a)) and sloping lines in the lower (right) frequency region. The equivalent circuit model of the EIS analysis is shown in Fig. 6(b), where  $R_e$ ,  $R_{ct}$ ,  $Z_w$ ,  $C_d$  and  $C_f$  are denoted as electrode series resistance, charge transfer resistance, Warburg impedance, electric double layer capacitance and faradic capacitance, respectively. From Fig. 6(a), we can see that NiCoO<sub>2</sub>/rGO displays a slightly bigger  $R_e$  value (1.327  $\Omega$ ) than that of rGO (0.898  $\Omega$ ), indicating that the outstanding electronic conductivity of rGO is maintained in NiCoO<sub>2</sub>/rGO composites. Moreover, the charge transfer resistance ( $R_{ct}$ ) of NiCoO<sub>2</sub>/rGO composites is estimated to be 0.978  $\Omega$ , which is bigger than that of pure rGO. This can be attributed to the following facts: a portion of the charges in NiCoO<sub>2</sub>/rGO composites is used to transfer between the rGO sheets, and the remainder is used to participate in the faradic redox reaction. In addition, the NiCoO<sub>2</sub>/rGO composite electrode exhibits a line that is more vertical than rGO in the low frequency region, indicating the fast ion diffusion in the electrolyte, and the adsorption onto the electrode surface.

## 4 Conclusion

We demonstrated a facile synthesis of novel hollow cubic NiCoO<sub>2</sub>/rGO composites with the structure of NiCoO<sub>2</sub> nanoparticles anchored on layers of rGO through a template-assisted method and we investigated their electrochemical performance as a faradic electrode for supercapacitors. The 1% NiCoO<sub>2</sub>/rGO composites achieve a specific capacity of 1375 F g<sup>-1</sup> at the

current density of 1 A g<sup>-1</sup> and maintain 742 F g<sup>-1</sup> at 10 A g<sup>-1</sup>. From a 3000 cycle test, we can see that the long-term cycling performance of the 1%NiCoO<sub>2</sub>/rGO electrode at a current density of 1 A g<sup>-1</sup>. In particular, the specific capacity of NiCoO<sub>2</sub>/rGO composites is still 778 F g<sup>-1</sup> after a 3000 cycle test of charging and discharging. Even if compared with other researchers' results (Table S2, ESI†), the hollow cubic 1% NiCoO<sub>2</sub>/rGO nanocage composites in this work show a superior specific capacity and high capacity retention. It has been observed that the 1% NiCoO<sub>2</sub>/rGO composites exhibit all improved capacitive performance, which can be attributed to the combination of mixed transition metal oxides and rGO, as well as its extraordinary hollow cubic structure. Owing to the synergistic effects between the two kinds of materials, there is efficient charge transport and electrolyte diffusion during the charge–discharge process. Moreover, the aggregation and volume expansion/contraction of electrochemical materials can be effectively prevented. These features make the NiCoO<sub>2</sub>/rGO composite a suitable and promising electrode material for efficient supercapacitors. Moreover, this template-assisted method can be easily generalized to other syntheses of mixed transition metals and carbon materials for supercapacitors.

## Conflicts of interest

The authors have declared that no conflicts of interest exist.

## Acknowledgements

This work was supported by the National Natural Science Foundation of China (No. 51672040) and the Fundamental Research Funds for the Central Universities.

## Notes and references

- 1 L. Wang, H. Tian, D. Wang, *et al.*, *Electrochim. Acta*, 2015, **151**, 407–414.
- 2 X. Q. Li, S. Y. Lin, M. Zhang, *et al.*, *Nano*, 2016, **11**, 1650050–1650057.
- 3 C. Zheng, C. Cao, Z. Ali, *et al.*, *J. Mater. Chem. A*, 2014, **2**, 16467–16473.
- 4 Z. Xing, Q. Chu, X. Ren, *et al.*, *Electrochem. Commun.*, 2013, **32**, 9–13.
- 5 A. P. D. Moura, L. H. D. Oliveira, P. F. S. Pereira, *et al.*, *Adv. Chem. Eng. Sci.*, 2012, **2**, 465–473.
- 6 Y. Wang, B. Chang, D. Guan, *et al.*, *Mater. Lett.*, 2014, **135**, 172–175.
- 7 M. Kundu and L. Liu, *Mater. Lett.*, 2015, **144**, 114–118.
- 8 W. Deng, Y. Sun, Q. Su, *et al.*, *Mater. Lett.*, 2014, **137**, 124–127.
- 9 J. Yang, X. Duan, Q. Qin, *et al.*, *J. Mater. Chem. A*, 2013, **1**(27), 7880–7884.
- 10 B. Hua, X. Qin, A. M. Asirib, *et al.*, *Electrochim. Acta*, 2013, **107**, 339–342.
- 11 C. Yuan, Y. Long, L. Hou, *et al.*, *Adv. Funct. Mater.*, 2012, **22**, 2560–2566.
- 12 J. Yang, M. Cho and Y. Lee, *Sens. Actuators, B*, 2016, **222**, 674–681.



- 13 W. Jiao and L. Zhang, *Curr. Appl. Phys.*, 2016, **16**, 115–119.
- 14 R. Wu, X. Qian, K. Zhou, *et al.*, *American Chemical Society*, 2014, **8**, 6297–6303.
- 15 L. Yu, L. Zhang, H. B. Wu, *et al.*, *Angew. Chem.*, 2014, **53**, 3711–3714.
- 16 Y. Q. Zou, I. A. Kinloch and R. A. W. Dryfe, *ACS Appl. Mater. Interfaces*, 2015, **7**, 22831–22838.
- 17 J. Zhang, Z. Chen, Y. Wang, *et al.*, *Energy*, 2016, **113**, 943–948.
- 18 S. Sharma, M. Kumar, S. Rani, *et al.*, *Mater. Sci. Semicond. Process.*, 2016, **48**, 1–8.
- 19 X. Leng, Y. Shao, L. Wu, *et al.*, *J. Mater. Chem. A*, 2016, **4**, 10304–10313.
- 20 H. Wan, X. Ji, J. Yu, *et al.*, *J. Power Sources*, 2013, **243**, 396–402.
- 21 A. Mondal, S. Maiti, S. Mahanty, *et al.*, *J. Mater. Chem. A*, 2017, **5**, 16854–16864.
- 22 L. Zhang, D. Zhang, Z. Ren, *et al.*, *ChemElectroChem*, 2017, **4**(2), 638–648.
- 23 H. Zhang, D. F. Zhan, L. Guo, *et al.*, *J. Mater. Chem.*, 2009, **19**, 5220–5225.
- 24 J. W. Nai, Y. Tian, X. Guan, L. Guo, *et al.*, *J. Am. Chem. Soc.*, 2013, **135**, 16082–16091.
- 25 M. C. Liu, L. B. Kong, C. Lu, *et al.*, *ACS Appl. Mater. Interfaces*, 2012, **4**, 4631–4636.
- 26 X. Xu, B. Dong, S. Ding, *et al.*, *J. Mater. Chem. A*, 2014, **2**, 13069–13074.
- 27 S. N. Tiruneh, B. K. Kang, Q. T. Ngoc, *et al.*, *RSC Adv.*, 2016, **6**, 4764–4769.
- 28 B. D. Chen, C. X. Peng and Z. Cui, *Trans. Nonferrous Met. Soc. China*, 2012, **22**, 2517–2522.
- 29 R. Zhang, J. Liu, H. Guo, *et al.*, *Mater. Lett.*, 2014, **136**, 198–201.
- 30 X. H. Guan, Z. W. Zhang, L. Yang, *et al.*, *Chempluschem*, 2017, **82**, 1174–1181.
- 31 F. Z. Deng, L. Yu, M. Sun, *et al.*, *Electrochim. Acta*, 2014, **133**, 382–390.
- 32 H. C. Chen, J. J. Jiang, L. Zhang, *et al.*, *Nanoscale*, 2013, **5**, 8879–8883.
- 33 M. S. Kolathodi, M. Palei and N. S. Tirupattur, *J. Mater. Chem. A*, 2015, **3**, 7513–7522.
- 34 J. B. Wu, R. Q. Guo, X. H. Huang, *et al.*, *J. Power Sources*, 2014, **248**, 115–121.
- 35 A. C. Ferrari and J. Robertson, *Phys. Rev. B*, 2000, **61**, 14095–14107.
- 36 J. W. Li, Y. Y. Liu, L. H. Xie, *et al.*, *Adv. Chem. Phys.*, 2015, **17**, 4919–4925.
- 37 L. M. Malard, M. A. Pimenta, G. Dresselhaus, *et al.*, *Phys. Rep.*, 2009, **473**, 51–87.
- 38 H. Peng, M. Sun, D. Zhang, *et al.*, *Surf. Coat. Technol.*, 2016, **306**, 171–175.
- 39 F. C. Tai, S. C. Lee, J. Chen, *et al.*, *J. Raman Spectrosc.*, 2009, **40**, 1055–1059.
- 40 R. Kumar, R. K. Singh, P. K. Dubey, *et al.*, *Adv. Mater. Interfaces*, 2015, **2**, 1500191.
- 41 X. Wang, W. Li, X. Wang, *et al.*, *RSC Adv.*, 2017, **7**, 50753–50759.
- 42 J. Liang, Z. Y. Fan, S. Chen, *et al.*, *Chem. Mater.*, 2014, **26**, 4354–4360.
- 43 S. Raj, S. K. Srivastava, P. Kar, *et al.*, *RSC Adv.*, 2016, **6**, 95760–95767.
- 44 R. A. Patil, C. P. Chang, R. S. Devan, *et al.*, *ACS Appl. Mater. Interfaces*, 2016, **8**, 9872–9880.
- 45 C. Yuan, L. Hou, Y. Feng, *et al.*, *Electrochim. Acta*, 2013, **88**, 507–512.
- 46 S. K. Meher, P. Justin and G. R. Rao, *ACS Appl. Mater. Interfaces*, 2011, **3**, 2063–2073.
- 47 A. Al-Osta, V. V. Jadhav, M. K. Zate, *et al.*, *Scr. Mater.*, 2015, **99**, 29–32.

