



Cite this: *RSC Adv.*, 2018, 8, 20557

# WS<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub> composite as an efficient heterojunction photocatalyst for biocatalyzed artificial photosynthesis†

Peng Zeng,<sup>ab</sup> Xiaoyuan Ji,<sup>ac</sup> Zhiguo Su<sup>a</sup> and Songping Zhang<sup>id</sup> \*<sup>a</sup>

A heterogeneous WS<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub> composite photocatalyst was prepared by a facile ultrasound-assisted hydrothermal method. The WS<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub> composite was used for photocatalytic regeneration of NAD<sup>+</sup> to NADH, which were coupled with dehydrogenases for sustainable bioconversion of CO<sub>2</sub> to methanol under visible light irradiation. Compared with pristine g-C<sub>3</sub>N<sub>4</sub> and the physical mixture of WS<sub>2</sub> and g-C<sub>3</sub>N<sub>4</sub>, the fabricated WS<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub> composite catalyst with 5 wt% of WS<sub>2</sub> showed the highest activity for methanol synthesis. The methanol productivity reached 372.1 μmol h<sup>-1</sup> g<sub>cat</sub><sup>-1</sup>, which is approximately 7.5 times higher than that obtained using pure g-C<sub>3</sub>N<sub>4</sub>. For further application demonstration, the activity of the WS<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub> composite catalyst toward photodegradation of Rhodamine B (RhB) was evaluated. RhB removal ratio approaching 100% was achieved in 1 hour by using the WS<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub> composite catalyst with 5 wt% of WS<sub>2</sub>, at an apparent degradation rate approximately 2.6 times higher than that of pure g-C<sub>3</sub>N<sub>4</sub>. Based on detailed investigations on physicochemical properties of the photocatalysts, the significantly enhanced reaction efficiency of the WS<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub> composite was considered to be mainly benefiting from the formation of a heterojunction interface between WS<sub>2</sub> and g-C<sub>3</sub>N<sub>4</sub>. Upon visible-light irradiation, the photo-induced electrons can transfer from the conduction band of g-C<sub>3</sub>N<sub>4</sub> to WS<sub>2</sub>, thus recombination of electrons and holes was decreased and the photo-harvesting efficiency was enhanced.

Received 1st April 2018  
 Accepted 27th May 2018

DOI: 10.1039/c8ra02807a

[rsc.li/rsc-advances](http://rsc.li/rsc-advances)

## 1. Introduction

With the increasing concerns regarding the energy crisis and greenhouse gas emissions, it has become urgent to develop a new channel to achieve the conversion of CO<sub>2</sub> to low-carbon fuel.<sup>1–5</sup> Among the energy conversion systems, methanol conversion from CO<sub>2</sub> by a cascade catalyzed by formate dehydrogenase (FateDH), formaldehyde dehydrogenase (FaldDH) and alcohol dehydrogenase (ADH) is considered to be one of the most promising ways.<sup>6,7</sup> However, the regeneration of coenzyme NADH in this multi-enzyme system is the key to the reaction process, since 3 moles of NADH are consumed for every mole of methanol produced.<sup>8,9</sup> In the past decade, inspired by natural photosynthesis, photocatalytic regeneration of coenzyme with the process of reducing CO<sub>2</sub> by multiple enzymes has brought new hope for solving this problem. For the success of such artificial photosynthesis systems, however, the major challenge

is the development of efficient visible-light active photocatalysts.<sup>10–12</sup>

Graphitic carbon nitride (g-C<sub>3</sub>N<sub>4</sub>), a polymeric semiconductor with a band gap of about 2.7 eV, has attracted significant attention in recent years because of its excellent visible light response,<sup>1,13,14</sup> non-toxicity, low cost, and abundant raw materials. As a visible-light active photocatalyst, g-C<sub>3</sub>N<sub>4</sub> has been widely applied for photocatalytic degradation of pollutants, water splitting, and regeneration of NADH since 2009.<sup>15,16</sup> Nevertheless, fast recombination of photogenerated electron-hole pairs and low quantum efficiency limits its further applications. In general, there are three routes to improve the photocatalytic efficiency of g-C<sub>3</sub>N<sub>4</sub>, which include construction of nanostructure, elemental doping, and hybridization. By fabricating nanosheets,<sup>17</sup> diatom frustule structure,<sup>18</sup> multishell nanocapsules,<sup>19</sup> and some other novel nanostructures,<sup>20</sup> more active sites were exposed on g-C<sub>3</sub>N<sub>4</sub> for enhanced light harvesting due to significantly increased specific surface area, and the migration rate of photo-generated electrons was promoted and the recombination of electrons and holes reduced.<sup>18–20</sup> Elemental doping was another widely adopted method for reducing the recombination of electron-hole pairs by replacing the lattice defects of g-C<sub>3</sub>N<sub>4</sub>.<sup>21,22</sup> Nevertheless, fabrication of new nanostructures and elemental doping often involve complicated preparation process and uncontrollable results. Compared with these above two methods, hybridization of g-

<sup>a</sup>State Key Laboratory of Biochemical Engineering, Institute of Process Engineering, Chinese Academy of Sciences, Beijing 100190, P. R. China. E-mail: spzhang@ipe.ac.cn; Fax: +86 10 82544958; Tel: +86 10 82544958

<sup>b</sup>University of Chinese Academy of Sciences, Beijing, 100049, P. R. China

<sup>c</sup>School of Pharmaceutical Sciences (Shenzhen), Sun Yat-sen University, Guangzhou 510275, P. R. China

† Electronic supplementary information (ESI) available. See DOI: 10.1039/c8ra02807a



$C_3N_4$  with some other semiconductors was relatively simple but efficient. The hybrid materials, which usually have an unsaturated outer layer electron, can act as a new electron carrier to trap the electrons in the conduction band (CB) of  $g-C_3N_4$  through formation heterojunction or “Z” scheme electron transfer chain.<sup>4,23,24</sup> Nevertheless, either construction of heterojunction or “Z” scheme transfer chain, there are certain requirements for the band structure of hybrid materials, which need a good coordinated relationship with that of  $g-C_3N_4$ .

In recent years, transition metal dichalcogenides (TMDCs) have emerged and received tremendous attentions. TMDCs such as  $WS_2$ ,  $MoS_2$ ,  $WSe_2$ , and  $MoSe_2$ , have various unique electronic, optical, mechanical and chemical properties, promising their potential applications in electronic devices, transistors, energy storage devices and catalysis.<sup>25–27</sup> Among TMDCs, the 2H- $WS_2$  has a band gap of about 2.64 eV, with conduction band (CB) and valence band (VB) positions at  $\approx -1.03$  V and 1.61 V versus normal hydrogen electrode,<sup>26,28</sup> respectively; which means the  $WS_2$  possesses energy level of CB and VB both lower than that of  $g-C_3N_4$ , but the CB offset between  $g-C_3N_4$  and  $WS_2$  is much shorter than the band gap of  $g-C_3N_4$ . Therefore, there would be a perfect band structure coordination between  $WS_2$  and  $g-C_3N_4$  to construct a heterojunction structure. The good match for the energy level would possibly enable fast transfer of the photo-induced electrons in the CB of  $g-C_3N_4$  to the CB of  $WS_2$  before recombination with holes in VB of itself, so that the light harvesting efficiency and utilization of photo-induced electrons would be improved largely.<sup>29–32</sup>

In this present work, a heterogeneous  $WS_2/g-C_3N_4$  composite photocatalyst was prepared *via* ultrasound assisted hydrothermal method. The photocatalytic performance was evaluated through the regeneration of NADH and degradation of RhB under visible light. Detailed investigations of the physicochemical and photochemical properties of the photocatalysts were performed to elucidate the photoinduced electron-transfer mechanism involved in the heterogeneous  $WS_2/g-C_3N_4$  composite photocatalyst. Therefore, our work highlights the promise of constructing heterojunction based on  $g-C_3N_4$  for photocatalyzed NADH regeneration and pollutant degradation, and encourages further in-depth investigations of this novel type of heterojunction for artificial photocatalysis.

## 2. Experimental section

### 2.1. Material

Formate dehydrogenase (FateDH), formaldehyde dehydrogenase (FaldDH), yeast alcohol dehydrogenase (ADH),  $\beta$ -nicotinamide adenine dinucleotide ( $\beta$ -NAD<sup>+</sup>), reduced nicotinamide adenine dinucleotide (NADH), dicyandiamide, triethanolamine (TEOA), dichloro (pentamethylcyclopentadienyl) rhodium(III) dimer, 1,10-phenanthroline were purchased from Sigma-Aldrich. Tungsten disulfide ( $WS_2$ ) was purchased from Shanghai Macklin Biochemical Co., Ltd (Shanghai, China).

The organometallic electron mediator (M),  $[Cp^*Rh(phen)H_2O]^{2+}$ , ( $Cp^* = 5-C_5Me_5$ , phen = 1,10-phenanthroline) was synthesized as follows. Briefly, 103.01 mg of dichloro

(pentamethylcyclopentadienyl) rhodium(III) dimer was added to 10 mL of methylene chloride, where the solid was insoluble. Then, 60.07 mg of 1,10-phenanthroline was added to the mixture. After stirring at room temperature for 3 h, the color of the solution changed from dark orange to orange. After removing the solvent by evaporation under reduced pressure, M was obtained.

### 2.2. Preparation of $g-C_3N_4$ and $WS_2/g-C_3N_4$ composites catalysts

To prepare graphite phase carbon nitride ( $g-C_3N_4$ ), 10 g of dicyandiamide was ground into a powder and placed in a capped alumina crucible covered with aluminum foil and then calcined at 550 °C for 4 hours in a muffle furnace at a rate of 3 °C min<sup>-1</sup>. The  $g-C_3N_4$  was obtained as yellow solid.

$WS_2/g-C_3N_4$  composites were synthesized *via* a two-step self-assembly procedure. Herein, 100 mg of  $g-C_3N_4$  was added into 100 mL deionized water and sonicated for one hour. Into the above suspension, definite amount of  $WS_2$  powder was added to obtain a  $WS_2$  mass fraction of 1, 5, 10%. The suspension mixture was sonicated for 30 min followed by 36 h mechanical stirring. To consolidate the heterojunction interface in the  $WS_2/g-C_3N_4$  composites, the mixture was sealed into a 100 mL Teflon-lined stainless steel autoclave and heated to 140 °C for 6 h. After cooling down to room temperature and evaporating the solvent,  $WS_2/g-C_3N_4$  composites with different composition proportions were obtained.

### 2.3. Catalyst characterization

Scanning electron microscope (SEM) analysis was performed on a JSM 6700F cold field emission scanning electron microscope at beam energy of 10.0 kV. Transmission electron microscope (TEM) images were taken on JEM 2100F instrument at an acceleration voltage of 200 kV. Atomic force microscopy was performed using Bruker FASTSCANIO microscope. Thermo gravimetric analysis (TGA), was carried out in a flow of nitrogen gas (10 mL min<sup>-1</sup>) at a heating rate of 10 °C min<sup>-1</sup> using Synchronous DSC-TGA Thermal Analysis (SDT Q600). The specific surface areas were measured on ASAP 2020HD88 by the BET method. The crystal structures of  $WS_2/g-C_3N_4$  composites were identified by X-ray diffraction (XRD) with Empyrean X-ray diffractometer from PANalytical B.V. of the Netherlands. X-ray photoelectron spectroscopy (XPS) analysis was performed on ESCALAB 250Xi instrument. The Fourier transform infrared (FT-IR) spectra were collected from 400 to 4000 cm<sup>-1</sup> at the spectral resolution of 0.482 cm<sup>-1</sup> on NICOLET iS 50 infrared spectrometer. UV-vis diffuse reflectance spectroscopy (UV-vis DRS) were recorded in the range of 200–900 nm by a TU-1901 spectrophotometer with the reference of  $BaSO_4$ . Photoluminescence (PL) spectra were determined on a NanoLOG-TCSPC steady state/transient fluorescence spectrometer. The wavelength of the excitation light was 340 nm.

### 2.4. Photocatalytic regeneration of NADH

The photocatalytic regeneration of NADH reaction was carried out in a side-irradiation vial under an irradiation of 300 W Xe



lamp with a 400 nm cut-off filter. In the regeneration procedure, the reaction medium (3 mL) was composed of  $\text{NAD}^+$  (1 mM), TEOA (15 w/v%), M (0.25 mM), phosphate buffer (100 mM, pH 7.0) and catalyst (3 mg). The distance between reactor and Xe lamp was fixed at 20 cm. Before irradiation, the reaction solution was placed in a dark environment for 1 h to achieve adsorption–desorption equilibrium. The concentration of NADH regenerated from  $\text{NAD}^+$  was monitored by measuring the absorbance at 340 nm ( $\epsilon^{\text{NADH}} = 6.22 \text{ mM}^{-1} \text{ cm}^{-1}$ ) using a UV-vis spectrophotometer (UV-2800, Unico).

### 2.5. Conversion $\text{CO}_2$ to methanol

The conversion of  $\text{CO}_2$  to methanol was performed in quartz reactor. The reaction solution was composed of 3 mg catalyst, NADH (1 mM),  $\text{KHCO}_3$  (0.1 M), 15 w/v% triethanolamine (TEOA), M (0.125 mM), FateDH (0.2 mg), FaldDH (0.3 mg), and ADH (1.5 mg) in 2 mL 0.1 M PBS buffer (pH 7.0). Prior to the addition of enzyme, the PBS buffer was firstly saturated with gaseous  $\text{CO}_2$ . The amount of methanol was detected by gas chromatograph as described in our previous reports.<sup>11</sup>

### 2.6. Degradation of RhB

The degradation of RhB was performed in quartz reactor. The photocatalytic reaction system consisted of 300 W Xe lamp with a 400 nm cut-off filter. All experiments were conducted at room

temperature. In a typical run, 5 mg of catalysts was added into 5 mL of  $10 \text{ mg L}^{-1}$  RhB solution. Prior to irradiation, the suspension was magnetically stirred in the dark for 1 h to ensure the adsorption–desorption equilibrium. The concentration of RhB was monitored by measuring the absorbance at 554 nm using a UV-vis spectrophotometer (UV-2800, Unico). The procedures of the scavenging experiments of reactive oxygen species were similar to that of the photo degradation experiment. Various scavengers, including isopropyl alcohol (IPA, 1 mM), TEOA (1 mM), KI (1 mM), and 0.5 h nitrogen purging ( $\text{N}_2$ ) were subjected into the RhB solution prior to irradiation.

## 3. Results and discussions

### 3.1. Fabrication and characterization of $\text{WS}_2/\text{g-C}_3\text{N}_4$ composites

The  $\text{WS}_2/\text{g-C}_3\text{N}_4$  composites were fabricated by a two-step self-assembly procedure, the morphologies of  $\text{g-C}_3\text{N}_4$ ,  $\text{WS}_2$  and the 5 wt%  $\text{WS}_2/\text{g-C}_3\text{N}_4$  composites were observed by TEM. As shown in Fig. 1a, a stacked layer structure is clearly observed in the  $\text{g-C}_3\text{N}_4$  sample, which is consistent with existing reports.<sup>33</sup> The  $\text{WS}_2$  sample displays a structure of hexagonal lamellar stacking (Fig. 1b).<sup>34</sup> For  $\text{WS}_2/\text{g-C}_3\text{N}_4$  composites,  $\text{g-C}_3\text{N}_4$  is found to be covered by  $\text{WS}_2$ . The darker part with hexagonal shape in Fig. 1c

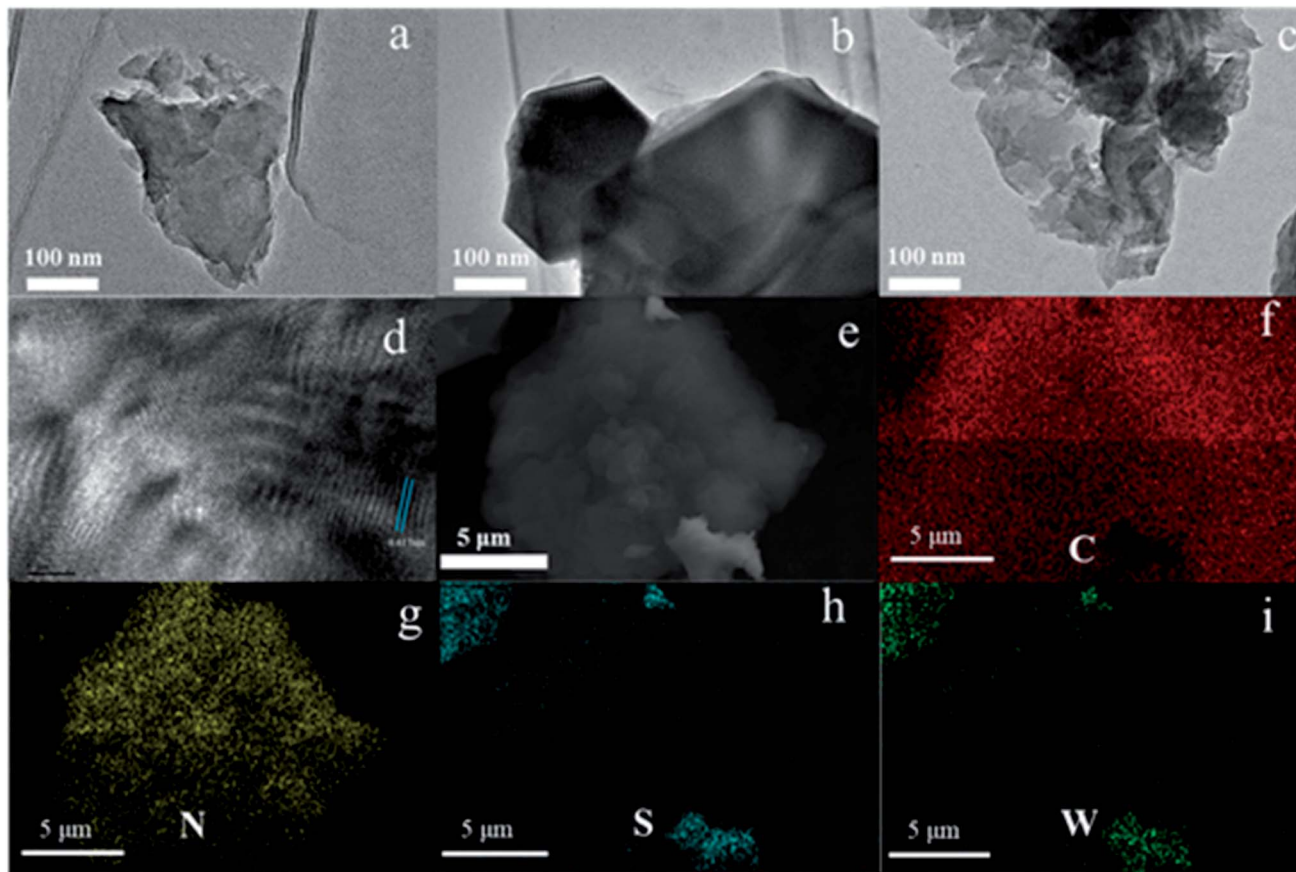


Fig. 1 TEM images of (a)  $\text{g-C}_3\text{N}_4$ , (b)  $\text{WS}_2$ , (c) 5 wt%  $\text{WS}_2/\text{g-C}_3\text{N}_4$  composite and its (d) HRTEM image. (e–i) SEM and the corresponding elemental mapping of C, N, S, and W elements in 5 wt%  $\text{WS}_2/\text{g-C}_3\text{N}_4$  composite.



should be WS<sub>2</sub> and the lighter part is g-C<sub>3</sub>N<sub>4</sub>, which demonstrates the well distribution of WS<sub>2</sub> on g-C<sub>3</sub>N<sub>4</sub>. The high-resolution TEM image shows the microstructure of the WS<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub> composite, in which the interplanar spacing is very close to the 001 plane of WS<sub>2</sub> (Fig. 1d). SEM images (Fig. 1e) of the 5 wt% WS<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub> composite and the corresponding energy-dispersive X-ray spectroscopy (EDS) elemental mapping of C, N, S and W, which are characteristic elements of g-C<sub>3</sub>N<sub>4</sub> and WS<sub>2</sub>, respectively, clearly confirmed the uniform coupling of g-C<sub>3</sub>N<sub>4</sub> with WS<sub>2</sub> (Fig. 1f–i). This coupling would be favorable for the charge transfer between WS<sub>2</sub> and g-C<sub>3</sub>N<sub>4</sub> and then promotes the separation of photo-generated electron–hole pairs. Moreover, the TGA measurement shows that the decomposition temperature of WS<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub> composites is lower than the pristine g-C<sub>3</sub>N<sub>4</sub>. Similar phenomena were also observed in some other g-C<sub>3</sub>N<sub>4</sub>-based heterojunction, such as g-C<sub>3</sub>N<sub>4</sub>/AgBr/Fe<sub>3</sub>O<sub>4</sub>, SnO<sub>2-x</sub>/g-C<sub>3</sub>N<sub>4</sub>, TiO<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub>, DyVO<sub>4</sub>/g-C<sub>3</sub>N<sub>4</sub>, g-C<sub>3</sub>N<sub>4</sub>/SmVO<sub>4</sub>.<sup>24,35–37</sup> The shift of weight loss towards lower temperature was considered due to some changes in surface chemistry of the g-C<sub>3</sub>N<sub>4</sub> during forming of heterojunction structure with other materials (Fig. 2).<sup>38,39</sup>

XRD were adopted to analyze the composition and structure of as-prepared WS<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub> composites. To understand the crystallization of the composite and also mutual interface of

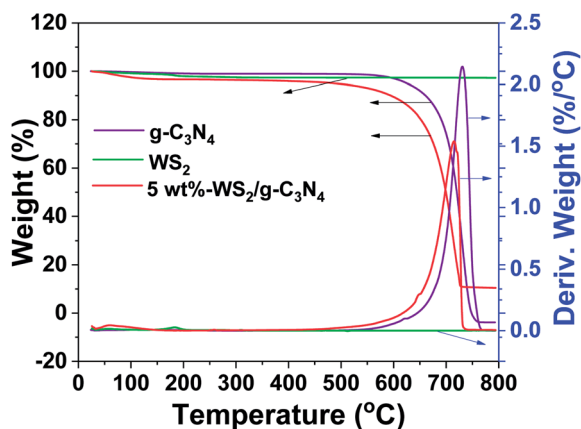


Fig. 2 TGA profiles of g-C<sub>3</sub>N<sub>4</sub>, WS<sub>2</sub> and 5 wt% WS<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub> composite.

each semiconductor over the other during composite formation, the XRD patterns of the following materials were presented in Fig. 3a, which include the obtained WS<sub>2</sub>, hydrothermally treated WS<sub>2</sub> (referred as HT WS<sub>2</sub>) and ultrasonicated WS<sub>2</sub> (referred as US WS<sub>2</sub>) in absence of g-C<sub>3</sub>N<sub>4</sub>; as formed g-C<sub>3</sub>N<sub>4</sub>; ultrasonicated 5% WS<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub> composite (US 5% WS<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub>), hydrothermally treated (HT 5% WS<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub>), as well as the 5% WS<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub> composites fabricated through combined ultrasonication-hydrothermal treatments. As shown in Fig. 3a, the XRD pattern of obtained g-C<sub>3</sub>N<sub>4</sub> showed the typical diffraction peaks at 13.1° and 27.3°, perfectly indexed as the (100) and (002) planes, respectively, which were ascribed to in-planar tri-s-triazine unit and the interplanar stacking of aromatic systems.<sup>17,40–44</sup> The XRD patterns of the obtained WS<sub>2</sub> exhibit many distinct diffraction peaks, indicating its hexagonal structure,<sup>28,34</sup> which is consistent with the 2H configuration in the standard card library. The HT WS<sub>2</sub> and US WS<sub>2</sub> presents the same XRD as that of the obtained WS<sub>2</sub>, indicating the crystallization of WS<sub>2</sub> was not affected by ultrasonication and hydrothermal treatments. For the 5% WS<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub> composites, the XRD patterns of all the three composites display the combination of the two sets of diffraction data for both g-C<sub>3</sub>N<sub>4</sub> and WS<sub>2</sub> and no other phase is detected, implying that WS<sub>2</sub> was not incorporated into the lattice of g-C<sub>3</sub>N<sub>4</sub>.

The FT-IR was also adopted to test the obtained g-C<sub>3</sub>N<sub>4</sub>, WS<sub>2</sub>, and WS<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub> composite. As shown in Fig. 3b, pure g-C<sub>3</sub>N<sub>4</sub> has a much stronger IR response than WS<sub>2</sub>, and the addition of WS<sub>2</sub> shows no obvious effect on the IR spectrum of g-C<sub>3</sub>N<sub>4</sub>. For the g-C<sub>3</sub>N<sub>4</sub>, the strong bands in the region of 1200–1700 cm<sup>-1</sup> are assigned to the typical stretching vibration modes of C–N heterocycles. The peaks at 3000–3700 cm<sup>-1</sup> represent the N–H and O–H stretching vibration. The sharp peak at 810 cm<sup>-1</sup> originates from the characteristic breathing mode of tri-s-triazine units.<sup>45–49</sup> For the WS<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub> composites, the overall patterns of the spectra are the same as the g-C<sub>3</sub>N<sub>4</sub>, confirming the existence of heptazine heterocyclic rings in WS<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub> composites. In generally, there is no obvious difference from the FTIR spectrogram before and after doping, but it's not difficult for us to see that the position of the characteristic peak from the tri-s-triazine vibration of g-C<sub>3</sub>N<sub>4</sub> has a certain degree of shift (Fig. 3c), indicating that there might be some interactions

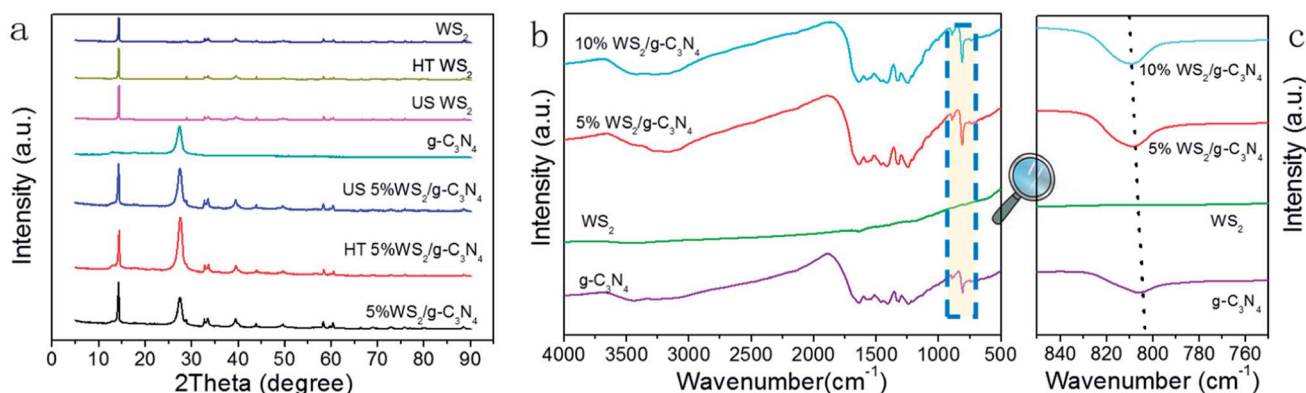


Fig. 3 (a) XRD patterns and (b) FT-IR spectra of obtained g-C<sub>3</sub>N<sub>4</sub>, WS<sub>2</sub>, WS<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub> composites; (c) local magnification of the FT-IR spectra at around 810 cm<sup>-1</sup> of spectra in (b).



between the “nitrogen pots” of  $g\text{-C}_3\text{N}_4$  and W species of  $\text{WS}_2$ .<sup>24</sup> As a complement to FT-IR, the Raman spectra of the  $g\text{-C}_3\text{N}_4$  and the 5%  $\text{WS}_2/g\text{-C}_3\text{N}_4$  were also recorded. As shown in Fig. S1,<sup>†</sup> the catalysts show several very weak distinctive peaks at 458, 679 and  $1220\text{ cm}^{-1}$ , which is basically consistent with the situation of  $g\text{-C}_3\text{N}_4$  reported in the literatures.<sup>50,51</sup> The formation of 5%  $\text{WS}_2/g\text{-C}_3\text{N}_4$  composite did not lead to apparent new peak, which may be due to the strong photoluminescence effect of  $g\text{-C}_3\text{N}_4$  and the small fraction of  $\text{WS}_2$  in the composite.

X-ray photoelectron spectroscopy (XPS) analysis was employed to determine the chemical composition and bonding configuration of the  $g\text{-C}_3\text{N}_4$ ,  $\text{WS}_2$  and the  $\text{WS}_2/g\text{-C}_3\text{N}_4$  composites (Fig. 4a), with the high-resolution spectrum of each sample were illustrated in Fig. 4b–d. The survey XPS spectra shown in

Fig. 4a indicate that the prepared  $\text{WS}_2/g\text{-C}_3\text{N}_4$  samples are composed of C, N, W and S. Specifically, the C1s spectrum (Fig. 4d1) of  $\text{WS}_2/g\text{-C}_3\text{N}_4$  composites show there are two C1s peaks located at 284.7 and 288.2 eV, the former is ascribed to the adventitious hydrocarbon from the XPS instrument, while the latter is assigned to  $\text{sp}^2$ -bonded carbon atom ( $\text{N}=\text{C}=\text{N}$ ) of  $g\text{-C}_3\text{N}_4$  in aromatic rings. The high-resolution N1s spectrum of the  $\text{WS}_2/g\text{-C}_3\text{N}_4$  composites could be fitted into four peaks (Fig. 4d2). The peaks centered at 398.7 and 399.5 eV were attributed to  $\text{sp}^2$ -hybridized nitrogen atom ( $\text{C}=\text{N}-\text{C}$  group) and tertiary nitrogen ( $\text{N}-\text{C}_3$  group or  $\text{H}-\text{N}-\text{C}_2$ ), respectively; the peaks at 401.0 and 404.7 eV derived from amino function groups and charging effect localization in heterocycles, respectively.<sup>4,24,52</sup> As compared with the C1s and N1s spectrum (Fig. 4b1 and b2) of pure  $g\text{-C}_3\text{N}_4$ , all

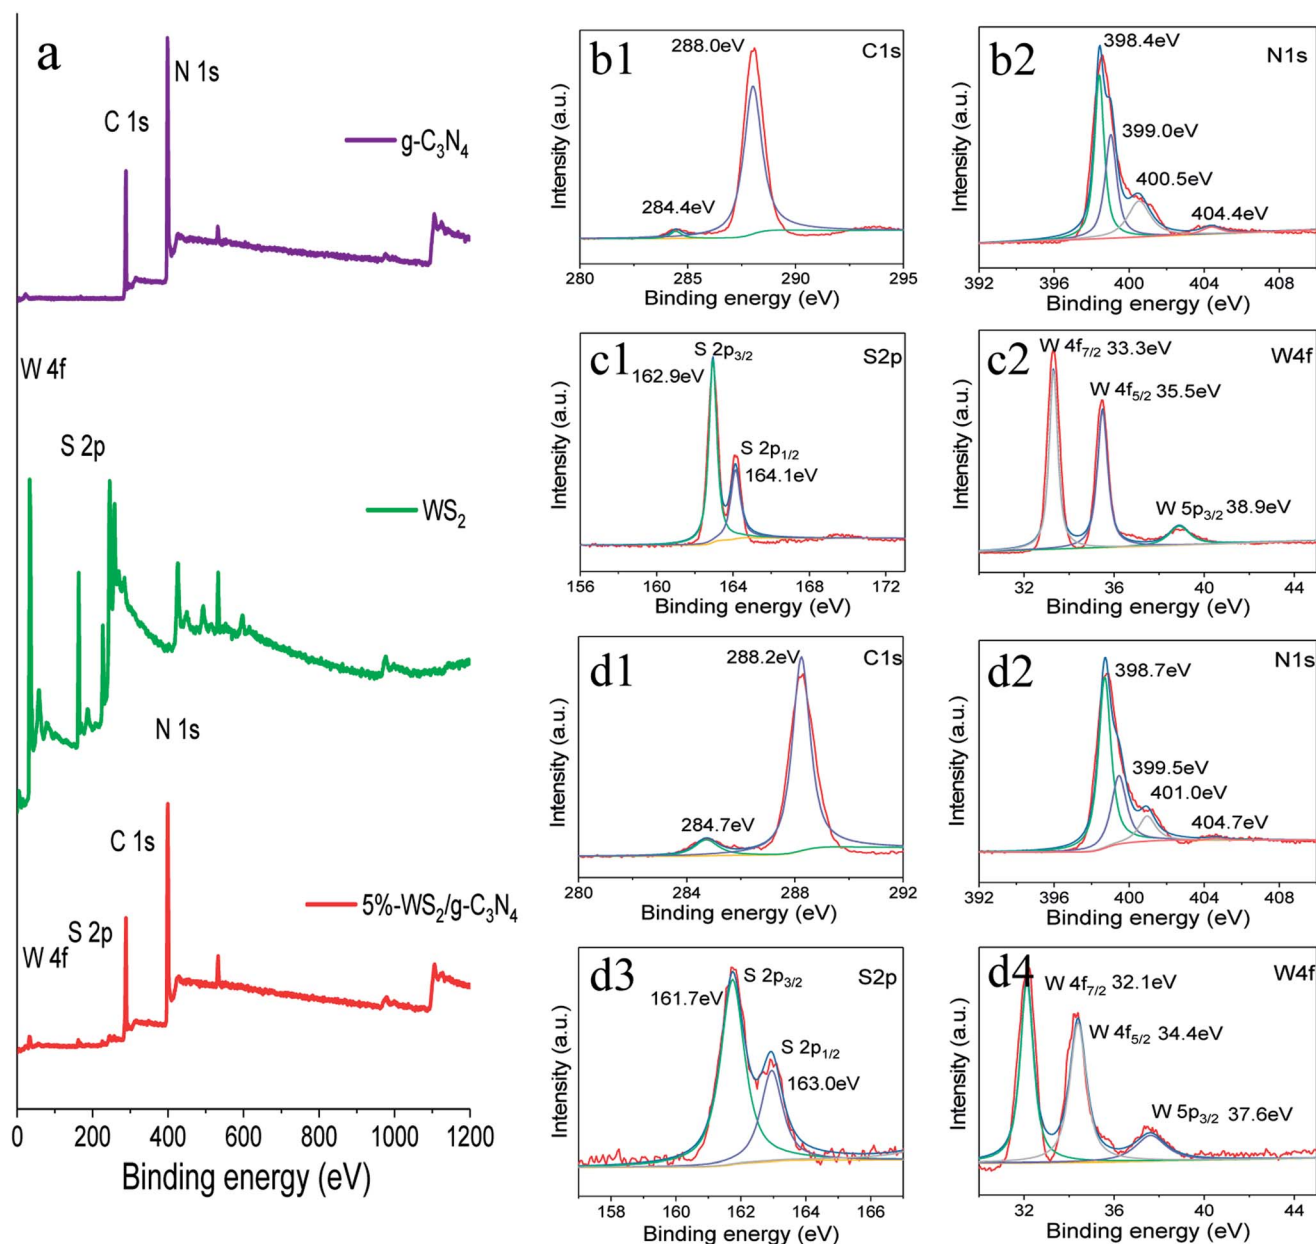


Fig. 4 The XPS survey spectra of (a)  $g\text{-C}_3\text{N}_4$ ,  $\text{WS}_2$  and 5 wt%  $\text{WS}_2/g\text{-C}_3\text{N}_4$  composite. High resolution C1s (b1), N1s (b2) spectra from  $g\text{-C}_3\text{N}_4$  and S2p (c1) W4f (c2) spectra from  $\text{WS}_2$ , as well as C1s (d1), N1s (d2), S2p (d3), W4f (d4) spectra from 5 wt%  $\text{WS}_2/g\text{-C}_3\text{N}_4$  composite.



those peaks of the WS<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub> composites shifted to a position with a higher binding energy.

Fig. 4d3 and d4 display the S2p spectra and the W4f spectra of the WS<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub> composites. The peaks at 161.7 and 163 eV can be ascribed to the S<sup>2-</sup> species, donated as S2p<sub>3/2</sub> and S2p<sub>1/2</sub>, respectively;<sup>34</sup> the W4f peaks at 32.1, 34.4, and 37.6 eV can be ascribed to the W<sup>4+</sup> species, donated as W4f<sub>7/2</sub>, W4f<sub>5/2</sub> and W5p<sub>3/2</sub>.<sup>28,53</sup> In contrast to the W4f and S2p spectrum (Fig. 4c1 and c2) of WS<sub>2</sub>, all these above peaks of the WS<sub>2</sub> shifted to a position with a lower binding energy after coupling with g-C<sub>3</sub>N<sub>4</sub>. Thus, the C1s and N1s peaks of g-C<sub>3</sub>N<sub>4</sub> shifted toward the higher binding energy, while the W4f and S2p peaks of WS<sub>2</sub> shifts towards the lower binding energy. It was suggested that there might be some S–C chemical bonds formed between the heterojunction interfaces of WS<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub> composites, thus electron transfer could occur from g-C<sub>3</sub>N<sub>4</sub> to WS<sub>2</sub> at this interfaces due to their different electron concentration.<sup>24,54</sup>

The optical properties of WS<sub>2</sub>, g-C<sub>3</sub>N<sub>4</sub> and the WS<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub> composites were revealed by the UV-vis diffuse reflectance spectra (DRS). As shown in Fig. 5a, pure g-C<sub>3</sub>N<sub>4</sub> had absorption from UV to visible region, with an absorption edge at 460 nm, which corresponding to a band gap about 2.7 eV according to the Kubelka–Munk conversion (Fig. 5b).<sup>55,56</sup> However, with the coupling of WS<sub>2</sub>, the absorption range of the composite became wider than that of pure g-C<sub>3</sub>N<sub>4</sub>, a remarkable enhanced light-harvesting ability is observed for the WS<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub>, and the band gap width estimated from the K–M equation became narrower accordingly, which implied that the light absorption ability of the WS<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub> composites became stronger. The coupling of WS<sub>2</sub> on g-C<sub>3</sub>N<sub>4</sub> may generate an impurity energy level in the valence band (VB) and narrow the band gap. The defect energy levels increased the light absorption efficiency of the materials and thus may exhibit photocatalytic performance superior to that of the individual material. In addition, the DRS spectra of US 5% WS<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub> and HT 5% WS<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub> composites were also measured and compared with that of the 5% WS<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub>, it is indicated that the omitting the ultrasonication or hydrothermal treatments during composite formation lead to negligible changes in the band structure (Fig. S2†).

Fig. 6 presents the BET surface areas measurement of 5 wt% WS<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub> composites. For comparison, the surface areas of g-C<sub>3</sub>N<sub>4</sub> and the physical mixture of g-C<sub>3</sub>N<sub>4</sub> with 5 wt% WS<sub>2</sub> (referred as PM-WS<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub> in the following text) were also determined, the results were listed in Table S2.† The specific surface area of g-C<sub>3</sub>N<sub>4</sub> was 7.34 m<sup>2</sup> g<sup>-1</sup>, which is similar to the value reported by He *et al.*,<sup>24</sup> but lower than those reported for most g-C<sub>3</sub>N<sub>4</sub> nanosheets,<sup>54,57</sup> which indicates that the g-C<sub>3</sub>N<sub>4</sub> has multi-layered structure. Slight decrease in surface area was observed for the PM-WS<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub> (6.87 m<sup>2</sup> g<sup>-1</sup>); while the 5 wt% WS<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub> composites exhibited much higher BET values (12.22 m<sup>2</sup> g<sup>-1</sup>), which indicated that some reactions might have occurred between g-C<sub>3</sub>N<sub>4</sub> and WS<sub>2</sub> during recombination. This larger specific surface area of WS<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub> composites also could supply more reactive sites for light and substrates, improve the whole efficiency of the reaction. It should be noted that the specific surface area of the 5 wt% WS<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub> composites are still far lower than the g-C<sub>3</sub>N<sub>4</sub> nanosheets, indicating the ultrasonication and hydrothermal treatments during composite formation still could not result in effective exfoliation of the g-C<sub>3</sub>N<sub>4</sub>. After BJH (Barrett–Joyner–Halenda) plotting, the pore size distribution of each samples were analyzed (Fig. 6b). Compared with the pure g-C<sub>3</sub>N<sub>4</sub>, coupling of WS<sub>2</sub> lead to slight decrease in pore diameter.

### 3.2. Photocatalytic performance for NADH regeneration and CO<sub>2</sub> reduction

Conversion of CO<sub>2</sub> to methanol through redox multienzymatic cascade reaction has been widely explored.<sup>7,10,12</sup> However, consumption of the expensive NADH cofactor at stoichiometric ratios imposes great hurdles to the practice of these processes. Here in the present work, we intended to develop a biocatalyzed artificial photosynthesis system by coupling the reduction of CO<sub>2</sub> catalyzed by FateDH, FaldDH, and ADH with the newly developed WS<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub> composite as the photocatalyst to regenerate NADH using solar energy.

Based on the above photochemical investigations of the g-C<sub>3</sub>N<sub>4</sub> and the WS<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub> composites, their performance for visible light-driven photocatalytic NADH regeneration were

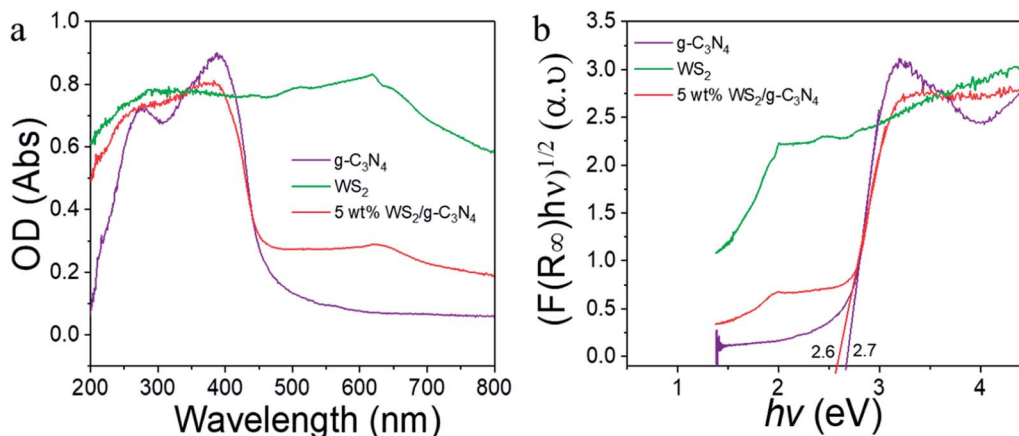


Fig. 5 (a) UV-vis diffuse reflection spectra of pure g-C<sub>3</sub>N<sub>4</sub>, WS<sub>2</sub> and 5 wt% WS<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub> composite; (b) corresponding bandgap of pure g-C<sub>3</sub>N<sub>4</sub>, WS<sub>2</sub> and 5 wt% WS<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub> composite estimated from Kubelka–Munk equation.



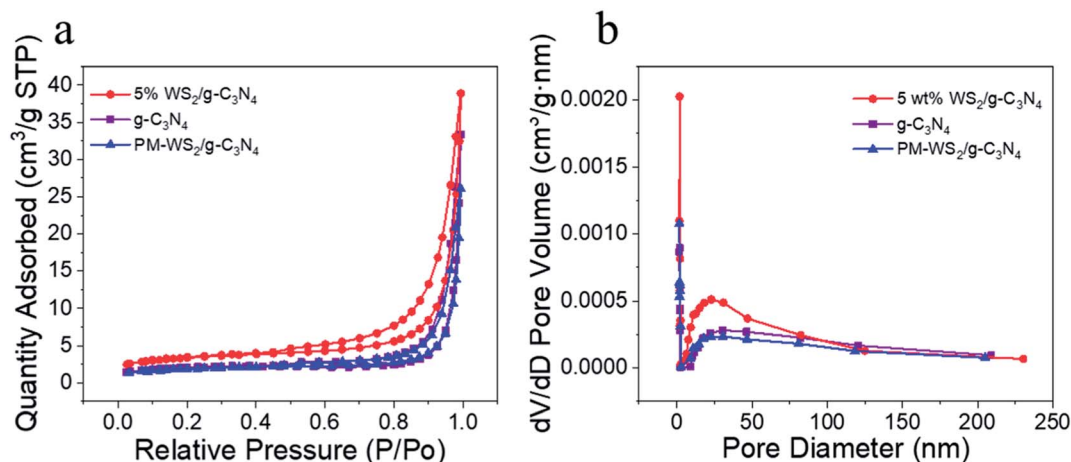


Fig. 6 (a) The N<sub>2</sub> adsorption/desorption isotherms, (b) the corresponding pore-size distribution. BET surface area was measured by nitrogen sorption isotherms at 77.5 K and up to 1.03 bar.

examined. The reactant solution consisted of 15 wt% TEOA, 0.25 mM electron mediator M, and NAD<sup>+</sup> with an initial concentration of 1 mM and an active g-C<sub>3</sub>N<sub>4</sub> content of 1 mg mL<sup>-1</sup> was maintained in all the experiments. The photocatalytic activity comparison among pure g-C<sub>3</sub>N<sub>4</sub>, WS<sub>2</sub>, PM-WS<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub> and WS<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub> composite with WS<sub>2</sub> content of 1%, 5% and 10% are presented in Fig. 7a. The monolithic g-C<sub>3</sub>N<sub>4</sub> and WS<sub>2</sub> had rather low catalytic efficiency, NADH regeneration yield at 6 h was below 10%. By physically mixing 5 wt% WS<sub>2</sub> with g-C<sub>3</sub>N<sub>4</sub>, the NADH photo-regeneration yield enhanced to 15%. While the 5 wt% WS<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub> composite presents the best performance, a NADH yield of 37.1% was achieved, which were about four times of those obtained by using monolithic g-C<sub>3</sub>N<sub>4</sub> and WS<sub>2</sub>. With further increasing the WS<sub>2</sub> content in the composite to 10 wt%, however, leading to decrement in activity for the photo-regeneration of NADH. Presumably, coupling of high amount WS<sub>2</sub> may lead to shielding of active site of g-C<sub>3</sub>N<sub>4</sub> by WS<sub>2</sub> or loss of favorable interfaces between g-C<sub>3</sub>N<sub>4</sub> and WS<sub>2</sub>. Similar phenomenon was also observed on the activity of

mesoporous graphitic carbon nitride (mpg-CN) loaded with WS<sub>2</sub> towards H<sub>2</sub> generation. About 0.3 at% WS<sub>2</sub> loading amount was found optimal to reach highest rate of hydrogen evolution, and heavy loading of WS<sub>2</sub> led to decrease in activity of the heterojunctions photocatalyst.<sup>29</sup>

To justify the necessity of multiplicative steps involving ultrasonication, mechanical stirring and hydrothermal treatment for the preparation of WS<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub>, a series of WS<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub> composites were prepared by simpler steps and evaluated for its activity towards NADH photoregeneration. Results presented in Fig. S3 and Table S3† clearly indicated that either omitting of the ultrasonication or hydrothermal treatments, or even the mechanical stirring between these two operations during composite formation, led to significantly lower activity of the fabricated WS<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub>. The hydrothermal time and temperature did not show remarkable influence on the activity of the composite photocatalyst. Therefore, the two-step sonication and subsequent hydrothermal treatments are necessary, though somewhat tedious, to ensure the photocatalyst a high activity of

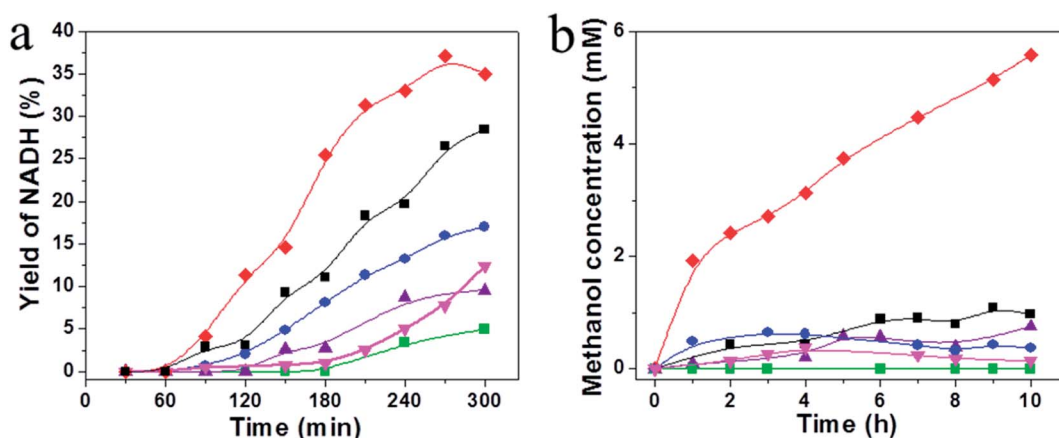


Fig. 7 (a) Photocatalytic NADH regeneration by (▲) g-C<sub>3</sub>N<sub>4</sub>, (■) WS<sub>2</sub>, (●) PM-WS<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub>, (▼) 1 wt% WS<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub>, (◆) 5 wt% WS<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub>, and (■) 10 wt% WS<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub> composite. A reaction medium was composed of photocatalyst (1 mg mL<sup>-1</sup>), NAD<sup>+</sup> (1 mM), TEOA (15 w/v%) and M (0.25 mM) in 100 mM, pH 7.0 phosphate buffer. (b) The production of methanol as a function of time.



the 5 wt% WS<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub> composite, which presents the highest NADH photo regeneration yield of 37.1%. It was believed that the first step of sonication was to ensure a good dispersion of g-C<sub>3</sub>N<sub>4</sub> particles, the second step of sonication of g-C<sub>3</sub>N<sub>4</sub> and WS<sub>2</sub> mixture was for a full contact between these two materials, which was crucial for the subsequent hydrothermal reaction.

In another set of experiment, we tried to address the more challenging question of a potential mediator-free regeneration of NADH. To our surprise, the mediator-free with system with 5 wt% WS<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub> composite as photocatalyst was also possible, though the regeneration yield at 6 h was only about half of that obtained in presence of M (Fig. S3, Table S3†). This can be explained from the following two points. Firstly, a mixture of 1,4-NADH and 1,6-NADH would possibly formed, while in presence of M, 1,4-NADH will be unique production; secondly, without a strong redox agent, *i.e.*, mediator, g-C<sub>3</sub>N<sub>4</sub> also catalyzes the back reaction, meaning an equilibrium between NAD<sup>+</sup> and NADH.<sup>18</sup>

We then evaluated the WS<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub> composite as a photocatalyst of the artificial photosynthesis system for bioconversion of CO<sub>2</sub> to methanol. As expected, the photocatalysts showed higher activity for NADH regeneration also exhibited

higher efficiency for methanol synthesis from CO<sub>2</sub>, when the NADH photoregeneration process was coupled with the biocatalytic process. The highest methanol concentration up to 5.58 mM were obtained by using 5 wt% WS<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub> composite as photocatalysts, corresponding to a methanol productivity of 372.1 μmol h<sup>-1</sup> g<sub>cat</sub><sup>-1</sup>, which was about 7.5 times higher than that obtained by using g-C<sub>3</sub>N<sub>4</sub> (50.31 μmol h<sup>-1</sup> g<sub>cat</sub><sup>-1</sup>). This result clearly indicated that the formation of WS<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub> heterojunction generated significant photo-synergistic effect and played key roles in the enhancement in the photocatalytic activity.

### 3.3. Photocatalytic performance for RhB degradation

To further demonstrate the effectiveness of formation of heterojunction structures between the components of the WS<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub> composites, the photocatalytic activity of the composites for the degradation of RhB was also evaluated, and results were compared with pure g-C<sub>3</sub>N<sub>4</sub> and WS<sub>2</sub>. As shown in Fig. 8a, the degradation ratio of RhB reached to about 100% by using the 5 wt% WS<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub> composites under visible light irradiation for 60 min, which was much higher than the corresponding

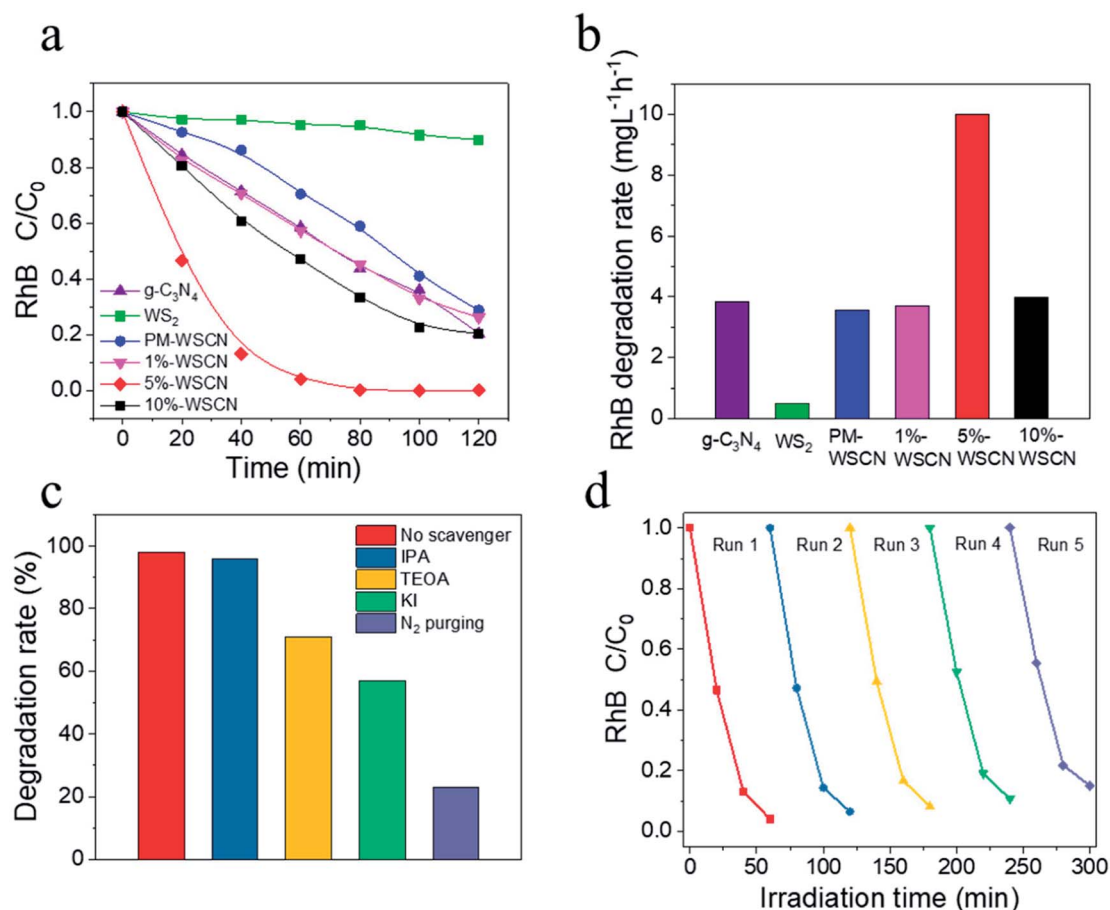


Fig. 8 (a) Photocatalytic degradation profiles of RhB under visible light irradiation in the presence of (▲) g-C<sub>3</sub>N<sub>4</sub>, (■) WS<sub>2</sub>, (●) PM-WS<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub>, (▼) 1 wt% WS<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub>, (◆) 5 wt% WS<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub>, and (■) 10 wt% WS<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub> composite; (b) the comparison chart of RhB degradation rate after 1 h's irradiation catalyzed by various catalysts; (c) effects of different scavengers on degradation of RhB in the presence of 5 wt% WS<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub> composite catalyst under visible-light irradiation; and (d) reusability of the 5 wt% WS<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub> composite catalyst for five successive runs (each run was lasted for 60 min).





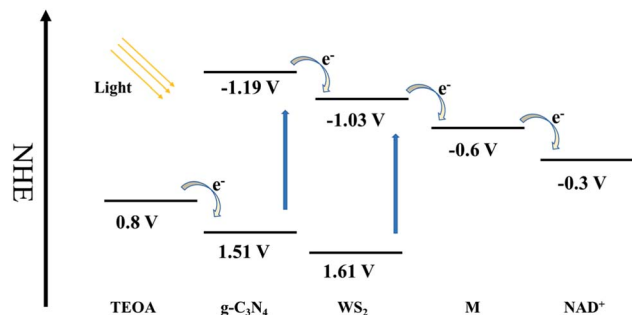


Fig. 9 Schematic diagram of electron flow and energy level during coenzyme regeneration.

degradation ratios obtained by using pristine  $g\text{-C}_3\text{N}_4$  ( $\sim 70\%$  at 120 min) and  $\text{WS}_2$  ( $\sim 10\%$  at 120 min), as well as the  $\text{PM-WS}_2/g\text{-C}_3\text{N}_4$  ( $\sim 70\%$  at 120 min). Fig. 8b presents the apparent degradation rate derived by simple linearly plotting of RhB concentration decrease against irradiation time. The results indicate that the degradation rate using composite photocatalyst containing 5 wt%  $\text{WS}_2$  was about 2.6 and 19.7 times higher than that of  $g\text{-C}_3\text{N}_4$  and  $\text{WS}_2$ , respectively.

In general, some reactive oxygen species including hydroxyl radicals ( $\cdot\text{OH}$ ) and superoxide radicals ( $\cdot\text{O}_2^-$ ), as well as holes ( $h^+$ ) are expected to be involved in the photocatalytic process of RhB degradation.<sup>55,58</sup> To investigate the role of these reactive species, the effects of some radical scavengers and  $\text{N}_2$  purging on the photodegradation of RhB were studied to propose the possible photocatalytic mechanism. Results in Fig. 8c indicate that the addition of IPA ( $\cdot\text{OH}$  scavengers) had almost no effect on RhB degradation. While addition of TEOA ( $h^+$  scavengers) and KI (scavenger of both  $\cdot\text{OH}$  and  $h^+$ ) led the degradation rate after 1 h's irradiation decreased to about 70% and 58%, respectively. When  $\text{N}_2$  purging was conducted which acts as  $\cdot\text{O}_2^-$  scavenger, the degradation rate decreased dramatically to about only 22%. These results suggested that the  $\cdot\text{O}_2^-$  plays major roles in the photodegradation of RhB catalyzed by the  $\text{WS}_2/g\text{-C}_3\text{N}_4$  heterojunction photocatalyst, which is consistent with results in other reports.<sup>55,58</sup>

Reusability of photocatalyst is a very important parameter from an economical viewpoint. The reusability and stability of

the 5 wt%  $\text{WS}_2/g\text{-C}_3\text{N}_4$  composites was examined by measuring the RhB degradation during repeated usages. As shown in Fig. 8d, after five successive runs, there is no remarkable decrease in its activity. Hence, the photocatalyst has a good stability during the photocatalytic reactions.

### 3.4. Proposed mechanism

High efficient charge separation was the crucial fact for the improvement of photocatalytic activity. Construction of heterojunction structure is one of the most effective means to improve photocatalytic activity *via* fast and efficient transfer photo-excited electron in the CBs in the heterojunction. In this study,  $\text{WS}_2$  was hybridized with  $g\text{-C}_3\text{N}_4$  to generate an efficient heterojunction structure. Based on the energy band structure of  $g\text{-C}_3\text{N}_4$  and  $\text{WS}_2$ , as shown in Fig. 9, the CB and VB of  $g\text{-C}_3\text{N}_4$  are all higher than that of  $\text{WS}_2$ .<sup>24,28</sup> Because of the unstable state of photo-generated electrons and holes, they will tend to recombine quickly to achieve steady state. However, due to the distance between CB of  $g\text{-C}_3\text{N}_4$  and CB of  $\text{WS}_2$  is much shorter than the band gap of  $g\text{-C}_3\text{N}_4$ , the CB offset of 0.16 eV will possibly drive the photo-excited electrons on the CB of  $g\text{-C}_3\text{N}_4$  transfer to the CB of  $\text{WS}_2$  before recombination with holes in the VB of  $g\text{-C}_3\text{N}_4$ . Based on the similar mechanism, the holes in the VB of  $\text{WS}_2$  tend to transfer to the VB of  $g\text{-C}_3\text{N}_4$ , driven by the VB offset of 0.10 eV. Therefore, an orientated transfer of the charge carrier across the heterojunction interface was realized.

To further demonstrate the photoinduced electron-transfer mechanism, as well as elucidate the effect of amount of  $\text{WS}_2$  in  $\text{WS}_2/g\text{-C}_3\text{N}_4$  heterojunction on the overall reaction efficiency, detailed investigations of the photochemical properties were performed on  $\text{WS}_2/g\text{-C}_3\text{N}_4$  heterojunction hybridized with different amount of  $\text{WS}_2$  ranging from 1 wt% to 10 wt%. For most semiconductors, photogenerated electrons and holes can bind after the excitation by incident light, leading to the transfer of partial energy to fluorescence. In general, the binding efficiency and photoelectron lifetime can be measured by monitoring fluorescence intensity and lifetime.<sup>17,57,59,60</sup> Fig. 10a presents the fluorescence spectrum of pure  $g\text{-C}_3\text{N}_4$ , which shows strong fluorescence intensity at 437 nm. However, the

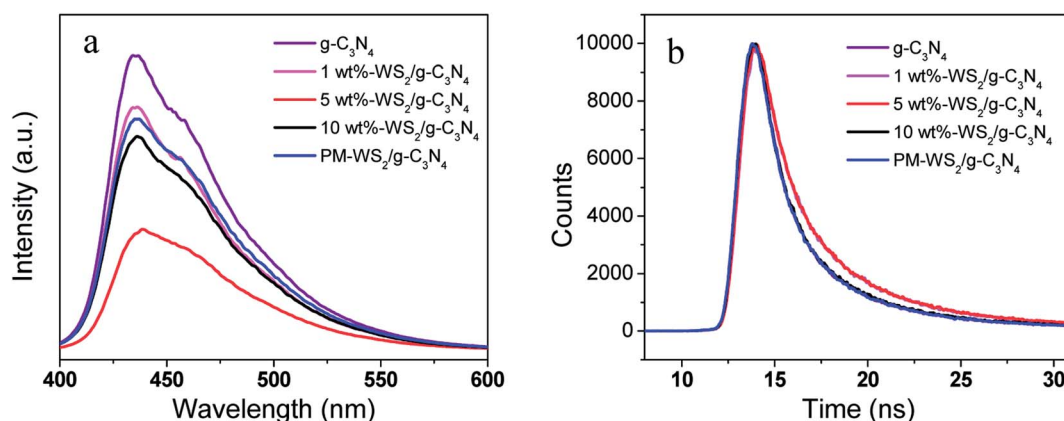


Fig. 10 (a) PL spectra of  $g\text{-C}_3\text{N}_4$ ,  $\text{WS}_2$  and  $\text{WS}_2/g\text{-C}_3\text{N}_4$  composite photocatalysts. (b) Excited state electron radioactive decay of  $g\text{-C}_3\text{N}_4$ ,  $\text{WS}_2$  and  $\text{WS}_2/g\text{-C}_3\text{N}_4$  composite.



physical mixing WS<sub>2</sub> and g-C<sub>3</sub>N<sub>4</sub> (PM-WS<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub>) and the WS<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub> heterojunction all show a decremental effect on the fluorescence spectra. More interesting, the WS<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub> heterojunction with 5 wt% WS<sub>2</sub> presents the lowest fluorescence intensity, which means more electrons on the CB of g-C<sub>3</sub>N<sub>4</sub> transfer to WS<sub>2</sub> instead of recombining with the holes in the VB of g-C<sub>3</sub>N<sub>4</sub>. The suppressed recombination of electron-hole pairs of g-C<sub>3</sub>N<sub>4</sub> may attribute to the fast electron transfer from CB of g-C<sub>3</sub>N<sub>4</sub> to the CB of WS<sub>2</sub>, which also demonstrate the electron transfer mechanism and explain the highest activity of 5 wt% WS<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub> heterojunction.

In order to confirm the suppressed recombination of electron-hole pairs in 5 wt% WS<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub> heterojunction, time-resolved fluorescence decay analysis was carried out. The excited state electron radioactive decay lifetime (Fig. 10b) show that the 5 wt% WS<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub> heterojunction owns the longest fluorescence lifetime (11.080 ns) compared with that of 10 wt% WS<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub> (10.549 ns), 1 wt% WS<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub> (10.368 ns), PM-WS<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub> (10.554 ns), and g-C<sub>3</sub>N<sub>4</sub> (10.487 ns), indicating that the incorporation of WS<sub>2</sub> increased the photoelectron lifetime of WS<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub>. This result further certified that 5 wt% WS<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub> heterojunction has the best coordination between g-C<sub>3</sub>N<sub>4</sub> and WS<sub>2</sub> for the most efficient and fastest photo-excited electrons transfer.

## 4. Conclusions

In summary, we successfully fabricated and applied a heterogeneous WS<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub> composite photocatalyst for methanol conversion from CO<sub>2</sub> and pollutant degradation under irradiation of visible light. A methanol generation rate of 372.1 μmol h<sup>-1</sup> g<sub>cat</sub><sup>-1</sup>, and 100% RhB removing efficiency within 1 h were achieved by using 5wt% WS<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub> heterojunction, which were improved greatly compared with pure g-C<sub>3</sub>N<sub>4</sub>. Based on detailed investigations of the photochemical properties, the heterojunction structure of WS<sub>2</sub>/g-C<sub>3</sub>N<sub>4</sub> composite was correlated with their electron-transfer efficacy and the overall reaction efficiency. The results show that the band structure coordination between WS<sub>2</sub> and g-C<sub>3</sub>N<sub>4</sub> made it possible to construct a structure of heterojunction. The photo-induced electrons in the CB of g-C<sub>3</sub>N<sub>4</sub> would transfer to the CB of WS<sub>2</sub> before recombination with holes in VB of g-C<sub>3</sub>N<sub>4</sub>, so that the recombination of electron-hole pairs was eliminated and coefficient of utilization of photo-induced electrons was improved greatly. This work provides a novel platform for the efficient and sustained production of a broad range of chemicals and fuels from sunlight.

## Conflicts of interest

The authors declare no conflicts of interest.

## Acknowledgements

The authors thank the support from the National Natural Science Foundation of China (Grant No. 91534126 and 21676276).

## Notes and references

- 1 S. Ye, R. Wang, M.-Z. Wu and Y.-P. Yuan, *Appl. Surf. Sci.*, 2015, **358**, 15–27.
- 2 K. Sekizawa, K. Maeda, K. Domen, K. Koike and O. Ishitani, *J. Am. Chem. Soc.*, 2013, **135**, 4596–4599.
- 3 W. Wang, S. Wang, X. Ma and J. Gong, *Chem. Soc. Rev.*, 2011, **40**, 3703–3727.
- 4 Y. He, Y. Wang, L. Zhang, B. Teng and M. Fan, *Appl. Catal., B*, 2015, **168**, 1–8.
- 5 Y. Amao, *ChemCatChem*, 2011, **3**, 458–474.
- 6 F. S. Baskaya, X. Zhao, M. C. Flickinger and P. Wang, *Appl. Biochem. Biotechnol.*, 2010, **162**, 391–398.
- 7 B. C. D. Obert and R. Obert, *J. Am. Chem. Soc.*, 1999, **121**, 12192–12193.
- 8 X. Tong, B. El-Zahab, X. Zhao, Y. Liu and P. Wang, *Biotechnol. Bioeng.*, 2011, **108**, 465–469.
- 9 H. Wu, C. Tian, X. Song, C. Liu, D. Yang and Z. Jiang, *Green Chem.*, 2013, **15**, 1773–1789.
- 10 Y. Jiang, Q. Sun, L. Zhang and Z. Jiang, *J. Mater. Chem.*, 2009, **19**, 9068–9074.
- 11 X. Ji, Z. Su, P. Wang, G. Ma and S. Zhang, *Small*, 2016, **12**, 4753–4762.
- 12 X. Ji, Z. Su, P. Wang, G. Ma and S. Zhang, *ACS Nano*, 2015, **9**, 4600–4610.
- 13 F. L. Yang, F. F. Xia, J. Hu, C. Z. Zheng, J. H. Sun and H. B. Yi, *RSC Adv.*, 2018, **8**, 1899–1904.
- 14 K. Xu and J. Feng, *RSC Adv.*, 2017, **7**, 45369–45376.
- 15 P. Wang, I. Sinev, F. Sun, H. Li, D. Wang, Q. Li, X. Wang, R. Marschall and M. Wark, *RSC Adv.*, 2017, **7**, 42774–42782.
- 16 X. Wang, K. Maeda, A. Thomas, K. Takanebe, G. Xin, J. M. Carlsson, K. Domen and M. Antonietti, *Nat. Mater.*, 2009, **8**, 76–80.
- 17 P. Niu, L. Zhang, G. Liu and H.-M. Cheng, *Adv. Funct. Mater.*, 2012, **22**, 4763–4770.
- 18 J. Liu and M. Antonietti, *Energy Environ. Sci.*, 2013, **6**, 1486–1493.
- 19 Z. Tong, D. Yang, Z. Li, Y. Nan, F. Ding, Y. Shen and Z. Jiang, *ACS Nano*, 2017, **11**, 1103–1112.
- 20 Z. Tong, D. Yang, Y. Sun, Y. Nan and Z. Jiang, *Small*, 2016, **12**, 4093–4101.
- 21 G. Liu, P. Niu, C. H. Sun, S. C. Smith, Z. G. Chen, G. Q. Lu and H. M. Cheng, *J. Am. Chem. Soc.*, 2010, **132**, 11642–11648.
- 22 X. C. Wang, X. F. Chen, A. Thomas, X. Z. Fu and M. Antonietti, *Adv. Mater.*, 2009, **21**, 1609–1612.
- 23 X. Lu, Q. Wang and D. Cui, *J. Mater. Sci. Technol.*, 2010, **26**, 925–930.
- 24 Y. He, L. Zhang, M. Fan, X. Wang, M. L. Walbridge, Q. Nong, Y. Wu and L. Zhao, *Sol. Energy Mater. Sol. Cells*, 2015, **137**, 175–184.
- 25 Y. Liu, X. She, X. Zhang, C. Liang, J. Wu, P. Yu, Y. Nakanishi, B. Xie, H. Xu, P. M. Ajayan and W. Yang, *RSC Adv.*, 2017, **7**, 55269–55275.
- 26 B. Peng, P. K. Ang and K. P. Loh, *Nano Today*, 2015, **10**, 128–137.



- 27 Q. Lu, Y. Yu, Q. Ma, B. Chen and H. Zhang, *Adv. Mater.*, 2016, **28**, 1917–1933.
- 28 B. Mahler, V. Hoepfner, K. Liao and G. A. Ozin, *J. Am. Chem. Soc.*, 2014, **136**, 14121–14127.
- 29 Y. Hou, Y. Zhu, Y. Xu and X. Wang, *Appl. Catal., B*, 2014, **156–157**, 122–127.
- 30 M. S. Akple, J. Low, S. Wageh, A. A. Al-Ghamdi, J. Yu and J. Zhang, *Appl. Surf. Sci.*, 2015, **358**, 196–203.
- 31 Y. Ma, J. Li, E. Liu, J. Wan, X. Hu and J. Fan, *Appl. Catal., B*, 2017, **219**, 467–478.
- 32 X. Xu, Y. Liu, Y. Zhu, X. Fan, Y. Li, F. Zhang, G. Zhang and W. Peng, *ChemElectroChem*, 2017, **4**, 1498–1502.
- 33 T. Zhou, Y. Xu, H. Xu, H. Wang, Z. Da, S. Huang, H. Ji and H. Li, *Ceram. Int.*, 2014, **40**, 9293–9301.
- 34 G. Pagona, C. Bittencourt, R. Arenal and N. Tagmatarchis, *Chem. Commun.*, 2015, **51**, 12950–12953.
- 35 A. Akhundi and A. Habibi-Yangjeh, *Ceram. Int.*, 2015, **41**, 5634–5643.
- 36 J. Lei, Y. Chen, F. Shen, L. Wang, Y. Liu and J. Zhang, *J. Alloys Compd.*, 2015, **631**, 328–334.
- 37 H. Xiao, W. Wang, G. Liu, Z. Chen, K. Lv and J. Zhu, *Appl. Surf. Sci.*, 2015, **358**, 313–318.
- 38 Y. He, J. Cai, T. Li, Y. Wu, Y. Yi, M. Luo and L. Zhao, *Ind. Eng. Chem. Res.*, 2012, **51**, 14729–14737.
- 39 T. Li, L. Zhao, Y. He, J. Cai, M. Luo and J. Lin, *Appl. Catal., B*, 2013, **129**, 255–263.
- 40 X. Wang, K. Maeda, A. Thomas, K. Takanebe, G. Xin, J. M. Carlsson, K. Domen and M. Antonietti, *Nat. Mater.*, 2009, **8**, 76–80.
- 41 X. Wang, X. Chen, A. Thomas, X. Fu and M. Antonietti, *Adv. Mater.*, 2009, **21**, 1609–1612.
- 42 Y. Wang, J. S. Zhang, X. C. Wang, M. Antonietti and H. R. Li, *Angew. Chem., Int. Ed.*, 2010, **49**, 3356–3359.
- 43 D. Portehault, C. Giordano, C. Gervais, I. Senkovska, S. Kaskel, C. Sanchez and M. Antonietti, *Adv. Funct. Mater.*, 2010, **20**, 1827–1833.
- 44 L. Lin, H. Ou, Y. Zhang and X. Wang, *ACS Catal.*, 2016, **6**, 3921–3931.
- 45 S. Thaweesak, S. Wang, M. Lyu, M. Xiao, P. Peerakiatkhajohn and L. Wang, *Dalton Trans.*, 2017, **46**, 10714–10720.
- 46 S. Zhang, L. Gao, D. Fan, X. Lv, Y. Li and Z. Yan, *Chem. Phys. Lett.*, 2017, **672**, 26–30.
- 47 Z. A. Lan, Y. Fang, Y. Zhang and X. Wang, *Angew. Chem., Int. Ed.*, 2018, **57**, 470–474.
- 48 H. Ou, L. Lin, Y. Zheng, P. Yang, Y. Fang and X. Wang, *Adv. Mater.*, 2017, **29**, 1700008.
- 49 H. Ou, P. Yang, L. Lin, M. Anpo and X. Wang, *Angew. Chem., Int. Ed.*, 2017, **56**, 10905–10910.
- 50 S. Kang, Y. Fang, Y. Huang, L.-F. Cui, Y. Wang, H. Qin, Y. Zhang, X. Li and Y. Wang, *Appl. Catal., B*, 2015, **168**, 472–482.
- 51 Y. Hou, Z. Wen, S. Cui, X. Guo and J. Chen, *Adv. Mater.*, 2013, **25**, 6291–6297.
- 52 H. Katsumata, Y. Tachi, T. Suzuki and S. Kaneco, *RSC Adv.*, 2014, **4**, 21405–21409.
- 53 D. Voiry, H. Yamaguchi, J. Li, R. Silva, D. C. Alves, T. Fujita, M. Chen, T. Asefa, V. B. Shenoy, G. Eda and M. Chhowalla, *Nat. Mater.*, 2013, **12**, 850–855.
- 54 Z. Zhang, J. Huang, M. Zhang, Q. Yuan and B. Dong, *Appl. Catal., B*, 2015, **163**, 298–305.
- 55 S. C. Yan, Z. S. Li and Z. G. Zou, *Langmuir*, 2010, **26**, 3894–3901.
- 56 Y. Imanaka, T. Anazawa, T. Manabe, H. Amada, S. Ido, F. Kumasaka, N. Awaji, G. Sanchez-Santolino, R. Ishikawa and Y. Ikuhara, *Sci. Rep.*, 2016, **6**, 35593.
- 57 L. Ma, H. Fan, J. Wang, Y. Zhao, H. Tian and G. Dong, *Appl. Catal., B*, 2016, **190**, 93–102.
- 58 S. Kumar, T. Surendar, B. Kumar, A. Baruah and V. Shanker, *RSC Adv.*, 2014, **4**, 8132–8137.
- 59 W. Li, C. Feng, S. Dai, J. Yue, F. Hua and H. Hou, *Appl. Catal., B*, 2015, **168–169**, 465–471.
- 60 S. G. Kumar and K. S. R. K. Rao, *RSC Adv.*, 2015, **5**, 3306–3351.

