

Cite this: *RSC Adv.*, 2018, 8, 30207

# Facile synthesis of 1.3 nm monodispersed Ag nanoclusters in an aqueous solution and their antibacterial activities for *E. coli*†

Chengpeng Jiao,<sup>‡ab</sup> Yuantao Pei,<sup>‡a</sup> Liqiong Wang,<sup>a</sup> Haijun Zhang,<sup>id</sup>\*<sup>a</sup> Zili Huang,<sup>b</sup> Yuhuan Dai,<sup>c</sup> Feng Liang,<sup>d</sup> Simin Liu,<sup>id</sup><sup>d</sup> Yuhua Wang<sup>e</sup> and Shaowei Zhang<sup>id</sup>\*<sup>f</sup>Received 23rd May 2018  
Accepted 13th August 2018

DOI: 10.1039/c8ra04387f

rsc.li/rsc-advances

A facile one-pot strategy was developed to prepare ultrastable monodispersed Ag nanoclusters (NCs) in aqueous solution by using ISOBAM-104, as a stabilizing agent. The as-prepared Ag NCs with an average size of 1.3 nm, which can be preserved in water solution for more than one year under ambient conditions without obvious agglomeration, exhibited excellent antibacterial activities for *E. coli* (DH5 $\alpha$ ), compared to most of the previously reported results.

## Introduction

Development of Ag nanoclusters with sizes less than 2 nm has been an attractive research frontier due to their unique fascinating physicochemical properties for application in catalysis, electrochemical devices, plasmonic related technologies or antibacterial agents for killing drug-resistant micro-organisms.<sup>1–6</sup> Two main strategies, *i.e.*, the reduction method and etching method, have been developed for the preparation of Ag NCs with tiny size. Despite these interesting results, these two methods still suffer from a serious problem: the process is complex and usually requires ligand exchange for the former; moreover, thiols are always used to control the nucleation, growth, and stability of the as-prepared Ag NCs in this case.<sup>7–22</sup> Nevertheless, it is known that thiols are unfavorable for applications in catalysis and biomedicine.<sup>23–26</sup> For the latter, special ligands with appropriate etching capacity are usually needed to remove the surface atoms of the pre-formed nanoparticles in the preparation process,<sup>27,28</sup> and the process is often carried out

in biphasic solvent mixtures or organic solvents, for example, at the oil/water interface.<sup>29</sup> In addition, toxic organic solvents such as carbon tetrachloride or toluene are generally necessary for the techniques.

To date, it is well-known that even polymers such as poly(*N*-vinyl-2-pyrrolidone) (PVP) are effective, commercially available, relatively inexpensive and nontoxic stabilizing agents for the preparation of noble-metal NCs.<sup>30–35</sup> However, the formation of Ag NCs with an average diameter below 2 nm using polymer as a protecting agent has proven to be a substantial technological challenge.<sup>36,37</sup> Thus, alternative thiol-free methods using easily accessible polymer as stabilizing agents for the preparation and stabilization of tiny Ag NCs in aqueous environment are of great interest.

Up to now, many metal-containing antibacterial nanoparticles especially Ag nanoparticles have been reported to show pronounced efficiency on deactivating and inhibiting growth of both Gram negative and Gram positive bacteria.<sup>38–40</sup> At current, a possible mechanism that Ag<sup>+</sup> with thiol groups in enzymes and proteins is accepted to be the main responsible for the antimicrobial action. And for Ag NPs case, it is also accepted that they can absorb onto cytomembrane of bacteria at first and then entry into cell, result in changes of membrane permeability and damage the intracellular structures of biomolecules, ultimately cause cell death.<sup>41</sup>

Based on above consideration. Here, for the first time, we report a facile one-pot versatile protocol for producing ultrastable monodispersed Ag NCs with an average size of 1.3 nm using poly (isobutylene-*alt*-maleic anhydride) (Fig. S1,† ISOBAM-104, molecular weight: 10<sup>4</sup> to 10<sup>5</sup> g mol<sup>−1</sup>) as stabilizing agent in aqueous solution. The as-prepared Ag NCs can be stable stored in ambient condition for at least one year and exhibited excellent antibacterial property for *E. coli* (DH5 $\alpha$ ). The antibacterial activities of as-prepared Ag NCs were evaluated by microdilution method characterized as minimal inhibitory

<sup>a</sup>The State Key Laboratory of Refractories and Metallurgy, Wuhan University of Science and Technology, Wuhan 430081, China. E-mail: zhanghaijun@wust.edu.cn; Fax: +86-27-68862829

<sup>b</sup>Hubei Key Laboratory for Efficient Utilization and Agglomeration of Metallurgical Mineral Resources, Wuhan University of Science and Technology, Wuhan 430081, China

<sup>c</sup>Institute of Biology and Medicine, Wuhan University of Science and Technology, Wuhan 430065, China

<sup>d</sup>College of Chemical Engineering and Technology, Wuhan University of Science and Technology, Wuhan 430081, China

<sup>e</sup>Hubei Province Key Laboratory of Science in Metallurgical Process, Wuhan University of Science and Technology, Wuhan 430081, China

<sup>f</sup>College of Engineering, Mathematics and Physical Sciences, University of Exeter, Exeter EX4 4QF, UK. E-mail: s.zhang@exeter.ac.uk

† Electronic supplementary information (ESI) available. See DOI: 10.1039/c8ra04387f

‡ Chengpeng Jiao and Yuantao Pei contributed equally to this work.

concentrations (MICs, indicate the ability of inhibiting the growth of bacteria but not necessarily killing them.) and minimal bactericidal concentrations (MBCs, indicating the ability of antibiotics in killing bacteria, defined as the lowest concentration of NPs where the bacterial colony was counted lower than five.) for *Escherichia coli* (*E. coli*).

## Results and discussion

The effect of precursor concentration on size and morphology of Ag NCs was investigated. The UV-Vis spectra (Fig. S2†) of as-prepared Ag NCs consisted of a single surface plasmon resonance (SPR) band at about 400 nm, and the absorbance of the plasmon peak increased with the  $\text{Ag}^+$  ion concentration increasing from 0.0138 mM to 1.32 mM. A series of Ag NCs were

prepared by a chemical reduction process with rapid injection of  $\text{KBH}_4$  respectively using  $\text{AgClO}_4$  and ISOBAM-104 as precursor and capping agent (Table S1†). A set of typical TEM images and size distribution histograms shown in Fig. 1 indicated that the mean particle size of Ag NCs was closely dependent on the  $\text{Ag}^+$  ion concentration, and that the average particle diameter initially decreased from  $1.8 \pm 0.5$  nm to the smallest ( $1.3 \pm 0.5$  nm) with increasing  $\text{Ag}^+$  ion concentration from 0.0138 to 0.055 mM, and then started to drastically increase to  $3.1 \pm 1.1$  nm upon further increasing the concentration to 1.32 mM. These results suggested that a medium  $\text{Ag}^+$  ion concentration is essential for preparation of Ag NCs with tiny size, this can be explained by nucleation-growth-agglomeration stepwise formation mechanism.<sup>42–44</sup>

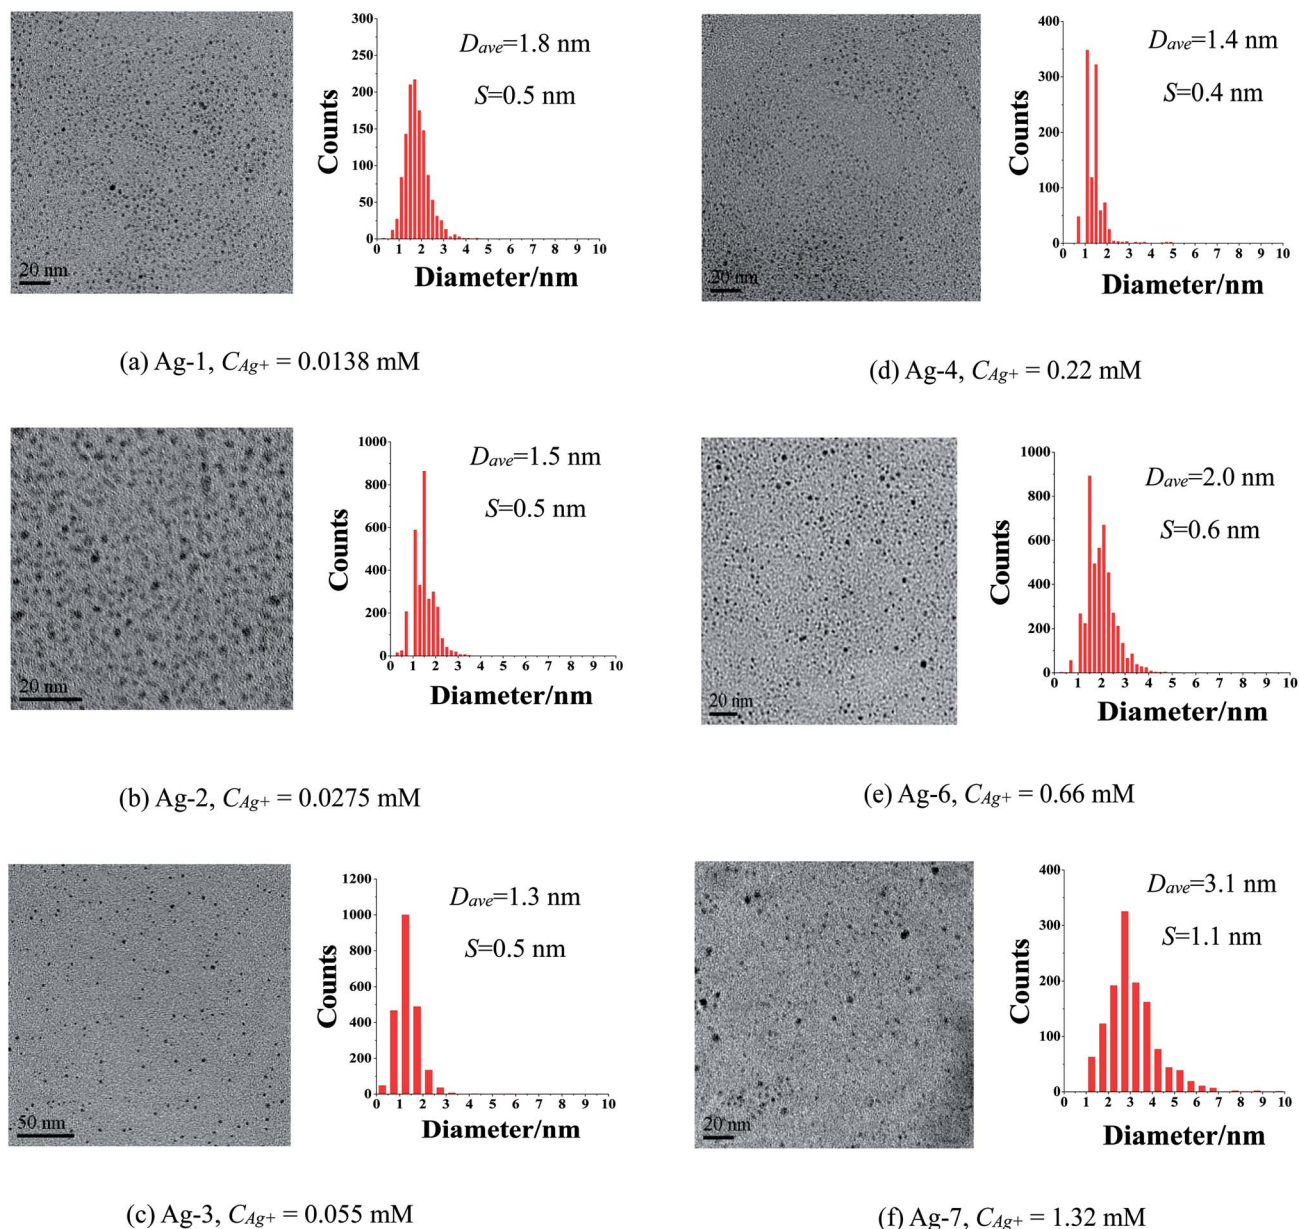


Fig. 1 TEM images of as-prepared Ag NCs with various  $\text{Ag}^+$  ion concentrations ( $\text{AgClO}_4$  as precursor,  $R_{\text{ISO}} = 40$ ,  $R_{\text{KBH}_4} = 2$ , ice-water bath for 1 h;  $D_{\text{ave}}$ : average particle sizes;  $S$ : standard deviation).



Effect of molar ratio of ISOBAM-104 to  $\text{Ag}^+$  ions (denoted as  $R_{\text{ISO}}$ ) on the preparation of Ag NCs was also investigated. UV-Vis spectra, TEM images and size distribution histograms of as-prepared Ag NCs were shown in Fig. 2. A plasmon characteristic peak around 420 nm of Ag was observed in all the UV-Vis spectra (Fig. S3†), indicating the formation of Ag NCs. Fig. 1 and 2 indicated that all the as-prepared Ag NCs are well-isolated and spherical without any form of aggregation. The size distribution analysis of these prepared NCs indicated that the amount of ISOBAM ( $R_{\text{ISO}}$ ) did not show clearly effect on the average size of the final Ag NCs, and that the average particle sizes are respectively about  $1.9 \pm 0.6$ ,  $1.4 \pm 0.4$ ,  $1.6 \pm 0.5$ ,  $1.4 \pm 0.4$ , and  $1.9 \pm 0.4$  nm for the samples prepared with  $R_{\text{ISO}} = 20$ ,  $R_{\text{ISO}} = 40$ ,  $R_{\text{ISO}} = 60$ ,  $R_{\text{ISO}} = 80$ , and  $R_{\text{ISO}} = 100$ . Moreover, size distribution of Ag NCs ( $R_{\text{ISO}} = 40$ ) based on dynamic light

scattering (DLS) measurement indicated that the diameter of present NCs was in range of 1–2 nm (Fig. S4†), which was agree with TEM results (Fig. 1). And the zeta potential of present Ag NCs was measured to be  $-33.7$  mV, indicating its excellent stability in this paper. To the best of our knowledge, this is the first report to prepare 1.3 nm Ag nanoclusters in aqueous solution using thiols-free polymer as stabilizing agent.

HRTEM was performed to characterize the structure of as-prepared Ag NCs. A typical HRTEM image of a random-chosen Ag NC prepared with  $R_{\text{ISO}} = 40$  shown in Fig. 3(a) indicated that the interplanar distances of the characterized NC was 0.238 nm, which was well consistent with bulk Ag interplanar spacing of (111) plane (0.2359 nm; Ag: ICDD 00-004-0783).

To further confirm the formation of ISOBAM-stabilized Ag NCs, X-ray photoelectron spectroscopy (XPS) was performed to


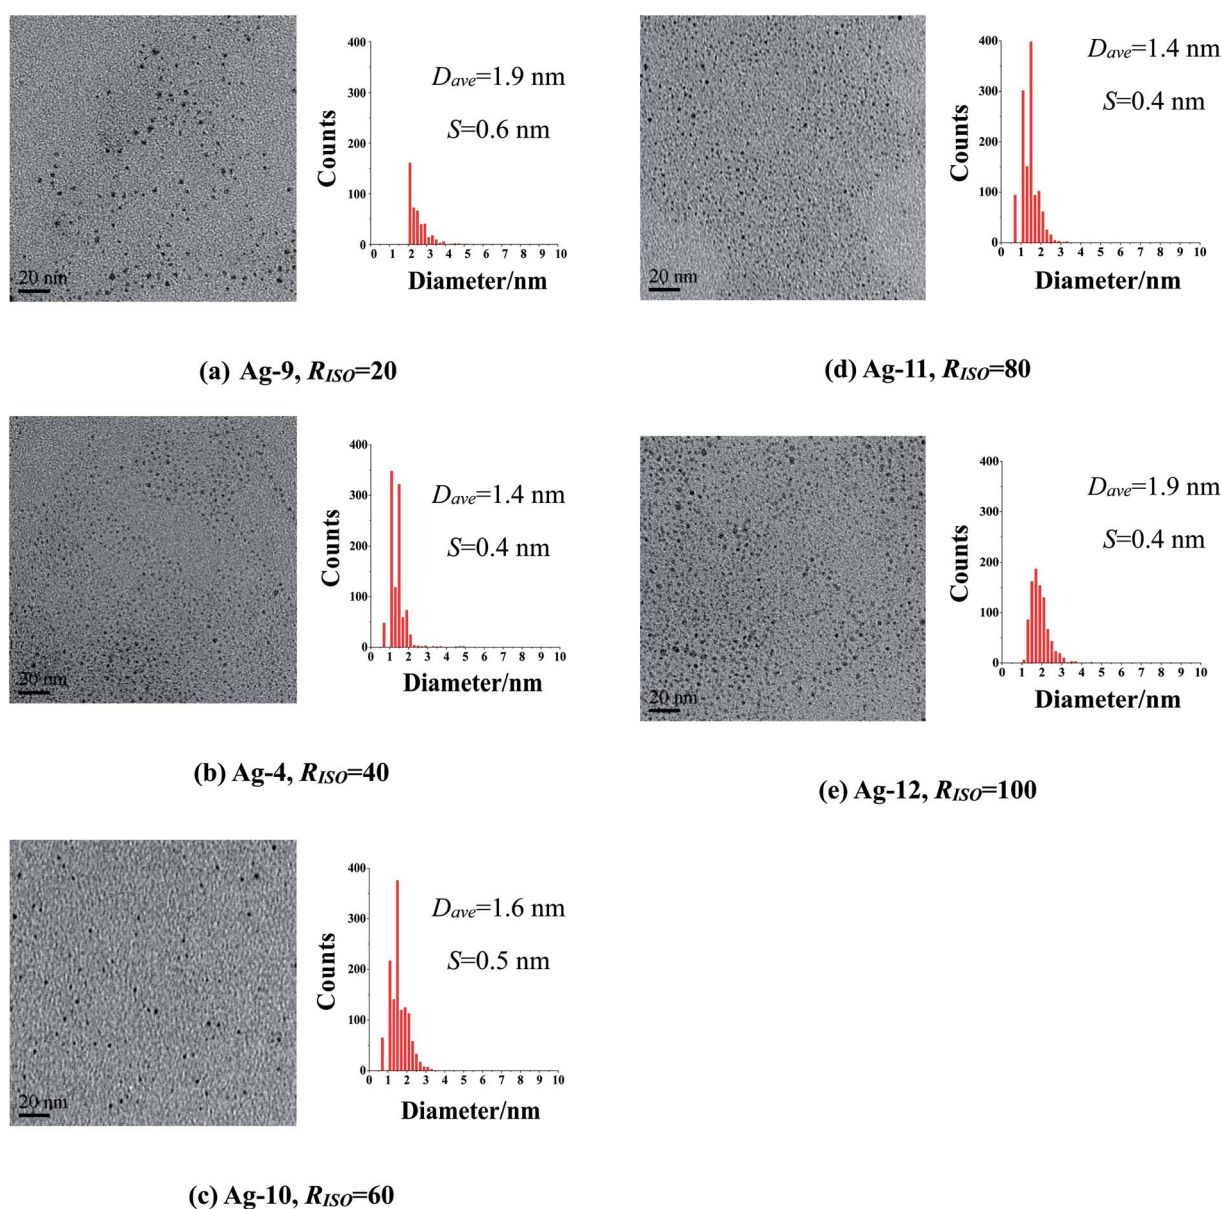



Fig. 2 TEM images and size distribution histograms of Ag NCs synthesized at varied  $R_{\text{ISO}}$  ranging from 20 to 100 ( $\text{AgClO}_4$  as precursor,  $C_{\text{Ag}^+} = 0.22$  mM, 50 mL,  $R_{\text{KBH}_4} = 2$ , ice-water bath for 1 h;  $D_{\text{ave}}$ : average particle sizes;  $S$ : standard deviation).






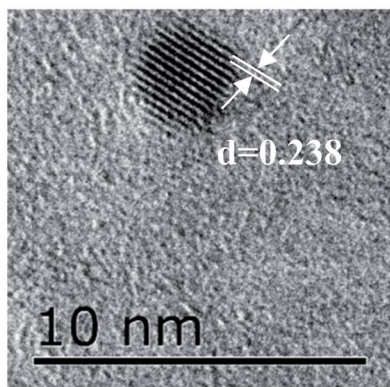


(a) HRTEM

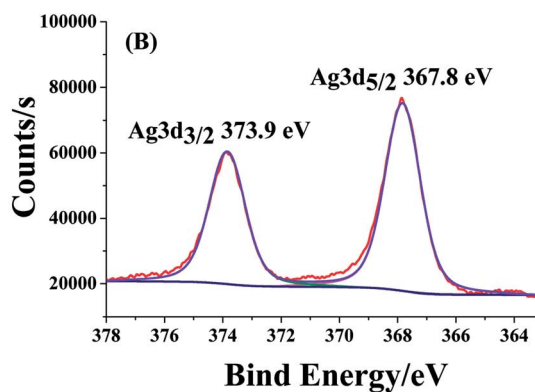


(b) XPS, Ag 3d

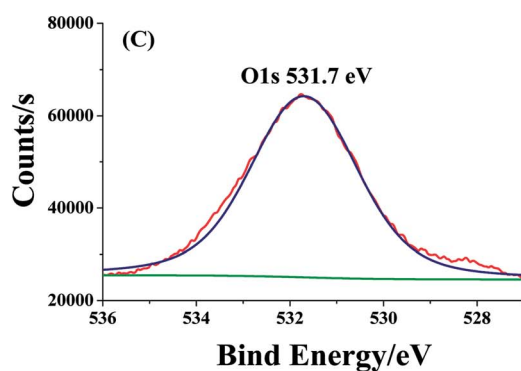


(c) XPS, O 1s

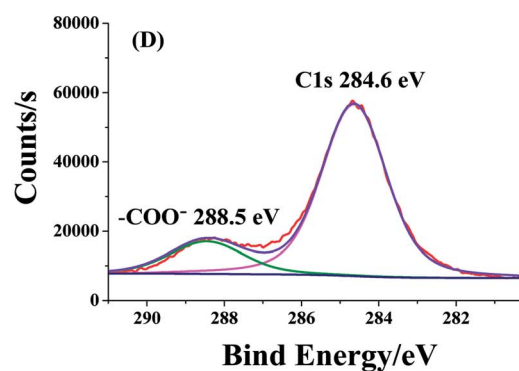

(d) XPS, C 1s

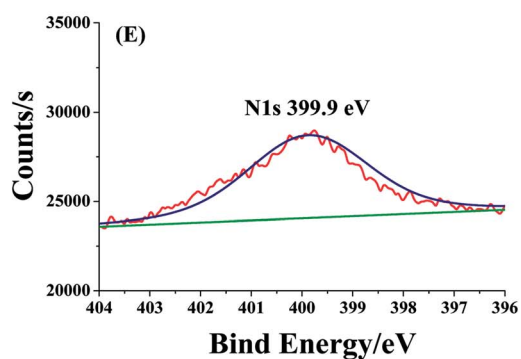

(e) XPS, N 1s

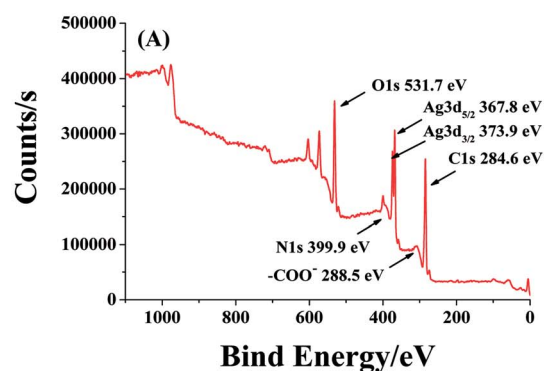

(f) XPS spectra

Fig. 3 HRTEM images (a) and XPS spectra (b–f) of as-prepared ISOBAM-104 stabilized Ag NCs, Ag 3d (b), O 1s (c), C 1s (d), N 1s (e) and whole range (f) ( $\text{Ag-4}$ ,  $C_{\text{Ag}^+} = 0.22 \text{ mM}$ ,  $R_{\text{ISO}} = 40$ ,  $R_{\text{KBH}_4} = 2$ , ice-water bath for 1 h).



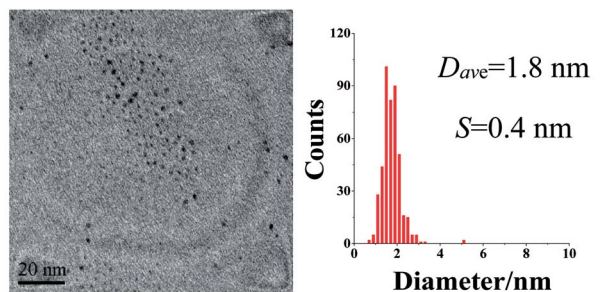
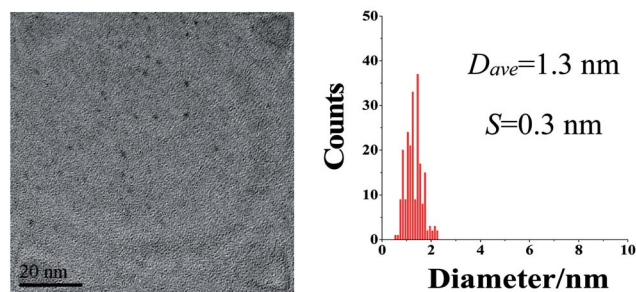
(a) Ag-3, AgClO<sub>4</sub>, C<sub>Ag<sup>+</sup></sub> = 0.055 mM(b) Ag-4, AgClO<sub>4</sub>, C<sub>Ag<sup>+</sup></sub> = 0.22 mM

Fig. 4 TEM images and size distribution histograms of Ag NCs stored for one year synthesized at varied C<sub>Ag<sup>+</sup></sub> ranging from 0.055 mM to 0.22 mM. (AgClO<sub>4</sub>, R<sub>ISO</sub> = 40, R<sub>KBH<sub>4</sub></sub> = 2, reduced under ice bath for 1 h; D<sub>ave</sub>: average particle sizes; S: standard deviation)

analyze the element composition of the prepared NCs, a typical XPS spectrum of the Ag NCs was shown in Fig. 3(b–f). Appearance of the binding energy peaks such as Ag 3d, C 1s, O 1s, and N 1s indicates that ISOBAM molecules were indeed adsorbed on the surface of the Ag NCs. Two peaks at 373.9 and 367.8 eV respectively result from Ag 3d<sub>3/2</sub> and Ag 3d<sub>5/2</sub> were observed shown in Fig. 3(b), confirming the formation of metal Ag. Moreover, both the electron apparent binding energy (BE) shifted towards a lower binding energy relative to bulk Ag (374.2 eV for Ag 3d<sub>3/2</sub>, 368.2 eV for Ag 3d<sub>5/2</sub>). On the other hand, the BE of O1s in carboxyl was slightly positively shifted from 529.7 eV to 531.7 eV, as shown in Fig. 3(c). These results suggested that there probably present strong electron interactions between the ISOBAM-104 and as-prepared Ag NCs. And the functional group of carboxyl and amide in ISOBAM-104 might act as effective coordination ligands for stability of Ag NCs *via* the electron interaction, which finally made ISOBAM-104 an efficient protective agent for the size control of Ag NCs.

For comparison, PVP (K30, average molecular-weight of about 30 000), a widely used polymer for metal nanocluster preparation was also chosen as stabilizing agent to synthesize Ag nanoparticles using rapid injection and dropwise addition of KBH<sub>4</sub> method, alcohol reduction method and sodium citrate reduction method, the results showed that most of the prepared Ag nanoparticles exhibited much larger average particle size and wider size distribution, and some of them showed irregular

morphology (Fig. S5†). Moreover, a comparison of Ag nanoparticles prepared with different protecting agents listed in Table S2† also indicated that the Ag NCs prepared in present paper has the smallest average size. These results demonstrated that ISOBAM is indeed an efficient stabilizing agent for preparation of Ag NCs with tiny size. What should be noted is that the average particle size of prepared Ag NPs synthesized with various C<sub>Ag<sup>+</sup></sub> ranging from 0.055 mM to 0.22 mM did not show obvious growth even after storage under ambient conditions for one year (Fig. 4). For the former sample prepared with C<sub>Ag<sup>+</sup></sub> = 0.055 mM whose average diameter changed from 1.3 ± 0.5 nm to 1.8 ± 0.4 nm after one year; and the latter one changing from 1.4 ± 0.4 nm to 1.3 ± 0.3 nm. Furthermore, it showed that the new stabilizing agent also makes it possible to prepare other metal NCs with tiny size, such as Au, Pt, Rh, and so on (Fig. S6†).

One important application of Ag NCs is the potential application as antibiotics, thus, antibacterial activities characterized as minimal inhibitory concentrations (MICs) and minimal bactericidal concentrations (MBCs) for *Escherichia coli* (*E. coli*) of as-prepared Ag NCs were evaluated by microdilution method according to the reported method.<sup>45,46</sup> MIC was initially confirmed by average OD<sub>600</sub> absorbance results of *E. coli* in 96-well microplate after incubating on a shaker bed at 200 rpm under 37 °C overnight, and MBC was confirmed by reinoculating 10 μL of each bacterial suspension after MIC test on nutrient agar plates at 37 °C for 10 h, 24 h and even 36 h (Fig. S7†). All the tests for MIC and MBC were performed at least three times. It showed that the as prepared Ag NCs did not show obvious disturbance on OD<sub>600</sub> test under the usage concentration below 1.35 mg L<sup>-1</sup> (more OD<sub>600</sub> results were shown in Table S3†). Moreover, the protective agent ISOBAM-104 did not show any inhibitory effects, and high ISOBAM-104 concentration, for example, 0.75 mg L<sup>-1</sup>, even promoted the growth of *E. coli*, which can be concluded *via* the higher OD<sub>600</sub> results of 0.770 than that of control group at 0.739 after cultivating for 24 h under 37 °C (shown in Table S4†). It also turns out that Ag NCs (Ag-4, C<sub>AgClO<sub>4</sub></sub> = 0.22 mM, 50 precursor solution, R<sub>ISO</sub> = 40) with an average particle size of about 1.4 ± 0.4 nm showed excellent antibacterial activities with MIC and MBC as low as 0.25 mg L<sup>-1</sup> and 0.50 mg L<sup>-1</sup> (shown in Tables 1 and S4†). The stability of present Ag NPs (Ag-4) in NaCl solutions was also investigated, and 4 mL as prepared Ag-4 NC colloid was mixed with 4 mL NaCl solution with different concentrations, the photos of the mixture after 5 min to 24 h were shown in Fig. S8†. Although it indicated that the color fading became severe with the NaCl concentration increase, however, the sample no. 5<sup>#</sup> which share an identical NaCl concentration for antibacterial experiment show negligible color fading compared with the blank control, and can be stably stored for 24 h. Since the mole ratio of NaCl : Ag in the sample is as high as 1545 : 1, it can be concluded that present Ag NCs are very stable in NaCl solution. TEM was used to characterize the morphology of present Ag NCs in NaCl solution, and it confirmed again that the Ag NCs were well dispersive. (Fig. S9†).

To the best knowledge of the authors, these antibiotic activities are the lowest reported so far for Ag NCs, and the excellent antibiotic activity for *E. coli* of as-prepared Ag NCs is



**Table 1** Antibacterial activity for *E. coli* of as-prepared ISOBAM-protected Ag NCs<sup>a</sup>

Code	Preparation conditions and size of NCs			Antibacterial activities	
	$C_{Ag^+}$ , mM	$R_{ISO}$	Average size, nm	MIC, mg L <sup>-1</sup>	MBC, mg L <sup>-1</sup>
Ag-2	0.0275	40	1.5 ± 0.5	0.50	0.75
Ag-3	0.055	40	1.3 ± 0.5	0.50	0.75
Ag-4	0.22	40	1.4 ± 0.4	0.25	0.50

<sup>a</sup>  $C_{Ag^+}$  refers to the concentration in 50 mL precursor solution for NCs preparation.

believed to be ascribed to its tiny size because it is demonstrated that the interaction of silver NCs with light or microorganisms can be manipulated by its size and capping agents.<sup>47,48</sup> Moreover, a comparison between the antibiotic activity of the present Ag NCs for *E. coli* and that of NCs reported in literature is given in Table S5.†

## Conclusion

In summary, a facile one-pot versatile approach for large-scale fabrication of monodispersed and spherical Ag NCs with size of 1.3 nm in aqueous solution was developed *via* using a novel thiols-free copolymer of ISOBAM-104 as stabilizing agent. The as-prepared Ag NCs stabilized by the polymer showed well stability and can be preserved in water for more than one year under ambient condition without changing its particle size. These NCs exhibits excellent antibacterial activity and lowest MIC and MBC so far reported for *E. coli* (DH5 $\alpha$ ). We believe that our finding in present paper not only extend the preparation method of Ag NCs with size less than 2.0 nm, but also provide a new protective agent for synthesis of metal NCs.

## Funding sources

This work was financially supported by the National Natural Science Foundation of China (Grant No. 51472184 and 51472185), and Program for Innovative Teams of Outstanding Young and Middle-aged Researchers in the Higher Education Institutions of Hubei Province (T201602), and the Key Program of Natural Science Foundation of Hubei Province, China (2017CFA004).

## Conflicts of interest

The authors declare that they have no conflict of interest.

## Acknowledgements

Haijun Zhang conceived and designed the experiment. Cheng-peng Jiao, Yuantao Pei and Liqiong Wang performed catalysts synthesis, whereas Zili Huang, Yuhuan Dai, Feng Liang, Simin Liu and Yuhua Wang carried out catalyst characterization and evaluation. Chengpeng Jiao, Shaowei Zhang and Haijun Zhang

contributed with the analysis and interpretation of characterization results. All authors reviewed the manuscript.

## References

- 1 M. A. Green, When small is better, *Nat. Mater.*, 2009, **8**, 450–451.
- 2 M. Rycenga, C. M. Cobley, J. Zeng, W. Li, C. H. Moran, Q. Zhang, D. Qin and Y. N. Xia, Controlling the synthesis and assembly of silver nanostructures for plasmonic application, *Chem. Rev.*, 2011, **111**, 3669–3712.
- 3 W. R. Li, X. B. Xie, Q. S. Shi, H. Y. Zeng, Y. S. Ou-Yang and Y. B. Chen, Antibacterial activity and mechanism of silver nanoparticles on *Escherichia coli*, *Appl. Microbiol. Biotechnol.*, 2010, **85**, 1115–1122.
- 4 C. Khurana, A. K. Vala, N. Andhariya, O. P. Pandey and B. Chudasama, Antibacterial activity of silver: the role of hydrodynamic particle size at nanoscale, *J. Biomed. Mater. Res., Part A*, 2014, **102**, 3361–3368.
- 5 S. Pal, E. J. Yoon, Y. K. Tak, E. C. Choi and J. M. Song, Synthesis of highly antibacterial nanocrystalline trivalent silver polydiguamide, *J. Am. Chem. Soc.*, 2009, **131**, 16147–16155.
- 6 M. Mahmoudi and V. Serpooshan, Silver-coated engineered magnetic nanoparticles are promising for the success in the fight against antibacterial resistance threat, *ACS Nano*, 2012, **6**, 2656–2664.
- 7 S. Kumar, M. D. Bolan and T. P. Bigioni, Glutathione-stabilized magic-number silver cluster compounds, *J. Am. Chem. Soc.*, 2010, **132**, 13141–13143.
- 8 B. Sengupta, K. Springer, J. G. Buckman, S. P. Story, O. H. Abe, Z. W. Hasan, Z. D. Prudowsky, S. E. Rudisill, N. N. Degtyareva and J. T. Petty, DNA templates for fluorescent silver clusters and i-motif folding, *J. Phys. Chem. C*, 2009, **113**, 19518–19524.
- 9 I. Díez, M. I. Kanyuk, A. P. Demchenko, A. Walther, H. Jiang, O. Ikkala and R. H. Ras, Blue, green and red emissive silver nanoclusters formed in organic solvents, *Nanoscale*, 2012, **4**, 4434–4437.
- 10 C. Guo and J. Irudayaraj, Fluorescent Ag clusters *via* a protein-directed approach as a Hg (II) ion sensor, *Anal. Chem.*, 2011, **83**, 2883–2889.
- 11 S. Liu, F. Lu and J. J. Zhu, Highly fluorescent Ag nanoclusters: microwave-assisted green synthesis and Cr<sup>3+</sup> sensing, *Chem. Commun.*, 2011, **47**, 2661–2663.
- 12 T. Zhou, M. Rong, Z. Cai, C. J. Yang and X. Chen, Sonochemical synthesis of highly fluorescent glutathione-stabilized Ag nanoclusters and S<sup>2-</sup> sensing, *Nanoscale*, 2012, **4**, 4103–4106.
- 13 J. Sharma, R. C. Rocha, M. L. Phipps, H. C. Yeh, K. A. Balatsky, D. M. Vu, A. P. Shreve, J. H. Werner and J. S. Martinez, A DNA-templated fluorescent silver nanocluster with enhanced stability, *Nanoscale*, 2012, **4**, 4107–4110.
- 14 L. Maretti, P. S. Billone, Y. Liu and J. C. Scaiano, Facile photochemical synthesis and characterization of highly





- fluorescent silver nanoparticles, *J. Am. Chem. Soc.*, 2009, **131**, 13972–13980.
- 15 Z. Shen, H. Duan and H. Frey, Water-soluble fluorescent Ag nanoclusters obtained from multiarm star poly (acrylic acid) as “molecular hydrogel” templates, *Adv. Mater.*, 2007, **19**, 349–352.
  - 16 J. Zheng and R. M. Dickson, Individual water-soluble dendrimer-encapsulated silver nanodot fluorescence, *J. Am. Chem. Soc.*, 2002, **124**, 13982–13983.
  - 17 C. Zhang, X. Sun, J. Li and Y. N. Liu, Synthesis of Ag nanoclusters by a pH-dependent etching method in aqueous solution, *Nanoscale*, 2013, **5**, 6261–6264.
  - 18 M. Brust, M. Walker, D. Bethell, D. J. Schiffrin and R. Whyman, Synthesis of thiol-derivatised gold nanoparticles in a two-phase liquid–liquid system, *J. Chem. Soc., Chem. Commun.*, 1994, **7**, 801–802.
  - 19 M. J. Hostetler, J. E. Wingate, C. J. Zhong, J. E. Harris, R. W. Vachet, M. R. Clark, G. L. Glish, *et al.*, Alkanethiolate gold cluster molecules with core diameters from 1.5 to 5.2 nm: core and monolayer properties as a function of core size, *Langmuir*, 1998, **14**, 17–30.
  - 20 M. T. Reetz and S. A. Quaiser, A new method for the preparation of nanostructured metal clusters, *Angew. Chem., Int. Ed. Engl.*, 1995, **34**, 2240–2241.
  - 21 M. J. Hostetler, A. C. Templeton and R. W. Murray, Dynamics of place-exchange reactions on monolayer-protected gold cluster molecules, *Langmuir*, 1999, **15**, 3782–3789.
  - 22 F. Manea, C. Bindoli, S. Polizzi, L. Lay and P. Scrimin, Expedition synthesis of water-soluble, monolayer-protected gold nanoparticles of controlled size and monolayer composition, *Langmuir*, 2008, **24**, 4120–4124.
  - 23 R. Munday, Toxicity of thiols and disulphides: involvement of free-radical species, *Free Radical Biol. Med.*, 1989, **7**, 659–673.
  - 24 B. P. Chauhan, J. S. Rathore and T. Bando, “Polysiloxane-Pd” Nanocomposites as Recyclable Chemoselective Hydrogenation Catalysts, *J. Am. Chem. Soc.*, 2004, **126**, 8493–8500.
  - 25 B. Panthi, A. Mukhopadhyay, L. Tibbitts, J. Saavedra, C. J. Pursell, R. M. Rioux and B. D. Chandler, Using Thiol Adsorption on Supported Au Nanoparticle Catalysts To Evaluate Au Dispersion and the Number of Active Sites for Benzyl Alcohol Oxidation, *ACS Catal.*, 2015, **5**, 2232–2241.
  - 26 S. Corra, U. Lewandowska, E. M. Benetti and H. Wennemers, Size-Controlled Formation of Noble-Metal Nanoparticles in Aqueous Solution with a Thiol-Free Tripeptide, *Angew. Chem., Int. Ed.*, 2016, **55**, 8542–8545.
  - 27 T. Udaya Bhaskara Rao and T. Pradeep, Luminescent Ag<sub>7</sub> and Ag<sub>8</sub> clusters by interfacial synthesis, *Angew. Chem., Int. Ed.*, 2010, **49**, 3925–3929.
  - 28 K. V. Mrudula, T. U. B. Rao and T. Pradeep, Interfacial synthesis of luminescent 7 kDa silver clusters, *J. Mater. Chem.*, 2009, **19**, 4335–4342.
  - 29 X. Yuan, Z. Luo, Q. Zhang, X. Zhang, Y. Zheng, J. Y. Lee and J. Xie, Synthesis of highly fluorescent metal (Ag, Au, Pt, and Cu) nanoclusters by electrostatically induced reversible phase transfer, *ACS Nano*, 2011, **5**, 8800–8808.
  - 30 H. J. Zhang, J. Okuni and N. Toshima, Preparation of novel Au/Pt/Ag trimetallic nanoparticles and their high catalytic activity for aerobic glucose oxidation, *Appl. Catal., A*, 2011, **400**, 9–13.
  - 31 H. J. Zhang, M. Okumura and N. Toshima, Stable dispersions of PVP-protected Au/Pt/Ag trimetallic nanoparticles as highly active colloidal catalysts for aerobic glucose oxidation, *J. Phys. Chem. C*, 2011, **115**, 14883–14891.
  - 32 H. J. Zhang, T. Watanabe, M. Okumura, M. Haruta and N. Toshima, Catalytically highly active top gold atom on palladium nanocluster, *Nat. Mater.*, 2012, **11**, 49–52.
  - 33 H. J. Zhang and N. Toshima, Fabrication of catalytically active AgAu bimetallic nanoparticles by physical mixture of small Au clusters with Ag ions, *Appl. Catal., A*, 2012, **447**, 81–88.
  - 34 H. J. Zhang, T. Watanabe, M. Okumura, M. Haruta and N. Toshima, Crown Jewel catalyst: How neighboring atoms affect the catalytic activity of top Au atoms?, *J. Catal.*, 2013, **305**, 7–18.
  - 35 H. J. Zhang, L. Lu, K. Kawashima, M. Okumura, M. Haruta and N. Toshima, Synthesis and catalytic activity of crown jewel-structured (IrPd)/Au trimetallic nanoclusters, *Adv. Mater.*, 2015, **27**, 1383–1388.
  - 36 H. J. Zhang, J. Okuni and N. Toshima, One-pot synthesis of Ag–Au bimetallic nanoparticles with Au shell and their high catalytic activity for aerobic glucose oxidation, *J. Colloid Interface Sci.*, 2011, **354**, 131–138.
  - 37 H. J. Zhang, M. Haba, M. Okumura, T. Akita, S. Hashimoto and N. Toshima, Novel formation of Ag/Au bimetallic nanoparticles by physical mixture of monometallic nanoparticles in dispersions and their application to catalysts for aerobic glucose oxidation, *Langmuir*, 2013, **29**, 10330–10339.
  - 38 H. Y. Wang, X. W. Hua, F. G. Wu, B. Li, P. Liu, N. Gu, Z. Wang and Z. Chen, Synthesis of Ultrastable Copper Sulfide Nanoclusters *via* Trapping the Reaction Intermediate: Potential Anticancer and Antibacterial Applications, *ACS Appl. Mater. Interfaces*, 2015, **7**, 7082–7092.
  - 39 C. C. S. Batista, L. J. C. Albuquerque, I. D. Araujo, B. L. Albuquerque, F. D. D. Silva and F. C. Giacomelli, Antimicrobial activity of nano-sized silver colloids stabilized by nitrogen-containing polymers: the key influence of the polymer capping, *RSC Adv.*, 2018, **8**, 10873–10882.
  - 40 G. Muhammad, M. A. Hussain, M. Amin, S. Z. Hussain, I. Hussain, S. N. A. Bukhari and M. Naeemulhassan, Glucuronoxylan-mediated silver nanoparticles: green synthesis, antimicrobial and wound healing applications, *RSC Adv.*, 2017, **7**, 42900–42908.
  - 41 T. Shi, X. Sun and Q. Y. He, Cytotoxicity of silver nanoparticles against bacteria and tumor cells, *Curr. Protein Pept. Sci.*, 2016, **19**, 525–536.
  - 42 J. Turkevich, P. C. Stevenson and J. Hillier, A study of the nucleation and growth processes in the synthesis of colloidal gold, *Faraday Discuss.*, 1951, **11**, 55–75.
  - 43 X. Peng, J. Wickham and A. P. Alivisatos, Kinetics of II–VI and III–V colloidal semiconductor nanocrystal growth:



- “focusing” of size distributions, *J. Am. Chem. Soc.*, 1998, **120**, 5343–5344.
- 44 H. J. Zhang, W. Q. Li, Y. J. Gu and S. W. Zhang, Preparation and catalytic activity of poly (N-vinyl-2-pyrrolidone)-protected Au nanoparticles for the aerobic oxidation of glucose, *J. Nanosci. Nanotechnol.*, 2014, **14**, 5743–5751.
- 45 Y. Y. Zhao, C. J. Ye, W. W. Liu, R. Chen and X. Y. Jiang, Tuning the composition of AuPt bimetallic nanoparticles for antibacterial application, *Angew. Chem., Int. Ed.*, 2014, **53**, 8127–8131.
- 46 Y. Y. Zhao, Y. Tian, Y. Cui, W. W. Liu, W. S. Ma and X. Y. Jiang, Small molecule-capped gold nanoparticles as potent antibacterial agents that target Gram-negative bacteria, *J. Am. Chem. Soc.*, 2010, **132**, 12349–12356.
- 47 K. B. Mogensen and K. Kneipp, Size-dependent shifts of plasmon resonance in silver nanoparticle films using controlled dissolution: monitoring the onset of surface screening effects, *J. Phys. Chem. C*, 2014, **118**, 28075–28083.
- 48 G. A. Sotiriou and S. E. Pratsinis, Antibacterial activity of nanosilver ions and particles, *Environ. Sci. Technol.*, 2010, **44**, 5649–5654.

