



Cite this: *RSC Adv.*, 2018, 8, 28131

Enhanced electrocatalytic performance of nickel diselenide grown on graphene toward the reduction of triiodide redox couples†

Xiao Zhang,  Haijun Zhang,  Xingyu Wang and Xiaomeng Zhou*

The promising activity of nickel diselenide (NiSe₂) towards electrocatalysis has made it especially attractive in energy conversion fields. However, NiSe₂ with high electrocatalytic performance always requires complicated fabrication or expensive conductive polymers, resulting in the scale-up still being challenging. Herein, we introduce a simple and cost-effective synthesis of NiSe₂ dispersed on the surface of graphene (NiSe₂/RGO NPs). NiSe₂/RGO NPs exhibited enhanced electrocatalytic performance and long-term stability for the reduction reaction of triiodide redox couples in dye-sensitized solar cells (DSSCs). Leveraging the advantageous features, the DSSC fabricated with NiSe₂/RGO NPs as CE had a smaller charge-transfer resistance (*R_{ct}*) value and higher short-circuit current density and fill factor than naked NiSe₂ NPs. Additionally, NiSe₂/RGO NPs achieved a PCE of 7.76%, higher than that of pure NiSe₂ (6.51%) and even exceeding that of Pt (7.56%). These prominent features demonstrated that the NiSe₂/RGO NPs in this work are a promising cheap and efficient electrocatalyst to replace state-of-the-art Pt.

Received 16th June 2018

Accepted 17th July 2018

DOI: 10.1039/c8ra05167d

rsc.li/rsc-advances

1. Introduction

Increasingly serious environmental problems and energy crises have resulted in an urgent need for renewable clean energy to replace the diminishing fossil fuel.^{1–4} Dye-sensitized solar cells (DSSCs) are a promising alternative to the conventional inorganic silicon-based solar cell owing to their environmental friendliness, facile fabrication, low cost and high power conversion efficiency (PCE).^{5–7} The cost and performance of a DSSC is strongly influenced by its counter electrode (CE) materials. Traditionally, noble metal platinum (Pt) coated on an FTO substrate has proven to be a preferable CE for DSSCs because of its excellent catalytic activity and high conductivity.^{8–10} Nevertheless, its drawbacks of high cost (US\$50/gram), low natural abundance in earth (0.0037 ppm), and being easily decomposed to harmful PtI₄ and H₂PtI₆ byproducts, make it unsuitable in terms of sustainable development.^{11,12} Given the above considerations, it is of great importance and desirability to develop a low-cost, earth-abundant and anticorrosive Pt-free electrocatalyst with high electrical conductivity and excellent catalytic activity simultaneously for the reduction of I₃.^{13–17}

Given the above considerations, earth-abundant transitional metal dichalcogenides (MX₂, M = Fe, Co, or Ni and X = S or Se) have been applied as CE electrocatalysts and found to be

competitive Pt alternatives, benefiting from their intrinsic metallic properties.^{15,18–21} Especially, nickel diselenide (NiSe₂) is a Pauli paramagnetic metal with a resistivity below 10^{−3} Ω cm, and its metallicity makes it use in electrocatalyst applications appealing.^{22–24} Although considerable advances have been made to NiSe₂ electrocatalysts, the lack of ability to engineer NiSe₂ nanostructures frequently leads to agglomeration of NiSe₂ during high-temperature synthesis and electrocatalytic reaction processes for the isotropic crystal structures, which leads to a decrease in surface area, electrical conductivity and the number of catalytically active sites. Although some modified preparation methods and conductive polymers have been employed to fabricate robust and stable NiSe₂ electrocatalysts with enhanced electrocatalytic performance, complicated and expensive electrode fabrication procedures mean that scale-up is still challenging. In this regard, the most practical fabrication is nothing more than using facile one-step solvothermal methods to grow nanostructured NiSe₂ anchored on self-standing conductive carbon supports (graphene, carbon cloth, carbon fiber paper).^{25,26} The assembly of pristine NiSe₂ onto suitable carbon supports improves the dispersed distribution of NiSe₂ nanostructures, maintains the exposed surface and enhances the application efficiency of active sites.

Following this line of thought, in the present work, we devoted our efforts to fabricating NiSe₂ nanoparticles grown on reduced graphene oxide (RGO) through a facile one-step solvothermal method. The as-obtained NiSe₂ nanoparticles dispersed on the surface of RGO (NiSe₂/RGO NPs) exhibited more efficient active sites and charge-transfer pathways

Center for Aircraft Fire and Emergency, Civil Aviation University of China, Tianjin 300300, P. R. China. E-mail: zhouxm@nankai.edu.cn

† Electronic supplementary information (ESI) available. See DOI: 10.1039/c8ra05167d



compared with pure NiSe₂ nanoparticles (NiSe₂ NPs). Taking advantage of this combination, the DSSC fabricated with the NiSe₂/RGO NPs as the CE exhibited a smaller charge-transfer resistance (R_{ct}) value and higher short-circuit current density (J_{sc}) than those of pure NiSe₂ NPs. Additionally, NiSe₂/RGO NPs achieved a PCE of 7.76%, higher than that of pure NiSe₂ (6.51%) and even exceeding that of Pt (7.56%). These prominent features demonstrated that NiSe₂/RGO NPs are one of the most ideal electroactive materials to replace expensive Pt material for DSSC.

2. Experimental

2.1 Synthesis of graphene oxide

Before synthesizing the NiSe₂/RGO NPs and NiSe₂ NPs, graphene oxide (GO) was firstly prepared by a modified Hummers' method; detailed information is shown in the ESI.†²⁷ The concentration of GO aqueous solution was about 10 mg mL⁻¹.

2.2 Synthesis of NiSe₂/RGO NPs and NiSe₂ NPs

NiSe₂/RGO NPs were prepared by a simple solvothermal method. A typical preparation procedure was as follows: 3 mmol of Ni(CH₃COO)₂·4H₂O was dissolved in 35 mL of distilled water. Then 5 mL of GO aqueous solution was added under continuous stirring for 1 hour to form a uniform dispersion. After this, 6 mmol of Se powder was placed into the mixture. Subsequently, 5 mL of hydrazine hydrate was added dropwise to reduce the Se and GO. The resulting solution was put into a Teflon-lined autoclave of 50 mL capacity and heated at 150 °C for 15 h. Then, the autoclave was allowed to cool to room temperature naturally. The product was washed with water and absolute ethanol to remove impurities, and then dried at 60 °C. Similarly, NiSe₂ NPs were synthesized by the same method without graphene.

2.3 Characterization of obtained samples

The crystallinity and composition of the samples were characterized by X-ray diffraction (XRD, D/max-2500, JAPAN SCIENCE) with Cu K α radiation ($\lambda = 1.54056 \text{ \AA}$). The chemical states and bonding characteristics of the samples were determined by Raman spectra (Renishaw inVia spectrometer, 514.5 nm laser) and X-ray photoelectron spectroscopy (XPS) analysis (PHI 5000 VersaProbe). The morphology of the samples was studied by field-emission scanning electron microscopy (FE-SEM, NanoSEM 430, FEI). More detailed insight into the microstructure of the sample was obtained by high-resolution transmission electron microscopy (TEM, Tecnai G2 F20, operating at 200 kV, FEI).

2.4 Fabrication of DSSCs

The CE materials slurry was made in ethanol by mixing 0.1 g of CE materials powder with 0.025 g of PEG20000, which was used as the dispersant as well as the binder, and stirred continuously. A film was then made by using a doctor-blade to wipe the CE materials slurry on FTO conductive glass (LOF, TEC-15, 15 W per square). After the film was steady, the conductive glass with

film was heated at 400 °C for 1 h under the protection of argon, and the counter electrode was obtained.

A commercial TiO₂ sol (Solaronix, Ti-Nanoxide T/SP) was used to prepare the TiO₂ film on FTO also through the doctor-blade method, and the film was soaked in an N719 dye solution (in ethanol) for 24 h to obtain dye-sensitized TiO₂ electrodes. DSSCs were assembled by injecting the electrolyte into the aperture between the dye-sensitized TiO₂ electrode and the counter electrode. The liquid electrolyte was composed of 0.05 M I₂, 0.1 M LiI, 0.6 M 1, 2-dimethyl-3-propylimidazolium iodide (DMPII), and 0.5 M 4-*tert*-butyl pyridine with acetonitrile as the solvent. Surlyn 1702 was used as the spacer between the two electrodes. The two electrodes were clipped together and solid paraffin was used as the sealant to prevent the electrolyte solution from leaking. The effective cell area was 0.25 cm². The standard sputtered Pt CE was purchased from Dalian Heptachroma Solar Tech Co., Ltd.

2.5 Characterization of CEs and DSSCs

All the electrochemical measurements were obtained using the Zahner IM6 electrochemical workstation. Photocurrent–voltage curves were obtained under simulated AM 1.5 illumination (100 mW cm⁻², Trusttech CHF-XM-500W) with a Keithley digital source meter (Keithley 2410, USA). Electrochemical impedance spectroscopy (EIS) analysis was conducted at zero bias potential and the impedance data covered a frequency range of 0.1 Hz to 1 MHz. The amplitude of the sinusoidal AC voltage signal was 5 mV. The analyses of the resulting impedance spectra were conducted using Zview 2.0 software. Tafel–polarization measurements were employed in a symmetrical dummy cell, which was used in the EIS experiments. The electrolyte was as the same of the electrolyte of DSSC. The scan rate was 20 mV s⁻¹, and the voltage range was -1.0 to 1.0 V. Cyclic voltammetry (CV) was recorded using a three-electrode system on the electrochemical workstation. Pt was used as the counter electrode and Ag/AgCl was used as the reference electrode. A solution of 10.0 mM LiI, 1.0 mM I₂, and 0.1 M LiClO₄ in acetonitrile served as the electrolyte.

3. Results and discussion

XRD and Raman spectroscopy were employed to determine the crystalline-phase structures and purity of the as-prepared NiSe₂/RGO, NiSe₂ and GO samples. Fig. 1a displays the XRD patterns of NiSe₂/RGO (red line) and NiSe₂ (green line) for reference. The XRD patterns revealed that all diffraction peaks of both NiSe₂/RGO and NiSe₂ samples are sharp, indicative of the good crystallization of the as-prepared samples. The strongest peak of NiSe₂/RGO and NiSe₂ samples was found at position 33.41°, corresponding to the (210) plane. Major diffraction peaks observed at diffraction angles are in a good agreement with the cubic NiSe₂ (JCPDS card, no. 88-1711) and a previous report.²⁸ It is worth noting that no other impurity phases were detected, confirming the very high purity of the obtained NiSe₂/RGO and NiSe₂ samples. Besides, the obtained NiSe₂ possesses a pyrite structure (Fig. 1b) with the octahedral arrangement of the



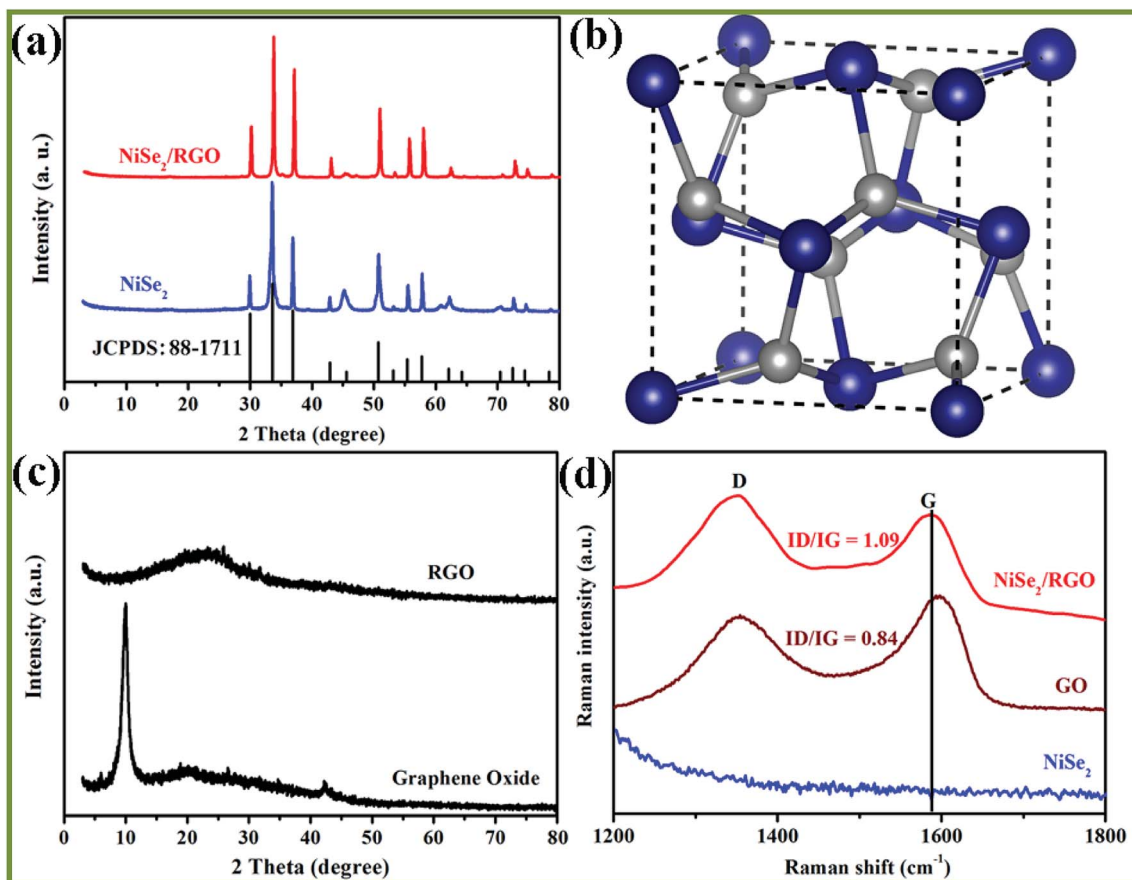


Fig. 1 XRD patterns of NiSe₂/RGO NPs and NiSe₂ NPs samples (a). The standard diffraction patterns for NiSe₂ (JCPDS no. 41-1495) appear below the pattern. Crystal structure of cubic pyrite NiSe₂ (Ni blue, Se grey) (b). XRD patterns of GO and RGO (c). Raman spectra of NiSe₂/RGO NPs, GO and NiSe₂ NPs (d).

adjacent Se atoms units between two Ni atoms.^{22,29} As seen in Fig. 1c, GO shows a significant (002) peak at 10.02°, while the main peak of RGO shifted to a larger angle at 23.6°. In the Raman spectra (Fig. 1d), two characteristic peaks in accordance with the D and G bands of NiSe₂/RGO and GO were clearly observed. Furthermore, the G band shifted to lower frequency with the increased I_D/I_G ratio (1.09) in NiSe₂/RGO compared with GO (I_D/I_G was 0.84). The shifted Raman frequency and increased I_D/I_G ratio further confirmed the reduction of GO and the presence of RGO in NiSe₂/RGO.³⁰

The chemical states and surface composition of NiSe₂/RGO were identified by XPS spectra (Fig. 2). In the high-resolution Ni 2p spectrum (Fig. 2a), six asymmetric peaks could be observed. Two peaks at 855.6 and 873.2 eV correspond to Ni 2p_{3/2} and Ni 2p_{1/2}, respectively. The peaks at 853.4 and 870.6 eV are ascribed to Ni²⁺ ions, the peaks at 855.6 and 873.2 eV are ascribed to Ni³⁺ ions in the surface oxide phase, while two satellite peaks at 861.8 and 880.8 eV are ascribed to the Ni²⁺ oxidation state.^{24,31} Deconvoluting the Se peak, the peaks with binding energies of 54.4 eV (Se 3d_{5/2}) and 55.2 eV (Se 3d_{3/2}) originate from a pyrite NiSe₂ compound, while another peak with binding energy of 58.4 eV corresponds to the surface oxidation of Se species.^{25,31} XRD, Raman and XPS characterizations confirmed that NiSe₂/RGO and NiSe₂ were obtained.

The microstructure and morphology of NiSe₂/RGO NPs was investigated by scanning electron microscopy (SEM) and transmission electron microscopy (TEM). The SEM image in Fig. 3a shows that the NiSe₂/RGO samples are nano-sized particles and tend to disperse on the surface of graphene nanosheets. The low magnification TEM image (Fig. 3b) further implies that the as-obtained NiSe₂/RGO samples were dispersed on the graphene, and the grey ultrathin nanosheets in the range of vision are graphene. The nanoparticle diameter of the NiSe₂/RGO samples is in the range of 35 to 50 nm, determined by magnified TEM image (Fig. 3c). From the HRTEM image (Fig. 3d), the distinct lattice spacing of the NiSe₂/RGO NPs nm can be observed. In contrast with the serious agglomeration of pure NiSe₂ NPs (Fig. S1†), the dispersed distribution of NiSe₂/RGO NPs with the addition of graphene could increase the amount of efficient catalytic active sites, improve the charge-transfer ability and enhance the catalytic activity. SEM and TEM measurements of graphene are shown in Fig. S2.†

To investigate the charge-transfer ability and catalytic activity of NiSe₂/RGO NPs and NiSe₂ NPs samples as CEs of DSSCs, Nyquist plots of the electrochemical impedance spectroscopy (EIS) for CEs were obtained using symmetric dummy cells fabricated with a sandwich-like structure (CE/electrolyte/CE). The Nyquist plots are shown in Fig. 4 and the relevant



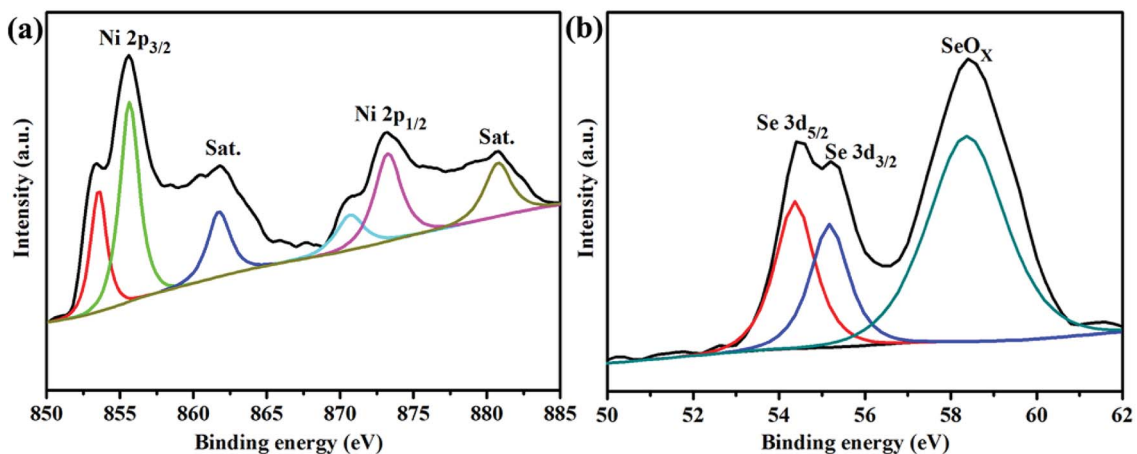


Fig. 2 XPS analysis of the Ni 2p and Se 3d spectra of NiSe₂/RGO NPs.

equivalent circuit diagram is shown as an inset; the corresponding parameters fitted by Z-view software are listed in Table 1. The intercept of the real axis of high frequency in Nyquist plots is series resistance (R_s), and the diameter of the high-frequency (left) semicircle is charge transfer resistance (R_{ct}).³² The R_s value of NiSe₂ NPs CE is 14.99 $\Omega\text{ cm}^{-2}$, and after being combined with graphene the R_s value of NiSe₂/RGO NPs CE is 14.26 $\Omega\text{ cm}^{-2}$, slightly lower than that of Pt CE ($R_s = 14.53\ \Omega\text{ cm}^{-2}$). R_{ct} is the other important parameter obtained in Nyquist plots, negatively correlating with the charge-transfer

ability and catalytic activity of the CEs.^{16,33} Simultaneously, from the parameters in Table 1, the R_{ct} value of NiSe₂/RGO NPs CE ($R_{ct} = 1.52\ \Omega\text{ cm}^{-2}$) is also lower than that of NiSe₂ NPs CE ($R_{ct} = 3.82\ \Omega\text{ cm}^{-2}$), and even inferior to that of Pt CE ($R_{ct} = 1.72\ \Omega\text{ cm}^{-2}$), indicative of its supreme electrocatalytic activity for triiodide reduction.^{19,34} The integration of low R_{ct} and R_s of NiSe₂/RGO NPs CE can efficiently lower the charge transfer resistance and facilitate the transfer of electron, thus contributing to the improvement of the electrocatalytic performance of DSSCs.³⁵

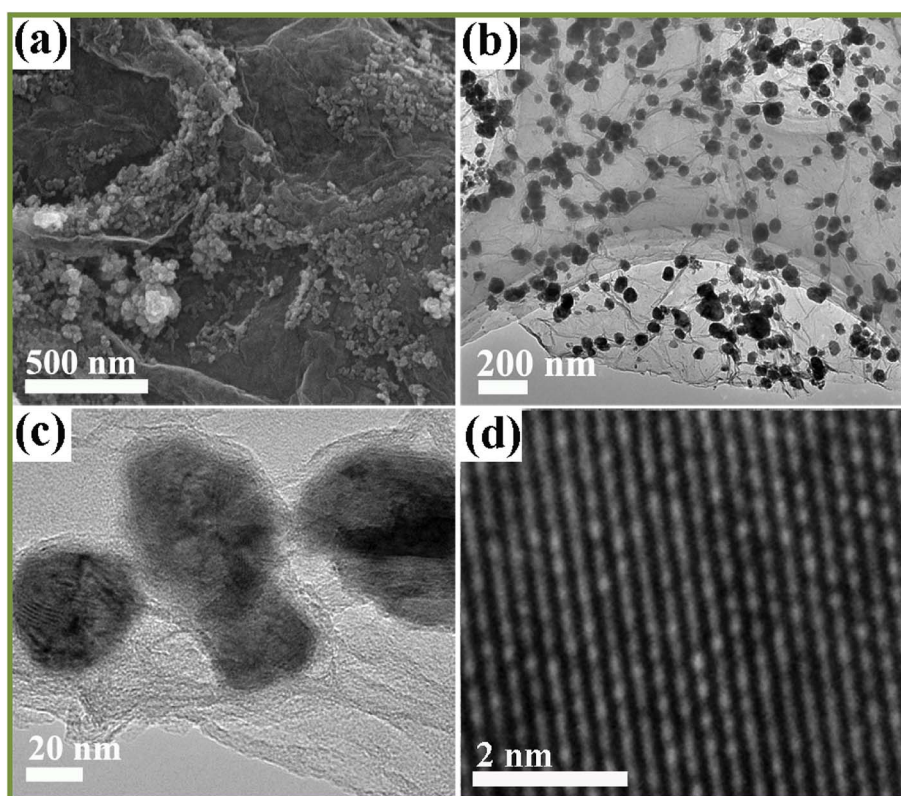


Fig. 3 SEM (a), TEM (b and c) and HRTEM (d) images of NiSe₂/RGO NPs.



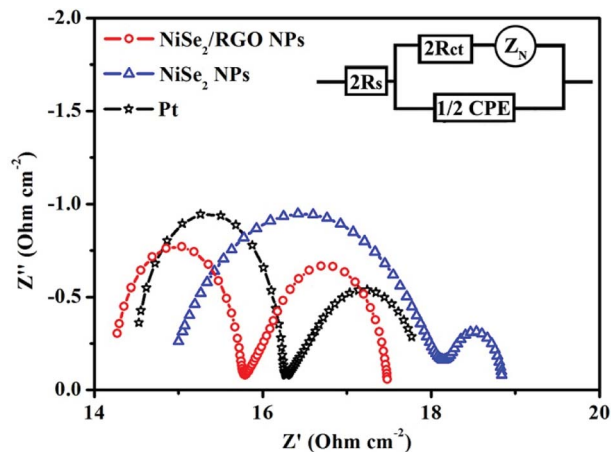


Fig. 4 Nyquist plots for dummy cells fabricated with NiSe₂/RGO NPs, NiSe₂ NPs and Pt CEs. The inset gives the equivalent circuit.

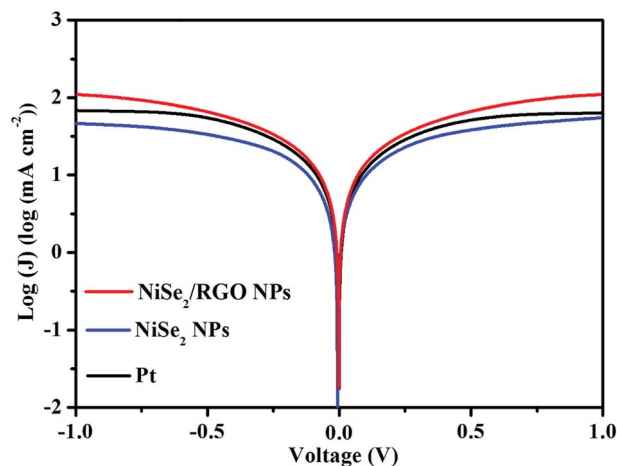


Fig. 5 Tafel polarization curves for dummy cells fabricated with NiSe₂/RGO NPs, NiSe₂ NPs and Pt CEs between 1.0 and -1.0 V.

Tafel polarization measurement is an effective technique for examining the charge-transfer kinetics of CEs. Symmetric cells with the sandwich-type configuration of CEs are fabricated using the same method as that used for the EIS. The polarization zone of the Tafel polarization curve (Fig. 5) corresponds to the high-frequency region of Nyquist plots, and the diffusion zone relates to the low-frequency region.^{36,37} In the Tafel polarization curve, the limiting diffusion current density (J_{lim} , the intersection of the anodic branch with the y axis) and the exchange current density (J_0 , the slope for the anodic or cathodic branch) are closely correlated with the diffusion ability of I_3^- at the electrode/electrolyte interface and the electrocatalytic activity of the CEs, respectively.^{38,39} A higher J_{lim} reveals a larger ionic diffusion coefficient between the two electrodes based on eqn (1):

$$D = lJ_{\text{lim}}/2nFC \quad (1)$$

where D is the diffusion coefficient, l is the distance between the two electrodes, n ($n = 2$) is the total number of electrons involved in the reduction at the electrolyte-CE interfaces, F is the Faraday constant, and C is the I_3^- concentration. The J_{lim} value of the NiSe₂/RGO NPs CE ($1.95 \log(\text{mA cm}^{-2})$) is higher than that of the NiSe₂ NPs CE ($1.67 \log(\text{mA cm}^{-2})$), and slightly exceeds that of the Pt CE ($1.83 \log(\text{mA cm}^{-2})$). On the other hand, a higher J_0 indicates better catalytic activity for I_3^- reduction, and there is also a positive correlation between J_0 and R_{ct} based on eqn (2).⁴⁰

$$J_0 = RT/nFR_{\text{ct}} \quad (2)$$

where R is the gas constant, T is the temperature and R_{ct} is the charge transfer resistance. Owing to the presence of graphene, NiSe₂/RGO NPs CE exhibited higher J_{lim} and J_0 values than NiSe₂ NPs CE, which are in good agreement with the results of the EIS.

In order to further study the reaction kinetics of NiSe₂/RGO NPs, NiSe₂ NPs and Pt CEs for the reduction of triiodide, cyclic voltammetry (CV) was performed with a three-electrode system at a scan rate of 25 mV s^{-1} . As presented in Fig. 6, two typical pairs of oxidation-reduction peaks can be clearly seen in each CV curve, indicating the same electrocatalytic mechanism toward triiodide reduction.^{12,41} From low potential to high

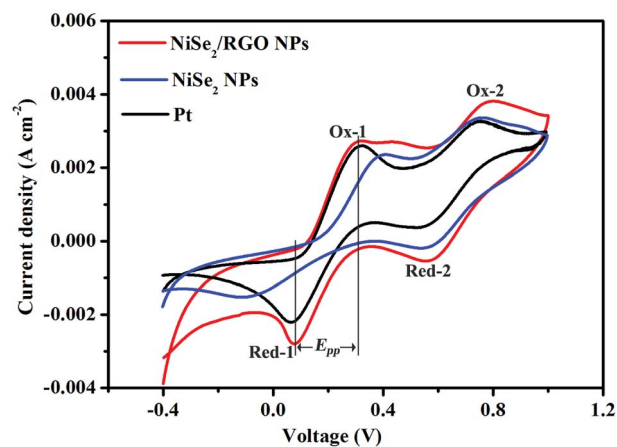






Fig. 6 Cyclic voltammograms of the NiSe₂/RGO NPs, NiSe₂ NPs and Pt CEs at a scan rate of 25 mV s^{-1} .

Table 1 The corresponding values of series resistance (R_s), charge-transfer resistance (R_{ct}), limiting diffusion current density (J_{lim}), peak-to-peak separation (E_{pp}) and cathodic peak current density ($J_{\text{Red-1}}$)

CE	R_s (Ohm cm^{-2})	R_{ct} (Ohm cm^{-2})	J_{lim} log (mA cm^{-2})	E_{pp} (mV)	$J_{\text{Red-1}}$ (mA cm^{-2})
NiSe ₂ /RGO NPs	14.26	1.52	1.95	232	2.80
NiSe ₂ NPs	14.99	3.28	1.67	499	1.56
Pt	14.53	1.72	1.83	261	2.22



potential, the reactions of four oxidation–reduction peaks can be ascribed to eqns (3)–(6):



The peak-to-peak potential separation (E_{pp}) between Red-1 and Ox-1 and the peak current intensity of Red-1 ($J_{\text{Red-1}}$) are two important parameters for assessing the electrocatalytic activity of a CE (Table 1). In detail, the E_{pp} value is negatively correlated with the standard electrochemical rate constant and positively with overpotential loss, and $J_{\text{Red-1}}$ is positively correlated with reaction velocity and electrocatalytic activity.^{10,42} The NiSe₂/RGO NPs CE exhibited a lower E_{pp} value (232 mV) and a higher $J_{\text{Red-1}}$ value (2.80 mA cm⁻²) than those of the NiSe₂ NPs CE ($E_{\text{pp}} = 499$ mV, $J_{\text{Red-1}} = 1.56$ mA cm⁻²), revealing the better intrinsic electrocatalytic activity of the NiSe₂/RGO NPs CE as well as a synergistic catalytic effect between NiSe₂ and graphene. In comparison with the Pt ($E_{\text{pp}} = 261$ mV, $J_{\text{Red-1}} = 2.22$ mA cm⁻²) CE, the E_{pp} and $J_{\text{Red-1}}$ of NiSe₂/RGO NPs CE are also better, signifying that the electrocatalytic activity of the NiSe₂/RGO NPs CE is even superior to that of the Pt CE.^{43,44}

Photocurrent density–voltage (J – V) curves of the integrated DSSCs fabricated with NiSe₂/RGO, NiSe₂ and Pt CEs were measured under irradiation at 100 mW cm⁻². The detailed photovoltaic parameters, including the values of open-circuit voltage (V_{OC}), short-circuit photocurrent density (J_{SC}), fill factor (FF) and power conversion efficiency (PCE), are summarized in Table 2. As shown in Fig. 7, it is obvious that the V_{OC} values of the NiSe₂/RGO NPs, NiSe₂ NPs and Pt CEs are similar, owing to the same photoanode, dye and electrolyte. Remarkably, the DSSC based on NiSe₂/RGO NPs CE reached a higher PCE (7.76%) compared to that of NiSe₂ NPs CE (6.51%), which is even higher than that of Pt (PCE = 7.56%). This improvement may be visually attributed to the higher J_{SC} value of the NiSe₂/RGO NPs CE (17.15 mA cm⁻²) than those of the NiSe₂ NPs CE (15.16 mA cm⁻²) and Pt CE (15.99 mA cm⁻²). On one hand, the well-dispersion of NiSe₂ nanoparticles on the surface of graphene increased the number of catalytic active sites of NiSe₂ nanoparticles for redox couple and enhanced the I₃⁻ reduction.⁴⁵ On the other hand, the high conductive graphene provided faster electron transfer paths and accelerated the

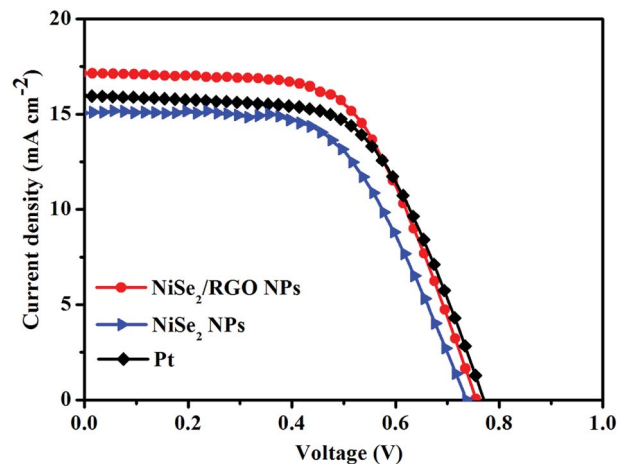


Fig. 7 Photocurrent density–voltage curves of DSSCs fabricated with NiSe₂/RGO NPs, NiSe₂ NPs and Pt CEs under simulated sunlight irradiation (100 mW cm⁻²).

transfer of photogenerated electrons collected from the external circuit to active sites, thus promoting the electrochemical reaction kinetics for the reduction of I₃⁻ to I⁻ at CE and the regeneration of the dye at the photoanode.⁴⁶ All these results demonstrated that dispersed NiSe₂ nanoparticles on graphene yielded enhanced electrocatalytic activity and high conversion efficiency. The electrocatalytic performance characterizations, EIS, CV, Tafel polarization and J – V curves of RGO are shown in Fig. S4.†

To elucidate the relationship between the peak current densities (Ox-1 and Red-1) and the scanning rates, cyclic voltammetry (CV) measurements of the NiSe₂/RGO NPs and NiSe₂ NPs electrodes were conducted at different scan rates. As shown in Fig. 8a and b, it can be clearly seen that NiSe₂/RGO NPs and NiSe₂ NPs electrodes both showed excellent reversible responses. Meanwhile, their reduction and oxidation peak currents increase gradually and regularly with the scan rate increasing from 10 to 100 mA cm⁻². Fig. 8c illustrates the Ox-1 and Red-1 peak current densities of the NiSe₂/RGO NPs and NiSe₂ NPs CEs *versus* the square root of the scan rate. Both CEs exhibit nearly linear relationships for all the lines. Furthermore, the Ox-1 and Red-1 peak current densities of the NiSe₂/RGO NPs at different scan rates are all higher than those of the NiSe₂ NPs, further proving the enhanced electrocatalytic activity of the dispersed NiSe₂ nanoparticles on graphene.^{36,47}

The long-term stability of the NiSe₂/RGO NPs and NiSe₂ NPs CEs was evaluated by repeatedly recording 20-cycle CV curves at a scan rate of 25 mV s⁻¹, as shown in Fig. 8d. It is apparent that the NiSe₂ NPs CE showed an obvious change in peak current density and E_{pp} after 20 cycles of scanning, which is owing to the aggregation during the electrocatalytic reaction. After being combined with graphene, the NiSe₂/RGO NPs CE exhibited excellent long-term stability and negligible change took place, revealing that dispersed distribution on graphene effectively improved the chemical stability of NiSe₂ NPs. The enhanced electrocatalytic performance and long-term stability demonstrated that NiSe₂/RGO NPs are a good candidate electrocatalyst to replace expensive Pt materials for DSSCs.

Table 2 The corresponding values of open-circuit voltage (V_{OC}), short-circuit current (J_{SC}), fill factor (FF), and power conversion efficiency (PCE)

CE	V_{OC} (mV)	J_{SC} (mA cm ⁻²)	FF	PCE (%)
NiSe ₂ /RGO NPs	755	17.15	0.60	7.76
NiSe ₂ NPs	740	15.16	0.58	6.51
Pt	770	15.99	0.61	7.51



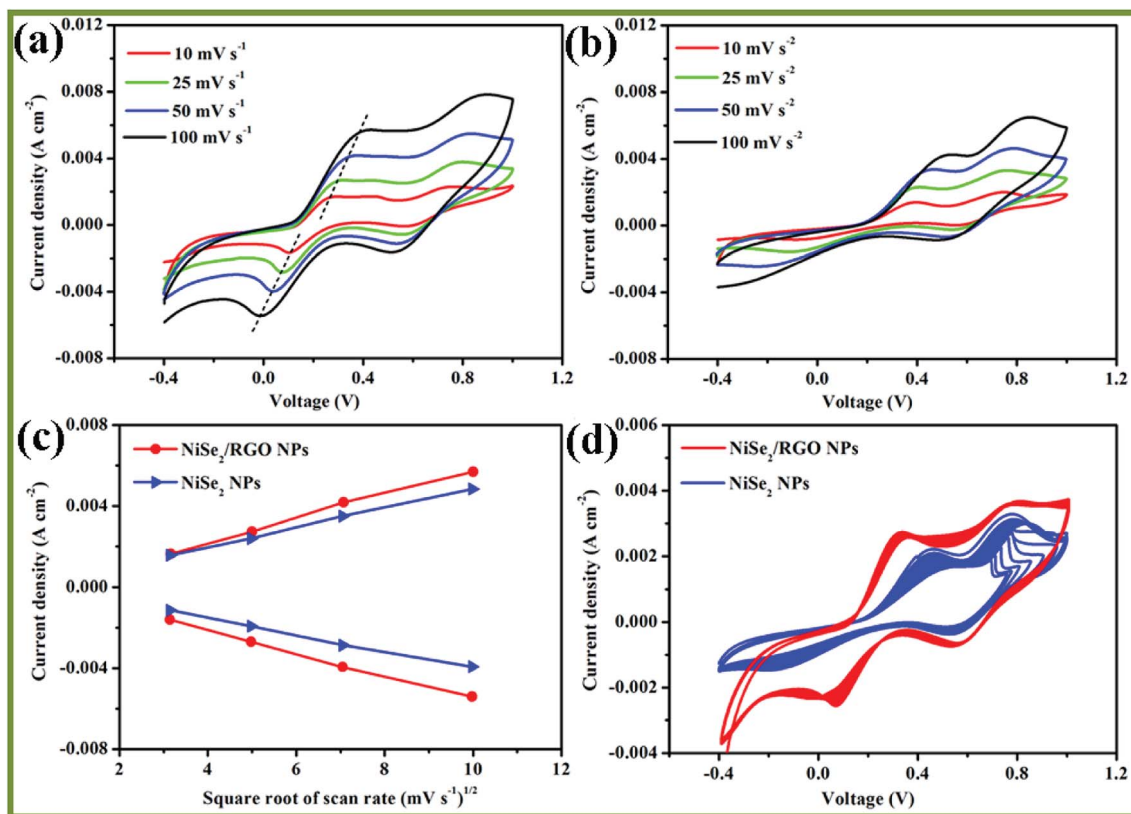


Fig. 8 Cyclic voltammograms of NiSe₂/RGO NPs (a), NiSe₂ NPs (b) at different scan rates. Relationship between redox current densities and the square root of the scan rates (c). 20 consecutive cyclic voltammograms of NiSe₂/RGO NPs and NiSe₂ NPs (d).

4. Conclusion

In summary, in this work we successfully fabricated nickel diselenide electrocatalysts with enhanced electrocatalytic performance through a simple and cost-effective method. With the assistance of graphene, NiSe₂/RGO NPs exhibited better charge-transfer ability and catalytic activity in comparison with expensive Pt electrodes. These enhanced electrocatalytic performance of NiSe₂/RGO NPs were well demonstrated *via* its lower R_{ct} , higher J_{SC} , FF and PCE values. We believe that this work will have significant implications for enhancing electrocatalytic performance and the further development of nickel diselenide.

Conflicts of interest

The authors declare no competing financial interest.

Acknowledgements

The authors acknowledge the financial support from the National Science Foundation of China (No. 51776219).

References

- U. Bach, D. Lupo, P. Comte, J. E. Moser, F. Weissortel, J. Salbeck, H. Spreitzer and M. Grätzel, *Nature*, 1998, **395**, 583–585.
- H. Chen, F. Ye, W. T. Tang, J. J. He, M. S. Yin, Y. B. Wang, F. X. Xie, E. B. Bi, X. D. Yang, M. Grätzel and L. Y. Han, *Nature*, 2017, **550**, 92–95.
- A. Shah, P. Torres, R. Tscharnner, N. Wyrsh and H. Keppner, *Science*, 1999, **285**, 692–698.
- A. Yella, H. W. Lee, H. N. Tsao, C. Y. Yi, A. K. Chandiran, M. K. Nazeeruddin, E. W. G. Diau, C. Y. Yeh, S. M. Zakeeruddin and M. Grätzel, *Science*, 2011, **334**, 629–634.
- S. F. Zhang, X. D. Yang, Y. H. Numata and L. Y. Han, *Energy Environ. Sci.*, 2013, **6**, 1443–1464.
- H. Ren, H. Shao, L. Zhang, D. Guo, Q. Jin, R. Yu, L. Wang, Y. Li, Y. Wang, H. Zhao and D. Wang, *Adv. Energy Mater.*, 2015, **5**, 1500296.
- K. Yoo, J. Y. Kim, J. A. Lee, J. S. Kim, D. K. Lee, K. Kim, J. Y. Kim, B. Kim, H. Kim, W. M. Kim, J. H. Kim and M. J. Ko, *ACS Nano*, 2015, **9**, 3760–3771.
- J. H. Wu, Z. Lan, J. M. Lin, M. L. Huang, Y. F. Huang, L. Q. Fan, G. G. Luo, Y. Lin, Y. M. Xie and Y. L. Wei, *Chem. Soc. Rev.*, 2017, **46**, 5975–6023.
- M. Chen, L. L. Shao, Z. Y. Yuan, Q. S. Jing, K. J. Huang, Z. Y. Huang, X. H. Zhao and G. D. Zou, *ACS Appl. Mater. Interfaces*, 2017, **9**, 17949–17960.
- S. Huang, J. Zai, D. Ma, Z. Hu, Q. He, M. Wu, D. Chen, Z. Chen and X. Qian, *Electrochim. Acta*, 2017, **241**, 89–97.
- H. Yuan, Q. Z. Jiao, J. Li, X. F. Liu, H. Y. Yang, Y. Zhao, Q. Wu, D. X. Shi and H. S. Li, *J. Power Sources*, 2016, **336**, 132–142.



- 12 S. S. Huang, D. Ma, Z. J. Hu, Q. Q. He, J. T. Zai, D. Y. Chen, H. Sun, Z. W. Chen, Q. Q. Qao, M. H. Wu and X. F. Qian, *ACS Appl. Mater. Interfaces*, 2017, **9**, 27607–27617.
- 13 F. Du, X. Q. Zuo, Q. Yang, G. Li, Z. L. Ding, M. Z. Wu, Y. Q. Ma and K. R. Zhu, *J. Mater. Chem. C*, 2016, **4**, 10323–10328.
- 14 F. Du, X. Q. Zuo, Q. Yang, B. Yang, G. Li, H. B. Tang, H. L. Zhang, M. Z. Wu and Y. Q. Ma, *Sol. Energy Mater. Sol. Cells*, 2016, **149**, 9–14.
- 15 S. N. Yun, A. Hagfeldt and T. L. Ma, *Adv. Mater.*, 2014, **26**, 6210–6237.
- 16 Q. L. Liu, Y. J. Dong, Y. Cao, H. Y. Chen, D. B. Kuang and C. Y. Su, *Electrochim. Acta*, 2017, **250**, 244–250.
- 17 P. J. Li, Y. G. Zhang, W. J. Fa, X. G. Yang and L. Wang, *J. Power Sources*, 2017, **360**, 232–242.
- 18 H. Q. Zhou, Y. M. Wang, R. He, F. Yu, J. Y. Sun, F. Wang, Y. C. Lan, Z. F. Ren and S. Chen, *Nano Energy*, 2016, **20**, 29–36.
- 19 X. D. Cui, Z. Q. Xie and Y. Wang, *Nanoscale*, 2016, **8**, 11984–11992.
- 20 Z. T. Jin, M. R. Zhang, M. Wang, C. Q. Feng and Z. S. Wang, *Acc. Chem. Res.*, 2017, **50**, 895–904.
- 21 C. Yu, X. Meng, X. Song, S. Liang, Q. Dong, G. Wang, C. Hao, X. Yang, T. Ma, P. M. Ajayan and J. Qiu, *Carbon*, 2016, **100**, 474–483.
- 22 F. Wang, Y. Li, T. A. Shifa, K. Liu, F. Wang, Z. Wang, P. Xu, Q. Wang and J. He, *Angew. Chem., Int. Ed.*, 2016, **55**, 6919–6924.
- 23 F. Gong, X. Xu, Z. Q. Li, G. Zhou and Z. S. Wang, *Chem. Commun.*, 2013, **49**, 1437–1439.
- 24 B. Yu, X. Wang, F. Qi, B. Zheng, J. He, J. Lin, W. Zhang, Y. Li and Y. Chen, *ACS Appl. Mater. Interfaces*, 2017, **9**, 7154–7159.
- 25 H. Zhou, F. Yu, Y. Liu, J. Sun, Z. Zhu, R. He, J. Bao, W. A. Goddard, S. Chen and Z. Ren, *Energy Environ. Sci.*, 2017, **10**, 1487–1492.
- 26 X. Meng, C. Yu, B. Lu, J. Yang and J. Qiu, *Nano Energy*, 2016, **22**, 59–69.
- 27 C. Y. Su, Y. P. Xu, W. J. Zhang, J. W. Zhao, X. H. Tang, C. H. Tsai and L. J. Li, *Chem. Mater.*, 2009, **21**, 5674–5680.
- 28 X. Zhang, Y. X. Yang, S. Q. Guo, F. Z. Hu and L. Liu, *ACS Appl. Mater. Interfaces*, 2015, **7**, 8457–8464.
- 29 Z. Zhuang, Q. Peng, J. Zhuang, X. Wang and Y. Li, *Chem. –Eur. J.*, 2005, **12**, 211–217.
- 30 B. Yang, X. Q. Zuo, P. Chen, L. Zhou, X. Yang, H. J. Zhang, G. Li, M. Z. Wu, Y. Q. Ma, S. W. Jin and X. S. Chen, *ACS Appl. Mater. Interfaces*, 2015, **7**, 137–143.
- 31 B. Wang, X. Wang, B. Zheng, B. Yu, F. Qi, W. Zhang, Y. Li and Y. Chen, *Electrochem. Commun.*, 2017, **83**, 51–55.
- 32 K. Ahmad, A. Mohammad and S. M. Mobin, *Electrochim. Acta*, 2017, **252**, 549–557.
- 33 X. Meng, C. Yu, X. Song, Z. Liu, B. Lu, C. Hao and J. Qiu, *J. Mater. Chem. A*, 2017, **5**, 2280–2287.
- 34 M. Chen, G. Zhao, L. L. Shao, Z. Y. Yuan, Q. S. Jing, K. J. Huang, Z. Y. Huang, X. H. Zhao and G. D. Zou, *Chem. Mater.*, 2017, **29**, 9680–9694.
- 35 H. Yuan, Q. Jiao, J. Liu, X. Liu, Y. Li, D. Shi, Q. Wu, Y. Zhao and H. Li, *Carbon*, 2017, **122**, 381–388.
- 36 X. Zhang, S. Q. Guo, M. M. Zhen, G. D. Gao and L. Liu, *J. Electrochem. Soc.*, 2015, **162**, H774–H779.
- 37 S. Q. Guo, L. C. Wang, C. G. Zhang, G. C. Qi, B. C. Gu, L. Liu and Z. H. Yuan, *Nanoscale*, 2017, **9**, 6837–6845.
- 38 L. Li, Q. Lu, J. Y. Xiao, J. W. Li, H. Mi, R. Y. Duan, J. B. Li, W. M. Zhang, X. W. Li, S. Liu, K. Yang, M. X. Wu and Y. C. Zhang, *J. Power Sources*, 2017, **363**, 9–15.
- 39 J. Balamurugan, S. G. Peera, M. Guo, T. T. Nguyen, N. H. Kim and J. H. Lee, *J. Mater. Chem. A*, 2017, **5**, 17896–17908.
- 40 H. M. Li, X. Qian, C. L. Zhu, X. C. Jiang, L. Shao and L. X. Hou, *J. Mater. Chem. A*, 2017, **5**, 4513–4526.
- 41 Y. H. Wu, B. Zhou, C. Yang, X. Zhou and W. H. Zhang, *Chem. Commun.*, 2017, **53**, 5445–5448.
- 42 W. Yang, X. Xu, Y. Gao, Z. Li, C. Li, W. Wang, Y. Chen, G. Ning, L. Zhang, F. Yang, S. Chen, A. Wang, J. Kong and Y. Li, *Nanoscale*, 2016, **8**, 13059–13066.
- 43 X. Meng, C. Yu, X. Song, J. Iocozzia, J. Hong, M. Rager, H. Jin, S. Wang, L. Huang, J. Qiu and Z. Lin, *Angew. Chem., Int. Ed.*, 2018, **57**, 4682–4686.
- 44 X. Meng, C. Yu, X. Song, Y. Liu, S. Liang, Z. Liu, C. Hao and J. Qiu, *Adv. Energy Mater.*, 2015, **5**, 1500180.
- 45 X. H. Miao, K. Pan, G. F. Wang, Y. P. Liao, L. Wang, W. Zhou, B. J. Jiang, Q. J. Pan and G. H. Tian, *Chem. –Eur. J.*, 2014, **20**, 474–482.
- 46 Y. Lou, W. J. Zhao, C. G. Li, H. Huang, T. Y. Bai, C. L. Chen, C. Liang, Z. Shi, D. Zhang, X. B. Chen and S. H. Feng, *ACS Appl. Mater. Interfaces*, 2017, **9**, 18046–18053.
- 47 X. Qian, H. M. Li, L. Shao, X. C. Jiang and L. X. Hou, *ACS Appl. Mater. Interfaces*, 2016, **8**, 29486–29495.

