


Showcasing research from Professor Zhan Chen's Laboratory, Department of Chemistry, University of Michigan, Ann Arbor, Michigan, USA.

Molecular interactions between single layered MoS₂ and biological molecules

With combined applications of surface sensitive Sum Frequency Generation (SFG) vibrational spectroscopy and optical microscopy, detailed mechanisms of interactions between single layered MoS₂ and alpha-helical peptides were elucidated in this study. By rationally designing peptides with varied sequences, it was found that charged amino acids in a peptide played a vital role in ensuring a standing-up pose for the peptide on a single layered MoS₂ surface. The conclusions obtained from experimental studies were validated by the coarse-grain molecular dynamics simulation.

Image reproduced by permission of Jiayi Tian.

As featured in:

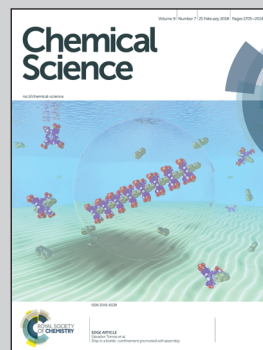

See Zhan Chen *et al.*,
Chem. Sci., 2018, 9, 1769.



rsc.li/chemical-science

Registered charity number: 207890

Cite this: *Chem. Sci.*, 2018, 9, 1769

Molecular interactions between single layered MoS₂ and biological molecules†

Minyu Xiao, Shuai Wei, Yaoxin Li, Joshua Jasensky, Junjie Chen, Charles L. Brooks, III and Zhan Chen*

Two-dimensional (2D) materials such as graphene, molybdenum disulfide (MoS₂), tungsten diselenide (WSe₂), and black phosphorous are being developed for sensing applications with excellent selectivity and high sensitivity. In such applications, 2D materials extensively interact with various analytes including biological molecules. Understanding the interfacial molecular interactions of 2D materials with various targets becomes increasingly important for the progression of better-performing 2D-material based sensors. In this research, molecular interactions between several *de novo* designed alpha-helical peptides and monolayer MoS₂ have been studied. Molecular dynamics simulations were used to validate experimental data. The results suggest that, in contrast to peptide–graphene interactions, peptide aromatic residues do not interact strongly with the MoS₂ surface. It is also found that charged amino acids are important for ensuring a standing-up pose for peptides interacting with MoS₂. By performing site-specific mutations on the peptide, we could mediate the peptide–MoS₂ interactions to control the peptide orientation on MoS₂.

Received 13th November 2017
Accepted 29th November 2017

DOI: 10.1039/c7sc04884j

rsc.li/chemical-science

Introduction

The unique properties of two-dimensional (2D) materials such as graphene allow ultra-sensitive electronic devices to be fabricated for gas sensing, biomolecular detection, *etc.*^{1,2} Molybdenum disulfide (MoS₂), a representative 2D material, has been extensively used for sensing applications,^{3,4} including the construction of biosensors or for biomolecular detection.^{5–7} For example, previous research has reported on a MoS₂-based fluorescence DNA sensor⁵ and the scalable production of MoS₂ based biosensors with proteins.⁷ Biological molecules have also been reported to help facilitate the exfoliation of monolayer MoS₂ flakes in the aqueous phase.^{8,9} We believe that it is therefore crucial to understand the interaction mechanisms between biological molecules and MoS₂ surfaces in order to help the design of MoS₂ based biological sensors.

Research has been performed to study molecular interactions between peptides/proteins and a MoS₂ sheet using simulation methods,^{10–12} but experimental studies to validate such simulation results are rare. In this study, we chose an alpha-helical antimicrobial peptide, a hybrid of cecropin and melittin, as our model to investigate the molecular interactions with MoS₂ using both molecular dynamics simulations and experiments.

Department of Chemistry, University of Michigan, Ann Arbor, Michigan, 48109, USA.
E-mail: zhanc@umich.edu

† Electronic supplementary information (ESI) available: SFG data analysis methods, spectral fitting parameters, additional spectra, CD spectrum, and details about MD simulation methods. See DOI: 10.1039/c7sc04884j

To probe the interactions between the alpha-helical hybrid peptide and a monolayer MoS₂ surface, we implemented optical microscopy with sum frequency generation (SFG) vibrational spectroscopy (Fig. 1). While optical microscopy can help us locate the positions of monolayer MoS₂ flakes, SFG can enable the study of peptide/MoS₂ interactions *in situ* with monolayer sensitivity. More details about the microscope-SFG setup can be found in the ESI.†

A MoS₂ monolayer was not visible on a CaF₂ substrate. To locate such a monolayer region, it was necessary to pre-determine a location of the monolayer MoS₂ flake by AFM,

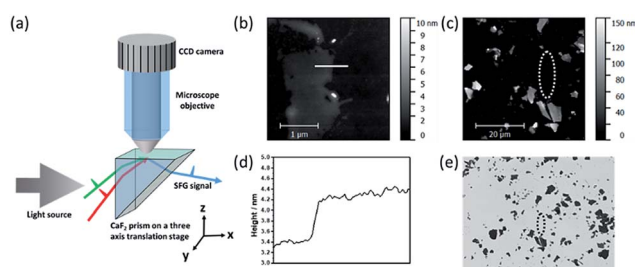


Fig. 1 (a) Schematic of the optical microscope-SFG setup; (b) and (c) AFM images of mechanically exfoliated MoS₂ flakes with different magnifications. (d) Thickness measured by AFM, indicating that the MoS₂ flake in (b) is a monolayer. (e) Optical image of MoS₂ on a CaF₂ prism surface (the circle is the focus of the visible beam for SFG data collection). According to the positions of the multilayered MoS₂ flakes below the circle in both AFM (c) and optical (e) images, we can identify the monolayer MoS₂ sample in the circle.



using thick multilayered MoS₂ regions nearby as fiducial markers (Fig. 1). Then the fiducial markers were located by SFG microscopy, and the visible and infrared beams were focused onto the nearby MoS₂ monolayer region to collect the SFG spectra (Fig. 1).

SFG is a second order nonlinear optical spectroscopic technique with excellent surface selectivity; its equipment and experimental details have been published and will not be repeated here.^{13–21} SFG has been extensively applied to investigate molecular interactions at various interfaces, including interfaces involving polymers, water, DNA, peptides and proteins.^{17–19,22–28} Specifically, for alpha-helical peptides, an SFG amide I peak centered near 1650 cm⁻¹ can be detected. The orientation of a single alpha helical peptide at an interface can be described by a tilt angle θ (the angle between the peptide main axis and the surface normal). Through analysis of the SFG amide I spectra collected using different combinations of p and s polarizations of the input/output beams, the tilt angle θ can be deduced by the measured $\chi_{\text{ppp}}/\chi_{\text{ssp}}$ ratio.²⁹

Materials and methods

Peptide sequence and experimental conditions

All MoS₂ samples were prepared on right-angled CaF₂ prisms through a mechanical exfoliation method. All peptide mutants were purchased from Peptide 2.0 and were used as received, and all peptide solutions were prepared at a concentration of 1.0 μM . Sequences of all peptides used were: wild-type hybrid peptide (KWKLFKKIGIGAVLKVLTGLPALIS), mutant A (KAKLAKKIGIGAVLKVLTGLPALIS), mutant B (SWSLFSSIGIGAVLKVLTGLPALIS), and mutant C (KWKFFKKIGIGAVLKVLTGLPALIS).

Brief description of microscope-SFG

Details about the microscope-SFG setup have been published previously.¹⁴ Briefly, to allow enough working space for an optical microscopic system, an “inverted” total internal reflection SFG sample geometry was used in this study (Fig. 1). Both the visible (532 nm) and tunable infrared (IR) beams were spatially and temporally overlapped onto the prism surface using two CaF₂ lenses. A right-angled CaF₂ prism substrate was placed on a three-axis translational stage: both positions on the x - y plane and the height of the sample can be fine-tuned. The optical microscopic system was positioned above the prism substrate to allow visual monitoring of the sample and the laser spot (for SFG signal detection) *in situ*. A 40 \times objective and telescope were used to magnify the image onto a CCD camera. While keeping the optical microscope stationary, the three-axis translational stage mentioned above allowed full freedom to move the sample to find an ideal position for data collection. Using AFM, we determined the location of a monolayer of MoS₂ with the help of neighboring thick multilayered MoS₂ regions (Fig. 1). Such a location of a monolayer MoS₂ region could be identified using the microscope-SFG with the help of the multilayered MoS₂ regions. Then both the visible and infrared beams were focused onto this region to collect SFG spectra

(Fig. 1). Structural information such as the molecular orientation of surface peptides on a single layer of MoS₂ could then be measured *via* SFG.

Results and discussion

The sequence of a native cecropin–melittin hybrid peptide is shown in Fig. 2, where charged, hydroxyl group-containing, hydrocarbon side chain-containing, or aromatic ring-containing amino acids are labeled in red (most hydrophilic), blue (hydrophilic), black (hydrophobic), and green (most hydrophobic) respectively.³⁰

SFG ssp (s-polarized signal, s-polarized input visible, p-polarized input IR beams) and ppp spectra were collected from the single layer MoS₂/hybrid peptide solution interface (Fig. 2a). Because no SFG signal could be detected from the bare CaF₂/peptide solution interface (not shown), such signals must be due to the peptides on MoS₂. Both SFG spectra exhibit a distinct amide I peak at 1650 cm⁻¹, indicating that the hybrid peptide adopts an alpha-helical secondary structure on the MoS₂ surface, with a non-parallel orientation. According to the ssp and ppp SFG amide I spectra, the orientation of the adsorbed hybrid peptide on MoS₂ was determined to be 15 to 25 degrees for the alpha helix *vs.* the surface normal using the method published previously (Fig. 3).²⁹ More details about the orientation determination can be found in the ESI.†

To better understand the interaction that this cecropin–melittin hybrid peptide has with MoS₂, we performed molecular dynamics simulations (see details about the simulation methods in the ESI.†). Simulation results showed that the C-terminus of this peptide readily interacts with MoS₂ and the remaining residues that are solvent accessible are at a calculated tilt angle of 20.9° from the surface normal (Fig. 4), agreeing with the experimental data quite well.

A cecropin–melittin hybrid peptide has nine amino acid residues in the C-terminus region including one aromatic group-containing residue, five non-aromatic hydrophobic groups, and three hydroxyl-containing hydrophilic residues. The N-terminus region of the cecropin–melittin hybrid peptide has two aromatic-containing amino acids, three hydrophobic (non-aromatic-containing) residues, and four charged residues. The N-terminus has one more aromatic functionality-containing residue. If the aromatic group-containing amino acid played the dominant role in surface–peptide interaction as previously reported for graphene,¹³ the peptide should interact with the MoS₂ surface with its N-terminus. But this was not what was observed in our molecular dynamics simulations: our simulation data indicate that the C-terminus interacts with the MoS₂ surface. We therefore believe that the aromatic amino acid/surface interaction does not play the major role in the peptide/MoS₂ interaction. Instead, the general hydrophobic interactions play the major role: the N-terminus is more hydrophilic because of its more charged groups, and therefore prefers to stay in the aqueous environment rather than on the surface. The C-terminus overall has more hydrophobic groups, which leads to the adsorption of the C-terminus on the surface.



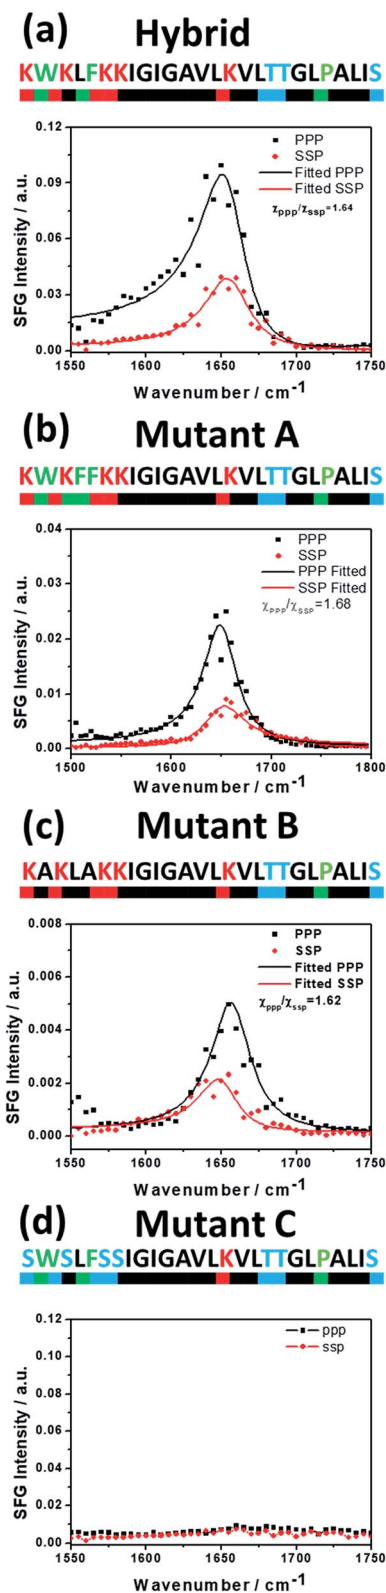


Fig. 2 Primary sequence (top) and SFG spectra collected from the interface between MoS₂ and solutions (bottom) of the native cecropin–melittin hybrid peptide (a), mutant A (b), mutant B (c) and mutant C (d).

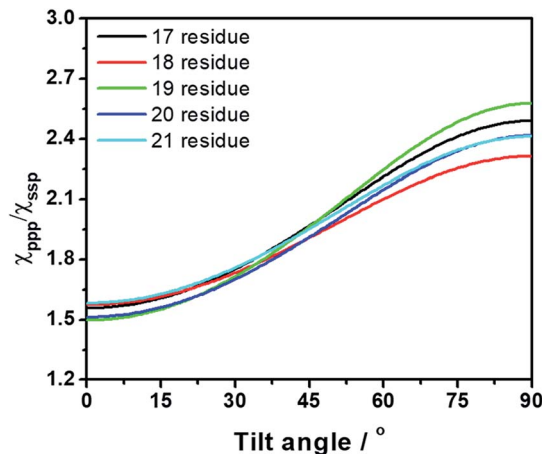


Fig. 3 Dependence of the tilt angle on the measured SFG signal strength $\chi_{\text{PPP}}/\chi_{\text{SSP}}$ ratio for several different lengths of alpha-helical peptide (17–21 residues).

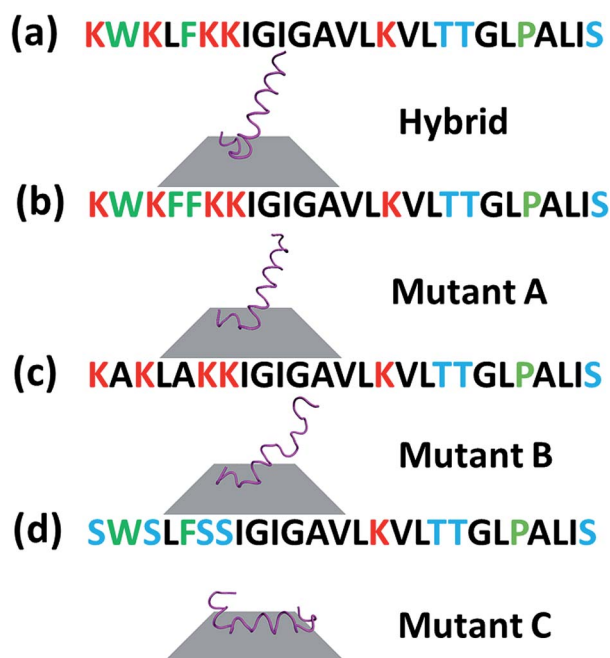


Fig. 4 Simulation results of cecropin–melittin hybrid peptide (a), mutant A (b), mutant B (c) and mutant C (d) on an MoS₂ surface.

To further understand the peptide–MoS₂ physico-adsorption process, we designed three cecropin–melittin hybrid peptide mutants (Fig. 2) and studied their interactions with the MoS₂ surface. For all three mutants, only the N-terminus of the peptide was modified, which was previously identified as being primarily driven into solution for MoS₂ interactions. Mutant A has one extra aromatic residue at the N-terminus. The goal of using this mutant was to examine whether one additional aromatic residue could increase the interaction with MoS₂ in order to change the peptide orientation to a lying-down pose, as previously observed in peptide–graphene interactions.¹³ SFG amide I signals were successfully detected from mutant A on the



MoS₂ surface (Fig. 2b), indicating a nonparallel pose in the α -helical conformation, which matched the MD simulation data (Fig. 4b). The simulation results again indicated that the C-terminus binds to the MoS₂ surface, while the N-terminus points away from the MoS₂ surface into the solution. Both the SFG experimental ratio and the simulation data showed an almost identical orientation of mutant A compared to the native hybrid peptide, showing no strong interaction between the mutant A N-terminus (with one extra aromatic residue) and MoS₂. Indeed, we found through both SFG experiments and MD simulations that even with two additional aromatic side chain-containing amino acids on the N-terminus (mutant A2), the mutant A2 could still adopt a tilting pose on MoS₂ without lying down (Fig. S2†).

The above study on mutant A indicated that it is likely that the aromatic amino acid–MoS₂ interaction is not stronger than the non-aromatic amino acid–MoS₂ interaction. We wanted to know whether this is true *vice versa* and see whether the replacement of the aromatic amino acids with non-aromatic hydrophobic residues affects the peptide/MoS₂ interaction. Therefore, the aromatic residues were all mutated to non-aromatic hydrophobic groups near the N-terminus in mutant B. SFG spectra were successfully collected from mutant B on MoS₂ (Fig. 2c); its orientation was measured to be 15° to 25° *versus* the surface normal, similar to that deduced from the MD simulation results (α -helix with a tilt angle of 29.7°) and also similar to the case of the wild-type peptide presented above. The similar structure of mutant B on MoS₂ to that of the wild-type hybrid indicated that the amino acids with non-aromatic functional groups do not interact with the MoS₂ surface to a greater extent than the aromatic hydrophobic amino acids.

We then studied the effect of charged amino acids on the N-terminus by replacing charged residues with serine (mutant C). If the hydrophilic hydroxyl groups interact with water less favorably than the charged residues, mutant C might lie down on the surface. Indeed, no discernable SFG amide I signal could be detected from the interface between MoS₂ and the mutant C solution. The absence of a SFG signal could be because (1) no peptide was adsorbed onto the MoS₂ surface, or (2) all adsorbed peptides were lying down. To differentiate between these two possibilities, circular dichroism (CD) spectroscopy, sensitive to only secondary structure and not orientation, was used (ESI†). CD data demonstrated that mutant C was present on the MoS₂ surface with an alpha helical secondary structure (Fig. S3†). The above finding was also validated by molecular dynamics simulation (Fig. 4d).

Conclusion

In conclusion, we applied a unique analytical platform to combine an optical microscope with an SFG spectrometer to study peptide interactions that occur on heterogeneous MoS₂ surfaces. This study elucidated the detailed molecular interactions between a cecropin–melittin hybrid peptide and a MoS₂ surface. We found that the aromatic amino acids do not have a substantial effect on peptides interacting with the MoS₂ surface. With three rationally designed peptide mutants

(mutants A, B and C), more details about the peptide interactions on MoS₂ were deduced. It was found that the charged groups in the N-terminus region are needed for the peptide to interact more favorably with the aqueous environment and ensure a “standing-up” peptide pose on MoS₂. SFG experimental results and MD simulation results showed excellent agreement, validating the results obtained in this research: the wild-type hybrid peptide, mutant A, and mutant B were all able to interact favorably with MoS₂ *via* their C-terminus while tilting at around 20° and being solvent accessible. Mutant C, on the other hand, lay down on the MoS₂ surface completely. This fundamental research on the hybrid peptide/MoS₂ interactions lay a foundation for future investigations on the interactions between other peptides and MoS₂, providing insight into the rational design of MoS₂ based biosensors using peptides and proteins. The different mechanisms of the peptide–MoS₂ interactions elucidated in this research, compared to the previously reported peptide–graphene interactions, clearly indicated that it is necessary to study peptide–2D material interactions when different 2D materials were chosen for sensor design. In biosensing applications, it is necessary to control the substrate surface–active biosensing unit interactions to optimize the sensing selectivity and sensitivity. This research also further demonstrated the power of using a microscope-SFG system to study heterogeneous surfaces and interfaces.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

This research is supported by the National Science Foundation (CHE-1505385 for Z. C. and CHE-1506273 for C. B.) and the University of Michigan.

Notes and references

- 1 A. K. Geim and K. S. Novoselov, The rise of graphene, *Nat. Mater.*, 2007, **6**, 183–191.
- 2 Y. Zhang, Y.-W. Tan, H. L. Stormer and P. Kim, Experimental observation of the quantum Hall effect and Berry's phase in graphene, *Nature*, 2005, **438**, 201–204.
- 3 F. K. Perkins, A. L. Friedman, E. Cobas, P. Campbell, G. Jernigan and B. T. Jonker, Chemical vapor sensing with monolayer MoS₂, *Nano Lett.*, 2013, **13**, 668–673.
- 4 D. Sarkar, W. Liu, X. Xie, A. C. Anselmo, S. Mitragotri and K. Banerjee, MoS₂ field-effect transistor for next-generation label-free biosensors, *ACS Nano*, 2014, **8**, 3992–4003.
- 5 C. Zhu, Z. Zeng, H. Li, F. Li, C. Fan and H. Zhang, Single-layer MoS₂-based nanoprobes for homogeneous detection of biomolecules, *J. Am. Chem. Soc.*, 2013, **135**, 5998–6001.
- 6 H. Nam, B.-R. Oh, M. Chen, S. Wi, D. Li, K. Kurabayashi and X. Liang, Fabrication and comparison of MoS₂ and WSe₂ field-effect transistor biosensors, *J. Vac. Sci. Technol., B: Nanotechnol. Microelectron.: Mater., Process., Meas., Phenom.*, 2015, **33**, 06FG01.



- 7 C. H. Naylor, N. Kybert, C. Schneier, J. Xi, G. Romero, J. Saven, R. Liu and A. T. C. Johnson, Scalable Production of Molybdenum Disulfide Based Biosensors, *ACS Nano*, 2016, **10**, 6173–6179.
- 8 G. Guan, S. Zhang, S. Liu, Y. Cai, M. Low, C. P. Teng, I. Y. Phang, Y. Cheng, K. L. Duei, B. M. Srinivasan and Y. Zheng, Protein induces layer-by-layer exfoliation of transition metal dichalcogenides, *J. Am. Chem. Soc.*, 2015, **137**, 6152–6155.
- 9 J. Paredes and S. Villar-Rodil, Biomolecule-assisted exfoliation and dispersion of graphene and other two-dimensional materials: a review of recent progress and applications, *Nanoscale*, 2016, **8**, 15389–15413.
- 10 H. Fan, D. Zhao, Y. Li and J. Zhou, Lysozyme orientation and conformation on MoS₂ surface: Insights from molecular simulations, *Biointerphases*, 2017, **12**, 02D416.
- 11 Z. Gu, Z. Yang, S.-g. Kang, J. R. Yang, J. Luo and R. Zhou, Robust denaturation of villin headpiece by MoS₂ nanosheet: Potential molecular origin of the nanotoxicity, *Sci. Rep.*, 2016, **6**, 28252.
- 12 Y. Ling, Z. Gu, S.-g. Kang, J. Luo and R. Zhou, Structural damage of a β -sheet protein upon adsorption onto molybdenum disulfide nanotubes, *J. Phys. Chem. C*, 2016, **120**, 6796–6803.
- 13 X. Zou, S. Wei, J. Jasensky, M. Xiao, Q. Wang, C. L. Brooks III and Z. Chen, Molecular Interactions between Graphene and Biological Molecules, *J. Am. Chem. Soc.*, 2017, **139**, 1928–1936.
- 14 C. Zhang, J. Jasensky, C. Leng, C. Del Grosso, G. D. Smith, J. J. Wilker and Z. Chen, Sum frequency generation vibrational spectroscopic studies on buried heterogeneous biointerfaces, *Opt. Lett.*, 2014, **39**, 2715–2718.
- 15 Z. Chen, Y. Shen and G. A. Somorjai, Studies of polymer surfaces by sum frequency generation vibrational spectroscopy, *Annu. Rev. Phys. Chem.*, 2002, **53**, 437–465.
- 16 Y. Shen, Surface properties probed by second-harmonic and sum-frequency generation, *Nature*, 1989, **337**, 519–525.
- 17 S. Y. Jung, S. M. Lim, F. Albertorio, G. Kim, M. C. Gurau, R. D. Yang, M. A. Holden and P. S. Cremer, The Vroman effect: a molecular level description of fibrinogen displacement, *J. Am. Chem. Soc.*, 2003, **125**, 12782–12786.
- 18 H. Lutz, V. Jaeger, L. Schmüser, M. Bonn, J. Pfaendtner and T. Weidner, The Structure of the Diatom Silaffin Peptide R5 within Freestanding Two-Dimensional Biosilica Sheets, *Angew. Chem., Int. Ed.*, 2017, **56**, 8277–8280.
- 19 J.-S. Samson, R. Scheu, N. Smolentsev, S. W. Rick and S. Roke, Sum frequency spectroscopy of the hydrophobic nanodroplet/water interface: Absence of hydroxyl ion and dangling OH bond signatures, *Chem. Phys. Lett.*, 2014, **615**, 124–131.
- 20 S. Ye, J. Tan, B. Zhang and Y. Luo, Ultrafast Vibrational Dynamics of Membrane-Bound Peptides at the Lipid Bilayer/Water Interface, *Angew. Chem., Int. Ed.*, 2017, **56**, 12977–12981.
- 21 X. Liu, C. Leng, L. Yu, K. He, L. J. Brown, Z. Chen, J. Cho and D. Wang, Ion-Specific Oil Repellency of Polyelectrolyte Multilayers in Water: Molecular Insights into the Hydrophilicity of Charged Surfaces, *Angew. Chem., Int. Ed.*, 2015, **54**, 4851–4856.
- 22 B. Ding, J. Jasensky, Y. Li and Z. Chen, Engineering and Characterization of Peptides and Proteins at Surfaces and Interfaces: A Case Study in Surface-Sensitive Vibrational Spectroscopy, *Acc. Chem. Res.*, 2016, **49**, 1149–1157.
- 23 Y. Li, X. Zhang, J. Myers, N. L. Abbott and Z. Chen, Room temperature freezing and orientational control of surface-immobilized peptides in air, *Chem. Commun.*, 2015, **51**, 11015–11018.
- 24 T. Weidner, J. S. Apte, L. J. Gamble and D. G. Castner, Probing the orientation and conformation of α -helix and β -strand model peptides on self-assembled monolayers using sum frequency generation and NEXAFS spectroscopy, *Langmuir*, 2009, **26**, 3433–3440.
- 25 D. Schach, C. Globisch, S. J. Roeters, S. Woutersen, A. Fuchs, C. K. Weiss, E. H. Backus, K. Landfester, M. Bonn, C. Peter and T. Weidner, Sticky water surfaces: Helix-coil transitions suppressed in a cell-penetrating peptide at the air-water interface, *J. Chem. Phys.*, 2014, **141**, 22D517.
- 26 E. C. Yan, L. Fu, Z. Wang and W. Liu, Biological macromolecules at interfaces probed by chiral vibrational sum frequency generation spectroscopy, *Chem. Rev.*, 2014, **114**, 8471–8498.
- 27 L. Schmueser, S. J. Roeters, H. Lutz, S. Woutersen, M. Bonn and T. Weidner, Determination of Absolute Orientation of Protein α -Helices at Interfaces using Phase Resolved SFG Spectroscopy, *J. Phys. Chem. Lett.*, 2017, **8**, 3101–3105.
- 28 A. G. De Beer and S. Roke, What interactions can distort the orientational distribution of interfacial water molecules as probed by second harmonic and sum frequency generation?, *J. Chem. Phys.*, 2016, **145**, 044705.
- 29 K. T. Nguyen, S. V. Le Clair, S. Ye and Z. Chen, Orientation determination of protein helical secondary structures using linear and nonlinear vibrational spectroscopy, *J. Phys. Chem. B*, 2009, **113**, 12169–12180.
- 30 O. D. Monera, T. J. Sereda, N. E. Zhou, C. M. Kay and R. S. Hodges, Relationship of sidechain hydrophobicity and α -helical propensity on the stability of the single-stranded amphipathic α -helix, *J. Pept. Sci.*, 1995, **1**, 319–329.

