


Showcasing research from Professor Wu's laboratory, Key Laboratory of Materials Physics, CAS Center for Excellence in Nanoscience, Institute of Solid State Physics, China, and the Institute of Physical Science and Information Technology, Anhui University, China.

Is the kernel–staples match a key–lock match?

Here we developed an acid-induction method for synthesizing a novel gold nanocluster whose composition was determined to be  $Au_{42}(TBBT)_{26}$  (TBBT: 4-tert-butylbenzenethiolate) by ESI-MS and single-crystal X-ray crystallography (SCXC). SCXC also reveals that  $Au_{42}(TBBT)_{26}$  has an identical kernel while having different staples with an existing gold nanocluster,  $Au_{44}(TBBT)_{28}$ , indicating that the kernel–staples match is not a key–lock match and the existence of the homo–ligand–homo–kernel–hetero–staples phenomenon in metal nanoclusters. Further experiments reveal that the staples greatly contribute to the stability and photoluminescence intensity of gold nanoclusters.

As featured in:

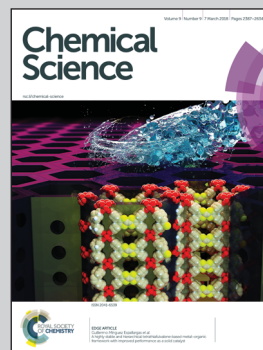

See Zhikun Wu *et al.*,  
*Chem. Sci.*, 2018, 9, 2437.



[rsc.li/chemical-science](http://rsc.li/chemical-science)

Registered charity number: 207890

Cite this: *Chem. Sci.*, 2018, 9, 2437

## Is the kernel–staples match a key–lock match?†

Shengli Zhuang,<sup>‡abc</sup> Lingwen Liao,<sup>‡ac</sup> Yan Zhao,<sup>‡abc</sup> Jinyun Yuan,<sup>id bd</sup>  
Chuanhao Yao,<sup>id ac</sup> Xu Liu,<sup>abc</sup> Jin Li,<sup>e</sup> Haiteng Deng,<sup>f</sup> Jinlong Yang,<sup>id bd</sup>  
and Zhikun Wu<sup>id \*ac</sup>

Metal nanoclusters provide excellent references for understanding metal nanoparticle surfaces, which remain mysterious due to the difficulty of atomically precise characterization. Although some remarkable advances have been achieved for understanding the structure of metal nanoclusters, it is still unknown if the inner kernel–outer staples match is a key–lock match and how the surface staples influence some of the properties of metal nanoclusters. Herein, we have developed an acid-induction method for synthesizing a novel gold nanocluster whose composition is determined to be Au<sub>42</sub>(TBBT)<sub>26</sub> (TBBT: 4-*tert*-butylbenzenethiolate) by ESI-MS and single-crystal X-ray crystallography (SCXC). SCXC also reveals that Au<sub>42</sub>(TBBT)<sub>26</sub> has an identical kernel but different staples with an existing gold nanocluster Au<sub>44</sub>(TBBT)<sub>28</sub>, indicating that the kernel–staples match is not a key–lock match and the existence of homo-ligand–homo-kernel–hetero-staples phenomenon in metal nanoclusters provides some reference for understanding the growth or transformation of metal nanoclusters. Further experiments reveal that the staples greatly contribute to the stability of gold nanoclusters and influence their photoluminescence intensity and that minute differences in the interfacial structure can lead to enhanced stability and photoluminescence.

Received 23rd November 2017  
Accepted 28th January 2018

DOI: 10.1039/c7sc05019d

rsc.li/chemical-science

## Introduction

Ligand-protected metal nanoparticles have received extensive interest not only for fundamental scientific research but also for their practical applications over the past several decades.<sup>1</sup> However, the surfaces of the nanoparticles remain mysterious due to the difficulty of atomically precise characterization. The recently emergent metal nanoclusters<sup>2</sup> provide excellent references for understanding metal nanoparticle surfaces because the compositions of the metal nanoclusters can be precisely

determined by mass spectrometry and because the total structures of metal nanoclusters can be resolved by single-crystal X-ray crystallography (SCXC). To date, over a dozen metal nanoclusters<sup>2b,3</sup> have been structurally resolved by SCXC, which reveals that metal nanoclusters consist of pure metal kernels and ligand-containing staples (herein, the bridging thiolates are also included in the staples for simplification). It is believed that the kernel is protected from aggregation or decomposition by the staples;<sup>4</sup> thus, the staples should match the kernel, otherwise the nanocluster cannot be stable.

Moreover, some theoretical calculations indicate that the protecting staple motifs should fit the curvature of the kernel of the nanoclusters.<sup>5</sup> Essential questions include the following: is this match a key–lock match (*i.e.*, if the metal, the thiolate and the kernel are all fixed, are the staples exclusive)? If not, will a variation of the staples lead to great change in the stability and other properties (*e.g.*, photoluminescence) of nanoclusters? These questions are important to understand the interaction between staples and the kernel, the staples' influence on the properties, and the growth (or transformation) mechanism of metal nanoclusters.<sup>6</sup> To address these questions, we have developed a method to synthesize a novel gold nanocluster protected by 4-*tert*-butylbenzenethiolate (TBBT), which has identical Au<sub>34</sub> kernels but varied staples with an existing gold nanocluster–Au<sub>44</sub>(TBBT)<sub>28</sub>, and we compare the stability and photoluminescence properties between the two homo-kernelled gold nanoclusters.

<sup>a</sup>Key Laboratory of Materials Physics, Anhui Key Laboratory of Nanomaterials and Nanotechnology, CAS Center for Excellence in Nanoscience, Institute of Solid State Physics, Chinese Academy of Sciences, Hefei, Anhui 230031, P. R. China. E-mail: zkwu@issp.ac.cn

<sup>b</sup>Department of Chemistry, University of Science and Technology of China, Hefei, Anhui 230026, P. R. China

<sup>c</sup>Institute of Physical Science and Information Technology, Anhui University, Hefei, Anhui 230601, P. R. China

<sup>d</sup>Hefei National Laboratory for Physics Sciences at the Microscale, University of Science and Technology of China, Hefei, Anhui 230026, P. R. China

<sup>e</sup>Tsinghua University–Peking University Joint Center for Life Sciences, School of Life Sciences, Tsinghua University, Beijing 100084, P. R. China

<sup>f</sup>MOE Key Laboratory of Bioinformatics, School of Life Sciences, Tsinghua University, Beijing 100084, P. R. China

† Electronic supplementary information (ESI) available: CCDC 1587211. For ESI and crystallographic data in CIF or other electronic format see DOI: 10.1039/c7sc05019d

‡ S. Zhuang, Dr L. Liao, Y. Zhao contributed equally to this work.



## Results and discussion

The synthesis of  $\text{Au}_{42}(\text{TBBT})_{26}$  nanoclusters was according to the method described by us in our previous study.<sup>3p</sup> Some modifications were made to this method, and the details are provided in the experimental section. Briefly, tetraoctylammonium bromide (TOAB) was dissolved in ethyl acetate in a tri-neck flask, and  $\text{HAuCl}_4 \cdot 4\text{H}_2\text{O}$  was added to the solution. After the solution was stirred for 10 min, 4-*tert*-butylbenzenethiol was added. When the color of the solution changed from deep red to yellow, an acetic acid-water mixture was added, and then, a cold water solution of  $\text{NaBH}_4$  was added all at once immediately. Please note that without the addition of acid, the  $\text{Au}_{42}(\text{TBBT})_{26}$  nanoclusters cannot be obtained, and very recently, we synthesized a rare aliphatic ligand-stabilized gold nanocluster with an fcc structure by similar protocols except that acetic acid was replaced by nitric acid in the reaction, indicating that these synthesis protocols are not exclusive and can be developed to a method (tentatively dubbed acid-induction synthesis method) for synthesizing novel nanoclusters that are otherwise difficult to obtain. Herein, acetic acid could also be replaced by other acids (nitric acid, hydrochloric acid, *etc.*), however, it showed better reproducibility compared with the other investigated acids in this work. Acetic acid played at least two roles: on one hand, acetic acid increased the hydrolysis of  $\text{NaBH}_4$  and strengthened the reduction of  $\text{NaBH}_4$ ;<sup>7</sup> on the other hand, it could weaken the interaction between Au and thiolate, reducing the reactivity of thiolate. Thus, the attack of acid probably influenced the kinetics and thermodynamics of the formation of nanocluster products<sup>8</sup> similar to that in a previous work reported by Xie *et al.*<sup>9</sup> who added a base instead to alter the reaction kinetics and thermodynamics. The growth of gold nanoclusters in the reaction was allowed to proceed for 2 h for enhancement in size.<sup>10</sup> The crude product was collected and thoroughly washed with methanol, and  $\text{Au}_{42}(\text{TBBT})_{26}$  nanoclusters were separated by preparative thin-layer chromatography (PTLC).<sup>3f,11</sup>

The precise composition of the  $\text{Au}_{42}(\text{TBBT})_{26}$  nanocluster was determined by electrospray ionization mass spectrometry (ESI-MS).<sup>3g,3k,8,12</sup> To impart charges, cesium acetate ( $\text{CsOAc}$ ) was added to the nanocluster solution to form cationic cluster adducts with  $\text{Cs}^+$ . The ESI-MS spectrum showed intense peaks centered at  $m/z$  6418.44 (see Fig. S1<sup>†</sup>), corresponding to the  $[\text{Au}_{42}(\text{TBBT})_{26}\text{Cs}_2]^{2+}$  species (calculated: 6418.17 Da, deviation: 0.27 Da). Because the charge number was equal to the number of adducted  $\text{Cs}^+$  ions, the  $\text{Au}_{42}(\text{TBBT})_{26}$  nanoclusters were proposed to be charge-neutral, which is supported by the fact that no sound signals were found in the mass spectrum without the addition of  $\text{CsOAc}$  and that the counter ions were not found by SCXC. Dark rhombic single crystals were formed in a mixed solution of toluene and acetonitrile after 3 days. The total structure of  $\text{Au}_{42}(\text{TBBT})_{26}$  was resolved by SCXC. The  $\text{Au}_{42}(\text{TBBT})_{26}$  crystal structure adopts the triclinic space group P-1. Similar to its counterpart,  $\text{Au}_{44}(\text{TBBT})_{28}$ ,<sup>3p</sup>  $\text{Au}_{42}(\text{TBBT})_{26}$  has a pair of enantiomeric nanoclusters in the unit cell. The left-handed isomer was chosen to explore the details of the atom packing structure of  $\text{Au}_{42}(\text{TBBT})_{26}$  and  $\text{Au}_{44}(\text{TBBT})_{28}$ .

The total structure of  $\text{Au}_{42}(\text{TBBT})_{26}$  is shown in Fig. 1A. The kernel of  $\text{Au}_{42}(\text{TBBT})_{26}$  is composed of four cuboctahedra, which are formed by 34 gold atoms, as shown in Fig. 1B, and it is identical to the kernel of  $\text{Au}_{44}(\text{TBBT})_{28}$  (ref. 3p) (see Fig. 1E; the total structure of  $\text{Au}_{44}(\text{TBBT})_{28}$  is shown in Fig. 1D). Please note that there are some other kernel assignments on the basis of different views.<sup>3p</sup> In another view, the two kernels adopt identical FCC packing as shown in Fig. 1C and F. However, although the two gold nanoclusters have identical  $\text{Au}_{34}$  kernels and protecting thiolate (TBBT), they have different staples. To better illustrate this, we give a detailed structural interpretation of the staples' species and adsorption sites (see Fig. 2).

The kernel of  $\text{Au}_{44}(\text{TBBT})_{28}$  is protected by four  $\text{Au}_2(\text{TBBT})_3$  dimers at the top and bottom and two  $\text{Au}(\text{TBBT})_2$  monomers at the waist (Fig. 2F-I).<sup>3p</sup> In contrast, there are two  $\text{Au}_2(\text{TBBT})_3$  dimers at the top and bottom of the  $\text{Au}_{42}(\text{TBBT})_{26}$  nanocluster and four  $\text{Au}(\text{TBBT})_2$  monomers at the waist (Fig. 2B-E). Of note, there are also 12 bridging thiolates for every nanocluster (see Fig. 2D and H). In addition to quantitative differences in the staples, the surface arrangement of the staples is varied as mentioned above. In  $\text{Au}_{42}(\text{TBBT})_{26}$ , the bridging thiolates and dimeric staples anchor the  $\{100\}$  facets (Fig. 3A), and each of the monomer staples anchor each  $\{110\}$  facet (Fig. 3C), with no staples anchoring the  $\{111\}$  facet (Fig. 3B). However, in  $\text{Au}_{44}(\text{TBBT})_{28}$ , the  $\{100\}$ ,  $\{111\}$  and  $\{110\}$  facets are protected by bridging thiolates, a dimeric staple and monomeric staple, respectively (Fig. 3D-F). Please note that each  $\{111\}$  facet is protected by one dimeric staple and each  $\{100\}$  square is protected by one bridging thiolate in the magic cluster series including  $\text{Au}_{28}(\text{TBBT})_{20}$ ,  $\text{Au}_{36}(\text{TBBT})_{24}$ ,  $\text{Au}_{44}(\text{TBBT})_{28}$  and  $\text{Au}_{52}(\text{TBBT})_{32}$ .<sup>3p</sup>

The average Au-S bond length of the staples in  $\text{Au}_{42}(\text{TBBT})_{26}$  (2.31 Å) is slightly shorter than that in  $\text{Au}_{44}(\text{TBBT})_{28}$  (2.33 Å).<sup>3p</sup> The average Au-S-Au and S-Au-S bond angles of the staples in  $\text{Au}_{42}(\text{TBBT})_{26}$  (112.6° and 171.2°, respectively) are different from those in  $\text{Au}_{44}(\text{TBBT})_{28}$  (100.1° and 171.8°, respectively). Please

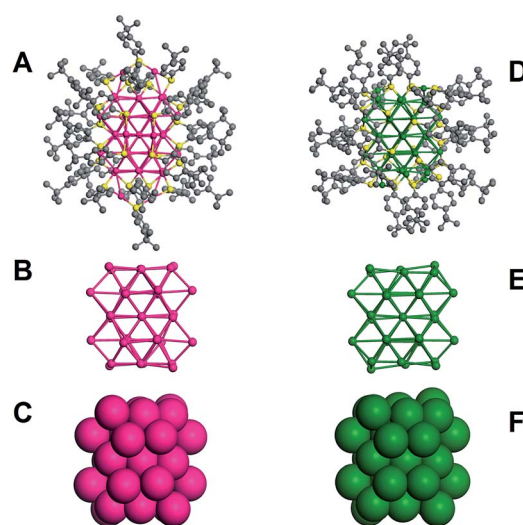


Fig. 1 Total structure and  $\text{Au}_{34}$  kernels of  $\text{Au}_{42}(\text{TBBT})_{26}$  (A–C) and  $\text{Au}_{44}(\text{TBBT})_{28}$  (D–F).



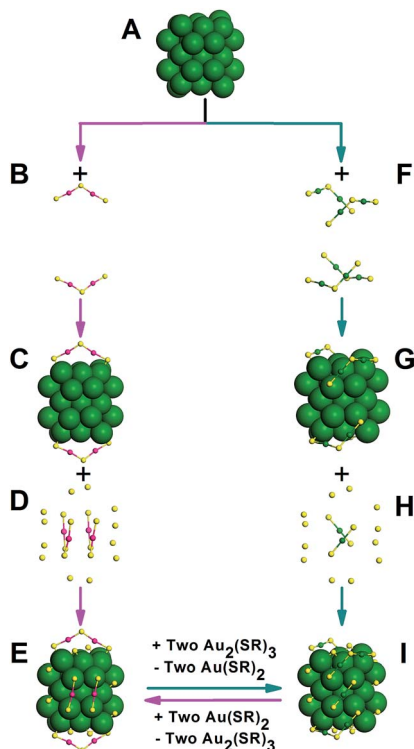


Fig. 2 Surface staples comparison of  $\text{Au}_{42}(\text{TBBT})_{26}$  and  $\text{Au}_{44}(\text{TBBT})_{28}$ :  $\text{Au}_{34}$  kernel (A); illustrating the anatomy of two  $\text{Au}_2(\text{TBBT})_3$ , four  $\text{Au}(\text{TBBT})_2$  and 12 TBBT capped on the kernel of  $\text{Au}_{42}(\text{TBBT})_{26}$  (from B to E); illustrating the anatomy of four  $\text{Au}_2(\text{TBBT})_3$ , two  $\text{Au}(\text{TBBT})_2$  and 12 TBBT capped on the kernel of  $\text{Au}_{44}(\text{TBBT})_{28}$  (from F to I). For clarity, C and H are omitted. Color labels: yellow = S; others = Au.

note that the bridging thioliates are not considered in the above comparisons.

Based on the above discussion,  $\text{Au}_{42}(\text{TBBT})_{26}$  has an identical  $\text{Au}_{34}$  kernel but different staples, which indicates that the kernel–staples match is not a key–lock match and that the homo–ligand–homo–kernel–hetero–staples phenomenon exists in metal nanoclusters, which has not been previously reported to the best of our knowledge. Of note, it is known that the hetero–ligand–homo–kernel–hetero–stapled metal nanoclusters have been known for some time.<sup>3f,12b,13</sup> The search for the homo–ligand–homo–kernel–hetero–staples phenomenon in metal nanoclusters indicates that the protecting staples on the kernel have some flexibility, which may provide some reference for understanding the growth or transformation of metal nanoclusters.<sup>6</sup> The pair of homo–ligand–homo–kernel–hetero–stapled nanoclusters  $\text{Au}_{42}(\text{TBBT})_{26}$  and  $\text{Au}_{44}(\text{TBBT})_{28}$  is ideal materials to investigate the influence that the staples have on nanocluster properties without interferences from some other factors (*e.g.* ligands). As discussed above, it is believed that the staples protect the kernels from aggregation or decomposition. This is indeed indicated by our stability experiments, which reveal that  $\text{Au}_{44}(\text{TBBT})_{28}$  in toluene is stable for at least 72 hours under 80 °C monitored by UV/vis/NIR spectrometry, whereas the less–stapled  $\text{Au}_{42}(\text{TBBT})_{26}$  is not stable for even 10 min under similar conditions (see Fig. 4). It is worth noting that there are some

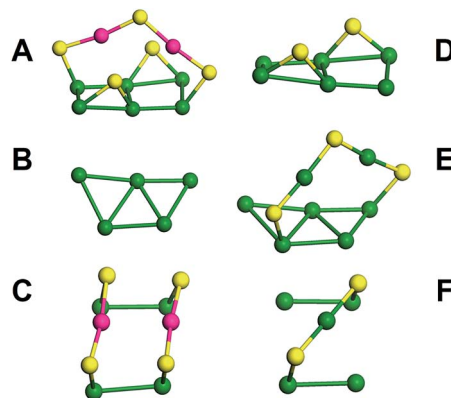


Fig. 3 Staples and bridging thioliates on the crystalline facets of  $\text{Au}_{42}(\text{TBBT})_{26}$  and  $\text{Au}_{44}(\text{TBBT})_{28}$ ; bridging thioliates, a dimeric staple and monomeric staple on the {100}, {111} and {110} facets of  $\text{Au}_{42}(\text{TBBT})_{26}$ , respectively (A, B and C); bridging thioliates, a dimeric staple and monomeric staple on the {100}, {111} and {110} facets of  $\text{Au}_{44}(\text{TBBT})_{28}$ , respectively (D, E, and F). Color labels: yellow = S; others = Au.

other perspectives to interpret the stability of metal nanoclusters.<sup>2a,14</sup>

Photoluminescence is an intriguing phenomenon, and the photoluminescence of gold/silver nanoclusters has recently received increasing attention not only for fundamental scientific research but also for practical applications in a large range of fields such as sensors<sup>2i,2l,15</sup> and biomedicine.<sup>2d,15f,16</sup> For fundamental scientific research, studies on the photoluminescence mechanism of gold/silver nanoclusters are of major importance, and there have been some pre-eminent contributions from different groups. For instance, Murray's group<sup>17</sup> found that the luminescence intensity of  $\text{Au}_{25}(\text{SR})_{18}$  increases linearly with the increasing number of polar ligands on the nanoclusters. Additionally, Wu and Jin<sup>18</sup> suggested that surface ligands can influence the photoluminescence by charge transfer and direct delocalized electron donation. Moreover, Xie *et al.*<sup>19</sup> found that aggregation-induced emission (AIE) also exists in gold nanoclusters, and Lee's group<sup>20</sup> revealed that the rigidity of the Au(I)–thiolate shell (staple) is beneficial to the emission of gold nanoclusters. Recently, our group<sup>16g</sup> discovered that both interlocked  $\text{Au}_4(\text{SR})_5$  staples and strengthened interactions between the kernel and the thioliates contribute to the enhanced photoluminescence of  $\text{Au}_{24}(\text{SR})_{20}$  nanoclusters. Even more recently, theoretical calculations conducted by Aikens and colleagues showed that the photoluminescence of

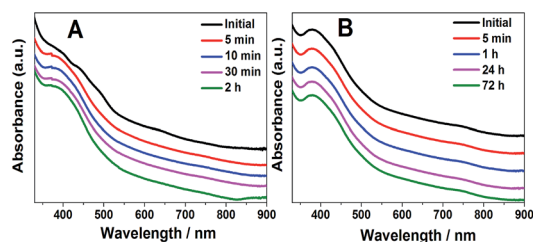


Fig. 4 Thermostability of  $\text{Au}_{42}(\text{TBBT})_{26}$  (A) and  $\text{Au}_{44}(\text{TBBT})_{28}$  (B).



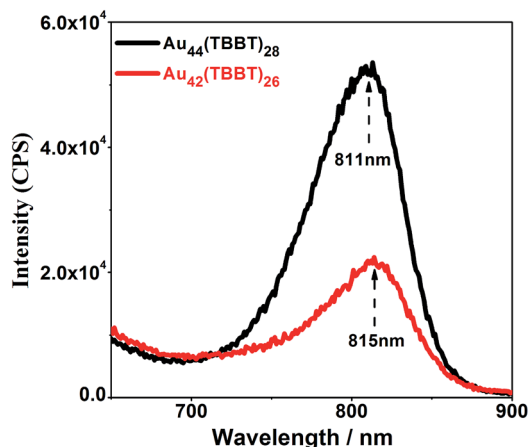


Fig. 5 Photoluminescence spectra of  $\text{Au}_{44}(\text{TBBT})_{28}$  and  $\text{Au}_{42}(\text{TBBT})_{26}$ .

gaseous  $\text{Au}_{25}(\text{SR})_{18}^-$  originates from kernel-based electron transitions rather than charge-transfer or semi-ring states.<sup>21</sup> Despite these distinguished contributions, the understanding of the photoluminescence mechanism of gold/silver nanoclusters is far from complete, and a major puzzle lies in the real roles of the kernel and staples in emission. This issue is challenging because the kernels and staples cannot be isolated and investigated separately. Thus, the finding of homo-ligand-homo-kernel-hetero-stapled gold nanoclusters might provide an opportunity to understand this issue. Although homo-kernelled,  $\text{Au}_{42}(\text{TBBT})_{26}$  and  $\text{Au}_{44}(\text{TBBT})_{28}$  (ref. 3p) have only slight difference in staples and show big difference in emission intensities: the more-stapled  $\text{Au}_{44}(\text{TBBT})_{28}$  exhibits  $\sim 2$  times stronger photoluminescence than the less-stapled  $\text{Au}_{42}(\text{TBBT})_{26}$  (see Fig. 5), indicating that the staples greatly contribute to the photoluminescence intensity of metal nanoclusters, which is also supported by the previous observations that ligands<sup>12e,18</sup> and solvents<sup>3f</sup> have important influence on the photoluminescence intensities of metal nanoclusters. The two nanoclusters have different excitation spectra, however, they have a close maximum excitation wavelength at  $\sim 470$  nm (Fig. S2†). They have also similar emission profiles when excited at 514 nm although their emission intensities are pre-eminently different (Fig. 5). In addition, the photoluminescence lifetimes of  $\text{Au}_{44}(\text{TBBT})_{28}$  (15.59 ns (15.23%) and 71.99 ns (84.77%)) are close to those of  $\text{Au}_{42}(\text{TBBT})_{26}$  (14.96 ns (13.10%) and 89.00 ns (86.90%)) (see Fig. S3†). Taken together, these results indicate that the two nanoclusters have a similar photoluminescence mechanism. Please note that a high  $\text{Au}(\text{I})/\text{Au}(\text{0})$  ratio in the nanoclusters cannot be the cause of stronger photoluminescence observed in our research because  $\text{Au}_{42}(\text{TBBT})_{26}$  has a higher  $\text{Au}(\text{I})/\text{Au}(\text{0})$  ratio than  $\text{Au}_{44}(\text{TBBT})_{28}$  (see Fig. S4†) but less photoluminescence intensity than that of  $\text{Au}_{44}(\text{TBBT})_{28}$ .<sup>19</sup>

## Conclusions

In summary, an acid-induction method was developed to synthesize a novel gold nanocluster  $\text{Au}_{42}(\text{TBBT})_{26}$  whose

composition was determined by using ESI-MS and SCXC and whose structure was resolved by SCXC. The as-obtained gold nanocluster had an identical  $\text{Au}_{34}$  kernel but reduced staples compared with those of the existing  $\text{Au}_{44}(\text{TBBT})_{28}$  nanocluster, indicating that the kernel-staples match was not a key-lock match and the existence of homo-ligand-homo-kernel-hetero-staples phenomenon in metal nanoclusters. The two Au-SR units' reduction led to a decreased stability of  $\text{Au}_{42}(\text{TBBT})_{26}$  compared with that of  $\text{Au}_{44}(\text{TBBT})_{28}$ , thus experimentally confirming the importance of the staples in protecting the kernels of metal nanoclusters from aggregation or decomposition. Furthermore, the reduced staples resulted in a photoluminescence decrease by  $\sim 2$  times, indicating that the staples greatly influenced the photoluminescence intensity of metal nanoclusters. The novelty and significance of this work lie in the following: (i) an acid-induction method was developed to synthesize a novel gold nanocluster  $\text{Au}_{42}(\text{TBBT})_{26}$ ; (ii) the structure of  $\text{Au}_{42}(\text{TBBT})_{26}$  was resolved by SCXC; (iii) the structure comparison between  $\text{Au}_{44}(\text{TBBT})_{28}$  and  $\text{Au}_{42}(\text{TBBT})_{26}$  indicated the existence of homo-ligand-homo-kernel-hetero-staples phenomenon in metal nanoclusters and that the kernel-staples match is not a key-lock match, which might have some important implication for understanding the growth or transformation of metal nanoclusters; (iv) it experimentally confirmed that the staples stabilize the gold nanoclusters; and (v) it was first unambiguously demonstrated that the staples greatly influence the photoluminescence intensity without interferences from other factors (*e.g.* ligands), which may have important implications on the understanding of the photoluminescence mechanism of metal nanoclusters. It is expected that our work will trigger more studies on the synthesis, structures and properties of metal nanoclusters and have important implications on understanding the kernel-staples interaction, staples-properties correlation and growth (or transformation) mechanism of metal nanoparticles.

## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

The authors would like to thank the National Natural Science Foundation of China (no. 21222301, 21528303, 21603234, 21771186, 21171170, 21501182 and 21601193), and the CAS/SAFEA International Partnership Program for Creative Research Teams for financial support.

## Notes and references

- (a) M.-C. Daniel and D. Astruc, *Chem. Rev.*, 2004, **104**, 293–346; (b) N. L. Rosi and C. A. Mirkin, *Chem. Rev.*, 2005, **105**, 1547–1562; (c) G. Schmid, *Chem. Soc. Rev.*, 2008, **37**, 1909–1930; (d) A. R. Tao, S. Habas and P. Yang, *Small*, 2008, **4**, 310–325.
- (a) M. Walter, J. Akola, O. Lopez-Acevedo, P. D. Jadzinsky, G. Calero, C. J. Ackerson, R. L. Whetten, H. Gronbeck and



- H. Hakkinen, *Proc. Natl. Acad. Sci. U. S. A.*, 2008, **105**, 9157–9162; (b) R. Jin, *Nanoscale*, 2010, **2**, 343–362; (c) J. F. Parker, C. A. Fields-Zinna and R. W. Murray, *Acc. Chem. Res.*, 2010, **43**, 1289–1296; (d) S. Choi, R. M. Dickson and J. Yu, *Chem. Soc. Rev.*, 2012, **41**, 1867–1891; (e) Y. Lu and W. Chen, *Chem. Soc. Rev.*, 2012, **41**, 3594–3623; (f) G. Li and R. Jin, *Acc. Chem. Res.*, 2013, **46**, 1749–1758; (g) T. Dainese, S. Antonello, J. A. Gascón, F. Pan, N. V. Perera, M. Ruzzi, A. Venzo, A. Zoleo, K. Rissanen and F. Maran, *ACS Nano*, 2014, **8**, 3904–3912; (h) S. Knoppe and T. Bürgi, *Acc. Chem. Res.*, 2014, **47**, 1318–1326; (i) A. Mathew and T. Pradeep, *Part. Part. Syst. Charact.*, 2014, **31**, 1017–1053; (j) S. Yamazoe, K. Koyasu and T. Tsukuda, *Acc. Chem. Res.*, 2014, **47**, 816–824; (k) Y. Wang, H. Su, C. Xu, G. Li, L. Gell, S. Lin, Z. Tang, H. Häkkinen and N. Zheng, *J. Am. Chem. Soc.*, 2015, **137**, 4324–4327; (l) N. Xia, J. Yang and Z. Wu, *Nanoscale*, 2015, **7**, 10013–10020; (m) M.-B. Li, S.-K. Tian, Z. Wu and R. Jin, *Chem. Mater.*, 2016, **28**, 1022–1025; (n) M. A. Tofanelli, K. Salorinne, T. W. Ni, S. Malola, B. Newell, B. Phillips, H. Hakkinen and C. J. Ackerson, *Chem. Sci.*, 2016, **7**, 1882–1890; (o) N. Yan, L. Liao, J. Yuan, Y.-j. Lin, L.-h. Weng, J. Yang and Z. Wu, *Chem. Mater.*, 2016, **28**, 8240–8247; (p) X.-K. Wan, J.-Q. Wang, Z.-A. Nan and Q.-M. Wang, *Sci. Adv.*, 2017, **3**, e1701823.
- 3 (a) P. D. Jadzinsky, G. Calero, C. J. Ackerson, D. A. Bushnell and R. D. Kornberg, *Science*, 2007, **318**, 430–433; (b) M. W. Heaven, A. Dass, P. S. White, K. M. Holt and R. W. Murray, *J. Am. Chem. Soc.*, 2008, **130**, 3754–3755; (c) M. Zhu, C. M. Aikens, F. J. Hollander, G. C. Schatz and R. Jin, *J. Am. Chem. Soc.*, 2008, **130**, 5883–5885; (d) G. Li, Z. Lei and Q.-M. Wang, *J. Am. Chem. Soc.*, 2010, **132**, 17678–17679; (e) C. Zeng, H. Qian, T. Li, G. Li, N. L. Rosi, B. Yoon, R. N. Barnett, R. L. Whetten, U. Landman and R. Jin, *Angew. Chem., Int. Ed.*, 2012, **51**, 13114–13118; (f) A. Desireddy, B. E. Conn, J. Guo, B. Yoon, R. N. Barnett, B. M. Monahan, K. Kirschbaum, W. P. Griffith, R. L. Whetten, U. Landman and T. P. Bigioni, *Nature*, 2013, **501**, 399–402; (g) D. Crasto, S. Malola, G. Brosofsky, A. Dass and H. Hakkinen, *J. Am. Chem. Soc.*, 2014, **136**, 5000–5005; (h) X.-K. Wan, S.-F. Yuan, Z.-W. Lin and Q.-M. Wang, *Angew. Chem., Int. Ed.*, 2014, **53**, 2923–2926; (i) C. P. Joshi, M. S. Bootharaju, M. J. Alhilaly and O. M. Bakr, *J. Am. Chem. Soc.*, 2015, **137**, 11578–11581; (j) S. B. Tian, Y. Z. Li, M. B. Li, J. Y. Yuan, J. L. Yang, Z. K. Wu and R. C. Jin, *Nat. Commun.*, 2015, **6**, 8667; (k) X.-K. Wan, Q. Tang, S.-F. Yuan, D.-e. Jiang and Q.-M. Wang, *J. Am. Chem. Soc.*, 2015, **137**, 652–655; (l) C. Zeng, Y. Chen, K. Kirschbaum, K. Appavoo, M. Y. Sfeir and R. Jin, *Sci. Adv.*, 2015, **1**, e1500045; (m) M. J. Alhilaly, M. S. Bootharaju, C. P. Joshi, T. M. Besong, A.-H. Emwas, R. Juarez-Mosqueda, S. Kaappa, S. Malola, K. Adil, A. Shkurenko, H. Häkkinen, M. Eddaoudi and O. M. Bakr, *J. Am. Chem. Soc.*, 2016, **138**, 14727–14732; (n) L. Liao, S. Zhuang, C. Yao, N. Yan, J. Chen, C. Wang, N. Xia, X. Liu, M. B. Li, L. Li, X. Bao and Z. Wu, *J. Am. Chem. Soc.*, 2016, **138**, 10425–10428; (o) H. Yang, Y. Wang, X. Chen, X. Zhao, L. Gu, H. Huang, J. Yan, C. Xu, G. Li, J. Wu, A. J. Edwards, B. Dittrich, Z. Tang, D. Wang, L. Lehtovaara, H. Häkkinen and N. Zheng, *Nat. Commun.*, 2016, **7**, 12809; (p) C. Zeng, Y. Chen, K. Iida, K. Nobusada, K. Kirschbaum, K. J. Lambright and R. Jin, *J. Am. Chem. Soc.*, 2016, **138**, 3950–3953; (q) J.-L. Zeng, Z.-J. Guan, Y. Du, Z.-A. Nan, Y.-M. Lin and Q.-M. Wang, *J. Am. Chem. Soc.*, 2016, **138**, 7848–7851; (r) T. Chen, S. Yang, J. Chai, Y. Song, J. Fan, B. Rao, H. Sheng, H. Yu and M. Zhu, *Sci. Adv.*, 2017, **3**, e1700956; (s) H. Dong, L. Liao, S. Zhuang, C. Yao, J. Chen, S. Tian, M. Zhu, X. Liu, L. Li and Z. Wu, *Nanoscale*, 2017, **9**, 3742–3746; (t) Z. Gan, J. Chen, J. Wang, C. Wang, M.-B. Li, C. Yao, S. Zhuang, A. Xu, L. Li and Z. Wu, *Nat. Commun.*, 2017, **8**, 14739; (u) L. Liao, S. Zhuang, P. Wang, Y. Xu, N. Yan, H. Dong, C. Wang, Y. Zhao, N. Xia, J. Li, H. Deng, Y. Pei, S.-K. Tian and Z. Wu, *Angew. Chem., Int. Ed.*, 2017, **56**, 12644–12648; (v) S. Zhuang, L. Liao, M.-B. Li, C. Yao, Y. Zhao, H. Dong, J. Li, H. Deng, L. Li and Z. Wu, *Nanoscale*, 2017, **9**, 14809–14813.
- 4 Y. Pei, Y. Gao, N. Shao and X. C. Zeng, *J. Am. Chem. Soc.*, 2009, **131**, 13619–13621.
- 5 (a) D.-e. Jiang, M. L. Tiago, W. Luo and S. Dai, *J. Am. Chem. Soc.*, 2008, **130**, 2777–2779; (b) S. Yamazoe, S. Takano, W. Kurashige, T. Yokoyama, K. Nitta, Y. Negishi and T. Tsukuda, *Nat. Commun.*, 2016, **7**, 10414.
- 6 Q. Yao, X. Yuan, V. Fung, Y. Yu, D. T. Leong, D. E. Jiang and J. Xie, *Nat. Commun.*, 2017, **8**, 927.
- 7 M. M. Kreevoy and J. E. C. Hutchins, *J. Am. Chem. Soc.*, 1972, **94**, 6371–6376.
- 8 Z. Wu, M. A. MacDonald, J. Chen, P. Zhang and R. Jin, *J. Am. Chem. Soc.*, 2011, **133**, 9670–9673.
- 9 X. Yuan, B. Zhang, Z. Luo, Q. Yao, D. T. Leong, N. Yan and J. Xie, *Angew. Chem., Int. Ed.*, 2014, **53**, 4623–4627.
- 10 Z. Wu, J. Suhan and R. Jin, *J. Mater. Chem.*, 2009, **19**, 622–626.
- 11 (a) S. Tian, C. Yao, L. Liao, N. Xia and Z. Wu, *Chem. Commun.*, 2015, **51**, 11773–11776; (b) C. Yao, J. Chen, M.-B. Li, L. Liu, J. Yang and Z. Wu, *Nano Lett.*, 2015, **15**, 1281–1287; (c) C. Yao, S. Tian, L. Liao, X. Liu, N. Xia, N. Yan, Z. Gan and Z. Wu, *Nanoscale*, 2015, **7**, 16200–16203; (d) L. Liao, C. Yao, C. Wang, S. Tian, J. Chen, M.-B. Li, N. Xia, N. Yan and Z. Wu, *Anal. Chem.*, 2016, **88**, 11297–11301.
- 12 (a) Y. Negishi, K. Nobusada and T. Tsukuda, *J. Am. Chem. Soc.*, 2005, **127**, 5261–5270; (b) K. M. Harkness, Y. Tang, A. Dass, J. Pan, N. Kothalawala, V. J. Reddy, D. E. Cliffler, B. Demeler, F. Stellacci, O. M. Bakr and J. A. McLean, *Nanoscale*, 2012, **4**, 4269–4274; (c) Y. Yu, Z. Luo, D. M. Chevrier, D. T. Leong, P. Zhang, D.-e. Jiang and J. Xie, *J. Am. Chem. Soc.*, 2014, **136**, 1246–1249; (d) Y. Chen, C. Zeng, D. R. Kauffman and R. Jin, *Nano Lett.*, 2015, **15**, 3603–3609; (e) A. Dass, S. Thevendran, P. R. Nimmala, C. Kumara, V. R. Jupally, A. Fortunelli, L. Sementa, G. Barcaro, X. Zuo and B. C. Noll, *J. Am. Chem. Soc.*, 2015, **137**, 4610–4613; (f) X.-K. Wan, S.-F. Yuan, Q. Tang, D.-e. Jiang and Q.-M. Wang, *Angew. Chem., Int. Ed.*, 2015, **54**, 5977–5980; (g) M. S. Bootharaju, C. P. Joshi, M. R. Parida, O. F. Mohammed and O. M. Bakr, *Angew. Chem., Int. Ed.*, 2016, **55**, 922–926; (h) C. Zeng, Y. Chen,



- K. Kirschbaum, K. J. Lambright and R. Jin, *Science*, 2016, **354**, 1580–1584; (i) M. A. Aljuhani, M. S. Bootharaju, L. Sinatra, J. M. Basset, O. F. Mohammed and O. M. Bakr, *J. Phys. Chem. C*, 2017, **121**, 10681–10685.
- 13 (a) H. Yang, Y. Wang, H. Huang, L. Gell, L. Lehtovaara, S. Malola, H. Häkkinen and N. Zheng, *Nat. Commun.*, 2013, **4**, 2422; (b) Y. Chen, C. Liu, Q. Tang, C. Zeng, T. Higaki, A. Das, D. E. Jiang, N. L. Rosi and R. Jin, *J. Am. Chem. Soc.*, 2016, **138**, 1482–1485; (c) W. Du, S. Jin, L. Xiong, M. Chen, J. Zhang, X. Zou, Y. Pei, S. Wang and M. Zhu, *J. Am. Chem. Soc.*, 2017, **139**, 1618–1624.
- 14 (a) Y. Pei, Y. Gao and X. C. Zeng, *J. Am. Chem. Soc.*, 2008, **130**, 7830–7832; (b) Z. K. Wu and R. C. Jin, *Chem.–Eur. J.*, 2011, **17**, 13966–13970.
- 15 (a) W. Guo, J. Yuan and E. Wang, *Chem. Commun.*, 2009, 3395–3397, DOI: 10.1039/B821518A; (b) Y. Liu, K. Ai, X. Cheng, L. Huo and L. Lu, *Adv. Funct. Mater.*, 2010, **20**, 951–956; (c) S. W. Yang and T. Vosch, *Anal. Chem.*, 2011, **83**, 6935–6939; (d) M. Wang, Z. Wu, J. Yang, G. Wang, H. Wang and W. Cai, *Nanoscale*, 2012, **4**, 4087–4090; (e) X. Yuan, Z. Luo, Y. Yu, Q. Yao and J. Xie, *Chem.–Asian J.*, 2013, **8**, 858–871; (f) L. Zhang and E. Wang, *Nano Today*, 2014, **9**, 132–157.
- 16 (a) C.-A. J. Lin, T.-Y. Yang, C.-H. Lee, S. H. Huang, R. A. Sperling, M. Zanella, J. K. Li, J.-L. Shen, H.-H. Wang, H.-I. Yeh, W. J. Parak and W. H. Chang, *ACS Nano*, 2009, **3**, 395–401; (b) M. A. H. Muhammed, P. K. Verma, S. K. Pal, R. C. A. Kumar, S. Paul, R. V. Omkumar and T. Pradeep, *Chem.–Eur. J.*, 2009, **15**, 10110–10120; (c) L. Shang, S. Dong and G. U. Nienhaus, *Nano Today*, 2011, **6**, 401–418; (d) L. Zhang, J. Zhu, Z. Zhou, S. Guo, J. Li, S. Dong and E. Wang, *Chem. Sci.*, 2013, **4**, 4004–4010; (e) Z. Luo, K. Zheng and J. Xie, *Chem. Commun.*, 2014, **50**, 5143–5155; (f) X. Zhang, F.-G. Wu, P. Liu, N. Gu and Z. Chen, *Small*, 2014, **10**, 5170–5177; (g) Z. Gan, Y. Lin, L. Luo, G. Han, W. Liu, Z. Liu, C. Yao, L. Weng, L. Liao, J. Chen, X. Liu, Y. Luo, C. Wang, S. Wei and Z. Wu, *Angew. Chem., Int. Ed.*, 2016, **55**, 11567–11571; (h) J. Yang, N. Xia, X. Wang, X. Liu, A. Xu, Z. Wu and Z. Luo, *Nanoscale*, 2016, **8**, 13078.
- 17 D. Lee, R. L. Donkers, G. Wang, A. S. Harper and R. W. Murray, *J. Am. Chem. Soc.*, 2004, **126**, 6193–6199.
- 18 Z. Wu and R. Jin, *Nano Lett.*, 2010, **10**, 2568–2573.
- 19 Z. Luo, X. Yuan, Y. Yu, Q. Zhang, D. T. Leong, J. Y. Lee and J. Xie, *J. Am. Chem. Soc.*, 2012, **134**, 16662–16670.
- 20 K. Pyo, V. D. Thanthirige, K. Kwak, P. Pandurangan, G. Ramakrishna and D. Lee, *J. Am. Chem. Soc.*, 2015, **137**, 8244–8250.
- 21 K. L. Weerawardene and C. M. Aikens, *J. Am. Chem. Soc.*, 2016, **138**, 11202–11210.

