

Cite this: *Nanoscale Adv.*, 2019, 1, 4669Received 20th August 2019
Accepted 12th October 2019

DOI: 10.1039/c9na00521h

rsc.li/nanoscale-advances

Engineering doping-vacancy double defects and insights into the conversion mechanisms of an Mn–O–F ultrafine nanowire anode for enhanced Li/Na-ion storage and hybrid capacitors†

Yongfa Huang, Rui Ding,[✉]* Danfeng Ying, Wei Shi, Yuxi Huang, Caini Tan, Xiujuan Sun, Ping Gao and Enhui Liu

The behavior of Li/Na-ion capacitors (LICs/NICs) is largely limited by the low number of electroactive sites in conventional insertion-type anodes. In this work, we demonstrated a novel doping-vacancy double-defective and conversion-type Mn–O–F ultrafine nanowire (denoted as MnF₂-E) anode to boost the number of electroactive sites for enhanced LICs/NICs. Owing to the unique hetero oxygen-doping and intrinsic fluorine-vacancy double defects, the Mn–O–F nanowires exhibited superior electroactive sites and thus dramatically enhanced Li/Na-ion storage capability than pristine MnF₂ micro/nanocrystals. Both the optimal MnF₂ screened by orthogonal experiments and derived Mn–O–F anodes and commercial activated carbon (AC) cathode were used to construct MnF₂//AC and MnF₂-E//AC LICs/NICs, which were optimized by tuning the active mass ratios of the cathode/anode and the working voltage windows of the hybrid capacitors. The LICs/NICs based on the Mn–O–F anode demonstrated a considerably superior performance than the devices based on the MnF₂ anode under the optimal voltages of 0–4 V and 0–4.3 V. The Mn–O–F anode exhibited dominant diffusion/surface-controlled kinetics for Li/Na-ion storage, respectively, showing a major conversion mechanism for the charge storage processes. This work provides a new concept of double-defective and conversion-type electrode materials to improve the Li/Na-ion storage capability and will have a significant impact on the relevant fields.

Introduction

Energy is increasingly inseparable from human life with the development of society; however, the disadvantages of the depletion of fossil fuel resources and environmental pollution limit their applications. Thus, electrochemical energy storage has become one of the most important strategies to solve these

issues.¹ Electrochemical energy storage, which is necessary for future large-scale power grids, is sustainable, green and responsive and can be used in electrochemical engines and smart devices.² Electrochemical capacitors (ECs) or supercapacitors (SCs) as an important part of electrochemical energy storage have attracted wide interest from researchers,³ especially lithium-ion capacitors (LICs)^{4,5} and sodium-ion capacitors (NICs).^{6,7} Furthermore, non-aqueous hybrid ion capacitors^{8,9} usually show a higher working voltage, larger energy density and wider temperature scope than aqueous hybrid ion capacitors.¹⁰

LIC was proposed by Amatucci's team in 2001.^{11,12} It uses a battery-type material as the negative electrode with high energy density and an electric double layer (EDL) carbon material as the positive electrode with high power density; thus, LICs can export high energy and power density simultaneously. However, the performance of LICs is largely limited by anode materials, which have low electrochemical activity. Thus, finding new anodes with high electroactive sites has become an important research direction. Various advanced materials such as Nb₂O₅,¹³ MnO,¹⁴ and BiVO₄¹⁵ have been reported as intriguing anodes for LICs.

Nowadays, the depletion of lithium resources has caused widespread concern and more seriously, the development of lithium resources cannot keep up with the development of lithium-ion energy storage devices.¹⁶ Therefore, it is very important to find electrochemical energy storage devices with low cost, high safety, high energy/power densities and long cycle stability. It is particularly attractive to develop other ion energy storage devices for this purpose. Sodium (Na) ions are highly abundant and low cost in nature and have received great attention from researchers as alternatives to lithium ions.¹⁷ Sodium ion capacitors (NICs) also have the advantages of sodium ion batteries of high energy density and EDL capacitors of high power density. Some NICs even exhibit the same performance as LICs, such as Nb₂O₅@C/reduced graphene oxide (rGO),¹⁸ TiO₂/C,¹⁹ N-TiO₂,²⁰ 3D framework carbon (3DFC),²¹ peanut skin-derived carbon nanosheets-A (SCN-A).²²

Key Laboratory of Environmentally Friendly Chemistry and Applications of Ministry of Education, College of Chemistry, Xiangtan University, Xiangtan, Hunan 411105, P. R. China. E-mail: drms122@163.com; drms122@xtu.edu.cn

† Electronic supplementary information (ESI) available. See DOI: 10.1039/c9na00521h



balance. The Mn 2p spectra of MnF₂ 8# and MnF₂ 8#-E are shown in Fig. 1D, where Mn 2p_{3/2} and Mn 2p_{1/2} are negatively shifted by 0.6 eV and 1.7 eV compared with the Mn 2p spectra of MnF₂ 8#, respectively, which is due to the formation of the Mn–O bond by oxygen doping. The F 1s spectrum of MnF₂ 8#-E in Fig. 1E is significantly lower than that of MnF₂ 8#, accompanied by a negative shift of 0.8 eV for MnF₂ 8#-E, which is due to the hetero oxygen doping and fluorine ion vacancy. Fig. 1F shows the O 1s spectra, where the O 1s peak of MnF₂ 8#-E exhibits a negative shift of 1.8 eV compared to that of MnF₂ 8#, which is due to the formation of a strong Mn–O bond by the hetero oxygen doping. Moreover, the ratio of Mn/O/F was estimated to be 1 : 0.934/0.132 based on the XPS results, and thus the formula of Mn–O–F can be expressed as MnO_{0.934}F_{0.132}. Herein, the doping of oxygen heteroatoms and fluorine vacancy double defects gave Mn–O–F a distinct advantage in electrochemical performance.

The SEM and TEM images of MnF₂ 8# are shown in Fig. 2A and B, respectively, showing a size range of around 0.5–2 μm. The HRTEM image of MnF₂ 8# in Fig. 2C shows the lattice fringes of 0.345 nm, which is matched with the (110) crystal plane of tetragonal MnF₂. The SAED patterns in Fig. 2D exhibit the single-crystalline diffraction characteristics of MnF₂ 8# with the marked standard crystalline planes of (110), which are in


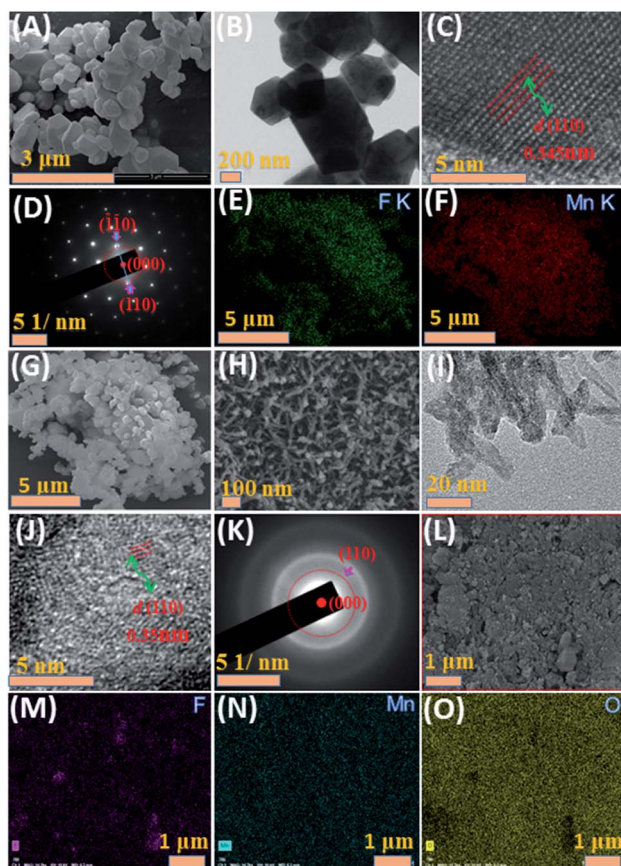


Fig. 2 SEM (A), TEM (B), HRTEM (C), SAED (D) and mapping (E–G) images of MnF₂ 8# sample. SEM (H), TEM (I), HRTEM (J), SAED (K) and mapping (L–O) images of MnF₂ 8#-E sample.

good agreement with the HRTEM and XRD results. Furthermore, the mapping images of MnF₂ 8# in Fig. 2E–G demonstrate the uniform distributions of F/Mn species. Fig. 2H, I and S3† show the SEM/TEM images of MnF₂ 8#-E, which exhibit an ultrafine nanowire morphology with a diameter of about 10 nm, and a much more porous structure can be clearly seen for MnF₂ 8#-E (the possible formation process can be seen in Scheme 1, ESI†), which endows the MnF₂ 8#-E sample with more electroactive sites than the pristine MnF₂ 8# sample. The ultrafine nanowire morphology and porous structure also ensure a shorter ion transport length and provide a larger electrode/electrolyte interface for charge transport reactions, which is also reflected in its superior electrochemical performance.³⁰ The HRTEM image and SAED pattern of MnF₂ 8#-E are shown in Fig. 2J and K, respectively, in which a typical amorphous



Scheme 1 Schematics of the possible reaction mechanisms for the MnF₂ (A) and MnF₂-E (B) electrodes during the first two cycles of discharging/charging processes.

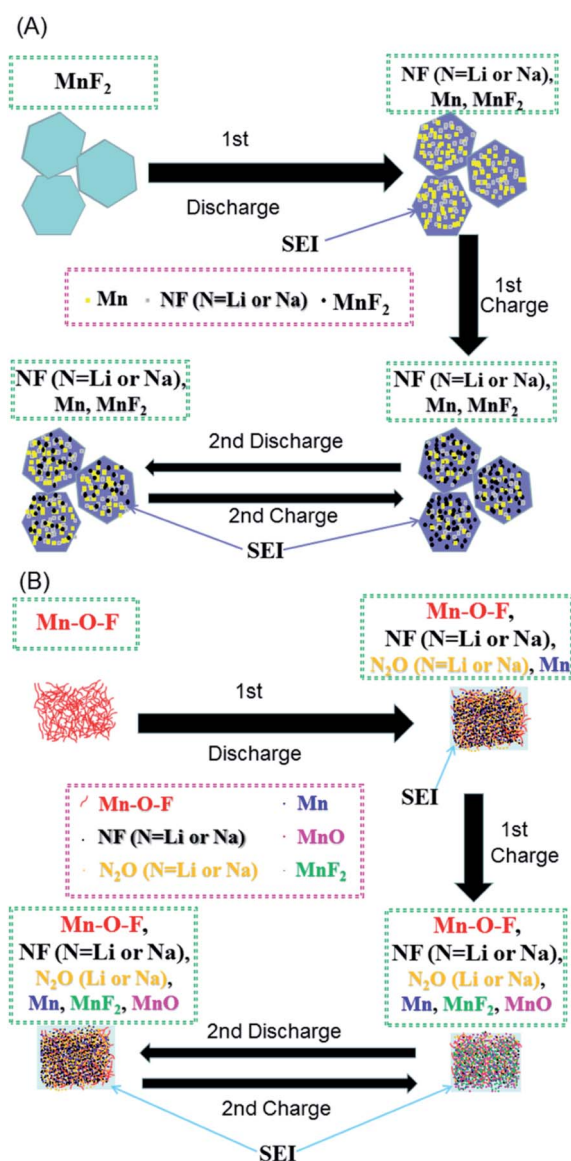

structure with a lightly larger lattice fringe of 0.35 nm corresponding to the (110) crystal plane can be detected. The mapping diagrams of MnF₂ 8#-E in Fig. 2L–O demonstrate the even distribution of Mn, O, and F elements in the MnF₂ 8#-E sample, which again prove hetero oxygen doping in the MnF₂ structure. The different colors of MnF₂ 8# and MnF₂ 8#-E in Fig. S4† and the element results from the EDS data in Fig. S5† also reflect the doping of oxygen heteroatoms and the change in the intrinsic structure of the materials. Further changes can be also seen from the nitrogen isothermal sorption data, pore volume and pore size distribution of MnF₂ 8# and MnF₂ 8#-E (Fig. 3A–F). Specifically, MnF₂ 8# has a very small specific surface area of only 2.75 m² g⁻¹, while MnF₂ 8#-E exhibits a staggering value of 198.96 m² g⁻¹, and the pore volume of MnF₂ 8# is also very small (0.008 cm³ g⁻¹) in comparison with the very large pore volume of MnF₂ 8#-E (0.95 cm³ g⁻¹), and the pore size of MnF₂ 8# is mainly distributed at 2.23 nm in comparison with the bigger pore size distribution of MnF₂ 8#-E (11.26 nm), which indicate an enormous increase in specific surface area, pore volume and pore size by the introduction of hetero oxygen doping and fluorine vacancy double defects, ensuring the exceptionally superior electrochemical performance of the double-defective Mn–O–F ultrafine nanowires for Li/Na-ion storage.

Performance for Li-ion storage

To evaluate the electrochemical performance of the MnF₂ (1#–9#) samples and select the optimal candidate from the orthogonal experiments, Li//MnF₂ half cells were assembled and

tested *via* cyclic voltammetry (CV) and galvanostatic charge/discharge (GCD) between 0.01 and 3 V (*vs.* Li/Li⁺). Based on the results of the orthogonal analysis and performance comparison in Tables S3, S4 and Fig. S6,† MnF₂ 8# exhibited an overall superior performance. The cyclic voltammogram of the first three revolutions at 0.1 mV s⁻¹ of MnF₂ 8# is shown in Fig. 4A, with one minor peak located at about 0.96 V and a sharp peak at around 0.29 V for the first cathode scan, which coincide with the platforms and the sloped regions at the low voltage appearing in the original discharge branch of the GCD curves at 0.1 A g⁻¹ (Fig. 4B), respectively. These peaks are largely owing to the conversion of MnF₂ into Mn/LiF and the formation of solid electrolyte interphase (SEI) films accompanied with a highly reversible interfacial Li-ion intercalation reaction within the Mn/LiF matrix in the low potential region, respectively.^{31–35} Also, the minor anodic peak at 1.01 V can be ascribed to the partial conversion of Mn/LiF into MnF₂.^{31,32} However, the redox peaks

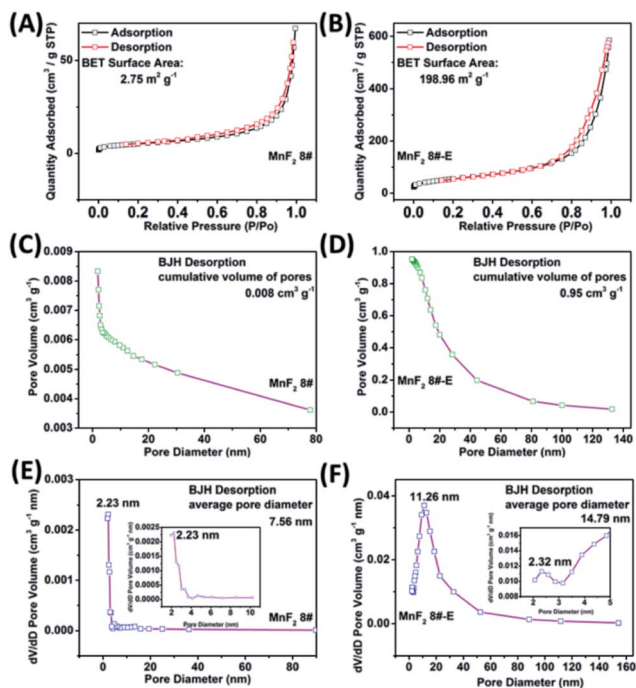


Fig. 3 N₂ isothermal sorption (A and B), pore volume (C and D) and pore size distribution (E and F) of the MnF₂ 8# and MnF₂ 8#-E samples, respectively.

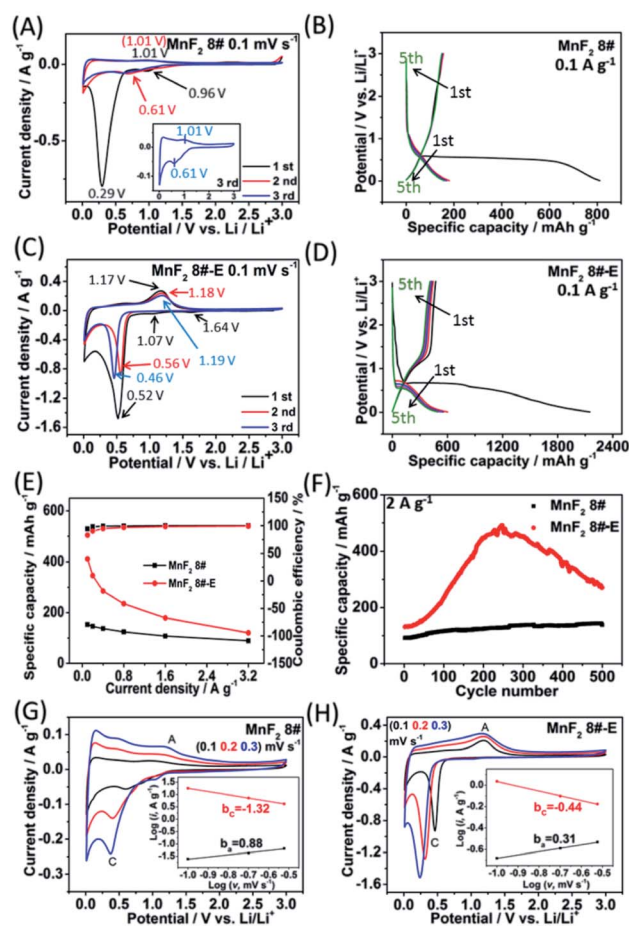


Fig. 4 CV plots for the first three cycles at 0.1 mV s⁻¹ (A) and GCD curves for the 5th cycle at 0.1 A g⁻¹ (B) of MnF₂ 8# electrode, CV plots for the first three cycles at 0.1 mV s⁻¹ (C) and GCD curves for the 5th cycle at 0.1 A g⁻¹ (D) of MnF₂ 8#-E electrode, specific capacity and coulombic efficiency derived from the respective 5th cycle at 0.1–3.2 A g⁻¹ of MnF₂ 8# and MnF₂ 8#-E electrodes (E), cycling stability for 500 cycles at 2 A g⁻¹ of MnF₂ 8# and MnF₂ 8#-E electrodes (F), and CV plots for the 3rd cycle at 0.1, 0.2, and 0.3 mV s⁻¹ of MnF₂ 8# and MnF₂ 8#-E (insets show the plots of lg *i* vs. lg *v*) (G and H).



were maintained at about 1.01/0.61 V in the subsequent cycles, and it can be seen from the charge–discharge curves that the capacity is basically unchanged in the subsequent cycles except for the much larger specific capacity of the original discharge, indicating that the internal structure is protected after the formation of the SEI films, and shows good electrochemical stability.^{31,32} Similar changing trends in the redox peaks and charge–discharge platforms can be also found from the CV curves and GCD plots of the other MnF₂ samples, as shown in Fig. S7 and S8.†

Fig. 4C shows the CV plots of MnF₂ 8#-E at a sweep speed of 0.1 mV s⁻¹, with two weak cathode peaks at 1.64 V and 1.07 V and a sharp cathode peak at 0.52 V in the first cathode sweep, which may be due to the conversion of Mn–O–F into Mn/LiF/Li₂O and the formation of the SEI films, and the minor anodic peak at 1.17 V can be ascribed to the partial conversion of Mn/LiF/Li₂O into MnF₂/MnO.^{14,31,32} In the next two cycles, the cathode peaks shifted slightly from 0.56 V to 0.46 V, and the anode peaks shifted slightly from 1.18 V to 1.19 V, indicating good reversibility. Fig. 4E and F show the specific capacity and cycle performance of the MnF₂ 8# and MnF₂ 8#-E electrodes, respectively, where MnF₂ 8#-E provided the much bigger specific capacity of 411–120 mA h g⁻¹ at 0.1–3.2 A g⁻¹ in comparison with that of 153–89 mA h g⁻¹ at 0.1–3.2 A g⁻¹ for the MnF₂ 8# electrode. The more obvious gap is also reflected in the cycle performance after 500 cycles at 2 A g⁻¹, where MnF₂ 8#-E exhibited 271 mA h g⁻¹ (207% retention), whereas MnF₂ 8# exhibited only 138 mA h g⁻¹ (152% retention). Moreover, the performance of the Mn–O–F anode is comparable or even superior to that of many state-of-the-art anode materials for Li-ion batteries (LIBs) (Table S5, ESI†) (the more detailed performance from the CV curves, GCD curves, rate capability and coulombic efficiency, cycling stability and coulombic efficiency of the MnF₂ (1#–9#) and MnF₂ 8#-E electrodes can be seen in Fig. S7–S14†). The enhanced performance of the Mn–O–F ultrafine nanowires with the hetero oxygen doping and fluorine vacancies provides an important strategy for the promotion of charge storage capability of Li-ion anode materials. Herein, the initial increase in capacity for the MnF₂ 8# and MnF₂ 8#-E electrodes may be owing to the formation of continuous conductivity networks *via* the conversion, reversible reactions of SEI films and enhanced electroactive sites by the activation of the electrode,³² while the subsequent decrease in capacity for the MnF₂ 8#-E electrode may be owing to the decrease in the electroactive sites by the agglomeration of the amorphous ultrafine nanoparticles. The XRD patterns of the electrodes after cycling (Fig. S15A and B, ESI†) demonstrate the very faint diffraction peaks of MnF₂ phase compared with the pristine states, and the TEM images of the electrodes after cycling (Fig. S15C–F, ESI†) show the presence of numerous ultrafine nanoparticles in the pristine nanocrystals or nanowires, suggesting the formation of a largely amorphous nanostructure for Li-ion storage after the long-term conversions. The CV plots at different sweep rates (0.1, 0.2, and 0.3 mV s⁻¹) of the MnF₂ 8# and MnF₂ 8#-E electrodes are shown in Fig. 4G and H, and the relationship of lg *i*–lg *v* (*i* = *av*^{*b*})³⁶ for MnF₂ 8# and MnF₂ 8#-E electrodes derived from the CV plots are shown in the insets of

Fig. 4G and H. Note that the slopes of *ba* and *bc* are 0.88 and –1.32 for MnF₂ 8#, in comparison with that of 0.31 and –0.44 for MnF₂ 8#-E, respectively. These results indicate that the kinetics of the MnF₂ 8# electrode is dominated by surface-controlled kinetics (*i.e.* pseudocapacitive behavior),³⁷ whereas the MnF₂ 8#-E electrode has the typical diffusion-controlled property. Herein, the absolute *b* values (0.31/0.44) of the MnF₂ 8#-E electrode are lower than 0.5, indicating the deviation from the typical planar diffusion characteristics, which may be owing to the highly porous and rough structure of the electrode, leading to the partial spherical diffusion. Moreover, the pseudocapacitive contribution (*k₁v*)^{36,37} at 0.1–0.3 mV s⁻¹ was estimated to be 73–82% and 31–44% for the MnF₂ 8# and MnF₂ 8#-E electrodes, respectively (Fig. S16 and S17, ESI†).

Electrochemical impedance spectroscopy (EIS) was used to investigate the electrochemical kinetics of the MnF₂ and MnF₂ 8#-E electrodes for Li-ion storage. As shown in Fig. S19,† the Nyquist plots include a *Z'*-axis intercept at the superhigh frequency, one semicircle in the high frequency region, a short sloping line in the intermediate frequency region and an oversized curved arc in the low frequency region, which are considered as the internal ohmic resistance (*R_s*) (including resistances of electrode and electrolyte, and contact resistances between particles and/or between electrode and current collector), charge transfer resistance (*R_{ct}*) related to the electrochemical kinetics process, Warburg impedance (*W*) related to the ion diffusion process and the electronic resistance related to the bulk materials, respectively.³² The equivalent circuit model is shown in Fig. S18 (ESI†), and the fitting results are listed in Table S6 (ESI†), in which the Mn–O–F electrode shows a smaller *R_{ct}* (37.33 Ω) than the MnF₂ electrodes (43.09–68.34 Ω), implying the faster electrochemical kinetics in the Mn–O–F electrode because of its superior morphology and porosity.

The MnF₂/AC and MnF₂-E//AC LICs were further assembled with MnF₂ 8# and MnF₂ 8#-E as the anodes and commercial AC as the cathode together with the anodes pre-charged (pre-lithiation) mode at 0.1 A g⁻¹ for 3.5 turns (Fig. S20†). Different active mass ratios of the cathode/anode were examined firstly. For the MnF₂/AC LICs, the performance comparison for different mass ratios in Fig. S22† makes it clear that MnF₂/AC (1 : 1) is the optimal LIC (the performance of the AC cathode is shown in Fig. S21,† and the voltage windows, GCD curves and CV plots of the MnF₂/AC LICs with different mass ratios are shown in Fig. S23 and S24†). For the MnF₂-E//AC LICs, the best mass ratio was determined to be 1 : 2 based on the results shown in Fig. S25 and S26.† After selecting the optimal mass ratios of the LICs, different voltage windows (0–4 V and 0–4.3 V) were further examined. Fig. 5A–H show the CV plots at 40 mV s⁻¹, GCD curves at 1 A g⁻¹, Ragone behavior and cycling performance at 5 A g⁻¹ of the MnF₂/AC (1 : 1) and MnF₂-E//AC (1 : 2) LICs under the voltages of 0–4 V and 0–4.3 V. The MnF₂-8#-E//AC capacitor exhibited a larger CV area and longer charge and discharge times, indicating its better performance (the CV plots at different sweep speeds and GCD curves under different current densities are shown in Fig. S26–S28†). Furthermore, the MnF₂-E//AC LICs exhibited remarkable performances under both 0–4 V (106.8–41.4 W h kg⁻¹/0.33–10.7 kW kg⁻¹, 63.4%



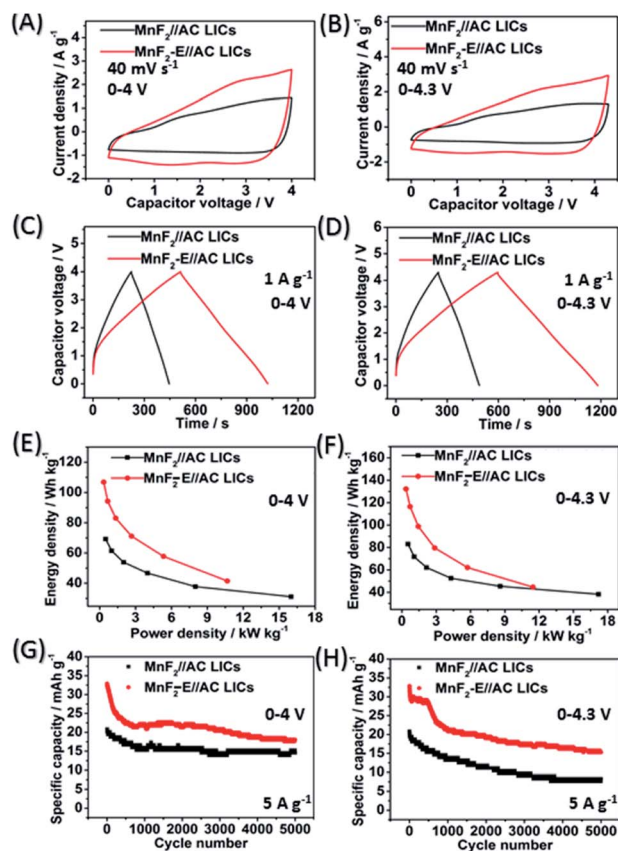


Fig. 5 CV plots at 40 mV s^{-1} (A and B), GCD curves at 1 A g^{-1} (C and D), Ragone plots (E and F) and cycling behavior for 5000 cycles at 5 A g^{-1} (G and H) of the MnF_2 //AC and MnF_2 8#-E//AC LICs under the voltages of 0–4 V and 0–4.3 V, respectively.

retention/3000 cycles/ 5 A g^{-1}) and 0–4.3 V (132.2 – 44.6 W h kg^{-1} / 0.36 – 11.5 kW kg^{-1} , 63.5% retention/1000 cycles/ 5 A g^{-1}) in comparison with the MnF_2 //AC LICs at 0–4 V (69.2 – 31.1 W h kg^{-1} / 0.5 – 16.0 kW kg^{-1} , 72.5% retention/3000 cycles/ 5 A g^{-1}) and 0–4.3 V (82.9 – 38.2 W h kg^{-1} / 0.54 – 17.2 kW kg^{-1} , 63.5% retention/1000 cycles/ 5 A g^{-1}) (more details are shown in Table S7[†]). The remarkable performance of the MnF_2 -E//AC LICs further proves that the double-defective Mn–O–F ultra-fine nanowire anode with hetero oxygen doping and intrinsic fluorine vacancy greatly enhances the energy storage performance. Moreover, the MnF_2 -E//AC and MnF_2 //AC LICs exhibited comparable or even better performance than many state-of-the-art LICs systems reported in the literature (Table S8[†]), demonstrating their promising application in Li-ion storage.

Performance for Na-ion storage

Due to the remarkable Li-ion storage capability of MnF_2 8# and MnF_2 8#-E, they were further investigated for Na-ion storage. In the CV plots of the MnF_2 8# electrode at 0.1 mV s^{-1} (Fig. 6A), there was a big reduction peak at around 1.03 V and a small reduction peak at about 0.16 V, corresponding to the conversion of MnF_2 into Mn/NaF and formation of SEI films in the first discharge, respectively. Moreover, the Na-ion storage capacity in

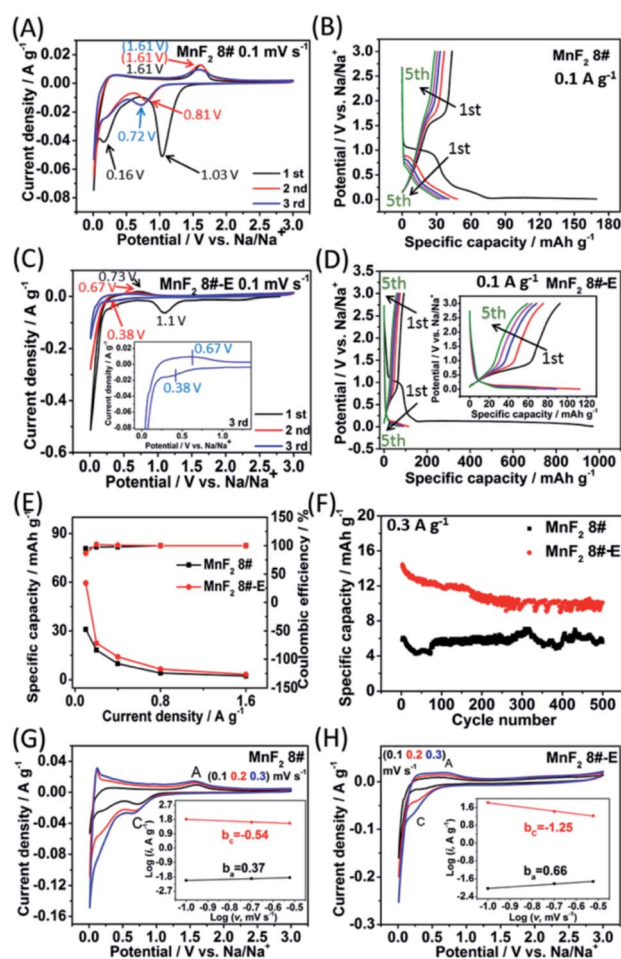


Fig. 6 CV plots for the first three cycles at 0.1 mV s^{-1} (A) and GCD curves for the 5th cycle at 0.1 A g^{-1} (B) of MnF_2 8# electrode, CV plots for the first three cycles at 0.1 mV s^{-1} (C) and GCD curves for the 5th cycle at 0.1 A g^{-1} (D) of the MnF_2 8#-E electrode, specific capacity and coulombic efficiency derived from the respective 5th cycle at 0.1– 1.6 A g^{-1} of the MnF_2 8# and MnF_2 8#-E electrodes (E), cycling stability for 500 cycles at 0.3 A g^{-1} of the MnF_2 8# and MnF_2 8#-E electrodes (F), and CV plots for the 3rd cycle at 0.1, 0.2, and 0.3 mV s^{-1} of MnF_2 8# and MnF_2 8#-E (insets show the plots of $\log i$ vs. $\log v$) (G and H).

the low potential region also originated from a reversible interfacial Na-ion intercalation reaction within the Mn/NaF matrix as Li-ion intercalation.^{31–35} Also, the minor anodic peak at about 1.61 V can be ascribed to the partial conversion of Mn/NaF into MnF_2 . In the second and third laps, the reduction peaks changed lightly from 0.81 V to 0.72 V, and the oxidation peaks were basically maintained at 1.61 V, indicating good reversibility. Fig. 6C shows the CV plots of the MnF_2 8#-E electrode at a sweep speed of 0.1 mV s^{-1} . A large cathode peak can be observed at about 1.1 V and small peak at around 0.4 V in the first round of negative sweep, which can be attributed to the conversion of Mn–O–F into $\text{Mn/NaF/Na}_2\text{O}$ and the formation of SEI films, respectively. Also, the minor anodic peak at 0.73 V during the first positive sweep can be ascribed to the partial conversion of $\text{Mn/NaF/Na}_2\text{O}$ into MnF_2/MnO . During the next two turns, the cathode peaks were basically maintained at



0.38 V, while the anode peaks shifted lightly from 0.73 V to 0.67 V, indicating good reversibility. Fig. 6B and D show the GCD curves for the MnF₂ 8# and MnF₂ 8#-E electrodes in the first five laps of 0.1 A g⁻¹, where the charge/discharge characteristics with the potential platforms coincide with the anodic/cathodic processes with redox peaks in their CV plots. Notably, the potential platforms of the MnF₂ 8#-E electrode are obviously lower than that of the MnF₂ 8# electrode for Na-ion storage, implying the superiority of the charge storage of the Mn-O-F anode. Fig. 6E and F show the gradient specific capacity and cycle behavior for the MnF₂ 8# and MnF₂ 8#-E electrodes, where MnF₂ 8# provides 31–2 mA h g⁻¹ at 0.1–3.2 A g⁻¹ with 5.4 mA h g⁻¹ after 500 cycles at 0.3 A g⁻¹ in comparison with the performance of 59–4 mA h g⁻¹ at 0.1–3.2 A g⁻¹ with 11 mA h g⁻¹ after 500 cycles at 0.3 A g⁻¹ for MnF₂ 8#-E (more details are shown in Fig. S29 and S30; Table S4[†]), which again shows that the double-defective Mn-O-F ultrafine nanowires anodes exhibit a big advantage in Na-ion storage. The XRD patterns of the electrodes after cycling (Fig. S31A and B[†]) show the slightly smaller diffraction peaks of the MnF₂ phase, and the TEM images of the electrodes after cycling (Fig. S31C–F[†]) show the presence of a few of ultrafine nanoparticles in the pristine nanocrystals or nanowires, suggesting the formation of partially amorphous nanostructural products for Na-ion storage after the long-term conversions. Fig. 6G and H show the CV plots at different sweep speeds and the relationship between peak current density and sweep rate ($\lg i = b \lg v + a$) for the MnF₂ 8# and MnF₂ 8#-E electrodes, respectively. The *ba* and *bc* values for the MnF₂ 8# electrode are 0.37 and -0.54, respectively, suggesting the typical diffusion-controlled kinetics, and the *ba* and *bc* values for the MnF₂ 8#-E electrode are 0.66 and -1.25, respectively, implying the dominant surface-controlled kinetics. Herein, the kinetic behavior of the MnF₂ 8# and MnF₂ 8#-E electrodes showed obvious differences between Li-ion storage (surface control/diffusion control) and Na-ion storage (diffusion control/surface control), which may be due to the difference in the radius of the Na and Li ions and the surface morphology and structure of the MnF₂ 8# and MnF₂ 8#-E materials. Moreover, the pseudocapacitive contribution (k_1v)^{36,37} at 0.1–0.3 mV s⁻¹ was estimated to be 72–82% and 15–24% for the MnF₂ 8# and MnF₂ 8#-E electrodes (Fig. S32 and S33, ESI[†]), respectively. The electrochemical kinetics of the MnF₂ 8# and Mn-O-F electrodes for Na-ion storage were further analyzed *via* EIS tests (Fig. S34 and Table S9, ESI[†]), which show that the Mn-O-F electrode possessed a smaller *R*_{ct} (106.7 Ω) than the MnF₂ electrode (144.8 Ω), suggesting the faster electrochemical kinetics of the Mn-O-F electrode owing to its superior morphology and porosity.

The MnF₂//AC and MnF₂-E//AC NICs were also assembled with MnF₂ 8# and MnF₂ 8#-E as anodes and commercial AC as the cathode along with the anodes pre-charged (pre-sodiation) at 0.1 A g⁻¹ for 3.5 turns (Fig. S35[†]). Initially, different active mass ratios of the cathode/anode were examined. The performance comparison for the different mass ratios in Fig. S37[†] indicate that the MnF₂//AC (1 : 1) NICs exhibited overall superior behavior (the performance of the AC cathode is shown in Fig. S36,† and the voltage windows, GCD curves and

CV plots of the MnF₂//AC NICs with different mass ratios are shown in Fig. S38 and S39[†]). The different potential windows were further examined under the optimal mass ratios of the NICs. Fig. 7A–H show the CV plots at 40 mV s⁻¹, GCD curves at 1 A g⁻¹, Ragone plots, and cycling behavior at 3 A g⁻¹ for 800 cycles of the NICs under the voltages of 0–4 V and 0–4.3 V. The MnF₂ 8#-E//AC capacitor exhibited a larger CV area and longer charge and discharge times, indicating its better performance (the CV plots at different sweep speeds and GCD curves under different current densities are shown in Fig. S40 and S41,† respectively). The MnF₂ 8#-E//AC NICs exhibited a remarkable performance of 42.1–8.9 W h kg⁻¹/0.5–8.0 kW kg⁻¹, and 63.1% retention/200 cycles/3 A g⁻¹ under 0–4 V and 55.9–19.2 W h kg⁻¹/0.48–7.7 kW kg⁻¹, and 45.3% retention/200 cycles/3 A g⁻¹ under 0–4.3 V in comparison with that of the MnF₂ 8#//AC NICs (16.4–4.4 W h kg⁻¹/0.5–8.0 kW kg⁻¹, 50.2% retention/200 cycles/3 A g⁻¹/0–4 V and 37–7.2 W h kg⁻¹/0.54–8.6 kW kg⁻¹, 66.7% retention/200 cycles/3 A g⁻¹/0–4.3 V, respectively). Furthermore, the MnF₂-E//AC NICs and MnF₂//AC NICs exhibited comparable or even better overall performances than that of many state-of-the-art NICs systems reported in the literature (Table S10[†]), showing their promising application in Na-ion storage.

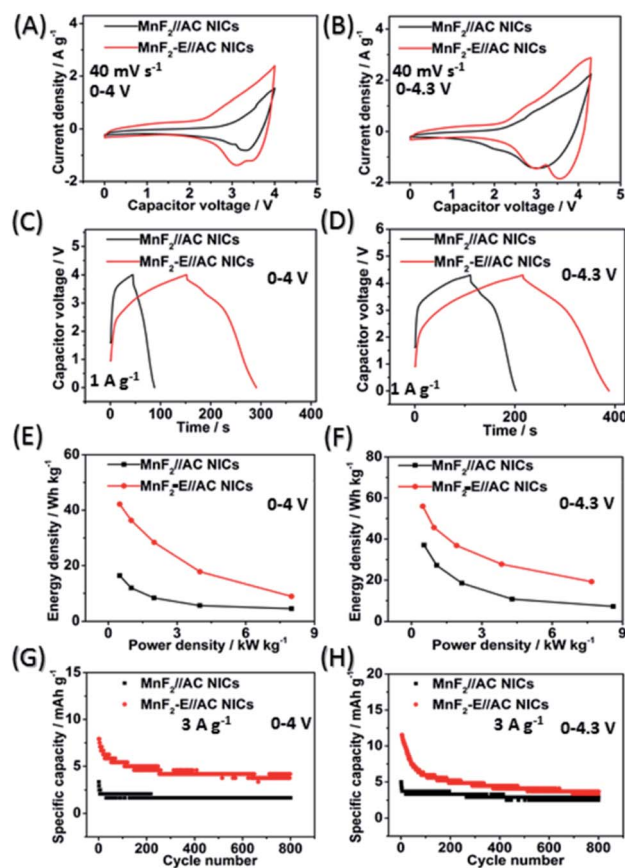


Fig. 7 CV plots at 40 mV s⁻¹ (A and B), GCD curves at 1 A g⁻¹ (C and D), Ragone plots (E and F), and cycling behavior for 800 cycles at 3 A g⁻¹ (G and H) of MnF₂ 8#//AC and MnF₂ 8#-E//AC NICs under the voltages of 0–4 V and 0–4.3 V, respectively.








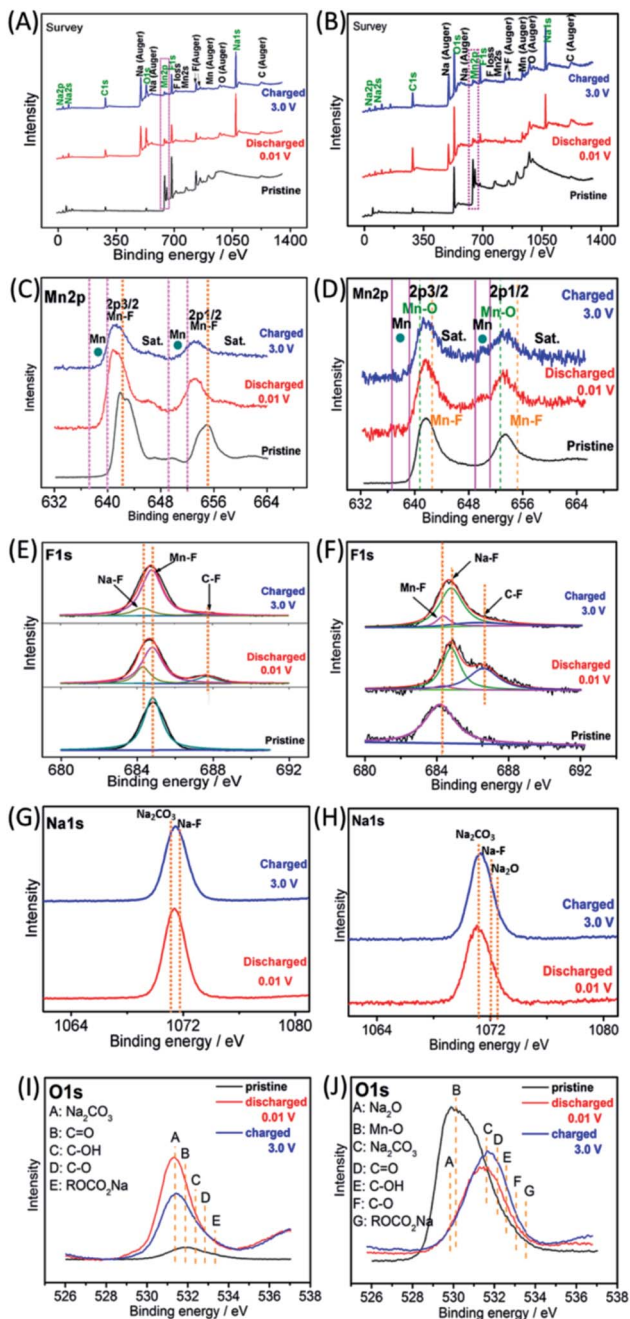


Fig. 9 *Ex situ* XPS spectra of MnF₂ 8# and MnF₂ 8#-E electrodes in the pristine, charged 3.0 V and discharged 0.01 V states during the first discharging/charging cycle at 0.02 A g⁻¹ for Na-ion storage: survey (A and B), Mn 2p (C and D), F 1s (E and F), Na 1s (G and H) and O 1s (I and J), respectively.

which again prove that MnF₂ 8# and MnF₂ 8#-E exhibit typical conversion reactions. The Na 1s spectra of MnF₂ 8# in Fig. 9G indicate the presence of NaF (mainly produced by the conversion reaction) and Na₂CO₃ (from the SEI films). Fig. 9H shows the Na 1s spectra of MnF₂ 8#-E, where the Na₂CO₃ bonds indicate the formation of SEI films, and NaF and Na₂O were formed by the feature reactions of Mn–O–F with Na-ion. Fig. 9I shows the O 1s spectra of MnF₂, where the Na₂CO₃, C=O, C–OH, C–O

and ROCO₂Na bonds in both the fully discharged/charged states are due to the formation of SEI films.^{32,39} Na₂O is also detected in the O 1s spectra of fully discharged/charged MnF₂ 8#-E (Fig. 9J), which is derived from the feature reaction of Mn–O–F with Na-ion.

Based on the above considerations, the possible reaction mechanisms of the MnF₂ and Mn–O–F anodes for both Li-ion and Na-ion storage can be expressed as eqn (1)–(6). For MnF₂, the mechanisms refer to eqn (1), (4) and (5) and for Mn–O–F, the mechanisms refer to eqn (2)–(6). A schematic of the possible processes for the first two discharging/charging cycles is illustrated in Scheme 1.



where N = Li, Na; 0 < x < 1; 0 < y < x.

Conclusions

In summary, double-defective Mn–O–F ultrafine nanowires with hetero oxygen-doping and intrinsic fluorine-vacancies were introduced as advanced anodes for high-efficiency LICs and NICs. Owing to the unique doping-vacancy double defects, the Mn–O–F anode exhibited a superior performance than the pristine MnF₂ anode, contributing to the superior performance of the Mn–O–F//AC LICs/NICs than the corresponding MnF₂//AC LICs/NICs. The *ex situ* characterizations and electrochemical methods revealed that the Mn–O–F anode demonstrates typical conversion reaction mechanisms with dominant diffusion-controlled and surface-controlled kinetics for Li/Na-ion storage, respectively. Overall, this work provides new insight into heteroatom-doping and anion vacancy double-defective Mn–O–F ultrafine nanowires anode to improve the Li/Na-ion storage and will have a significant impact on the development of advanced electrochemical energy storage devices.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

Thanks for the financial support from National Natural Science Foundation of China (21506182), Natural Science Foundation of Hunan Province (2018JJ2382), Education Department of Hunan



Province (18B077) and Hunan 2011 Collaborative Innovation Center of Chemical Engineering & Technology with Environmental Benignity and Effective Resource Utilization.

Notes and references

- J. M. Tarascon and M. Armand, *Nature*, 2001, **414**, 359–367.
- Z. G. Yang, J. L. Zhang, M. W. KintnerMeyer, X. C. Lu, D. Choi, J. Lemmon and J. Liu, *Chem. Rev.*, 2011, **111**, 3577–3613.
- J. Miller and P. Simon, *Science*, 2008, **321**, 651–652.
- B. Li, J. S. Zheng, H. Y. Zhang, L. M. Jin, D. J. Yang, H. Lv, C. Shen, A. Shellikeri, Y. R. Zheng, R. Q. Gong, J. Zheng and C. M. Zhang, *Adv. Mater.*, 2018, **30**, 1705670.
- H. W. Wang, C. R. Zhu, D. L. Chao, Q. Y. Yan and H. J. Fan, *Adv. Mater.*, 2017, **29**, 1702093.
- J. Ding, W. B. Hu, E. Paek and D. Mitlin, *Chem. Rev.*, 2018, **118**, 6457–6498.
- F. Li and Z. Zhou, *Small*, 2018, **14**, 1702961.
- S. Natarajan, Y.-S. Lee and V. Aravindan, *Chem.–Asian J.*, 2019, **14**, 936–951.
- P. Sennu, N. Arun, S. Madhavi, V. Aravindan and Y.-S. Lee, *J. Power Sources*, 2019, **414**, 96–102.
- P. Pazhamalai, K. Krishnamoorthy, S. Sahoo and S.-J. Kim, *J. Alloys Compd.*, 2018, **765**, 1041–1048.
- G. G. Amatucci, F. Badway, A. D. Pasquier and T. Zheng, *J. Electrochem. Soc.*, 2001, **148**, A930–A939.
- S. Dsoke, B. Fuchs, E. Gucciardi and M. Wohlfahrt-Mehrens, *J. Power Sources*, 2015, **282**, 385–393.
- P. Y. Wang, R. T. Wang, J. W. Lang, X. Zhang, Z. K. Chen and X. B. Yan, *J. Mater. Chem. A*, 2016, **4**, 9760–9766.
- C. F. Liu, C. K. Zhang, H. Q. Song, C. P. Zhang, Y. G. Liu, X. H. Nan and G. Z. Cao, *Nano Energy*, 2016, **22**, 290–300.
- D. P. Dubal, K. Jayaramulu, R. Zboril, R. A. Fischer and P. G. Romero, *J. Mater. Chem. A*, 2018, **6**, 6096–6106.
- R. Ding, Q. Li and H. Y. Wang, *Electrochim. Acta*, 2013, **114**, 726–735.
- N. Yabuuchi, K. Kubota, M. Dahbi and S. Komaba, *Chem. Rev.*, 2014, **114**, 11636–11682.
- E. Lim, C. Jo, M. S. Kim, M. H. Kim, J. Y. Chun, H. Kim, J. Park, K. C. Roh, K. Kang, S. Yoon and J. Lee, *Adv. Funct. Mater.*, 2016, **26**, 3711.
- H. X. Li, J. W. Lang, S. L. Lei, J. T. Chen, K. J. Wang, L. Y. Liu, T. Y. Zhang, W. S. Liu and X. B. Yan, *Adv. Funct. Mater.*, 2018, **28**, 1800757.
- M. L. Kang, Y. Y. Wu, X. Huang, K. Q. Zhou, Z. G. Huang and Z. S. Hong, *J. Mater. Chem. A*, 2018, **6**, 22840–22850.
- B. J. Yang, J. T. Chen, S. L. Lei, R. S. Guo, H. X. Li, S. Q. Shi and X. B. Yan, *Adv. Energy Mater.*, 2018, **8**, 1702409.
- H. L. Wang, D. Mitlin, J. Ding, Z. Li and K. Cui, *J. Mater. Chem. A*, 2016, **4**, 5149–5158.
- Y. L. Huang, Y. X. Zeng, M. H. Yu, P. Liu, Y. X. Tong, F. L. Cheng and X. H. Lu, *Small Methods*, 2018, **2**, 1700230.
- D. F. Yan, Y. X. Li, J. Huo, R. Chen, L. M. Dai and S. Y. Wang, *Adv. Mater.*, 2017, **29**, 1606459.
- S. B. Yang, L. J. Zhi, K. Tang, X. L. Feng, J. Maier and K. Müllen, *Adv. Funct. Mater.*, 2012, **22**, 3634–3640.
- Z. F. Li, C. Bommier, Z. S. Chong, Z. L. Jian, T. W. Surta, X. F. Wang, Z. Y. Xing, J. C. Neuefeind, W. F. Stickle, M. Dolgos, P. A. Greaney and X. L. Ji, *Adv. Energy Mater.*, 2017, **7**, 1602894.
- T. Zhai, X. Lu, Y. Ling, M. Yu, G. Wang, T. Liu, C. Liang, Y. Tong and Y. Li, *Adv. Mater.*, 2014, **26**, 5869.
- Y. C. Wang, T. Zhou, K. Jiang, P. M. Da, Z. Peng, J. Tang, B. Kong, W. B. Cai, Z. Q. Yang and G. F. Zheng, *Adv. Energy Mater.*, 2014, **4**, 1400696.
- Y. W. Liu, H. Cheng, M. J. Lyu, S. J. Fan, Q. H. Liu, W. S. Zhang, Y. D. Zhi, C. M. Wang, C. Xiao, S. Q. Wei, B. J. Ye and Y. Xie, *J. Am. Chem. Soc.*, 2014, **136**, 15670–15675.
- L. Qie, W. M. Chen, Z. H. Wang, Q. G. Shao, X. Li, L. X. Yuan, X. L. Hu, W. X. Zhang and Y. H. Huang, *Adv. Mater.*, 2012, **24**, 2047.
- K. Rui, Z. Y. Wen, Y. Lu, J. Jin and C. Shen, *Adv. Energy Mater.*, 2015, **5**, 1401716.
- D. F. Ying, R. Ding, Y. F. Huang, W. Shi, Q. L. Xu, C. N. Tan, X. J. Sun, P. Gao and E. H. Liu, *J. Mater. Chem. A*, 2019, **7**, 18257–18266.
- P. Balaya, H. Li, L. Kienle and J. Maier, *Adv. Funct. Mater.*, 2003, **13**, 621–625.
- H. Li, G. Richter and J. Maier, *Adv. Mater.*, 2003, **15**, 736–739.
- S. Grugeon, S. Laruelle, R. Herrera-Urbina, L. Dupont, P. Poizot and J.-M. Tarascon, *J. Electrochem. Soc.*, 2001, **148**, A285–A292.
- J. Wang, J. Polleux, J. Lim and B. Dunn, *J. Phys. Chem. C*, 2007, **111**, 14925–14931.
- V. K. Mariappan, K. Krishnamoorthy, P. Pazhamalai, S. Sahoo, S. S. Nardekar and S.-J. Kim, *Nano Energy*, 2019, **57**, 307–316.
- Q. L. Xu, R. Ding, W. Shi, D. F. Ying, Y. F. Huang, T. Yan, P. Gao, X. J. Sun and E. H. Liu, *J. Mater. Chem. A*, 2019, **7**, 8315–8326.
- W. Shi, R. Ding, Q. L. Xu, T. Yan, Y. X. Huang, C. N. Tan, X. J. Sun, P. Gao and E. H. Liu, *Chem. Commun.*, 2019, **55**, 6739–6742.

