

Cite this: *RSC Adv.*, 2019, 9, 18815

A cobalt-doped iron oxide nanozyme as a highly active peroxidase for renal tumor catalytic therapy†

Yixuan Wang,^a Hongjun Li,^{*b} Lihua Guo,^a Qi Jiang^a and Feng Liu^a

The Fe₃O₄ nanozyme, the first reported nanozyme with intrinsic peroxidase-like activity, has been successfully employed for various diagnostic applications. However, only a few studies have been reported on the therapeutic applications of the Fe₃O₄ nanozyme partly due to its low affinity to the substrate H₂O₂. Herein, we report a new strategy for improving the peroxidase-like activity and affinity of the Fe₃O₄ nanozyme to H₂O₂ to generate reactive oxygen species (ROS) for kidney tumor catalytic therapy. We showed that cobalt-doped Fe₃O₄ (Co@Fe₃O₄) nanozymes possessed stronger peroxidase activity and a 100-fold higher affinity to H₂O₂ than the Fe₃O₄ nanozymes. The lysosome localization properties of Co@Fe₃O₄ enable Co@Fe₃O₄ to catalyze the decomposition of H₂O₂ at ultralow doses for the generation of ROS bursts to effectively kill human renal tumor cells both *in vitro* and *in vivo*. Moreover, our study provides the first evidence that the Co@Fe₃O₄ nanozyme is a powerful nanozyme for the generation of ROS bursts upon the addition of H₂O₂ at ultralow doses, presenting a potential novel avenue for tumor nanozyme catalytic therapy.

Received 22nd December 2018

Accepted 8th March 2019

DOI: 10.1039/c8ra05487h

rsc.li/rsc-advances

Introduction

Nanozymes are a class of nanomaterials with intrinsic enzyme-like activities.^{1–3} Over the last decade, a wide variety of nanomaterials have been reported to possess natural enzyme-like activities.^{1–5} The biochemical reactions catalyzed by these types of nanozymes exhibit similar enzymatic kinetics as in the case of natural enzymes. Nanozymes exhibit comparable enzymatic activity but with much higher stability and lower cost as compared to natural enzymes. In addition, their activities are tunable, and they can be easily integrated with nanosystems to achieve multifunctionality;^{6,7} therefore, nanozymes possess significant potential for a wide range of applications in biomedicine such as in immunoassays, biosensors, and anti-bacterial and antibiofilm agents.^{4,8,9}

As a classical magnetic nanomaterial, iron oxide (Fe₃O₄) nanoparticles are the first reported nanozyme with intrinsic peroxidase-like activity.^{10,11} Fe₃O₄ nanozymes with intrinsic magnetic properties have been extensively used for biological applications including magnetic resonance imaging, magnetic drug delivery, magnetic hyperthermia and magnetic separation.^{12–14} Based on its newly discovered catalytic properties, the Fe₃O₄ nanozyme can act as a multifunctional enzyme mimetic for versatile biomedical applications.¹²

Recently, significant efforts have been made to explore the feasibility of application of nanozymes in *in vivo* clinical diagnosis and therapy.^{9,15–18} As the first well-studied nanozyme, Fe₃O₄ nanozymes have already been evaluated in tumor catalytic therapy for catalyzing the decomposition of hydrogen peroxide to generate ROS.^{16,19,20} However, because of the low affinity of the Fe₃O₄ nanozymes to H₂O₂, Fe₃O₄ nanozyme-based catalytic therapy typically requires an additional high dose of H₂O₂ (approximately 10^{−3} to 10^{−4} M);^{19,20} this makes this nanozyme-based catalytic tumor therapy strategy unviable for practical application.

Some heterogeneous oxide nanomaterials, such as ZnFeO₃²¹ and NiFeO₄²², formed by iron and other metals have been reported to exhibit enhanced peroxidase-like behavior; this indicates that transition metal doping of Fe₃O₄ nanozymes may be an effective way to improve the enzymatic activity of these nanoenzymes;²³ interestingly, Chen *et al.* have reported that Fe–Co bimetallic alloy nanoparticles also exhibit high peroxidase-like activity.²⁴ Moreover, Vetr *et al.* have investigated the effect of transition metal (Co, Ni, and Zn) doping on the catalytic performance of Fe₃O₄ nanozymes. They have demonstrated that NiFe₂O₄ and ZnFe₂O₄ NPs exhibit lower catalytic activity as compared to CoFe₂O₄ NPs.²⁵ Thus, doping of cobalt, a non-noble metal, into Fe₃O₄ nanozymes is a promising method to improve the peroxidase-like activity of Fe₃O₄ nanozymes; however, all these studies focus on the *in vitro* biosensing applications of metal-doped Fe₃O₄ nanozymes, and the applications of these nanozymes in tumor catalytic therapy have not been explored.

^aDepartment of Nephrology, China-Japan Union Hospital of Jilin University, Changchun, 130033, China

^bThe Examination Center, China-Japan Union Hospital of Jilin University, Changchun, 130033, China. E-mail: lihongjun1960@126.com

† Electronic supplementary information (ESI) available. See DOI: 10.1039/c8ra05487h



In this study, we demonstrated that doping of Co into Fe₃O₄ nanozymes (Co@Fe₃O₄) resulted in not only excellent peroxidase-like activity, but also a 100-fold higher affinity of Co@Fe₃O₄ to H₂O₂ than that in the case of Fe₃O₄ nanozymes. By employing Co@Fe₃O₄ nanozymes, we successfully achieved effective antitumor activity with the addition of an ultralow dose (10 nM) of H₂O₂ both *in vitro* and *in vivo*. This study provides a promising strategy to enhance the peroxidase-like activity of the Fe₃O₄ nanozyme and achieves the purpose of Fe₃O₄ nanozyme based-renal tumor catalytic therapy.

Materials and methods

Materials

Chemicals and materials were supplied by Sigma-Aldrich (St. Louis, MO) unless otherwise specified.

Synthesis and characterization of the Fe₃O₄ and Co@Fe₃O₄ nanozymes

The Fe₃O₄ nanozymes and Co-doped Fe₃O₄ nanozymes were synthesized according to the solvothermal method reported in the literature^{10,26} with some modifications. Briefly, for the Fe₃O₄ nanozymes, FeCl₃·6H₂O (0.82 g) was dissolved in 40 mL ethylene glycol. When the solution became clear, NaAc (3.6 g) was added under continuous vigorous stirring for 30 min. The mixture was sonicated for 10 min, then transferred to a 50 mL Teflon-lined stainless-steel autoclave and reacted at 200 °C for 12 h. After the reaction was completed, the autoclave was cooled down to room temperature. Then, the products obtained were washed several times with ethanol and dried at 60 °C.

The Co@Fe₃O₄ nanozymes were also synthesized using the same procedure but extra Co(NO₃)₃·6H₂O (0.82 g) was added to the reaction system.

The morphology and structure of the Fe₃O₄ and Co@Fe₃O₄ nanozymes were characterized by transmission electron microscopy (TEM, JEOL JEM-1400 120 kV), scanning electron microscopy (SEM, Zeiss Supra55) and dynamic light scattering (DLS, DynaPro Titan). Energy dispersive X-ray spectroscopy (EDX) of the Fe₃O₄ and Co@Fe₃O₄ nanozymes was conducted using the Tecnai G2 F30 instrument. X-ray diffraction (XRD) measurements were performed using the X'Pert pro Philips X-ray powder diffractometer. X-ray photoelectron spectroscopy (XPS) was performed by the ESCALab220i-XL high-performance electron spectrometer with a monochromatic Al K α source.

Kinetic analysis of the Fe₃O₄ and Co@Fe₃O₄ nanozymes

The kinetic parameters of the Fe₃O₄ and Co@Fe₃O₄ nanozymes were determined by monitoring the absorbance change at 652 nm using the iMark™ Microplate Reader (Bio-Rad, USA) in the time course mode at room temperature. Kinetic assays were carried out using the Fe₃O₄ nanozymes (0.2 μ g) or Co@Fe₃O₄ nanozymes (0.2 μ g) in a 100 μ L of reaction buffer (0.2 M NaAc buffer, pH 4.5) in the presence of H₂O₂ and TMB. The kinetic analysis of Fe₃O₄ and Co@Fe₃O₄

with H₂O₂ as the substrate was performed by varying the concentrations of H₂O₂ with 0.8 mM TMB and *vice versa*. The absorbance (652 nm) changes were calculated relative to the changes in the molar concentration of TMB using the molar absorption coefficient of 39 000 M⁻¹ cm⁻¹ for the TMB-derived oxidation products according to the Beer-Lambert law.²⁷ All the measurements were performed at least in triplicate, and the values were then averaged. The results are provided as mean \pm the standard deviation (SD). The Michaelis-Menten constant was calculated using the Lineweaver-Burk plots of the double reciprocal of the Michaelis-Menten equation $\nu = V_{\max} \times [S]/(K_M + [S])$ by GraphPad Prism 6.02 (GraphPad Software), where ν is the initial velocity, V_{\max} is the maximal reaction velocity, $[S]$ is the concentration of the substrate and K_M is the Michaelis-Menten constant.

ESR spectroscopy measurements

The ESR measurements were carried out using a Bruker electron spin resonance (ESR) spectrometer (A300-10/12, Germany) at ambient temperature. Herein, fifty microliter aliquots of the control or sample solutions were put in glass capillary tubes with the internal diameters of 1 mm and sealed. The capillary tubes were then inserted into the ESR cavity, and the spectra were obtained at selected times. The instrument settings are as follows: 1 G field modulation, 100 G scan range, and a 20 mW microwave power for the detection of spin adducts using spin traps. The spin trap BMPO was employed to verify the formation of hydroxyl radicals (OH \cdot) during the degradation of H₂O₂ in the presence of the Fe₃O₄ or Co@Fe₃O₄ nanozymes under the same conditions. The amount of hydroxyl radicals was quantitatively estimated by the ESR signal intensity of the hydroxyl radical spin adduct (BMPO/OH \cdot) using the peak-to-peak height of the second line of the ESR spectrum.

Cell viability assay

The cytotoxicity of the Fe₃O₄ and Co@Fe₃O₄ nanozymes with the addition of 10 nM H₂O₂ was determined using the CCK-8 cell viability assay kit (Dojindo Molecular Technologies). Briefly, A-498 cells (Human renal cancer cell, ATCC, HTB-44) were plated in 96-well plates (BD Biosciences) with the density of 5×10^3 cells per well and cultured in 100 μ L EMEM (Catalog No. 30-2003) for 1 day before the addition of Fe₃O₄, Co@Fe₃O₄ nanozymes, or only the buffer as a control. On each plate, blank wells ($n = 6$) with media were defined as 0% viability. Moreover, the wells with only PBS-treated cells ($n = 6$) were defined as 100% viability. The dilutions of the Fe₃O₄ and Co@Fe₃O₄ nanozymes were prepared using a buffer containing 10 nM H₂O₂. The cells were then exposed to the Fe₃O₄ or Co@Fe₃O₄ nanozymes at a series of concentrations (from 0 to 0.2 mg mL⁻¹) for 24 hours. After stimulation, a 10 μ L CCK-8 solution was added to each well. The plates were then incubated for 4 h at 37 °C. After this, the absorbance was determined at 450 nm using the Benchmark Plus microplate spectrophotometer (Bio-Rad Laboratories, Inc.). The results presented herein are the average of those obtained *via* three independent experiments.



Localization of the Fe₃O₄ and Co@Fe₃O₄ nanozymes in cytoplasm

The cellular uptake and distribution of Fe₃O₄ or Co@Fe₃O₄ nanozymes in human renal tumor cells were investigated by a confocal laser scanning microscope. Briefly, the A-498 cells were plated on poly-L-lysine-treated coverslips (BD Biosciences) and cultured in a six-well plate (Corning) for 12 h before use. After stimulation for 48 h with the Alexa-488-labeled Fe₃O₄ or Co@Fe₃O₄ nanozymes (0.2 mg mL⁻¹), the cells were washed with PBS, fixed in 4% cold formaldehyde in PBS for 5 min, and then permeabilized with 0.1% Triton X-100. After being washed with PBS, the cells were blocked in a 5% normal goat serum for 30 min at room temperature. To visualize the lysosomes, the cells were incubated with anti-Lamp1 mAb (1 : 200, clone H4A3; Invitrogen) at 37 °C for 1 h. The cells were then washed three times with PBS and incubated with goat anti-mouse IgG1 conjugated with Alexa-555 (1 : 500; Invitrogen) for 1 h at 37 °C. Finally, the nuclei of the cells were stained with 4',6'-diamidino-2-phenylindole (DAPI, 1 μg mL⁻¹, Roche Applied Science) for 10 min at room temperature. The samples were examined using a confocal laser scanning microscope (Olympus FluoView FV-1000, Tokyo, Japan).

Intracellular ROS assay

The fluorescent probe 2',7'-dichlorofluorescein diacetate (H₂DCFDA, Sigma-Aldrich, D6883) was used to measure the intracellular generation of ROS by the Fe₃O₄ or Co@Fe₃O₄ nanozymes. Briefly, the confluent A-498 cells on the coverslips (BD Biosciences) were incubated with Fe₃O₄ or Co@Fe₃O₄ nanozymes (0.2 mg mL⁻¹) for 4 hours. After being washed with PBS, the cells were incubated with 10 μM H₂DCFDA in a serum-free DMEM for 20 min at 37 °C in the dark. The fluorescence intensities of H₂DCFDA were measured by a confocal laser scanning microscope (Olympus FluoView FV-1000, Tokyo, Japan).

Apoptosis analysis

The apoptosis analysis of the treated tumor cells was conducted by PI and annexin V staining and flow cytometry (FACSCalibur™, Becton Dickinson, Franklin Lakes, NJ, USA). Briefly, the Fe₃O₄ and Co@Fe₃O₄ (0.2 mg mL⁻¹) nanozymes were incubated with the A-498 tumor cell lines for 24 h. After trypsinization, the treated A-498 tumor cells were incubated with annexin V and PI for 15 min to achieve nuclear staining. After this, the cells were fixed and incubated with streptavidin-fluorescein (5 μg mL⁻¹) (Sigma, USA) for 15 min. Cell death was evaluated by the quantification of annexin-stained apoptotic cells and PI-stained necrotic cells using flow cytometry.

Therapy studies

Herein, eighteen female BALB/c nude mice bearing A-498 tumors were randomly assigned to four groups (*n* = 6 mice per group). All the mice were intratumorally treated with a single dose of Fe₃O₄ and Co@Fe₃O₄ nanozymes (3 mg mL⁻¹,

100 μL) with 10 nM H₂O₂ when the diameter of the tumors was about 100 mm³. For the controls, PBS was administered. The tumor size was measured 3 times a week. The tumor size was calculated as volume [mm³] = length × width² × π/6. The measured values are presented as mean ± SD.

Results

Characterization of the Co@Fe₃O₄ nanozymes

The Fe₃O₄ nanozymes and Co-doped Fe₃O₄ nanozymes (Co@Fe₃O₄) used in this study were synthesized by the solvothermal method. To study the composition of the as-prepared nanozymes, the EDX analysis was performed. As shown in Fig. S1,† the EDX spectrum of the Co@Fe₃O₄ nanozymes indicated that the Fe and Co elements were present in the nanoparticles. Based on the EDX mapping analysis, the content of Fe and Co in the Co@Fe₃O₄ nanozymes were determined as 33.48% and 16.23%, respectively (Table S1†). In conclusion, herein, the synthesized Co@Fe₃O₄ nanozymes contained Fe and Co with the ratio of approximately 2 : 1; this confirmed that Co was successfully doped into the Fe₃O₄ nanozymes by the simple solvothermal method.

To characterize the structure of the Co@Fe₃O₄ nanozymes, TEM, SEM, DLS and X-ray diffraction (XRD) analysis were performed. The TEM images of the as-prepared Fe₃O₄ and Co@Fe₃O₄ nanozymes are shown in Fig. 1A and B, respectively. The SEM images of the Fe₃O₄ and Co@Fe₃O₄ nanozymes are presented in Fig. S2A and B,† respectively. The results indicate that the Fe₃O₄ and Co@Fe₃O₄ nanozymes present a typical spherical morphology. The average size of the Fe₃O₄ nanozymes was determined to be 89.8 ± 7.9 nm by the TEM images, whereas that of the Co@Fe₃O₄ nanozymes was determined to be 94.6 ± 8.6 nm. Moreover, the Fe₃O₄ and Co@Fe₃O₄ nanozymes exhibited the average size of 90.31 ± 0.62 nm and 95.82 ± 3.57 nm in solution (Fig. S2C and D)†, respectively. The XRD patterns of the as-prepared nanozymes are shown in Fig. 1C and D, which indicate that both the Fe₃O₄ and Co@Fe₃O₄ nanozymes are well crystallized. Moreover, each characteristic diffraction peak of the Co@Fe₃O₄ nanozymes was similar to that of the Fe₃O₄ nanozymes and the standard PDF card of Fe₃O₄ (JCPDS card no. 19-0629); this indicated that Co-doping of the Fe₃O₄ nanozymes did not affect the phase pattern of Fe₃O₄.

To characterize the oxidation state of cobalt in the Co@Fe₃O₄ nanozyme, we further performed XPS analysis of the as-prepared Co@Fe₃O₄ nanozyme. The high-resolution XPS spectrum of Co 2p is shown in Fig. 2A. The Co 2p XPS peak at 780.8 eV was assigned to Co (2p_{3/2}), with a shake-up satellite peak at 785.9 eV. In addition, the Co 2p XPS peak at 797.2 eV was attributed to Co (2p_{1/2}), with a satellite peak at 803.0 eV.²⁸ These characteristic and satellites peaks confirm that Co²⁺ is present in the Co@Fe₃O₄ nanozyme. Moreover, as shown in Fig. 2B, the Fe 2p XPS spectrum exhibited characteristic peaks with the binding energy values at 711.0 and 724.0 eV, assigned to the Fe (2p_{3/2}) and Fe (2p_{1/2}) peaks,²⁹ respectively. Since the atomic radius of iron (140 pm) is



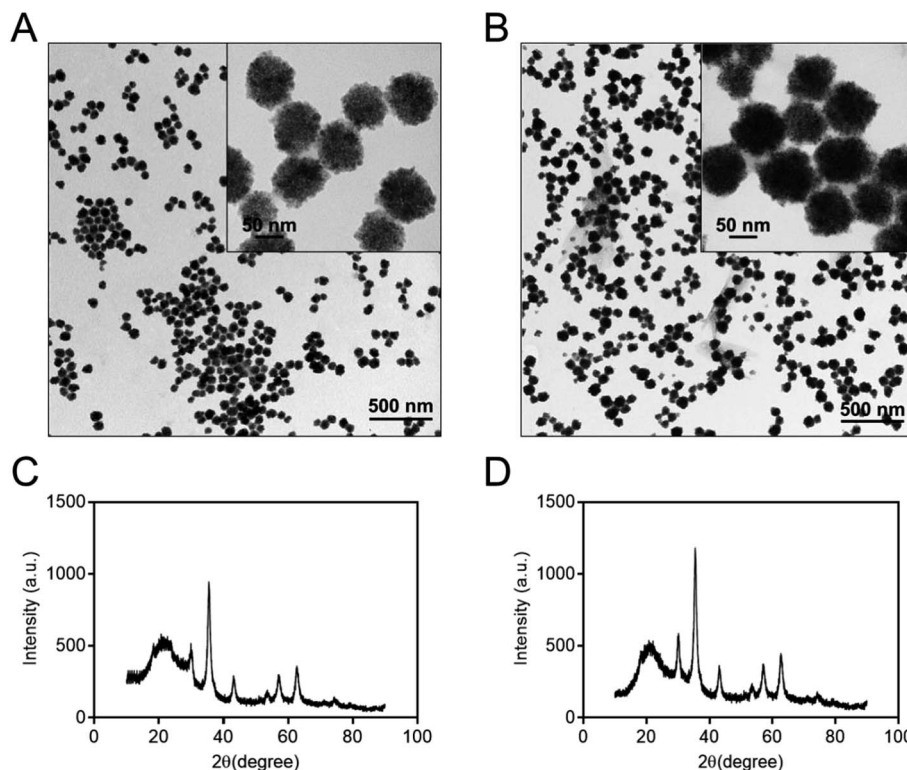


Fig. 1 TEM images and XRD diffraction patterns of the Fe₃O₄ (A and C) and Co@Fe₃O₄ nanozymes (B and D), respectively.

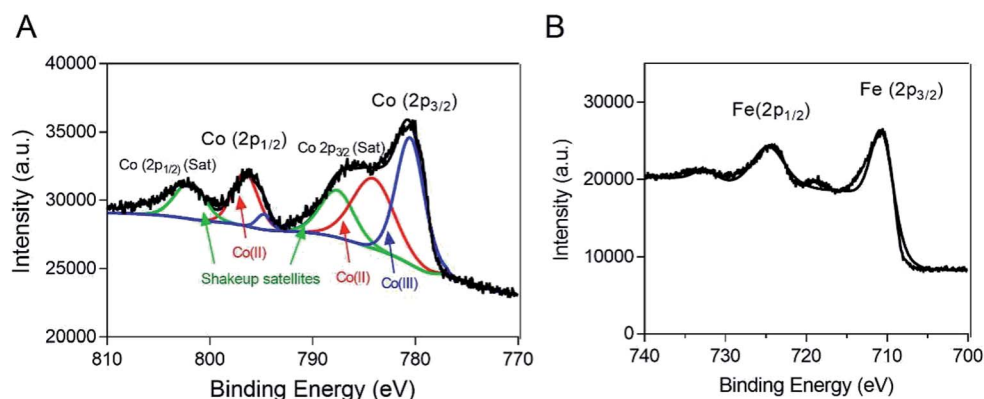


Fig. 2 XPS spectra of the Co@Fe₃O₄ nanozyme. (A) The Co 2p XPS spectrum of the Co@Fe₃O₄ nanozyme. (B) The Fe 2p XPS spectrum of the Co@Fe₃O₄ nanozyme.

similar to that of the cobalt atom (135 pm), these results suggest that the cobalt atoms are probably located only at the lattice positions of the Fe₃O₄ crystal structure.

Peroxidase-like activity and steady-state kinetic assay of the Co@Fe₃O₄ nanozymes

To directly compare the peroxidase-like activity of the Fe₃O₄ and Co@Fe₃O₄ nanozymes, we performed typical catalytic experiments using the peroxidase substrate 3,3',5,5'-tetramethylbenzidine (TMB) and H₂O₂ as previously reported.¹¹ The results showed that both the Fe₃O₄ and Co@Fe₃O₄

nanozymes catalyzed the oxidation of TMB with H₂O₂ to produce blue color products with absorption at 652 nm (Fig. 3A). Moreover, the results demonstrated that the Co@Fe₃O₄ nanozymes exhibited a significant improvement in the peroxidase-like activity as compared to the Fe₃O₄ nanozymes; this indicated that a significant improvement in the nanozyme activity was achieved by Co doping of the Fe₃O₄ nanozymes.

The mechanism of action of the Co@Fe₃O₄ nanozymes was investigated using the ESR method. As shown in Fig. 3B, similar to the previously reported Fe₃O₄ nanozymes, the Co@Fe₃O₄ nanozymes significantly enhanced the generation



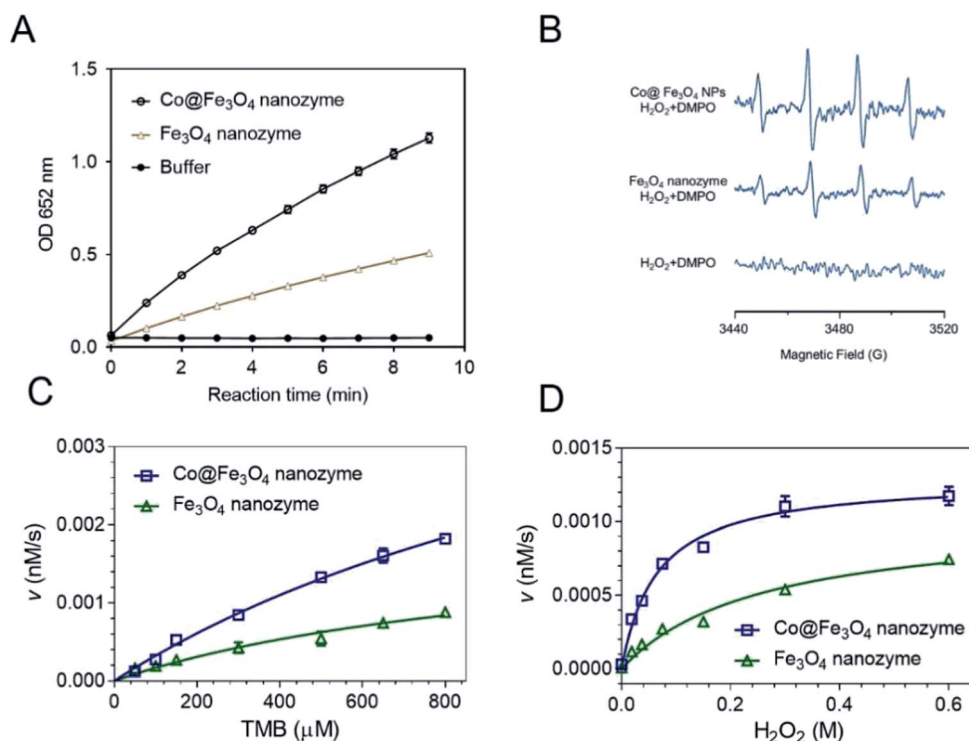


Fig. 3 Steady-state kinetic assay and the catalytic mechanism study for the Fe₃O₄ and Co@Fe₃O₄ nanozymes. (A) Comparison between the peroxidase-like activities of the Fe₃O₄ and Co@Fe₃O₄ nanozymes. (B) ESR detection of the hydroxyl radical generation during the catalytic reactions of the Fe₃O₄ and the Co@Fe₃O₄ nanozymes. (C–D) Kinetic assay of Fe₃O₄ and Co@Fe₃O₄ nanozymes with TMB (C) or H₂O₂ (D). For C, the concentration of H₂O₂ was 100 mM, whereas the TMB concentration varied. For (D), the concentration of TMB was 0.8 mM, whereas the H₂O₂ concentration varied.

of hydroxyl radicals under acidic conditions. Importantly, the Co@Fe₃O₄ nanozymes generated more hydroxyl radicals than the Fe₃O₄ nanozymes under the same conditions; this further confirmed that Co doping significantly improved the peroxidase-like activity of the Fe₃O₄ nanozymes.

To obtain the apparent kinetic parameters of the Co@Fe₃O₄ nanozymes, the Michaelis–Menten experiments were performed. Fig. 3C and D show the typical kinetics for TMB and H₂O₂, respectively. The apparent Michaelis–Menten constant (K_M) and the maximum initial reaction rate (V_{max}) of the Co@Fe₃O₄ and Fe₃O₄ nanozymes were calculated. Moreover, these kinetic parameters of the Co@Fe₃O₄ nanozymes

were compared with those of the Fe₃O₄ and Co₃O₄ nanozymes and the natural enzyme HRP (Table 1). The Fe₃O₄ nanozymes typically exhibited low affinity to H₂O₂. The K_M value to H₂O₂ for the Co@Fe₃O₄ nanozymes was much lower than that for the Fe₃O₄ and Co₃O₄ nanozymes; this indicated that there was a significant improvement in the affinity of the nanozymes towards substrates after Co doping. More importantly, the K_M value to H₂O₂ for Co@Fe₃O₄ was nearly 50-fold and 100-fold lower than that of the HRP enzyme and the Fe₃O₄ nanozymes, respectively; this demonstrated that the Co@Fe₃O₄ nanozymes exhibited much higher affinity to H₂O₂ than HRP and the other nanozymes. The V_{max} values to H₂O₂ for the Co@Fe₃O₄ nanozymes were also significantly improved.

Table 1 Comparison between the apparent Michaelis–Menten constants (K_M) and maximum initial reaction rates (V_{max}) of the Fe₃O₄, Co@Fe₃O₄, Co₃O₄ nanozymes and horseradish peroxidase (HRP) enzymes

Nanozyme	K_M (mM)		V_{max} ($10^{-8} \text{ M}^{-1} \text{ s}^{-1}$)		References
	H ₂ O ₂	TMB	H ₂ O ₂	TMB	
Co@Fe ₃ O ₄	0.19	1.17	71.5	37.9	This work
Fe ₃ O ₄	56.89	1.06	59.6	16.8	This work
Co ₃ O ₄	1.14	5.09	1.72	9.98	24
HRP	10.35	3.95	0.689	37.65	11

Anti-tumor activities and mechanistic study of the Co@Fe₃O₄ nanozymes

Tumor cells typically possess higher levels of endogenous H₂O₂ and reactive oxygen species (ROS) than normal cells.^{9,20} The balance of the ROS determines the fate of the tumor cells. It has been previously shown that stimulation of ROS is a common strategy for cancer chemotherapy.^{30,31} Thus, we employed the Co@Fe₃O₄ nanozymes to trigger the burst of ROS to kill the tumor cells.

Fe₃O₄ nanozymes, as the first well-studied nanozyme, have already been evaluated in tumor catalytic therapy for



catalyzing the decomposition of hydrogen peroxide to generate ROS.^{19,20} However, because of the low affinity of these nanozymes to H₂O₂, the Fe₃O₄ nanozyme-based catalytic therapy typically requires additional high doses of H₂O₂ (approximately 10⁻³ to 10⁻⁴ M);^{19,20} this makes this nanozyme-based catalytic tumor therapy strategy unfeasible for practical application. In this study, we demonstrated that the Co@Fe₃O₄ nanozymes exhibited a 100-fold higher affinity to H₂O₂ than the Fe₃O₄ nanozymes. Therefore, we next evaluated the catalytic antitumor activity of the Co@Fe₃O₄ nanozymes with ultra-low doses of H₂O₂.

Considering that the typically used concentration of H₂O₂ is around 10⁻³ to 10⁻⁴ M, we have tried to use 10 nM (10⁻⁸ M) H₂O₂ to evaluate the antitumor activities of the Co@Fe₃O₄ nanozymes. As shown in Fig. 4A, the buffer group containing 10 nM H₂O₂ exhibited no significant toxicity to kidney cancer cells; this indicated that the tumor cells were able to survive at 10 nM H₂O₂. After incubation with 0.2 mg mL⁻¹ Fe₃O₄ nanozymes and 10 nM H₂O₂ for 24 hours, only less than 20% tumor cells were killed. These results are consistent with the previously reported results. Only a high dose of H₂O₂ allows the Fe₃O₄ nanozymes to effectively kill tumor cells. In the case of the Co@Fe₃O₄ nanozymes, 0.02 mg mL⁻¹ Co@Fe₃O₄ nanozymes with 10 nM H₂O₂ achieved similar antitumor activities as 0.2 mg mL⁻¹ Fe₃O₄ nanozymes. Moreover, 0.2 mg

mL⁻¹ Co@Fe₃O₄ nanozymes and 10 nM H₂O₂ killed more than 60% of the tumor cells within 24 hours. Thus, the Co@Fe₃O₄ nanozymes effectively killed tumor cells with the addition of H₂O₂ at ultralow doses.

As is well-known, the Fe₃O₄ nanozymes exhibit peroxidase-like activity only under acidic conditions.¹² Since the Co@Fe₃O₄ nanozymes exhibit significant antitumor activity, we infer that the Co@Fe₃O₄ nanozymes localize in the lysosome (pH 4–5) after incubation with the tumor cells. To verify this hypothesis, we labeled the nanozymes with Alexa Fluor 488 to track their intracellular localization. As shown in Fig. 4B, we found that after incubation with tumor cells for 4 hours, most of the internalized Fe₃O₄ nanozymes co-localized with lysosomes. Similar to the Fe₃O₄ nanozymes, nearly all of the internalized Co@Fe₃O₄ nanozymes localized in the lysosomes, the highly acidic microenvironment of which would favor the peroxidase-like activities. Thus, the co-localization analysis of the nanozymes and lysosomes demonstrated that the nanozyme-based tumor catalytic therapy strategy is feasible.

In our hypothesis, the antitumor activities of the Co@Fe₃O₄ nanozymes are attributed to the catalytic generation of ROS by the decomposition of hydrogen peroxide, resulting in oxidative stress in the tumor cells. To verify this hypothesis, the intracellular ROS levels in the tumor cells

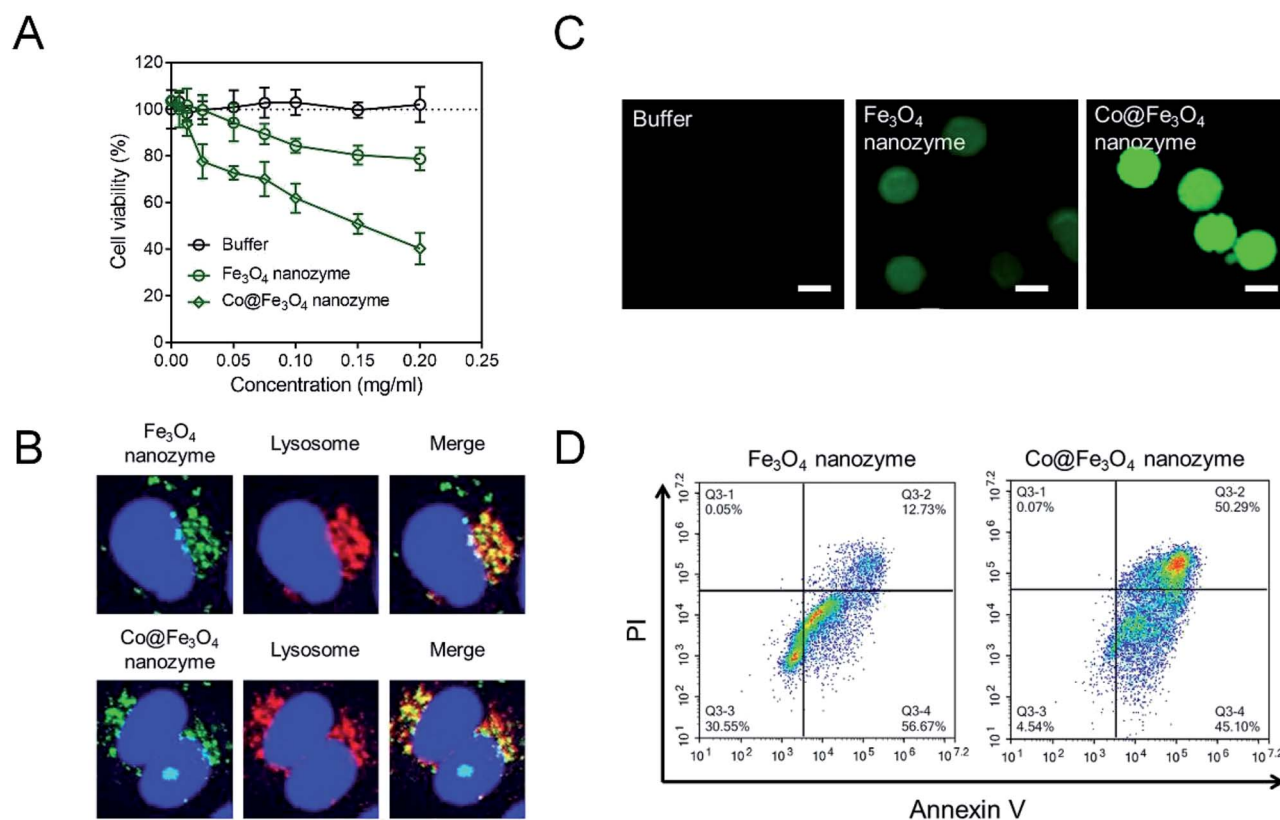


Fig. 4 The antitumor cell activities and mechanistic study of the Fe₃O₄ and Co@Fe₃O₄ nanozymes *in vitro*. (A) Cell viability of the human renal cancer cells A-498 incubated with the Fe₃O₄ and Co@Fe₃O₄ nanozymes. The buffer contained 10 nM H₂O₂. (B) Localization of the Fe₃O₄ and Co@Fe₃O₄ nanozymes in the A-498 cells. (C) The ROS level in the A-498 cells after stimulation with nanozymes and 10 nM H₂O₂. Scale bar = 20 μm. (D) Apoptosis analysis of the A-498 cells after incubation with nanozymes and 10 nM H₂O₂.



were detected by employing 2',7'-dichlorofluorescein diacetate (H_2DCFDA), a typical ROS fluorescent dye. As shown in Fig. 4C, the tumor cells treated with only 10 nM H_2O_2 exhibited no significant ROS signal. After incubation with the Fe_3O_4 nanozymes and 10 nM H_2O_2 , the green fluorescence intensity increased. In contrast, the tumor cells treated with the $Co@Fe_3O_4$ nanozymes and 10 nM H_2O_2 presented strong green fluorescence intensity, indicating that the $Co@Fe_3O_4$ nanozymes catalyzed the decomposition of H_2O_2 to generate an ROS burst to cause cell apoptosis. As shown in Fig. 4D, the tumor cells treated with the $Co@Fe_3O_4$ nanozymes and 10 nM H_2O_2 exhibited a significant apoptosis pattern. When the tumor cells were stimulated with the nanozymes at same concentration, the apoptosis induced by the $Co@Fe_3O_4$ nanozymes in the tumor cells was 4-fold higher than that of the Fe_3O_4 nanozymes.

To further evaluate the antitumor activity of the $Co@Fe_3O_4$ nanozymes *in vivo*, we employed the human renal cancer cell A-498 xenograft in nude mice as a tumor model. The Fe_3O_4 nanozymes and $Co@Fe_3O_4$ nanozymes were intratumorally injected at the dose of 0.3 mg in 100 μ L PBS and 10 nM H_2O_2 when the tumor volume reached 100 mm^3 . After this, the tumor volumes were determined 3 times a week. As shown in Fig. 5, the $Co@Fe_3O_4$ nanozyme-treated mice exhibited significant tumor inhibition after $Co@Fe_3O_4$ administration, whereas the Fe_3O_4 nanozyme-treated mice exhibited only slight tumor inhibition when compared with the PBS-treated mice. Thus, the $Co@Fe_3O_4$ nanozymes exhibited excellent *in vivo* renal tumor catalytic therapy activity, whereas the Fe_3O_4 nanozymes only partially inhibited the renal tumor growth due to their relative low peroxidase activity and low binding affinity to H_2O_2 ;¹¹ this was consistent with previous studies.⁹

Overall, these results provide strong evidence that the $Co@Fe_3O_4$ nanozymes possess the ability to regulate intracellular ROS upon the addition of H_2O_2 at ultralow concentrations. Once located in the acidic microenvironment of lysosomes, these nanozymes induce cell death by boosting the level of ROS. The $Co@Fe_3O_4$ nanozymes exhibited significant antitumor activities against human renal tumor both *in vitro* and *in vivo*.

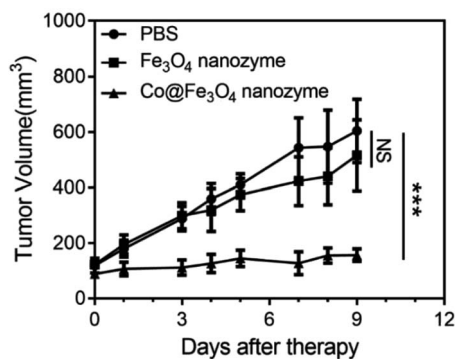


Fig. 5 Antitumor activities of the Fe_3O_4 and $Co@Fe_3O_4$ nanozymes *in vivo*. $n = 6$, $***p < 0.001$, NS, no significance, unpaired Student's t test on day 9.

Discussion and conclusion

ROS-induced apoptosis is a popular strategy for cancer therapy.^{32–34} The tumor therapy strategies utilizing nanozymes mainly act by stimulating the production of ROS.⁹ The Fe_3O_4 nanozymes can simulate peroxidase and thereby efficiently catalyze the decomposition of H_2O_2 to generate ROS to inhibit tumors *in vivo*. However, the low binding affinity of the Fe_3O_4 nanozyme to H_2O_2 and its relatively low catalytic activity limit the development of the Fe_3O_4 nanozyme-based tumor catalytic therapy.

Transition metal doping has been demonstrated to be an effective and easy way to improve the peroxidase-like activity of Fe_3O_4 nanozymes.²³ Among the transition metals, cobalt, a non-noble metal, has been proven to be a promising dopant to enhance the enzymatic activity of the Fe_3O_4 nanozyme.²⁵ Importantly, Chen *et al.* have systematically studied the effects of doping Fe/Co at different ratios on the enzymatic activity of the Fe_3O_4 nanozyme. They have demonstrated that when the ratio of Fe/Co is around 2 : 1, the peroxidase-like activity of the Co-doped Fe_3O_4 nanozyme is the best enzymatic activity.²⁴ In this study, by employing a simple solvothermal method, we fabricated the $Co@Fe_3O_4$ nanozyme with the ratio of Fe/Co around 2 : 1. Compared with the case of other strategies, including metal doping, biomimetic coating, and C-dot modification methods, that significantly improved the peroxidase-like activity of the Fe_3O_4 nanozyme, our $Co@Fe_3O_4$ nanozyme exhibited the best binding affinity to H_2O_2 (Table S2†).

The XPS and EDX analysis of the $Co@Fe_3O_4$ nanozyme demonstrated that the cobalt atoms were probably located only at the lattice positions of the Fe_3O_4 crystal structure. Although the Co atom possesses a similar size as the Fe atom, the Co atoms doped into the Fe_3O_4 crystal may still slightly change the surface physical environment,³⁵ resulting in an improved binding affinity of the nanozyme to H_2O_2 . In addition, the Co dopant may produce more catalytically active sites and substrate-binding sites on the surface of the $Co@Fe_3O_4$ nanozyme when compared with the case of the Fe_3O_4 nanozyme.³⁶ Moreover, the higher redox potential of Co^{3+}/Co^{2+} (1.30 V) as compared to that of Fe^{3+}/Fe^{2+} (0.771 V) in the Fe_3O_4 nanozyme may be another reason for the improvement in the peroxidase-like activities of $Co@Fe_3O_4$.^{37,38}

In conclusion, using a simple solvothermal method, we successfully synthesized Co-doped Fe_3O_4 ($Co@Fe_3O_4$) nanozymes that contained Fe and Co at the ratio of approximately 2 : 1. The well-crystallized $Co@Fe_3O_4$ nanozymes exhibited excellent peroxidase-like activity. More importantly, Co doping makes the $Co@Fe_3O_4$ nanozymes exhibit a 50-fold and 100-fold higher affinity to H_2O_2 than that of the HRP and Fe_3O_4 nanozymes, respectively. The improvement of the H_2O_2 affinity renders the $Co@Fe_3O_4$ nanozymes with excellent antitumor activity upon the addition of H_2O_2 at ultralow concentrations. When the $Co@Fe_3O_4$ nanozymes with enhanced peroxidase-like activities are specifically located in the acidic microenvironment of the lysosomes, they induce apoptosis of human renal tumor cells (A-498) by catalyzing the decomposition of H_2O_2 to



generate an ROS burst. Importantly, the Co@Fe₃O₄ nanozymes exhibited excellent antitumor activities both *in vitro* and *in vivo* for kidney tumor catalytic therapy.

Conflicts of interest

There are no conflicts to declare.

References

- H. Wei and E. K. Wang, *Chem. Soc. Rev.*, 2013, **42**, 6060–6093.
- Y. H. Lin, J. S. Ren and X. G. Qu, *Acc. Chem. Res.*, 2014, **47**, 1097–1105.
- R. Ragg, M. N. Tahir and W. Tremel, *Eur. J. Inorg. Chem.*, 2016, 1906–1915, DOI: 10.1002/ejic.201501237.
- X. Y. Wang, Y. H. Hu and H. Wei, *Inorg. Chem. Front.*, 2016, **3**, 41–60.
- H. Y. Shin, T. J. Park and M. I. Kim, *J. Nanomater.*, 2015, 756278.
- Z. Zhang, X. Zhang, B. Liu and J. Liu, *J. Am. Chem. Soc.*, 2017, **139**, 5412–5419.
- B. W. Liu and J. W. Liu, *Nano Res.*, 2017, **10**, 1125–1148.
- K. F. Xiangqin Meng, *Prog. Biochem. Biophys.*, 2018, **45**, 218–236.
- K. Fan, J. Xi, L. Fan, P. Wang, C. Zhu, Y. Tang, X. Xu, M. Liang, B. Jiang, X. Yan and L. Gao, *Nat. Commun.*, 2018, **9**, 1440.
- L. Gao, J. Zhuang, L. Nie, J. Zhang, Y. Zhang, N. Gu, T. Wang, J. Feng, D. Yang, S. Perrett and X. Yan, *Nat. Nanotechnol.*, 2007, **2**, 577–583.
- K. Fan, H. Wang, J. Xi, Q. Liu, X. Meng, D. Duan, L. Gao and X. Yan, *Chem. Commun.*, 2017, **53**, 424–427.
- L. Gao, K. Fan and X. Yan, *Theranostics*, 2017, **7**, 3207–3227.
- J. Xie, G. Liu, H. S. Eden, H. Ai and X. Chen, *Acc. Chem. Res.*, 2011, **44**, 883–892.
- K. Ulbrich, K. Hola, V. Subr, A. Bakandritsos, J. Tucek and R. Zboril, *Chem. Rev.*, 2016, **116**, 5338–5431.
- L. L. Dugan, L. L. Tian, K. L. Quick, J. I. Hardt, M. Karimi, C. Brown, S. Loftin, H. Flores, S. M. Moerlein, J. Polich, S. D. Tabbal, J. W. Mink and J. S. Perlmutter, *Ann. Neurol.*, 2014, **76**, 393–402.
- M. Huo, L. Wang, Y. Chen and J. Shi, *Nat. Commun.*, 2017, **8**, 357.
- J. Yao, Y. Cheng, M. Zhou, S. Zhao, S. Lin, X. Wang, J. Wu, S. Li and H. Wei, *Chem. Sci.*, 2018, **9**, 2927–2933.
- Y. Zhang, F. Wang, C. Liu, Z. Wang, L. Kang, Y. Huang, K. Dong, J. Ren and X. Qu, *ACS Nano*, 2018, **112**(1), 651–661.
- D. Zhang, Y. X. Zhao, Y. J. Gao, F. P. Gao, Y. S. Fan, X. J. Li, Z. Y. Duan and H. Wang, *J. Mater. Chem. B*, 2013, **1**, 5100–5107.
- S. Fu, S. Wang, X. Zhang, A. Qi, Z. Liu, X. Yu, C. Chen and L. Li, *Colloids Surf., B*, 2017, **154**, 239–245.
- L. Su, J. Feng, X. Zhou, C. Ren, H. Li and X. Chen, *Anal. Chem.*, 2012, **84**, 5753–5758.
- L. Su, W. Qin, H. Zhang, Z. U. Rahman, C. Ren, S. Ma and X. Chen, *Biosens. Bioelectron.*, 2015, **63**, 384–391.
- N. Chaibakhsh and Z. Moradi-Shoeili, *Mater. Sci. Eng., C*, 2019, **99**, 1424–1447.
- Y. Chen, H. Cao, W. Shi, H. Liu and Y. Huang, *Chem. Commun.*, 2013, **49**, 5013–5015.
- F. Vetr, Z. Moradi-Shoeili and S. Özkar, *Appl. Organomet. Chem.*, 2018, **32**, e4465.
- L. Z. Gao, J. M. Wu, S. Lyle, K. Zehr, L. L. Cao and D. Gao, *J. Phys. Chem. C*, 2008, **112**, 17357–17361.
- W. B. Shi, Q. L. Wang, Y. J. Long, Z. L. Cheng, S. H. Chen, H. Z. Zheng and Y. M. Huang, *Chem. Commun.*, 2011, **47**, 6695–6697.
- X. Niu, Y. Xu, Y. Dong, L. Qi, S. Qi, H. Chen and X. Chen, *J. Alloys Compd.*, 2014, **587**, 74–81.
- W. Wu, Q. He, H. Chen, J. Tang and L. Nie, *Nanotechnology*, 2007, **18**, 145609.
- L. Y. Tong, C. C. Chuang, S. Y. Wu and L. Zuo, *Cancer Lett.*, 2015, **367**, 18–25.
- G. Y. Liou and P. Storz, *Free Radical Res.*, 2010, **44**, 479–496.
- D. Trachootham, J. Alexandre and P. Huang, *Nat. Rev. Drug Discovery*, 2009, **8**, 579–591.
- T. I. Lakshmi Raj, A. U. Gurkar, A. Mandinova, S. L. Schreiber and S. W. Lee, *Nature*, 2011, **475**, 231–234.
- J. S. Zijian Zhou, L. Nie and X. Chen, *Chem. Soc. Rev.*, 2016, **45**, 6597–6626.
- R. Gargallo-Caballero, L. Martin-Garcia, A. Quesada, C. Granados-Miralles, M. Foerster, L. Aballe, R. Bliem, G. S. Parkinson, P. Blaha, J. F. Marco and J. de la Figuera, *J. Chem. Phys.*, 2016, **144**, 094704.
- H. Sun, Y. Zhou, J. Ren and X. Qu, *Angew. Chem., Int. Ed.*, 2018, **57**, 9224–9237.
- J. Dong, L. Song, J. J. Yin, W. He, Y. Wu, N. Gu and Y. Zhang, *ACS Appl. Mater. Interfaces*, 2014, **6**, 1959–1970.
- B. Jiang, L. Yan, J. Zhang, M. Zhou, G. Shi, X. Tian, K. Fan, C. Hao and X. Yan, *ACS Appl. Mater. Interfaces*, 2019, **11**(10), 9747–9755.

