




Cite this: *RSC Adv.*, 2019, 9, 1284

# Hierarchical structured Mn<sub>2</sub>O<sub>3</sub> nanomaterials with excellent electrochemical properties for lithium ion batteries†

Su Meng,<sup>ac</sup> Wenchao Yan,<sup>\*ab</sup> Xiaodi Ma,<sup>a</sup> Deye Sun,<sup>a</sup> Yongcheng Jin <sup>\*a</sup> and Kuang He<sup>\*d</sup>

A series of Mn<sub>2</sub>O<sub>3</sub> nanomaterials with hierarchical porous structures was synthesized using three types of leaves as templates. In addition to their different morphologies, different porous nanostructures were achieved by choosing different leaves. The Mn<sub>2</sub>O<sub>3</sub> nanomaterial prepared by using ginkgo leaves as a template provides a larger pore volume and a higher Brunauer–Emmett–Teller (BET) surface area. At the same time, this material also displays excellent electrochemical performance, that is, the specific capacities are 1274.6 mA h g<sup>-1</sup> after 300 cycles and 381.5 mA h g<sup>-1</sup> at current densities of 300 and 3000 mA g<sup>-1</sup>, respectively.

Received 30th October 2018  
 Accepted 2nd January 2019

DOI: 10.1039/c8ra08985j

[rsc.li/rsc-advances](http://rsc.li/rsc-advances)

## Introduction

Rechargeable Li-ion batteries (LIBs) are one of the most promising power sources for portable devices, next-generation transportation devices, and electric vehicles due to their superior electrochemical performance, such as high energy density, environmental friendliness, and low cost.<sup>1,2</sup> In the last few decades, extensive studies were focused on improving the electrochemical performance of LIBs, and searching for new electrode materials with unique nanostructures. For example, transition metal oxides have been extensively studied as anode materials. It was found that these materials have high theoretical capacity and excellent electrochemical performance, the reason is mainly attributed to their unique nanostructure.<sup>3</sup> Among them, manganese oxide (MnO, Mn<sub>2</sub>O<sub>3</sub>, MnO<sub>2</sub>) has been studied because of its diverse structure, compositional flexibility, and novel physicochemical properties.<sup>3–5</sup> Meanwhile, Mn<sub>2</sub>O<sub>3</sub> is abundant, inexpensive, and environmentally benign, and it can provide a high energy density. Therefore, Mn<sub>2</sub>O<sub>3</sub> is deemed to be a suitable next-generation anode material for LIBs.<sup>6</sup>

To date, Mn<sub>2</sub>O<sub>3</sub> as an anode material had been adopted in many studies; however, it also has many disadvantages, such as

volume expansion and aggregation in the charge/discharge cycles, resulting in rapid capacity fading.<sup>7</sup> As an efficient strategy for reducing the influence of volume expansion, preparing a material with a porous nanostructure is considered to be more beneficial than other methods.<sup>8–11</sup> For example, Chen *et al.* synthesized and evaluated porous double-shelled Mn<sub>2</sub>O<sub>3</sub> with hollow microspheres, they found that the Mn<sub>2</sub>O<sub>3</sub> as an anode material provided a discharge capacity of 471 mA h g<sup>-1</sup> at 3.2C rate after 100 cycles.<sup>12</sup> Tang *et al.* reported the synthesis of porous Mn<sub>2</sub>O<sub>3</sub> nanomaterials by controlling the volume ratio of ethylene glycol and water using the hydrothermal method. After optimization, the prepared Mn<sub>2</sub>O<sub>3</sub> electrode with a porous architecture and thin thickness, it showed a stable capacity of 521 mA h g<sup>-1</sup> after 100 cycles.<sup>13</sup> Previous research results clearly showed that electrode materials with unique nanoscale pore structures can provide excellent electrochemical performance for Li-ion batteries, and these materials need unique synthesis method.

The template method is a simple and convenient route to synthesize porous nanomaterials. Nature offers us a wide variety of biomaterials, such as green plants, flowering plants, proteins, diatoms, and bacteria, all of these materials have different morphologies and porous structures.<sup>14–16</sup> Among them, leaves showed outstanding light-harvesting efficiency owing to the three-dimensional (3D) architecture and porous framework of veins.<sup>17,18</sup> These interesting nanostructures and characteristics have inspired many researchers to synthesize leaf-templated metal oxides, which have been applied as electrode materials and photocatalysts.<sup>17,19–23</sup> For example, porous Co<sub>3</sub>O<sub>4</sub> with a three-dimensional (3D) hierarchical structure showed higher sensing performance between glucose and H<sub>2</sub>O<sub>2</sub> than Co<sub>3</sub>O<sub>4</sub> prepared by using a classical method.<sup>19</sup> Meanwhile, leaves are universal, inexpensive, reproducible, and widely

<sup>a</sup>Center of Materials Science and Optoelectronics Engineering, University of Chinese Academy of Sciences, Beijing 100049, China. E-mail: [jinye@qibebt.ac.cn](mailto:jinye@qibebt.ac.cn)

<sup>b</sup>School of Materials Science & Engineering, Linyi University, Linyi 276000, China

<sup>c</sup>University of Chinese Academy of Science, 19A Yuquanlu Road, Beijing 100049, P. R. China

<sup>d</sup>Institute of Metal Research, Chinese Academy of Sciences, Wenhua Road 72, Shenhe District, Shenyang 110016, China

† Electronic supplementary information (ESI) available. See DOI: 10.1039/c8ra08985j



accessible, which can be applied as abundant biotemplated materials.<sup>19</sup>

In this paper,  $\text{Mn}_2\text{O}_3$  nanomaterials were successfully synthesized *via* a facile bio-templated method using three kinds of leaves as templates. The results showed that as-prepared materials reflected the porous nanostructure and characteristics of the original leaves. The detailed characterization and evaluation of the three kinds of  $\text{Mn}_2\text{O}_3$  nanomaterials showed that the G- $\text{Mn}_2\text{O}_3$  material as anode material delivers a remarkable improved electrochemical performance.

## Results and discussions

A simple synthesis strategy to obtain leaf-templated  $\text{Mn}_2\text{O}_3$  materials is shown in Fig. 1. In order to remove impure elements of leaves, these leaves were pretreated with HCl solution. What we can see after this process is that the colour of Ginkgo leaves changed from yellow to brown, indicated that metal ions in the porphyrins were replaced by  $\text{H}^+$  ions. Then, the treated leaves were soaked in the manganese acetate solution (0.2 M) to absorb  $\text{Mn}^{2+}$  ions and then exchange  $\text{Mn}^{2+}$  ions for  $\text{H}^+$  ions, resulting in the formation of active sites of  $\text{Mn}(\text{CH}_3\text{COO})_2$  in the leaves. Lastly, according to the TG curves as shown in the Fig. S1,<sup>†</sup> the leaves were calcined at 600 °C to remove the original substances and obtain the target material  $\text{Mn}_2\text{O}_3$ .

In order to analyze the phase composition of the prepared materials, the XRD patterns are shown in Fig. 2. Diffraction peaks matching with pure cubic phase of  $\text{Mn}_2\text{O}_3$  (JCPDS no. 41-1442). The diffraction peaks matched well with the diffraction peaks at  $2\theta$  values of 23.1°, 32.9°, 38.2°, 45.2°, 49.3°, 55.2°, 64.1°, 65.8°, and 67.5°, which coincided with the (211), (222), (400), (332), (431), (440), (541), (622), and (631) crystal planes, respectively. No other impurity phase were detected in the spectrum.

The SEM images of different leaves and relative  $\text{Mn}_2\text{O}_3$  materials are displayed in Fig. 3. Morphologies of  $\text{Mn}_2\text{O}_3$  materials prepared by different templates, observing at low magnification, were very similar to those of the epidermis layers of leaves, as shown in Fig. 3. These indicated that the prepared  $\text{Mn}_2\text{O}_3$  materials successfully maintained the morphology of

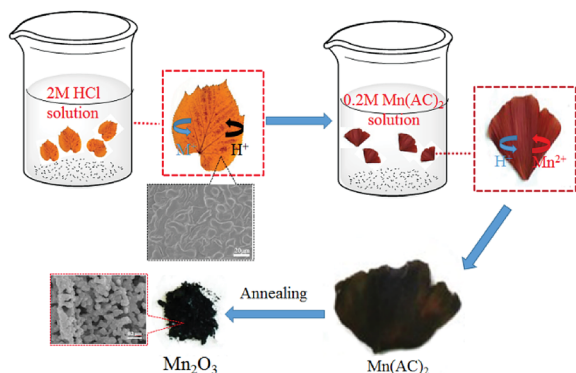


Fig. 1 Synthesis strategy of leaf-temple to obtain  $\text{Mn}_2\text{O}_3$  materials.

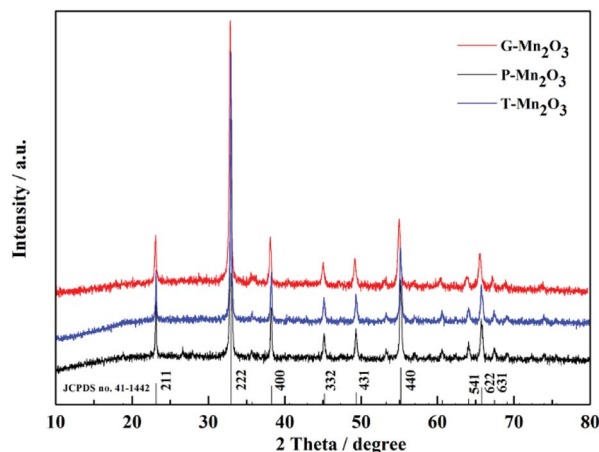


Fig. 2 XRD patterns of as-prepared  $\text{Mn}_2\text{O}_3$  materials.

their respective leaves templates. A deeper study of the microstructure of as-prepared  $\text{Mn}_2\text{O}_3$  materials, all samples displayed a hierarchical structure, as shown in the SEM images (Fig. 4a, c and e). Compared to the prepared products, G- $\text{Mn}_2\text{O}_3$  and T- $\text{Mn}_2\text{O}_3$  materials with hierarchical structures were composed of some interconnected  $\text{Mn}_2\text{O}_3$  nanoparticles about 30–100 nm in size (Fig. 4b and f), the P- $\text{Mn}_2\text{O}_3$  nanoparticles are rod-like shape and particle sizes are approximately 100–300 nm (Fig. 4d). In addition, G- $\text{Mn}_2\text{O}_3$  and P- $\text{Mn}_2\text{O}_3$  had porous framework structures, whereas T- $\text{Mn}_2\text{O}_3$  comprised tightly bound nanoparticles.

As shown in Fig. S2,<sup>†</sup> the TEM images further illustrated detailed structures of prepared materials. TEM images of

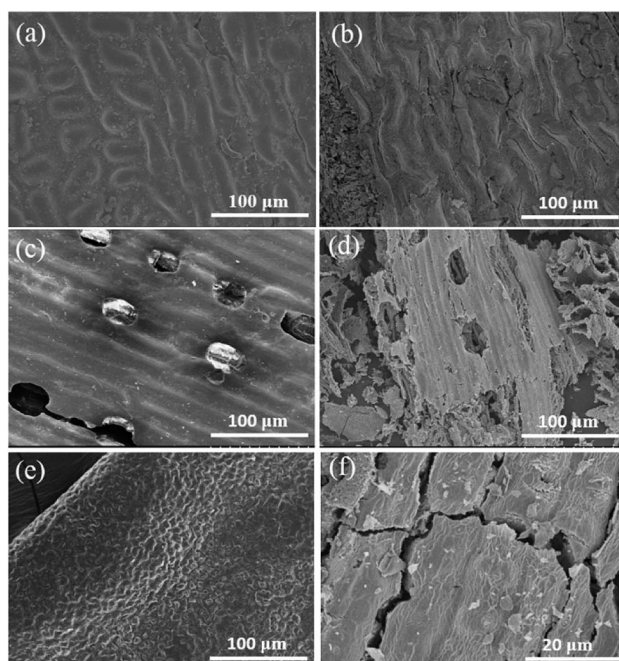


Fig. 3 SEM images of the original ginkgo leaves (a), pine needles (c), tea leaves (e) and  $\text{Mn}_2\text{O}_3$  prepared by ginkgo leaves (b), pine needles (d), tea leaves (f) templates.



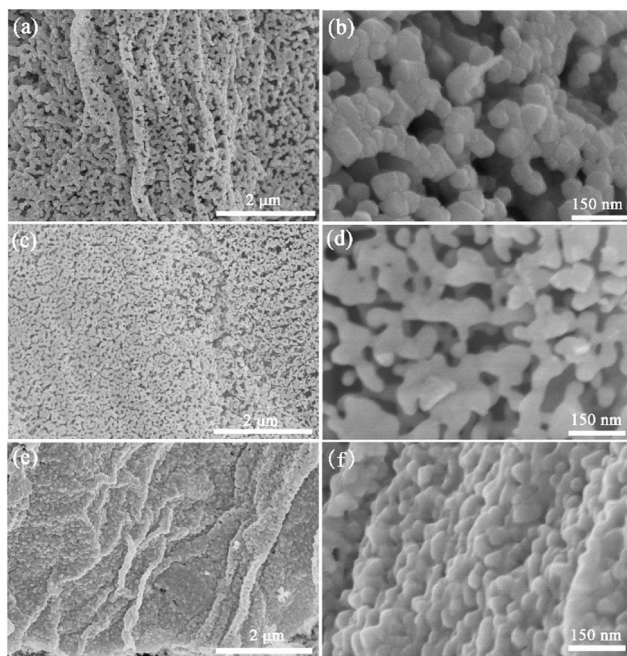


Fig. 4 SEM images of  $\text{Mn}_2\text{O}_3$  prepared by gingko leaves (a and b), pine needles (c and d) and tea leaves (e and f) template.

$\text{Mn}_2\text{O}_3$  materials showed hierarchical structures, where irregular shapes of nanoparticles were connected to each other to form a multilayer network structures. And these images also proved that the formation of porous structures with broad pore-size distributions. The HR-TEM images also showed well-ordered atomic columns, which indicate that the prepared materials had good crystal structures.

To further investigate the pore structures and inner architectures of as-prepared  $\text{Mn}_2\text{O}_3$  materials,  $\text{N}_2$  adsorption-desorption cryosorption are used and relative results are shown in Fig. 5. All of the isotherms exhibited combined characteristics of types I/IV with distinct hysteresis loops, predicting a wide range of pore structures, which was proven by the pore-width distribution (Fig. 5b, d and f).<sup>24</sup> In addition, the G- $\text{Mn}_2\text{O}_3$  material showed the highest BET surface area ( $59.445 \text{ m}^2 \text{ g}^{-1}$ ) and largest pore volume ( $0.067 \text{ cm}^3 \text{ g}^{-1}$ ) (as shown in Table 1). This larger pore volume and higher BET surface area allow better accessibility of the electrolyte, and it would be propitious to the transport of  $\text{Li}^+$  during the cycling process. The BET surface area of T- $\text{Mn}_2\text{O}_3$  higher than that of P- $\text{Mn}_2\text{O}_3$ , but the SEM image showed that the latter had a more abundant pore structure. These contradictory results mainly due to the T- $\text{Mn}_2\text{O}_3$  material had smaller particles, which formed a raised surface between particles and then achieved higher specific surface area.

Fig. 6a–c shows the typical discharge-charge profiles of G- $\text{Mn}_2\text{O}_3$ , P- $\text{Mn}_2\text{O}_3$ , and T- $\text{Mn}_2\text{O}_3$  at a rate of 0.3C. In the first discharge profile, the voltage dropped from 3.0 V to 0.25 V, which was mainly due to the reduction from  $\text{Mn}_2\text{O}_3$  to MnO (Fig. S3a and b†). By degrees then the potential decreased to 0.01 V, which corresponds to the formation of metal Mn and

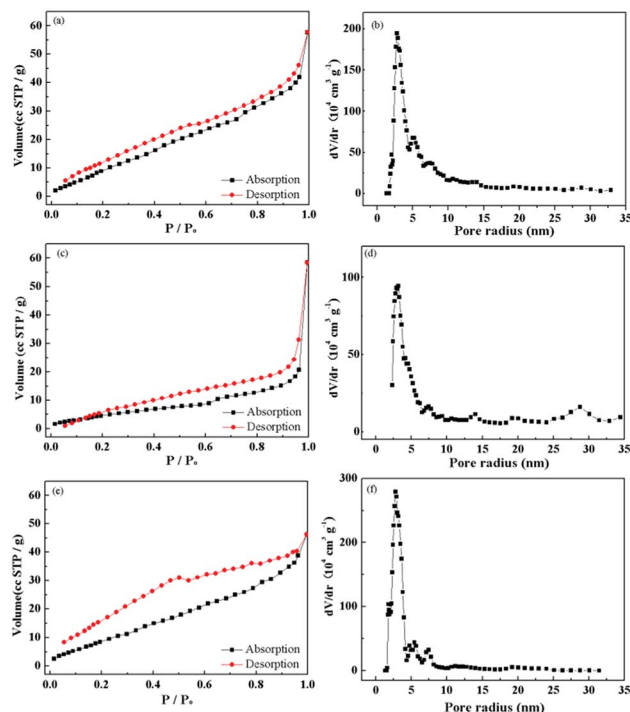


Fig. 5  $\text{N}_2$  adsorption-desorption isotherms of G- $\text{Mn}_2\text{O}_3$  (a), P- $\text{Mn}_2\text{O}_3$  (c) and T- $\text{Mn}_2\text{O}_3$  (e) and the inserted pore size distributions of G- $\text{Mn}_2\text{O}_3$  (b), P- $\text{Mn}_2\text{O}_3$  (d) and T- $\text{Mn}_2\text{O}_3$  (f).

phase transformation reaction with amorphous  $\text{Li}_2\text{O}$  formed (Fig. S3c†).<sup>6,25</sup> The theoretical value of  $\text{Mn}_2\text{O}_3$  is  $1018 \text{ mA h g}^{-1}$ , however, the first discharge capacity is  $1215.7 \text{ mA h g}^{-1}$ , the improved capacity may be attributed to the decomposition of the electrolyte and a gel-like film formed on the surface of materials.<sup>26,27</sup> As shown in Fig. 6d, the discharge capacities of as-prepared  $\text{Mn}_2\text{O}_3$  electrodes showed rapid decrease before 25 cycles, the reason due to irreversible structure transformation and/or side reaction at electrode and electrolyte interface.<sup>6,27</sup> After 25 cycles, the as-prepared materials presented an upward trend at a rate of 0.3C, which ascribed to the slow activation of internal pore structure during cycling, this phenomenon often observes in transition metal oxides.<sup>28–30</sup> However, the discharge capacity of P- $\text{Mn}_2\text{O}_3$  electrode decreases after 150 cycles, which caused by the poor crystallinity, the result is consistent with SEM and TEM images.

Fig. 7a shows representative charge-discharge profiles of the three prepared samples at various current densities. Remarkably, the charge-discharge potential of G- $\text{Mn}_2\text{O}_3$  has a longer

Table 1  $\text{N}_2$  adsorption-desorption data of the various synthesized  $\text{Mn}_2\text{O}_3$  materials

Materials	$S_{\text{BET}}$ ( $\text{m}^2 \text{ g}^{-1}$ )	Pore vol. ( $\text{cm}^3 \text{ g}^{-1}$ )	Pore size (nm)
G- $\text{Mn}_2\text{O}_3$	59.445	0.067	2.769
P- $\text{Mn}_2\text{O}_3$	21.701	0.045	3.169
T- $\text{Mn}_2\text{O}_3$	45.696	0.059	2.769



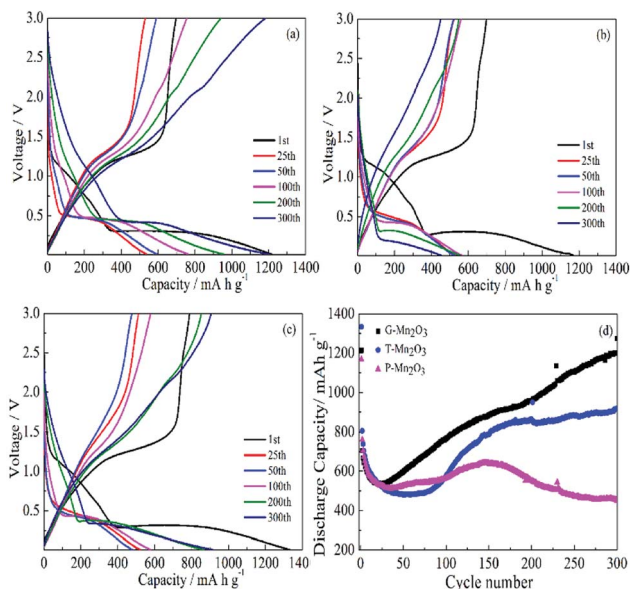


Fig. 6 Typical discharge–charge profiles of G-Mn<sub>2</sub>O<sub>3</sub> (a), P-Mn<sub>2</sub>O<sub>3</sub> (b) and T-Mn<sub>2</sub>O<sub>3</sub> (c) and (d) cycling performance of G-Mn<sub>2</sub>O<sub>3</sub>, P-Mn<sub>2</sub>O<sub>3</sub> and T-Mn<sub>2</sub>O<sub>3</sub> at a current density of 0.3 A g<sup>-1</sup>.

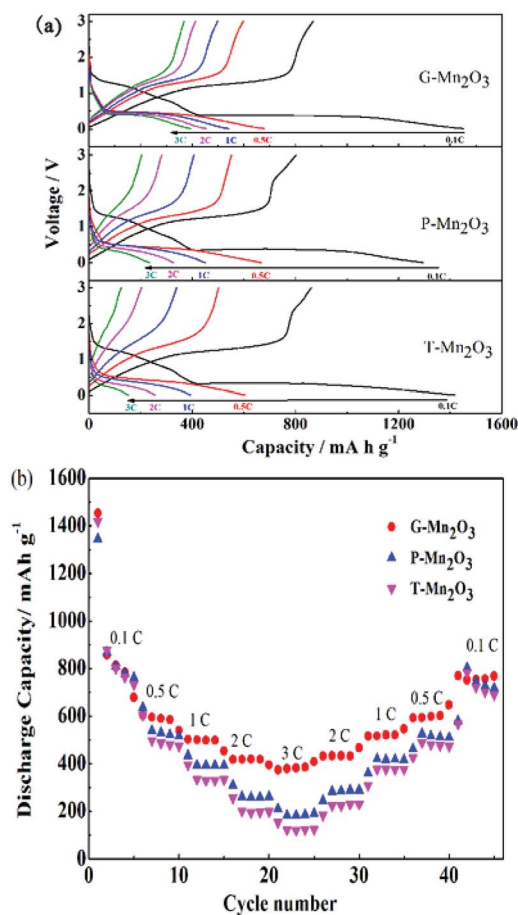


Fig. 7 Typical discharge–charge profiles (a) and (b) rate performance of G-Mn<sub>2</sub>O<sub>3</sub>, P-Mn<sub>2</sub>O<sub>3</sub> and T-Mn<sub>2</sub>O<sub>3</sub> at different current densities.

plateau, indicating a longer Li ion diffusion path even at high rates. Fig. 7b exhibits the rate capabilities of G-Mn<sub>2</sub>O<sub>3</sub>, P-Mn<sub>2</sub>O<sub>3</sub>, and T-Mn<sub>2</sub>O<sub>3</sub> materials at various current densities. With increasing the current densities, the internal polarization of the battery is increased and the interface features also had effect on the discharge capacity. The G-Mn<sub>2</sub>O<sub>3</sub> showed the best electrochemical performance, even at the rate of 3C, the specific capacity can reach 381.5 mA h g<sup>-1</sup>. The reason may be ascribed to the G-Mn<sub>2</sub>O<sub>3</sub> electrode has higher surface area and larger pore volume, which led to an increased effective electrode/electrolyte interface area, thus increasing the rate of Li<sup>+</sup> transport. At the same time, this material has smaller particles with abundant porosity, which not only reduces the diffusion distance of lithium ions but also serves as an electrolyte reservoir to ensure Li<sup>+</sup> diffusion at high rates, resulting in superior rate performance.

For comparison, non-templated Mn(CH<sub>3</sub>COO)<sub>2</sub> was also heated in air at 600 °C for 3 h to obtain powder Mn<sub>2</sub>O<sub>3</sub> with larger nanoparticles (Fig. S4†). Its electrochemical performance is not as good as that of G-Mn<sub>2</sub>O<sub>3</sub> anode material, which was synthesized by the leaf-templated method. The discharge capacity was 427.6 mA h g<sup>-1</sup> after 100 cycle at 0.3C and 220.7 mA h g<sup>-1</sup> at rate of 3C (Fig. S5†). The obvious difference demonstrated leaf-templated method can keep the morphology of the leaf and control the growth of primary particles. The electrochemical properties of Mn<sub>2</sub>O<sub>3</sub> anode material in this work and published literature are compared in Table S1,† the results showed that the material prepared in this work have superior properties.

In order to study the interface characteristics of G-Mn<sub>2</sub>O<sub>3</sub>, the EIS tests were also applied. Fig. 8 shows the Nyquist plot of G-Mn<sub>2</sub>O<sub>3</sub> at the discharge state (0.01 V) after cycling at 0.3C in the 1st, 100th, 200th, and 300th cycles, the related parameters as shown in Table S2.† All curves of G-Mn<sub>2</sub>O<sub>3</sub> electrode showed a semicircle and a straight line, which are corresponding to high and low frequency regions. The diameter of the semicircle represents the charge transfer resistance ( $R_{ct}$ ). Upon cycling, the

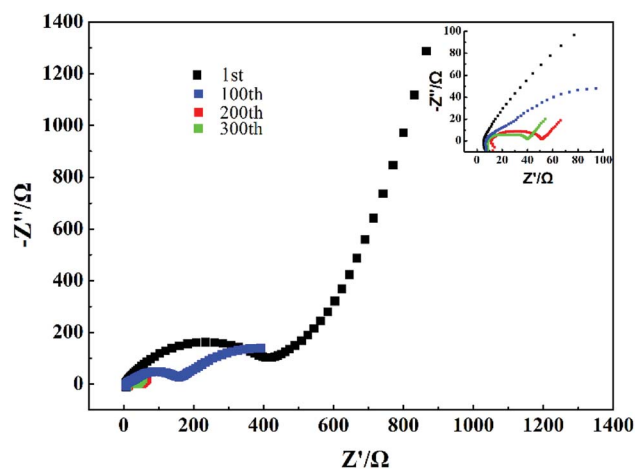


Fig. 8 Nyquist plots of G-Mn<sub>2</sub>O<sub>3</sub> were performed after cycling at 0.3C in the 1st, 100th, 200th and 300th.



charge-transfer resistance decreased gradually, which could partially explain the observed capacity increasing on cycling.<sup>31,32</sup>

In addition, the diameter of the semicircle obtained in the Nyquist plot for the G-Mn<sub>2</sub>O<sub>3</sub> electrode was clearly smaller than that of the other electrodes when measured at a discharge potential of 0.01 V in the 300th cycle, as shown in Fig. S6.† This low impedance of G-Mn<sub>2</sub>O<sub>3</sub> electrode owing to large surface area and abundant porous structure, which shortened the Li<sup>+</sup> diffusion distance and enhanced the reaction kinetics, resulted in superior rate capability and cycle performance.<sup>33</sup>

## Conclusions

Mn<sub>2</sub>O<sub>3</sub> materials with porous hierarchical structure were synthesized *via* a facile leaf-templated method and calcination process. The obtained Mn<sub>2</sub>O<sub>3</sub> materials with different morphologies were studied as anode materials for LIBs. Among as-prepared Mn<sub>2</sub>O<sub>3</sub> materials, the G-Mn<sub>2</sub>O<sub>3</sub> exhibited better cycling retention and higher discharge capacity of 1274.6 mA h g<sup>-1</sup> at 0.3C after 300 cycles. The G-Mn<sub>2</sub>O<sub>3</sub> electrode also showed the best rate performance: a specific discharge capacity of 381.5 mA h g<sup>-1</sup> at 3C. We believe that porous hierarchical structure with a large surface area and abundant pore structure may provide more active sites, which shortened the Li<sup>+</sup> diffusion distance and decreased interfacial contact resistance, resulting in superior electrochemical properties.

## Experimental

### Materials synthesis

Ginkgo leaves, pine needles, and tea leaves were immersed with a 2 M hydrochloric acid solution for 24 h. Then the leaves were washed for several times and subsequently dried at 80 °C for 5 h. The leaves (0.5 g) were then immersed in a Mn(CH<sub>3</sub>COO)<sub>2</sub> solution (0.2 M, 50 mL) with stirring for 24 h at 25 °C. After being filtered and then dried at 100 °C, the leaves were calcined at 600 °C for 3 h in air and cooled naturally to 25 °C. The prepared powders using ginkgo leaves, pine needles, and tea leaves as templates were labelled as G-Mn<sub>2</sub>O<sub>3</sub>, P-Mn<sub>2</sub>O<sub>3</sub>, and T-Mn<sub>2</sub>O<sub>3</sub>, respectively. For comparison, Mn<sub>2</sub>O<sub>3</sub> nanoparticles was synthesized at the same starting materials by non-templated method.

### Structure characterization

The Bruker AXS D8 X-ray diffractometer with Cu K<sub>α</sub> radiation was used to study the crystal structure of Mn<sub>2</sub>O<sub>3</sub> materials. The morphology and nanostructure of Mn<sub>2</sub>O<sub>3</sub> materials were evaluated by Hitachi S-4800 field emission scanning electron microscope (FE-SEM) and transmission electron microscopy (TEM). In order to evaluate the pore structure and surface areas of Mn<sub>2</sub>O<sub>3</sub> materials, nitrogen adsorption-desorption isotherms at 77 K *via* the Brunauer-Emmett-Teller (BET) method.

### Electrochemical evaluation

Mixed anode electrodes with copper foil as current collector were mixed using the prepared materials as the active material,

conductive carbon (super-P), and polyvinylidene fluoride (PVDF) binder (60 : 30 : 10 wt%) in *N*-methyl-2-pyrrolidone (NMP). The average areal density of Mn<sub>2</sub>O<sub>3</sub> electrodes is 1.8 mg cm<sup>-2</sup> for each cell. Li metal as counter electrode, Celgard 2500 as separator, and 1 M LiPF<sub>6</sub> dissolved in mixture of EC/DEC/DMC (1 : 1 : 1 vol%) as the electrolyte.

The LAND-2010 automatic battery tester was used to evaluate the electrochemical performance at different current densities from 0.1C to 3C (1C = 1000 mA g<sup>-1</sup>) between 0.01–3.0 V. The cyclic voltammograms (CV) were carried on a CHI660E electrochemical workstation at the scan rate of 0.2 mV s<sup>-1</sup> in the voltage range of 0.01 to 3.0 V. Electrochemical impedance spectroscopy (EIS) was studied by an electrochemical station (CHI 660) in the frequency between 100 kHz and 0.1 Hz with 5 mV amplitude.

## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

The authors appreciate the financial support of “YZ201641” and “ZR2017BEM044”.

## Notes and references

- 1 P. G. Bruce, B. Scrosati and J. M. Tarascon, *Angew. Chem., Int. Ed.*, 2008, **47**, 2930–2946.
- 2 G. Ceder, Y. M. Chiang, D. R. Sadoway, M. K. Aydinol, Y. I. Jang and B. Huang, *Nature*, 1998, **392**, 694–696.
- 3 Y. Dai, H. Jiang, Y. Hu and C. Li, *RSC Adv.*, 2013, **3**, 19778–19781.
- 4 Y. J. Zhang, Y. Yan, X. Y. Wang, G. Li, D. R. Deng, L. Jiang, C. Y. Shu and C. R. Wang, *Chem. - Eur. J.*, 2014, **20**, 6126–6130.
- 5 M. W. Xu, Y. B. Niu, S. J. Bao and C. M. Li, *J. Mater. Chem. A*, 2014, **2**, 3749.
- 6 Y. Qiu, G. L. Xu, K. Yan, H. Sun, J. Xiao, S. Yang, S. G. Sun, L. Jin and H. Deng, *J. Mater. Chem.*, 2011, **21**, 6346–6353.
- 7 C. X. Guo, M. Wang, T. Chen, X. W. Lou and C. M. Li, *Adv. Energy Mater.*, 2011, **1**, 736–741.
- 8 Y. C. Zhang, J. T. Li, Z. G. Wu, L. Huang and S. G. Sun, *J. Alloys Compd.*, 2017, **721**, 229–235.
- 9 J. Xu, Y. Sun, M. Lu, L. Wang, J. Zhang, J. Qian and E. J. Kim, *J. Alloys Compd.*, 2017, **717**, 108–115.
- 10 P. Wu, D. Wang, J. Ning, J. Zhang, X. Feng, J. Dong and Y. Hao, *J. Alloys Compd.*, 2018, **731**, 1063–1068.
- 11 M. Pudukudy, Z. Yaakob and R. Rajendran, *Mater. Lett.*, 2014, **136**, 85–89.
- 12 Y. Qiao, Y. Yu, Y. Jin, Y. B. Guan and C. H. Chen, *Electrochim. Acta*, 2014, **132**, 323–331.
- 13 X. Zhang, Y. T. Qian, Y. C. Zhu and K. B. Tang, *Nanoscale*, 2014, **6**, 1725–1731.
- 14 E. Katz and I. Willner, *Angew. Chem., Int. Ed.*, 2004, **43**, 6042–6108.
- 15 L. Berti and G. A. Burley, *Nat. Nanotechnol.*, 2008, **3**, 81–87.



- 16 S. Sotiropoulou, Y. S. Sastre, S. S. Mark and C. A. Batt, *Chem. Mater.*, 2008, **20**, 821–834.
- 17 H. Zhou, X. Li, T. Fan, F. E. Osterloh, J. Ding, E. M. Sabio, D. Zhang and Q. Guo, *Adv. Mater.*, 2010, **22**, 951–956.
- 18 E. Shimoni, O. R. Hon, I. Ohad, V. Brumfeld and Z. Reich, *Plant Cell*, 2005, **17**, 2580–2586.
- 19 L. Han, D. P. Yang and A. Liu, *Biosens. Bioelectron.*, 2015, **63**, 145–152.
- 20 X. Li, T. Fan, H. Zhou, S. K. Chow, W. Zhang, D. Zhang, Q. Guo and H. Ogawa, *Adv. Funct. Mater.*, 2009, **19**, 45–56.
- 21 Z. Schnepp, W. Yang, M. Antonietti and C. Giordano, *Angew. Chem., Int. Ed.*, 2010, **122**, 6714–6716.
- 22 S. Zhu, D. Zhang, Z. Chen, G. Zhou, H. Jiang and J. Li, *J. Nanopart. Res.*, 2010, **12**, 2445–2456.
- 23 X. Li, T. Fan, Z. Liu, J. Ding, Q. Guo and D. Zhang, *J. Eur. Ceram. Soc.*, 2006, **26**, 3657–3664.
- 24 C. Zhao, C. Yu, M. Zhang, J. Yang, S. Liu, M. Li, X. Han, Y. Dong and J. Qiu, *J. Mater. Chem. A*, 2015, **3**, 21842–21848.
- 25 Y. Deng, Z. Li, Z. Shi, H. Xu, F. Peng and G. Chen, *RSC Adv.*, 2012, **2**, 4645–4647.
- 26 Y. Ren, A. R. Armstrong, F. Jiao and P. G. Bruce, *J. Am. Chem. Soc.*, 2010, **132**, 996–1004.
- 27 L. Zhou, H. B. Wu, T. Zhu and X. W. Lou, *J. Mater. Chem.*, 2012, **22**, 827–829.
- 28 R. Liu, S. Zhao, M. Zhang, F. Feng and Q. Shen, *Chem. Commun.*, 2015, **51**, 5728.
- 29 K. Li, F. Shua, X. Guo and D. Xue, *CrystEngComm*, 2015, **17**, 5094–5100.
- 30 H. B. Lin, H. B. Rong, W. Z. Huang, Y. H. Liao, L. D. Xing, M. Q. Xu, X. P. Li and W. S. Li, *J. Mater. Chem. A*, 2014, **2**, 14189.
- 31 W. Duan, W. Yan, X. Yan, H. Munakata, Y. Jin and K. Kanamura, *J. Power Sources*, 2015, **293**, 706–711.
- 32 D. Li, X. Li, X. Hou, X. Sun, B. Liu and D. He, *Chem. Commun.*, 2014, **50**, 9361–9364.
- 33 X. Xu, R. Cao, S. Jeong and J. Cho, *Nano Lett.*, 2012, **12**, 4988–4991.

