





Cite this: *RSC Adv.*, 2019, 9, 4001

Colloidal $\text{Cd}_x\text{Zn}_{1-x}\text{S}$ nanocrystals as efficient photocatalysts for H_2 production under visible-light irradiation†

JingJing Xiang, Hanbin Wang, * Xina Wang, Xu Chen, Tianci Wu, Houzhao Wan, Yongzheng Liu and Hao Wang *

$\text{Cd}_x\text{Zn}_{1-x}\text{S}$ nanocrystals with sizes ranging from 3–11 nm were synthesized by a simple organic solution method. The nanocrystals possess a cubic zinc-blende structure and the bandgap blue-shifts from 2.1 eV to 3.4 eV by increasing the composition of Zn ions in the solid solutions. After a facile ligand exchange process, the photocatalytic activity for H_2 production of the $\text{Cd}_x\text{Zn}_{1-x}\text{S}$ nanocrystals was investigated under visible-light irradiation ($\lambda \geq 420$ nm) with $\text{Na}_2\text{SO}_3/\text{Na}_2\text{S}$ as the electron donor. It was found that the $\text{Cd}_{0.8}\text{Zn}_{0.2}\text{S}$ had the highest photoactivity with H_2 evolution rate of $6.32 \text{ mmol g}^{-1} \text{ h}^{-1}$. By *in situ* adding Pt precursors into the reaction solution, inhomogeneous Pt– $\text{Cd}_x\text{Zn}_{1-x}\text{S}$ nanoheterostructures were formed, which accounted for a 30% enhancement for the H_2 evolution rate comparing with that of pure $\text{Cd}_{0.8}\text{Zn}_{0.2}\text{S}$ nanocrystals. This work highlights the use of facile organic synthesis in combination with suitable surface modification to enhance the activity of the photocatalysts.

Received 15th November 2018

Accepted 17th January 2019

DOI: 10.1039/c8ra09408j

rsc.li/rsc-advances

Introduction

Hydrogen, as a clean and renewable fuel, occupies an important position in the research of future energy. The mass production of hydrogen by traditional steam reforming process is uneconomical and nonrenewable while photocatalytic water splitting methods have shown great potential for the production of hydrogen in a clean, sustainable and economic manner.^{1–3} To make full use of solar energy, numerous visible-light-driven photocatalysts have been developed among which CdS has attracted intensive study. However, CdS always suffers from photocorrosion in catalytic reactions and alloying CdS with other metal sulfides such as ZnS, In_2S_3 and MnS is effective to enhance its activity as well as stability.^{4–7} In this regard, $\text{Cd}_x\text{Zn}_{1-x}\text{S}$ solid solutions have been extensively studied due to their controllable band structure and better activity.^{8,9} So far, $\text{Cd}_x\text{Zn}_{1-x}\text{S}$ nanostructures with various morphologies and structures were synthesized and high photoactivity was obtained in solid solutions with special compositions. For example, volvox-like $\text{Cd}_x\text{Zn}_{1-x}\text{S}$ was synthesized through a template-free ethylene glycol process and $\text{Cd}_{0.57}\text{Zn}_{0.43}\text{S}$ nanospheres showed the highest activity with a hydrogen production rate of $1.76 \text{ mmol g}^{-1} \text{ h}^{-1}$.¹⁰ A hybrid structure of $\text{Cd}_{0.5}\text{Zn}_{0.5}\text{S}$ quantum dots on 2D graphitic carbon nitride were synthesized by an *in situ* growth

hydrothermal method. The composites exhibited the highest H_2 generation rate of $33.41 \text{ mmol g}^{-1} \text{ h}^{-1}$ under visible irradiation.¹¹ The graphene–ZnCdS composites were prepared by hydrothermal method and the highest H_2 production value of $1.06 \text{ mmol g}^{-1} \text{ h}^{-1}$ was achieved on 0.5 wt% graphene loaded $\text{Zn}_{0.5}\text{Cd}_{0.5}\text{S}$ sample.¹² $\text{Zn}_{0.5}\text{Cd}_{0.5}\text{S}$ solid solutions with zinc blende/wurtzite (ZB/WZ) twin-induced crystal structure were reported by some groups and the type-II staggered band alignment between the ZB and WZ segments greatly improved the charge separation process in hydrogen production.^{13–15}

There have been many reports on $\text{Cd}_{1-x}\text{Zn}_x\text{S}$ solid solutions for photocatalytic H_2 production under visible-light irradiation. In most previous work, the synthetic protocols often involved with solvothermal and hydrothermal methods. On the other hand, the organic solution synthesis (including hot injection method) has emerged as a potential route for efficient photocatalysts. The high temperature synthesis in the chelating reagents favors the formation of crystals with good crystallinity and well-controlled size, two of which are critical factors determining the photoactivity of the catalysts. There still limit reports on the organic solution route for high-efficient photocatalysts. For example, monodisperse $\text{Cu}_2\text{ZnSnS}_4$ nanoparticles were fabricated by a colloidal method and after Pt loading the Pt– $\text{Cu}_2\text{ZnSnS}_4$ nanoheterostructures showed the highest H_2 evolution rate of $1.02 \text{ mmol g}^{-1} \text{ h}^{-1}$.¹⁶ The CuGaS_2 –ZnS heterostructures were synthesized by an organic solution route, and after surface modification the rate of hydrogen production was measured to be $750 \mu\text{mol g}^{-1} \text{ h}^{-1}$ under visible light.¹⁷ In most of the organic synthesis, the photocatalysts suffered from low yield and complicated operation, and these

Hubei Collaborative Innovation Center for Advanced Organic Chemical Materials, Faculty of Physics and Electronic Science, Hubei University, Wuhan, 430062, China. E-mail: 123272314@qq.com; nanoguy@126.com

† Electronic supplementary information (ESI) available. See DOI: 10.1039/c8ra09408j



drawbacks should be fully addressed to extend their capability in the exploit of green energy materials.

In the present work, a convenient organic solution method was employed to synthesize zinc-blende structured $\text{Cd}_{1-x}\text{Zn}_x\text{S}$ nanocrystals (NCs) with size ranging from 3 nm to 11 nm. The bandgap of $\text{Cd}_{1-x}\text{Zn}_x\text{S}$ solid solutions was easily tuned by changing their composition and the photocatalytic activity of the nanocrystals was investigated after a ligand exchanging process. It was shown that the $\text{Cd}_{0.8}\text{Zn}_{0.2}\text{S}$ sample possessed the highest activity with H_2 production rate of $6.32 \text{ mmol g}^{-1} \text{ h}^{-1}$. After directly reducing 2 wt% Pt precursors in the reaction solution, inhomogeneous Pt- $\text{Cd}_{0.8}\text{Zn}_{0.2}\text{S}$ nanoheterostructures were formed, which accounted for 30% enhancement for the H_2 evolution rate comparing with that of pure $\text{Cd}_{0.8}\text{Zn}_{0.2}\text{S}$ NCs. The work highlights the use of facile organic synthesis cooperated with suitable surface modification to hence the activity of the semiconductors.

Experimental

Synthetic procedures

Firstly, a certain amount of $\text{Cd}(\text{CH}_3\text{COO})_2$ and $\text{Zn}(\text{CH}_3\text{COO})_2$ was dissolved in 30 mL oleylamine in a 100 mL three-necked flask. The molar ratio of Cd : Zn was tuned by changing the amount of $\text{Cd}(\text{CH}_3\text{COO})_2$ and $\text{Zn}(\text{CH}_3\text{COO})_2$ while the total molar of Cd + Zn precursors remained constant. The mixed solution was magnetically stirred and heated to 140°C under the protection of N_2 , then 10 mL of 0.4 M sulfur solution in oleylamine was poured into the $\text{Cd}(\text{CH}_3\text{COO})_2 + \text{Zn}(\text{CH}_3\text{COO})_2$ solution. The mixture was heated from 140°C to 280°C for 1 h with heating rate of 5°C min^{-1} . After the reaction, $\text{Cd}_x\text{Zn}_{1-x}\text{S}$ nanocrystals were formed and cooled to room temperature. The precipitates were washed with 50 mL of ethanol for three times to remove the redundant oleylamine and by-products. The yellow or orange products were dispersed in hexane. For the preparation of Pt- $\text{Cd}_x\text{Zn}_{1-x}\text{S}$ nanoheterostructures, a small quantity of $\text{Pt}(\text{acac})_2$ was added into the $\text{Cd}_x\text{Zn}_{1-x}\text{S}$ solution in oleylamine at 140°C and heated to 280°C again for 30 min. The products were cleaned following the washing process of $\text{Cd}_x\text{Zn}_{1-x}\text{S}$.

Ligand exchange procedure

The above nanocrystals should be dissolved in water for photocatalytic H_2 production. The hydrophobic surface of particles is converted to hydrophilic surface by a simple ligand exchange procedure. In detail, 15 mL of $\text{Cd}_x\text{Zn}_{1-x}\text{S}/\text{Pt}-\text{Cd}_x\text{Zn}_{1-x}\text{S}$ solutions in hexane were adding 10 mL 3-MPA and the mixture was stirred for 10 hours. Ligand exchange was completed as yellow particles were transferred from dispersing in hexane to dispersing in water. After the upper hexane was removed the nanocrystals were precipitated by centrifugation at 3000 rpm and further washed with alcohol for two times and with deionised water for one time. The final products were dried at 70°C for 2 h in a vacuum oven.

Photocatalytic H_2 generation and EIS measurements

For the photocatalytic experiments, 50 mg of $\text{Cd}_x\text{Zn}_{1-x}\text{S}$ powder was dispersed in 100 mL of deionised water, with 0.25 M Na_2S

and 0.35 M Na_2SO_3 as hole scavengers. A 300 W halogen lamp with a cutoff filter ($>420 \text{ nm}$, Newport) was used to irradiate the samples. Photocatalytic reaction was conducted in a quartz reactor under continuous magnetic stirring (1500 rpm) during light irradiation. The irradiation intensity was measured to be 300 mW cm^{-2} by optical power meter at 20°C . The amount of evolved hydrogen was analysed by online gas chromatograph (GC-2014C, Shimadzu, TCD and 5 \AA molecular sieve column). The electrochemical impedance spectroscopy (EIS) measurements were conducted by electrochemical analyzer. The working electrode were made by blade-coating the photocatalysts onto FTO substrates and sintering at 400°C for 30 min. A platinum sheet was used as the counter electrode while an Ag/AgCl electrode as reference in a standard three-electrode system. The EIS data were analysed with Zview software. The EIS frequency ranged from 0.1 to 100 000 Hz, and the alternating current signal amplitude was 10 mV.

Characterization techniques

The structural and composition characterizations of the $\text{Cd}_x\text{Zn}_{1-x}\text{S}$ NCs were analysed by transmission electron microscopy (TEM, JEM-2100F) equipped with energy dispersive spectroscopy (EDS). Elemental analysis was also carried out on an X-ray fluorescence spectrum (XRF, XRF1800). The phase of the $\text{Cd}_x\text{Zn}_{1-x}\text{S}$ solid solutions was identified by X-ray diffraction (XRD, Bruker D8) with Cu $K\alpha 1$ radiation. The UV-Vis absorption spectra of the samples were recorded by UV-Vis spectrophotometer (UV-3600, Shimadzu). BET specific surface areas were measured through the nitrogen adsorption-desorption isotherms on a micrometrics ASAP 2020 M apparatus.

Results and discussion

Crystalline phase and structures

Fig. 1 shows the XRD patterns of as-synthesized $\text{Cd}_x\text{Zn}_{1-x}\text{S}$ photocatalysts. All the samples are identified as cubic zinc-blende phase, of which the three main diffraction peaks, such as (111), (220) and (311) are observed. The diffraction peaks of $\text{Cd}_x\text{Zn}_{1-x}\text{S}$ photocatalysts shift to lower angles as the value of x increase, indicating the formation of single-phase $\text{Cd}_x\text{Zn}_{1-x}\text{S}$ solid solutions. The average nanocrystal size was ranging from 3.8–12.2 nm according to the Debye-Scherrer equation, indicating that the oleylamine provided a strong coordinate environment to restrict the crystal growth of $\text{Cd}_x\text{Zn}_{1-x}\text{S}$. The bonding characteristics of the $\text{Cd}_x\text{Zn}_{1-x}\text{S}$ NCs were characterized by X-ray photoelectron spectroscopy (XPS). Fig. S1† shows the XPS spectra of the Zn 2p $_{3/2}$ and Cd 3d $_{5/2}$ peaks located at 1021.6 eV and 404.5 eV respectively, indicating that Zn and Cd ions exist in the 2+ formal oxidation state in a S^{2-} surrounding environment.¹⁸

The microstructures of the nanocrystals were analyzed by STEM with high-angle annular dark field (HAADF) mode. It's known that in HAADF image, the heavy elements show brighter contrast compared with the light elements due to different Z contrast. Such advantages help to distinguish noble metal cocatalysts onto the $\text{Cd}_x\text{Zn}_{1-x}\text{S}$ NCs and additionally, provide



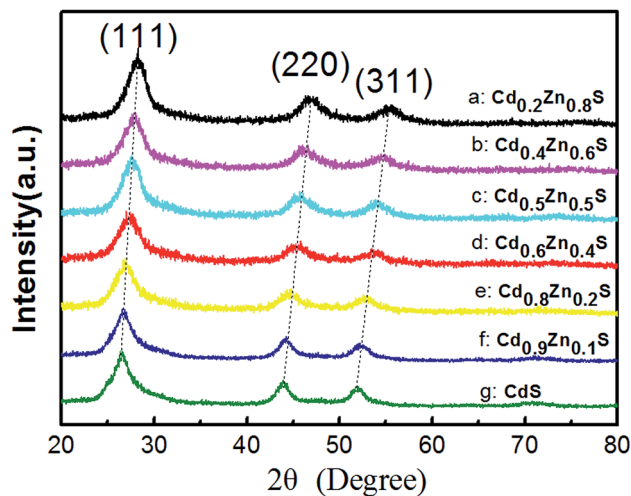


Fig. 1 XRD patterns of as-synthesized $\text{Cd}_x\text{Zn}_{1-x}\text{S}$ nanocrystals.

higher contrast between the $\text{Cd}_x\text{Zn}_{1-x}\text{S}$ NCs and carbon film. The HAADF image of pure $\text{Cd}_x\text{Zn}_{1-x}\text{S}$ NCs was shown in Fig. 2a. Single-crystalline $\text{Cd}_x\text{Zn}_{1-x}\text{S}$ particles with size between 3 nm to 11 nm were well-dispersed on carbon film. The HRTEM images of several $\text{Cd}_x\text{Zn}_{1-x}\text{S}$ nanoparticles are shown in Fig. 2b. The clear lattice fringe of the single particles reveals the good crystallization of the samples. The labeled inter-fringe distance is measured to be 0.323 nm and 0.197 nm, respectively, matching well with the (111) and (2-20) lattice spacing of $\text{Cd}_x\text{Zn}_{1-x}\text{S}$ solid solution with cubic phase. The composition of the $\text{Cd}_x\text{Zn}_{1-x}\text{S}$ samples was analyzed by EDS and XRF and in comparison with the stoichiometric ratio of the precursors. As listed by Table 1, the Cd/Zn ratio determined by EDS are slightly lower than those

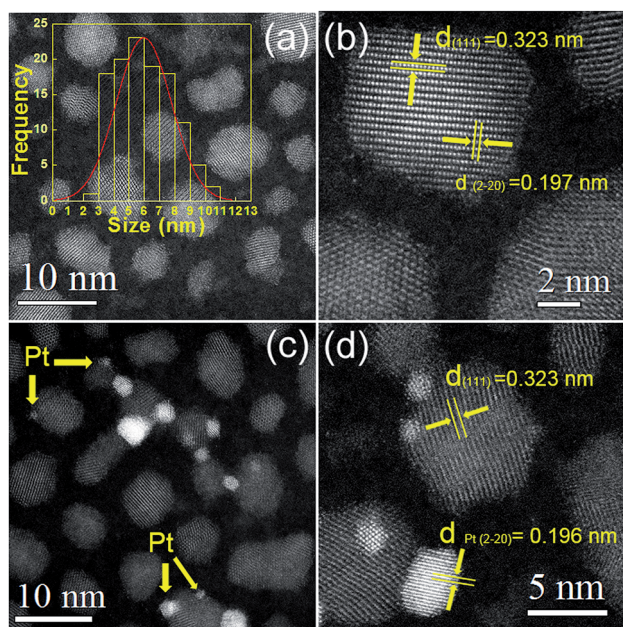


Fig. 2 (a) and (b) STEM images of the $\text{Cd}_{0.8}\text{Zn}_{0.2}\text{S}$ nanocrystals, (c) and (d) STEM images of the 2 wt% Pt- $\text{Cd}_{0.8}\text{Zn}_{0.2}\text{S}$ nanocrystals. Inset of (a) particle size distribution of the $\text{Cd}_{0.8}\text{Zn}_{0.2}\text{S}$ nanocrystals.

of precursors, while the Cd : Zn ratio determined by XRF were more close to their stoichiometric composition. There exists slight deviation between the bulk elemental composition (XRF) and surface elemental composition (EDX). Besides of the measuring error of the instruments, such deviation may be associated with the formation mechanism of the $\text{Cd}_x\text{Zn}_{1-x}\text{S}$ nanocrystals. It was inferred that in organic solvents the Cd-rich cores were initially formed due to higher reactivity of Cd than Zn toward S. Then the Zn-rich outer layers were gradual formed on the Cd-rich core because of the rapid depletion of the Cd concentration in the reaction medium.^{19,20} Such formation mechanisms lead to the excess of Zn in the exterior of the $\text{Cd}_x\text{Zn}_{1-x}\text{S}$. Since EDX technology tends to obtain surface elemental composition of the materials, the ratio of Cd : Zn by EDX measurement is reasonably lower than the stoichiometric ratio.

The HAADF images of the 2 wt% Pt- $\text{Cd}_x\text{Zn}_{1-x}\text{S}$ were also presented in Fig. 2. It's interesting to observe inhomogeneous metal-semiconductor heterostructures among many bare $\text{Cd}_x\text{Zn}_{1-x}\text{S}$ NCs. As shown by Fig. 2c and d, Pt nanoparticles with size between 1 to 5 nm attached tightly with bigger $\text{Cd}_x\text{Zn}_{1-x}\text{S}$ particles, forming typical metal-semiconductor heterostructures. Such architectures are different from those fabricated by two step colloidal approaches,²¹ implying inhomogeneous deposition of Pt atoms on the $\text{Cd}_x\text{Zn}_{1-x}\text{S}$ surface with high surface energy. The Pt nanoparticles in the heterostructures have larger size compared with those fabricated by photoreduction methods. Traditional photoreduction of H_2PtCl_6 could result small Pt nanoparticles or clusters on photocatalysts. However, the loose interface by chemical adsorption may create a space barrier between Pt and semiconductors, which hinders the directional migration of electrons between them. In contrast, the separation the photogenerated carriers would be more efficient in nano-heterostructures due to the tightly bonded metal-semiconductor interface.¹⁶ It should note that our experiments adopted a convenient procedure to form Pt- $\text{Cd}_x\text{Zn}_{1-x}\text{S}$ heterostructures and such synthetic protocols might benefit to yield hetero-structured photocatalysts in a cheap and simple way.


The diffuse UV-visible absorption spectra of $\text{Cd}_x\text{Zn}_{1-x}\text{S}$ photocatalysts were plotted in Fig. 3. The absorption edges of the as-synthesized $\text{Cd}_x\text{Zn}_{1-x}\text{S}$ photocatalysts obviously red-shifted as the ratio of Cd/Zn increased, indicated the atomic level incorporation between CdS and ZnS components. Tauc equation was used to estimate the band gap of the samples by plotting $(\alpha h\nu)^2$ as a function of $h\nu$.²² The bandgap pure CdS and ZnS nanocrystals were calculated to be 2.10 eV and 3.4 eV, respectively, being consistent with those fabricated by solvothermal or hydrothermal methods.^{10,23} As will be shown in following part, the optimal photoactivity of the solid solutions was achieved on sample $\text{Cd}_{0.8}\text{Zn}_{0.2}\text{S}$ with bandgap of 2.43 eV, suggesting that it possessed optimized conduction band level and band gap among the samples.

The BET surface area of the $\text{Cd}_x\text{Zn}_{1-x}\text{S}$ NCs after ligand exchange were measured by nitrogen adsorption-desorption method. As given in Table 1, the surface areas of the nanocrystals were in the range of 89.5–122.5 $\text{m}^2 \text{g}^{-1}$, with the



Table 1 XRF, EDS and BET results of the Cd_xZn_{1-x}S nanocrystals

| Sample | Precursor composition of Cd _x Zn _{1-x} S | Cd/Zn atomic ration | | BET surface area (m ² g ⁻¹) |
|--------|--|---------------------|-----------|--|
| | | XRF ratio | EDS ratio | |
| a | Cd _{0.2} Zn _{0.8} S | 1.86 : 8.14 | 1.9 : 8.1 | 89.5 |
| b | Cd _{0.4} Zn _{0.6} S | 3.77 : 6.23 | 3.9 : 6.1 | 95.8 |
| c | Cd _{0.5} Zn _{0.5} S | 4.91 : 5.09 | 4.8 : 5.2 | 113.3 |
| d | Cd _{0.6} Zn _{0.4} S | 6.31 : 3.69 | 5.6 : 4.4 | 109.0 |
| e | Cd _{0.8} Zn _{0.2} S | 8.34 : 1.64 | 7.3 : 2.7 | 122.5 |
| f | Cd _{0.9} Zn _{0.1} S | 9.20 : 0.80 | 8.7 : 1.3 | 115.7 |



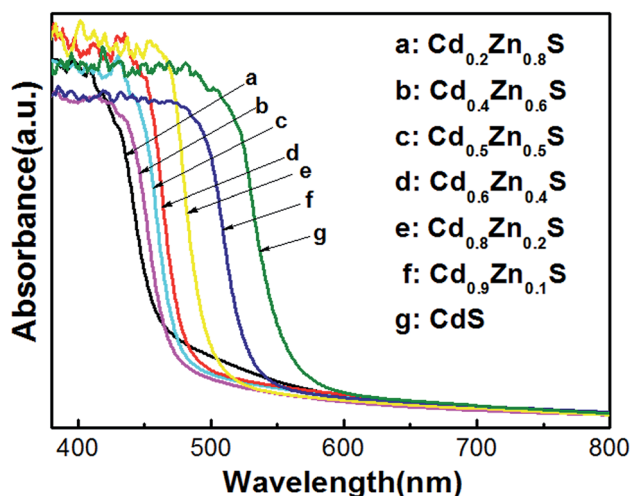
Fig. 3 UV-visible absorption spectra of Cd_xZn_{1-x}S photocatalysts.

Cd_{0.8}Zn_{0.2}S sample showed the largest value. Such high surface area is in accordance with the small size of the Cd_xZn_{1-x}S NCs, which offer a convenient path for the diffusion of photo-generated carriers and provide more active sites for efficient photocatalytic reaction.


Photocatalytic activity

Before photocatalytic measurement, the hydrophilic surface of Cd_xZn_{1-x}S NCs was converted into hydrophobic surface by a ligand-exchange process. Such process was achieved *via* replacing the amino ligand (NH₂) of oleylamine by thiol ligand of 3-MPA. The scheme in Fig. 4 illustrates the ligand-exchange process of oleylamine-capped Cd_xZn_{1-x}S nanocrystals by using thiol ligands (3-MPA). As shown in Fig. 4, the as-prepared Cd_xZn_{1-x}S and Pt-Cd_{0.8}Zn_{0.2}S nanocrystals dispersed well in hexane and were soluble in water after thiol ligands exchange.

The photocatalytic reactions occurred in the Na₂S/Na₂SO₃ sacrificial electron donor system can be expressed as following:²³



Therefore, the overall reaction of the photocatalytic system can be expressed by eqn (6).



The photocatalytic hydrogen production activity was measured under visible light in Na₂S/Na₂SO₃ aqueous solution. As displayed in the Fig. 5a, the photocatalytic activity gradually enhances with increase of *x* values at the initial stage and reached the maximum of 6.32 mmol g⁻¹ h⁻¹ for Cd_{0.8}Zn_{0.2}S. This value is higher than our previous work on Cd_{0.5}Zn_{0.5}S solid solutions synthesized in ethylene glycol.²⁴ Further increase of Cd content suppressed the hydrogen production of the Cd_xZn_{1-x}S solid solutions. Pure CdS nanocrystals only yield a hydrogen evolution rate of 1.79 mmol g⁻¹ h⁻¹, demonstrating that alloying with ZnS is effective for the improvement of catalytic activity. The stability of the photocatalysts were tested in the experiments. Fig. S2† shows the results of the four-cycle test runs of the Cd_{0.8}Zn_{0.2}S sample with the same conditions from Fig. 5. It's found that the curves of H₂ production rate of the

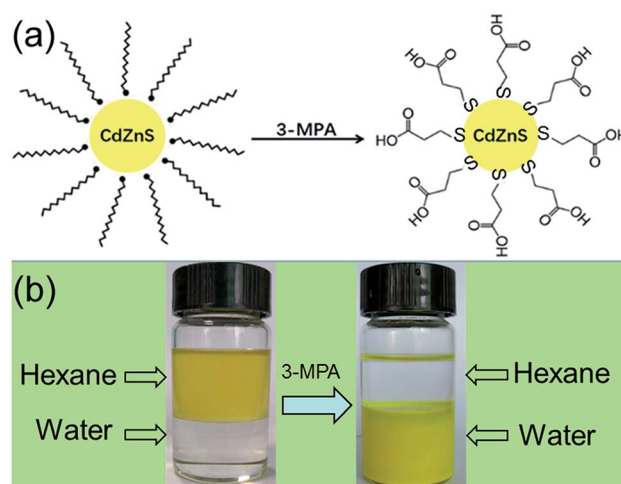


Fig. 4 (a) Scheme illustrating the ligand exchange of oleylamine-capped CdZnS nanoparticles using 3-MPA; (b) photograph of Cd_{0.8}Zn_{0.2}S solutions before and after ligand exchange using 3-MPA.



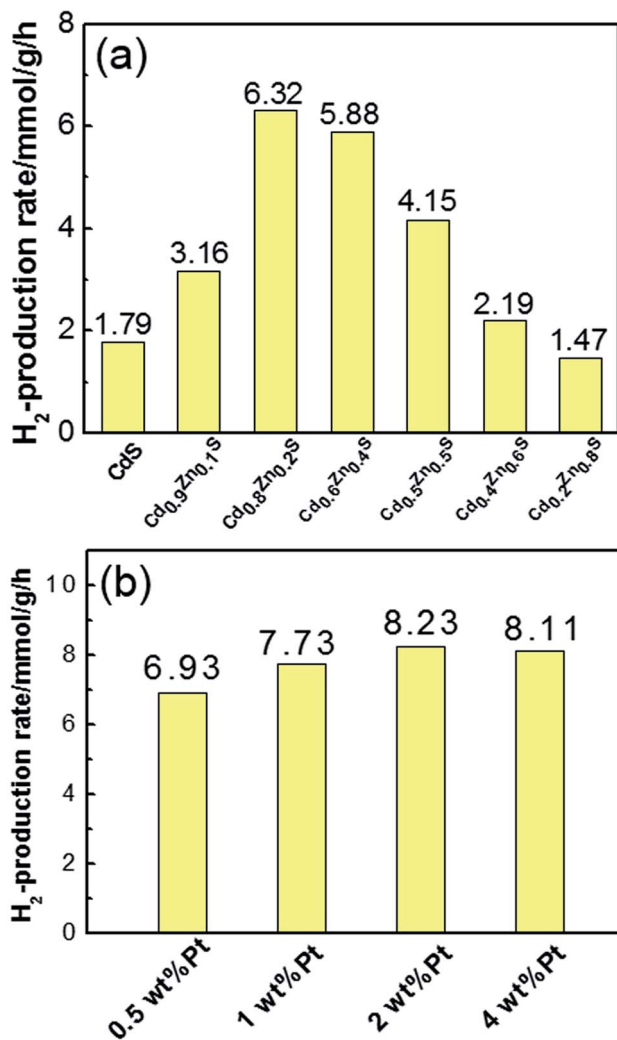


Fig. 5 (a) Comparison of H₂ production rates of Cd_xZn_{1-x}S photocatalysts with different x value; (b) the H₂ production rates of Pt-Cd_{0.8}Zn_{0.2}S nanocrystals with different Pt content.

photocatalysts are linear and no obvious decrease is observed for the photoactivity of the sample. This confirms the good stability for the samples during the photocatalytic reaction.

Fig. 5b shows the H₂ evolution rate of Pt-Cd_{0.8}Zn_{0.2}S NCs with different Pt content. After loading 1 wt% Pt on Cd_{0.8}Zn_{0.2}S nanocrystals, the H₂ evolution rate increased to 7.73 mmol g⁻¹ h⁻¹. As 2 wt% Pt was loaded on Cd_{0.8}Zn_{0.2}S nanocrystals the H₂ evolution rate reached the highest value of 8.23 mmol g⁻¹ h⁻¹, which was increased by 30% compared with that of pure Cd_{0.8}Zn_{0.2}S nanocrystals. Further increase the content of Pt to 4 wt% the H₂ evolution rate reduced slightly to 8.11 mmol g⁻¹ h⁻¹. Such decrease in photoactivity are probably caused by two factors. First, the loading of excessive Pt precursors led to independent nucleation of Pt atoms in oleylamine, which had not contribution to the photoactivity. Second, the free and attached Pt nanoparticles had optical shield effects on Cd_xZn_{1-x}S NCs since they could scatter or absorb incident light,²⁵ thus decreased the number of photons absorbed by Cd_xZn_{1-x}S NCs. In a comparison experiment, Pt (2 wt%) was photodeposited *in situ* on the MPA-3 capped

Cd_xZn_{1-x}S nanocrystals from the precursor of H₂PtCl₆. The improvement of H₂ production rate was measured to be 12% compared with pure Cd_{0.8}Zn_{0.2}S sample, suggesting the inefficient contact of Pt and Cd_{0.8}Zn_{0.2}S nanocrystals by this method.

It was found that the H₂ production rate of the Cd_xZn_{1-x}S decreased as the samples were over-cleaned by ethanol and water. This implies that the loss of 3-MPA molecules influences the activity of Cd_xZn_{1-x}S NCs. The effects of 3-MPA-capping on sulfides nanoparticles were studied by some reports. For instance, Jeong *et al.* conducted a series of electrical and optical measurements on MPA-treated PbS quantum dot films and demonstrated that 3-MPA capping could result in low densities of midgap states in PbS, which facilitate charge collection over relatively long distances outside the depletion region.²⁶ It was also reported that 3-MPA was beneficial to prevent the recombination of electron and hole at surface sites of quantum dots and the aggregation *via* steric hindrance.^{27,28} Based on these observations, it's inferred that the capping of 3-MAP molecules have positive effects on the activity of Cd_xZn_{1-x}S NCs since it might promote charge collection and transport processes in semiconductors, accelerating H₂ evolution in the photocatalytic reaction. Such mechanisms have been confirmed in the development of quantum-dot-based solar cells (QDSCs). For example, high conversion efficiency was achieved on ZnCuInSe and CdSe cosensitized QDSCs with 3-MPA serving as an anchor to bind QDs to TiO₂ surface.²⁹ The 3-MPA capped ZnCuInS based QDSCs exhibited good photovoltaic performance and the presence of 3-MPS molecules suppress charge recombination and accelerate electron injection from QD to TiO₂.³⁰

To further investigate the role of heterostructures on the charge separation process of Cd_xZn_{1-x}S NCs, the electrode charge-transfer properties of the Pt-Cd_xZn_{1-x}S samples were studied by EIS. Shown in Fig. 6 are the EIS Nyquist plots and simulated equivalent-circuit of the Cd_{0.8}Zn_{0.2}S, 1 wt% and 2 wt% Pt-Cd_{0.8}Zn_{0.2}S films, respectively. The R_t of the Cd_{0.8}Zn_{0.2}S film has the largest value of 90 990 Ω cm² and the values of 1 wt% and 2 wt% Pt-Cd_{0.8}Zn_{0.2}S films were fitted to be 79 803 and 60551 Ω cm², respectively. The smaller R_t value

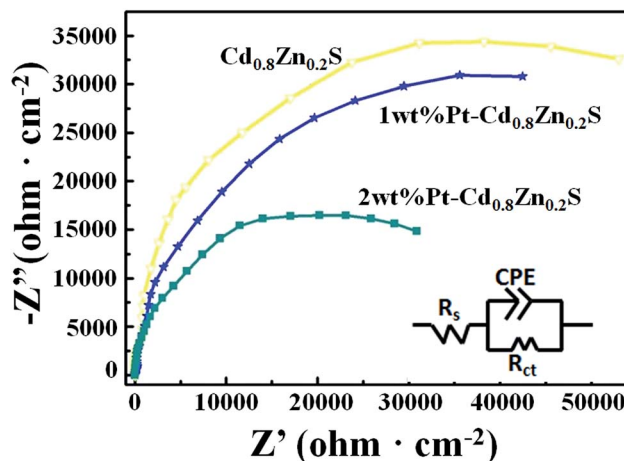


Fig. 6 The EIS Nyquist plots and equivalent circuit of the Cd_{0.8}Zn_{0.2}S, 1 wt% and 2 wt% Pt-Cd_{0.8}Zn_{0.2}S films.



indicated that the electron-hole pairs in the Pt-Cd_{0.8}Zn_{0.2}S heterostructures possessed faster separation and transfer rate than that of Cd_{0.8}Zn_{0.2}S.^{31,32} The tendency is in line with the photoactivity of the samples, confirming the formation of Pt-Cd_xZn_{1-x}S nanoheterostructures enhance the activity of Cd_xZn_{1-x}S NCs. In such structures the Schottky barrier in the Pt-Cd_xZn_{1-x}S interface promoted the photoexcited electron-hole pair separation and reduced the activation potentials for H₂ evolution. As a result, the activity of the photocatalysts was improved. It is noteworthy that the activity improvement is not as novel as other photocatalysts do after Pt loading.³³ Such difference could be understood based on the microstructures of the photocatalysts. On one hand the 3-MPA capped Cd_{0.8}Zn_{0.2}S NCs already have abundant hydrogen reactive sites at the surface. On the other hand only a part of Cd_xZn_{1-x}S NCs in sample were successfully incorporation with Pt nanoparticle. These two factors finally contributed to limit increase for the activity of the Cd_{0.8}Zn_{0.2}S samples.

Conclusions

Cd_xZn_{1-x}S nanocrystals with size ranging from 3–11 nm were synthesized in oleylamine at 280 °C by using Cd(CH₃COO)₂ and Zn(CH₃COO)₂ as the metal precursors and Na₂S as the sulfur source. The hydrophilic surface of Cd_xZn_{1-x}S NCs was converted into hydrophobic surface by using 3-MPA as the ligand-exchange reagent. It was found that Cd_xZn_{1-x}S NCs with the *x* value of 0.8 showed the highest photocatalytic H₂ production rate (6.32 mmol g⁻¹ h⁻¹) under visible light. The formation of Pt-Cd_xZn_{1-x}S heterostructures were achieved by *in situ* adding of Pt(acac)₂ into the reaction solution and the 2 wt% Pt-Cd_{0.8}Zn_{0.2}S sample reached the highest H₂ evolution rate (8.23 mmol g⁻¹ h⁻¹). The high activity of the photocatalysts were attributed to the small size, good crystallite as well as 3-MPA capping of the nanocrystals. The simple and cheap method for colloidal metal-semiconductors heterostructures in our work provides a new insight for photocatalytic hydrogen production from water splitting.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

The authors acknowledge financial support from Hubei Provincial Department of Education (No. D20171006).

Notes and references

- H. Ahmad, S. K. Kamarudin, L. J. Minggu and M. Kassim, *Renewable Sustainable Energy Rev.*, 2015, **43**, 599–610.
- S. Chen, S. S. Thind and A. Chen, *Electrochem. Commun.*, 2016, **63**, 10–17.
- S. Chen, T. Takata and K. Domen, *Nat. Rev. Mater.*, 2017, **2**, 17050–17067.

- Q. Li, X. Li, S. Wageh, A. A. Al-Ghamdi and J. Yu, *Adv. Energy Mater.*, 2015, **5**, 1500010–1500038.
- Y. Huang, Y. Liu, D. Zhu, Y. Xin and B. Zhang, *J. Mater. Chem. A*, 2016, **4**, 13626–13635.
- S. B. Wang, B. Y. Guan, Y. Lu and X. W. D. Lou, *J. Am. Chem. Soc.*, 2017, **139**, 17305–17308.
- W. Y. Lim and M. H. G. W. Ho, *Dalton Trans.*, 2015, **44**, 10991–10996.
- D. Dai, H. Xu, L. Ge, C. Han, Y. Gao, S. Li and Y. Lu, *Appl. Catal., B*, 2017, **217**, 429–436.
- H. L. Guo, H. Du, Y. F. Jiang, N. Jiang, C. C. Shen, X. Zhou, Y. N. Liu and A. W. Xu, *J. Phys. Chem. C*, 2016, **121**, 107–114.
- H. Zhou, Q. Liu, W. Liu, J. Ge, M. Lan, C. Wang, J. Geng and P. Wang, *Chem.-Asian J.*, 2014, **9**, 811–818.
- L. Yao, D. Wei, Y. Ni, D. Yan and C. Hu, *Nano Energy*, 2016, **26**, 248–256.
- J. Zhang, J. Yu, M. Jaroniec and J. R. Gong, *Nano Lett.*, 2012, **12**, 4584–4589.
- M. Liu, D. Jing, Z. Zhou and L. Guo, *Nat. Commun.*, 2013, **4**, 2278–2286.
- M. Liu, L. Wang, G. Lu, X. Yao and L. Guo, *Energy Environ. Sci.*, 2011, **4**, 1372–1378.
- B. J. Ng, L. K. Putri, X. Y. Kong, K. P. Y. Shak, P. Pasbakhsh, S. P. Chai and A. R. Mohamed, *Appl. Catal., B*, 2017, **224**, 360–367.
- X. Yu, A. Shavel, X. An, Z. Luo, M. Ibáñez and A. Cabot, *J. Am. Chem. Soc.*, 2014, **136**, 9236–9239.
- X. Yu, X. An, A. Shavel, M. Ibáñez and A. Cabot, *J. Mater. Chem. A*, 2014, **2**, 12317–12322.
- E. Dutková, P. Baláž, P. Pourghahramani, A. V. Nguyen, V. Šepelák, A. Feldhoff, J. Kováč and A. Šatka, *Solid State Ionics*, 2008, **179**, 1242–1245.
- J. Y. Ouyang, C. I. Ratcliffe, D. Kingston, B. Wilkinson, J. Kuijper, X. H. Wu, J. A. Ripmeester and K. Yu, *J. Phys. Chem. C*, 2008, **112**, 4908–4919.
- X. H. Zhong, Y. Y. Feng, W. Knoll and M. Y. Han, *J. Am. Chem. Soc.*, 2003, **125**, 13559–13563.
- Y. Huang, J. Chen, W. Zou, L. X. Zhang, L. Hu, R. B. Yu, J. X. Deng and X. R. Xing, *Dalton Trans.*, 2015, **44**, 10991–10996.
- X. Yu, X. An, A. Genç, M. Ibáñez, J. Arbiol, Y. Zhang and A. Cabot, *J. Phys. Chem. C*, 2015, **119**, 21882–21888.
- C. C. Chan, C. C. Chang, C. H. Hsu, Y. C. Weng, K. Y. Chen, H. H. Lin, W. C. Huang and S. F. Cheng, *Int. J. Hydrogen Energy*, 2014, **39**, 1630–1639.
- X. Zhou, X. Wang, X. Feng, K. Zhang, X. Peng, H. Wang, C. Liu, Y. Han, H. Wang and Q. Li, *ACS Appl. Mater. Interfaces*, 2017, **9**, 22560–22567.
- X. Wang, G. Liu, Z. G. Chen, F. Li, G. Q. Lu and H. M. Cheng, *Electrochem. Commun.*, 2009, **11**, 1174–1178.
- K. S. Jeong, J. Tang, H. Liu, J. Kim, A. W. Schaefer, K. Kemp, L. Levina, X. Wang, S. Hoogland and R. Debnath, *ACS Nano*, 2012, **6**, 89–99.
- G. M. Durán, M. R. Plata, M. Zougagh, A. M. Contento and Á. Ríos, *J. Colloid Interface Sci.*, 2014, **428**, 235–241.
- S. Jagadeeswari, M. A. Jhonsi, A. Kathiravan and R. Renganathan, *J. Lumin.*, 2011, **131**, 597–602.



Paper

- 29 W. Wang, W. Feng, J. Du, W. Xue, L. Zhang, L. Zhao, Y. Li and X. Zhong, *Adv. Mater.*, 2018, **30**, 1705746–1705753.
- 30 L. Yue, H. Rao, J. Du, Z. Pan, J. Yu and X. Zhong, *RSC Adv.*, 2018, **8**, 3637–3645.
- 31 Q. Li, H. Meng, J. Yu, W. Xiao, Y. Zheng and J. Wang, *Chem. – Eur. J.*, 2014, **20**, 1176–1185.
- 32 J. Low, J. Yu, M. Jaroniec, S. Wageh and A. A. Alghamdi, *Adv. Mater.*, 2017, **29**, 1601694–1601714.
- 33 S. R. Lingampalli, U. K. Gautam and C. N. R. Rao, *Energy Environ. Sci.*, 2013, **6**, 3589–3594.

