



Cite this: *RSC Adv.*, 2019, 9, 3927

Compatibility and thermal decomposition mechanism of nitrocellulose/Cr₂O₃ nanoparticles studied using DSC and TG-FTIR

Yu Guo,^a Ningning Zhao,^a Ting Zhang,^a Hujun Gong,^b Haixia Ma,^{id}*^a Ting An,^c Fengqi Zhao^c and Rongzu Hu^c

Nano metal oxides are common combustion catalysts for enhancing the burning rate of solid propellants. Cr₂O₃ nanoparticles (NPs) are efficient combustion catalysts for the pyrolysis of energetic components. In this study, Cr₂O₃ NPs were synthesized *via* a modified sol-gel method and further used for studying the thermal decomposition of nitrocellulose (NC). Differential scanning calorimetry (DSC) and thermogravimetry-Fourier-transform infrared spectroscopy (TG-FTIR) analyses indicate that the Cr₂O₃ NPs can be safely used with NC and the mechanism of the reaction between Cr₂O₃/NC and pure NC follows the Avrami-Erofeev equation: $f(\alpha) = 3(1 - \alpha)[- \ln(1 - \alpha)]^{1/3}/2$. The peak temperature and activation energy (E_a) for the thermal decomposition of Cr₂O₃/NC are lower than those of pure NC. NO₂ was detected at a lower temperature after NC was mixed with Cr₂O₃ NPs; this indicated the catalytically accelerated bond cleavage of NC by Cr₂O₃ NPs.

Received 23rd November 2018

Accepted 15th January 2019

DOI: 10.1039/c8ra09632e

rsc.li/rsc-advances

Introduction

Solid propellants as the power source of missiles and rocket engines are significant. They are composite materials that are made up of an oxidation agent, a burning catalyst, a binder and so on. For solid propellants, the core of the propulsion technology is combustion performance.¹ The combustion performance refers to the burning rate and the pressure index. A propellant without a catalyst has a low burning rate, a high-pressure index, and unstable combustion. Therefore, a burning-rate catalyst is an indispensable key material in solid propellants. Nitrocellulose (NC) is a common oxidant in solid propellants, and its decomposition properties are closely connected to the combustion performances of propellants.² Several studies have demonstrated that by adding burning catalysts, the oxidizer decomposition can be significantly accelerated and the burning rate of the propellant can be enhanced.³ In recent years, nanoscale metal oxides have exhibited high catalytic activity due to their large surface area, high mobility of their surface atoms, small particle size, and varied lattice defects, which have drawn extensive attention in various fields such as in photocatalysis,⁴ electrochemistry,⁵ solid-oxide fuel cells,⁶ magnetic materials,⁷ *etc.*⁸ As a common transition metal oxide

in nature, Cr₂O₃ is environmentally compatible, low-cost, less toxic, and naturally abundant and exhibits good catalytic activity; moreover, it has been widely applied as a burning catalyst. For instance, annealed Cr₂O₃ nanorods could accelerate the thermal decomposition process of cyclotrimethylenetrinitramine (RDX) and reduce the decomposition temperature by 10 °C.⁹ Another study showed that nanosized Cr₂O₃ NPs decreased the ignition delay time by a factor of 3.5 (16 ± 2 vs. 54 ± 4 ms) and accelerated the combustion rate (340 ± 10 mm s⁻¹) of the Al/Cr₂O₃ thermite, which was fabricated by Cr₂O₃ micro- or nanoparticles ($\Phi \approx 20$ nm) and Al NPs ($\Phi \approx 50$ nm).¹⁰

A number of efforts have been devoted towards the exploration of the catalytic effects of Cr₂O₃, and as a burning catalyst, Cr₂O₃ exhibits excellent catalyst performance. However, studies on the compatibility and thermal decomposition mechanism of nitrocellulose/Cr₂O₃ NPs have been rarely reported. Compatibility is one of the most important measures for energetic materials, which determines whether two components can be used together. Moreover, investigation of the thermal decomposition mechanism could help to understand the catalytic mechanism and design efficient catalysts.

In this study, we prepared Cr₂O₃ NPs using a sol-gel method and studied the thermal behaviour and non-isothermal decomposition kinetics of the Cr₂O₃/NC composite. DSC thermal analysis was applied to evaluate the compatibility between Cr₂O₃ NPs and NC. Thermal decomposition mechanism of NC under catalysis by Cr₂O₃ was investigated using DSC and TG-FTIR techniques. The results indicate that the Cr₂O₃ NPs have good compatibility with NC

^aSchool of Chemical Engineering, Northwest University, Shaanxi, Xi'an 710069, P. R. China. E-mail: mahx@nwu.edu.cn

^bState Key Laboratory of Continental Dynamics, Northwest University, Shaanxi, Xi'an 710069, P. R. China

^cScience and Technology on Combustion and Explosion Laboratory, Xi'an Modern Chemistry Research Institute, Shaanxi, Xi'an 710065, P. R. China



and can be used as a potential catalyst in the solid propellant due to their potential catalytic effect on the decomposition of the main components of propellants.

Experimental

Materials

The chemicals used in the experiment are as follows: chromic chloride ($\text{CrCl}_3 \cdot 6\text{H}_2\text{O}$, 99.0%, Xilong Chemical Reagent Co.), alcohol ($\text{C}_2\text{H}_5\text{OH}$, anhydrous, Xilong Chemical Reagent Co.), propylene oxide ($\text{C}_3\text{H}_6\text{O}$, 99.0%, Kelong Chemical Reagent Co.),

NC (12.6% N, Xi'an Modern Chemistry Research Institute), and Al powders (≈ 50 nm, Jiaozuo Banlv Nano Material Engineering Co.). The chemicals were of analytical grade and used without any further purification. Deionized water was used throughout the experiment.

Caution! NC is an explosive hazardous material. It is strongly recommended to wear safety glasses and face shields while handling these materials in large quantities. Metal spatulas are strictly forbidden. Fire and static electricity discharge should be avoided. For the TG-FTIR and DSC analyses, not more than 2 mg of sample should be used to avoid

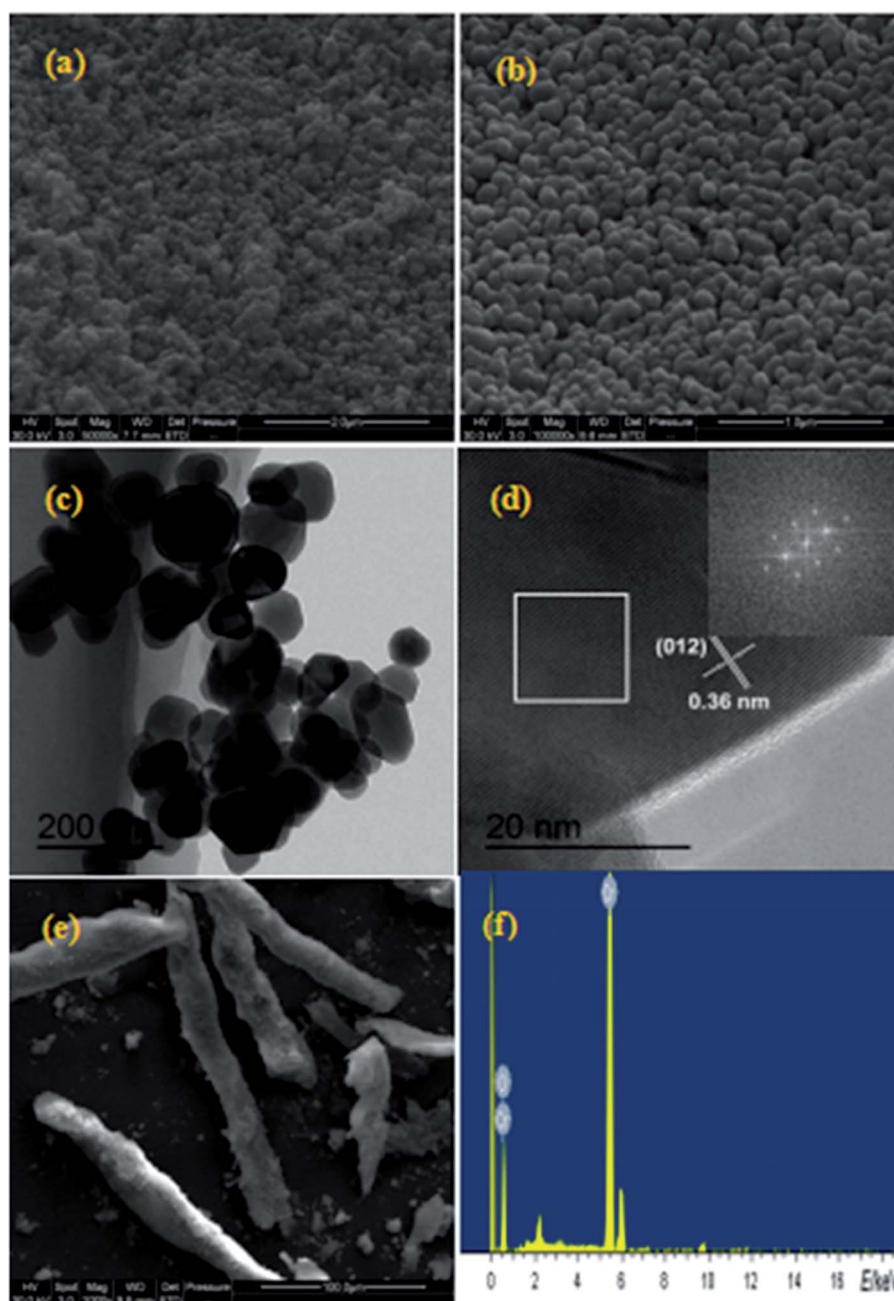


Fig. 1 SEM and TEM images of the prepared samples; (a and b) SEM images of Cr_2O_3 ; (c and d) TEM images of Cr_2O_3 ; (e and f) SEM images of the $\text{Cr}_2\text{O}_3/\text{NC}$ composite and the EDS spectra of Cr_2O_3 NPs, respectively.



instrument damage. NC was provided by the Xi'an Modern Chemistry Research Institute.

Preparation of the Cr₂O₃ NPs

Cr₂O₃ nanopowders were prepared by a sol-gel method. In the synthesis of the Cr₂O₃ gel, CrCl₃·6H₂O was used as the chromium source, and propylene oxide was used as the complexing agent. Typically, 0.66 g of CrCl₃·6H₂O was dissolved in 2.0 mL of anhydrous ethanol, and a green transparent solution was obtained by ultrasonic dispersion at room temperature. Then, 0.85 mL of propylene oxide was added to form a uniform, stable dark green wet gel within 10 minutes. After aging for 24 h, the precursors were removed by drying in an oven at 60 °C. The resulting xerogel was calcined at 800 °C for 2 h.

Preparation of composite materials

The Cr₂O₃ NPs were evenly mixed with NC to obtain composite materials at a 1 : 1 proportion by mass. The products were used for the DSC experiment to assess the compatibility of Cr₂O₃ NPs with the main component of the double-base (DB) propellant.

Samples characterization

Physical phase, composition, morphology and structure of the raw materials and products were characterized by XRD, SEM-EDS and FTIR spectroscopy. X-ray diffractograms were obtained *via* the D/MAX-3C (Japan) instrument using Cu K α radiation ($\lambda = 0.15406$ nm) at 40 kV voltage and 40 mA current in the range from 15° to 65°. Scanning electron microscopy (SEM) observations were carried out using the Quanta 400 FESEM (FEI Co., USA) at the acceleration voltage of 30 kV. Energy Dispersive Spectroscopy (EDS) were obtained using the INCAIE350 testing device, obtained from OXFORD Instruments INC (UK), with the discharge voltage of 4–10 kV and a distance of exactly 1 mm

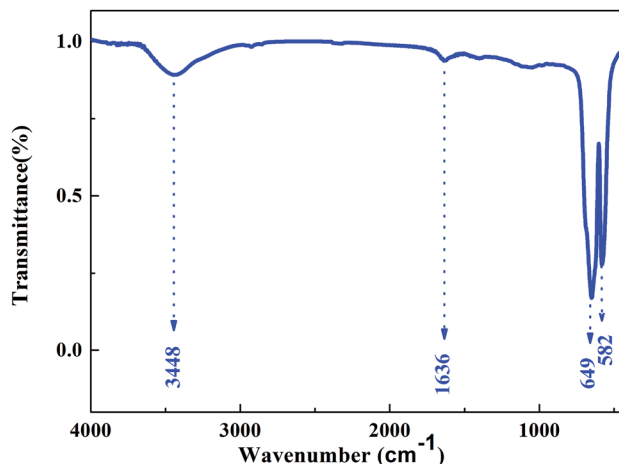


Fig. 3 The FTIR spectrum of Cr₂O₃ NPs.

between electrodes. The morphology and size of the as-obtained products were investigated *via* transmission electron microscopy (TEM) and high-resolution TEM using Libra 200FE (Carl Zeiss SMT Pte Ltd., Germany). FTIR spectra were obtained using the Bruker Tensor 27 (KBr) spectrometer. The Brunauer-Emmett-Teller (BET) specific surface areas were obtained using the Micromeritics Tristar 3000 automated gas adsorption analyzer.

Thermal behaviors of the samples were determined using differential scanning calorimetry (DSC) at the heating rate of 10 °C min⁻¹ from room temperature to 350 °C under a N₂ atmosphere at the flow rate of 50 mL min⁻¹ under ambient atmospheric pressure. To explore the reaction mechanism of the intense exothermic decomposition processes of NC and Cr₂O₃/NC composite energetic materials and obtain the

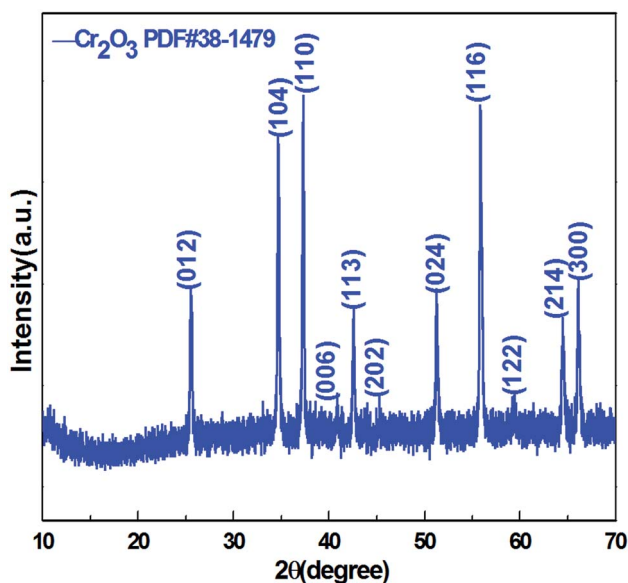


Fig. 2 XRD pattern of the Cr₂O₃ NPs.

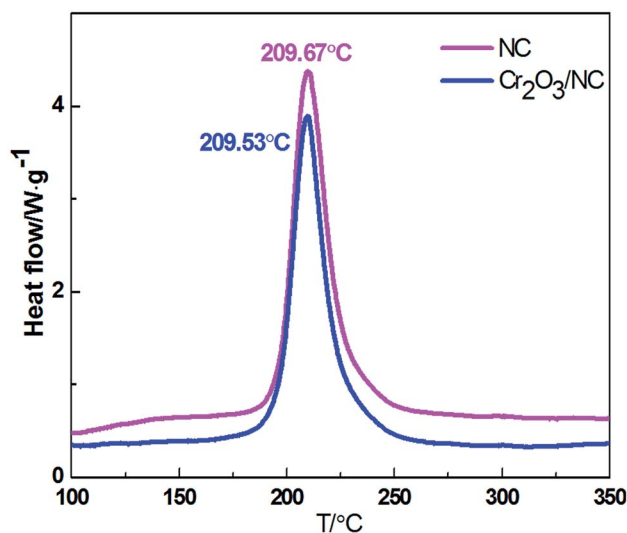


Fig. 4 DSC curves of NC and Cr₂O₃/NC obtained at the heating rate of 10 °C min⁻¹.



Table 1 Calculated values of the kinetic parameters of the decomposition reaction for Cr₂O₃/NC^a

Eq	$\beta/^\circ\text{C min}^{-1}$	$E/\text{kJ mol}^{-1}$	$\lg(A/\text{s}^{-1})$	r
MacCallum–Tanner	5.0	172.16	16.57	0.9961
	10.0	178.83	17.34	0.9965
	15.0	188.42	18.39	0.9962
	20.0	191.07	18.68	0.9966
	25.0	189.04	18.45	0.9964
	30.0	187.49	18.29	0.9965
Šatava–Šesták	5.0	170.73	16.45	0.9961
	10.0	177.03	17.18	0.9965
	15.0	186.08	18.17	0.9962
	20.0	188.59	18.45	0.9966
	25.0	186.67	18.23	0.9964
	30.0	185.20	18.08	0.9965
Agrawal	5.0	171.61	16.56	0.9957
	10.0	178.12	17.30	0.9962
	15.0	187.57	18.33	0.9958
	20.0	190.16	18.62	0.9963
	25.0	188.10	18.39	0.9961
	30.0	186.53	18.22	0.9962
General integral	5.0	175.57	15.34	0.9959
	10.0	182.14	16.07	0.9963
	15.0	191.63	17.08	0.9960
	20.0	194.24	17.36	0.9965
	25.0	192.20	17.14	0.9963
	30.0	190.64	16.98	0.9963
Universal integral	5.0	190.64	16.98	0.9963
	10.0	178.12	17.31	0.9962
	15.0	187.57	18.33	0.9958
	20.0	190.16	18.62	0.9963
	25.0	188.10	18.39	0.9961
	30.0	186.53	18.22	0.9962
Mean		184.40	17.64	
Flynn–Wall–Ozawa		189.16 (E_{po})		1.0000
Kissinger		190.86 (E_{K})	18.87	1.0000
Mean (E_{eo} , E_{po} , E_{K})		179.14		

^a E with the subscript eo and po is the apparent activation energy obtained from the onset temperature (T_{c}) and the peak temperature (T_{p}), respectively, by the Ozawa's method, E with the subscript K is the apparent activation energy obtained from the peak temperature (T_{p}) by the Kissinger's method.

corresponding kinetic parameters [apparent activation energy ($E_{\text{a}}/\text{kJ mol}^{-1}$) and the pre-exponential constant (A/s^{-1})] and the most probable kinetic model function, the DSC curves were obtained at the heating rates of 5.0, 10.0, 15.0, 20.0, 25.0 and 30.0 $^\circ\text{C min}^{-1}$. Thermal decomposition studies of NC and Cr₂O₃/NC were also performed using the TG-FTIR simultaneous analysis device (Netzsch STA 409, Bruker V70) under a nitrogen atmosphere at the heating rate of 10 $^\circ\text{C min}^{-1}$.

Results and discussion

The morphology and size of the nanometer oxides and composite materials were investigated by SEM and TEM. Fig. 1a and b show the SEM images of Cr₂O₃ NPs obtained with $\times 50\,000$ and $\times 100\,000$ magnification, respectively. In these images, a loosely agglomerated structure can be observed. The Cr₂O₃ NPs are spherical in shape with an average diameter of

~ 100 nm. As determined from the typical TEM image (Fig. 1c), thickly dotted pits were found on the surface of the Cr₂O₃ NPs. The cross-sectional HRTEM image of a small part of the Cr₂O₃ nanoparticle is shown in Fig. 1d. Only one set of clear lattice fringes with an interplanar distance of 0.36 nm could be seen, which could be indexed to the 012 plane of the Cr₂O₃ structure. Good crystallinity is also confirmed by the corresponding fast Fourier-transform (FFT) image (the inset in Fig. 1d). As displayed in Fig. 1e, the Cr₂O₃/NC composite material shows a claviform structure with rough and irregular surfaces, diameter in the range from 25 to 35 μm and length in the range from 80 to 200 μm . Elemental analysis (as shown in Fig. 1e) reveals that the presence of only chromium and oxygen elements agrees with the chemical composition of Cr₂O₃.

Crystal structure and phase composition of the resulting sample were characterized using the X-ray powder diffraction (XRD) technique. Fig. 2 displays the XRD pattern of the as-prepared Cr₂O₃ NPs. The reflection peaks shown in Fig. 2 are consistent with those provided in the Joint Committee on Powder Diffraction Standards (JCPDS) card 38-1479 of the Cr₂O₃ structure. The sharp peaks suggest that the Cr₂O₃ NPs are highly crystalline. These peaks are attributed to the rhombohedral structure (space group $R\bar{3}c$) with the unit cell parameters $a = b = 4.9619$ Å, $c = 13.7128$ Å, $\alpha = \beta = 90^\circ$ and $\gamma = 120^\circ$ of the Cr₂O₃ phase.

The FTIR spectrum of Cr₂O₃ NPs (Fig. 3) in the 4000–400 cm^{-1} region displayed the characteristic bands at 3448, 1636, 649, and 582 cm^{-1} . The band at 3448 cm^{-1} is due to the O–H stretching of the surface hydroxyls groups and undissociated water molecules.¹¹ Absorption at 1636 cm^{-1} can be relatively assigned to the bending modes of undissociated water molecules. Strong bands at 649 and 582 cm^{-1} were observed and indicated the presence of crystalline α -Cr₂O₃;¹² this was consistent with the XRD analysis results. Furthermore, the absorption peaks of α -Cr₂O₃ NPs have an obvious

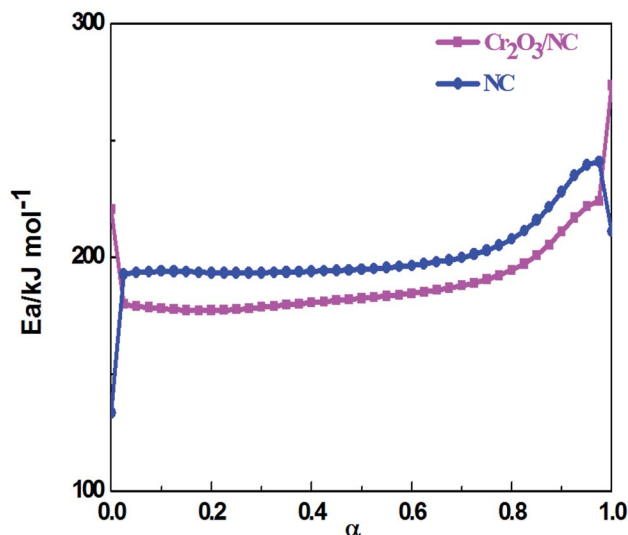


Fig. 5 E_{a} vs. α curves of NC and Cr₂O₃/NC obtained by the Flynn–Wall–Ozawa's methods.



blue-shift *via* the quantum confinement effect relative to those of the bulk crystal.¹³

Thermal behavior of NC and composite materials

Fig. 4 shows the thermal decomposition behavior of NC and Cr₂O₃/NC at the heating rate of 10 °C min⁻¹. It can be seen that the entire decomposition processes of NC and Cr₂O₃/NC are similar, and the peak temperature of Cr₂O₃/NC is lower than that of pure NC at 0.14 °C. To obtain the kinetic parameters [apparent activation energy (E_a) and pre-exponential factor (A)] of the exothermic main decomposition reaction for Cr₂O₃/NC and find out the catalytic effect of Cr₂O₃, DSC curves were obtained at the heating rates of 5.0, 10.0, 15.0, 20.0, 25.0 and 30.0 °C min⁻¹. Moreover, two model-free isoconversional methods, the Kissinger equation¹⁴ and the Flynn–Wall–Ozawa (F–W–O) equation,¹⁵ were employed for calculations.

As listed in Table 1, the E_a obtained by the Kissinger method¹⁴ is determined to be 190.86 kJ mol⁻¹, and the pre-exponential constant (A) is 10^{18.87} s⁻¹. The linear correlation coefficient (r_k) is 1.0000. The value of E_a obtained by the Ozawa's method¹⁵ is 189.16 kJ mol⁻¹, and the value of r_o is 1.0000.

The values of E_a obtained by the Ozawa's method from the isoconversional DSC curves at the heating rates of 5.0, 10.0, 15.0, 20.0, 25.0 and 30.0 °C min⁻¹ were used to draw the

E_a - α (α , the extent of the reaction) relation (Fig. 5). To compare the thermal behaviors of NC and the composite material, the E_a - α relation of NC was obtained by the same method as shown in Fig. 5. The Cr₂O₃ NPs had an obvious catalytic effect on NC due to their lower apparent activation energy. From the curve of Cr₂O₃/NC shown in Fig. 5, it could be seen that the values of E_a in the range of $\alpha = 0.25$ – 0.675 were in good agreement with the calculated values of E_a obtained by the Kissinger's method and Ozawa's method. The E values calculated using the Flynn–Wall–Ozawa equation¹⁴ were used to check the validity of the activation energy values determined by other methods.

The integral equations (MacCallum–Tanner, Šatava–Šesták, Agrawal, general integral, universal integral, and Flynn–Wall–Ozawa) have been cited to obtain the values of E , A and the most probable kinetic model function $G(\alpha)$ from a single non-isothermal DSC curve.¹⁶

Herein, forty-one types of kinetic model functions reported in the ref. 17 and basic data were put into the integral equations and the Kissinger equation for calculation, respectively. The kinetic parameters and the probable kinetic model function were selected by the logical choice method, satisfying the ordinary range of the thermal decomposition kinetic parameters for energetic materials ($E = 80$ – 250 kJ mol⁻¹, log $A = 7$ – 30 s⁻¹). These data together with the appropriate

Table 2 Calculated values of the kinetic parameters of the decomposition reaction for NC and Cr₂O₃/NC^a

Sample	E_a	$\log(A/s^{-1})$	$T_{e0}/^{\circ}C$	$T_{p0}/^{\circ}C$	$T_{beo}/^{\circ}C$	$T_{bpo}/^{\circ}C$	ΔS^{\ddagger} J mol ⁻¹ k ⁻¹	ΔH^{\ddagger} kJ mol ⁻¹	ΔG^{\ddagger} kJ mol ⁻¹
NC	207.48	20.22	181.76	197.00	191.42	206.69	138.40	199.68	134.61
Cr ₂ O ₃ /NC	184.40	17.64	180.74	193.50	192.18	203.49	112.61	190.86	138.31

^a The values (T_{e0} and T_{p0}) of the onset temperature (T_e) and peak temperature (T_p), the thermal ignition temperature (T_{beo}), and the critical temperatures of thermal explosion (T_{bpo}).

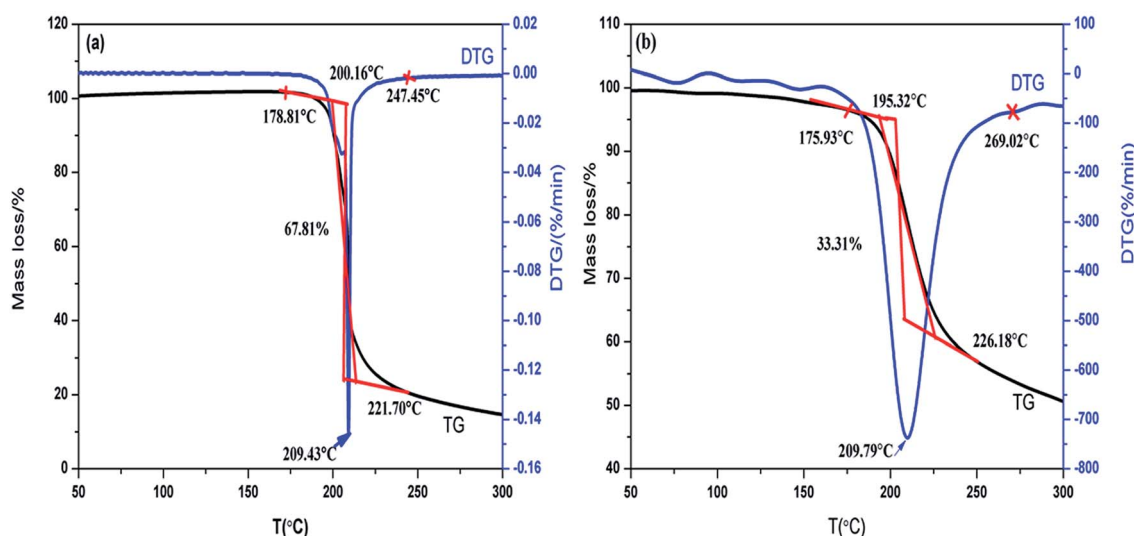


Fig. 6 TG-DTG curves of NC (a) and Cr₂O₃/NC (b).



values for the linear correlation coefficient (r), standard mean square deviation (S) and believable factor (d , where $d = (1 - r) S$) are presented in Table 1. The values of E are very close to each other. The values of E and A obtained from a single non-isothermal DSC curve are in good agreement with the calculated values obtained by the Kissinger's method and Ozawa's method. Therefore, we concluded that the main exothermic decomposition reaction mechanism of $\text{Cr}_2\text{O}_3/\text{NC}$ could be classified as the nucleation and growth mechanism, and the mechanism followed the Avrami-Erofeev equation, where $n = 2/3$.¹⁸ The reaction mechanism of the exothermic main decomposition process of the compound is classified as $f(\alpha) = 3(1 - \alpha)[- \ln(1 - \alpha)]^{1/3}/2$, $G(\alpha) = [- \ln(1 - \alpha)]^{2/3}$. $f(\alpha)$ was substituted with $3(1 - \alpha)[- \ln(1 - \alpha)]^{1/3}/2$, E was substituted with $184.40 \text{ kJ mol}^{-1}$ and A was substituted with $10^{17.64} \text{ s}^{-1}$ in eqn (1).

$$d\alpha/dT = \frac{A}{\beta} f(\alpha) e^{-E/RT} \quad (1)$$

where $f(\alpha)$ and $d\alpha/dT$ are the differential model function and the rate of conversion, respectively.

The kinetic equation for the exothermic decomposition reaction can be described as

$$\frac{d\alpha}{dT} = \frac{10^{17.82}}{\beta} (1 - \alpha)[- \ln(1 - \alpha)]^{1/3} \exp(-2.22 \times 10^4/T)$$

The values T_{e0} and T_{p0} of the onset temperature (T_e) and the peak temperature (T_p) corresponding to $\beta \rightarrow 0$ obtained by eqn (2) are $180.74 \text{ }^\circ\text{C}$ and $193.50 \text{ }^\circ\text{C}$, respectively.

$$T_{e \text{ or } p} = T_{e0 \text{ or } p0} + a\beta_i + b\beta_i^2 + c\beta_i^3 \quad i = 1-6 \quad (2)$$

where a , b and c are coefficients.

The corresponding critical temperatures of thermal explosion (T_b) obtained from eqn (3) taken from the ref. 17 is $203.49 \text{ }^\circ\text{C}$.

$$T_b = \frac{E_O - \sqrt{E_O^2 - 4E_O RT_{PO}}}{2R} \quad (3)$$

where R is the gas constant ($8.314 \text{ J mol}^{-1} \text{ K}^{-1}$) and E_O is the value of E obtained by the Ozawa's method.

The entropy of activation (ΔS^\ddagger), enthalpy of activation (ΔH^\ddagger) and free energy of activation (ΔG^\ddagger) corresponding to $T = T_{PO}$, $E_a = E_k$ and $A = A_k$ (obtained by eqn (4)–(6)) are $112.61 \text{ J mol}^{-1} \text{ K}^{-1}$, $190.86 \text{ kJ mol}^{-1}$ and $138.31 \text{ kJ mol}^{-1}$, respectively.

$$A = \frac{k_B T}{h} e^{\Delta S^\ddagger/R} \quad (4)$$

$$A \exp(-E_a/RT) = \frac{k_B T}{h} \exp\left(\frac{\Delta S^\ddagger}{R}\right) \exp\left(-\frac{\Delta H^\ddagger}{RT}\right) \quad (5)$$

$$\Delta G^\ddagger = \Delta H^\ddagger - T\Delta S^\ddagger \quad (6)$$

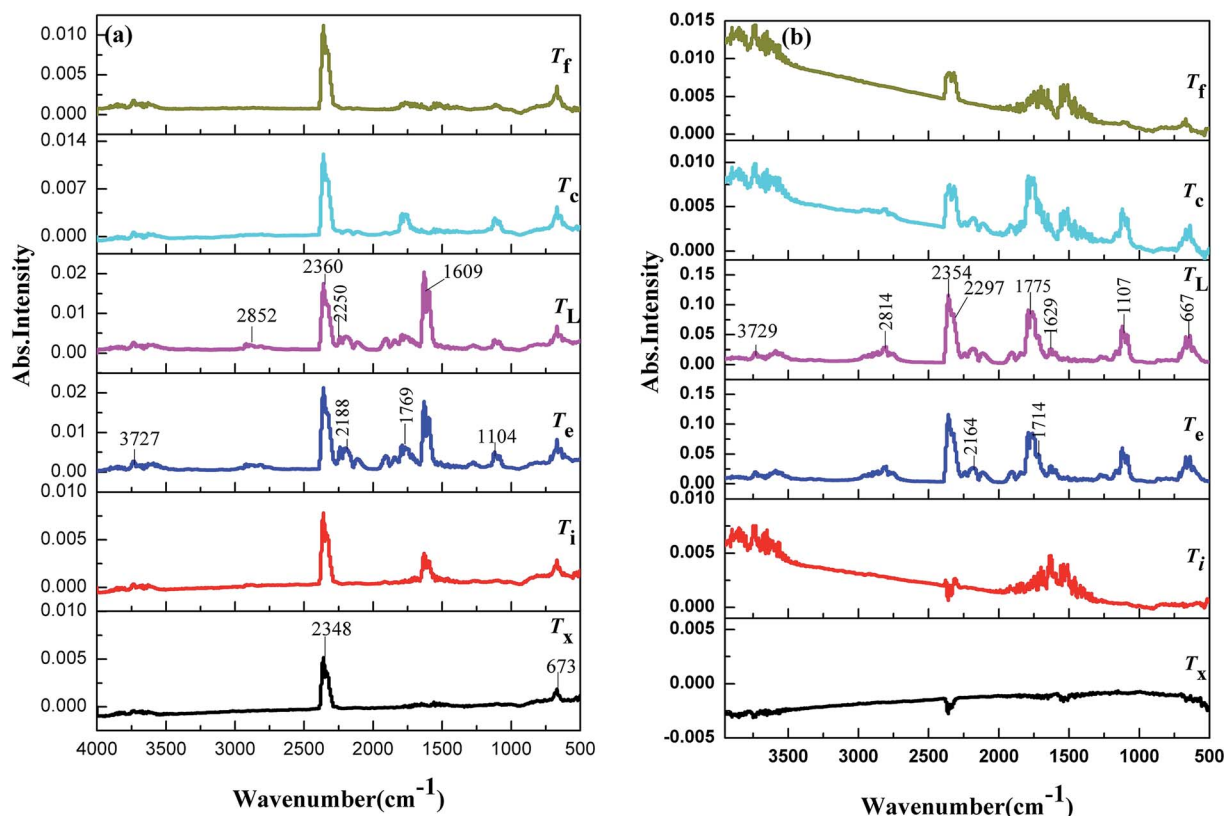


Fig. 7 IR spectra at some temperature before decomposition (T_x), the initial temperature (T_i), the extrapolated onset temperature (T_e), the peak temperature (T_L), the extrapolated end temperature (T_c) and the final temperature (T_f) evolved from the degradation of NC (a) and $\text{Cr}_2\text{O}_3/\text{NC}$ (b).



Table 3 Gaseous products generated during the decomposition processes of NC and Cr₂O₃/NC at different temperatures^a

NC		Cr ₂ O ₃ /NC	
Temperature/°C	Gaseous products	Temperature/°C	Gaseous products
164.92 (<i>T_x</i>)	H ₂ O, CO ₂	159.96 (<i>T_x</i>)	H ₂ O, CO ₂
178.81 (<i>T_i</i>)	H ₂ O, CO ₂ , NO ₂	175.93 (<i>T_i</i>)	H ₂ O, CO ₂ , NO ₂
200.16 (<i>T_c</i>)	H ₂ O, CO ₂ , NO ₂ , NO, CO	195.32 (<i>T_c</i>)	H ₂ O, CO ₂ , NO ₂ , NO, CO
209.43 (<i>T_L</i>)	H ₂ O, CO ₂ , NO ₂ , NO, N ₂ O, HCHO, HCOOH	209.79 (<i>T_L</i>)	H ₂ O, CO ₂ , CO, NO ₂ , NO, N ₂ O, HCHO, HCOOH
221.70 (<i>T_c</i>)	H ₂ O, CO ₂ , NO, HCOOH	226.18 (<i>T_c</i>)	H ₂ O, CO ₂ , CO, NO ₂ , NO, N ₂ O, HCHO, HCOOH
247.45 (<i>T_f</i>)	H ₂ O, CO ₂ , NO, HCOOH	269.02 (<i>T_f</i>)	H ₂ O, CO ₂ , NO, NO ₂ , HCOOH

^a *T_x*, some temperature below the initial decomposition temperature; *T_i*, the initial decomposition temperature; *T_c*, the extrapolated onset temperature; *T_L*, the peak temperature; *T_c*, the extrapolated end temperature; and *T_f*, the final temperature.

where k_B is the Boltzmann constant ($k_B = 1.3806505 \times 10^{-23}$ J K⁻¹) and h is the Planck's constant ($h = 6.6260693 \times 10^{-34}$ J s).

The thermal behavior of NC was analyzed using the same method. The results show that the reaction mechanism of the intense exothermic decomposition process can be classified as the reaction order $f(\alpha) = 3(1 - \alpha)[- \ln(1 - \alpha)]^{1/3}/2$, $G(\alpha) = [- \ln(1 - \alpha)]^{2/3}$. The calculated values of the kinetic parameters of the decomposition reaction for NC and Cr₂O₃/NC are listed in Table 2. According to the ref. 19, the higher the values of T_{e0} , T_p , T_b , E_a and ΔH^\ddagger , the better the heat resistant feature of the materials. This means that materials with low values of T_{e0} , T_p , T_b , E_a and ΔH^\ddagger easily decompose when heated. Compared to NC, the Cr₂O₃/NC composite will easily decompose based on the calculated thermal parameters.

The compatibility analysis

Compatibility of two or more materials refers to their ability to maintain their original physical and chemical properties when mixed together. Poor compatibility may result in changes in the formulation quality, activity and efficiency. It can also lead to variations in thermal safety. Analytical techniques such as differential scanning calorimetry (DSC), pressure differential scanning calorimetry (PDSC),^{20,21} thermogravimetry/differential thermal analysis (TG/DTA), isothermal storage tests (IST), pressure isothermal storage tests (PIST), manometric vacuum stability tests (MVST), pressure vacuum stability tests (PVST),²² and isothermal microcalorimetry (IMC)²³ have been used for compatibility studies. The DSC thermal analysis method²⁴ is widely applied to evaluate the

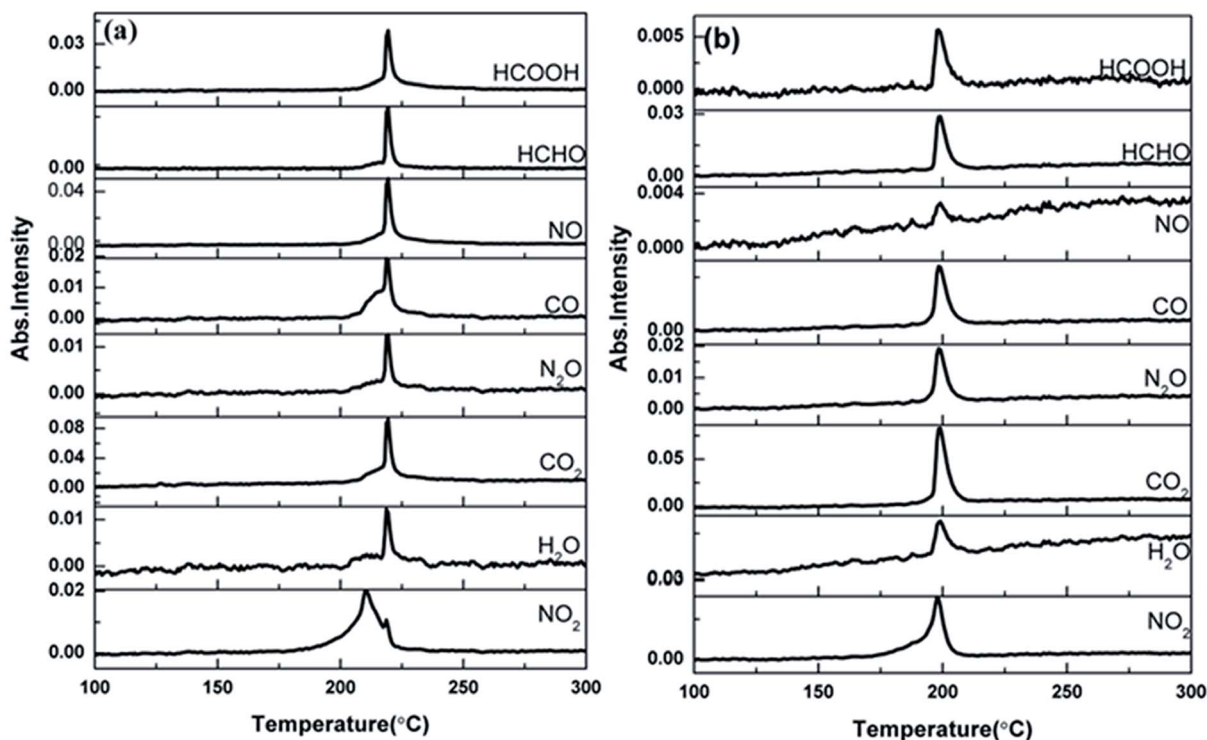


Fig. 8 The density distribution of the gas phase decomposition products of NC (a) and Cr₂O₃/NC (b). The temperature refers to the peak temperature.



chemical compatibility between explosives and the contacted materials at high temperatures due to its features such as time-saving ability, reduced sample usage and operation convenience. Herein, the DSC thermal analysis method was applied to evaluate the compatibility of Cr₂O₃ NPs with NC. The experimental data show that the decomposition peak temperature of Cr₂O₃/NC is lower than that of NC at 0.14 °C, which is within the experimental and instrumental error. The result indicates that the compatibility of the Cr₂O₃ powder with NC is good.²⁵ Therefore, the Cr₂O₃/NC composite can be used as a component in the preparation of propellants and explosives.

Thermal decomposition mechanism

The TG-FTIR simultaneous analysis technique was employed to investigate the thermal degradation process of NC and Cr₂O₃/NC at the heating rate of 10 °C min⁻¹. It was found from the TG-DTG curves of NC and Cr₂O₃/NC (Fig. 6) that only one stage of the total mass loss occurred. The onset decomposition temperature (*T_i*) of Cr₂O₃/NC is 175.93 °C, which is 2.88 °C lower than that of NC.

The apparent variation in the IR characteristic absorption peaks of the gaseous decomposition products of NC and Cr₂O₃/NC formed due to the thermal decomposition process at typical temperatures, including the temperature before decomposition (*T_x*), the initial temperature (*T_i*), the extrapolated onset temperature (*T_e*), the peak temperature (*T_p*), the extrapolated end temperature (*T_c*), and the final temperature (*T_f*), are shown

in Fig. 7 and Table 3. For pure NC, the IR absorption peaks of H₂O (3600–3740 cm⁻¹), CO₂ (2300–2380, 660–670 cm⁻¹) and NO₂ (1593–1635 cm⁻¹)^{26,27} are detected at 178.81 °C (*T_i*), which is the initial temperature of NC. The IR spectrum acquired at 164.92 °C was obtained (Fig. 7a (*T_x*)) to determine whether H₂O and CO₂ detected at 178.81 °C originated from the decomposition of NC. The intensities of the IR absorption of H₂O and CO₂ remained basically unchanged at both 164.92 °C and 178.81 °C; this indicated that H₂O and CO₂ were not the initial degradation products of NC. Therefore, NO₂ was considered to be the initial degradation product; this meant that the breakage of the O–NO₂ bond was deemed to be the first decomposition step as reported in previous studies.^{28–32} When the temperature increased (*T_e*, *T_p*, *T_c*), the gaseous products such as NO (1762–1965 cm⁻¹), CO (2150–2194 cm⁻¹), N₂O (2200–2300 cm⁻¹), HCHO (2700–2900 cm⁻¹, 1720–1740 cm⁻¹), and HCOOH (1080–1128 cm⁻¹) were detected.^{27,28} The peaks at 2852 cm⁻¹ and 1769 cm⁻¹ are attributed to the modes of the C–H and C=O stretching bands of HCHO, respectively,²⁸ which are generated by the –CH₂ONO₂ group.³³ Evolution of the HCOOH gas is due to the secondary autocatalytic reactions of NC.^{31–33} At the end of the decomposition process (*T_f*), the IR absorption peaks of H₂O, CO₂, NO and HCOOH^{26,27} are still easily identifiable in Fig. 7a (*T_f*). The species and the intensities of the gas products obtained *via* the degradation of NC are also shown in the 3D FTIR spectra (Fig. 9a).

From the gaseous product data obtained at *T_x* and *T_i* of Cr₂O₃/NC listed in Table 3, we can see that H₂O and CO₂

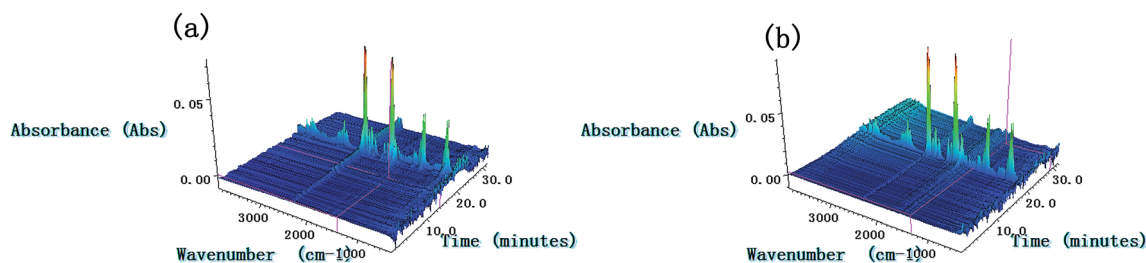


Fig. 9 3D-IR spectra of the gas products of NC (a) and Cr₂O₃/NC (b) at the heating rate of 10 °C min⁻¹.

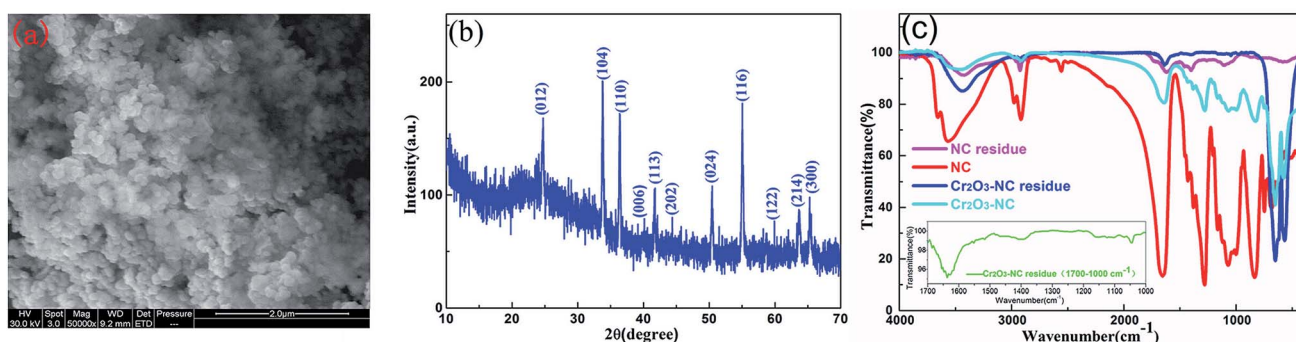


Fig. 10 (a) SEM image of the Cr₂O₃/NC reaction residue, (b) XRD pattern of the Cr₂O₃/NC reaction residue, and (c) FTIR spectra of the NC, Cr₂O₃/NC and Cr₂O₃/NC residues, inset: FTIR spectrum of the Cr₂O₃/NC residue in the range of 1700–1000 cm⁻¹.



Table 4 Assignments of the IR characteristic absorption peaks of NC, NC residue, Cr₂O₃/NC and Cr₂O₃/NC residue^a

NC		NC residue		Cr ₂ O ₃ /NC		Cr ₂ O ₃ /NC residue	
Frequency/cm ⁻¹	Assignments	Frequency/cm ⁻¹	Assignments	Frequency/cm ⁻¹	Assignments	Frequency/cm ⁻¹	Assignments
3565	$\nu(\text{O-H})$	3429	$\nu(\text{O-H})$	3467	$\nu(\text{O-H})$	3435	$\nu(\text{O-H})$
2978	$\nu_{\text{as}}(-\text{CH}_2)$			2973	$\nu_{\text{as}}(-\text{CH}_2)$		
2919	$\nu_{\text{s}}(-\text{CH})$	2929	$\nu_{\text{s}}(-\text{CH})$	2908	$\nu_{\text{s}}(-\text{CH})$	2922	$\nu_{\text{s}}(-\text{CH})$
1654	$\nu_{\text{as}}(-\text{NO}_2)$; $\delta(\text{O-H})$	1621	$\delta(\text{O-H})$	1637	$\nu_{\text{as}}(-\text{NO}_2)$; $\delta(\text{O-H})$	1627	$\delta(\text{O-H})$
1376	$\delta(-\text{CH})$	1403	$\delta(-\text{CH})$	1382	$\delta(-\text{CH})$	1399	$\delta(-\text{CH})$
1279	$\nu_{\text{s}}(-\text{NO}_2)$			1279	$\nu_{\text{s}}(-\text{NO}_2)$		
1159	$\nu_{\text{as}}(\text{oxygen bridges})$			1164	$\nu_{\text{as}}(\text{oxygen bridges})$		
1122	$\nu_{\text{as}}(\text{ring})$	1111	$\nu_{\text{as}}(\text{ring})$	1122	$\nu_{\text{as}}(\text{ring})$		
1067	$\nu(\text{interannular C-O})$			1062	$\nu(\text{interannular C-O})$		
1029	$\nu(\text{C-O})$	1040	$\nu(\text{C-O})$	1025	$\nu(\text{C-O})$	1045	$\nu(\text{C-O})$
996	$\nu(\text{C-O})$			996	$\nu(\text{C-O})$		
833	$\nu(\text{O-NO}_2)$			822	$\nu(-\text{NO}_2)$		
741	$\tau(\text{O-NO}_2)$			747	$\tau(\text{O-NO}_2)$		
681	$\tau(\text{O-NO}_2)$						
				649	$\nu(\text{Cr-O})$	649	$\nu(\text{Cr-O})$
				573	$\nu(\text{Cr-O})$	578	$\nu(\text{Cr-O})$

^a ν is the stretching vibration, ν_{s} is the symmetrical stretching vibration, ν_{as} is the asymmetrical stretching vibration, δ is the bending vibration, and τ is the twisting vibration.

originate from gases in the environment, and NO₂ can be first detected at 175.93 °C. Moreover, the noticeable IR peaks of CO and NO can be found at a lower temperature of 195.32 °C (T_{e} , Fig. 7b) than those obtained for pure NC. After comparing the gaseous species with pure NC, we found that the Cr₂O₃/NC composite released more gaseous products at T_{e} and T_{f} . This is additional evidence of the catalytic effect of Cr₂O₃ NPs on the thermal decomposition of NC, which may be due to the released NO₂ or radical stagnate in the polymer skeleton, which then reacts with the other radicals or degradation products to produce several small molecular products. The density distributions of the gas-phase decomposition products of NC and Cr₂O₃/NC are shown in Fig. 8. It can be seen that NO₂ is the initial released gas during the thermal decomposition process of NC and Cr₂O₃/NC. Other products were released afterward. Notably, due to the catalytic effect of Cr₂O₃, NO, CO, N₂O, HCHO and HCOOH gases were gradually released and reached their highest densities at lower temperatures. Upon comprehensive analysis of the density distribution and IR spectra of two samples, we can conclude that Cr₂O₃ can accelerate the bond cleavage of NC and the secondary reactions of the condensed phases to form numerous gaseous products.

The Brunauer–Emmett–Teller (BET) specific surface area of Cr₂O₃ NPs is 11.2 m² g⁻¹. The specific surface area of NPs is the dominant factor for adsorption capacity. Generally, the larger the surface areas that the NPs possess, the higher the adsorption capacity and the better the catalytic ability that the NPs exhibit. The decomposition reaction is controlled by the condensed phase, the gaseous products or the reaction between the condensed phase and the gaseous products. With the adsorption effect of Cr₂O₃ NPs, gaseous products such as NO₂ do not escape easily from the condensed phase. Therefore, the concentration of intermediate reactants


increased during the secondary reaction. Then, the reaction rate increased, and the activation energy of Cr₂O₃/NC decreased under the direct control of the secondary reaction including the reaction between the condensed phase and the gaseous products or among the gaseous products. In other words, the Cr₂O₃ NPs could accelerate the thermal decomposition of NC.

The decomposition residue of the Cr₂O₃/NC composite was characterized by SEM and XRD measurements, as shown in Fig. 10a and b, respectively. Fig. 10a shows that there exists obvious aggregation in the reaction residue. The particle size (about 100 nm) of Cr₂O₃ showed no obvious change before and after the decomposition reaction. Most of the particles are spherical in shape, except for a few particles sticking together in clumps at elevated temperatures. Fig. 10b shows that the diffraction peaks in the pattern are indexed to the rhombohedral phase of Cr₂O₃ (JCPDS: 38-1479), which reveals that the vast majority of the Cr₂O₃/NC residues obtained after the thermal treatment are Cr₂O₃ powders.

Fig. 10c displays the FTIR spectra of NC, NC residue, Cr₂O₃/NC and Cr₂O₃/NC residue. The characteristic absorption peaks and the corresponding assignments are listed in Table 4. It can be seen that the quantities and varieties of the absorption peaks of NC and Cr₂O₃/NC are consistent in the range of 4000–400 cm⁻¹. The Cr–O vibrational absorption bands are found in the FTIR spectrum of both Cr₂O₃/NC (649 and 573 cm⁻¹) and the Cr₂O₃/NC residue (649 and 578 cm⁻¹).¹² Furthermore, the FTIR spectrum of the Cr₂O₃/NC residue shows the characteristic peaks of the –CH and C–O groups, indicating that the NC residues (Fig. 10c) exist in the Cr₂O₃ NPs after thermal treatment.

Based on the TG-FTIR analyses and literature results,³⁴ the proposed thermal decomposition mechanism of NC and Cr₂O₃/NC composite has been suggested as follows (Scheme 1):



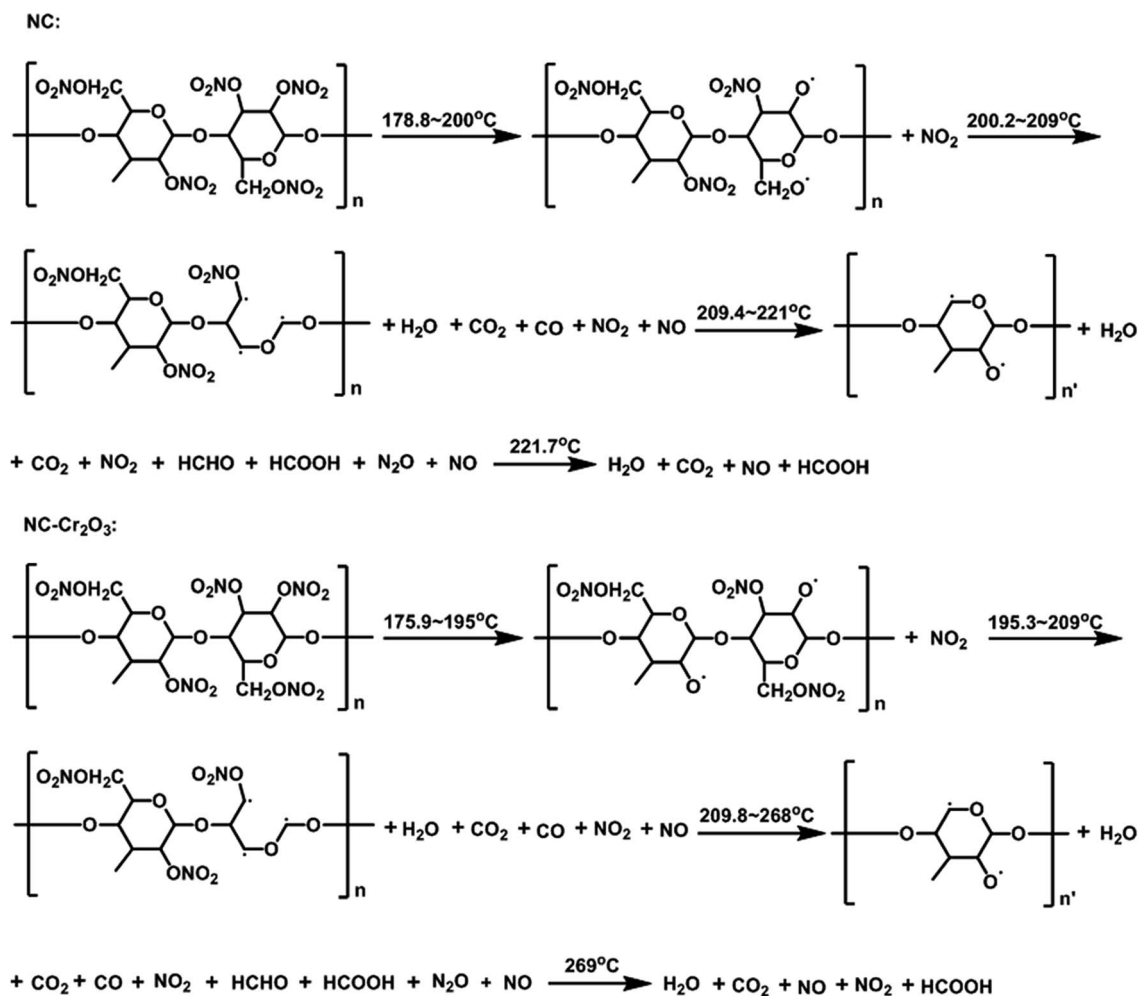

Scheme 1 The proposed thermal decomposition mechanism of NC and the Cr₂O₃-NC composite.

Conclusion

Herein, Cr₂O₃ NPs were synthesized by a sol-gel method with a shortened synthesis time when compared with the case of the reported method. The prepared Cr₂O₃ NPs were subsequently combined with NC to evaluate their catalytic effect. The non-isothermal decomposition kinetic studies carried out on NC and Cr₂O₃/NC showed that the Cr₂O₃ NPs could decrease the activation energy and the decomposition temperature of the thermal explosion of NC. Cr₂O₃ NPs were found to have good compatibility with NC and could be safely used in NC-based propellants. Through the TG-IR simultaneous analyses, we suggested that Cr₂O₃ NPs could accelerate the bond cleavage of NC and speed up the secondary reaction of the condensed phase. The results indicate the potential application of Cr₂O₃ NPs in solid propellants due to the potential catalytic effect of these NPs on the decomposition of the main components of propellants.

Conflicts of interest

The authors declare that they have no conflict of interest.

Acknowledgements

This work was supported by the program for the National Natural Science Foundation of China (No. 21673179) and the Opening Foundation of the State Key Laboratory of Continental Dynamics (Northwest University, No. 12LCD07).

References

- 1 T. Zhang, N. Zhao, J. C. Li, H. J. G. Gong, T. An, F. Q. Zhao and H. X. Ma, *RSC Adv.*, 2017, 7, 23583-23590.
- 2 Y. Zu, Y. Zhao, K. Xu, *et al.*, *Ceram. Int.*, 2016, 42, 18844-18850.
- 3 N. Zhao, J. Li, H. Gong, *et al.*, *J. Anal. Appl. Pyrolysis*, 2016, 120, 165-173.
- 4 K. M. Parida, K. H. Reddy, S. Marthia, *et al.*, *Int. J. Hydrogen Energy*, 2010, 35(22), 12161-12168.
- 5 M. L. Grilli, E. D. Bartolomeo and E. Traversa, *J. Electrochem. Soc.*, 2001, 148(9), H98-H102.
- 6 T. H. Shin, S. Ida and T. Ishihara, *J. Am. Chem. Soc.*, 2011, 133(48), 19399-19407.



- 7 M. Sivakumar, A. Gedanken, W. Zhong, *et al.*, *J. Mater. Chem.*, 2004, **14**(4), 764–769.
- 8 S. Xiang, Z. Zhang, C. Gong, *et al.*, *Mater. Lett.*, 2018, **216**, 1–4.
- 9 H. W. Liao, L. Mu, M. Zheng and Y. Y. Meng, *Chin. J. Explos. Propellants*, 2009, **32**, 50–53.
- 10 P. Gibot, M. Comet, A. Eichhorn, F. Schnell, O. Muller, F. Ciszek, Y. Boehrer and D. Spitzer, *Propellants, Explos., Pyrotech.*, 2011, **36**, 80–87.
- 11 Z. M. Yao, Z. H. Li and Y. Zhang, Studies on thermal dehydration of hydrated chromic oxide, *J. Colloid Interface Sci.*, 2003, **266**, 382–387.
- 12 L. Znaidi and C. Pommier, *Eur. J. Solid State Inorg. Chem.*, 1998, **35**, 405–417.
- 13 L. Q. Zhou, C. W. Wang, N. H. Yang, Y. G. Liang, L. J. Yuan, M. Li, J. G. Cheng and J. T. Sun, *J. Wuhan Univ., Nat. Sci. Ed.*, 2005, **51**(4), 404–410.
- 14 H. E. Kissinger, *Anal. Chem.*, 1957, **29**, 1702–1706.
- 15 T. Ozawa, *Bull. Chem. Soc. Jpn.*, 1957, **38**, 1881–1886.
- 16 R. Z. Hu, Z. Q. Yang and Y. J. Liang, *Thermochim. Acta*, 1988, **123**, 135–151.
- 17 R. Z. Hu and Q. Z. Shi, *Thermal analysis kinetics*, Science Press, Beijing, 2001, pp. 127–131.
- 18 T. L. Zhang, R. Z. Hu, Y. Xie and F. P. Li, *Thermochim. Acta*, 1994, **244**, 171–176.
- 19 R. Z. Hu, F. Q. Zhao, H. X. Gao and J. R. Song, *Calorimetry basis and application*, Science Press, Beijing, 2011, pp. 463–464.
- 20 Q. L. Yan, X. J. Li, L. Y. Zhang, J. Z. Li, H. L. Li and Z. R. Liu, *J. Hazard. Mater.*, 2008, **160**, 529–534.
- 21 J. Z. Li, X. Z. Fan, X. P. Fan, F. Q. Zhao and R. Z. Hu, *J. Therm. Anal. Calorim.*, 2006, **85**, 779–784.
- 22 W. P. C. De Klerk, M. A. Schrader and A. C. Van der Steen, *J. Therm. Anal. Calorim.*, 1999, **56**, 1123–1131.
- 23 A. S. Tompa and W. F. Bryant, *Thermochim. Acta*, 2001, **367–368**, 433–441.
- 24 T. An, F. Q. Zhao, H. X. Gao, H. X. Ma, H. X. Hao, J. H. Yi and Y. Yang, *J. Mater. Eng.*, 2011, **11**(23–28), 34.
- 25 Z. F. Yang, F. Q. Zhao, X. Li and J. Sichuan, *Ordnance*, 2015, **36**(3), 141–146.
- 26 Y. Li, K. Chenxia, C. Huang and Y. Cheng, *J. Therm. Anal. Calorim.*, 2002, **109**, 171–176.
- 27 Q. Dong, *Infrared spectrometry*, Press, Beijing, 1977, pp. 165–170.
- 28 A. Gratien, E. Nilsson, J. F. Doussin, M. S. Johnson, C. J. Nielsen, Y. Stenstrom and B. Picquet-Varrault, *J. Phys. Chem. A*, 2007, **111**, 11506–11513.
- 29 A. L. Kon'Kin, B. G. Ershov, Y. M. Kargin, A. A. Chichirov and M. N. Agafonov, *Russ. Chem. Bull.*, 1989, **38**, 2426–2428.
- 30 P. S. Makashir, R. R. Mahajan and J. P. Agrawal, *J. Therm. Anal.*, 1995, **45**, 501–509.
- 31 A. B. Shehata, M. A. Hassan and M. A. Nour, *J. Hazard. Mater.*, 2003, **102**, 121–136.
- 32 K. Katoh, E. Higashi, K. Nakano, S. Ito, Y. Wada, J. Kasamatsu, H. Miya, M. Yamamoto and Y. Wada, *Propellants, Explos., Pyrotech.*, 2010, **35**, 461–467.
- 33 J. K. Chen and T. B. Brill, *Combust. Flame*, 1991, **85**, 479–488.
- 34 Y. Wang, R. Liu, B. K. Ning, Q. Pan and R. Z. Hu, *Chin. J. Mater. Res.*, 1998, **6**, 157–168.

