



Cite this: *RSC Adv.*, 2019, 9, 10445

NiFe₂O₄@ nitrogen-doped carbon hollow spheres with highly efficient and recyclable adsorption of tetracycline†

Zhe Chen,^a Dongzhao Mu,^a Feng Chen^b and Naidi Tan^{*a}

Antibiotics can affect ecosystems and threaten human health; therefore, methods for removing antibiotics have become a popular subject in environmental management and for the protection of human health. Adsorption is considered an effective approach for the removal of antibiotics from water. In this study, NiFe₂O₄@nitrogen-doped carbon hollow spheres (NiFe₂O₄/NCHS) were synthesized *via* a facile hydrothermal method followed by calcination using NCHS as a hard template. The nanocomposite exhibited high adsorption activity and good recyclability. The nanocomposite was characterized by X-ray diffraction, field emission scanning electron microscopy, transmission electron microscopy, X-ray photoelectron spectroscopy, and nitrogen adsorption–desorption to study its micromorphology, structure, and chemical composition/states. In addition, the factors affecting the adsorption process were systematically investigated, including tetracycline (TC) concentration, solution pH, ionic strength, and temperature. The maximum adsorption capacity for TC was calculated to be 271.739 mg g⁻¹ based on the Langmuir adsorption model, which was higher than various other materials. This study provides an effective method for constructing the NiFe₂O₄/NHCS core–shell structure, which can be applied for the removal of TC from water.

Received 25th January 2019
Accepted 13th March 2019

DOI: 10.1039/c9ra00670b
rsc.li/rsc-advances

Introduction

Antibiotics have been one of the greatest discoveries for humans, and various types of antibiotics have been excessively used in human and veterinary medicine, and in aquaculture.^{1–3} However, the widespread use of antibiotics and the large amounts excreted by humans and animals have resulted in increasingly more pharmaceuticals being discharged into wastewaters and manures, which have led to adverse effects on ecosystem health.^{4,5} Therefore, the development of efficient methods to effectively eliminate antibiotics from wastewater is an important research topic for human health and environmental system management.

To date, many researchers have developed effective methods to remove traditional pollutants from the aquatic environment, such as adsorption,^{5,6} coagulation/flocculation,⁷ photocatalysis,^{8–10} chemical oxidation,¹¹ ion-exchange,¹² biodegradation,¹³ and advanced oxidation.¹⁴ Of these, adsorption is the most pragmatic and convenient method for the removal of antibiotics from water sources, owing to its easy operation, convenience, low energy requirements, high efficiency, cost

effectiveness, and facile recovery or reuse of the adsorbent. In addition, this process does not produce secondary pollutants. Hence, the selection of an appropriate adsorbent is an important and imminent task for the management of the aquatic environment. Until now, activated carbon,¹⁵ metal oxides,¹⁶ clay minerals,¹⁷ and silicon nanomaterials^{18,19} have been applied as conventional adsorbents for the removal of antibiotics from wastewater. However, the low adsorption capacity, high cost, and poor recyclability have restricted their practical application. Thus, the application of magnetic adsorbents is an innovative method to resolve environmental problems.^{20–22} For example, multifunctional magnetic microspheres (Mag@ZnO–Co₃O₄) with bimetal oxide shells have been synthesized and showed excellent adsorption properties for oxytetracycline, with the maximum adsorption capacity of oxytetracycline found to be 128 mg g⁻¹,²³ and core–shell Fe₃O₄@ZIF-8 has been prepared and showed excellent adsorptive capacity for tetracycline (TC) antibiotics.²⁴ However, there is still a challenge in producing a new generation of separation media magnetic nanocomposites.

In recent years, transition-metal oxides such as ZnFe₂O₄, MnFe₂O₄, and NiFe₂O₄ have attracted extensive attention as anode materials,^{25–27} photocatalyst materials,^{28,29} electronics materials,³⁰ and solar cell materials³¹ because of their low cost, excellent visible light response, and good photochemical stability. However, seldomly have these transition-metal oxides been used as adsorption materials.

^aSchool of Material Science and Technology, Jilin Institute of Chemical Technology, Jilin, 132022, PR China. E-mail: chenzhez999@163.com

^bJinlin Petrochemical Company Organic Synthetic Plants, Jinlin, 132021, P. R. China

† Electronic supplementary information (ESI) available. See DOI: 10.1039/c9ra00670b



To the best of our knowledge, this is the first study to fabricate and grow magnetic porous NiFe_2O_4 nanosheets on N-doped carbon hollow spheres (NCHS), where NCHS also served as a hard template, which utilized a facile, mild, and ecofriendly method. A range of techniques including X-ray diffraction (XRD), scanning electron microscopy/transmission electron microscopy (SEM/TEM), X-ray photoelectron spectroscopy (XPS), nitrogen sorption, and magnetic hysteresis loop were employed to fully characterize the obtained materials. It was found that $\text{NiFe}_2\text{O}_4/\text{NCHS}$ had a higher adsorption capacity for TC ($271.739 \text{ mg g}^{-1}$) than that of pure NiFe_2O_4 , as well as good recyclability and stability. The results from the present study provide a practical method for the removal of TCs from water. Furthermore, this magnetic material may have potential practical uses in sensors and for energy storage.

Experimental section

1. Preparation of NCHS carbon hollow spheres


All reagents used in the present study were purchased without any further purification. The NCHS was fabricated based on a previously reported method.³² Briefly, 12 mL of anhydrous ethanol and 0.5 mL of ammonia (25%) were added to 40 mL of distilled water and vigorously stirred for 20 min, and then 1 mL of TEOS was added dropwise to the above solution. Then, 8 mL of dopamine hydrochloride (DA) aqueous solution (50 mg mL^{-1}) was added into the above mixture and the mixture was stirred continuously for 32 h. The material (PDA/SiO_2) was collected after centrifugation, washed four times with purified water, and then collected and dried *via* vacuum freeze drying. The precipitates were heated at 800°C for 3 h at a heating rate of 5°C min^{-1} under a N_2 atmosphere, and the NCHS was obtained.

2. Preparation of $\text{NiFe}_2\text{O}_4/\text{NCHS}$ composite

The obtained NCHS (20 mg) was dispersed into 60 mL of deionized water under sonication for 30 min. Then, 0.2 mmol $\text{Ni}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$, 0.4 mmol $\text{Fe}(\text{NO}_3)_3 \cdot 9\text{H}_2\text{O}$, 0.38 mmol sodium citrate, 1 mmol NH_4F , and 5 mmol urea were slowly added into the above suspension solution while being stirred for 60 min. Subsequently, the uniform mixture was transferred to an 80 mL Teflon-lined stainless-steel autoclave and heated at 150°C for 36 h. The product was then collected after centrifugation and washing several times with distilled water and ethanol. Finally, the obtained product was annealed at 300°C for 2 h in a N_2 atmosphere with a heating rate of 2°C min^{-1} . For comparison, NiFe_2O_4 was obtained under the same conditions except for the exclusion of NCHS.

Results and discussion

The synthetic procedure of $\text{NiFe}_2\text{O}_4/\text{NCHS}$ is rationally demonstrated in Scheme 1. First, PDA/SiO_2 with uniform spheres were prepared *via* the hydrolysis of TEOS and the polymerization of dopamine in a mixture of water and ethanol, combined in a one-pot process. Second, Ni^{2+} and Fe^{3+} ions were randomly adsorbed onto the surface of the PDA/SiO_2 and

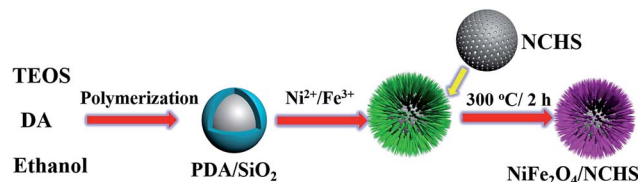

Scheme 1 Schematic of the synthesis and application of the $\text{NiFe}_2\text{O}_4/\text{NCHS}$ composite.

formed a Ni/Fe-based precursor with a hollow interior under facile hydrothermal treatment in an alkaline solution. Lastly, the $\text{NiFe}_2\text{O}_4/\text{NCHS}$ with a hollow structure was obtained after calcination treatment at 350°C for 2 h in a N_2 atmosphere.

The crystalline structures of the synthesized samples were investigated with XRD, as shown in Fig. 1. The XRD pattern of $\text{NiFe}_2\text{O}_4/\text{NCHS}$ displayed broader diffraction peaks of (002) corresponding to graphitized carbon.³³ In addition, the other characteristic peaks showed the reflection planes of (220), (311), and (400) that were in agreement with the cubic spinel phase of NiFe_2O_4 (JCPDS 54-0964).³⁴ The peaks were broader than that of pure NiFe_2O_4 because of an overlap with the corresponding peak of the NCHS substrate.

Fig. 2a and b show representative field emission SEM (FE-SEM) images of $\text{NiFe}_2\text{O}_4/\text{NCHS}$ with hollow nanospheres. Clearly, the sample displays uniformly dispersed spherical structures with an average diameter of approximately 200–300 nm. Moreover, the high-magnification FE-SEM image revealed the sample was composed of nanosheets. The microstructures of the $\text{NiFe}_2\text{O}_4/\text{NCHS}$ sample were further characterized using TEM. The $\text{NiFe}_2\text{O}_4/\text{NCHS}$ sample exhibited a hollow structure that was composed of interconnected nanosheets, which was similar to the results obtained from the FE-SEM image (Fig. 2c). The resolved interplanar distances of the lattice fringes were 0.25 nm apart, which corresponded to the (311) plane of the face-centered cubic lattice of NiFe_2O_4 (JCPDS 54-0964).^{35,36} Importantly, it was found that the pattern and the surface morphology of the adsorbent did not change significantly and remained relatively stable after adsorption (Fig. S2†).

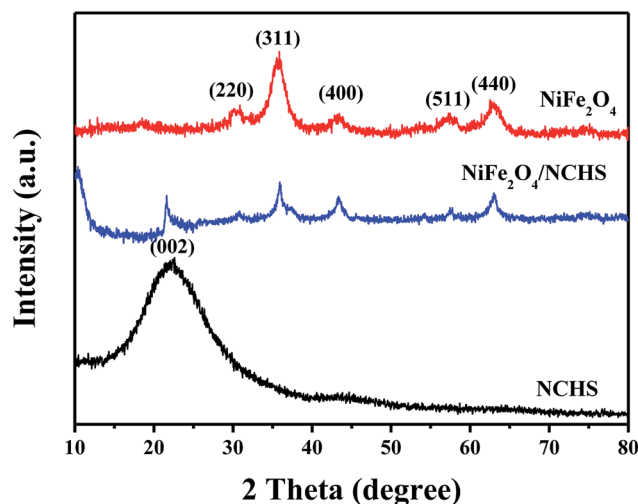


Fig. 1 XRD spectra of NiFe_2O_4 , $\text{NiFe}_2\text{O}_4/\text{NCHS}$ and NCHS.



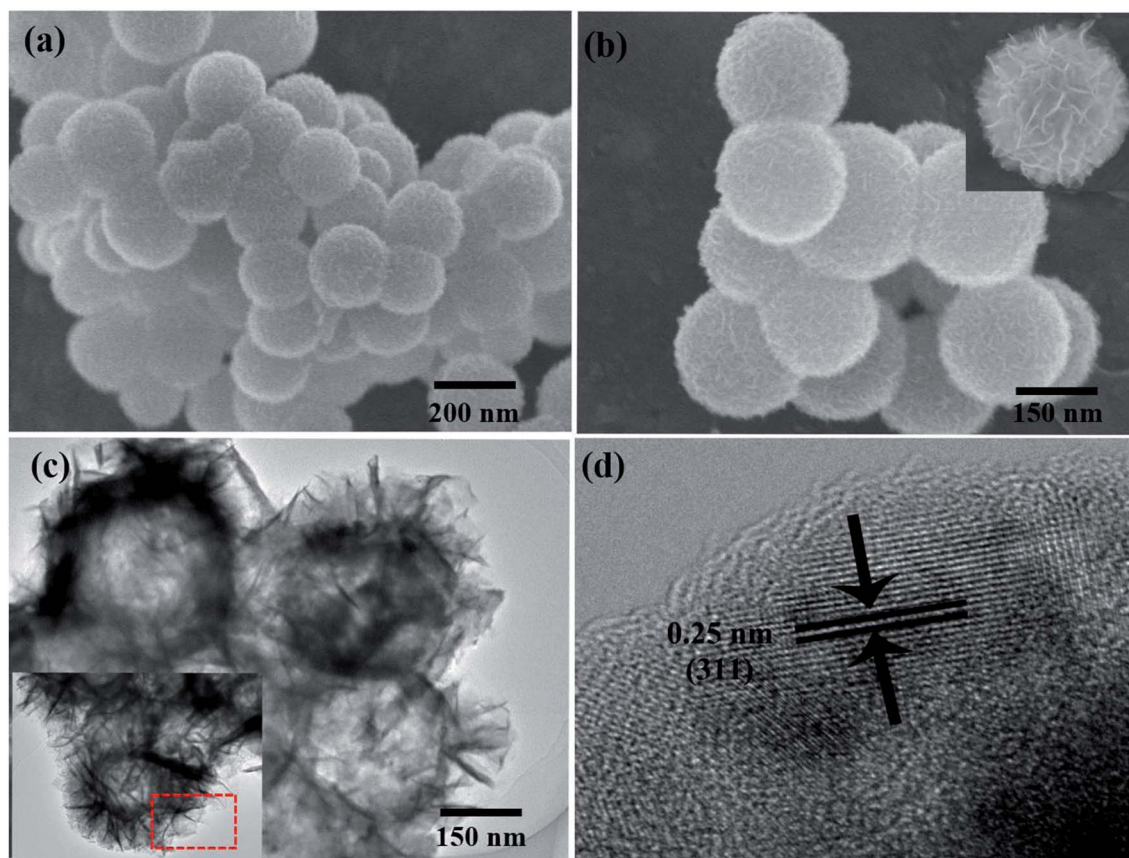


Fig. 2 SEM and TEM image of NiFe₂O₄/NCHS hollow nanospheres.

The surface chemical composition and structure of the NiFe₂O₄/NCHS were further studied with the XPS spectra. The XPS results displayed the existence of Ni, Fe, N, and O elements in the sample (Fig. 3a). For the Ni 2p spectrum shown in Fig. 3b, two main peaks were located at 854.2 and 871.9 eV, corresponding to the two spin-orbits Ni 2p_{3/2} and Ni 2p_{1/2}, respectively, whereas the binding energy at 718.2 and 724.1 eV were in agreement with Fe 2p_{3/2} and Fe 2p_{1/2}, respectively. In addition, the two spin-orbits Ni 2p and Fe 2p spectra of NiFe₂O₄/NCHS corresponded to two shake-up satellites (denoted as Sat.).³⁷ Meanwhile, the spin-orbit peaks in Ni 2p and Fe 2p could be fitted to two distinct peaks, which were attributed to the coexistence of Ni²⁺/Ni³⁺ and Fe²⁺/Fe³⁺ cations, respectively. The O 1s XPS spectrum showed two peaks at binding energies of 529.5 and 531.1 eV, which were consistent with the Ni–Fe–O bonds and oxygenic functional groups.³⁸ XPS measurement further revealed the valence state of NiFe₂O₄/NCHS after adsorption (Fig. S3†). For comparison, the survey XPS curves of NiFe₂O₄/NCHS showed that existence of C, N, and O elements in the sample were remarkable enhancement. Importantly, the Ni 2p spectra of NiFe₂O₄/NCHS shifted from 854.2 and 871.9 eV to 856.1 and 873.9 eV, while the Fe 2p spectrum of NiFe₂O₄/NCHS shifted from 718.2 and 724.1 eV to 711.4 and 724.7 eV, respectively. This is due to the fact that the hydroxyl, carbonyl and amino groups of the tetracycline molecule provided a large number of electrons to Ni and Fe to form a metal complex. Furthermore, due to forming active oxygen-containing

functional groups lead to the positions of O 1s offset occurs. As a result, the tetracycline molecule was successfully adsorbed NiFe₂O₄/NCHS.

N₂ adsorption–desorption and pore size distribution were used to analyze the textural properties of the NiFe₂O₄ and NiFe₂O₄/NCHS composite. As shown in Fig. 4, the N₂ adsorption–desorption isotherms of the pure NiFe₂O₄ and NiFe₂O₄/NCHS composite exhibited a type IV isotherm with a type H3 hysteresis loop, which were characteristic of a mesoporous structure.³⁹ The hysteresis loop of the NiFe₂O₄/NCHS in the broad *P/P*₀ range of 0.45–1 indicated the presence of large mesopores and macropores, which further confirmed the hierarchically porous structure of this carbon material. The Brunauer–Emmett–Teller specific surface area and the pore volume of NiFe₂O₄/NCHS were 268.8 m² g^{−1} and 0.22 cm³ g^{−1}, respectively, which were much larger than that of pure NiFe₂O₄ (21.85 m² g^{−1} and 0.04 cm³ g^{−1}, respectively), as shown in Table S1.†^{40,41} The increased surface area and hierarchical pore could be attributed to the adsorption of TC. In addition, the pore diameter of NiFe₂O₄/NCHS after adsorption of tetracycline was smaller than that of before adsorption, indicating that the pollutants with large molecules may cause blockage of the external channel of adsorbent pores with small diameters (Fig. S4†). Zeta potential measurements were carried out at pH 7 to investigate the surface charge of the samples in aqueous solution. As displayed in Fig. S5,† the TC dispersions are positive charged with a zeta potential of about 36.31 mV. Upon



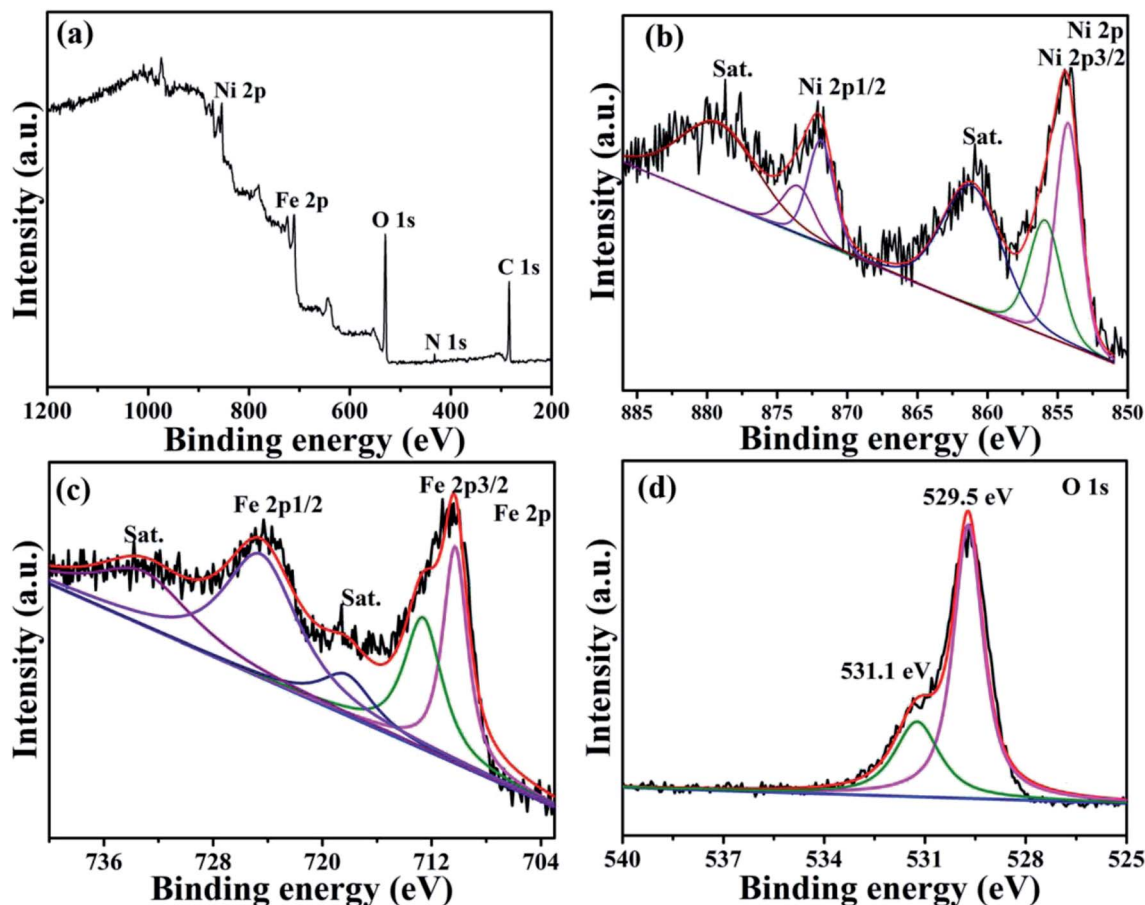


Fig. 3 X-ray photoelectron spectroscopy (XPS) spectra of (a) the survey spectrum, (b) Ni 2p, (c) Fe 2p, (d) O 1s for NiFe₂O₄/NCHS composite.

addition of NCHS, the porous carbon shell can immediately adsorb Ni²⁺ and Fe³⁺ from the solution, resulting in the crystal nucleation and formation of Ni(OH)₂ and Fe(OH)₃ on the surface of porous NCHS. These initial Ni(OH)₂ and Fe(OH)₃ precipitates on the surface of NCHS could provide nucleation spots to direct the growth of Ni(OH)₂ and Fe(OH)₃ nanosheets.

Finally, loose Ni(OH)₂ and Fe(OH)₃ nanosheets were vertically grown on the surface of NCHS by self-assembly. After calcination at 300 °C for 2 h in O₂, nanoflower-like Ni(OH)₂/Fe(OH)₃/NCHS composite were transformed to NiFe₂O₄/NCHS. The NiFe₂O₄/NCHS possess a negative ζ potential of −20.16 mV. The good dispersity and stability of NiFe₂O₄/NCHS/TC in the suspension, this indicates that tetracycline hydrochloride is not easy to be separated from NiFe₂O₄/NCHS suspension and can achieve good adsorption effect.

The magnetic properties of NiFe₂O₄/NCHS were further analyzed at room temperature (25–30 °C), as shown in Fig. 5. The field-dependent magnetization curves were completely reversible, which further indicated that the as-synthesis materials were superparamagnetic without coercivity and remanence. The saturation magnetization value of 85 emu g^{−1} demonstrated its excellent magnetic properties, allowing it to be easily separated from the treated samples by an external magnet.⁴²

In order to examine the surface groups of NiFe₂O₄/NCHS before and after adsorbent, the FTIR spectra were performed (Fig. 6). The absorption peaks in the range from 1700–1200 cm^{−1} is attributed to the skeleton vibration absorption peaks of the benzene ring in the tetracycline molecule.⁴³ The characteristic peak of NiFe₂O₄/NCHS/TC at 1455 cm^{−1} represent the skeleton vibration of the benzene ring in the tetracycline

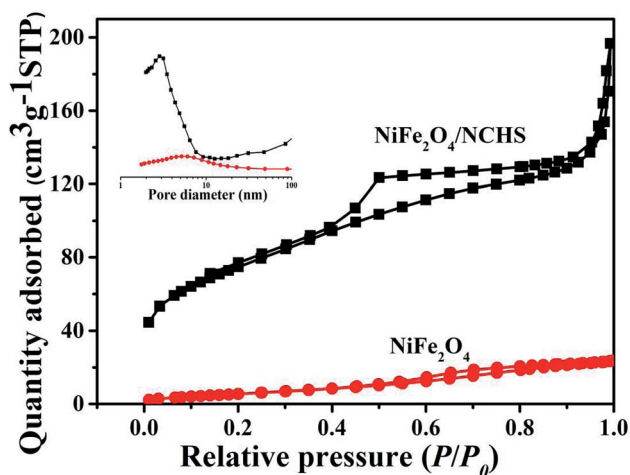


Fig. 4 N₂ adsorption/desorption isotherm and the corresponding pore size distribution (inset) of pure NiFe₂O₄ and NiFe₂O₄/NCHS composite.



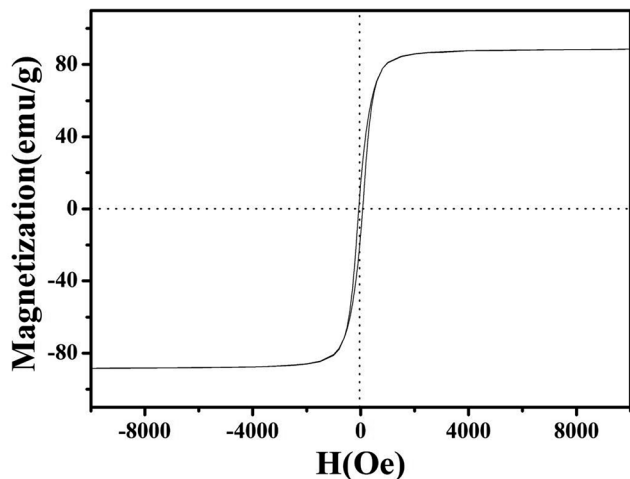


Fig. 5 Magnetic hysteresis loop of NiFe₂O₄/NCHS.

molecule. The absorption peak at 1040 cm⁻¹ is ascribed to the stretching vibration of C–OH of the tetracycline molecule, which was moved to the 1047 cm⁻¹ after tetracycline adsorption due to the tetracycline molecule was participated in its adsorption through hydrogen bond. Based on the above analysis, the tetracycline molecule was successfully adsorbed NiFe₂O₄/NCHS.

The adsorption behavior of TC using NiFe₂O₄/NCHS was influenced by pH ranging from 3.0 to 11.0 with an initial concentration of 10 mg L⁻¹ at 298 K (Fig. 7a).^{43–46} The adsorption of TC was increased with increasing pH from 3.0 to 5.0, and the maximum adsorption capacity for TC was reached at 43.95 mg g⁻¹ when the solution pH was 5. This was attributed to electrostatic and complexation attractions; thus, increasingly more TC was easily attracted to the surface of NiFe₂O₄/NCHS. However, the adsorption capacity of TC showed a similar rapidly decreasing uptake trend when pH values ranged from 5 to 7. Subsequently, when pH values exceeded 9, no significant effect was found except for a slight decrease. Therefore, the optimum pH is a highly significant factor for controlling the adsorption capacity of TC.

To investigate the effect of temperature on the adsorption process, a batch experiment was undertaken at four different temperatures (Fig. 7b) with an initial concentration of 10 mg L⁻¹ at a pH of 5. The adsorption performance of the NiFe₂O₄/NCHS sample was significantly improved with an increase in temperature from 288 K to 318 K, causing the adsorption amount to quickly increase after 50 min from 32.5 mg g⁻¹ to 41.3 mg g⁻¹. Hence, the adsorption process of TC on the NiFe₂O₄/NCHS sample was an endothermic process based on the calculated values of Gibb's free energy.

The removal of pollutants is often influenced by salt (especially inorganic salt) or ions (*e.g.*, Na⁺, Ca²⁺, K⁺, Mg²⁺, Al³⁺, and so on) in water and further affects the adsorption capacity of TC. Three commonly encountered inorganic salts, NaCl, CaCl₂, and KNO₃, in tap water and natural water were selected to investigate the effect of coexisting ionic species on the adsorption of TC (Fig. 7c). The different concentrations of NaCl and KNO₃ had little effect on the adsorption of TC. By contrast, after the addition of CaCl₂ the adsorption capacity of TC was obviously decreased, which implies that it competes with TC for the active site on the surface of the adsorbent, causing a rapid decrease in the adsorption process of TC.^{47,48}

The kinetic curves for TC adsorption of NiFe₂O₄/NCHS and NiFe₂O₄ are shown in Fig. 7d. The two curves revealed that the initial TC uptake rate was quite fast during the first 20 min and reached adsorption equilibria within 40 min. Besides, because the NiFe₂O₄/NCHS sample had a much larger specific surface area and more positive surface charge, it showed faster adsorption rates and enhanced adsorption capacity than that of NiFe₂O₄ under the same experimental conditions. The maximum TC adsorption quantities for the NiFe₂O₄/NCHS and NiFe₂O₄ samples were 41.30 and 28.70 mg g⁻¹, respectively, after 40 min of adsorption, with NiFe₂O₄/NCHS having more adsorption sites and faster adsorption rates than that of NiFe₂O₄. In addition, a series of NiFe₂O₄/NCHS with different dosages of Ni and Fe, pure NiFe₂O₄, and NCHS were tested as adsorbents for TC adsorption (Fig. S1†). Comparing the different samples, NiFe₂O₄/NCHS exhibited much higher adsorption capacity than that of NiFe₂O₄ and NCHS. In

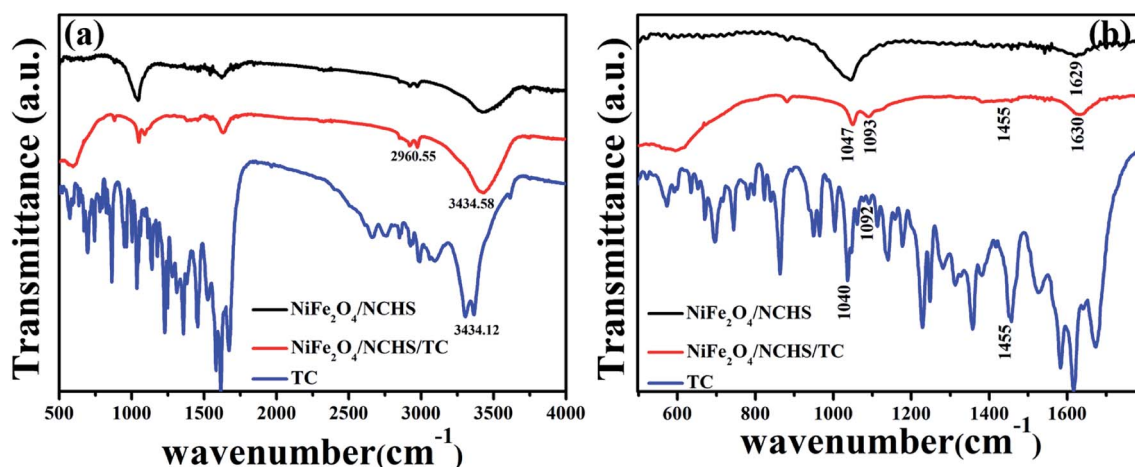


Fig. 6 FT-IR spectra of NiFe₂O₄/NCHS before adsorption and after adsorption of tetracycline.



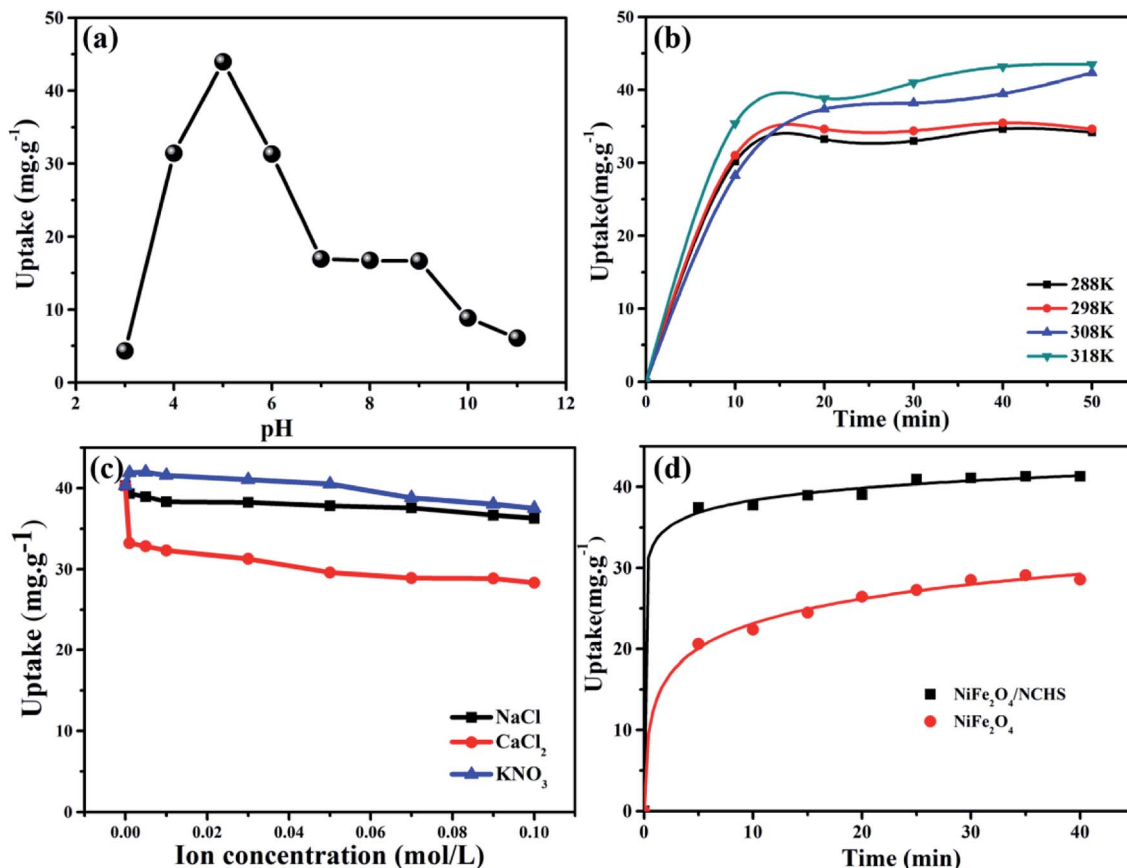


Fig. 7 Effect of (a) pH, (b) temperature, (c) ion species (d) different sample of adsorption amount over time on TC adsorption ($T = 298\text{ K}$; initial TC concentration = 10 mg L^{-1} ; adsorbent dose = 10 mg L^{-1} ; pH = 5).

addition, under a dosage of Ni and Fe of 0.1 : 0.2, NiFe₂O₄/NCHS revealed the best adsorption quantity of TC.

Two well-known kinetic models were adopted to analyze the adsorption mechanism of NiFe₂O₄/NCHS and pure NiFe₂O₄, as shown in Fig. 8. The corresponding parameters (k_1 and k_2) obtained by linear regression are listed in Table S2.† The results showed that all experimental data were distributed on the fitted straight lines, which indicated that it did not match well with

the pseudo-first-order model (Fig. 8a).^{49,50} However, the experimental data displayed good agreement with the pseudo-second-order model owing to the calculated q_e values being matched with the experimental adsorption amount and values of R^2 were higher than 0.995 for NiFe₂O₄/NCHS (Fig. 8b). Hence, the pseudo-second-order kinetic model was more appropriate than the pseudo-first-order kinetic model for the adsorption process, which displayed the adsorption process of tetracycline on

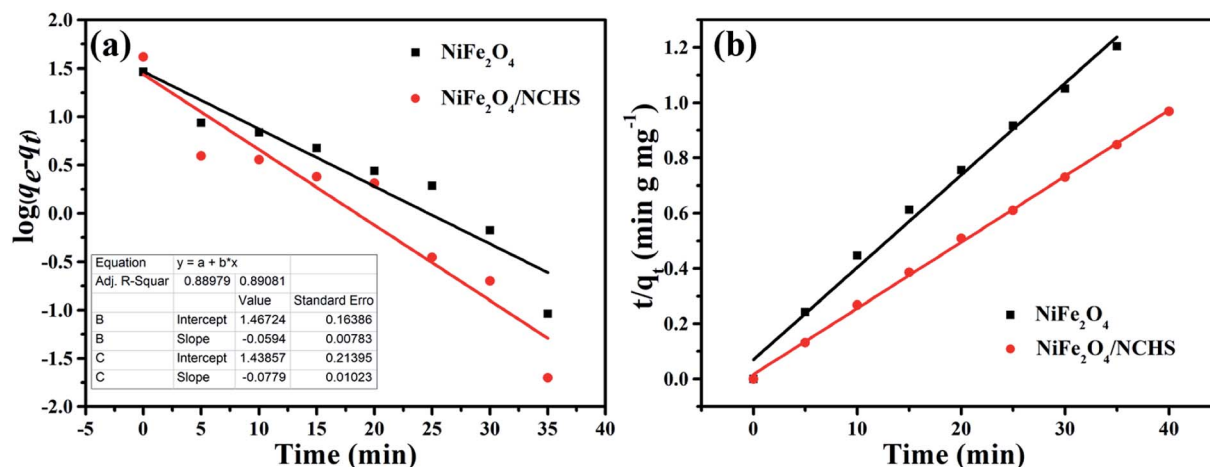


Fig. 8 The kinetic models for TC adsorbed on the samples: (a) pseudo-first-order, (b) pseudo-second-order.



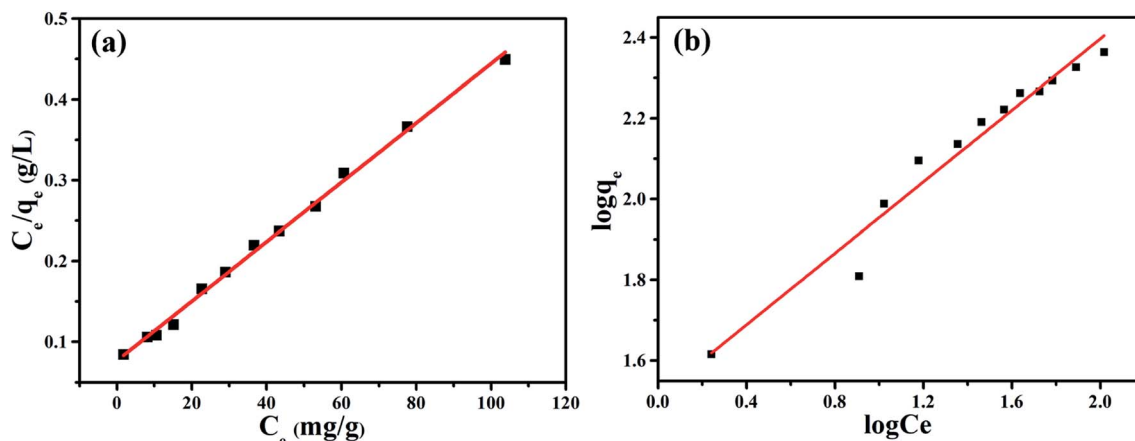


Fig. 9 (a) Langmuir and (b) Freundlich modeling of the isotherms for TC on the sample NiFe₂O₄/NCHS composite at 30 °C.

NiFe₂O₄/NCHS was more in accordance with chemical adsorption. In summary, the adsorption process of tetracycline NiFe₂O₄/NCHS was based on chemical adsorption, which was supplemented by physical adsorption. This is because tetracycline could be bound to metal ions (Ni²⁺, Fe³⁺) to form an antibiotic–metal complex owing to its electron donor groups which could form strong coordination.

The Langmuir and Freundlich isotherm equations were used to analyze the adsorption process of NiFe₂O₄/NCHS for TC (Fig. 9).^{51–54} The respective fitted parameters of the Langmuir isotherm equation and Freundlich model are listed in Table S3.† Compared with the different correlation coefficient (R^2) values, the Langmuir model simulation ($R^2 \geq 0.994$) was larger than the Freundlich isotherm model ($R^2 \geq 0.960$); therefore, the Langmuir adsorption model was more suitable to describe the TC adsorption equilibrium process. The maximum TC adsorption capacity of NiFe₂O₄/NCHS based on the Langmuir equation was 271.739 mg g⁻¹, which was consistent with the experimental data.⁵⁵ In addition, the maximal TC adsorption capacity of NiFe₂O₄/NCHS was superior to that of previously reported materials (Table S4†).

To evaluate the performance of NiFe₂O₄/NCHS for the removal of TC, the reusability and stability of the sample were

studied (Fig. 10). NiFe₂O₄/NCHS was collected from the aqueous suspension by magnetic separation. The experiment results showed that there was a slight adsorbed activity loss of TC at the 4 cycle and 5 cycle, and there was over 85.6% TC removal ratio achieved after 5 cycle tests. In addition, the adsorption–desorption cycle studies were implemented to access the regeneration of NiFe₂O₄/NCHS. Adsorption desorption and regeneration deeply studies. The adsorbed NiFe₂O₄/NCHS was desorbed by NaOH and NH₃·H₂O to achieve the regeneration of NiFe₂O₄/NCHS after equilibrium adsorption. The regeneration efficiency of NiFe₂O₄/NCHS and removal ratio of TC was illustrated in Fig. S6.† It was clearly observed that although the adsorption capacity of NiFe₂O₄/NCHS decreased with the increment in the times of adsorption–desorption of the adsorbent, the removal ratio of tetracycline was maintained at 80% or more after five times of adsorption–desorption cycles of the adsorbent with NaOH(0.001 M)/NH₃·H₂O(0.01 M), which indicated that NiFe₂O₄/NCHS had a relatively good reusability and were a promising candidate for tetracycline adsorption in the practical condition.^{56–62} Therefore, the as-prepared sample possessed an efficient and stable adsorbed TC activity, making it useful for the removal of TC from water.

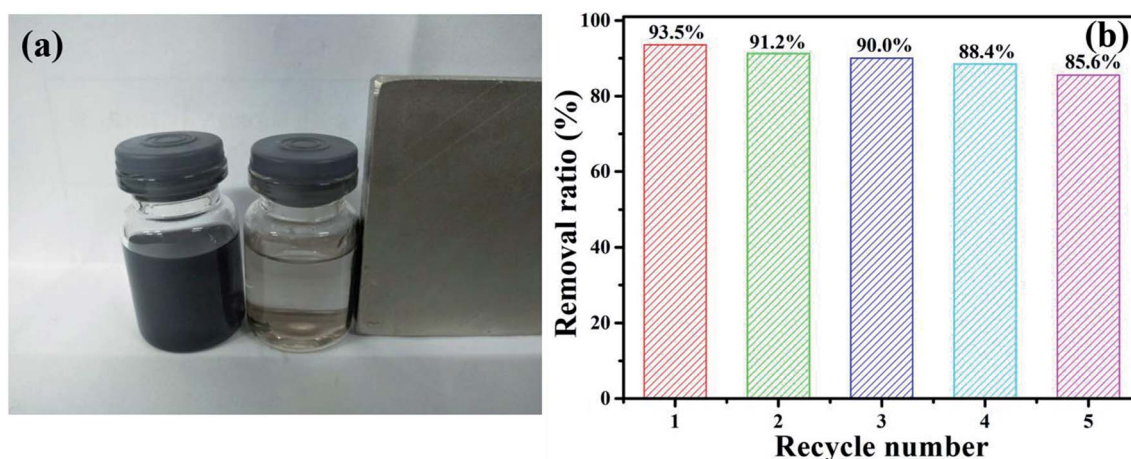


Fig. 10 (a) The digital photograph of the NiFe₂O₄/NCHS responding to a magnet, and (b) TC removal efficiency of the sample in recycle experiments.



Conclusions

In summary, NiFe₂O₄/NCHS was prepared *via* a simple hydrothermal method followed by calcination using NCHS as a hard template. The nanocomposite was characterized by a range of techniques to study its micromorphology, structure, and chemical composition/states. The NiFe₂O₄/NCHS had a large specific surface area and good adsorption capacity for TC. Based on the experimental results, we found that the adsorption kinetics followed the pseudo-second-order model and the adsorption isotherms obeyed the Langmuir adsorption model. Importantly, NiFe₂O₄/NCHS can be effectively separated for reuse by applying an external magnetic field and it has an efficient and stable adsorbed TC activity, thus making it useful for the practical removal of TC from water. In addition, this magnetic material may have potential practical uses in sensors and for energy storage. The present study provides an effective approach to construct other hierarchical carbon-bimetal oxide composite materials.

Conflicts of interest

The authors declare no competing financial interest.

Acknowledgements

This project is supported by National Natural Science Foundation of China (Grant No. 21801091), Science Technology Development Planning of Jilin Province (20170520069JH) and Education Department Project of Jilin Province (JJKH20180556KJ).

References

- 1 S. Ahmed, J. Ning, Y. G. Cheng, I. Ahmad, J. Li, M. Y. Liu, W. Qu, M. Iqbal, M. A. B. Shabbir and Z. H. Yuan, *Talanta*, 2017, **166**, 176–186.
- 2 M. B. Ahmed, J. L. Zhou, H. H. Ngo and W. Guo, *Sci. Total Environ.*, 2015, **532**, 112–126.
- 3 D. Yu, X. Yi, Y. Ma, B. Yin, H. Zhuo, J. Li and Y. Huang, *Chemosphere*, 2009, **76**, 915–920.
- 4 Y. Hai, L. J. Chen, Y. Jing, T. Guo and S. W. Jin, *J. Hazard. Mater.*, 2018, **348**, 75–83.
- 5 M. R. Azhar, H. R. Abid, H. Sun, V. Periasamy, M. O. Tadè and S. Wang, *J. Colloid Interface Sci.*, 2016, **478**, 344–352.
- 6 C. Lei, X. Zhu, B. Zhu, J. Yu and W. Ho, *J. Colloid Interface Sci.*, 2016, **466**, 238–246.
- 7 Y. F. Wang, B. Y. Gao, Q. Y. Yue, Y. Wang and Z. L. Yang, *Bioresour. Technol.*, 2012, **133**, 265–271.
- 8 D. Xu, B. Cheng, S. Cao and J. Yu, *Appl. Catal., B*, 2015, **164**, 380–388.
- 9 X. Yuan, C. Zhou, Y. Jin, Q. Jing, Y. Yang, X. Hen, Q. Tang, Y. Mu and A. K. Du, *J. Colloid Interface Sci.*, 2016, **468**, 211–219.
- 10 P. F. Xia, B. C. Zhu, B. Cheng, J. G. Yu and J. S. Xu, *ACS Sustainable Chem. Eng.*, 2018, **6**, 965–973.
- 11 M. E. Osugi, K. Rajeshwar, E. R. A. Ferraz, D. P. Oliveira, Â. R. Araújo and M. V. B. Zanoni, *Electrochim. Acta*, 2009, **54**, 2086–2093.
- 12 S. J. Lim and T. H. Kim, *Sep. Purif. Technol.*, 2015, **146**, 42–49.
- 13 I. M. Bulai and E. Venturino, *J. Math. Chem.*, 2016, **54**, 1387–1403.
- 14 B. D. Witte, J. Dewulf, K. Demeestere and H. V. Langenhove, *J. Hazard. Mater.*, 2009, **161**, 701–708.
- 15 B. Acevedo, R. P. Rocha, M. F. Pereira, J. L. Figueiredo and C. Barriocanal, *J. Colloid Interface Sci.*, 2015, **459**, 189–198.
- 16 C. Wang, Y. Le and B. Cheng, *Ceram. Int.*, 2014, **40**, 10847–10856.
- 17 M. Z. Momčilović, M. S. Randelović, M. M. Purenović, J. S. Đorđević, A. Onjia and B. Matović, *Sep. Purif. Technol.*, 2016, **163**, 72–78.
- 18 C. F. Wang, E. M. Mäkilä, C. Bonduelle, J. Rytönen, J. Raula, S. Almeida, A. Närvänen, J. J. Salonen, S. Lecommandoux, J. T. Hirvonen and H. A. Santos, *ACS Appl. Mater. Interfaces*, 2015, **7**, 2006–2015.
- 19 S. W. Zhang, H. H. Gao, J. X. Li, Y. S. Huang, A. Alsaedi, T. Hayat, X. J. Xu and X. K. Wang, *J. Hazard. Mater.*, 2017, **321**, 92–102.
- 20 R. Guo, T. F. Jiao, R. F. Li, Y. Chen, W. C. Guo, L. X. Zhang, J. X. Zhou, Q. R. Zhang and Q. M. Peng, *ACS Sustainable Chem. Eng.*, 2018, **6**, 1279–1288.
- 21 S. Kumar, R. R. Nair, P. B. Pillai, S. N. Gupta, M. A. R. Iyengar and A. K. Sood, *ACS Appl. Mater. Interfaces*, 2014, **6**, 17426–17436.
- 22 S. Zhang, H. Niu, H. Cai, X. Zhao and Y. Shi, *Chem. Eng. J.*, 2010, **158**, 599–607.
- 23 L. L. Lian, J. Y. Lv and D. W. Lou, *ACS Sustainable Chem. Eng.*, 2017, **5**, 10298–10306.
- 24 H. C. Liu, L. G. Chen and J. Ding, *Microchim. Acta*, 2017, **184**, 4091–4098.
- 25 Z. Zhang, Y. Wang, Q. Tan, Z. Zhong and F. Su, *J. Colloid Interface Sci.*, 2013, **398**, 185–192.
- 26 D. Zhao, Y. Xiao, X. Wang, Q. Gao and M. H. Cao, *Nano Energy*, 2014, **7**, 124–133.
- 27 L. N. Qu, X. H. Hou, X. Y. Huang, Q. Liang, Q. Ru, B. Wu and K. Lam, *ChemElectroChem*, 2017, **4**(12), 3148–3155.
- 28 Q. Gao and Z. Q. Sun, *J. Nanosci. Nanotechnol.*, 2018, **18**, 5645–5653.
- 29 X. J. Guo, K. B. Wang, D. Li and J. B. Qin, *Appl. Surf. Sci.*, 2017, **420**, 792–801.
- 30 U. Lüders, A. Barthélémy, M. Bibes, K. Bouzehouane, S. Fusil and E. Jacquet, *Adv. Mater.*, 2006, **18**, 1733–1736.
- 31 Q. Luo, Y. Gu, J. Li, N. Wang and H. Lin, *J. Power Sources.*, 2016, **231**, 93–100.
- 32 T. Liu, C. J. Jiang, W. You and J. G. Yu, *J. Mater. Chem. A*, 2017, **5**, 8635–8643.
- 33 Y. Wang, G. Wang, H. Wang, C. Liang, W. Cai and L. Zhang, *Chem. –Eur. J.*, 2010, **16**, 3497–3503.
- 34 K. K. Zeynep, B. Recep, H. K. İbrahim and E. Mehmet, *J. Magn. Magn. Mater.*, 2015, **374**, 298–306.
- 35 X. W. Li, L. Wang, L. Zhang and S. P. Zhuo, *Appl. Surf. Sci.*, 2017, **419**, 586–594.



- 36 Y. Zhao, L. Xu and J. Yan, *J. Alloys Compd.*, 2017, **726**, 608–617.
- 37 P. Zhao, X. K. Ye, Y. C. Zhu, H. D. Jiang, L. L. Wang, Z. Y. Yue, Z. Q. Wan and C. Y. Jia, *Electrochim. Acta*, 2018, **281**, 717–724.
- 38 J. L. Liu, D. D. Zhu, T. Ling, A. Vasileff and S.-Z. Qiao, *Nano Energy*, 2017, **40**, 264–273.
- 39 K. S. W. Sing, D. H. Everett, R. A. W. Haul, L. Moscou, R. A. Pierotti, J. Rouquerol and T. Siemieniewska, *Pure Appl. Chem.*, 1985, **57**, 603–619.
- 40 J. Fu, B. Zhu, C. Jiang, B. Cheng, W. You and J. Yu, *Small*, 2017, **13**, 1603938.
- 41 S. Gao, G. Li, Y. Liu, H. Chen, L. Feng, Y. Wang, M. Yang, D. Wang, S. Wang and X. Zou, *Nanoscale*, 2017, **7**, 2306–2316.
- 42 H. Chen, Y. Q. Zheng, B. Cheng, J. G. Yu and C. J. Jiang, *J. Alloys Compd.*, 2018, **735**, 1041–1051.
- 43 Y. Gao, Y. Li, L. Zhang, H. Huang, J. J. Hu, S. Shah and X. G. Su, Adsorption and removal of tetracycline antibiotics from aqueous solution by graphene oxide, *J. Colloid Interface Sci.*, 2012, **368**, 540–546.
- 44 E. Daneshvar, A. Vazirzadeh, A. Niazi, M. Kousha, M. Naushad and A. Bhatnagar, *J. Cleaner Prod.*, 2017, **152**, 443–453.
- 45 M. Naushad, *Chem. Eng. J.*, 2014, **235**, 100–108.
- 46 M. Naushad, T. Ahamad, B. M. Al-Maswari, A. A. Alqadami and S. M. Alshehri, *Chem. Eng. J.*, 2017, **330**, 1351–1360.
- 47 Y. Q. Zheng, B. C. Zhu, H. Chen, W. You, C. J. Jiang and J. G. Yu, *J. Colloid Interface Sci.*, 2017, **504**, 688–696.
- 48 M. A. Ulbarri, I. Pavlovic, C. Barriga, M. C. Hermosun and J. Cornejo, *Appl. Clay Sci.*, 2001, **18**, 17–27.
- 49 C. S. Lei, X. F. Zhu, B. C. Zhu, C. J. Jiang, Y. Le and J. G. Yu, *J. Hazard. Mater.*, 2017, **321**, 801–811.
- 50 I. Langmuir, *J. Am. Chem. Soc.*, 1917, **38**, 102–105.
- 51 H. M. F. Freundlich, *Z. Phys. Chem.*, 1906, **57**, 385–470.
- 52 H. Y. Zhu, R. Jiang, Y. Q. Fu, R. R. Li, J. Yao and S. T. Jiang, *Appl. Surf. Sci.*, 2016, **369**, 1–10.
- 53 X. F. Wu, W. Wang, F. Li, S. Khaimanov, N. Tsidaeva and M. Lahoubi, *Appl. Surf. Sci.*, 2016, **389**, 1003–1011.
- 54 C. S. Lei, M. Pi, C. J. Jiang, B. Cheng and J. G. Yu, *J. Colloid Interface Sci.*, 2017, **490**, 242–251.
- 55 J. Zhou, Z. Zhang, B. Cheng and J. Yu, *Chem. Eng. J.*, 2012, **211**, 153–160.
- 56 M. K. Rai, G. Shahi, V. Meena, R. Meena, S. Chakraborty, R. S. Singh and B. N. Rai, *Resour.-Effic. Technol.*, 2016, **2**, 63–S70.
- 57 G. Sharma, M. Naushad, A. Kumar, S. Rana, S. Sharma, A. Bhatnagar, F. J. Stadler, A. A. Ghfar and M. R. Khan, *Process Saf. Environ. Prot.*, 2017, **109**, 301–310.
- 58 A. B. Albadarin, M. N. Collins, M. Naushad, S. Shirazian, G. Walker and C. Mangwandi, *Chem. Eng. J.*, 2017, **307**, 264–272.
- 59 M. Naushad, T. Ahamad, G. Sharma, A. H. Al-Muhtaseb, A. B. Albadarin, M. M. Alam, Z. A. AlOthman, S. M. Alshehri and A. A. Ghfar, *Chem. Eng. J.*, 2016, **300**, 306–316.
- 60 A. A. Alqadami, M. Naushad, Z. A. AlOthman and A. A. Ghfar, *ACS Appl. Mater. Interfaces*, 2017, **9**, 36026–36037.
- 61 A. A. Alqadami, M. Naushad, M. A. Abdalla, T. A. Zeid and A. A. Saad, *J. Cleaner Prod.*, 2017, **156**, 426–436.
- 62 A. Kumar, A. Kumar, G. Sharma, A. H. Al-Muhtaseb, M. Naushad, A. A. Ghfar and F. J. Stadler, *Chem. Eng. J.*, 2018, **334**, 462–478.

