

Cite this: *RSC Adv.*, 2019, 9, 22289

Heat treatment to improve the wear resistance of PTFE/PMMA composites

Dapeng Gu,^{ab} Longxiao Zhang,^a Suwen Chen,^{cd} Kefeng Song,^a Deng Pan,^{ab} Bingchao Yang^d and Shouyao Liu^a

Polytetrafluoroethylene/poly(methyl methacrylate) (PTFE/PMMA) composites were prepared by a self-curing method. The influence of heat treatment processes on the friction and wear behaviors of PTFE/PMMA composites against bearing steel balls were studied by a ball-on-disk tribometer. The thermal performance of PTFE/PMMA composites with heat treatment was analyzed by Thermogravimetric Analysis (TGA). The surface morphologies and element distribution of PTFE/PMMA composites in a PMMA matrix were detected by Field Emission Scanning Electron Microscopy (FE-SEM) and Energy Dispersive Spectroscopy (EDS). The results indicated that the wear rates of PTFE/PMMA composites with different heat treatments significantly declined compared with the unheated treatment composite. The wear rate of the PTFE/PMMA composite decreased firstly and then increased with molding temperature and time increasing, and reduced with the molding pressure increasing. The main wear mechanisms of PTFE/PMMA composites with different heat treatments were fatigue wear and abrasive wear.

Received 11th June 2019

Accepted 13th July 2019

DOI: 10.1039/c9ra04362d

rsc.li/rsc-advances

1. Introduction

Poly(methyl methacrylate) (PMMA) is an extensively used polymer material which benefits from excellent physical and mechanical properties. However, pure PMMA is rarely used as the tribological material due to its relatively poor wear resistance and heat resistance.^{1–3} In Polymer Tribology, wear mechanisms include abrasive wear, adhesive wear and fatigue wear.^{4,5} Abrasive wear is a material-loss phenomenon due to the extrusion and movement of hard particles on the friction surface. Adhesive wear is the adhesion and tearing of micro-local materials during friction. While fatigue wear is the peeling of small pieces of material under the repeated action of high contact compressive stress. In the past few years, a number of improvement methods have been extensively carried out in order to enhance the wear resistance properties of polymers.

Modification by special fillers is one of the successful ways to improve the tribological and mechanical properties of polymer materials.^{6–9} Therefore, many studies on filling modification of PMMA based composites have been reported.^{10–15} For example, filling nano-calcium oxide (CaO),¹⁰ zirconium oxide (ZrO₂),¹¹ silica,¹² nano-calcium carbonate (CaCO₃),¹³ carbon nanotubes (CNTs)¹⁴ and SiO₂ + titanium oxide (TiO₂)¹⁵ into PMMA can

obviously reduce the friction coefficient or wear rate. In addition, the friction and wear of PMMA based composite can be obviously reduced by either filling PTFE alone¹⁶ or PTFE/Cu/Al₂O₃ in synergetic action.¹⁷

Heat treatment is also considered as one of the effective methods to improve the mechanical and tribological properties of polymers.¹⁸ Ayman *et al.*¹⁹ found that heat treatment process could improve the tribological properties of polyamide (PI). Wang *et al.*²⁰ studied the effect of different molding pressures on the mechanical and tribological properties of ultra-high molecular weight polyethylene (UHMWPE) and found that the molding pressures were conducive to decrease the friction coefficient and wear rate of UHMWPE. Sarkar *et al.*²¹ found that the friction coefficient and wear rate of polyamide 6 (PA6) were both decreased by heat treatment. Therefore, the friction coefficient and wear rate of polymer can be reduced by the appropriate heat treatment process.

However, there are few literature studies focusing on the influence of heat treatment process on the tribological performances of PMMA based composites. In this paper, self-curing PTFE/PMMA composites were prepared and the dry sliding tribological behavior of PTFE/PMMA composites with various molding pressures, molding temperatures and molding times were studied.

2. Experimental

2.1. Material

A commercial acrylic product of PMMA powder was supplied by Arkema, Serquigny, France. The methyl methacrylate (MMA)

^aSchool of Mechanical Engineering, Yanshan University, Qinhuangdao 066004, China^bAviation Key Laboratory of Science and Technology on Generic Technology of Self-Lubricating Spherical Plain Bearing, Yanshan University, Qinhuangdao 066004, China^cDepartment of Environmental and Chemical Engineering, Yanshan University, Qinhuangdao 066004, China. E-mail: chensuwende@163.com^dSchool of Physics and Physical Engineering, Qufu Normal University, Qufu, 273165, China

($\geq 99.5\%$) monomer liquid, PTFE (5 μm) powder and catechol ($\geq 99.5\%$) were all supplied by Aladdin Reagent Co. Ltd., Shanghai, China. The dibenzoyl peroxide (BPO, $\geq 98\%$; containing water 28–32%), *N,N*-dimethyl-*p*-toluidine (Dmpt, 98%) were both supplied by Sinopharm Group Chemical Reagent Co. Ltd., Shanghai, China.

2.2. Specimen preparation

The PMMA matrix was synthesized by self-curing at room temperature. The synthesis process of PMMA based composite was introduced in detail in ref. 16 and 17. In this paper, the mass ratio of the powder mixture to the liquid mixture was 3 : 2 and the mass ratio of PTFE was 25 wt%.

2.3. Heat treatment

The PTFE/PMMA composites were secondary molding by means of hot press molding technique. Heat treatment parameters of PTFE/PMMA composites are listed in Table 1. At the end of each run of heat treatment process, the resulting specimens were cooled along with the furnace. The mold for heat treatment of PTFE/PMMA composite was made of steel. The inner diameter of the steel mold was the same as PTFE/PMMA composite fabricated by self-curing.

2.4. Material characterization

The worn surfaces of PTFE/PMMA composites were examined by Field Emission Scanning Electron Microscopy (FE-SEM, Sigma 500, Carl Zeiss, Oberkochen, Germany). To establish the degree of PTFE dispersion within the PMMA matrix, the worn and fractured surfaces were observed by FE-SEM and Energy Dispersive Spectroscopy (EDS). Thermal properties of PTFE/PMMA composites were studied by Thermogravimetric Analysis (TGA, STA449C, NETZSCH, Germany). And PTFE/PMMA composite were heated from 35 $^{\circ}\text{C}$ to 500 $^{\circ}\text{C}$ with the temperature increasement rate of 10 $^{\circ}\text{C min}^{-1}$ in the presence of argon atmosphere (100 ml min^{-1}).

2.5. Tribology tests

The friction and wear tests were carried out in a ball-on-disk tribometer (CSM Instruments, Peseux, Switzerland) in which the stationary bearing steel ball was in contact with a rotating polymer disk. The size of the ball (bearing steel, AISI E52100, hardness of HRC 60–65, $R_a < 0.2 \mu\text{m}$) was 6 mm diameter. The

size of PTFE/PMMA composite was 50 mm diameter and 10 mm height. Before each test, the ball was cleaned for 30 min in alcohol using an ultrasonic cleaner. The PTFE/PMMA composites were polished ($R_a = 0.4\text{--}0.6 \mu\text{m}$) by a polishing machine and washed with alcohol and deionized water, then ultrasonic cleaned for 30 min in deionized water. The PTFE/PMMA composites were performed at ambient temperature with sliding speed of 0.2 m s^{-1} , normal load of 5 N and total sliding distance of 500 m. In order to ensure the correctness of the data, each group of experiment was repeated three times.

At the end of the experiment, the friction coefficient curve with sliding distance could be obtained directly by the CSM tribometer. The average value of the friction coefficient was calculated from five points of relative stationary part. The wear volume was measured by a conscan confocal optical profilometer (Anton Paar Compact Platform Company, Graz, Austria). The wear performance was expressed by the specific wear rate calculated by the following equation,

$$\omega = \Delta V / (FL) \quad (1)$$

where ω is the specific wear rate in $\text{mm}^3 (\text{N m})^{-1}$, ΔV is the volume loss in mm^3 , F is the applied normal load in N, L is the total sliding distance in m.

3. Results and discussion

3.1. Element distribution analysis

Fig. 1 shows the SEM photo and the distribution of C, F and O elements by EDS in the section of PTFE/PMMA composites. C element is mainly from PMMA matrix and PTFE. O element mainly comes from PMMA matrix. F element originates from PTFE. According to the distribution of F element, it could be found that the distribution of PTFE was relatively uniform in the PMMA matrix.

3.2. Thermal properties

3.2.1. Effect of molding temperatures. The Thermogravimetric (TG) curves of PTFE/PMMA composites under different molding temperatures are shown in Fig. 2. And the results are summarized in Table 2. 5 and 10 wt% decomposition of PTFE/PMMA composites were measured and designated as T_5 and T_{10} , respectively. T_c was defined as the complete decomposition temperature. From Fig. 2 and Table 2, T_5 and T_{10} of PTFE/PMMA

Table 1 Heat treatment parameters of PTFE/PMMA composites

Test number	Molding pressure/Mpa	Molding temperature/ $^{\circ}\text{C}$	Molding time/min
1	10	80	15
2	10	110	15
3	10	140	15
4	10	110	5
5	10	110	25
6	5	110	15
7	15	110	15



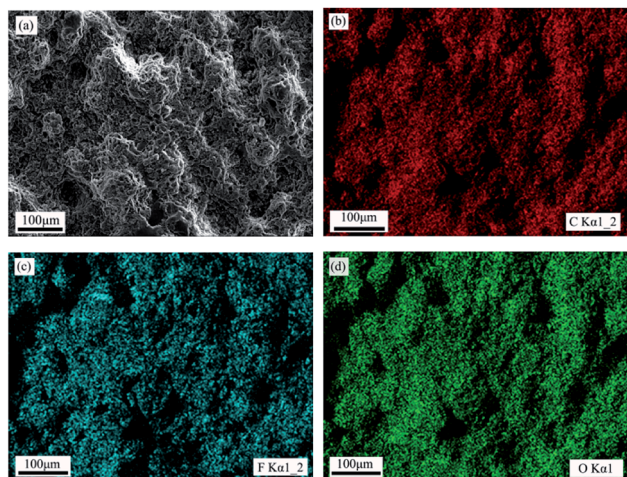


Fig. 1 The section's SEM photo and EDS mappings of characteristic elements for PTFE/PMMA composites under 10 MPa, 110 °C and 15 min. (a) SEM; (b) C element; (c) F element; (d) O element.

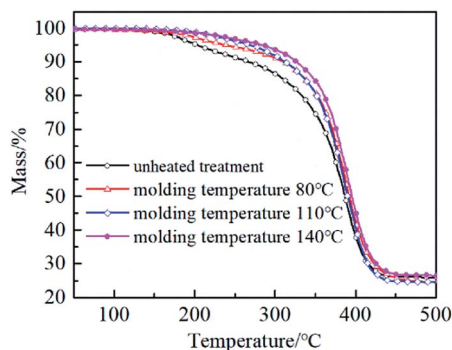


Fig. 2 TG curves of PTFE/PMMA composites under different molding temperatures (molding pressure is 10 MPa and molding time is 15 min).

Table 2 Thermal decomposition temperatures of PTFE/PMMA composites under different molding temperatures

Molding temperatures	T_5 (°C)	T_{10} (°C)	T_c (°C)
Unheated treatment	207	266	444
80 °C	243	309	448
110 °C	274	314	450
140 °C	280	327	453

composites under different molding temperatures were in the range of 243–280 °C and 309–327 °C respectively, which were significantly higher than that of unheated treatment PTFE/PMMA composites. This indicates that molding temperatures could improve the thermal stability of PTFE/PMMA composites. Fouad and Pegoretti *et al.*^{22,23} found that the mechanical properties of crystalline polymers (such as UHMWPE and polyethylene (PE)) were improved by heat treatment process. This enhancement is achieved by increasing crystallinity. For amorphous and self-curing PMMA, the main reasons for the

improvement of thermal properties may be the fact that the residual small molecules in PMMA matrix will continue to participate in the polymerization reaction under the action of temperature, which leads to the increase of the molecular weight of PMMA. T_5 values of PTFE/PMMA composites under different molding temperatures increased with the molding temperature increasing. T_5 value of PTFE/PMMA composite with molding temperature 140 °C was 37 °C higher than that of composite with molding temperature 80 °C. With the increase of molding temperature, PTFE/PMMA composites gradually transit from glassy state to highly elastic state. And in this process, PTFE particles are more dispersed with the expansion of PMMA matrix, which effectively prevents the diffusion of degradation products in PMMA matrix and slows down the thermal degradation process.^{24–26}

3.2.2. Effect of molding times. The TG curves of PTFE/PMMA composites under different molding times are shown in Fig. 3. And the results are summarized in Table 3. From Fig. 3 and Table 3, molding time had also importance to thermal properties of PTFE/PMMA composites when the molding pressure and temperature were constant. Compared with the unheated treatment PTFE/PMMA composites, T_5 values of composites under different molding times were 67–80 °C higher. Within the range of the molding time (5–25 min), the thermal decomposition temperature fluctuated with the molding time increasing. T_5 and T_{10} values of PTFE/PMMA composites were optimal when the molding time was 5 min.

3.2.3. Effect of molding pressures. The TG curves of PTFE/PMMA composites under different molding pressures are shown in Fig. 4. And the results are summarized in Table 4. From Fig. 4 and Table 4, the thermal properties of PTFE/PMMA composites could be improved significantly by changing the molding pressure when the molding temperature and time were constant. The largest values of T_5 and T_{10} of PTFE/PMMA composites were 296 °C and 337 °C respectively, under the molding pressure 15 MPa.

Compared with the unheated treatment PTFE/PMMA composites, T_5 and T_{10} values of PTFE/PMMA composites increased about 89 °C and 71 °C respectively. This can be explained by the fact that the compactness of the composite becomes better with the molding pressure increasing, and the

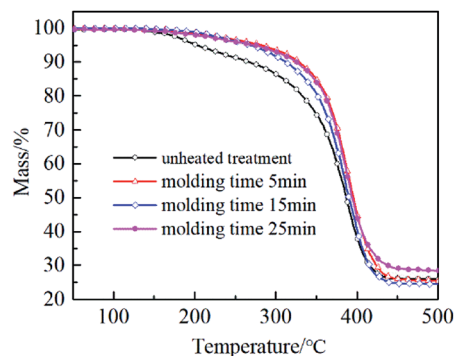
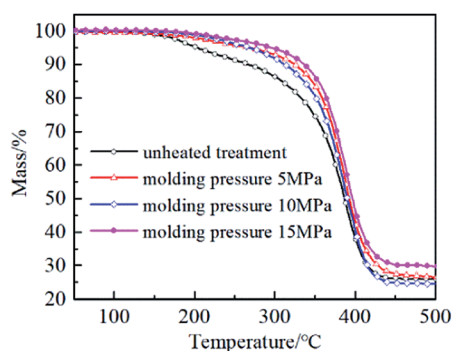


Fig. 3 TG curves of PTFE/PMMA composites under different molding times (molding pressure is 10 MPa and molding temperature is 110 °C).



Table 3 Thermal decomposition temperatures of PTFE/PMMA composites under different molding times

Molding times	T_5 (°C)	T_{10} (°C)	T_c (°C)
Unheated treatment	207	266	444
5 min	287	329	444
15 min	274	314	450
25 min	278	324	453


**Fig. 4** TG curves of PTFE/PMMA composites under different molding pressures (molding time is 15 min and molding temperature is 110 °C).**Table 4** Thermal decomposition temperatures of PTFE/PMMA composites under different molding pressures

Molding pressures	T_5 (°C)	T_{10} (°C)	T_c (°C)
Unheated treatment	207	266	444
5 MPa	270	324	453
10 MPa	274	314	450
15 MPa	296	337	460

interaction force between the long molecular chains in the matrix becomes stronger.^{20,27} Thus the thermal decomposition temperature rose.

3.3. Friction and wear behaviors


3.3.1. Effect of molding temperatures. The effects of molding temperatures on the friction coefficient and wear rate of PTFE/PMMA composite are shown in Fig. 5. It is evident from Fig. 5 that the friction coefficients of PTFE/PMMA composites had little difference under various molding temperatures. The friction coefficients of different molding temperatures lay in the range of 0.142–0.145 and the lowest friction coefficient was observed when the molding temperature was 110 °C. But there were obvious difference about the wear rates of PTFE/PMMA composites with different molding temperatures. The lowest wear rate of PTFE/PMMA composite was about $3.95 \times 10^{-6} \text{ mm}^3 (\text{N m})^{-1}$ under the molding temperature 110 °C. This was obviously lower than the unheated treatment composite. Table 2 shows that the molding temperature improves the thermal properties of PTFE/PMMA composites, which may be the reason for the better wear resistance of heat treated composites. In

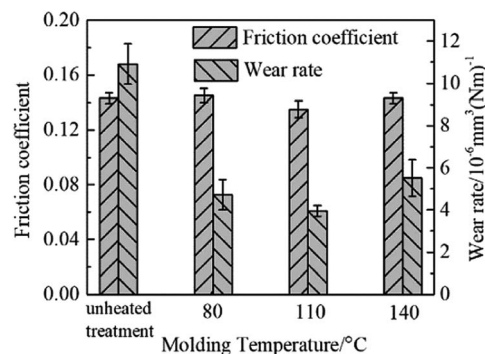**Fig. 5** Effect of the molding temperature on the friction coefficient and wear rate of PTFE/PMMA composite (molding pressure is 10 MPa and molding time is 15 min).

addition, the wear rate firstly decreased and then increased within the molding temperature 80–140 °C. Compared with the PTFE/PMMA composites under the molding temperature 80 °C and 140 °C, the wear rate under the molding temperature 110 °C decreased about 16% and 28%, respectively.

3.3.2. Effect of molding times. The effects of molding times on the friction coefficient and wear rate of PTFE/PMMA composite are shown in Fig. 6. From Fig. 6, it is found that the friction coefficients under different molding times of PTFE/PMMA composites had slight fluctuation and the lowest friction coefficient was about 0.142 under the molding time 15 min. As it can be seen, the smallest wear rate of PTFE/PMMA composite was almost $3.95 \times 10^{-6} \text{ mm}^3 (\text{N m})^{-1}$ with the molding time 15 min. Compared with PTFE/PMMA composite under the molding time 25 min, the wear rate of PTFE/PMMA composite under the molding time 15 min declined about 35%. Similarly, compared with the unheated treatment PTFE/PMMA composite, the wear rates with different molding times significantly decreased.

3.3.3. Effect of molding pressures. The effect of molding pressure on the friction coefficient and wear rate of PTFE/PMMA composite is shown in Fig. 7. From Fig. 7, the friction coefficient of PTFE/PMMA composite decreased slightly with the molding pressure increasing. The friction coefficient with

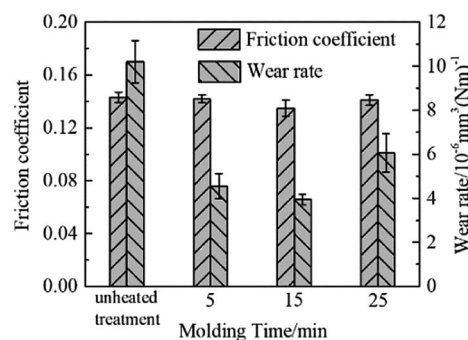**Fig. 6** Effect of the molding time on the friction coefficient and wear rate of PTFE/PMMA composite (molding temperature is 110 °C and molding pressure is 10 MPa).

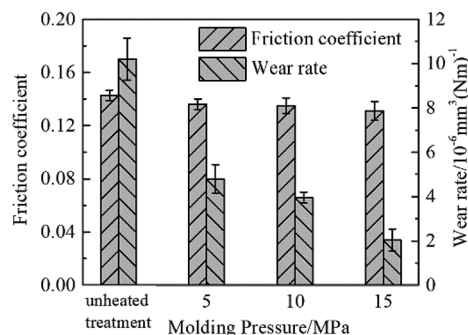


Fig. 7 Effect of the molding pressure on the friction coefficient and wear rate of PTFE/PMMA composite (molding temperature is 110 °C and molding time is 15 min).

the molding pressure 15 MPa was relatively low, showing an average value 0.140. It is seen that the wear rate of PTFE/PMMA composite could obvious reduce with the molding pressure increasing. The lowest wear rate was $2.04 \times 10^{-6} \text{ mm}^3 (\text{N m})^{-1}$ under the molding pressure 15 MPa and decreased approximately 58% comparing with that under the molding pressure 5 MPa. The main reason is that the hardness²⁰ and thermal stability of the composite increase with the molding pressure, so the PTFE/PMMA composite performed better wear resistance.

3.4. SEM analysis

The typical morphologies of the worn surfaces of PTFE/PMMA composites under different heat treatments were investigated by SEM, as shown in Fig. 8. It can be seen that there are many circular areas with different sizes on the PTFE/PMMA composite surfaces. In order to determine the compositions of those circular areas, EDS of typical elements were recoded and the results were shown in Fig. 8(f). It indicates that those circular areas are PMMA matrix. Meanwhile, it can be seen that the circular areas tended to become larger with the molding temperature and time increasing. Ref. 16 has proved that pure PMMA has poor wear resistance. When more PMMA matrix was exposed, the wear rates of composites began to increase. This may be the reason that the wear rate increased when the molding temperature is high (140 °C) and the molding time is long (25 min). Fig. 8(a), (c) and (f) show that the worn surfaces of PTFE/PMMA composite are accompanied by severe abrasive wear, which correspond to the relatively high wear rate. While Fig. 8(b) and (f) show a relatively stable worn surface with only slight scratch, which indicates that there is slight wear during the wear process of PTFE/PMMA composite. This is consistent with the results of the lower friction coefficient and wear rate described above (Fig. 5–7). However, Fig. 8(b) (molding pressure 10 MPa) shows many spalling on the worn surfaces of PTFE/PMMA composites. It indicates that adhesion wear occurs on the worn surface. And this eventually leads to the wear rate higher than Fig. 8(g) (molding pressure 15 MPa). From Fig. 8(a)–(g), there are some cracks on the worn surfaces. This indicates

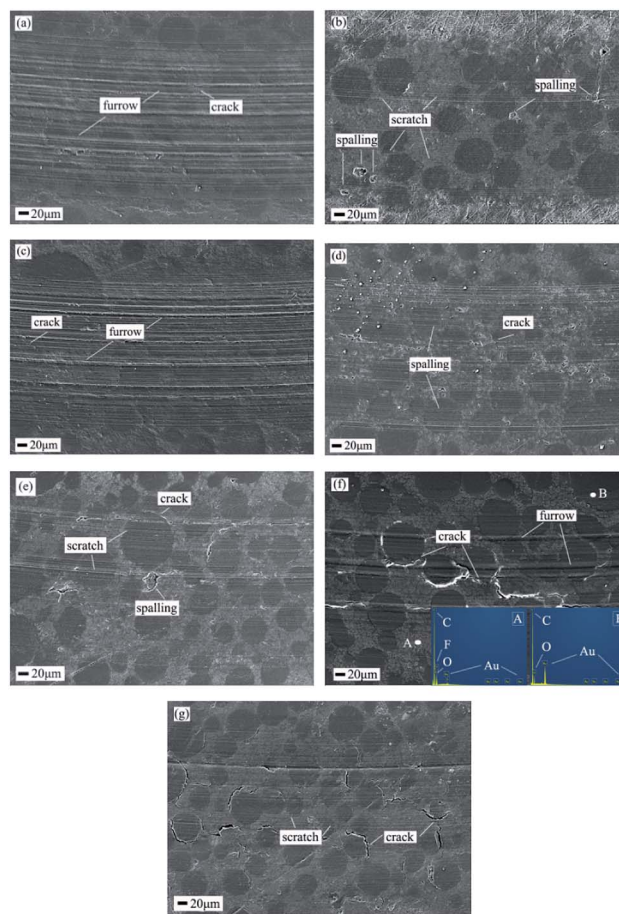


Fig. 8 SEM pictures of the representative worn surface morphologies for PTFE/PMMA composites under different molding pressures, temperatures and times. (a) 10 MPa, 80 °C, and 15 min; (b) 10 MPa, 110 °C and 15 min; (c) 10 MPa, 140 °C and 15 min; (d) 10 MPa, 110 °C and 5 min; (e) 10 MPa, 110 °C and 25 min; (f) 5 MPa, 110 °C and 15 min; (g) 15 MPa, 110 °C and 15 min.

that the fatigue wear occurs during the wear process of PTFE/PMMA composites.

4. Conclusions

(1) Compared with the unheated treatment PTFE/PMMA composite, the thermal properties of the composites significantly increased under different heat treatment processes. Within the parameters of heat treatment, the temperature of mass loss 5 wt% (T_5) increased with the increasing of the molding temperature and pressure, but fluctuated with the molding time increasing.

(2) Compared with the unheated treatment PTFE/PMMA composite, the friction coefficient changed slightly under different heat treatment conditions, but the wear rate significantly decreased.

(3) The wear rate of PTFE/PMMA composite decreased firstly and then increased with the molding temperature and time increasing, and reduced with the molding pressure increasing. When the molding pressure was 15 MPa, molding temperature



was 110 °C and molding time was 15 min, the wear rate of PTFE/PMMA composite was the lowest.

(4) The main wear mechanisms of PTFE/PMMA composite under different heat treatments were fatigue wear and abrasive wear. And there was slight adhesive wear.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

This work was supported by National Natural Science Foundation of China (Grant No. 51605418), Natural Science Foundation of Hebei Province (Grant No. E2016203103), Youth Projects of Department of Education of Hebei Province (Grant No. QN2017148).

Notes and references

- 1 Z. B. Cai, M. H. Zhu, S. Yang, X. B. Xiao, X. Z. Lin and H. Y. Yu, *Wear*, 2011, **271**, 2242–2251.
- 2 M. M. Demir, M. Memesa, P. Castignolles and G. Wegner, *Macromol. Rapid Commun.*, 2006, **27**, 763–770.
- 3 S. Gross, D. Camozzo, V. Di Noto, L. Armelao and E. Tondello, *Eur. Polym. J.*, 2007, **43**, 673–696.
- 4 C. Dong, C. Yuan, X. Bai, X. Yan and Z. Peng, *RSC Adv.*, 2014, **4**, 19034–19042.
- 5 C. Gao, G. Zhang, T. Wang and Q. Wang, *RSC Adv.*, 2016, **6**, 51247–51256.
- 6 J. G. Xu, H. B. Yan and D. G. Gu, *Mater. Des.*, 2014, **61**, 270–274.
- 7 M. Kalin, M. Zalaznik and S. Novak, *Wear*, 2015, **332**–**333**, 855–862.
- 8 V. Pettarin, M. J. Churrua, D. Felhös and K. J. Karger, *Wear*, 2010, **269**, 31–45.
- 9 L. Chang, Z. Zhang, H. Zhang and A. K. Schlarb, *Compos. Sci. Technol.*, 2006, **66**, 3188–3198.
- 10 L. D. Aguilera-Camacho, C. Hernández-Navarro, K. J. Moreno and J. S. García-Miranda, *J. Coat. Technol. Res.*, 2015, **12**, 347–355.
- 11 A. Akinci, S. Sen and U. Sen, *Composites, Part B*, 2014, **56**, 42–47.
- 12 L. Y. Lin and D. E. Kim, *Tribol. Int.*, 2011, **44**, 1926–1931.
- 13 M. Avella, M. E. Errico and E. Martuscelli, *Nano Lett.*, 2001, **1**, 213–217.
- 14 Z. Yang, B. Dong, Y. Huang, L. Liu, F. Y. Yan and H. L. Li, *Mater. Lett.*, 2005, **59**, 2128–2132.
- 15 G. T. Gu, Z. J. Zhang and H. X. Dang, *Appl. Surf. Sci.*, 2004, **221**, 129–135.
- 16 D. P. Gu, L. X. Zhang, S. W. Chen, K. F. Song and S. Y. Liu, *Polymers*, 2018, **10**, 966.
- 17 D. P. Gu, L. X. Zhang, S. W. Chen, K. F. Song and S. Y. Liu, *J. Appl. Polym. Sci.*, 2018, **135**, 46705.
- 18 A. A. Ayman, *Int. J. Mater. Chem. Phys.*, 2015, **1**, 132–140.
- 19 A. A. Ayman, E. B. Zeidan, A. M. Hamed and W. Y. Ali, *EGTRIB Journal of the Egyptian Society of Tribology*, 2010, **7**, 52–64.
- 20 S. B. Wang and S. R. Ge, *Wear*, 2007, **263**, 949–956.
- 21 A. D. Sarkar, *Friction and Wear*, Academic Press, London, 1980.
- 22 H. Fouad, A. H. I. Mourad and D. C. Barton, *Polym. Test.*, 2005, **24**, 549–556.
- 23 A. Pegoretti, M. Ashkar, C. Migliaresi and G. Marom, *Compos. Sci. Technol.*, 2000, **60**, 1181–1189.
- 24 T. Kashiwagi, F. Du, J. F. Douglas, K. I. Winey, R. H. Harris and J. R. Shields, *Nat. Mater.*, 2005, **4**, 928.
- 25 L. Chen, Z. Huang, G. Dong, C. He, L. Liu, Y. Hu and Y. Li, *Polym. Compos.*, 2009, **30**, 239–247.
- 26 L. Q. Cui, N. H. Tarte and S. L. Woo, *Macromolecules*, 2008, **41**, 4268–4274.
- 27 N. C. Prasnis and K. Ramani, *J. Mater. Sci.*, 1998, **9**, 165–172.

