

Cite this: *RSC Adv.*, 2019, 9, 33465

# In-chain functionalized syndiotactic 1,2-polybutadiene by a Ziegler–Natta iron(III) catalytic system†

Shanshan Liang,<sup>ab</sup> Huaqiang Zhang,<sup>c</sup> Rixin Cong,<sup>c</sup> Heng Liu,<sup>b</sup> Feng Wang,<sup>\*bd</sup> Yanming Hu<sup>b</sup> and Xuequan Zhang<sup>\*b</sup>

Copolymerization of 1,3-butadiene with four 1-substituted 1,3-diene comonomers bearing amino and alkoxy groups by a Ziegler–Natta iron(III) catalytic system to access in-chain functionalized syndiotactic 1,2-polybutadiene is reported herein. The polar comonomer content can be easily regulated by varying the comonomer loadings or polymerization conditions, affording functionalized syndiotactic 1,2-polybutadiene with different amounts of functionalities. The incorporation of a polar comonomer showed little influence on the 1,2-content and stereoregularity of the resulting polymers, giving a 1,2-structure as high as ~85% and an *rrrr* pentad of 81.0%. Significantly improved surface properties of the polymers was obtained after incorporation of polar comonomer, as revealed from the remarkably decreased water contact angles.

Received 19th August 2019  
Accepted 8th October 2019

DOI: 10.1039/c9ra06499k

rsc.li/rsc-advances

## Introduction

Syndiotactic 1,2-polybutadiene (sPB), a promising crystalline material that bears alternately located vinyl groups on opposite positions along the polymer main chain,<sup>1</sup> was firstly synthesized by Natta *et al.*,<sup>2</sup> and later successfully industrialized by the Japan Synthetic Rubber Co. Ltd. (JSR) by using a Co/AlR<sub>3</sub>/CS<sub>2</sub> catalytic system.<sup>3–7</sup> Due to its unique mechanical properties that originate from the combination of properties of plastic and rubber, sPB reveals a wide range of applications in the fields of fibres, films, moulded articles, and recently has been used as synthetic rubber reinforcing fillers.<sup>8–12</sup> Despite this, the inherent shortfall of low surface energy makes sPB display inferior properties with respect to adhesion, toughness, paintability, miscibility and rheological properties. Improving the hydrophilicity and developing functionalized sPB has been the long-term pursuit for scientists.

Similar to achieving other functionalized polyolefin materials,<sup>13–15</sup> two strategies are generally available for accessing

functionalized sPB, *i.e.* post functionalization of polymer products and *in situ* functionalization by statistical copolymerization with polar monomers. In the past few years, colossal advances have been made for the former strategy, due to the presence of highly active pendent vinyl substituents.<sup>16–22</sup> For instance, Mecking, Ndoni, *et al.*, presented efficient functionalization of sPB *via* thiol–ene reaction, through which various types of functional groups, including ester, L-cysteine, carboxylic acid were successfully introduced;<sup>23–25</sup> Linford and Tang reported hydrosilation and hydrozirconation of 1,2-polybutadiene (1,2-PB) by Si–H and Zr–H reagents, and provided a platform for accessing diversified functional 1,2-PBs.<sup>26,27</sup> Despite of the facility and efficiency in these reports, all of them were built on the sacrifice of pendent double bonds, which might cause irreversible damage to the inherent nature of sPB, such as crystallinity,<sup>28</sup> molecular weights,<sup>16</sup> and even causing cross-linking.<sup>28</sup> On the other hand, incorporation of functional groups through coordination copolymerization strategy not only has a good control on the regio- and/or stereo-regularities, but also is able to regulate the comonomer sequence and content conveniently by varying the feed ratio. Nevertheless, up to date, no reports on this strategy were involved, perhaps due to the highly electrophilic nature of the active species, which are likely to be deactivated in the presence of heteroatom-containing polar comonomers. Moreover, directly coordination copolymerization of 1,3-butadiene with traditional polar monomers, such as methyl methacrylate, vinyl acetate, *etc.*, is strikingly difficult due to the different mechanisms presented in diene and monoene polymerization,<sup>29</sup> alternative comonomers can be inspired from Cui's and Mecking's recent reports, in which the preparation of in-chain functionalized *cis*-1,4

<sup>a</sup>College of Material Science and Engineering, Shenyang University of Chemical Technology, Shenyang 110142, China

<sup>b</sup>CAS Key Laboratory of High-Performance Synthetic Rubber and Its Composite Materials, Changchun Institute of Applied Chemistry, Chinese Academy of Sciences, 5625 Renmin Street, Changchun 130022, P. R. China. E-mail: fengwang@ciac.ac.cn; xqzhang@ciac.ac.cn

<sup>c</sup>Lanzhou Petrochemical Research Center, Petrochemical Research Institute, PetroChina, Lanzhou, 730060, China

<sup>d</sup>School of Chemical Engineering, Changchun University of Technology, Changchun, Jilin, China

† Electronic supplementary information (ESI) available. See DOI: 10.1039/c9ra06499k



polydienes by using a type of new comonomers (Scheme 1).<sup>30–34</sup> Alternatively, this unique comonomer, *i.e.* functional-group-substituted 1,3-butadiene, can also be polymerized in a 3,4-manner through a  $\eta^3$ -coordinated  $\pi$ -allylic unit,<sup>35</sup> and therefore serves the best candidate for accessing functionalized sPB.


We have been interested in tapping effective Ziegler–Natta iron(III) catalytic systems to syndiotactically polymerize 1,3-butadiene,<sup>36–39</sup> to circumvent the environmental toxicity and bad-smelling issues that encountered in the industrialized Co(II)-based systems. In the present study, we disclose the first example of functionalized sPB prepared through copolymerization strategy, detailed catalytic behaviours of the iron(III) catalytic system together with various functionalized sPB with different types and amounts of functionalities were systematically evaluated.

## Experimental section

### General considerations

Iron(III) acetylacetonate (Fe(acac)<sub>3</sub>) and diethyl phosphite (DEP) were purchased from J&K (Beijing, China) and diluted to 0.06 mol L<sup>-1</sup> solution in toluene. Al(<sup>*i*</sup>Bu)<sub>3</sub> (1.0 mol L<sup>-1</sup> in toluene) was a commercial product of Akzo Nobel and used as received. 1,3-Butadiene was supplied by Jinzhou Petrochemical Corporation in China and purified by passing through four columns packed with activated molecular sieves (4 Å) and KOH prior to use. Toluene and THF were refluxed over sodium/diphenylketyl under nitrogen and then distilled before use. All other commercial chemicals were used as received.

<sup>1</sup>H NMR spectra were recorded on a Varian Unity-400 MHz spectrometer at 125 °C in C<sub>6</sub>D<sub>4</sub>Cl<sub>2</sub>. IR spectra was recorded on BRUKE Vertex-70 FIR spectrophotometer. The molecular weights and molecular weight distributions of the polymers were estimated by gel permeation chromatography (GPC) on a PL-GPC 220 high-temperature chromatograph at 150 °C. 1,2,4-Trichlorobenzene containing 0.05% (w/v) BHT was used as eluent at a flow rate of 1.0 mL min<sup>-1</sup> and the values of *M<sub>n</sub>* and *M<sub>w</sub>*/*M<sub>n</sub>* were calculated by using polystyrene calibration. The melting points were estimated on a Q100 DSC (TA Instruments) under nitrogen atmosphere. The samples were heated and cooled down at a rate of 10 °C min<sup>-1</sup>.

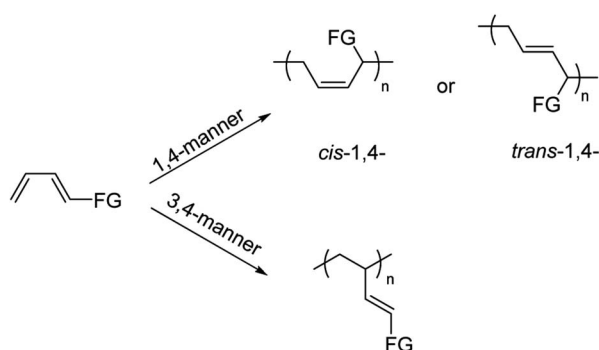

Scheme 1 Polymerization of functional-group-substituted 1,3-butadiene (1-substituted 1,3-diene was taken as an example).

### Synthesis and characterization of polar 1-substituted 1,3-dienes

All reactions were carried out under a nitrogen atmosphere in flame-dried glassware with magnetic stirring. A general procedure was as follows: allyltriphenylphosphonium bromide (20 g, 52.18 mmol) was reacted with potassium *t*-butoxide (molar ratio 1 : 1.2, dissolved in THF) in an ice bath for one hour, then 1.0 equivalent of the benzaldehyde derivative (52.18 mmol) was slowly added over 10 minutes, and the reaction was continued for 4 hours in room temperature. The reaction was quenched by addition of 150 mL of saturated aqueous ammonium chloride and then extracted with 100 mL ethyl acetate for 4 times to get crude products. The crude products were purified by silica gel chromatography (eluent: petroleum ether (or hexane) : ethyl acetate = 50 : 1) to give the target product.

#### 1-(4-Methoxy)phenyl-1,3-butadiene (a)

Yield: 7.79 g, 65%. *Z* : *E* = 60 : 40. For *E* isomer: <sup>1</sup>H NMR (400 MHz, CDCl<sub>3</sub>, ppm): 7.36 (d, 2H, H<sub>ph</sub>); 6.89 (d, 2H, H<sub>ph</sub>); 6.68 (m, 1H, -CH); 6.55–6.45 (m, 2H, -CH); 5.35 (d, 1H, -CH<sub>2</sub>); 5.20 (d, 1H, -CH<sub>2</sub>); 3.80 (s, 3H, -CH<sub>3</sub>); for *Z* isomer: <sup>1</sup>H NMR (400 MHz, CDCl<sub>3</sub>, ppm): 7.29 (d, 2H, H<sub>ph</sub>); 6.92 (m, 1H, -CH); 6.89 (d, 2H, H<sub>ph</sub>); 6.41 (m, 1H, -CH); 6.20 (t, 1H, -CH); 5.29 (d, 1H, -CH<sub>2</sub>); 5.17 (d, 1H, -CH<sub>2</sub>); 3.82 (s, 3H, -CH<sub>3</sub>). <sup>13</sup>C NMR (400 MHz, CDCl<sub>3</sub>, ppm): 159.38; 158.78; 137.48; 133.44; 132.51; 131.42; 130.33; 130.03; 129.41; 127.70; 118.97; 116.43; 114.10; 113.74; 55.23. EI-MS for C<sub>11</sub>H<sub>12</sub>O (*m/z*): 161.0 (M + H<sup>+</sup>).

#### 1-(4-*N,N*-Dimethylamino)phenyl-1,3-butadiene (b)

Yield: 7.93 g, 68%. *Z* : *E* = 57 : 43. For *E* isomer: <sup>1</sup>H NMR (400 MHz, CDCl<sub>3</sub>, ppm): 7.32 (d, 2H, H<sub>ph</sub>); 7.00 (m, 1H, -CH); 6.73–6.60 (m, 2H, H<sub>ph</sub>); 6.54–6.45 (m, 2H, -CH); 5.34 (d, 1H, -CH<sub>2</sub>); 5.18 (d, 1H, -CH<sub>2</sub>); 2.97 (s, 6H, -N(CH<sub>3</sub>)<sub>2</sub>); for *Z* isomer: <sup>1</sup>H NMR (400 MHz, CDCl<sub>3</sub>, ppm): 7.27 (d, 2H, H<sub>ph</sub>); 6.65 (m, 1H, -CH); 6.73–6.60 (m, 2H, H<sub>ph</sub>); 6.38 (m, 1H, -CH); 6.13 (t, 1H, -CH); 5.25 (d, 1H, -CH<sub>2</sub>); 5.06 (d, 1H, -CH<sub>2</sub>); 2.97 (s, 6H, -N(CH<sub>3</sub>)<sub>2</sub>). <sup>13</sup>C NMR (400 MHz, CDCl<sub>3</sub>, ppm): 149.97; 149.45; 137.78; 133.79; 130.54; 130.03; 127.64; 127.44; 125.74; 125.48; 117.77; 114.87; 112.29; 111.99; 40.30. EI-MS for C<sub>12</sub>H<sub>15</sub>N (*m/z*): 174.1 (M + H<sup>+</sup>).

#### 1-(4-Propoxy)phenyl-1,3-butadiene (c)

Yield: 4.47 g, 46%. *Z* : *E* = 83 : 17. For *E* isomer: <sup>1</sup>H NMR (400 MHz, CDCl<sub>3</sub>, ppm): 7.34 (d, 2H, H<sub>ph</sub>); 6.89 (d, 2H, H<sub>ph</sub>); 6.68 (m, 1H, -CH); 6.53 (t, 1H, -CH); 6.49 (t, 1H, -CH); 5.37 (d, 1H, -CH<sub>2</sub>); 5.21 (d, 1H, -CH<sub>2</sub>); 3.92 (s, 2H, -O-CH<sub>2</sub>-); 1.75 (m, 2H, -CH<sub>2</sub>-); 1.05 (t, 3H, -CH<sub>3</sub>); for *Z* isomer: <sup>1</sup>H NMR (400 MHz, CDCl<sub>3</sub>, ppm): 7.29 (d, 2H, H<sub>ph</sub>); 6.92 (m, 1H, -CH); 6.89 (d, 2H, H<sub>ph</sub>); 6.41 (d, 1H, -CH); 6.21 (t, 1H, -CH); 5.30 (d, 1H, -CH<sub>2</sub>); 5.12 (d, 1H, -CH<sub>2</sub>); 3.95 (s, 2H, -O-CH<sub>2</sub>-); 1.75 (m, 2H, -CH<sub>2</sub>-); 1.05 (t, 3H, -CH<sub>3</sub>). <sup>13</sup>C NMR (400 MHz, CDCl<sub>3</sub>, ppm): 158.76; 158.15; 137.29; 133.23; 132.35; 130.11; 129.90; 129.69; 129.07; 127.46; 127.36; 118.67; 116.11; 114.48; 114.12; 69.17; 22.47; 10.40. EI-MS for C<sub>13</sub>H<sub>16</sub>O (*m/z*): 188.1 (M<sup>+</sup>).




1-(2-Methoxy)phenyl-1,3-butadiene (**d**)

Yield: 3.68 g, 44%. *Z*:*E* = 80 : 20. For *E* isomer:  $^1\text{H}$  NMR (400 MHz,  $\text{CDCl}_3$ , ppm): 7.49 (d, 1H,  $-\text{CH}$ ); 7.33–6.74 (m, 4H,  $\text{H}_{\text{ph}}$ ); 6.61–6.29 (m, 2H,  $-\text{CH}$ ); 5.38–5.29 (m, 1H,  $-\text{CH}_2$ ); 5.19–5.13 (m, 1H,  $-\text{CH}_2$ ); 3.86 (d, 3H,  $-\text{O}-\text{CH}_3$ ); for *Z* isomer:  $^1\text{H}$  NMR (400 MHz,  $\text{CDCl}_3$ , ppm): 6.95 (d, 1H,  $-\text{CH}$ ); 7.33–6.74 (m, 4H,  $\text{H}_{\text{ph}}$ ); 6.61–6.29 (m, 2H,  $-\text{CH}$ ); 5.38–5.29 (m, 1H,  $-\text{CH}_2$ ); 5.19–5.13 (m, 1H,  $-\text{CH}_2$ ); 3.84 (d, 3H,  $-\text{O}-\text{CH}_3$ ).  $^{13}\text{C}$  NMR (400 MHz,  $\text{CDCl}_3$ , ppm): 156.97; 156.68; 137.84; 133.44; 130.48; 130.03; 128.47; 127.55; 126.36; 126.10; 120.57; 119.89; 118.76; 116.79; 110.75; 110.28; 55.25. EI-MS for  $\text{C}_{11}\text{H}_{12}\text{O}$  (*m/z*): 161.0 ( $\text{M} + \text{H}^+$ ).

## Copolymerization procedure of 1,3-butadiene and 1-substituted 1,3-dienes

All the manipulations were performed under an atmosphere of dry nitrogen. 1,3-Butadiene in toluene ( $1.85 \text{ mol L}^{-1}$ ) and quantitative 1-substituted 1,3-dienes were placed in an oxygen- and moisture-free ampule capped with a rubber septum. Then,  $\text{Fe}(\text{acac})_3$ , DEP, and  $\text{Al}(\text{tBu})_3$  at designed ratios were injected sequentially. The polymerization was kept at  $50^\circ\text{C}$  for 4 h, then terminated by adding 2.0 mL of acidified ethanol containing 1.0 wt% 2,6-di-*tert*-butyl-4-methylphenol (BHT) as stabilizer. The resulting products were repeatedly washed with ethanol and dried under vacuum at  $40^\circ\text{C}$  to constant weight.

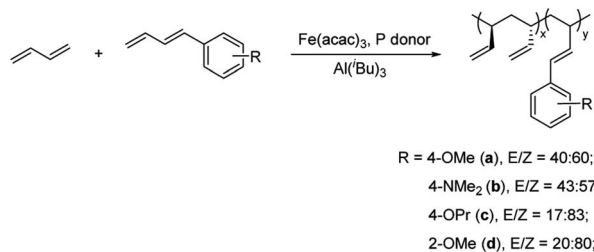

Scheme 2 Copolymerization of 1,3-butadiene with 1-substituted 1,3-dienes **a–d**.

## Results and discussion

The 1-substituted 1,3-diene comonomers bearing different types of functionalities, including 1-(4-methoxy)phenyl-1,3-butadiene (**a**), 1-(4-*N,N*-dimethylamino)phenyl-1,3-butadiene (**b**), 1-(4-propoxy)phenyl-1,3-butadiene (**c**), 1-(2-methoxy)phenyl-1,3-butadiene (**d**), were prepared by Wittig reaction between allyltriphenylphosphonium bromide and substituted benzaldehydes (Scheme 2). Further purification by flash column chromatography afforded the targeted compounds **a–d** in high yields (for detailed procedures and NMR spectra *cf.* Experimental section and ESI<sup>†</sup>). As evidenced from  $^1\text{H}$  NMR spectra, two isomers were obtained for each of the comonomer, with *E/Z* ratios of 40/60, 43/57, 17/83, and 20/80 for **a–d**, respectively.

Copolymerizations of 1,3-butadiene with comonomers **a–d** were carried out by using syndiotactically 1,2-selective catalytic system,  $\text{Fe}(\text{acac})_3/\text{Al}(\text{tBu})_3/\text{phosphorous compound}$ . To optimize the polymerization conditions, the influences of the types and/or amounts of phosphorous donors and cocatalysts were studied with 1-(4-*N,N*-dimethylamino)phenyl-1,3-butadiene (**b**) as a comonomer. As the results shown in Table 1, in the presence of 10 mol% polar comonomer **b**, the polymerization proceeded smoothly, affording copolymers from mediate to high yields, and the catalytic activity and the properties of the resulting polymers were found to be highly dependent on the cocatalysts and phosphorous donors. When the polymerizations were undertaken at smaller cocatalyst/Fe ratios ( $\text{Al}/\text{Fe} < 15$ ), only a small amount of copolymers were isolated, perhaps due to the insufficiency of cocatalyst to activate the active species or due to the poison of catalytic active species by dimethylamino functionality in comonomer **b**. These speculations can also be shed light from increment of comonomer contents in the resultant copolymers with an increasing  $\text{Al}/\text{Fe}$  ratio, in which Lewis acidic aluminum cocatalyst would bond with dimethylamino group and thus hinder it from decomposing iron(III) active centres. Moreover, polymerization

Table 1 Copolymerization of 1,3-butadiene with **b** under different conditions<sup>a</sup>

Run	$\text{P}^b$	P/Fe	Al/Fe	Yield (%)	$M_n \times 10^{-3}^c$	PDI <sup>c</sup>	Comon. content in polymer <sup>d</sup> (%)	Microstructure of PB <sup>d</sup>		$X_c^e$ (%)	$T_m^f$ ( $^\circ\text{C}$ )
								1,2-	<i>Trans</i> -1,4-		
1	DEP	3	5	<5%	—	—	—	—	—	—	—
2	DEP	3	10	22	9.3	2.32	3.14	64.94	35.06	—	—
3	DEP	3	15	14	6.4	2.67	4.00	59.52	40.48	—	—
4	DEP	3	30	54	40.2	3.19	4.51	75.19	24.81	14.74	157
5	DEP	1	30	65	32.5	2.29	2.89	81.30	18.7	23.71	157
6	DEP	5	30	90	4.1	2.90	6.69	53.76	46.24	—	—
7	DEP	10	30	<5%	6.4	2.45	6.32	61.35	38.65	—	—
8	DBP	3	30	78	50.5	1.96	2.48	84.75	15.25	16.19	158
9	TBP	3	30	<5%	30.3	2.37	1.32	33.33	66.67	—	—
10	TPP	3	30	28	70.2	2.06	1.02	77.52	22.48	12.66	167

<sup>a</sup> Polymerization conditions: solvent, toluene; polymerization time, 4 h;  $T$ :  $50^\circ\text{C}$ ; 1,3-butadiene,  $1.85 \text{ mol L}^{-1}$ ;  $[\text{M}]/[\text{Fe}] = 1000$ ; comonomer **b**,  $1.665 \text{ mmol}$  ( $\text{Bd}/\text{b} = 9/1$ ). <sup>b</sup> DEP: diethyl phosphite; DBP: dibutyl phosphite; TBP: tributyl phosphite; TPP: triphenyl phosphite. <sup>c</sup> Determined by GPC in trichlorobenzene vs. polystyrene standards. <sup>d</sup> Determined by  $^1\text{H}$  NMR analysis.<sup>36</sup> <sup>e</sup> Estimated by the formula of  $\Delta H/\Delta H_0$ ,  $\Delta H$  was calculated by DSC and  $\Delta H_0$  referred to standard enthalpy of 1,2-polybutadiene with 100% crystallinity, equal to  $60.7 \text{ J g}^{-1}$ . <sup>f</sup> Determined by DSC at heat rate of  $10^\circ\text{C min}^{-1}$ .



Table 2 Copolymerization of 1,3-butadiene with different polar 1-substituted 1,3-diene derivatives<sup>a</sup>

Run	Comon.	Comon./Bd <sup>b</sup>	Yield (%)	$M_n^c \times 10^{-3}$	PDI <sup>c</sup>	Comon. content in polymer <sup>d</sup> (%)	Microstructure of PB <sup>d</sup>		$X_c^e$ (%)	$T_m^f$ (°C)
							1,2-	Trans-1,4-		
11	—	0/100	93	22.8	2.22	0	85.47	14.53	42.75	165
12	<b>a</b>	2/98	90	37.3	1.79	1.63	84.71	15.29	35.25	167
13	<b>a</b>	5/95	83	38.1	3.93	3.63	80.65	19.35	28.19	157
14	<b>a</b>	10/90	75	41.0	3.69	7.40	80.00	20.00	12.14	154
15	<b>a</b>	20/80	61	45.0	2.97	8.88	74.92	25.08	9.41	147
16	<b>a</b>	30/70	47	62.7	2.26	17.18	72.46	27.54	6.40	140
17	<b>b</b>	2/98	82	75.6	1.78	0.83	84.03	15.97	30.97	158
18	<b>b</b>	5/95	66	55.2	5.62	1.84	80.65	19.35	24.18	158
19	<b>b</b>	10/90	54	40.2	3.19	4.51	75.19	24.81	14.74	157
20	<b>b</b>	20/80	Oligomer	—	—	—	—	—	—	—
21	<b>c</b>	5/95	77	30.6	2.26	1.59	80.65	19.35	31.83	163
22	<b>c</b>	10/90	66	72.2	2.57	3.03	78.13	21.87	30.61	161
23	<b>c</b>	20/80	47	67.1	2.41	5.71	75.76	24.24	21.37	159
24	<b>d</b>	5/95	79	95.6	2.49	2.12	81.30	18.70	30.64	163
25	<b>d</b>	10/90	66	176.4	2.08	4.00	78.74	21.26	23.94	156
26	<b>d</b>	20/80	48	102.9	2.16	6.29	77.52	22.48	13.99	152

<sup>a</sup> Polymerization conditions: solvent, toluene; polymerization time, 4 h;  $T$ : 50 °C; 1,3-butadiene, 1.85 mol L<sup>-1</sup>; [M]/[Fe]/[Al]/[P] = 1000/1/30/3.

<sup>b</sup> Molar ratio. <sup>c</sup> Determined by GPC in trichlorobenzene vs. polystyrene standards. <sup>d</sup> Determined by <sup>1</sup>H NMR analysis. <sup>e</sup> Estimated by the formula of  $\Delta H/\Delta H_0$ ,  $\Delta H$  was calculated by DSC and  $\Delta H_0$  referred to standard enthalpy of 1,2-polybutadiene with 100% crystallinity, equal to 60.7 J g<sup>-1</sup>. <sup>f</sup> Determined by DSC at heat rate of 10 °C min<sup>-1</sup>.

at Al/Fe ratio lower than 15 gave amorphous rubber-like 1,2-PB, whereas crystalline syndiotactic sPB was obtained when higher Al/Fe is employed. This result agrees with our previous research on Fe(III)-mediated 1,3-butadiene homopolymerization.<sup>40</sup>

External phosphorous donors also significantly influenced the copolymerization performances. Increasing the P/Fe ratio from 1 to 10 first led to the formation of sPB and then produced amorphous 1,2-PB rubber, this is consistent with our previous conclusion that higher P/Fe molar ratio favours the formation of amorphous 1,2-polybutadiene.<sup>41</sup> Although the best catalytic activity was observed when P/Fe = 5 in the present study, sPB can only be formed when P/Fe = 1 or 3, therefore, P/Fe = 3 was applied in the following study. Moreover, it was observed that the molecular weights of the resultant amorphous 1,2-PBs were much lower than that of crystalline sPB, which might be due to the over-coordination of DEP slowed down coordination of 1,3-butadiene monomer to the vacant site of active centre and thus reduced chain propagation rate. Different types of phosphorous donors were also investigated, and dibutyl phosphite (DBP) was found to give the highest polymer yield (78%), and simultaneously affording sPB with high 1,2-contents. Whereas tributyl phosphite (TBP) and triphenyl phosphite (TPP)-based systems showed much lower catalytic activities under identical conditions; the polymer yields were <5% and 28%, respectively.

Copolymerizations were then expanded to other 1-substituted 1,3-dienes to evaluate the influence of different functionalities on copolymerization behaviour. As the results summarized in Table 2, the presence of a small amount of polar comonomer could deactivate the active species obviously, in spite of the relative lower electrophilicity of late-transition metal iron(III) center, when comparing to early-transition or lanthanide metal counterparts. For instance, when 5% of

comonomers **a–d** were added into the system, the isolated copolymer yields dropped significantly from 93% for 1,3-butadiene homopolymerization to 83%, 66%, 77%, and 79% for copolymerizations with **a**, **b**, **c**, and **d**, respectively. Further increasing the comonomer/Bd ratio led to gradual reduction in the polymer yields. For instance, the presence of 30% comonomer **a** gave the polymer yield almost half of that in the 1,3-butadiene homopolymerization (46.5% vs. 92.9%); and the presence of 20% **b** poisoned the active species significantly, and only oligomers, rather than copolymers, were produced eventually. The decrement of polymer yield in the copolymerizations can be explained by the formation of relatively stable intermediates through coordination of heteroatoms to iron(III) center, which retards subsequent insertion reaction. In spite of these results, to our knowledge, the synthesis of polar group-

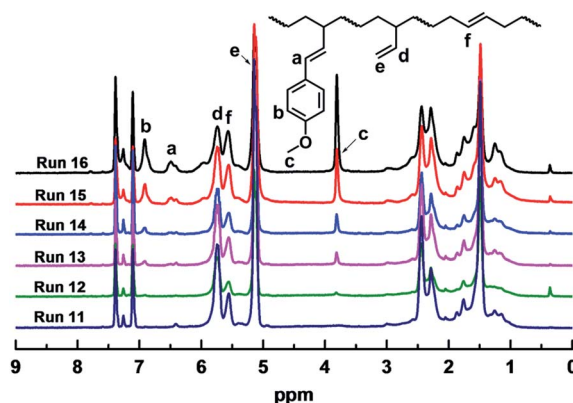


Fig. 1 <sup>1</sup>H NMR spectra of the copolymers obtained from 1,3-butadiene and comonomer **a**.





functionalized sPB *via* direct polymerization approach has not been reported thus far, this is the first example in this field. Regarding the effect of functionality on copolymerization performances, an order of  $a > c \sim d > b$  was revealed from the catalytic activities. The most unreactive comonomer **b** was ascribed to the strongest electro-donating ability of dimethylamino group, which displayed high coordination capability with the electrophilic active species and/or the alkyl aluminum cocatalyst. Similar reasons can also be explainable for the inferior reactivity of monomers **c**, when comparing with **a**, the presence of long alkyl group generally imparts them more pronounced electron-donating ability. Nevertheless, the relative smaller reactivity of **d** was ascribed to steric effect, *i.e.*, 2-substituted phenyl groups brought in a sterically hindered space, which thus prohibited itself being coordinated to the metal center.

Incorporation of polar 1-substituted 1,3-diene comonomer was clearly observed for all the copolymerization studies. When comonomer  $a/Bd = 2/98$  in the feed ratio, the resulting copolymer contained *ca.* 1.63% of comonomers. The increase in the comonomer feed resulted in the increment of comonomer content in the resulting polymer. Fig. 1 illustrated the  $^1H$  NMR spectra of the resultant copolymers, in which the resonance peaks at 3.81 ppm assignable to the methoxyl group gradually increased if more **a** was incorporated into the copolymer. Moreover, the resonance peaks of phenyl protons at 6.92 ppm, can also be clearly observed. For other comonomers **b–d**, a monotonous increasing of incorporation content could also be witnessed if more comonomer feed ratio was applied.

Increasing the amount of comonomer **a** from 2% to 30% led to slight decrement of 1,2-content in the resultant copolymers from 84.71% to 72.46%, while the rest microstructure was kept as *trans*-1,4- moiety. Similar results were also observed for other comonomer **b**, **c**, and **d**. While the increase in the comonomer feed led to a decrement in the catalytic activity (*vide supra*) and 1,2 selectivity, the catalytic system still exhibited syndio 1,2-selectivity, affording in-chain functionalized sPBs. As the tendency revealed from Fig. 1, the resonance peaks, that assigned to the vinyl protons, at 5.75, 5.14 ppm revealed a clear decrement. Similar conclusion can also be made for other comonomers, as revealed from Fig. S9–S11.† It is of note that,

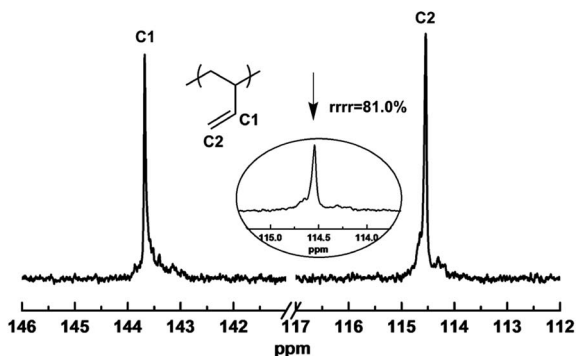


Fig. 2  $^{13}C$  NMR spectrum (olefinic region) of the resultant copolymers (run 19).

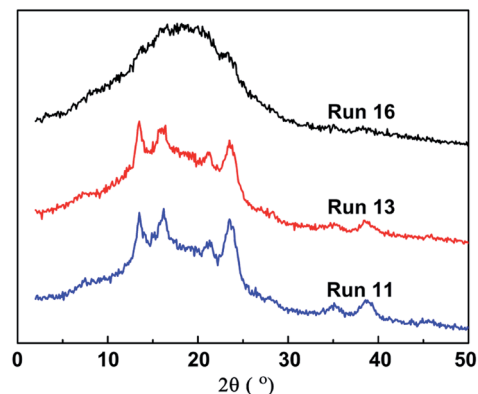


Fig. 3 X-ray spectra of the resultant copolymer products (runs 11, 13, 16).

the slight decrease of 1,2-structure didn't affect the stereoregularity of the resultant copolymers. As the representative  $^{13}C$  NMR shown in Fig. 2, when 10% comonomer **b** was incorporated into the polymer chain, the syndiotactic *rrrr* pentad was maintained as high as 81.0%, which is about same with that of sPB homopolymers,<sup>35</sup> implying that the presence of polar comonomer displayed subtle influence on the stereoselectivity of the iron(III) catalytic active species.

The incorporation of polar 1-substituted 1,3-diene comonomer into sPB resulted in, as expected, a decrease in the crystallinity degree  $X_c$  and melting temperature  $T_m$  of the resulting copolymers. Fig. 3 shows the WXR D spectra of the resultant copolymer, the diffraction peaks at  $2\theta = 13.50, 16.17, 21.22,$  and  $23.50^\circ$  ascribed to 1,2-syndiotactic PB,<sup>42</sup> clearly weakened with an increasing incorporation amount of comonomer **a**. Fig. 4 illustrates the DSC analysis curves, in which a gradual decrease of  $T_m$  and gradual broadening of the melting transition were observed when more comonomer was in cooperated.

In order to clearly elucidate of the improved surface property upon incorporation of polar monomer, static water contact angles of the resultant copolymers was tested. The results demonstrated that the static water contact angle of the copolymers decreased from  $115.1^\circ$  (run 11) to  $104.2^\circ$  (run 14) with an addition of 10 mol% **a**. Analogous results were observed for

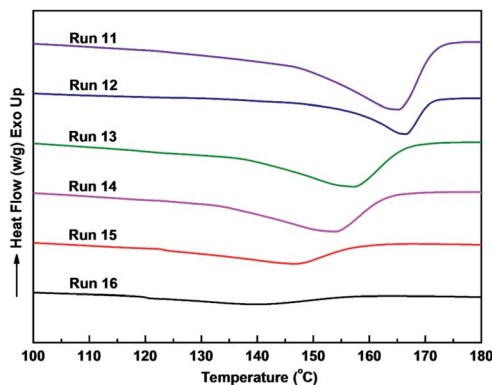


Fig. 4 DSC curves of the resultant copolymer products (runs 11–16).



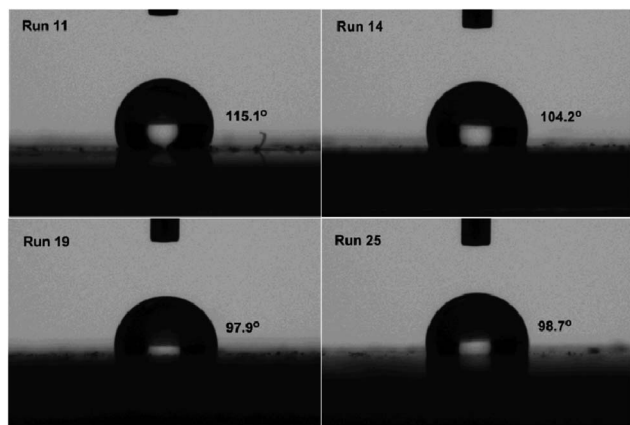


Fig. 5 Static water contact angle measurements for the resultant copolymer products (runs 11, 14, 19, 25).

other comonomer **b-d**, implying the significant increased surface energy therein (Fig. 5).

## Conclusions

In-chain functionalized syndiotactic 1,2-polybutadiene *via* copolymerization strategy is disclosed in this research. Through changing copolymerization conditions, the Ziegler–Natta catalytic system,  $\text{Fe}(\text{acac})_3/\text{Al}(\text{tBu})_3/\text{P}$ , was able to efficiently copolymerize 1,3-butadiene with 1-substituted 1,3-dienes containing amino and alkoxy groups to produce functionalized syndiotactic 1,2-polybutadiene. Copolymerization conditions, including phosphorous donors, cocatalyst, *etc.*, imposed significant influence on the copolymerization activities, as well as the properties of resulting functionalized copolymers. Although slight decreased 1,2-contents was revealed when increasing the comonomer content, but the resultant copolymers still exhibited syndiotactic structure. The incorporation of polar comonomers greatly improved the energy surface of copolymer products.

## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

This work was supported by the National Natural Science Foundation of China (No. 21801236), PetroChina Company Limited (2018B-2707), Joint Funds of the National Natural Science Foundation of China (U186220053) and Jilin Provincial Science and Technology Development program (20190103122JH).

## Notes and references

- 1 J. E. Mark, *Handbook, Polymer Data*, Oxford University Press, New York, 1999.
- 2 V. G. Natta, *Makromol. Chem.*, 1955, **16**, 213–237.

- 3 H. Ashitaka, H. Ishikawa, H. Ueno and A. Nagasaka, *J. Polym. Sci., Polym. Chem. Ed.*, 1983, **21**, 1853–1860.
- 4 M. Ichikawa, Y. Takeuchi, A. Kogure and H. Kurita, *US Pat.*, 3498963A, 1970.
- 5 K. Makino, K. Komatsu, Y. Takeuchi and M. Endo, *US Pat.*, 4182813A, 1980.
- 6 S. Luo, *US Pat.*, 6331594, 2001.
- 7 S. Luo, *US Pat.*, 6528588, 2003.
- 8 H. Ashitaka, Y. Kusuki, S. Yamamoto, Y. Ogata and A. Nagasaka, *J. Appl. Polym. Sci.*, 1984, **29**, 2763–2776.
- 9 X. Hao and X. Zhang, *Mater. Lett.*, 2007, **61**, 1319–1322.
- 10 M. Hitrik, V. Gutkin, O. Lev and D. Mandler, *Langmuir*, 2011, **27**, 11889–11898.
- 11 W. Pan, H. Chen, J. Mu, W. Li, F. Jiang, G. Weng, Y. Hu, D. Gong and X. Zhang, *Polymer*, 2017, **111**, 20–26.
- 12 Y. Takahashi, X. Liang and K. Nakajima, *J. Appl. Polym. Sci.*, 2019, **136**, 47934.
- 13 T. C. Chung, *Prog. Polym. Sci.*, 2002, **27**, 39–85.
- 14 P. Zinck, F. Bonnet, A. Mortreux and M. Visseaux, *Prog. Polym. Sci.*, 2009, **34**, 369–392.
- 15 N. M. G. Franssen, J. N. H. Reek and B. de Bruin, *Chem. Soc. Rev.*, 2013, **42**, 5809–5832.
- 16 B. Marciniak, M. Lewandowski, C. Pietraszuk and Z. Foltynowicz, *Polymer*, 1997, **38**, 5169–5172.
- 17 M. I. Abdullin, A. B. Glazyrin, R. N. Asfandiyarov, V. R. Akhmetova and V. N. Zaboristov, *Polym. Sci., Ser. B*, 2006, **48**, 104–107.
- 18 M. I. Abdullin, A. B. Glazyrin, R. N. Asfandiyarov and R. R. Muslukhov, *Polym. Sci., Ser. B*, 2009, **51**, 303–308.
- 19 A. B. Glazyrin, M. I. Abdullin, R. R. Muslukhov and V. A. Kraikin, *Polym. Sci., Ser. A*, 2011, **53**, 110–115.
- 20 A. B. Glazyrin and M. I. Abdullin, *Russ. J. Appl. Chem.*, 2016, **89**, 1655–1661.
- 21 A. B. Glazyrin, M. I. Abdullin, E. R. Atnabaeva, R. M. Sultanova, V. P. Volodina and V. A. Dokichev, *Polym. Bull.*, 2019, **76**, 3643–3657.
- 22 F. Guo, K. Jankova, L. Schulte, M. E. Vigild and S. Ndoni, *Langmuir*, 2010, **26**, 2008–2013.
- 23 B. Korthals, M. C. Morant-Miñana, M. Schmid and S. Mecking, *Macromolecules*, 2010, **43**, 8071–8078.
- 24 A. Berthold, K. Sagar and S. Ndoni, *Macromol. Rapid Commun.*, 2011, **32**, 1259–1263.
- 25 L. Lotti, S. Coiai, F. Ciardelli, M. Galimberti and E. Passaglia, *Macromol. Chem. Phys.*, 2009, **210**, 1471–1483.
- 26 T. D. Wickard, E. Nelsen, N. Madaan, N. ten Brummelhuis, C. Diehl, H. Schlaad, R. C. Davis and M. R. Linford, *Langmuir*, 2010, **26**, 1923–1928.
- 27 J. Zheng, F. Liu, Y. C. Lin, Z. J. Zhang, G. C. Zhang, L. Wang, Y. Liu and T. Tang, *Macromolecules*, 2012, **45**, 1190–1197.
- 28 B. Korthals, M. C. Morant-Miñana, M. Schmid and S. Mecking, *Macromolecules*, 2010, **43**, 8071–8078.
- 29 The growing active specieses are  $\eta^3$  and  $\sigma^1$  coordinated mode for diene and monoene monomers respectively.
- 30 C. Yao, N. Liu, S. Long, C. Wu and D. Cui, *Polym. Chem.*, 2016, **7**, 1264–1270.
- 31 S. Long, F. Lin, C. Yao and D. Cui, *Macromol. Rapid Commun.*, 2017, **38**, 1700227.



- 32 H. Leicht, I. Göttker-Schnetmann and S. Mecking, *J. Am. Chem. Soc.*, 2017, **139**, 6823–6826.
- 33 H. Leicht, I. Göttker-Schnetmann and S. Mecking, *Macromolecules*, 2017, **50**, 8464–8468.
- 34 H. Leicht, I. Göttker-Schnetmann and S. Mecking, *ACS Macro Lett.*, 2016, **5**, 777–780.
- 35 C. Yao, H. Xie and D. Cui, *RSC Adv.*, 2015, **5**, 93507–93512.
- 36 D. Gong, W. Dong, Y. Hu, J. Bi, X. Zhang and L. Jiang, *Polymer*, 2009, **50**, 5980–5986.
- 37 D. Gong, W. Pan, T. Zhu, H. Chen, Z. Zhou, F. Jiang, Y. Hu and X. Zhang, *Polymer*, 2016, **98**, 136–142.
- 38 W. Pan, H. Chen, R. Sun, D. Gong, X. Jia, Y. Hu and X. Zhang, *Ind. Eng. Chem. Res.*, 2016, **55**, 7580–7586.
- 39 D. Gong, W. Dong, J. Hu, X. Zhang and L. Jiang, *Polymer*, 2009, **50**, 2826–2829.
- 40 W. Zheng, F. Wang, J. Bi, H. Zhang, C. Zhang, Y. Hu, C. Bai and X. Zhang, *J. Polym. Sci., Polym. Chem. Ed.*, 2015, **53**, 1182–1188.
- 41 J. Lu, Y. Hu, X. Zhang, J. Bi, W. Dong, L. Jiang and B. Huang, *J. Appl. Polym. Sci.*, 2006, **100**, 4265–4269.
- 42 J. Cai, Q. Yu, X. Zhang, J. Lin and L. Jiang, *J. Polym. Sci., Part B: Polym. Phys.*, 2005, **43**, 2885–2897.

