


Cite this: *RSC Adv.*, 2019, 9, 40348

High-performance sono/nano-catalytic system: CTSN/Fe₃O₄–Cu nanocomposite, a promising heterogeneous catalyst for the synthesis of *N*-arylimidazoles†

Reza Taheri-Ledari, Seyed Masoud Hashemi and Ali Maleki *

Herein, a promising heterogeneous nanoscale catalytic system constructed of chitosan (CTSN, as a polymeric basis), iron oxide nanoparticles (Fe₃O₄ NPs, as the magnetic agent), and copper oxide nanoparticles (CuO NPs, as the main catalytic active site) is presented. Firstly, a convenient synthetic route for preparation of this novel nanocatalyst (CTSN/Fe₃O₄–Cu) is presented. Further, the synergistic catalytic effect between the novel-designed catalyst and ultrasound waves (USW) in *N*-arylation coupling reactions of the imidazole derivatives (using various aryl halides) is precisely discussed. Concisely, high reaction yields (98%) have been obtained in short reaction time (10 min) through applying a partial amount (0.01 g) of this nanocatalyst. As the main reason for high catalytic activity of CTSN/Fe₃O₄–Cu, nanosized cluster-shaped morphology, which provides a wide surface active area, can be expressed. However, as the most distinguished properties of CTSN/Fe₃O₄–Cu catalytic system, high convenience in separation and excellent reusability could be mentioned. CTSN/Fe₃O₄–Cu nanocomposite can be easily recovered by using an external magnet and reused at least for eight times with no significant decline in the catalytic activity. Structural characterizations of this novel system have been done by various analytical methods and the obtained results have been well interpreted in the context.

Received 4th October 2019
Accepted 29th November 2019

DOI: 10.1039/c9ra08062g

rsc.li/rsc-advances

1. Introduction

Recently, science and technology are shifting more toward design and development of the novel safe energy resources to create a healthier world. Thus, using clean and nonhazardous materials and executing the green methods have attracted so much attentions in different research fields. In chemical catalysis scope, numerous efforts have been made to design and fabricate efficient catalytic systems that include nontoxic materials in their structures and do not need any hazardous reagent for running the catalytic process.^{1,2} In recent decade, ultrasound wave (USW) irradiation has been introduced as one of the most effective strategies that can also be considered as a great co-catalyst agent for chemical reactions.^{3,4} From both physical and chemical aspects, USW irradiation activates the catalytic sites of the chemicals to enhance the performance of the catalytic systems. Also, USW irradiation leads to obtain high reaction yields in short reaction times, with the least amount of the wasted materials. Moreover, the structure of the

heterogeneous catalytic systems will not be damaged under USW irradiation. Concisely, USW irradiation is more convenient, fast, safe and simple than traditional heating sources.^{5–7} Therefore, diverse organic reactions can efficiently be carried out under USW irradiation. As the main reasons, acoustic cavitation and cage effect through microproject bubbles (micro-bubbles) that create high temperatures and microscopic pressures within few seconds lead to acceleration of the chemical reactions.⁸ As a result, USW irradiation is classified as a green, powerful, economical and environmentally-friendly approach in chemical reactions. In this study, we try to show the synergistic catalytic effect between USW (using an US cleaner bath) with a novel nanoscale catalytic system for facilitating the chemical synthesis reactions.

Proportional to the impressive and fast progress in nanotechnology, several nanoscale heterogeneous catalytic systems have been introduced by researchers to perform the complex chemical reactions with more convenience.^{9–12} Among various species of the reported heterogeneous catalytic systems, magnetic nanocatalysts have attracted more attentions due to including high convenience in separation and recycling processes. For instance, we recently reported some novel magnetic nanoparticles (NPs) that have been functionalized and applied for different catalytic aims such as facilitating peptide couplings and multicomponent synthesis reactions of

Catalysts and Organic Synthesis Research Laboratory, Department of Chemistry, Iran University of Science and Technology, Tehran 16846-13114, Iran. E-mail: maleki@iust.ac.ir; Fax: +98 21 73021584; Tel: +98 21 73228313

† Electronic supplementary information (ESI) available: The ESI file includes the NMR (H and C) of selected *N*-arylimidazole products and also SEM and EDX results of recovered nanocatalyst. See DOI: 10.1039/c9ra08062g




pharmaceutical compounds.^{13,14} However, wide surface active area, great functionalization capability, nontoxicity, excellent stability and thermal resistance, and *etc.* could also be mentioned as the additional important reasons for employing the magnetic NPs for catalytic purposes. Among all of the different categories of magnetic NPs, iron oxide NPs species (Fe_3O_4 , $\gamma\text{-Fe}_2\text{O}_3$, and *etc.*) are extremely used due to their easy preparation and superparamagnetic behavior.^{15–17} In this work, we report a novel magnetic nanocatalyst that is constructed of copper nanoparticles (Cu NPs) as the main catalytic active sites, iron oxide nanoparticles (Fe_3O_4 NPs) as the magnetic agent, and chitosan (CTSN) as the natural polymeric matrix for composition and stabilization of the nanoscale ingredients (CTSN/ Fe_3O_4 -Cu).

In recent decades, *N*-arylated azoles *e.g.*, arylpyrroles, arylpyrazoles, arylimidazoles, aryltriazoles, arylindoles, arylcarbazoles, and *etc.* have attracted so much attentions because of their important applications in medicinal and materials fields. Some of these scaffolds are also found in many bioactive natural products.¹⁸ Among all of the heterocyclic compounds, study on the *N*-aryl imidazoles is very intensive because of its famous biomedical properties such as receptor antagonists and thromboxane synthase inhibitors.^{19,20} In this regard, some ligand-free copper-catalyzed *N*-arylation reactions have been reported. For instance, Son *et al.* have prepared coated-CuO nanoparticles by thermal decomposition using copper acetylacetonate.²¹ Choudary *et al.* have designed a catalyst for *N*-arylation of imidazoles *via* the cation exchange of fluorapatite and *tert*-butoxyapatite with copper.²² Thus, designing a simple and

efficient route for the synthesis of *N*-aryl or heteroarylamines remains highly desirable.

In this work, we try to facilitate the *N*-arylation of imidazoles and its derivatives by using a novel designed CTSN/ Fe_3O_4 -Cu nanocomposite, as an inexpensive magnetic nanocatalyst, under 'ligand-free' conditions. Firstly, a convenient route is introduced for preparation of this novel catalytic system. Then, as the distinguished advantages, high magnetic behavior that leads to easily separation after completion of the synthetic reactions with no need to some complex purification processes. Moreover, high stability of this heterogeneous catalytic system provides a great opportunity to reuse this system for several times without any decline in the catalytic performance. High performance of this catalytic system origins from a synergistic catalytic effect between the fabricated nanocomposite (CTSN/ Fe_3O_4 -Cu) and ultrasound waves, which is considered as a faster and safer method in comparison with other methods.²³ For this purpose, all of the synthetic reactions have been carried out in an ultrasound cleaner bath with 50 kHz frequency and 200 W L⁻¹ power density. From physical aspect, well-known cluster shape of the composite provide an extreme surface active area for catalytic aims. In addition of the mentioned excellences, substantial biocompatibility and biodegradability is obtained for this catalytic system, through applying a natural basis (CTSN) in the structure of the catalyst. As a result, a fast and safe strategy for the synthesis of the *N*-arylated imidazole derivatives is presented in this study, through which high reaction yields (98%) are obtained in short reaction time (10 min) with high safety and convenience.

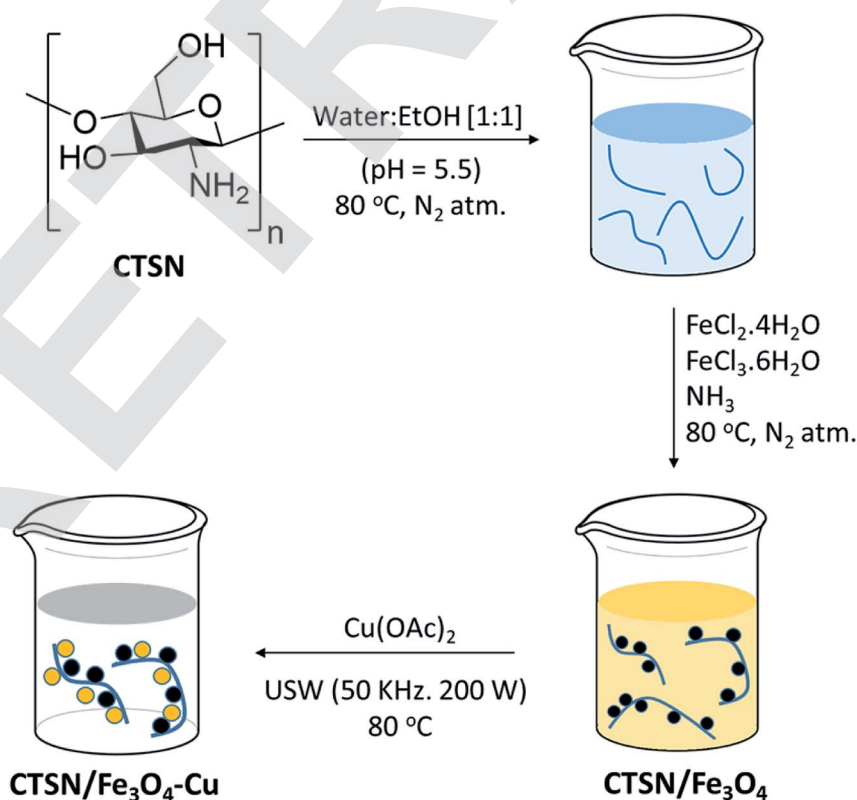

Scheme 1 Preparation route of CTSN/ Fe_3O_4 -Cu nanocomposite.

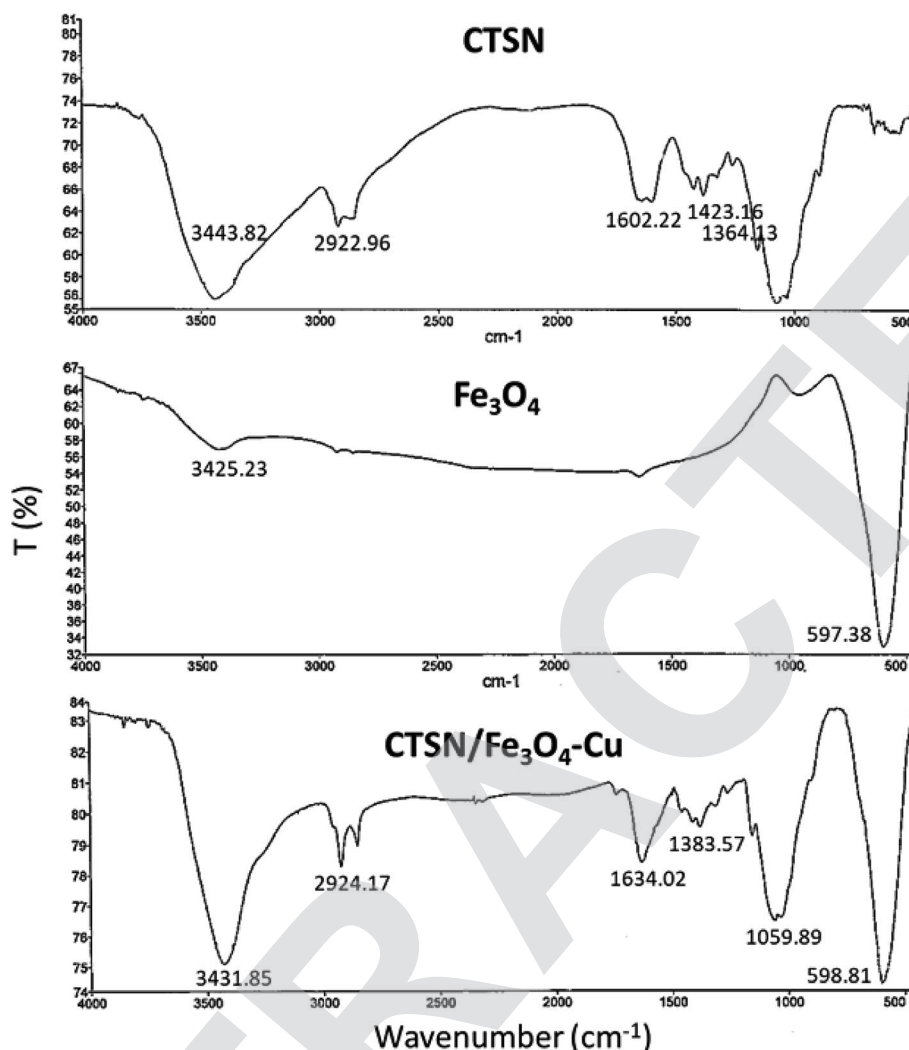


Fig. 1 FT-IR spectra of CTSN, Fe_3O_4 , and CTSN/ Fe_3O_4 -Cu nanocomposite.

2. Experimental

2.1. Materials and equipment

All the solvents, chemicals and reagents were purchased from Merck, Sigma and Aldrich. Melting points were measured on an Electrothermal 9100 apparatus and are uncorrected. FT-IR spectra were recorded on a Shimadzu IR-470 spectrometer by the method of KBr pellet. ^1H and ^{13}C Nuclear Magnetic Resonance (NMR) spectra were recorded on a Bruker DRX-500 Avance spectrometer at 500, 300, 75 and 125 MHz, respectively. Thermal analysis (TGA) was also done by using of BahrSTA 504 instrument under argon atmosphere. FESEM images were taken by Sigma-Zeiss microscope with attached camera. Magnetic measurements of the solid samples were performed using Lakeshore 7407 and Meghnatis Kavir Kashan Co., Iran vibrating sample magnetometers (VSMs). Elemental analysis of the nanocatalyst was carried out by energy-dispersive X-ray (EDX) analysis which was recorded on a Numerix DXP-X10P. XRD measurements were carried out by using a DRON-8 X-ray diffractometer.

2.2. Practical methods

2.2.1. Synthesis of CTSN/ Fe_3O_4 nanocomposite. In a round-bottom flask (100 mL), CTSN (high purity, 180 kDa) (0.5 g) was dissolved in a mix of dilute acidic deionized water (4.0 mL, pH = 5.5 by HCl) and ethanol (4.0 mL), at 80 °C under N_2 atmosphere. Then, two aqueous solutions (0.1 M) of $\text{FeCl}_2 \cdot 4\text{H}_2\text{O}$ and $\text{FeCl}_3 \cdot 6\text{H}_2\text{O}$ were simultaneously added to the flask. Next, concentrate NH_3 was slowly added to the mixture, until pH = 12 was obtained. The dark particles of the Fe_3O_4 were produced *via* co-deposition method and composited with CTSN during an *in situ* process. After completion of the addition, the magnetized CTSN was collected by an external magnet and washed with distilled water and ethanol, and dried in a vacuum oven.

2.2.2. Synthesis of CTSN/ Fe_3O_4 -Cu nanocomposite. In a round-bottom flask (50 mL), CTSN/ Fe_3O_4 (0.1 g) was placed and well dispersed in deionized water (3.0 mL), *via* ultrasonication (10 min). Next, $\text{Cu}(\text{OAc})_2$ aqueous solution (5% wt, 2.0 mL) was added drop by drop to the aqueous mixture of CTSN/ Fe_3O_4 , and the mixture were ultrasonicated into an US bath (50 kHz, 200 W



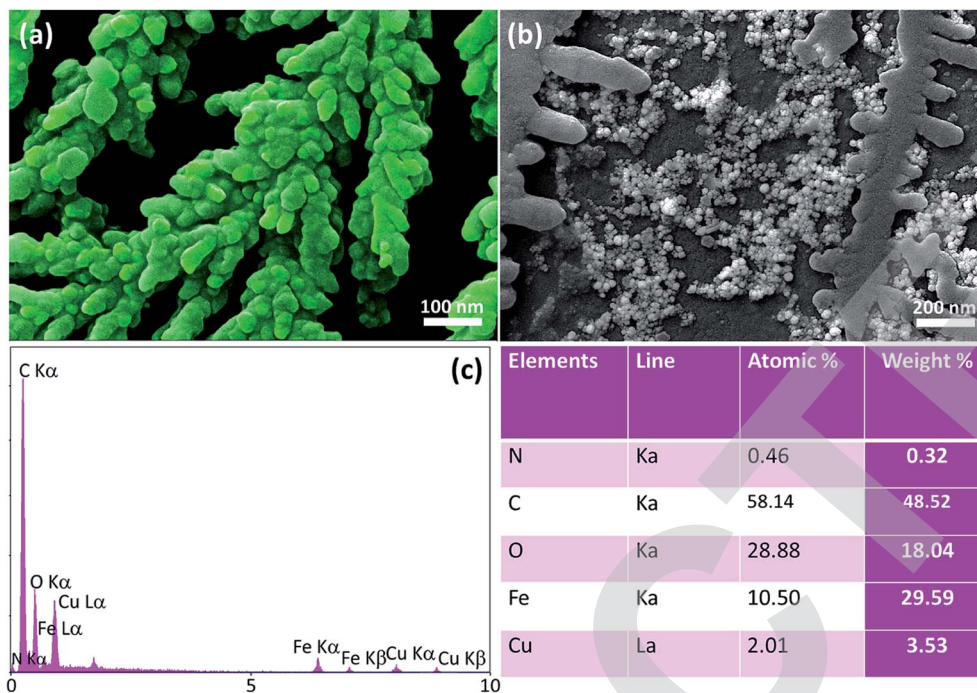


Fig. 2 (a) FE-SEM image of CTSN/Fe₃O₄, and (b) the prepared CTSN/Fe₃O₄-Cu nanocomposite. (c) EDX analysis results of the prepared CTSN/Fe₃O₄-Cu nanocomposite [Y-axis: count, X-axis: energy (keV)].

L⁻¹) for 1 h, at 80 °C. Finally, the fabricated CTSN/Fe₃O₄-Cu nanocomposite were magnetically separated and washed with deionized water and ethanol and dried at room temperature.

2.2.3. General procedure for *N*-arylation of imidazoles by CTSN/Fe₃O₄-Cu nanocatalyst via USW irradiation. In a glass tube (Threaded Test Tube with Phenolic Cap, 13 × 100 mm), aryl halide (1.0 mmol), imidazole (2.0 mmol), CTSN/Fe₃O₄-Cu (0.01 mg), CTAB (0.5 mmol) and K₂CO₃ (1.5 mmol) were added in deionized water (4.0 mL). The mixture was sonicated for 10 min, at room temperature in an ultrasonic bath (50 kHz, 200 W). After completion of the reaction, the mixture was diluted with H₂O (5.0 mL) and extracted with EtOAc (4 × 10 mL). The combined organic phases was washed with water and brine, dried over anhydrous Na₂SO₄, and concentrated in vacuum. The residue was purified by flash column chromatograph on silica gel (ethyl acetate/*n*-hexane, 2 : 1) to afford the target pure product. As same as excellent results were obtained in gram scale of the reaction by starting these ratio of raw materials and reagents.

2.2.4. Spectral data for selected products

1-Phenyl-1*H*-imidazole 3a. ¹H NMR (DMSO-*d*₆, 300 MHz), δ (ppm): 7.14 (s, 1H), 7.37 (t, 1H, *J* = 7.2 Hz), 7.53 (t, 2H, *J* = 7.4 Hz), 7.67–7.78 (m, 3H), 8.3 (s, 1H). ¹³C NMR (DMSO-*d*₆, 75 MHz): δ (ppm): 118.5, 121.5, 127.8, 130.1, 130.8, 135.7, 137.7.

1-*p*-Tolyl-1*H*-imidazole 3b. ¹H NMR (CDCl₃, 500 MHz), δ (ppm): 7.79 (s, 1H), 7.22 (m, 5H), 7.17 (s, 1H), 2.37 (s, 3H). ¹³C NMR (CDCl₃, 125 MHz): δ (ppm): 137.7, 135.8, 135.4, 130.7, 130.4, 121.6, 118.6, 21.2.

3. Results and discussion

3.1. Preparation of CTSN/Fe₃O₄-Cu nanocatalyst

Initially, CTSN was dissolved in a mix of dilute acidic water (pH = 5.5) and ethanol with equal ratios, at 80 °C under N₂ atmosphere. When a clear and homogeneous mixture was obtained, two aqueous solutions of FeCl₂·4H₂O and FeCl₃·6H₂O were added drop by drop to into the flask. Next, ammonia was slowly added to the mixture, until pH = 12 was obtained. The dark particles of the Fe₃O₄ were synthesized *via* an *in situ* co-deposition method and composited with CTSN. After completion of the addition, the magnetized CTSN was collected by an external magnet and washed with distilled water and ethanol, and dried in a vacuum oven. Afterward, copper(II) acetate aqueous solution (5% wt) was added drop by drop to a dispersed aqueous mixture of CTSN/Fe₃O₄, and the mixture were ultra-sonicated into an US bath (with frequency: 50 kHz and power density: 200 W L⁻¹) for 1 h, at 80 °C. Finally, the CTSN/Fe₃O₄-Cu nanocomposite was magnetically separated and washed with deionized water and ethanol and dried at room temperature (Scheme 1).

3.2. Characterization of CTSN/Fe₃O₄-Cu nanocatalyst

After preparation of the nanocomposite, various conventional instrumental techniques were used for the characterization of the structure and morphology. The comparative FT-IR spectra of the synthesized CTSN/Fe₃O₄-Cu nanocomposite and its individual components are shown in Fig. 1. In the spectrum of



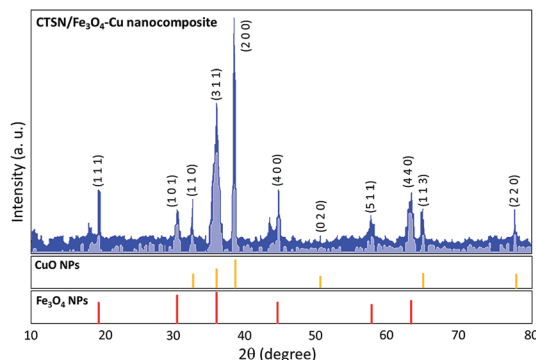


Fig. 3 XRD pattern of the fabricated CTSN/Fe₃O₄-Cu nanocomposite.

CTSN, The absorption band at 3443 cm⁻¹ is related to the vibrational stretching of the N-H and O-H groups. The absorption band that is appeared at 2922 cm⁻¹ coming from the stretching vibrations of aliphatic C-H groups, and the appeared peak at 1155 cm⁻¹ origins from the stretching vibrations of C-O-C bond. The absorption band at 1602 cm⁻¹ indicates the presence of N-H of amide groups. The absorption bands appeared at 1423 and 1384 cm⁻¹ refer to C-N vibrations. The absorption bands at ca. 598 cm⁻¹ can be seen in the spectrum of Fe₃O₄ NPs, corresponds to the stretching vibrations of Fe-O band. The intensive broad absorption at 3425 cm⁻¹ represented the stretching mode of H₂O molecules and -OH groups. In the spectrum of CTSN/Fe₃O₄-Cu nanocomposite, absorption band at 3431 cm⁻¹ refers to the stretching vibrations of O-H and N-H groups of chitosan that bonded to the copper ferrite nanoparticles and shift to lower frequency. It also refers to O-H groups of nanoparticles. The absorption band at ca. 1059 cm⁻¹ shows the stretch vibrations of C-O bond and the 598 cm⁻¹ band represented the Fe-O group of Fe₃O₄ NPs. Therefore, the FT-IR analysis confirmed the supporting of Fe₃O₄ and Cu NPs on the surface and matrix of chitosan. EDX analysis was also performed for determination of the elements constitutes catalyst.²⁴ EDX spectra shows that there are C, Fe, Cu and O atoms in the structure of the fabricated nanocomposite. The EDX spectrum of the fabricated CTSN/Fe₃O₄-Cu nanocomposite and also the quantitative results have been exhibited in Fig. 2(c).

Table 1 Optimization of the reaction conditions of the synthesis of phenyl imidazole as the pilot experiment under USW irradiation

Entry	Solvent	Cat. (g)	Temp. (°C)	Time (min)	Yield ^a (%)
1	DMF	0.01	r.t.	10	88
2	DCM	0.01	r.t.	10	85
3	Water	0.01	r.t.	10	76
4	EtOH	0.01	r.t.	10	96
5	MeOH	0.01	r.t.	10	91
6	Water	0.01	r.t.	10	98^b
7	Water/EtOH	0.05	r.t.	10	98
8	Water/EtOH	0.01	50	10	97
9	Water/EtOH	0.01	80	10	97
10	Water/EtOH	0.01	r.t.	30	98

^a Isolated yield for product **3a**, via coupling reaction between bromobenzene (1.0 mmol) and imidazole (2.0 mmol), CTAB (0.5 mmol), in the presence of K₂CO₃ (1.5 mmol), and the solvent (4.0 mL), in the USW bath (50 kHz, 200 W). ^b Optimum conditions.

Field-emission scanning electron microscopy (FE-SEM) images were used to investigate shape and size of the prepared nanocomposite (Fig. 2). As seen in Fig. 2(a), suitable distribution of the spherical Fe₃O₄ NPs on the chitosan surfaces has formed a cluster-shaped nanocomposite. This morphology provides more extreme active areas for catalytic applications. Moreover, the size of the spherical Fe₃O₄ NPs is in a range of 40–60 nm diameter. Most likely, these regular cluster-shaped structures are produced via the *in situ* co-deposition process (described in preparation section). Then, the uniform spherical Cu NPs have been incorporated into the CTSN polymeric network, as can be observed in Fig. 2(b). Overall, this is clearly seen that an extreme catalytic active area is provided by the nanosized CTSN/Fe₃O₄-Cu nanocomposite.

The XRD pattern of the CTSN/Fe₃O₄-Cu nanocomposite has been demonstrated in Fig. 3, and the average size of the particles is calculated by the Scherrer equation; $D = k\lambda/\beta \cos \theta$. According to the figure, the resulted diffraction pattern has been precisely compared with the reference patterns of the Fe₃O₄ and CuO NPs and it was strongly confirmed that they have been thoroughly produced and distributed onto the textures of


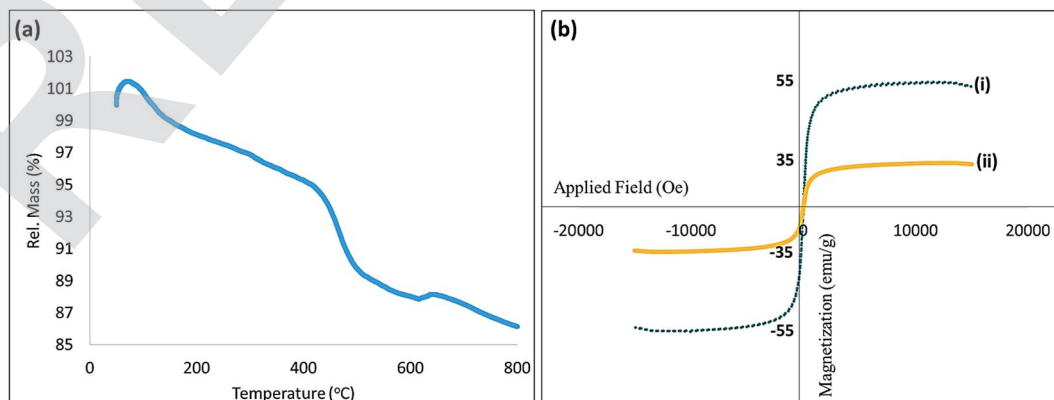


Fig. 4 (a) TGA of the fabricated CTSN/Fe₃O₄-Cu nanocomposite, and (b) VSM analysis of (i) Fe₃O₄ NPs and (ii) CTSN/Fe₃O₄-Cu nanocomposite.

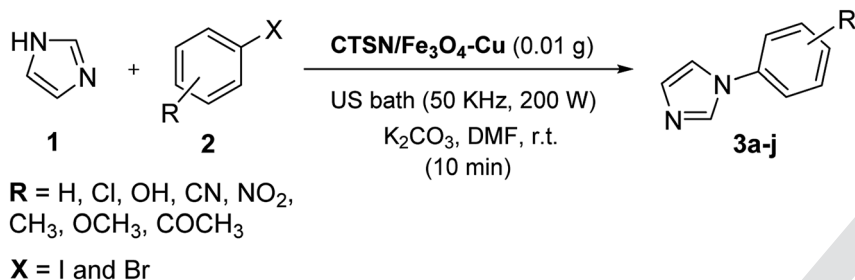

Scheme 2 Schematic of the synthesis of aryl imidazole derivatives by CTSN/Fe₃O₄-Cu nanocatalyst, in US bath.

CTSN matrix. Accordingly, the peaks at the dispersion angles $2\theta = 19.11^\circ, 31.64^\circ, 33.91^\circ, 36.56^\circ, 38.42^\circ, 45.15^\circ, 58.65^\circ, 63.25^\circ, 64.25^\circ$ and 78.65° , which have been marked with miller indices,

are attributed to the formed Fe₃O₄ and CuO NPs. There are strong correlations between the obtained XRD pattern and the reported references.^{13,25}

Table 2 Synthesis of various aryl imidazole derivatives using CTSN/Fe₃O₄-Cu nanocatalyst

Entry	R-Ar-X		Product structure	Product no.	Yield ^a (%)
	R	X			
1	H	Br		3a	98
2	Me	Br		3b	92
3	Me	I		3c	90
4	OMe	I		3d	85
5	OH	Br		3e	82
6	Cl	I		3f	93
7	COMe	Br		3g	92
8	CN	I		3h	98
9	NO ₂	Br		3i	96
10	NO ₂	I		3j	97

^a Isolated yield.



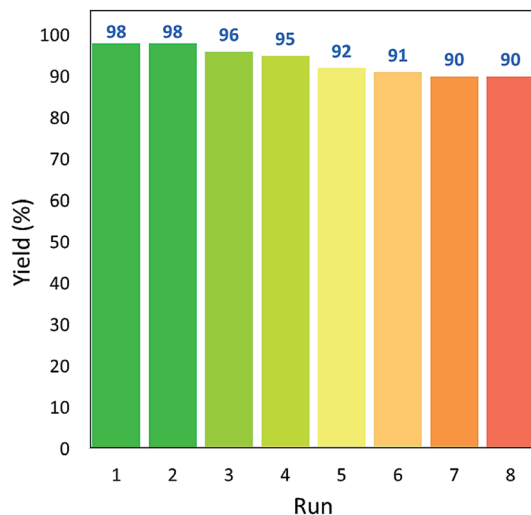


Fig. 5 Reusability diagram of CTSN/Fe₃O₄-Cu nanocomposite.

Thermal resistance of the fabricated CTSN/Fe₃O₄-Cu nanocomposite has also been studied by thermogravimetric analysis (TGA). As shown in Fig. 4(a), initially a partial increase in the weight was observed that is attributed to the physical adsorption of the moisture of the air onto the hot surfaces of NPs. Then, the weight percentage was decreased to *ca.* 98% due to removal of the water molecules. In continue, by increasing the temperature to around 420 °C, the first important shoulder was appeared that coming from the weight loss of CTSN. According to the literature,

decomposition of the CTSN is started above 420 °C.²⁶ Further, the second shoulder is observed at 620 °C, which is ascribed to the decomposition of the NPs. Totally, from the TGA, this is well proven that the degradation and decomposition of CTSN polysaccharide is greatly inhibited by the composited Cu and Fe₃O₄ NPs. Magnetic property of the fabricated CTSN/Fe₃O₄-Cu nanocomposite has also been investigated by vibrating-sample magnetometer (VSM) analysis and related spectra are shown in Fig. 4(b). As it can be seen in the spectra, the magnetic feature of the neat Fe₃O₄ NPs is reduced proportional to more core coating by various layers. Graph (i) that belongs to the neat Fe₃O₄ NPs exhibits a typical super-paramagnetic behavior (55 emu g⁻¹) through applying the magnetic field, as presented in the figure. This property was ~20 emu g⁻¹ decreased through subsequent coating by CTSN (graph ii). However, this is clearly seen that super-paramagnetic behavior of the produced CTSN/Fe₃O₄-Cu nanocomposite is adequate for easily separation of the catalyst from the reaction mixture.

3.3. Catalytic activity of CTSN/Fe₃O₄-Cu nanocatalyst

3.3.1. Optimization of the catalyzed-reaction conditions & catalytic performance screening. In order to obtain the optimum conditions for the synthesis reactions by novel prepared heterogeneous CTSN/Fe₃O₄-Cu nanocatalyst, control reaction was carried out using imidazole **1** (2.0 mmol), bromobenzene **2** (1.0 mmol), cetyltrimethylammonium bromide (CTAB, 0.5 mmol), and

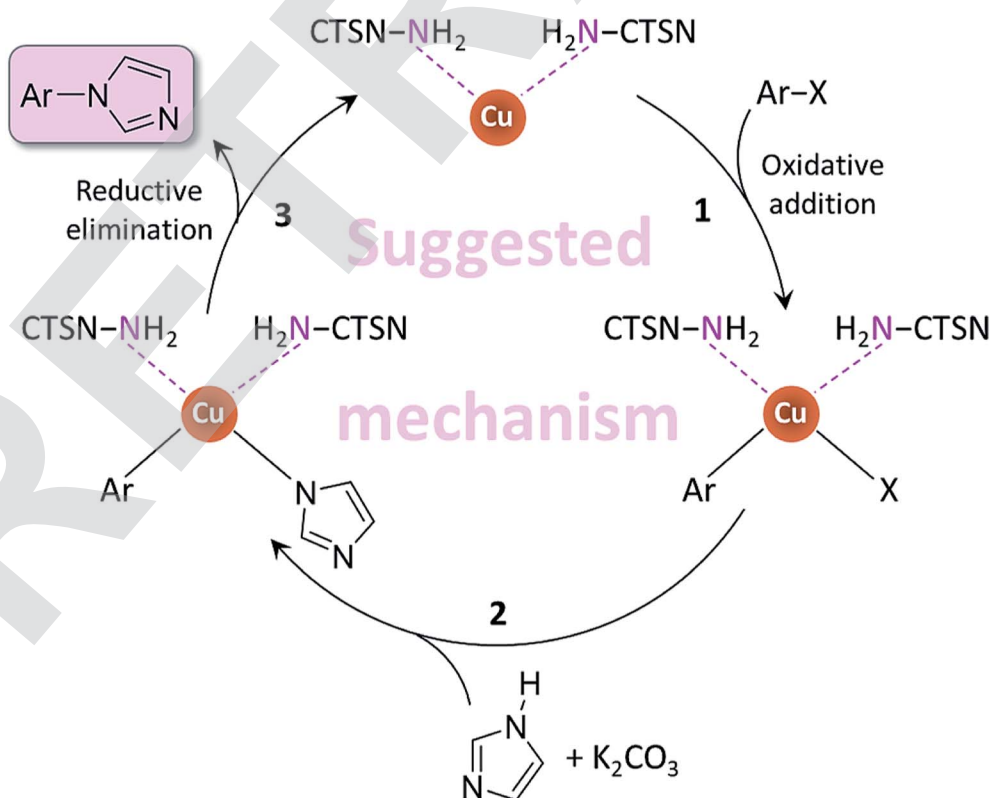


Fig. 6 The plausible mechanism for *N*-arylation of imidazole derivatives assisted by CTSN/Fe₃O₄-Cu nanocomposite.



different amounts of CTSN/Fe₃O₄-Cu in various conditions (Scheme 2 and Table 1). Accordingly, the same reaction conditions were applied for all of the control reactions. Different amounts of the magnetic nanocatalyst, different reaction times, and the synergistic effect between the magnetic nanocomposite and USW were precisely investigated. As reported in Table 1, the best result was observed when 0.01 g of CTSN/Fe₃O₄-Cu was used in deionized water, under 10 min ultrasonication (50 kHz frequency and 200 W power density), at room temperature. The reaction progress was screened using thin-layer chromatography (TLC). After completion of the reaction, the heterogeneous nanocatalyst were conveniently collected using an external magnet, then resulted aryl imidazole was immediately separated and purified *via* flash column chromatography and identified with ¹H-NMR and ¹³C-NMR (see the ESI section†). However, in order to evaluate the scope and generality of this approach, the optimized reaction condition was applied for the synthesis reactions of the diverse aryl imidazole derivatives, as summarized in Table 2. The *N*-arylation of imidazoles with aryl iodides and aryl bromides bearing both electron-donating and electron-withdrawing groups was done effectively and gave good yields. As same as excellent results were obtained in gram scale of the reaction by starting these ratio of raw materials and reagents.

3.3.2. Catalyst reusability. Another important advantage of this active, non-toxic, and environmentally-benign heterogeneous catalyst is its well recyclability. In this regard, the nanocatalyst performance was carefully monitored in the model reaction (product **3a**) after eight times recycling. For this purpose, after completion of the reaction, the CTSN/Fe₃O₄-Cu nanocomposite were magnetically isolated from the mixture and washed with ethanol, then dried and reused in subsequent reactions. It is observed that the nanocatalyst can be reused at least for eight successive times without any significant reduction in coupling reaction yield (Fig. 5). The observed reduction in catalytic activity probably origins from the separation of Cu NPs from the total structure of the nanocatalyst and deformation of the cluster-shaped structure of CTSN/Fe₃O₄-Cu nanocomposite during the catalytic process. These claims have been proven by SEM imaging and EDX spectroscopy of the recovered nanocatalyst after eight times usages (Fig. S5 and S6, in the ESI section†).

3.4. Suggested mechanism

A plausible mechanism for this catalytic reaction has been depicted in Fig. 6. As can be seen, at the first stage, an oxidative addition is occurred through which Cu inserts into the Ar-X bond. Then, the resulted complex reacts with imidazole that was activated by potassium carbonate, at stage 2. In the following step (stage 3), a reductive elimination is occurred and the desirable product is obtained.²⁷

4. Conclusion

In summary, a novel catalytic system constructed of chitosan, iron oxide NPs, and copper NPs has been designed and

presented as an instrumental tool for facilitating the synthesis of *N*-arylimidazole derivatives. There are several advantages for applying this nanoscale system. The first and foremost excellence, well execution of synthesis reactions under mild conditions (98% yielded in 10 min at room temperature) through using a partial amount (0.01 g) of this heterogeneous catalytic system can be referred. This high catalytic performance is due to a synergistic catalytic effect between the fabricated nanocomposite (CTSN/Fe₃O₄-Cu) and the ultrasound waves with 50 kHz frequency and 200 W L⁻¹ power density. In addition, the nanocatalyst is conveniently separated from the reaction mixture and recovered by an external magnetic field and reused efficiently for additional seven times without significant decrease in its catalytic activity. Moreover, there are several advantages for the presented catalytic system such as high heterogeneity, great biocompatibility and biodegradability (through applying CTSN as a natural basis), economic advantages, excellent structural stability due to assisting by ultrasound waves, and no need to another chemical additive or applying intense reaction conditions to provide the required driving force. Thus, this catalytic system could be suggested for scaling up and using in industry.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

The authors gratefully acknowledge the partial support from the Research Council of the Iran University of Science and Technology and Iran National Science Foundation (INSF).

References

- 1 Z. Wang, S. Yao, S. Pan, J. Su, C. Fang, X. Houa and M. Zhan, Synthesis of silver particles stabilized by a bifunctional SiH_x-NH_y-PMHS oligomer as recyclable nanocatalysts for the catalytic reduction of 4-nitrophenol, *RSC Adv.*, 2019, **9**, 31013–31020.
- 2 R. Eisavi and A. Karimi, CoFe₂O₄/Cu(OH)₂ magnetic nanocomposite: an efficient and reusable heterogeneous catalyst for one-pot synthesis of β-hydroxy-1,4-disubstituted-1,2,3-triazoles from epoxides, *RSC Adv.*, 2019, **9**, 29873–29887.
- 3 P. Bai, S. Wei, X. Loua and L. Xu, An ultrasound-assisted approach to bio-derived nanoporous carbons: disclosing a linear relationship between effective micropores and capacitance, *RSC Adv.*, 2019, **9**, 31447–31459.
- 4 Y. Yang, M. Chen, Y. Wu, P. Wang, Y. Zhao, W. Zhu, Z. Song and X. B. Zhang, Ultrasound assisted one-step synthesis of Au@Pt dendritic nanoparticles with enhanced NIR absorption for photothermal cancer therapy, *RSC Adv.*, 2019, **9**, 28541–28547.
- 5 A. Maleki, H. Movahed, P. Ravaghi and T. Kari, Facile *in situ* synthesis and characterization of a novel PANI/Fe₃O₄/Ag



- nanocomposite and investigation of catalytic applications, *RSC Adv.*, 2016, **6**, 98777–98787.
- 6 A. Maleki, Green oxidation protocol: Selective conversions of alcohols and alkenes to aldehydes, ketones and epoxides by using a new multiwall carbon nanotubebased hybrid nanocatalyst via ultrasound irradiation, *Ultrason. Sonochem.*, 2018, **40**, 460–464.
 - 7 R. Taheri-Ledari, J. Rahimi and A. Maleki, Synergistic catalytic effect between ultrasound waves and pyrimidine-2,4-diamine-functionalized magnetic nanoparticles: Applied for synthesis of 1,4-dihydropyridine pharmaceutical derivatives, *Ultrason. Sonochem.*, 2019, **59**, 104737.
 - 8 A. H. Liao, Y. J. Lu, C. R. Hung and M. Y. Yang, Efficacy of transdermal magnesium ascorbyl phosphate delivery after ultrasound treatment with microbubbles in gel-type surrounding medium in mice, *Mater. Sci. Eng., C*, 2016, **61**, 591–598.
 - 9 J. Rahimi, R. Taheri-Ledari, M. Niksefat and A. Maleki, Enhanced reduction of nitrobenzene derivatives: Effective strategy executed by Fe₃O₄/PVA-10% Ag as a versatile hybrid nanocatalyst, *Catal. Commun.*, 2020, **134**, 105850.
 - 10 A. Maleki, R. Rahimi, S. Maleki and N. Hamidi, Synthesis and characterization of magnetic bromochromate hybrid nanomaterials with triphenylphosphine surface-modified iron oxide nanoparticles and their catalytic application in multicomponent reactions, *RSC Adv.*, 2014, **4**, 29765–29771.
 - 11 A. Maleki, R. Taheri-Ledari, R. Ghalavand and R. Firouzi-Haji, Palladium-decorated o-phenylenediamine-functionalized Fe₃O₄/SiO₂ magnetic nanoparticles: A promising solid-state catalytic system used for Suzuki–Miyaura coupling reactions, *J. Phys. Chem. Solids*, 2020, **136**, 109200.
 - 12 A. Maleki, P. Zand and Z. Mohseni, Fe₃O₄@PEG-SO₃H rod-like morphology along with the spherical nanoparticles: novel green nanocomposite design, preparation, characterization and catalytic application, *RSC Adv.*, 2016, **6**, 110928–110934.
 - 13 A. Maleki, R. Taheri-Ledari, J. Rahimi, M. Soroushnejad and Z. Hajizadeh, Facile peptide bond formation: effective interplay between isothiazolone rings and silanol groups at silver/iron oxide nanocomposite surfaces, *ACS Omega*, 2019, **4**, 10629–10639.
 - 14 A. Maleki, M. Niksefat, J. Rahimi and R. Taheri-Ledari, Multicomponent synthesis of pyrano[2,3-d]pyrimidine derivatives via a direct one-pot strategy executed by novel designed copperated Fe₃O₄@polyvinyl alcohol magnetic nanoparticles, *Mater. Today Chem.*, 2019, **13**, 110–120.
 - 15 A. Maleki, M. Aghaei, H. R. Hafizi-Atabak and M. Ferdowsi, Ultrasonic treatment of CoFe₂O₄@B₂O₃-SiO₂ as a new hybrid magnetic composite nanostructure and catalytic application in the synthesis of dihydroquinazolinones, *Ultrason. Sonochem.*, 2017, **37**, 260–266.
 - 16 A. Maleki, M. Aghaei and N. Ghamari, Synthesis of benzimidazolo[2,3-b]quinazolinone derivatives via a one-pot multicomponent reaction promoted by chitosan-based composite magnetic nanocatalyst, *Chem. Lett.*, 2015, **44**, 259–261.
 - 17 A. Maleki, R. Taheri-Ledari and M. Soroushnejad, Surface functionalization of magnetic nanoparticles via palladium-catalyzed Diels–Alder approach, *ChemistrySelect*, 2018, **3**, 13057–13062.
 - 18 D. Koseki, E. Aoto, T. Shoji, K. Watanabe, Y. In, Y. Kita and T. Dohi, Efficient N-arylation of azole compounds utilizing selective aryl-transfer TMP-iodonium(III) reagents, *Tetrahedron Lett.*, 2019, **60**, 1281–1286.
 - 19 J. Ohmori, H. Kubota, M. Shimizu-Sasamata, M. Okada and S. Sakamoto, Novel α -Amino-3-hydroxy-5-methylisoxazole-4-propionate Receptor Antagonists: Synthesis and Structure–Activity Relationships of 6-(1H-Imidazol-1-yl)-7-nitro-2,3(1H,4H)-pyrido[2,3-b]pyrazinedione and Related Compounds, *J. Med. Chem.*, 1996, **39**, 1331–1338.
 - 20 P. Cozzi, G. Carganico, D. Fusar, M. Grossoni, M. Menichincheri, V. Pinciroli, R. Tonani, F. Vaghi and P. Salvati, Imidazol-1-yl and pyridin-3-yl derivatives of 4-phenyl-1,4-dihydropyridines combining Ca²⁺ antagonism and thromboxane A₂ synthase inhibition, *J. Med. Chem.*, 1993, **36**, 2964–2972.
 - 21 S. U. Son, I. K. Park, J. Park and T. Hyeon, Synthesis of Cu₂O coated Cu nanoparticles and their successful applications to Ullmann-type amination coupling reactions of aryl chlorides, *Chem. Commun.*, 2004, **7**, 778–779.
 - 22 B. M. Choudary, C. Sridhar, M. L. Kantam, G. T. Venkanna and B. Sreedhar, Design and evolution of copper apatite catalysts for N-Arylation of heterocycles with chloro- and fluoroarenes, *J. Am. Chem. Soc.*, 2005, **127**, 9948–9949.
 - 23 R. Taheri-Ledari, A. Maleki, E. Zolfaghari, M. Radmanesh, H. Rabbani, A. Salimi and R. Fazel, High-performance sono/nano-catalytic system: Fe₃O₄@ Pd/CaCO₃-DTT core/shell nanostructures, a suitable alternative for traditional reducing agents for antibodies, *Ultrason. Sonochem.*, 2020, **61**, 104824.
 - 24 A. Maleki, R. Taheri-Ledari, R. Eivazzadeh-Keihan, M. de la Guardia and A. Mokhtarzadeh, Preparation of Carbon-14 Labeled 2-(2-mercaptoacetamido)-3-phenylpropanoic Acid as Metallo-beta-lactamases Inhibitor (MBLI), for Coadministration with Beta-lactam Antibiotics, *Curr. Org. Synth.*, 2019, **16**, 765–771.
 - 25 S. Suresh, S. Karthikeyan and K. Jayamoorthy, FTIR and multivariate analysis to study the effect of bulk and nano copper oxide on peanut plant leaves, *Journal of Science: Advanced Materials and Devices*, 2016, **1**, 343–350.
 - 26 G. Cardenas and S. P. Miranda, FTIR and TGA studies of chitosan composite films, *J. Chil. Chem. Soc.*, 2004, **49**, 291–295.
 - 27 A. R. Sardarian, N. Zohourian-Mashmoul and M. Esmaeilpour, Salen complex of Cu(II) supported on superparamagnetic Fe₃O₄@SiO₂ nanoparticles: an efficient and magnetically recoverable catalyst for N-arylation of imidazole with aryl halides, *Monatsh. Chem.*, 2018, **149**, 1101–1109.

