Chemical Science

EDGE ARTICLE



View Article Online

View Journal | View Issue

Check for updates

Cite this: Chem. Sci., 2019, 10, 9822

All publication charges for this article have been paid for by the Royal Society of Chemistry

Received 2nd July 2019 Accepted 2nd September 2019

DOI: 10.1039/c9sc03242h

Introduction

Carbon dioxide (CO₂) is an abundant, readily available, nontoxic and renewable C1 building block, and its transformation into value-added chemicals and fuels is of great significance for green and sustainable development.¹⁻⁶ The reactions of amines with CO₂ in the presence of reductants such as hydrosilanes and H₂ have been widely investigated, and they generally produce formamides or methylamines.⁷⁻¹¹ For the reaction of amines with CO₂/H₂, the production of methylamines is more difficult than the formation of formamides,¹²⁻¹⁷ and it requires harsh reaction conditions and catalysts with very high activity.¹⁸⁻²¹ 1,2-Bis(N-heterocyclic)ethanes (*e.g.*, 1,2-bis(piperidine)ethane) are a kind of high value chemical and are generally synthesized *via* the reaction of cyclic amines with ethyl halides, suffering from production of a large amount of acid

Selective synthesis of formamides, 1,2-bis(N-heterocyclic)ethanes and methylamines from cyclic amines and CO_2/H_2 catalyzed by an ionic liquid–Pd/C system[†]

Ruipeng Li,^{ab} Yanfei Zhao,^{*a} Huan Wang,^{ab} Junfeng Xiang,^a Yunyan Wu,^{ab} Bo Yu,^a Buxing Han^b^{abc} and Zhimin Liu^{*abc}

The reduction of CO₂ with amines and H₂ generally produces *N*-formylated or *N*-methylated compounds over different catalysts. Herein, we report the selective synthesis of formamides, 1,2-bis(N-heterocyclic) ethanes, and methylamines, which is achieved over an ionic liquid (IL, *e.g.*, 1-butyl-3-methylimidazolium tetrafluoroborate, [BMIm][BF₄])–Pd/C catalytic system. By simply varying the reaction temperature, formamides and methylamines can be selectively produced, respectively, in high yields. Interestingly, 1,2-bis(N-heterocyclic)ethanes can also be obtained *via* the McMurry reaction of the formed formamide coupled with subsequent hydrogenation. It was found that [BMIm][BF₄] can react with formamide to form a [BMIm]⁺–formamide adduct; thus combined with Pd/C it can catalyze McMurry coupling of formamide in the presence of H₂ to afford 1,2-bis(N-heterocyclic)ethane to access methylamine. [BMIm][BF₄]–Pd/C was tolerant to a wide substrate scope, giving the corresponding formamides, 1,2-bis(N-heterocyclic)ethanes or methylamines in moderate to high yields. This work develops a new route to produce *N*-methylamine and opens the way to produce 1,2-bis(N-heterocyclic)ethane from cyclic amine as well.

waste and complicated post-treatment.^{22,23} The synthesis of 1,2bis(N-heterocyclic)ethanes from cyclic amines and CO_2/H_2 is a green and promising route, but this has not been realized yet.

Compared to molecular solvents (e.g., water and organic solvents), ionic liquids (ILs) that are completely composed of ions have unique properties, such as a wide liquid window, very low vapor pressure, specific H-bonding between anions and cations, and so on, which make them promising media for chemical processes.²⁴⁻²⁸ In particular, they can be designed with specific functions via selection of suitable cations and/or anions, and have been widely applied in catalysis, showing great potential. For example, as both the solvent and catalyst, 1ethyl-3-methylimidazolium acetate worked well for the transformation of alcohols to esters using O2 as an oxidant under metal-free conditions.²⁹ CO₂-philic ILs that can capture CO₂ via forming carbonates or carbamates have been reported to be excellent media and/or catalysts for CO2 transformation into chemicals.30,31 value-added 1-Butyl-3-methylimidazolium ([BMIm]⁺) chloride combined with Rh nanoparticles and ZnCl₂, could realize the efficient reduction of heteroarenes.³² Carbanion-functionalized IL along with Pd(OAc)₂ was capable of catalyzing the alkoxycarbonylation reactions of CO to benzoate products under ambient conditions.33 In these

^aBeijing National Laboratory for Molecular Sciences, Key Laboratory of Colloid, Interface and Thermodynamics, CAS Research, Institute of Chemistry, Chinese Academy of Sciences, Beijing 100190, China. E-mail: liuzm@iccas.ac.cn; lianyi302@ iccas.ac.cn

^bUniversity of Chinese Academy of Sciences, Beijing 100049, China

^cPhysical Science Laboratory, Huairou National Comprehensive Science Center, China † Electronic supplementary information (ESI) available: Supporting figures and tables. See DOI: 10.1039/c9sc03242h


reactions, ILs generate synergistic effects with other active species, promoting or catalyzing the reactions.

Herein, we report the reduction of CO₂ with amine and H₂ over an IL-Pd/C catalytic system, which accomplished the selective synthesis of formamides, 1,2-bis(N-heterocyclic) ethanes and methylamines. Interestingly, the combination of Pd/C with [BMIm][BF₄] could realize the selective production of formamides (at 120 °C) or N-methylamines (at 160 °C) in high yields, respectively, as illustrated in Scheme 1. Moreover, 1,2bis(N-heterocyclic)ethanes can also be obtained via the McMurry reaction of the formed formamide coupled with subsequent hydrogenation. It was found that $[BMIm][BF_4]$ could react with formamide to form a [BMIm]⁺-formamide adduct; thus combined with Pd/C, it can catalyse McMurry coupling of formamide in the presence of H₂ to afford 1,2-bis(Nheterocyclic)ethane and further catalyse hydrogenolysis of 1,2bis(N-heterocyclic)ethanes to access methylamine. In addition, detailed studies indicate that the IL played multiple roles in the reactions including modifying the electronic properties of the metallic Pd particles to enhance their catalytic activity and activating the amine and the intermediate via strong hydrogen bonding. [BMIm][BF₄]-Pd/C was tolerant to a wide substrate scope, giving the corresponding formamides, 1,2-bis(Nheterocyclic)ethanes or methylamines in moderate to high yields. This work develops a new route to N-methylamine and opens the way to produce 1,2-bis(N-heterocyclic)ethane from cyclic amine and CO_2/H_2 .

Results and discussion

Preparation and characterization of the Pd/C catalyst

To prepare the Pd/C catalyst with a loading of 5 wt%, a porous carbon support was first fabricated according to our previous report,³⁴ on which Pd nanoparticles were immobilized *via* the equal volume impregnation method followed by hydrogen reduction. In the TEM images of the Pd/C catalyst (Fig. 1a and b), the dark dots were identified as Pd nanoparticles, which were uniformly distributed on the support with an average particle size around 1.7 nm. The N₂ adsorption/desorption isotherms (Fig. 1c) indicated that the carbon support exhibited microporous and mesoporous structures with a specific surface area of 950.6 m² g⁻¹. The pore radius distribution curve (Fig. 1d) showed that the pore radii were centered at 15 nm according to the BJH model, a typical feature of mesoporous materials accompanied by some micropores.

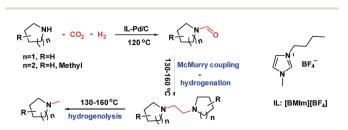

Scheme 1 Selective reduction of CO₂ with amines and H₂.


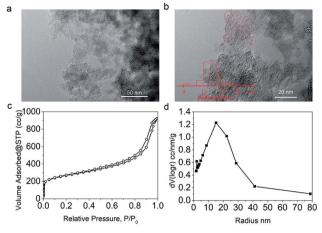


Fig. 1 TEM (a) and HRTEM (b) images, N_2 sorption isotherms (c) and pore size distribution (d) of the Pd/C catalyst used in this work.

Exploration of the catalytic system for the reaction of piperidine with $\rm CO_2/H_2$

In our initial experiments, the reaction of piperidine (1a) with CO_2/H_2 was performed using Pd/C as the catalyst to screen the catalytic system and reaction conditions for selective formation of formylpiperidine (2a), 1,2-bis(piperidine)ethane (3a) or methylpiperidine (4a). In the absence of CO_2 and H_2 , no product was detected. As shown in Table 1, the solvents significantly

Table 1 The reaction of piperidine with CO_2/H_2 over various catalytic systems^{*a*}



Entry	Solvent	Yield ^e (%)		
		2a	3a	4a
1	Ethanol	99	0	0
2	THF	99	0	0
3	Octane	99	0	0
4	[BMIm][BF ₄]	6	11	82
5^{b}	[BMIm][BF ₄]	3	6	90
6	[HMIm][BF ₄]	17	22	49
7	[BMIm][Cl]	81	14	1
8	[BMIm][PF ₆]	46	Trace	53
9	[BMIm][NTf ₂]	67	13	18
10	$[P_{4444}][BF_4]$	99	0	0
11	$[N_{4444}][BF_4]$	99	0	0
12^{c}	$[BMIm][BF_4] + [BMIm][Cl]$	16	57	26
13^d	$[BMIm][BF_4] + THF$	1	77	22

 a Conditions: 1a (0.5 mmol), Pd/C (20 mg), solvent (1 mL) or IL (5 mmol), H₂ (6 MPa), total pressure of 10 MPa, 160 °C, 6 h. b 9 h. c H₂ (5 MPa), total pressure of 8 MPa, [BMIm][BF₄] (1.7 mmol), [BMIm][Cl] (3.3 mol), 9 h. d H₂ (5 MPa), total pressure of 8 MPa, [BMIm][BF₄] (2.5 mmol), THF (2.5 mL), 9 h. e Yield was determined by GC using trimethoxybenzene as the internal standard.

affected the product selectivity. Molecular solvents including ethanol, tetrahydrofuran (THF) and octane exclusively afforded 2a (Table 1, entries 1-3), while imidazolium-based ILs including [BMIm][BF₄], [BMIm][PF₆], [BMIm][NTf₂] and [BMIm][Cl] could offer 2a, 3a and 4a in different yields under the experimental conditions (Table 1, entries 4–9). Among these ILs, $[BMIm][BF_4]$ showed the best performance for the production of 4a, achieving a yield of 90% within 9 h (Table 1, entry 5). However, only 2a was obtained in the ILs $[P_{4444}]\![BF_4]$ and $[N_{4444}]\![BF_4]$ (Table 1, entries 10 and 11). These results indicated that for the imidazolium-based ILs the cations played a key role in the formation of 4a, and the anions influenced the activity of the cations. Given that 3a is an important chemical and it has not been accessed from 1a and CO_2/H_2 , we optimized the reaction conditions to obtain 3a as the main product (Table S1[†]). Combined with Pd/C the mixtures of [BMIm][BF₄] with THF or with [BMIm][Cl] could afford 3a in yields higher than 50% at 160 °C (Table 1, entries 12 and 13). Considering that using THF as the reaction medium only 2a was obtained, it can be deduced that [BMIm][BF₄] and Pd/C combine to catalyze the formation of 3a and 4a.

Since [BMIm][BF₄]-Pd/C showed the best performance for methylation of **1a** with CO_2/H_2 to **4a**, it was applied to explore the effects of temperature and reaction time on the reaction. As illustrated in Fig. 2a, the reaction temperature significantly influenced the product selectivity. At 120 °C, **2a** was the sole product in an almost quantitative yield within 9 h, while both **3a** and **4a** were detected in the temperature range of 130–160 °C with the **4a** yield increasing with temperature up to 90% at 160 °C. Notably, the yield of **3a** was maintained around 20% in this temperature range, while at 160 °C it decreased significantly and **4a** became the main product. From the dependence of the **2a** and **3a** yields on the reaction time at 160 °C (Fig. 2b), it was deduced that **2a** and **3a** were finally converted into **4a** under the experimental conditions.

Generality of the [BMIm][BF₄]-Pd/C catalytic system

To explore the generality of the $[BMIm][BF_4]$ -Pd/C catalytic system, it was applied in the reactions of various cyclic amines with CO₂/H₂. As shown in Scheme 2, this catalytic system was effective for catalyzing the reactions of the tested substrates with CO₂/H₂, and formylated and methylated products were selectively obtained at 120 and 160 °C, respectively. Pyrrolidine, piperidine, hexamethyleneimine, and morpholine exhibited


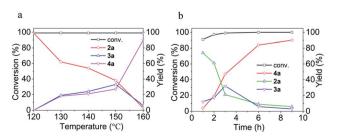


Fig. 2 Effects of temperature (a) and reaction time (b) on the conversion of 1a and the yields of 2a, 3a and 4a. (a) 9 h. (b) 160 °C.

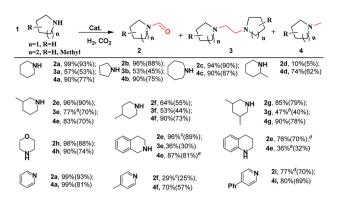

Scheme 2 Substrate scope for selective reduction of CO₂ with amine and H₂ over the Pd/C catalyst. For *N*-formylation: substrate (0.5 mmol), Pd/C (20 mg), [BMIm][BF₄] (5 mmol), H₂ (3 MPa), total pressure of 5 MPa, 120 °C, 6 h; isolated yield in brackets. For methylation: H₂ (6 MPa), total pressure of 10 MPa, 160 °C, 6 h; the others are the same as those for *N*-formylation. For accessing 1,2-bis(N-heterocyclic) ethanes: substrate (0.5 mmol), Pd/C (20 mg), [BMIm][BF₄] (1.7 mmol), [BMIm][CI] (3.3 mmol), H₂ (5 MPa), total pressure of 8 MPa, 6 h. ^a12 h. ^b10 h. ^c140 °C, 9 h. ^d140 °C, 12 h, ^e160 °C, 24 h.

good reactivity, affording corresponding formylated and methylated products in 90–99% yields under the optimized conditions. By using substituted piperidines like 3-methylpiperidine, 4-methylpiperidine, 2-methylpiperidine, 3,5-dimethylpiperidine, 1,2,3,4-tetrahydroisoquinoline and 1,2,3,4-tetrahydroquinoline as substrates, the reaction also proceeded smoothly and selectively furnished the desired products in moderate to high yields. However, 2-methylpiperidine was converted into the corresponding formamide (**2d**) only in 10% yield at 120 °C and 1,2,3,4-tetrahydroquinoline led to the corresponding methylamine in low yield.

After detailed screening of the reaction conditions, 1,2-bis(N-heterocyclic)ethanes could be achieved in moderate yields in most cases. The highest yield of 1,2-bis(N-heterocyclic)ethane (*e.g.*, **3e**) reached up to 77%. Interestingly, using pyridine, 4-methylpyridine, and 4-phenylpyridine as the substrates, they were first hydrogenated, and the corresponding formamides and methylamines were obtained in high yields. However, in these cases corresponding 1,2-bis(N-heterocyclic)ethanes were detected in small amounts, and the reason is unclear. In addition, $[BMIm][BF_4]$ -Pd/C was also effective in the reaction of chain secondary amines (*e.g.*, 1,2-diaminopropane) with CO₂/H₂, selectively producing formamide or methylamine in excellent yields, but it was difficult to access the corresponding 1,2-bis(amino)ethane (Scheme S1[†]).

The roles of the IL

To explore the roles of the IL in the reactions, the interactions of the IL with Pd/C and with **1a**, **2a**, and **3a** were investigated. Thermogravimetric analysis on the Pd/C catalysts after adsorption of IL at 120 °C and 160 °C (Fig. S1†) indicates that the amounts of the IL adsorbed on Pd/C reached 1.28 and 0.69 wt%, respectively, and its decomposition temperature (500 °C) was much higher than that of the free IL (380 °C). These results indicate that the IL had strong interaction with Pd/C.

The Pd/C adsorbing 1.28 wt% [BMIm][BF₄] (denoted as IL-Pd/C) was examined by XPS. In the XPS spectrum of IL-Pd/C, the peaks at 340.8 (Pd 3d_{3/2}) and 335.5 eV (Pd 3d_{5/2}) attributed to Pd⁰ in Pd/C-IL exhibited a downshift of 0.3 eV compared with those of Pd/C (Fig. 3), indicating a possible electron transfer from the IL to the metallic Pd particles. This was also verified by the upshift of the N 1s peak of IL-Pd/C as compared to that of IL-C (Fig. S2,† IL-C refers to the IL adsorbed on a carbon support). The IR analysis (Fig. S3[†]) indicates that the adsorbed IL on Pd/C showed a red-shifted C-N stretching band of the IL cation from 1580 to 1575 cm⁻¹, which is consistent with electron donation from N atoms in [BMIm]⁺ to the Pd particles. FT-EXAFS spectra also gave evidence that the IL was complexed with Pd (Fig. S4[†]). It is reasonable that the lone electron pair of N can affect the electronic state of the Pd particles attached to it because one N atom in the [BMIm]⁺ cation is essentially in the sp^2 hybridization state.

Furthermore, the interactions of [BMIm][BF₄] with CO₂, 1a, 2a and 3a were investigated via NMR analysis. No new signals or obvious chemical shifts were observed in the ¹H, ¹³C, ¹⁹F and ¹¹B NMR spectra of the mixture of [BMIm][BF₄] and CO₂ (Fig. S5[†]), indicating that this IL cannot activate CO₂ noticeably. Given that 1a is easily converted to a white solid, dihydropyridine-monocarboxylic acid, once exposed to CO2, it is supposed that CO₂ is activated by **1a** via forming an adduct. ¹H, ¹⁵N, ¹¹B NMR (Fig. S6, S7A and B†) and FTIR (Fig. S8†) analyses on the [BMIm][BF₄]-1a mixture indicate that 1a was activated by the IL via hydrogen bonding and electrostatic interaction. In the ¹H NMR spectrum of the [BMIm][BF₄]-2a mixture (Fig. 4a), the ¹H signal of the formyl group in **2a** and that of the H atoms in [BMIm]⁺ shifted greatly, suggesting the strong C-H···O interaction between the acidic H(2) of $[BMIm]^+$ and the O atom of the formyl group in 2a. Specifically, the ¹³C NMR signals of the formyl group also shifted accordingly (Fig. S9[†]), further revealing the activation of the formyl group by the IL. In the FTIR spectrum, the absorption band at 1669 cm⁻¹ attributed to the stretching vibration of C=O of 1a shifted to 1664 cm^{-1} upon 1a interacting with [BMIm][BF₄], and the peaks at 3162 and 3122 cm⁻¹ belonging to the stretching vibration of C-H from the imidazole ring of [BMIm]⁺ shifted accordingly. The FTIR analysis gave evidence of interaction between 1a and the IL, also supporting the NMR results (Fig. 4b). As reported, reactive carbenes can be generated at the C(2) position of [BMIm]⁺ under mild basic conditions.³⁵ In this work, the basic reaction environment provided by 1a or 4a may be favorable for

Fig. 3 Pd 3d XPS spectra of (a) Pd/C and (b) IL-Pd/C.

341 1

342.7

ntensity (a.u.)

334

336 338 340 342 344 346

Binding energy (eV)

346

336 338 340 342 344

Binding energy (eV)

335.8

334

Intensity (a.u.)

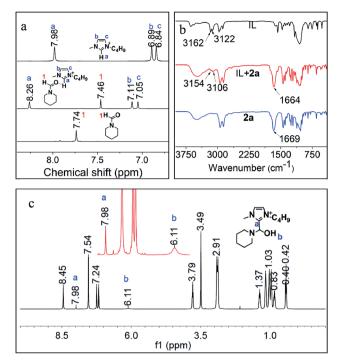



Fig. 4 1 H NMR (a) and FT-IR spectra (b) of [Bmim][BF₄], 2a and their mixture, and 1 H NMR (c) of the mixture of IL and 2a together with K₂CO₃.

the formation of carbenes from [BMIm]⁺, which may further react with 2a to form an intermediate. To confirm this hypothesis, a mixture of IL and 2a together with K₂CO₃ was examined. Based on ¹H NMR and ¹H-¹H correlation spectroscopy (COSY) analysis (Fig. 4c and S10[†]), an intermediate from $[BMIm][BF_4]$ and 2a (denoted as $[BMIm-OH-2a][BF_4]$) was detected (Fig. 4c), which was also confirmed by the detection of $\{[BMIm-OH-2a][BF_4][BMIm](2a)\}^+$ (m/z)=591.4) by electrospray-ionization mass spectrometry (ESI-MS) (Fig. S11⁺). The above results indicate that the IL can activate 2a to form a [BMIm]⁺-formamide adduct, which may be favorable for the formation of 3a and 4a. In addition, 3a can also be activated by the IL, as supported by NMR analysis with the obvious changes of chemical shifts as it mixed with the IL in the presence of 2a (Fig. S12[†]), which can explain why the IL promotes the hydrogenolysis of 3a.


Possible reaction pathway

To gain deep insight into the reaction pathway of the formation of **3a** and **4a**, control experiments were performed. Previous reports revealed that **2a** could be catalytically converted to **4a** *via* hydrogenation under appropriate conditions.³⁶ However, in this work taking **2a** as the substrate to react with CO_2/H_2 or only with H_2 over Pd/C in [BMIm][BF₄], no **4a** was detectable (Scheme S2A and B†). This indicates that Pd/C could not catalyze the direct hydrogenation of **2a** to **4a** in [BMIm][BF₄], which excludes the pathway of **2a** reduction with H_2 , and implies that **2a** undergoes transformation to **3a** to form **4a**.

As is known, McMurry coupling is a reductive reaction, in which two ketone or aldehyde groups are coupled to form an alkene using a titanium chloride compound (e.g., titanium(IV) chloride) and a reducing agent (e.g., zinc) in the presence of a base.³⁷ In the process of 1a reacting with CO₂/H₂, the reaction system is always kept in a basic environment due to the presence of the amine feedstock or the formed methylamine, which might facilitate the occurrence of the McMurry reaction of the formed formamide. To verify this, we treated 2a in the presence of 1a or 4a over Pd/C in [BMIm][BF₄] (Scheme 3a and b), and 3a was excitingly obtained in appreciable yields in both cases, different from the results shown in Scheme S2A and B.† This suggests that the McMurry reaction of 2a may occur to produce 1,2-bis(piperidine)ethylene although it was not detected in the reaction process, because it can be rapidly hydrogenated to 3a catalyzed by Pd/C (Scheme 3c). Notably, on prolonging the reaction time to 12 h, both 2a and 3a disappeared, and 4a became the sole product (Scheme 3b). This indicates that 3a was further converted into 4a via hydrogenolysis under the experimental conditions, which was confirmed by the reaction of 3a with H₂ over Pd/C in [BMIm][BF₄] containing t-BuOK to produce 4a (Scheme 3d). Generally, the C-N bond breaks more easily than the C-C bond. However, in this work the C-C bond rather than the C-N bond in 3a was broken. To give a reasonable explanation for this, Gaussian calculation was performed, which showed that the acidic hydrogen atom H(2) of $[BMIm]^+$ could interact with an N atom of 3a, causing the length of the C-C bond in 3a to become longer (Fig. S13[†]). This may be responsible for the cleavage of the C-C bond in 3a to give 4a. [BMIm][BF₄] played a crucial role in the hydrogenolysis of 3a to 4a, deduced from the fact that without the IL the hydrogenolysis of 3a did not occur even in the presence of the base t-BuOK (Scheme S2C[†]).

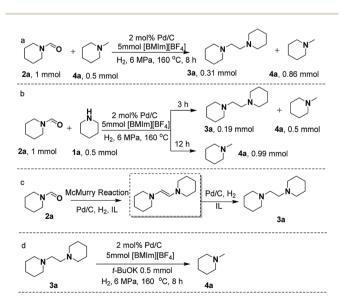

Scheme 3 Control experiments. Conversion of 2a to 3a in the presence of 4a (a). Conversion of 2a to 3a and/or 4a in the presence of 1a for different reaction times (b). The possible reaction pathway from 2a to 3a (c). Conversion of 3a to 4a in the presence of *t*-BuOK (d).

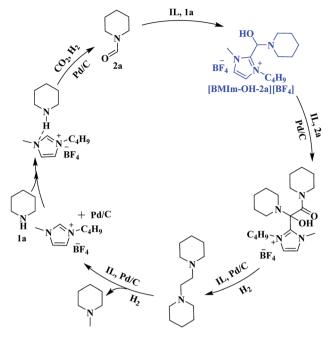

Scheme 4 Plausible pathways for the formation of 2a, 3a and 4a.

To identify possible intermediates in the reaction process, the reaction solution was analyzed by means of electrospray ionization mass spectrometry (ESI-MS.) As shown in Fig. S14,† {H[BMIm][BF₄](1a)}⁺ (m/z = 312.2), {H[BMIm][BF₄](3a)}⁺ (m/z = 423.3), {[BMIm][N-(N-piperidinoglycolyl)piperidine](4a)}⁺ (m/z = 464.4), {[BMIm-[N-(N-piperidinoglycolyl)piperidine](2a)}⁺ (m/z = 476.4), {[BMIm-OH-2a][BF₄][BMIm](2a)}⁺ (m/z = 591.4) and {([BMIm][BF₄])₂[BF₄][N-(N-piperidinoglycolyl)piperidine]}⁻ (m/z = 765.4) were detected, suggesting that under the experimental conditions, [BMIm-OH-2a][BF₄] and N-(N-piperidinoglycolyl) piperidine] (BF₄] played a vital role in activating and stabilizing them.

Based on the experimental results, a possible pathway is proposed, as shown in Scheme 4. Initially, **1a** is activated by the IL *via* hydrogen bonding and electrostatic interaction and undergoes formylation with CO_2/H_2 to yield **2a** over Pd/C. Subsequently, an intermediate [BMIm–OH–**2a**][BF₄] is formed from **2a** and [BMIm]⁺ in the presence of **1a**, and the McMurry reaction proceeds through coupling of [BMIm–OH–**2a**][BF₄] with **2a** to produce *N*-(*N*-piperidinoglycolyl)piperidine, followed by hydrogenation to form **3a**. Finally, hydrogenolysis of **3a** results in the formation of **4a**. Notably, this is the first time that the McMurry reaction of formamide over Pd/C using H₂ as a reductant has been realized, very different from the traditional routes.

Conclusions

In summary, selective reduction of CO_2 with cyclic amines and H_2 was realized over the [BMIm][BF₄]–Pd/C catalytic system, and 1,2-bis(N-heterocyclic)ethanes were obtained *via* the McMurry reaction of formamide coupled with subsequent hydrogenation. [BMIm][BF₄] displayed multiple functions including improving

the catalytic activity of Pd particles and activating the amine substrate and the formed formamide intermediate. [BMIm] [BF₄]-Pd/C was tolerant to a wide substrate scope, giving the corresponding formamides, 1,2-bis(N-heterocyclic)ethanes or methylamines in moderate to high yields. We believe that these findings provide insights into achieving cooperativity between the IL and metal catalysts.

Experimental

General procedures for the reaction of N-containing compounds with CO_2/H_2

All reactions were performed in a stainless steel autoclave equipped with a Teflon tube (16 mL inner volume) and a magnetic stirrer. In a typical experiment, piperidine (0.5 mmol), $[BMIm][BF_4]$ (5 mmol) and Pd/C (20 mg) were successively loaded into the autoclave under an N₂ atmosphere, and then the autoclave was sealed. H₂ (6 MPa) and CO₂ were charged successively into the reactor until the total pressure reached 10 MPa at room temperature. The autoclave was moved to a heating furnace at 433 K. After the desired reaction time, the reactor was cooled down in ice water and the gas inside was vented slowly. Trimethoxybenzene (internal standard) and diethyl ether were added to the reaction solution, stirred vigorously and centrifuged. The upper liquid was extracted for analysis.

Product analysis

Liquid samples were analysed using a gas chromatograph (Agilent 4890D) equipped with an ultra-inert capillary column (19091S-433UI HP-5 ms). NMR spectra were collected using a coaxial insert NMR tube with d⁶-DMSO in the internal tube as a reference, recorded using Bruker 400 HD (¹H NMR, ¹¹B NMR and ¹³C NMR spectra) and Bruker 600 instruments (¹⁵N NMR and ¹⁹F NMR spectra and the ¹H-¹H correlation spectrum (¹H-¹H COSY). ¹¹B NMR and ¹⁹F NMR spectra were obtained using the same equipment in succession. ¹H NMR data recorded in d⁶-DMSO were listed with the residual DMSO at 2.50 ppm, while ¹³C NMR data were listed with the residual DMSO at 39.51 ppm; ¹H NMR data in d-CDCl₃ were listed with the residual CHCl₃ at 7.26 ppm, while ¹³C NMR data were listed with the residual CHCl₃ at 77.17 ppm. FT-IR spectra were recorded using a Bruker Tensor-27 instrument, scanning from 400 to 4000 cm^{-1} . Transmission electron microscopy (TEM) images were obtained using a JEOL-2100F. X-ray photoelectron spectroscopy (XPS) was performed on an ESCALab220i-XL electron spectrometer from VG Scientific at a pressure of 3 \times 10^{-9} mbar using 300 W Al-K α radiation. The binding energies (BEs) were referenced to the C 1s line at 284.8 eV from adventitious carbon. X-ray absorption data at the Pd K-edge of the samples were recorded at room temperature in fluorescence mode with a silicon drift fluorescence detector at beam line BL14W1 of the Shanghai Synchrotron Radiation Facility (SSRF), China. The electron storage ring was operated at 3.5 GeV. Data processing was performed using the program ATHENA. The electrospray ionization mass spectrometry (ESI-MS) data (in

both negative and positive modes) were collected using a Bruker 9.4T Solarix instrument.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

This work was financially supported by the National Key Research and Development Program of China (2017YFA0403102 and 2017YFA0403003), Natural Science Foundation of China (21890761, 21533011, and 21773266), Chinese Academy of Sciences (QYZDY-SSW-SLH013-2), and Beijing Municipal Science & Technology Commission (Z181100004218004).

Notes and references

- 1 M. Y. He, Y. H. Sun and B. X. Han, Angew. Chem., Int. Ed., 2013, 52, 9620.
- 2 D. X. Yang, Q. G. Zhu, C. J. Chen, H. Z. Liu, Z. M. Liu, Z. J. Zhao, X. Y. Zhang, S. J. Liu and B. X. Han, *Nat. Commun.*, 2019, **10**, 677.
- 3 Z. Lian, D. U. Nielsen, A. T. Lindhardt, K. Daasbjerg and T. Skrydstrup, *Nat. Commun.*, 2016, 7, 13782.
- 4 Y. M. Ni, Z. Y. Chen, Y. Fu, Y. Liu, W. L. Zhu and Z. M. Liu, *Nat. Commun.*, 2018, **9**, 3457.
- 5 C. X. Qian, W. Sun, D. L. H. Hung, C. Y. Qiu, M. Makaremi, S. G. Hari Kumar, L. Wan, M. Ghoussoub, T. E. Wood, M. K. Xia, A. A. Tountas, Y. F. Li, L. Wang, Y. C. Dong, I. Gourevich, C. V. Singh and G. A. Ozin, *Nat. Catal.*, 2019, 2, 46.
- 6 C. S. Yang, R. T. Mu, G. S. Wang, J. M. Song, H. Tian, Z. J. Zhao and J. L. Gong, *Chem. Sci.*, 2019, **10**, 3161.
- 7 A. Tlili, E. Blondiaux, X. Frogneux and T. Cantat, *Green Chem.*, 2015, **17**, 157–168.
- 8 Y. H. Li, X. J. Cui, K. W. Dong, K. Junge and M. Beller, *ACS Catal.*, 2017, 7, 1077.
- 9 R. H. Lam, C. M. A. McQueen, I. Pernik, R. T. McBurney, A. F. Hill and B. A. Messerle, *Green Chem.*, 2019, 21, 538.
- 10 X.-D. Li, S.-M. Xia, K.-H. Chen, X.-F. Liu, H.-R. Li and L.-N. He, *Green Chem.*, 2018, **20**, 4853.
- 11 R. L. Nicholls, J. A. McManus, C. M. Rayner, J. A. Morales-Serna, A. J. P. White and B. N. Nguyen, ACS Catal., 2018, 8, 3678.
- 12 O. Jacquet, C. Das Neves Gomes, M. Ephritikhine and T. Cantat, *J. Am. Chem. Soc.*, 2012, **134**, 2934.
- 13 H. Lv, Q. Xing, C. T. Yue, Z. Q. Lei and F. W. Li, *Chem. Commun.*, 2016, **52**, 6545.
- 14 M. A. Affan and P. G. Jessop, *Inorg. Chem.*, 2017, 56, 7301–7305.
- 15 Y. J. Zhang, H. L. Wang, H. K. Yuan and F. Shi, ACS Sustainable Chem. Eng., 2017, 5, 5758.
- 16 U. Jayarathne, N. Hazari and W. H. Bernskoetter, *ACS Catal.*, 2018, **8**, 1338.

- 17 X. J. Cui, X. C. Dai, Y. Zhang, Y. Q. Deng and F. Shi, *Chem. Sci.*, 2014, 5, 649.
- 18 K. Beydoun, G. Ghattas, K. Thenert, J. Klankermayer and W. Leitner, Angew. Chem., Int. Ed., 2014, 53, 11010.
- 19 K. Kon, S. M. A. H. Siddiki, W. Onodera and K.-i. Shimizu, *Chem.-Eur. J.*, 2014, **20**, 6264.
- 20 I. Sorribes, J. R. Cabrero-Antonino, C. Vicent, K. Junge and M. Beller, J. Am. Chem. Soc., 2015, 137, 13580.
- 21 C. Fang, C. L. Lu, M. H. Liu, Y. L. Zhu, Y. Fu and B. L. Lin, *ACS Catal.*, 2016, **6**, 7876.
- 22 H. Yang and F. C. Thyrion, Int. J. Chem. Kinet., 1994, 26, 309.
- 23 S. A. Gamzaeva, P. S. Mamedova, K. M. Allakhverdieva, G. K. Velieva, M. A. Akhundova and M. A. Allakhverdiev, *Russ. J. Appl. Chem.*, 2009, 82, 1577.
- 24 K. H. Chen, G. L. Shi, W. D. Zhang, H. R. Li and C. M. Wang, J. Am. Chem. Soc., 2016, **138**, 14198.
- 25 Z. R. Zhang, J. L. Song and B. X. Han, *Chem. Rev.*, 2017, **11**7, 6834.
- 26 A. Weilhard, M. I. Qadir, V. Sans and J. Dupont, *ACS Catal.*, 2018, **8**, 1628.
- 27 Y. F. Zhao, Z. Z. Yang, B. Yu, H. Y. Zhang, H. J. Xu, L. D. Hao,
 B. X. Han and Z. M. Liu, *Chem. Sci.*, 2015, 6, 2297.
- 28 X. X. Sang, J. L. Zhang, J. F. Xiang, J. Cui, L. R. Zheng, J. Zhang, Z. H. Wu, Z. H. Li, G. Mo, Y. Xu, J. L. Song,

C. C. Liu, X. N. Tan, T. Luo, B. X. Zhang and B. X. Han, *Nat. Commun.*, 2017, **8**, 175.

- 29 M. Y. Liu, Z. R. Zhang, H. Z. Liu, Z. B. Xie, Q. Q. Mei and B. X. Han, *Sci. Adv.*, 2018, **4**, eaas9319.
- 30 Y. F. Zhao, B. Yu, Z. Z. Yang, H. Y. Zhang, L. D. Hao, X. Gao and Z. M. Liu, Angew. Chem., Int. Ed., 2014, 53, 5922.
- 31 Y. F. Zhao, Y. Y. Wu, G. F. Yuan, L. D. Hao, X. Gao, Z. Z. Yang,
 B. Yu, H. Y. Zhang and Z. M. Liu, *Chem.-Eur. J.*, 2016, 11, 2735.
- 32 A. Karakulina, A. Gopakumar, İ. Akçok, B. L. Roulier, T. LaGrange, S. A. Katsyuba, S. Das and P. J. Dyson, *Angew. Chem., Int. Ed.*, 2015, 55, 292.
- 33 D. J. Tao, F. F. Chen, Z. Q. Tian, K. Huang, S. M. Mahurin, D. E. Jiang and S. Dai, *Angew. Chem., Int. Ed.*, 2017, **56**, 6843.
- 34 Z. S. Ma, H. Y. Zhang, Z. Z. Yang, Y. F. Zhao, B. Yu and Z. M. Liu, J. Mater. Chem. A, 2014, 2, 19324.
- 35 V. K. Aggarwal, I. Emme and A. Mereu, *Chem. Commun.*, 2002, 1612.
- 36 X. L. Du, G. Tang, H. L. Bao, Z. Jiang, X. H. Zhong, D. S. Su and J. Q. Wang, *ChemSusChem*, 2015, 8, 3489.
- 37 X. F. Duan, J. Zeng, J. W. Lü and Z. B. Zhang, *J. Org. Chem.*, 2006, **71**, 9873.