




 Cite this: *RSC Adv.*, 2020, **10**, 40916

A one-pot synthesis of a monolithic Cu₂O/Cu catalyst for efficient ozone decomposition†

 Mohammad Ghasem Rahimi,^{ab} Anqi Wang,^{ab} Guojun Ma,^{cd} Ning Han ^{*ac} and Yunfa Chen ^{*ac}

Nowadays, it is necessary and challenging to prepare monolithic catalysts, which are ready for use, preventing the tedious and complicated integration procedure of the powder materials onto a porous substrate. Herein, Cu₂O nanoparticles are successfully synthesized onto a porous Cu foam in one pot *via* the surface oxidation, coordination and precipitation reactions in a NH₄OH and HCl solution, and the optimum synthesis conditions are a NH₃ : HCl ratio of 1 : 0.9, oxidation temperature of 80 °C and time of 18 h. The obtained Cu₂O/Cu catalyst (mostly <100 nm) shows a highly active O₃ decomposition performance with >98% and >80% conversion efficiency in dry and 90% relative humidity air for >10 h at an O₃ concentration of 20 ppm and a gas hourly space velocity of 12 500 h⁻¹. The high efficiency can be attributed to the porous Cu foam providing a large contact area, abundant crystal defects in the nanometer-sized Cu₂O materials serving as the active sites, and also to the Schottky barrier formed in the Cu₂O/Cu interface facilitating the electron transfer for O₃ degradation. All these results show the potency of the easily fabricated monolithic Cu₂O/Cu catalyst for the highly efficient O₃ contaminant removal.

 Received 11th June 2020
 Accepted 16th September 2020

DOI: 10.1039/d0ra05157h

rsc.li/rsc-advances

Introduction

It is well understood that the stratospheric ozone layer hinders short-wavelength ultraviolet light from threatening lives on the surface of Earth.¹ However, the ground-level ozone is a destructive chemical, which has been generated in high concentrations *via* photo-chemical reactions over the past few decades in the summers and is commonly detected in surrounding human environments, such as aircraft cabins, photocopier offices, laser printers, and sterilizers. (Batakliev *et al.*, 2015;⁴ Hollósy, 2002;¹ Oyama, 2000;³ Rim *et al.*, 2018 (ref. 2)). Therefore, the ozone exposure standard has regularly been set at about 70 ppb over an average time of 8 hours.⁵

The degradation rate of ozone in ambient atmosphere is comparatively low, and thus the contaminants cannot be entirely removed naturally. Hence, the catalytic ozone

decomposition process has received considerable attention than other removal techniques such as adsorption^{6,7} and thermal decomposition.^{8,9} Lately, the catalytic ozone decomposition technique at low temperatures has also been communicated,^{10–12} and long-term studies confirmed the approach as safe, efficient, cost-effective, and fast ozone conversion under ambient conditions.^{11–13} A series of essential catalysts for ozone decomposition have been developed, of which the most active and productive candidates for catalytically converting ozone to oxygen molecules are indeed noble metals and transition metal oxides.^{12,14} Transition metal oxide-based catalysts are incredibly efficient from an environmental perspective and simultaneously provide a convenient and affordable way to decompose the ozone molecules. In this regard, transition metal oxides including MnO₂,^{15–17} Cu₂O/CuO,^{10,18} Fe₂O₃,^{19,20} and NiO²¹ have been reported as active catalysts.¹²

Due to the low price, environmental friendliness, and other versatile functionalities, Cu-based materials have been extensively studied and synthesized through various routes in the recent past decades. Our group has recently communicated Cu₂O powder as a promising catalyst to decompose 20 ppm ozone with 100% conversion at space velocity of 240 000 mL g⁻¹ h⁻¹, which has been acknowledged as one of the most active powder-based catalysts.^{10,18,22} However, the reported powder-based catalysts are not practical to render for the gas-phase catalytic decomposition until they are integrated into a porous substrate to form a monolithic catalyst. Then, problems such as weak adhesion between the substrate and catalyst powders,

^aState Key Laboratory of Multiphase Complex Systems, Institute of Process Engineering, Chinese Academy of Sciences, P.O. Box 353, Beijing 100190, PR China. E-mail: nhan@ipe.ac.cn; chenyf@ipe.ac.cn; Fax: +86-10-62525716; Tel: +86-10-62558356; +86-10-82544896

^bCenter of Materials Science and Optoelectronics Engineering, University of Chinese Academy of Sciences, Beijing, 100049, China

^cCenter for Excellence in Regional Atmospheric Environment, Institute of Urban Environment, Chinese Academy of Sciences, Xiamen 361021, PR China

^dKey Laboratory of Science and Technology on Particle Materials, Chinese Academy of Sciences, Beijing 100190, PR China

† Electronic supplementary information (ESI) available: Fig. S1–S3. See DOI: 10.1039/d0ra05157h



sophisticated multi-step or long term integration, and fabrication at high temperatures have been encountered.^{23–27} In this study, we successfully propose a one-pot synthesis of the monolithic Cu₂O nanocatalyst on the surface of a Cu foam by a facile chemical oxidation approach without using additives, which offer superior ozone catalytic performance with high stability and low production cost. This study provides not only a simple synthesis method of the supported catalyst, but also a highly active Cu₂O/Cu ozone decomposition material.

Experimental

Material and method

Hydrochloric acid (HCl), aqueous ammonia (NH₄OH), and acetone (CH₃COCH₃) of analytical grade were purchased from Sinopharm Chemical Reagent Co. Ltd. and utilized as received without further purification. The ultrapure water with a resistivity of 18.2 MΩ cm was used for all the synthesis and experiments. A commercial Cu foam sample (500 mesh) was first cut into round-shape pieces (diameter 12 mm, thickness 2 mm). In general, the foam was first immersed in diluted HCl and thoroughly washed with deionized water, then put in acetone and sonicated for 5 min to remove impurities and native oxides on the Cu foam. Afterward, the sample was dried in N₂ gas for further use. In a typical synthesis experiment, the pre-processed Cu foam was quickly transferred to a glass beaker and immersed in a solution containing 0.4 mL of 1 M HCl, 27 μL of 13.38 M NH₃, and 20 mL distilled water. The glass beaker was covered by an aluminum foil. Then, the experiments were carried out at constant temperatures (60, 70, 80, and 90 °C) for a given oxidation time (8, 12, 18, and 24 h). The Cu oxidation condition in the solution was then labeled as Cu_{Temperature, Time} (e.g., Cu_{80 °C, 8 h} denotes 80 °C, 8 h).

Characterization

The crystalline structures were recorded using a powder X-ray diffractometer (XRD) on a PANalytical X'Pert high score system (40 kV, 40 mA) with Cu-Kα radiation (λ = 0.15418 nm). The diffraction angles were selected from 5° to 90° with a step size of 0.033° and at a rate of 17° min⁻¹. The morphology was studied using a scanning electron microscope (SEM, JEOL JSM-6700F, Japan, 15 kV, 10 mA). The Raman spectra were recorded on Jobin-Yvon LABRAM HR800 Raman Microscope with a resolution of 2 cm⁻¹ at an excitation of 532 nm laser. The surface analyses were determined *via* X-ray photoelectron spectroscopy (XPS) on an XLESCALAB 250Xi electron spectrometer from VG Scientific with mono-chromatic Al-Kα radiation. The surface area was characterized by a BET specific surface area and pore size analyser (BJBUILDER SSA-7300, China). The humidity was measured by a humidity sensor (Center 310 RS-233, TES, Taiwan).

Catalyst test

The as-synthesized sample was loaded in a continuous tube reactor (inner diameter 14 mm). 20 ppm ozone was generated by a commercial ozone generator (COM-AD-01-OEM, Anseros

Company, Anshan, China) and the total flow rate was maintained at 200 standard cubic centimeters per minute (scm, 190 scm air and 10 scm oxygen) using mass-flow controllers, equivalent to a gas hourly space velocity (GHSV) of 12 500 h⁻¹. The inlet and outlet ozone concentrations (*C*_{in} and *C*_{out}, respectively) in the gas phase were determined by an ozone detector (Model 106M, 2B Technologies, USA), and the conversion was calculated as 100% × (*C*_{in} - *C*_{out})/*C*_{in}.

Results and discussions

Cu₂O/Cu was initially synthesized *via* a simple oxidation approach in the solution containing 0.4 mL 1 M HCl, 27 μL 13.38 M NH₄OH and 20 mL distilled water. Upon the introduction of fresh Cu foam into the solution, the first sign of the oxidation reaction appeared from the change in the solution color to blue after a couple of minutes, as shown in Fig. S1 in the ESI.† Also, the molar ratio of NH₄OH : HCl was optimized as 1 : 0.9, as shown in Table S1.†

XRD and SEM were employed to investigate the crystal structure and morphology of the samples prepared at different reaction temperatures of 60–90 °C for 12 h. As exhibited in Fig. 1a, the XRD patterns of the Cu foam reacted at 60, 70 and 90 °C were observed with three sharp peaks at 43.4°, 50.6° and 74.3°, which can be indexed to the (111), (200) and (220) planes of the Cu crystal structure (JCPDS 03-065-9743), respectively. However, after the reaction at 80 °C, the oxidation of superficial Cu leads to the formation of the Cu₂O nanocatalyst, which can be verified by the additional XRD peak at 2θ = 36.6°, attributing to the (111) plane of the face-centered cubic structure of Cu₂O (JCPDS 00-001-1142). This confirms that the hybrid Cu₂O/Cu

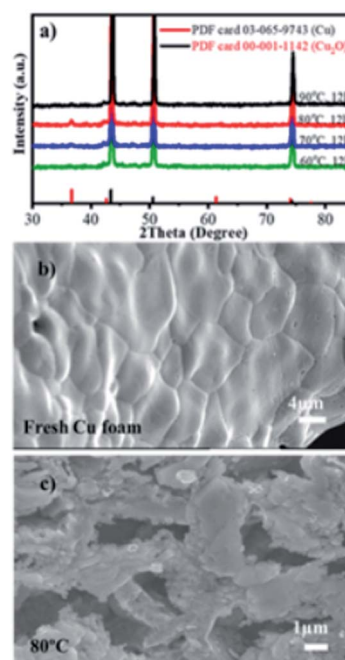


Fig. 1 (a) XRD patterns of Cu₂O/Cu obtained at different temperatures, and SEM images of (b) fresh Cu foam (c) Cu_{80 °C, 12 h}.



nanocatalysts have been successfully obtained by the one-pot synthesis method, which can be further verified by the SEM images in Fig. 1b and c. Fig. 1b shows a relatively smooth surface of pure Cu foam with a three-dimensional open network framework. Notably, crystalline Cu₂O particles were observed at Cu₈₀ °C, 12 h (mean < 100 nm), as shown in Fig. 1c. Therefore, the synthesis temperature was set at 80 °C, and the growth time was further investigated in order to obtain as much Cu₂O particles as possible on the surface of the Cu foam. The size of Cu₂O formed at 60 °C is 90 nm, and at 70 and 90 °C are less than 115 nm. It should also be noted that after 8 h treatment at 80 °C, the BET specific surface area of the Cu foam was only 5.8 m² g⁻¹, as shown in Fig. S2,† showing the existence of few pores in the Cu₂O/Cu catalyst.

Afterward, the reaction time was varied from 8 to 24 h, and the XRD patterns were obtained and are shown in Fig. 2a. It is clear that the Cu₂O peaks at 36.6° become more visible as the reaction time increases from 8 to 18 h, thereby signifying that the crystallinity of Cu₂O was controlled by the oxidation time and temperature and the Cu foam turned brick reddish after 18 h, as shown in the inset of Fig. 2a. It should also be noted that the XRD patterns only belong to the deposited Cu₂O layer and the underlying Cu metal substrate without any detectable impurities such as CuO. However, after 24 h reaction time, the surface Cu₂O was partially dissolved in the solution as clearly depicted in Fig. 2b. As a comparison, the Cu₂O layer obtained after 18 h (mostly < 100 nm) is dense and homogeneously covers the entire surface of the Cu foam as shown in the surface and cross-sectional SEM images in Fig. 2c and d. The micro and nanoscale morphology of Cu₂O plays a vital role in determining their properties such as catalytic activity.²⁸ Further, the cross-sectional SEM images are employed to measure the average thickness of the layer, which is about 2.67 μm for the Cu₈₀ °C, 18 h sample. The SEM images reveal that the proper depth and the bridging structure of the as-synthesized irregular Cu₂O nanoparticles provide a significantly extra high contact surface area for ozone decomposition.



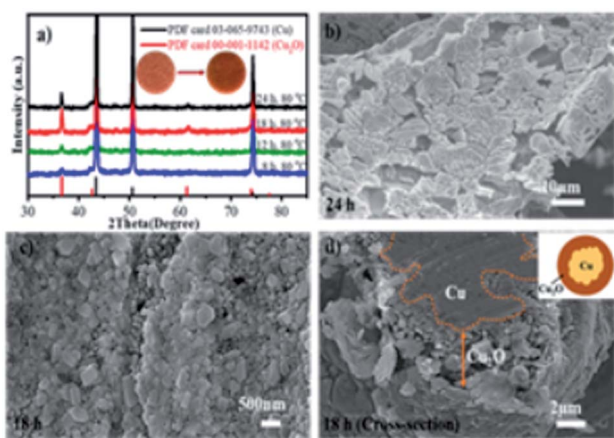


Fig. 2 (a) XRD patterns of Cu₂O/Cu obtained at different oxidation times, SEM images of (b) Cu₈₀ °C, 24 h, (c) surface SEM and (d) cross-sectional SEM images of Cu₈₀ °C, 18 h.

To understand the reaction mechanism of the Cu₂O formation on the Cu foam, control experiments were carried out. If aqueous ammonia was solely used without HCl, the Cu foam would dissolve gradually and the solution would change into blue color, which infers that the role of aqueous ammonia is to dissolve Cu. On the other side, if aqueous ammonia is not used, Cu foam would remain unchanged in HCl as HCl cannot dissolve Cu. Therefore, initially, Cu dissolves readily with the help of dissolved oxygen in aqueous ammonia, as shown in eqn (1). This step is fast to occur and the deep blue color infers the product of the Cu and NH₃H₂O complex (Cu(NH₃)₄²⁺, coordination constant 10^{13.32}). This ammine complex has a relatively higher oxidation potential as to oxidize the metallic Cu further into the Cu(NH₃)₂⁺ complex (coordination constant 10^{10.86}), as shown in eqn (2).²⁹ Further, with the help of Cl⁻, CuCl would precipitate onto the surface of the Cu foam due to the low solubility product of 1.72 × 10⁻⁷, as shown in eqn (3). Then, CuCl would react fast with local OH⁻ to form less soluble CuOH (solubility product 1 × 10⁻¹⁴), as shown in eqn (4).^{30–32} Finally, the intermediate CuOH would immediately decompose into Cu₂O due to its thermodynamic instability, as shown in eqn (5).³³



Herein, a stable layer of Cu₂O was formed with noticeable thickness as Cu was exposed to NH₃H₂O and Cl⁻. The outline mechanism of the Cu₂O synthesis is illustrated schematically in Fig. 3.

In order to further verify the crystal structure of the product, Raman spectra were obtained, as shown in Fig. 4. The Cu₂O layer exhibited four distinct peaks in the spectra at 150, 220, 420, and ~640 cm⁻¹.³⁴ The origin of 150, 220, and ~640 cm⁻¹ peaks are known to be due to the Γ₁₅⁽¹⁾, 2Γ₁₂⁻ and Γ₁₅⁽²⁾ phonons in good agreement with the literature,^{34–36} respectively. Also, the peak at 420 cm⁻¹ is assigned to the region of the multiphonon process.³⁷ Different orientations of the samples may cause a discrepancy in the Cu₂O Raman peak intensities.³⁸ Naturally,

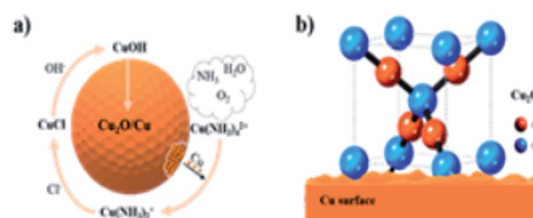


Fig. 3 Schematic of (a) the Cu₂O formation mechanism and (b) the lattice model.



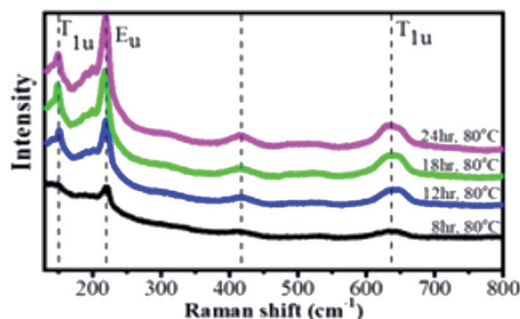


Fig. 4 Raman spectra with main peaks at 150, 220, 420, and 635 cm^{-1} (dashed vertical lines) excited by a 532 nm laser.

the $\Gamma_{15}^{-(1)}$ and $\Gamma_{15}^{-(2)}$ phonons can be activated by either local defects or impurities in Raman scattering. The Raman results are consistent with the SEM results, in which catalysts are formed incompletely. The $\Gamma_{15}^{-(1)}$ and $2\Gamma_{12}^{-}$ phonons at 150 and 220 cm^{-1} can be ascribed to the Cu tetrahedron rotations around its center and was reported to be very sensitive to the surface damages.³⁹

Then, the catalytic performances of the $\text{Cu}_2\text{O}/\text{Cu}$ samples were tested for the removal of O_3 at ambient temperature, as depicted in Fig. 5. In general, three dimensional porous Cu foam provides the contact possibility and Cu_2O provides the active sites compared with the bulk Cu.²⁶ In this study, 20 ppm ozone with 200 sccm flow rate (190 sccm air and 10 sccm O_2) and a GHSV of 12 500 h^{-1} was introduced into the as-prepared $\text{Cu}_2\text{O}/\text{Cu}$. The efficiency remains 100% over 6 h of continuous operation in dry air conditions for the $\text{Cu}_2\text{O}/\text{Cu}$ catalyst prepared at 80 °C for 12 h and 24 h, and then slightly deviated. The efficiency of the $\text{Cu}_2\text{O}/\text{Cu}$ catalyst for 18 h oxidation time is up to 98% over 10 h among the other samples. Also, to explore the catalytic activity and stability in the real situation, ozone conversion was performed in the presence of water vapor (relative humidity, RH). It is not much affected by 90% RH, and after an 8 h test, the ozone conversion maintained approximately 80% efficiency. This high performance can be ascribed to the as-prepared interconnected Cu_2O nanoparticles and ultra-high surface area on the surface of porous Cu foam. However, the activity was dramatically dropped for a higher flow rate of 800 sccm (GHSV of 50 000 h^{-1}), which might be the



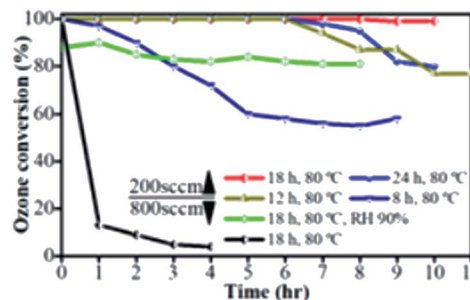


Fig. 5 Catalytic performance of ozone conversion over the as-prepared catalysts, flow rate = 200 sccm and 800 sccm, ozone concentration = 20 ppm, GHSV = 12 500 and 50 000 h^{-1} .

result of the low contact time of O_3 with the catalyst for such a high flow rate. Besides, the Cu foam was separately verified and possessed low efficiency (less than 15 min activity) in ozone decomposition performance. The monolithic ozone catalysts are compared in Table 1, where it is clear that the obtained catalyst shows highly active O_3 decomposition performance in dry and relative humidity compared to other monolithic catalysts.

It has been earlier reported that the catalytic ozone decomposition on Cu_2O can be described as per the eqn (6)–(8), where freeing adsorbed oxygen species such as O_2^{2-} on Cu_2O is the rate-determining step (eqn (8)).¹⁸



To further explore the surface property difference of the catalysts, XPS was conducted to verify and address the Cu_2O composites before and after performing the ozone decomposition test, as shown in Fig. 6. The two main peaks located at $\sim 932\text{--}935$ eV and $\sim 952\text{--}955$ eV come from the Cu $2p_{3/2}$ and Cu $2p_{1/2}$ orbits from Cu_2O .⁴⁴ Moreover, the shakeup satellite feature located at 943–947 eV in Fig. 6a demonstrated the unfilled electron state of Cu 3d orbitals⁴⁵ and the 3d shell may contain 9.6 or 9.5 electrons,^{46,47} which can be used to prove the presence of Cu_2O . LMM-2 Auger transition in the XPS spectra is checked

Table 1 A comparison of the ozone decomposition performance of the reported monolithic catalysts

| Catalysts | Conc. (ppm) | T (°C) | RH (%) | SV (h^{-1}) | Conv. (%) | Reaction rate ($\text{mmol L}^{-1} \text{h}^{-1}$) | Ref. |
|---|-------------|----------|---------|------------------------|-----------|--|-----------|
| $\text{MO}_x/\gamma\text{-Al}_2\text{O}_3$ | 2 | 40 | 40 | 31 940 | ≤ 42 | 1.04 | 12 |
| $\text{MnO}_x + \text{MnCO}_3$ | 14 | 25 | Dry air | 460 000 | 85 | 244.34 | 40 |
| $\text{Pd-MnO}_x/\text{La-Al}_2\text{O}_3$ | 0.6 | 14 | 85–90 | 380 000 | 82 | 7.94 | 41 |
| $\text{Pd-MnO}_x/\text{SiO}_2$ | 0.6 | 14 | 85–90 | 380 000 | 82 | 7.94 | 41 |
| $\text{Pd-MnO}_x/\gamma\text{-Al}_2\text{O}_3$ | 0.6 | 14 | 85–90 | 380 000 | 77 | 7.45 | 41 |
| $\text{Pd-MnO}_x/\text{SiO}_2\text{-Al}_2\text{O}_3\text{-}350^\circ\text{C}$ | 0.6 | 40 | 55–65 | 635 000 | 90 | 13.34 | 42 |
| $\text{Pd-MnO}_x/\text{SiO}_2\text{-Al}_2\text{O}_3$ with 80% MnO_x | 0.58 | 45 | 55–65 | 510 000 | >90 | 10.19 | 43 |
| $\text{Cu}_2\text{O}/\text{Cu}$ | 20 | 25 | 90 | 12 500 | >80 | 8.19 | This work |
| $\text{Cu}_2\text{O}/\text{Cu}$ | 20 | 25 | Dry air | 12 500 | >98 | 10.04 | This work |



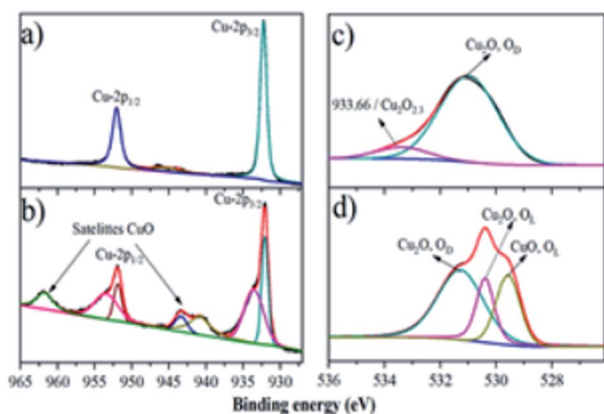


Fig. 6 Composition study of Cu_2O . Cu 2p XPS spectra of (a) $\text{Cu}_{80\text{ }^\circ\text{C}, 18\text{ h}}$, (b) $\text{Cu}_{80\text{ }^\circ\text{C}, 18\text{ h}}$ after the O_3 catalytic process, and O 1s XPS spectra of (c) $\text{Cu}_{80\text{ }^\circ\text{C}, 18\text{ h}}$, and (d) $\text{Cu}_{80\text{ }^\circ\text{C}, 18\text{ h}}$ after the O_3 catalytic process.

to discriminate Cu from Cu_2O owing to the overlapping binding energies. The LMM-2 Auger transition peak is located at about 570 eV (Fig. S3† in the ESI) in the samples, which can be ascribed to Cu_2O rather than Cu (568 eV).⁴⁸ Therefore, the Cu foam surface was totally covered by the Cu_2O nanoparticles. In the meanwhile, after the ozone decomposition experiment, a shoulder peak at 933 eV and satellite peaks at about 943 and 962 eV appeared, as shown in Fig. 6b, inferring that some of the Cu(I) ions are oxidized into Cu(II). The oxidation of Cu(I) into Cu(II) would not be the main reason of the catalyst activity according to a previous study.¹⁸ Therefore, O 1s spectra were obtained and compared as shown in Fig. 6c and d.

As shown in Fig. 6c, the broad O 1s peak has been generally deconvoluted into multiple overlapping peaks at about 529.6, 530.2, and 531.4 eV, attributing to the lattice oxygen (O_L) in CuO, lattice oxygen in Cu_2O , and defective oxide (oxygen vacancy),^{27,49–51} respectively. It is clear in Fig. 6c that $\text{Cu}_{80\text{ }^\circ\text{C}, 18\text{ h}}$ has relatively high oxygen defect, which might be the reason of the relatively higher catalytic property. A very weak peak at 933.66 eV resulting from the Cu–O bonds of a small fraction of none crystalline $\text{Cu}_2\text{O}_{2.3}$ (ref. 51) in the O 1s spectra of $\text{Cu}_{80\text{ }^\circ\text{C}, 18\text{ h}}$ (Fig. 6c), might also contribute to the high catalytic performance.⁵⁰ After the O_3 test, the appearance of the lattice oxygen of CuO is in good agreement with the Cu 2p spectra. It should be noted that Cu_2O would be deactivated if the intermediate surface adsorbed oxygen (O_2^{2-}) would accumulate on the surface, whilst the partial oxidation of Cu(I) would not deactivate the catalyst as revealed in this study. Cu_2O is an intrinsically p-type semiconductor, where the positively charged holes would attract electrons from the O_2^{2-} and thus release the intermediate to accelerate the decomposition of O_3 .

As a comparison, sodium hydroxide and urea were used instead of NH_3 in the preparation. As shown in Fig. 7, the catalytic effect was clearly worse than using NH_3 when NaOH and urea were applied in the processing of Cu foam. NaOH can react rapidly with HCl, and the product NaCl is too stable to participate in the oxidation reaction; on the other hand, 1 mol urea decomposes in an acidic aqueous solution at $80\text{ }^\circ\text{C}$ into

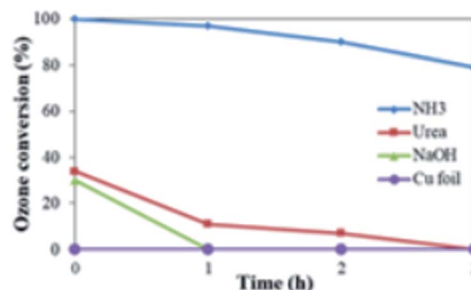


Fig. 7 Comparison of the catalytic effect in using different alkali at $80\text{ }^\circ\text{C}$, 8 h.

2 mol NH_3 , excessive ammonia can form complex $\text{Cu}(\text{NH}_3)_2^+$, which may destroy the cuprous oxide layer of the Cu foam. When a copper foil was used instead of the copper foam, almost no catalytic effect on ozone decomposition was observed under the same conditions (equal mass). It may be due to the nonporous structure and thus limited the contact of copper foil with ozone.

In the meanwhile, there would also exist a Schottky barrier between the surface Cu_2O and the Cu foam, as reported by Iwanoski *et al.*⁵² For p-type Cu_2O semiconductors, the Fermi level lies approximately at 0.3 eV above the valence band level.^{53,54} Also, it is reported that the measured electron affinity is about 3.2 eV that does not vary on changing the temperature of the Cu_2O samples.^{55,56} Consequently, considering the estimated energy gap of 2.1–2.2 eV,^{55–58} the work function for Cu_2O lies in the range of 5.0–5.1 eV. Furthermore, the reported work function values for bulk Cu vary between 4.2 and 4.6 eV.^{59,60} Taking these into considerations, it is likely for the electrons to drift from Cu towards Cu_2O at the interface. In this study, the most possible scenario for the barrier-height results is establishing an electron-rich region at the $\text{Cu}_2\text{O}/\text{Cu}$ interface. Based on the Schottky–Mott rule, a suggested energy band structure diagram of Cu/ Cu_2O and an ozone reaction process are exhibited in Fig. 8, where the Schottky barrier would also contribute to the electron transfer in the O_3 degradation process. Therefore, all these results show the potency of these defective nanometer-sized Cu_2O particles heterojunctioned on the Cu foam for highly active ozone decomposition.

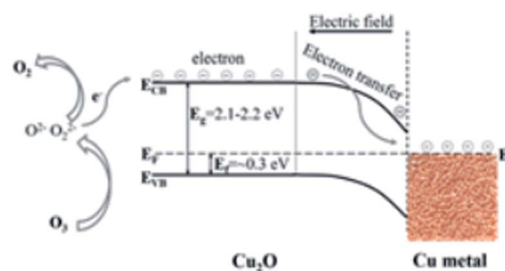


Fig. 8 Schematic of the possible charge transfer mechanism at the Cu– Cu_2O interface with consideration of ozone decomposition illustration.



Conclusions

A monolithic Cu₂O/Cu hybrid catalyst was successfully synthesized by a one pot wet chemical oxidation of Cu foam in an aqueous solution containing NH₃ and HCl. The obtained Cu₂O/Cu could be readily used for O₃ decomposition, and the optimized preparation conditions are NH₃ : HCl = 1 : 0.9, oxidation temperature of 80 °C and time 18 h. When adopted for decomposing 20 ppm O₃ at gas hourly space velocity of 12 500 h⁻¹, the catalyst shows a high degradation efficiency of >98% in 10 h run in dry air and >80% in 90% relative humidity. The high efficiency can be attributed to the porous structure and abundant defects in Cu₂O nanoparticles and also to the Schottky barrier between Cu₂O and Cu, facilitating the electron transfer from O₃ degradation intermediate O₂²⁻ to the catalyst. Therefore, the Cu₂O/Cu-supported catalyst not only possesses the advantage of a facile synthesis and low cost, but also shows its promise in depredeating O₃ contaminants.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

This research was financially supported by the National Key R&D Program of China (2016YFC0207100), the Strategic Priority Research Program of the Chinese Academy of Sciences (XDB05050400).

References

- 1 F. Hollósy, *Micron*, 2002, **33**, 179–197.
- 2 D. Rim, E. T. Gall, S. Ananth and Y. Won, *Buuld. Environ.*, 2018, **130**, 40–48.
- 3 S. T. Oyama, *Catal. Rev. - Sci. Eng.*, 2000, **42**, 279–322.
- 4 T. Batakliiev, V. Georgiev, M. Anachkov, S. Rakovsky and G. E. Zaikov, *Phys. Chem. Res. Eng. Appl. Sci.*, 2015, **1**, 273.
- 5 J. R. Balmes, *Am. J. Respir. Crit. Care Med.*, 2019, **200**, 958–959.
- 6 K. Thomas, P. E. Hoggan, L. Mariey, J. Lamotte and J. C. Lavalley, *Catal. Lett.*, 1997, **46**, 77–82.
- 7 K. M. Bulanin, J. C. Lavalley and A. A. Tsyganenko, *J. Phys. Chem.*, 1995, **99**, 10294–10298.
- 8 S. W. Benson and A. E. Axworthy, *J. Chem. Phys.*, 1957, **26**, 1718–1726.
- 9 E. Castellano and H. J. Schumacher, *J. Chem. Phys.*, 1962, **36**, 2238.
- 10 S. Gong, J. Chen, X. Wu, N. Han and Y. Chen, *Catal. Commun.*, 2018, **106**, 25–29.
- 11 J. Ji, Y. Fang, L. He and H. Huang, *Catal. Sci. Technol.*, 2019, **9**, 4036–4046.
- 12 B. Dhandapani and S. T. Oyama, *Appl. Catal., B*, 1997, **11**, 129–166.
- 13 C. Subrahmanyam, D. A. Bulushev and L. Kiwi-Minsker, *Appl. Catal., B*, 2005, **61**, 98–106.
- 14 T. Batakliiev, V. Georgiev, M. Anachkov, S. Rakovsky and G. E. Zaikov, *Interdiscip. Toxicol.*, 2014, **7**, 47–59.
- 15 H. Wang, P. Rassu, X. Wang, H. Li, X. Wang, X. Wang, X. Feng, A. Yin, P. Li, X. Jin, S.-L. Chen, X. Ma and B. Wang, *Angew. Chem.*, 2018, **130**, 16654–16658.
- 16 W. Li, G. V. Gibbs and S. T. Oyama, *J. Am. Chem. Soc.*, 1998, **120**, 9041–9046.
- 17 J. Ma, C. Wang and H. He, *Appl. Catal., B*, 2017, **201**, 503–510.
- 18 S. Gong, W. Li, Z. Xie, X. Ma, H. Liu, N. Han and Y. Chen, *New J. Chem.*, 2017, **41**, 4828–4834.
- 19 D. Mehandjiev and A. Naidenov, *Ozone: Sci. Eng.*, 1992, **14**, 277–282.
- 20 L. Yan, J. Bing and H. Wu, *Sci. Rep.*, 2019, **9**, 1–10.
- 21 M. Stoyanova, P. Konova, P. Nikolov, A. Naydenov, S. Christoskova and D. Mehandjiev, *Chem. Eng. J.*, 2006, **122**, 41–46.
- 22 S. Gong, X. Wu, J. Zhang, N. Han and Y. Chen, *CrystEngComm*, 2018, **20**, 3096–3104.
- 23 C. H. Kuo and M. H. Huang, *J. Am. Chem. Soc.*, 2008, **130**, 12815–12820.
- 24 X. Liang, L. Gao, S. Yang and J. Sun, *Adv. Mater.*, 2009, **21**, 2068–2071.
- 25 L. Wan, Q. Zhou, X. Wang, T. E. Wood, L. Wang, P. N. Duchesne, J. Guo, X. Yan, M. Xia, Y. F. Li, A. A. Jelle, U. Ulmer, J. Jia, T. Li, W. Sun and G. A. Ozin, *Nat. Catal.*, 2019, **2**, 889–898.
- 26 W. Lu, Y. Sun, H. Dai, P. Ni, S. Jiang, Y. Wang, Z. Li and Z. Li, *Sens. Actuators, B*, 2016, **231**, 860–866.
- 27 B. Long, H. Yang, M. Li, M. S. Balogun, W. Mai, G. Ouyang, Y. Tong, P. Tsiakaras and S. Song, *Appl. Catal., B*, 2019, **243**, 365–372.
- 28 A. J. Zarur and J. V. Ying, *Nature*, 2000, **403**, 65–67.
- 29 E. O. Charles, *J. Chem. Educ.*, 1991, **68**, 248–249.
- 30 J. A. Dean, *Lange's handbook of chemistry*, 15th edn, 2005.
- 31 Y. Shang, D. Zhang and L. Guo, *J. Mater. Chem.*, 2012, **22**, 856–861.
- 32 Y. Shang, Y. M. Shao, D. F. Zhang and L. Guo, *Angew. Chem.*, 2014, **126**, 11698–11702.
- 33 Y. Shang, Y. M. Shao, D. F. Zhang and L. Guo, *Angew. Chem., Int. Ed.*, 2014, **53**, 11514–11518.
- 34 C. C. Hou, Q. Q. Chen, C. J. Wang, F. Liang, Z. Lin, W. F. Fu and Y. Chen, *ACS Appl. Mater. Interfaces*, 2016, **8**, 23037–23048.
- 35 H. Solache-Carranco, G. Juárez-Díaz, A. Esparza-García, M. Briseño-García, M. Galván-Arellano, J. Martínez-Juárez, G. Romero-Paredes and R. Peña-Sierra, *J. Lumin.*, 2009, **129**, 1483–1487.
- 36 Y. Deng, A. D. Handoko, Y. Du, S. Xi and B. S. Yeo, *ACS Catal.*, 2016, **6**, 2473–2481.
- 37 N. G. Elfadill, M. R. Hashim, K. M. Chahrour, M. A. Qaeed and M. Bououdina, *Superlattices Microstruct.*, 2015, **85**, 908–917.
- 38 P. Y. Yu, Y. R. Shen and Y. Petroff, *Solid State Commun.*, 1973, **12**, 973–975.
- 39 A. Compaan, *Solid State Commun.*, 1975, **16**, 293–296.
- 40 J. Jia and P. Zhang, *Ozone: Sci. Eng.*, 2018, **40**, 21–28.



- 41 C.-J. Ren, L.-N. Zhou, H.-Y. Shang and Y.-Q. Chen, *Acta Phys.-Chim. Sin.*, 2014, **30**, 957–964.
- 42 Q. Yu, H. Pan, M. Zhao, Z. Liu, J. Wang, Y. Chen and M. Gong, *J. Hazard. Mater.*, 2009, **172**, 631–634.
- 43 Q. Yu, M. Zhao, Z. Liu, X. Zhang, L. Zheng, Y. Chen and M. Gong, *Chin. J. Catal.*, 2009, **30**, 1–3.
- 44 O. Akhavan, R. Azimirad, S. Safa and E. Hasani, *J. Mater. Chem.*, 2011, **21**, 9634–9640.
- 45 X. Xiang, X. Li, Z. Huang, T. Gao, H. Yuan and D. Xiao, *ChemElectroChem*, 2019, **6**, 1078–1087.
- 46 M. Grioni, J. B. Goedkoop, R. Schoorl, F. M. F. de Groot, J. C. Fuggle, F. Schäfers, E. E. Koch, G. Rossi, J.-M. Esteve and R. C. Karnatak, *Phys. Rev. B*, 1989, **39**, 1541–1545.
- 47 A. R. Williams and N. D. Lang, *Phys. Rev. Lett.*, 1978, **40**, 954–957.
- 48 J. Y. Park, Y. S. Jung, J. Cho and W. K. Choi, *Appl. Surf. Sci.*, 2006, **252**, 5877–5891.
- 49 C. D. Wagner, W. M. Riggs, L. E. Davis, J. F. Moulder and G. E. Muilenberg, *Handbook of X-ray Photoelectron Spectroscopy*, 1979.
- 50 J. Ghijsen, L. H. Tjeng, J. Van Elp, H. Eskes, J. Westerink, G. A. Sawatzky and M. T. Czyzyk, *Phys. Rev. B*, 1988, **38**, 11322–11330.
- 51 M. C. Biesinger, *Surf. Interface Anal.*, 2017, **49**, 1325–1334.
- 52 R. J. Iwanowski and D. Trivih, *Sol. Cells*, 1985, **13**, 253–264.
- 53 L. Liao, Q. Zhang, Z. Su, Z. Zhao, Y. Wang, Y. Li, X. Lu, D. Wei, G. Feng, Q. Yu, X. Cai, J. Zhao, Z. Ren, H. Fang, F. Robles-Hernandez, S. Baldelli and J. Bao, *Nat. Nanotechnol.*, 2014, **9**, 69–73.
- 54 T. A. Shifa, F. Wang, Z. Cheng, P. He, Y. Liu, C. Jiang, Z. Wang and J. He, *Adv. Funct. Mater.*, 2018, **28**, 1–8.
- 55 S. C. Wu, C. S. Tan and M. H. Huang, *Adv. Funct. Mater.*, 2017, **27**, 1–8.
- 56 F. Biccari, *Defects and doping in Cu₂O*, Lulu.com, 2012.
- 57 H. Raebiger, S. Lany and A. Zunger, *Phys. Rev. B*, 2007, **76**, 1–5.
- 58 P. He, X. Shen and H. Gao, *J. Colloid Interface Sci.*, 2005, **284**, 510–515.
- 59 G. D. M. R. Dabera, M. Walker, A. M. Sanchez, H. J. Pereira, R. Beanland and R. A. Hatton, *Nat. Commun.*, 2017, **8**, 1894.
- 60 B. De Boer, A. Hadipour, M. M. Mandoc, T. Van Woudenberg and P. W. M. Blom, *Adv. Mater.*, 2005, **17**, 621–625.

