


Cite this: *RSC Adv.*, 2020, 10, 41393

# Visible light responsive TiO<sub>2</sub> photocatalysts for degradation of indoor acetaldehyde†

Suzuko Yamazaki,<sup>ID</sup>\* Keisuke Kozasa, Kohshiro Okimura and Kensuke Honda

Photocatalysis is a promising technique for developing sustainable and environmentally friendly materials to improve indoor air quality. Visible-light-responsive TiO<sub>2</sub> has been widely investigated but there are inconsistent results because photocatalytic properties depend strongly on synthetic methods. Herein, we synthesize TiO<sub>2</sub> doped with 10 different metal ions (M–TiO<sub>2</sub>) by conducting a dialysis in a sol–gel method to obtain the best photocatalyst for the degradation of acetaldehyde under LED irradiation. Purification of a sol by dialysis enables us to discuss pure effects of dopants on the photocatalytic activity because impurities such as counter ions of metal salts are removed before sintering. Only Cr–, Pt–, V–, and Fe–TiO<sub>2</sub> show photocatalytic activity and the optimal doping amounts are 0.50–1.7, 0.10, 1.0, and 0.10 atom%, respectively. Such differences in the optimal amounts can be explained in terms of the dopant ions having different valence states, suggesting the formation of oxygen vacancies. The Cr–TiO<sub>2</sub> powder exhibits high activity even at the doping amount of 4.2 atom%. We also demonstrate that the Cr–TiO<sub>2</sub> film prepared on a glass substrate can be used to degrade acetaldehyde by changing the film thickness and the LED intensity depending on the degree of the indoor contamination.

Received 3rd September 2020

Accepted 5th November 2020

DOI: 10.1039/d0ra07567a

rsc.li/rsc-advances

## Introduction

Indoor air quality has become a major concern since people spend more than 80% of their time in indoor environments.<sup>1,2</sup> Many volatile organic compounds (VOCs) including formaldehyde, acetaldehyde (CH<sub>3</sub>CHO), and toluene are detected as indoor pollutants.<sup>3</sup> These chemicals are emitted continuously to the indoor air from household products such as paints, cleaning agents, constructive materials, and furniture.<sup>4–6</sup> Many technologies have been investigated to reduce the concentration of indoor VOCs by using mainly CH<sub>3</sub>CHO as a probe molecule. Adsorption on carbon-based materials is the most used technology for the removal of VOCs because of its easy operation.<sup>7,8</sup> However, regeneration of adsorbents is needed for the use of adsorption process. Photocatalytic oxidation is the most promising technique for developing sustainable and environmentally friendly materials to improve indoor air quality<sup>9,10</sup> because it promotes the decomposition of VOCs to CO<sub>2</sub> and H<sub>2</sub>O. Especially, titanium dioxide (TiO<sub>2</sub>) has been widely investigated for outdoor and indoor air purification.<sup>5,6,11</sup> However, TiO<sub>2</sub> can be activated only under ultraviolet (UV) irradiation because of the wide band gap (3.2 eV). Such UV light is scarce in indoor lighting since white light emitting diode (LED) has been widely utilized instead of fluorescent lamps for

energy saving. Doping of TiO<sub>2</sub> with metal or non-metal elements is a well-known strategy for promoting the absorption of visible light (VL) by creating new energy levels in the band gap of TiO<sub>2</sub>. TiO<sub>2</sub> doped with Pt,<sup>12</sup> Mn,<sup>1</sup> Ir,<sup>13</sup> or C<sup>4</sup> and co-doped with C and V<sup>14</sup> or with N and Fe<sup>2</sup> have been reported as active photocatalysts for the degradation of CH<sub>3</sub>CHO under VL irradiation. There are many studies on photocatalysis of TiO<sub>2</sub> doped with other elements. However, photocatalytic properties depend strongly on the synthetic method. This fact seems to be reasonable because the location and the energy level of the dopants in TiO<sub>2</sub> might be affected by the presence of impurities (*e.g.* counter ions of metal salts) during the sintering process and might be varied depending on whether the doping is conducted by using commercially available TiO<sub>2</sub> powder or by preparing TiO<sub>2</sub> nanoparticles in a sol–gel method. On the other hand, understanding the factors affecting photocatalytic activity is needed to develop more excellent materials for indoor air purification. In this study, TiO<sub>2</sub> doped with 10 different metal ions (M–TiO<sub>2</sub>) are synthesized by conducting a dialysis in the sol–gel method using Ti(OC<sub>3</sub>H<sub>7</sub>)<sub>4</sub> (TTIP) as a starting material. By conducting the dialysis, proton, 2-propanol which is formed by hydrolysis of TTIP, and counter ions of the metal salts used for doping are removed before the sintering. Furthermore, we have already found that during dialysis, V(III), Pt(IV) or Ru(IV) remained in the TiO<sub>2</sub> sol but in the case of a larger metal ion such as Cu(II) or Co(II), most of them moved out of the TiO<sub>2</sub> sol through the dialysis tube.<sup>15,16</sup> This finding indicates that metal ion dopants can be divided into two groups, *i.e.* with and without some interaction with TiO<sub>2</sub> nanoparticles in the sol. By sintering the

Department of Chemistry, College of Science, Graduate School of Sciences and Technology for Innovation, Yamaguchi University, Yamaguchi 753-8512, Japan.  
E-mail: yamazaki@yamaguchi-u.ac.jp

† Electronic supplementary information (ESI) available. See DOI: 10.1039/d0ra07567a



purified sol after the dialysis, only metal ions which interact with  $\text{TiO}_2$  nanoparticles in the sol can be doped. This might be useful to elucidate the factors affecting the photocatalysis because we do not have to consider two different situations, with and without the interaction between metal ions and  $\text{TiO}_2$  nanoparticles. The purpose of this study is clarifying the best choice of  $\text{M-TiO}_2$  for the degradation of  $\text{CH}_3\text{CHO}$  under LED irradiation and understanding the factors affecting the photocatalysis. Furthermore, the photocatalytic activity of the  $\text{M-TiO}_2$  film is evaluated because the film is more appropriate than powders to the practical application for indoor air purification.

## Experimental

### Synthesis of photocatalysts

Approximately 15 ml of TTIP was added dropwise to 180 ml of aqueous solutions containing 1.3 ml of  $\text{HNO}_3$ . The obtained suspension was stirred at room temperature with a magnetic stirrer for 6 days to get a highly dispersed colloidal solution. This sol was dialyzed in 2750 ml of water by using a precleaned molecularly porous dialysis tubing (Spectra/Por® 3, molecular weight cut-off: 3500) for 2 days by changing water once a day to get pH 2. The cleaning method of the dialysis tubing was described in ESI†. Then, the obtained transparent sol was placed in a beaker and mixed with 2 ml of aqueous solutions containing  $\text{CrCl}_3 \cdot 6\text{H}_2\text{O}$ ,  $\text{H}_2\text{PtCl}_6 \cdot 6\text{H}_2\text{O}$ ,  $\text{VCl}_3$ ,  $\text{FeCl}_3 \cdot 6\text{H}_2\text{O}$ ,  $\text{CuCl}_2$ ,  $\text{MnCl}_2 \cdot 4\text{H}_2\text{O}$ ,  $\text{Na}_2\text{MoO}_4 \cdot 2\text{H}_2\text{O}$ ,  $\text{Na}_2\text{WO}_4 \cdot 2\text{H}_2\text{O}$ ,  $\text{NbCl}_5$ , or  $\text{RuCl}_3 \cdot n\text{H}_2\text{O}$  to get the concentration of metal ion of 0.1–10 atom% against the total of Ti and the metal ion. After stirring, this solution was dialyzed for 1 day to remove counter ions of metal salts. Removal of the counter ions was confirmed by using ion chromatograph (Shimadzu, PIA-1000, column: Shim-pack IC-A3(S)). For example, 0.1036 g of  $\text{CrCl}_3 \cdot 6\text{H}_2\text{O}$  was used for the synthesis of 0.8 atom%  $\text{Cr-TiO}_2$ . The concentration of metal ion which was moved out of the dialysis tube during the dialysis was evaluated by inductively coupled plasma atomic emission spectroscopy (Varian, ICP-AES Liberty Series II and Agilent Technologies, 5110 ICP-OES). A finally obtained solution ( $\text{M-TiO}_2$  sol) was dried, crushed into powder, and sintered at  $500^\circ\text{C}$  for 3 h with ramping rate at  $3^\circ\text{C min}^{-1}$ . For comparison, pure  $\text{TiO}_2$  was synthesized by conducting the dialysis for 3 days without the addition of the metal ions. Table S1† lists the amounts of metal ions added in the synthesis and those doped in the finally obtained samples.

### Preparation of films

Three coating methods were employed to prepare the  $\text{Cr-TiO}_2$ ,  $\text{Pt-TiO}_2$  and  $\text{V-TiO}_2$  films on slide glasses ( $4.0 \times 1.5 \text{ cm}^2$ ) which were precleaned with sonication in water and acetone. A suspension of 0.10 g of the  $\text{Cr-TiO}_2$ ,  $\text{Pt-TiO}_2$  or  $\text{V-TiO}_2$  powder in 10 ml of ethanol was used for making films by using a spin coater (Kyowariken, K359S1) with a rotation at 500 rpm for 15 s followed by that at 2000 rpm for 30 s. This process was repeated 5 times as a standard condition before the sintering. The obtained film was denoted as  $\text{M-TiO}_2\text{-SC}$ . To make a thick  $\text{Cr-TiO}_2$  film ( $\text{Cr-TiO}_2\text{-TK}$ ), 0.30 g of  $\text{Cr-TiO}_2$  was mixed with

0.015 g of polyethylene glycol and 1.5 ml of ethanol by using a mortar and a pestle and was spread in a recess which was made by using adhesive tapes with a height of  $53 \mu\text{m}$  as spacers on the slide glass. The obtained surface was flattened by moving a glass rod, dried and sintered after removing the tapes. The  $\text{Cr-TiO}_2\text{-DC}$  film was prepared by using the  $\text{Cr-TiO}_2$  sol just after the dialysis and a dip-coater (SDI, DT-0001-S1) under the condition of withdrawal/immersion rate of  $9.0 \text{ mm s}^{-1}$  and dip-duration of 10 min followed by the sintering. This procedure was repeated three times. Sintering conditions for making all films were the same as those for the synthesis of the  $\text{M-TiO}_2$  powder.

### Characterization

X-ray diffraction (XRD, Rigaku, Miniflex 600) analysis was performed with  $\text{Cu K}\alpha$  radiation (40 kV, 15 mA) at  $2\theta$  angles from  $10^\circ$  to  $90^\circ$  with a scan speed of  $10^\circ \text{ min}^{-1}$ . The Brunauer–Emmett–Teller (BET) specific surface area was measured with nitrogen as the adsorptive gas by automatic surface area analyzer (Shimadzu, Tristar II 3020). Diffuse reflectance UV-vis absorption spectra of the powder samples were obtained by using a spectrophotometer (JASCO, V-670). The valence state of Cr, Pt or V ion near the  $\text{TiO}_2$  surface was analyzed by X-ray photoelectron spectroscopy (XPS, Thermo SCIENTIFIC, K-Alpha). The binding energies were calibrated with reference to the C 1s peak (284.6 eV) originating from the surface impurity carbons. Electrochemical Impedance Spectroscopy (EIS) was measured to evaluate a flat band potential of  $\text{TiO}_2$  or  $\text{M-TiO}_2$  electrode by using potentiostat/galvanostat (Solartron Analytical, SI 1287) and frequency response analyzer (Solartron Analytical, SI 1260). These electrodes were prepared on transparent conductive substrate (fluorine-doped tin oxide (FTO) on glass, GEOMATEC,  $10 \Omega \text{ sq}^{-1}$ ) in the same way as  $\text{Cr-TiO}_2\text{-DC}$  film although the coating process was not repeated. In the electrochemical cell, a platinum electrode was used as the counter electrode,  $\text{Ag/AgCl}$  (in saturated KCl) as a reference, and  $1.0 \text{ mol dm}^{-3}$  NaOH solution as an electrolyte and bubbling with argon gas was conducted to remove oxygen before the measurements.

### Photocatalytic degradation of gaseous $\text{CH}_3\text{CHO}$

The synthesized  $\text{M-TiO}_2$  powder (0.03 g) or film was placed in a transparent Pyrex vial (40 ml, capped with a Mininert valve) with two small branches, each of which was connected with a two-way valve by Fluran tubing. Reactant gas stream containing  $\text{CH}_3\text{CHO}$ , oxygen, and water vapor was prepared by adjusting the flowrate of the gas stream from gas cylinders containing  $\text{CH}_3\text{CHO}$  (199 ppmv,  $\text{N}_2$  balance, Taiyo Nippon Sanso Co.), oxygen (>99.9%, Iwatani Co.) and nitrogen (>99.9%, Taiyo Nippon Sanso Co.) and by passing partly through the saturator containing water. After the reactant gas was passed through the vial for 1 h in the dark to achieve an adsorption–desorption equilibrium on  $\text{M-TiO}_2$ , the two-way valves were closed. The gas of 300  $\mu\text{l}$  was taken by using a gas-tight syringe through the Mininert valve and analyzed by gas-chromatography (Shimadzu, GC-2014, equipped with flame ionization and thermal conductivity detectors). It is noted that



300  $\mu\text{l}$  of nitrogen was injected in the vial just before the sampling to suppress the pressure decrease through the experiments. After confirming the constant concentration of  $\text{CH}_3\text{CHO}$  by GC, the vial was irradiated with 16 W LED (LDR100-220 V 16N-H, Mitsubishi) or 4.4 W LED (LDA4N-G/40 W, Toshiba) which did not emit light with wavelength shorter than 400 nm. The light intensity was measured with a solar power meter (MK-Scientific, TM-207) to be 1.0 or 0.10  $\text{mW cm}^{-2}$  for 16 W or 4.4 W LED, respectively. The photocatalytic experiments were performed at  $25 \pm 1^\circ\text{C}$  by circulating the surrounding air and the sampling was conducted every 20 min. Initial reaction rate ( $r_0$ ) was evaluated from the slope of the plots of the concentration of  $\text{CH}_3\text{CHO}$  vs. irradiation time ( $r_0 = -d[\text{CH}_3\text{CHO}]_{t=0}/dt$ ). In this paper,  $r_0$  is expressed in the unit of  $\text{ppmv min}^{-1}$  where 1  $\text{ppmv min}^{-1}$  corresponds to  $1.64 \times 10^{-9} \text{ mol min}^{-1}$ . Unless otherwise noted, the photocatalytic experiments were performed in the reactant gas containing  $\text{CH}_3\text{CHO}$  (mole fraction:  $1.0 \times 10^{-4}$ ), oxygen (0.20), and water vapor ( $6.0 \times 10^{-3}$ ).

## Result and discussion

### Effect of amounts of metal ion dopants in M-TiO<sub>2</sub>

Fig. 1 indicates dependence of  $r_0$  on the amounts of metal ion in M-TiO<sub>2</sub> sintered at 500  $^\circ\text{C}$ . Only Cr-, Pt-, V-, and Fe-TiO<sub>2</sub> show higher activity than TiO<sub>2</sub> which possesses  $r_0$  of 0.42  $\text{ppmv min}^{-1}$  as shown by a dashed line in Fig. 1. The Cr-TiO<sub>2</sub> powder exhibits the highest  $r_0$  value (1.17  $\text{ppmv min}^{-1}$ ) at 0.5 atom% but the  $r_0$  value does not change significantly at the doping amount of 0.5–1.7 atom% ( $r_0 = 1.12 \pm 0.05 \text{ ppmv min}^{-1}$ ). Thus, we select 0.8 atom% Cr-TiO<sub>2</sub> as a standard sample in later discussion. In the case of Pt-TiO<sub>2</sub> powder, the  $r_0$  value is 1.11  $\text{ppmv min}^{-1}$  at 0.10 atom% and decreases drastically with an increase in the doping amount. A similar behavior is observed with Fe-TiO<sub>2</sub> although the highest  $r_0$  value is about half of that of Pt-TiO<sub>2</sub>. The optimal doping amount of V-TiO<sub>2</sub> is 1.0 atom% ( $r_0 = 1.08 \text{ ppmv min}^{-1}$ ). Doping of Pt  $\geq 1.0$  atom%, Fe  $\geq 0.5$  atom% or other metal ions lowers the photocatalytic activity of TiO<sub>2</sub>, suggesting that these metal ions might act as the recombination center of the photogenerated holes and electrons. Hereafter, characterization of the Cr-TiO<sub>2</sub>, Pt-TiO<sub>2</sub>, and V-TiO<sub>2</sub> powder was compared to explain their differences in the photocatalytic performance.

### Comparison of Cr-TiO<sub>2</sub>, Pt-TiO<sub>2</sub>, and V-TiO<sub>2</sub>

Fig. S1† shows XRD patterns of Cr-TiO<sub>2</sub>, Pt-TiO<sub>2</sub>, V-TiO<sub>2</sub>, and TiO<sub>2</sub> sintered at 500  $^\circ\text{C}$ , indicating that the former three samples exhibit the peaks attributable to anatase, brookite, and rutile but TiO<sub>2</sub> shows only rutile which is the most thermodynamically stable phase. Fig. 2 indicates the composition ratio of anatase, rutile, and brookite, which was evaluated by Rietveld analysis for the XRD patterns. We also examined the effect of the sintering temperature on the  $r_0$  values in the range of 200–600  $^\circ\text{C}$  by using 0.8 atom% Cr-TiO<sub>2</sub>, 0.1 atom% Pt-TiO<sub>2</sub>, and 1.0 atom% V-TiO<sub>2</sub>. Both Pt-TiO<sub>2</sub> and V-TiO<sub>2</sub> exhibited the highest  $r_0$  values when being sintered at 500  $^\circ\text{C}$  although the  $r_0$  value for Cr-TiO<sub>2</sub> sintered at 400  $^\circ\text{C}$  was slightly higher than that at

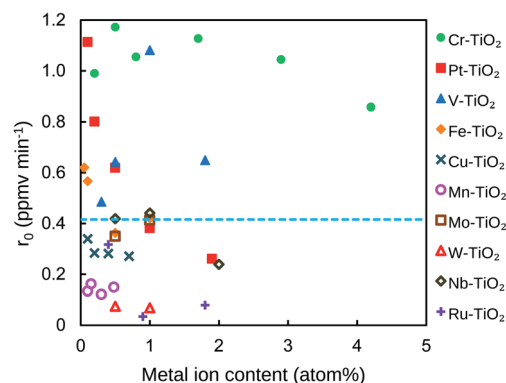


Fig. 1 Effect of metal ion content in M-TiO<sub>2</sub> on the initial degradation rate of  $\text{CH}_3\text{CHO}$ . The broken line indicates the initial degradation rate of  $\text{CH}_3\text{CHO}$  on TiO<sub>2</sub> powder.

500  $^\circ\text{C}$  (Fig. S2†). Besides, for the preparation of the FTO electrode and the slide glass which were coated with M-TiO<sub>2</sub> as discussed later, sintering at 500  $^\circ\text{C}$  was needed to prevent the film from being peeled off from the substrates. Thus, we selected the sintering temperature to be 500  $^\circ\text{C}$  for the comparison of the  $r_0$  values for Cr-TiO<sub>2</sub>, Pt-TiO<sub>2</sub>, and V-TiO<sub>2</sub> powder.

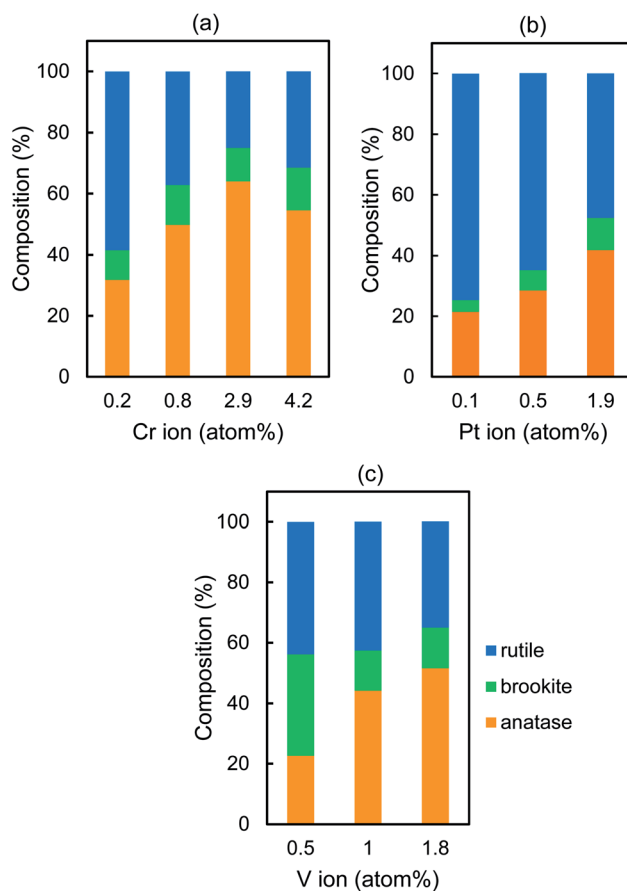


Fig. 2 Crystal phase composition of (a) Cr-TiO<sub>2</sub>, (b) Pt-TiO<sub>2</sub>, and (c) V-TiO<sub>2</sub> powder.



**Table 1** Band gap energy ( $E_g$ ) and BET specific surface area (SSA) of Cr-TiO<sub>2</sub>, Pt-TiO<sub>2</sub>, and V-TiO<sub>2</sub> powder

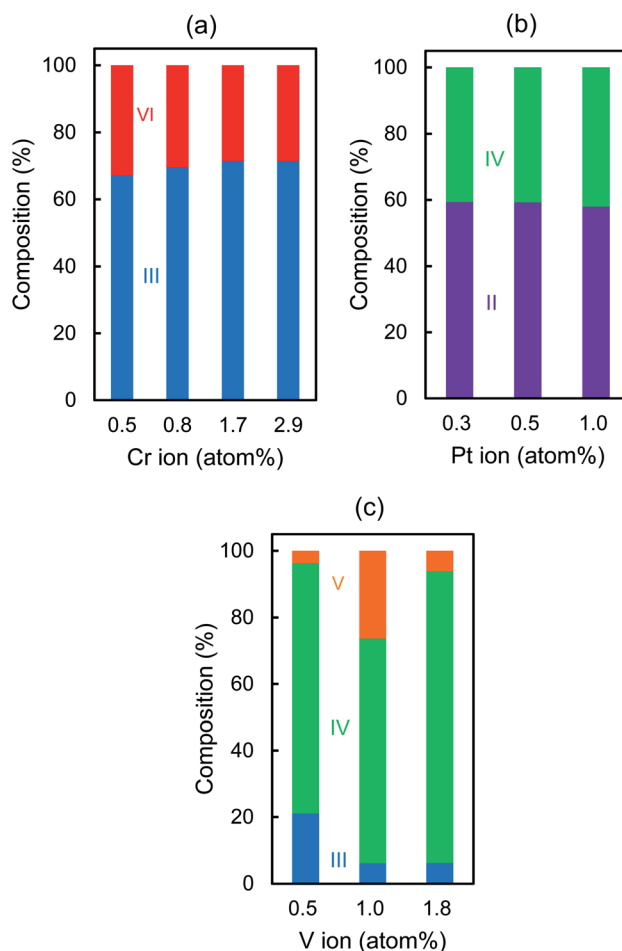
Cr content (atom%)	Cr-TiO <sub>2</sub>		Pt content (atom%)	Pt-TiO <sub>2</sub>		V content (atom%)	V-TiO <sub>2</sub>	
	$E_g$ (eV)	SSA (m <sup>2</sup> g <sup>-1</sup> )		$E_g$ (eV)	SSA (m <sup>2</sup> g <sup>-1</sup> )		$E_g$ (eV)	SSA (m <sup>2</sup> g <sup>-1</sup> )
0.20	2.82	75.5	0.10	2.90	34.4	0.50	3.01	56.9
0.80	2.80	50.5	0.50	2.70	51.9	1.0	2.86	38.8
1.7	2.44	40.0	1.0	2.69	43.0	1.8	2.71	65.4
2.9	2.40	—	1.9	2.47	—			

Fig. S3† shows the UV-vis diffuse reflectance spectra, indicating that absorption edge is shifted to the longer wavelength with increasing the doping amount. The band gap energy ( $E_g$ ) was calculated by Tauc plots in which indirect transition band gap was postulated (Table 1).<sup>17–19</sup> The Cr-TiO<sub>2</sub>, Pt-TiO<sub>2</sub>, and V-TiO<sub>2</sub> samples possess a similar tendency that the transformation to rutile is suppressed and  $E_g$  decreases as the doping amount increases. Table 1 also lists the BET specific surface area (SSA) of these samples, which does not change systematically except for Cr-TiO<sub>2</sub>. These findings cannot explain the different behavior observed with Cr-TiO<sub>2</sub>, Pt-TiO<sub>2</sub>, and V-TiO<sub>2</sub> as shown in Fig. 1.

Fig. 3 shows the valence states of the metal ion dopants which are evaluated from the peak area after deconvolution in the XPS spectra (Fig. S4†). In the case of Cr-TiO<sub>2</sub> or Pt-TiO<sub>2</sub>, Cr(vi) or Pt(II) is formed during the synthesis and the ratio of Cr(III)/Cr(vi) or Pt(II)/Pt(IV) keeps almost constant, *i.e.*  $2.3 \pm 0.3$  or  $1.4 \pm 0.1$ , respectively, regardless of the doping amounts. On the other hand, V(III), V(IV), and V(V) are detected and V(IV) exists predominantly in all V-TiO<sub>2</sub> samples. Flat band potential of TiO<sub>2</sub> is affected by the doping of metal ions. Fig. S5† indicates Mott-Schottky plots of the TiO<sub>2</sub> film prepared on FTO under various frequencies in the range of 250–10 000 Hz, indicating positive slopes which are typical for n-type semiconductors. A carrier density ( $N_D$ ) and a flat band potential ( $V_{FB}$ ) of TiO<sub>2</sub> were estimated to be  $3.6 \times 10^{18}$  cm<sup>-3</sup> and  $-0.76$  V vs. Ag/AgCl, respectively, at 1000 Hz.

Fig. 4 shows the effect of the doping amounts on  $V_{FB}$  and  $N_D$  of the Cr-TiO<sub>2</sub>, Pt-TiO<sub>2</sub> and V-TiO<sub>2</sub> film, which were evaluated at 1000 Hz. The  $N_D$  values of these samples are almost the same as that of TiO<sub>2</sub> even if the doping amounts are changed. This fact is presumably due to the low doping amounts in this study. The  $V_{FB}$  values of Cr-TiO<sub>2</sub> and V-TiO<sub>2</sub> are estimated to be  $-0.74 \pm 0.04$  and  $-0.73 \pm 0.05$  V, respectively. The position of the CB edge of n-type semiconductor is adjacent to  $V_{FB}$ . Takle *et al.* reported that the doping of Cr(III) created a new energy level just above the VB edge of TiO<sub>2</sub>.<sup>20</sup> Rossi *et al.* reported that the energy level induced by doping of V(IV) was located at *ca.* 2.2 eV below the CB edge of TiO<sub>2</sub>.<sup>21</sup> Because of such deep levels of Cr(III) and V(IV) dopants, it is likely that the  $V_{FB}$  values of Cr-TiO<sub>2</sub> and V-TiO<sub>2</sub> are not affected by the doping and are nearly equal to that of TiO<sub>2</sub>. On the other hand, the  $V_{FB}$  of Pt-TiO<sub>2</sub> increases from  $-0.75$  to  $-0.61$  V with increasing the doping amount from 0.1 to 1.0 atom%. Kim *et al.* also reported that  $V_{FB}$  was shifted positively by 50 mV by doping Pt ion in TiO<sub>2</sub>, indicating the CB edge

position was slightly lowered.<sup>22</sup> The remarkable decrease in the photocatalytic degradation of CH<sub>3</sub>CHO on Pt-TiO<sub>2</sub> with increasing the doping amounts is attributable to the lower CB edge which retards the transfer of the photogenerated electron to oxygen, resulting in the enhancement of the recombination. Table 2 lists the average values of the composition ratio of the dopant ions which are calculated from Fig. 3 with their ionic radii in parentheses. The ionic radius of Cr(III), Pt(IV), or V(III), whose compounds are used as the starting materials in the synthesis, is 0.755, 0.765, or 0.78 Å, respectively.<sup>23</sup> Because their size is close to Ti(IV) (0.745 Å), they are easily substituted for Ti(IV) during the

**Fig. 3** Atomic valence composition of (a) Cr-TiO<sub>2</sub>, (b) Pt-TiO<sub>2</sub>, and (c) V-TiO<sub>2</sub> powder.

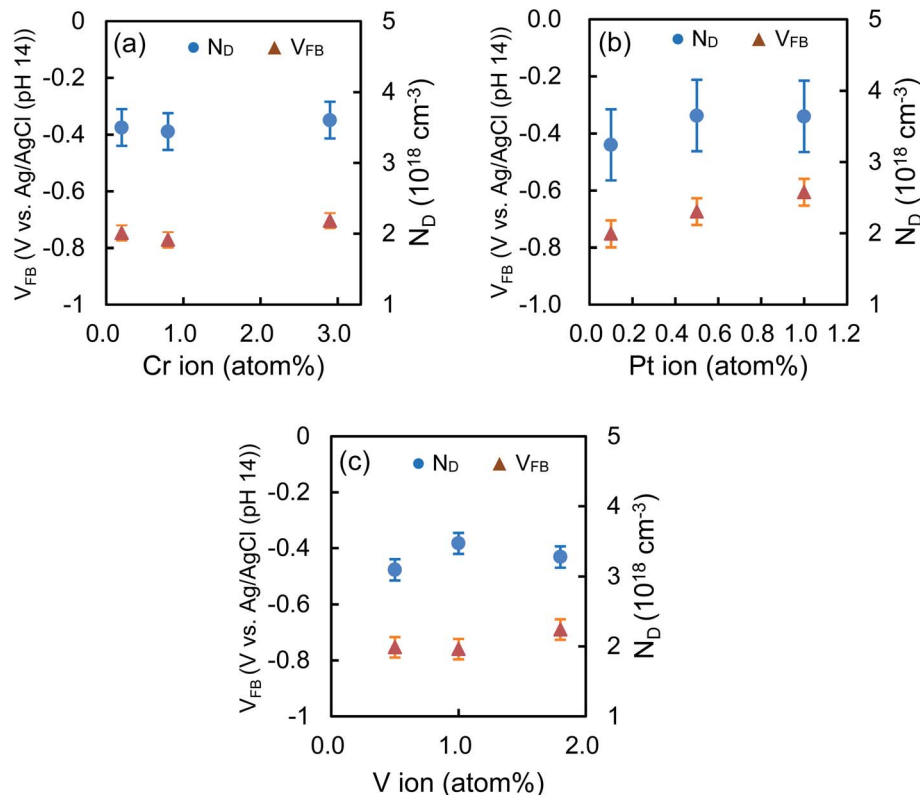


Fig. 4  $V_{FB}$  and  $N_D$  of (a) Cr-TiO<sub>2</sub>, (b) Pt-TiO<sub>2</sub>, and (c) V-TiO<sub>2</sub> powder.

synthesis. After being sintered at 500 °C, Cr(III) still exists predominantly (69.9%) and is partially oxidized to Cr(VI) (30.1%).

In the case of V-TiO<sub>2</sub>, V(IV) is formed predominantly (76.8%) together with V(III) (11.1%) and V(V) (12.1%), among which V(IV) and V(III) have a similar size as Ti(IV). Substitution of Ti(IV) with metal ions having a lower valence state, e.g. Cr(III) or V(III), induces the removal of oxygen atom from the TiO<sub>2</sub> lattice to balance the charge, leading to the formation of oxygen vacancy. Some research groups reported that the presence of oxygen vacancy enhanced the photocatalytic activity by trapping the photogenerated electron to suppress the recombination.<sup>24–29</sup> It is likely that more oxygen vacancies are created in Cr-TiO<sub>2</sub> compared with V-TiO<sub>2</sub> because the main component of Cr-TiO<sub>2</sub> or V-TiO<sub>2</sub> is Cr(III) or V(IV), respectively. Therefore, the high performance of Cr-TiO<sub>2</sub> is attributable to the formation of more

oxygen vacancies. In the case of V-TiO<sub>2</sub>, the optimal doping amount was 1.0 atom% where the highest amount of V(V) was detected (Fig. 3c). This finding suggests that the presence of V(V) enhances the photocatalytic activity. Ren *et al.* synthesized the V-doped TiO<sub>2</sub> by using titanate acid and  $\text{NH}_4\text{VO}_3$  and reported that a part of V(V) was reduced to V(IV) into TiO<sub>2</sub> lattice and others existed as  $\text{V}_2\text{O}_5$  on the surface where V(V) received the photogenerated electrons, resulting in the effective separation of the photogenerated carriers.<sup>30</sup> In the case of Pt-TiO<sub>2</sub>, more Pt(II) are formed than Pt(IV). The ionic radius of Pt(II) (0.94 Å) is much larger than Pt(IV) or Ti(IV). Previously, we demonstrated by measuring XPS and XANES of Pt-TiO<sub>2</sub> sintered at 200 °C that Pt(II) ion existed near the surface and only Pt(IV) was located in the bulk.<sup>31</sup> This finding was easily explained in terms of their ionic radii. Mukri *et al.* reported that the presence of Pt(II) brought about its d states above the VB edge and oxygen vacancies.<sup>32</sup> They demonstrated that Pt(II)-substituted TiO<sub>2</sub> with oxygen vacancies exhibited higher photocatalytic activity for CO oxidation than Pt(IV)-substituted TiO<sub>2</sub> without oxygen vacancies. Kim *et al.* mentioned that Pt dopants created energy levels above the VB edge where the trapped holes are highly localized and the oxygen vacancies were created near the Pt(II) sites.<sup>33</sup> Indeed, we reported that the photocatalytic degradation of 4-chlorophenol was enhanced with increasing the ratio of Pt(II)/Pt(IV) in the range of 2.7–21.2 in Pt-TiO<sub>2</sub> sintered at 200 °C.<sup>31</sup> On the other hand, in this study, the ratio of Pt(II)/Pt(IV) was estimated to be  $1.4 \pm 0.1$  for Pt-TiO<sub>2</sub> sintered at 500 °C, indicating that the amounts of Pt(II) and Pt(IV) are almost comparable. Kim

Table 2 Ionic radii (Å) of metal ions and their average composition ratio (%)<sup>a</sup>

Valence				
6+	5+	4+	3+	2+
Ti (0.745)				
Cr (0.58) 30.1			Cr (0.755) 69.9	
		Pt (0.765) 41.2		Pt (0.94) 58.8
	V (0.68) 12.1	V (0.72) 76.8	V (0.78) 11.1	

<sup>a</sup> Ionic radii cited from literature<sup>23</sup> are written in parentheses.

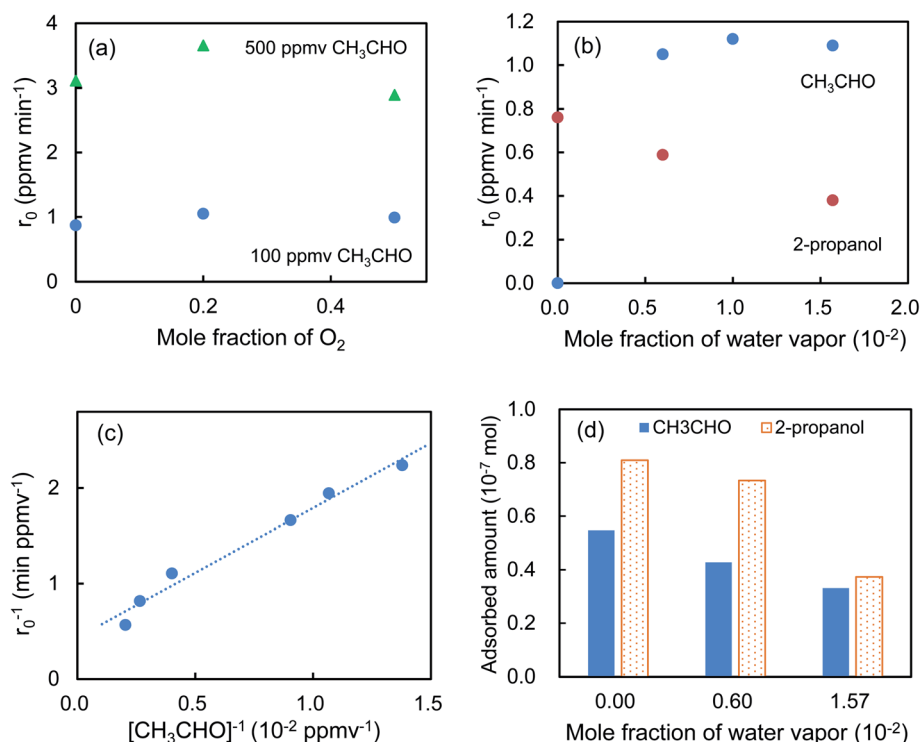



Fig. 5 Effect of mole fractions of (a) oxygen, (b) water vapor, and (c) CH<sub>3</sub>CHO on the  $r_0$  values. (d) Dependence of the adsorbed amount of CH<sub>3</sub>CHO on the mole fraction of water vapor. For comparison, the data obtained with 2-propanol were also depicted in (b) and (d).

*et al.* mentioned that the presence of both Pt(II) and Pt(IV) might reduce the beneficial role of Pt(II) because the energy level created with Pt(II) and Pt(IV) lay close to each other, leading to the recombination of the photogenerated electron-hole pair.<sup>33</sup> Therefore, lower photocatalytic activity observed with Pt-TiO<sub>2</sub> is due to the less formation of effective oxygen vacancies near Pt(II) compared with the oxygen vacancies around Cr(III) in Cr-TiO<sub>2</sub>. There is another possibility that oxygen vacancies induced by Cr(III) in the TiO<sub>2</sub> bulk and those by Pt(II) near the surface might be different. Our findings on the different dependence of  $r_0$  on the doping amounts of Cr-, Pt- and V-TiO<sub>2</sub> can be explained in terms of the difference in their main valence states which are correlated with the formation of the oxygen vacancies. Further studies are needed to conclude the oxygen vacancies as the most important factor for the VL-responsive M-TiO<sub>2</sub> photocatalyst. For that purpose, developing the method for a quantitative analysis of the oxygen vacancies is required. It is worthy to note that 0.8 atom% Cr-TiO<sub>2</sub> prepared by conducting the dialysis shows much higher activity than that without the dialysis

(Fig. S6†). Conducting dialysis is beneficial not only for the removal of impurities before the sintering process but also for the enhancement of the photocatalytic activity. Hereafter, the photocatalytic activity of 0.8 atom% Cr-TiO<sub>2</sub> for the degradation of CH<sub>3</sub>CHO is discussed.

#### Photocatalytic degradation of CH<sub>3</sub>CHO on Cr-TiO<sub>2</sub>

Fig. 5a shows that the  $r_0$  value is almost independent on the mole fraction of oxygen ( $5.0 \times 10^{-6}$ –0.50) when the experiments are performed in the reactant gas containing water vapor (mole fraction:  $6.0 \times 10^{-3}$ ) and CH<sub>3</sub>CHO (mole fraction:  $1.0 \times 10^{-4}$  or  $5.0 \times 10^{-4}$ ). In the absence of water vapor, CH<sub>3</sub>CHO is not degraded and the  $r_0$  value increases to reach a constant value of  $1.09 \pm 0.03$  ppmv min<sup>-1</sup> (Fig. 5b). Fig. 5c exhibits a linear relationship between  $r_0^{-1}$  vs. [CH<sub>3</sub>CHO]<sup>-1</sup>, indicating that the reaction follows the Langmuir-Hinshelwood kinetic model where adsorption of the reactant is assumed prior to reaction. Generally, for the photocatalytic degradation of organic

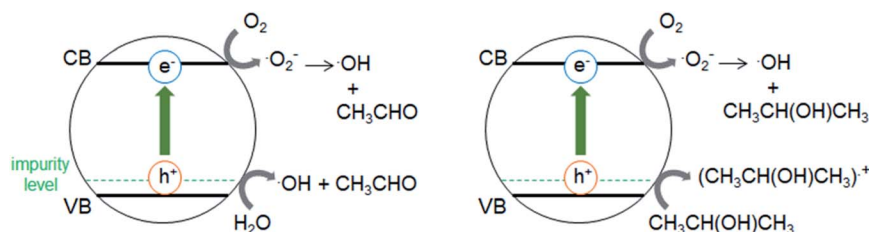

Scheme 1 Illustration of photocatalytic degradation of CH<sub>3</sub>CHO and 2-propanol on Cr-TiO<sub>2</sub> under VL irradiation.



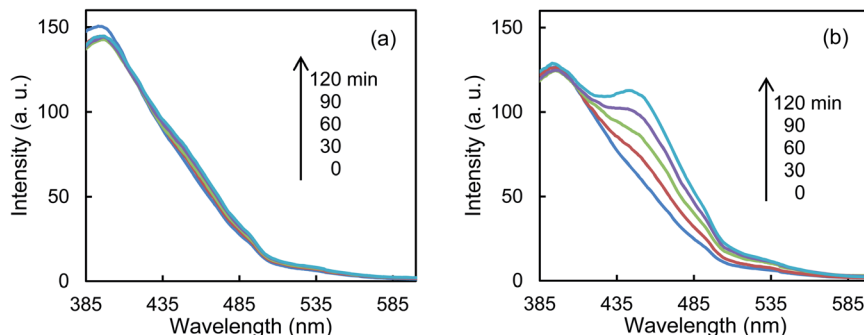


Fig. 6 Fluorescence spectra of an aqueous solution containing coumarin and (a)  $\text{TiO}_2$  or (b)  $\text{Cr-TiO}_2$  powder under VL irradiation for 120 min.

compounds in the gas phase, the degradation rate decreases with an increase in the mole fraction of water vapor due to the competitive adsorption on reactive sites. Indeed, as shown in Fig. 5b, when 2-propanol is used instead of  $\text{CH}_3\text{CHO}$  in the experiments, the  $r_0$  value decreases with increasing mole fraction of water vapor. To understand such a different behavior, we measured the time course of the concentration of  $\text{CH}_3\text{CHO}$  or 2-propanol in the dark by injecting 10 ml of 198 ppmv  $\text{CH}_3\text{CHO}$  or 199 ppmv 2-propanol to the vial containing oxygen (mole fraction of 0.20), water vapor (0,  $6.0 \times 10^{-3}$ , or  $1.6 \times 10^{-2}$ ) and  $3.0 \times 10^{-3}$  g of 0.8 atom%  $\text{Cr-TiO}_2$ . In the absence of water vapor,  $17.9 \pm 1.4$  ppmv of  $\text{CH}_3\text{CHO}$  was detected but no 2-propanol was observed, indicating all of 2-propanol was adsorbed on the  $\text{Cr-TiO}_2$  surface (Fig. S7†). The adsorbed amounts of  $\text{CH}_3\text{CHO}$  or 2-propanol was calculated by analyzing the data in Fig. S7.† Fig. 5d shows the adsorbed amount of  $\text{CH}_3\text{CHO}$  decreases with an increase in the water vapor and is less than that of 2-propanol at any water vapor mole fraction. These results indicate that both  $\text{CH}_3\text{CHO}$  and 2-propanol adsorb on  $\text{Cr-TiO}_2$  competitively with water but the adsorption of 2-propanol is more strongly than  $\text{CH}_3\text{CHO}$ . The different dependence of  $r_0$  on the mole fraction of water vapor as shown in Fig. 5b suggests that 2-propanol is mainly degraded by the photogenerated holes whereas  $\text{CH}_3\text{CHO}$  is degraded by OH radicals which are formed by the oxidation of water vapor by the photogenerated holes (Scheme 1). Therefore, the presence of water vapor is crucial for the degradation of  $\text{CH}_3\text{CHO}$ . Takeuchi *et al.* reported that  $\text{CH}_3\text{CHO}$  was oxidized by the OH radicals which were formed by

the photooxidation of  $\text{H}_2\text{O}$  molecules on  $\text{TiO}_2$  under UV irradiation.<sup>34</sup> It is well-known that coumarin traps OH radical to generate 7-hydroxycoumarin (7-HC) which emits fluorescence at *ca.* 460 nm.<sup>35</sup> We measured the fluorescence spectra of aqueous solutions containing coumarin ( $5.0 \times 10^{-5}$  mol  $\text{dm}^{-3}$ ) and 0.2 wt% of  $\text{TiO}_2$  or  $\text{Cr-TiO}_2$  under VL irradiation for 120 min. Fig. 6 shows that the fluorescence at 460 nm increases slightly in the presence of  $\text{TiO}_2$  whereas it remarkably increases in the case of  $\text{Cr-TiO}_2$ . This finding demonstrates the formation of OH radicals on  $\text{Cr-TiO}_2$  under VL irradiation. Fig. 7a shows the time course of  $\text{CH}_3\text{CHO}$  and  $\text{CO}_2$  on  $\text{Cr-TiO}_2$ , indicating that 80 ppmv of  $\text{CH}_3\text{CHO}$  is degraded under VL irradiation for 80 min but the concentration of  $\text{CO}_2$  continues to increase. At the irradiation for 720 min, the stoichiometric ratio of  $[\text{CO}_2]_{\text{formed}}/[\text{CH}_3\text{CHO}]_{\text{degraded}}$  was estimated to be 2.39, which is above the theoretical value for the complete mineralization and can be ascribed to  $\text{CH}_3\text{CHO}$  preadsorbed on  $\text{Cr-TiO}_2$  before the VL irradiation. Fig. 7b shows diffuse reflectance FTIR spectra of FTIR on  $\text{Cr-TiO}_2$ , indicating that new peaks appear at 1529 and 1440  $\text{cm}^{-1}$  at the VL irradiation for 20 min and decrease gradually with increasing the irradiation time. These two peaks are coincident with those observed with  $\text{TiO}_2$  which was immersed in acetic acid (1 mol  $\text{dm}^{-3}$ ) followed by dryness (Fig. 7b). Acetic acid is formed by the photocatalytic oxidation of  $\text{CH}_3\text{CHO}$  on  $\text{TiO}_2$  under UV irradiation.<sup>36</sup> Therefore, the peaks at 1529 and 1440  $\text{cm}^{-1}$  are attributable to  $\nu_{\text{as}}(\text{COO})$  and  $\delta_{\text{as}}(\text{CH}_3)$ , respectively.<sup>37</sup> It is noted that these peaks can be seen even at the VL

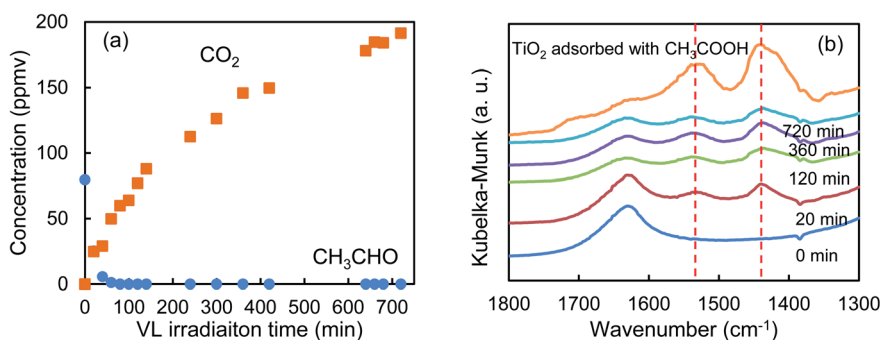


Fig. 7 Time course of (a) the concentrations of  $\text{CH}_3\text{CHO}$  and  $\text{CO}_2$  and (b) diffuse reflectance FTIR spectra of  $\text{Cr-TiO}_2$  under VL irradiation for 720 min. For comparison, diffuse reflectance FTIR spectra of  $\text{TiO}_2$  adsorbed with acetic acid is depicted.

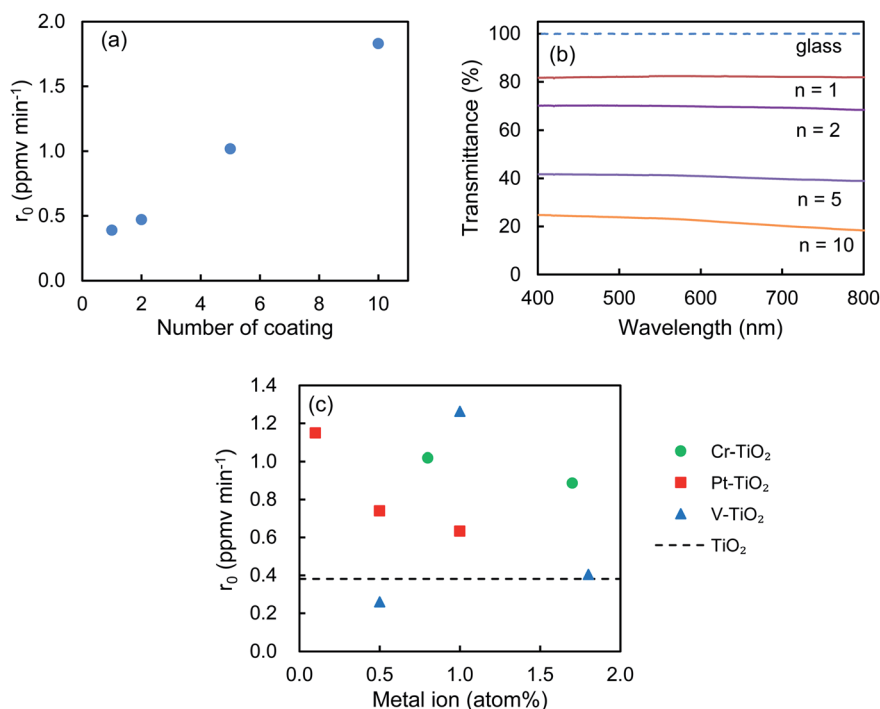


Fig. 8 Effect of number of coating ( $n$ ) on (a) the  $r_0$  value and (b) the transmittance of 0.8 atom% Cr-TiO<sub>2</sub>-SC films. (c) Effect of metal ion content on the  $r_0$  value of M-TiO<sub>2</sub>-SC ( $n = 5$ ) film (M = Cr, Pt, V).

irradiation for 720 min, indicating that a small quantity of acetic acid exists on the Cr-TiO<sub>2</sub> surface.

### Photocatalytic degradation of CH<sub>3</sub>CHO on Cr-TiO<sub>2</sub>, Pt-TiO<sub>2</sub> and V-TiO<sub>2</sub> films for practical application

Effect of number of coating on the  $r_0$  value and on the transmittance of the 0.8 atom% Cr-TiO<sub>2</sub>-SC films were investigated. Fig. 8a and b indicate that  $r_0$  increases but the transmittance decreases with increasing the number of coating ( $n$ ). These findings suggest that CH<sub>3</sub>CHO is degraded more effectively by increasing the amounts of the photocatalysts. Fig. 8c shows the effect of the doping amounts of the metal ions on the  $r_0$  values of M-TiO<sub>2</sub>-SC ( $n = 5$ ) film. As the doping amount increases, the  $r_0$  value for Pt-TiO<sub>2</sub> decreases, that for V-TiO<sub>2</sub> shows the highest

at 1.0 atom% and that for Cr-TiO<sub>2</sub> slightly decreases, indicating a similar tendency as the M-TiO<sub>2</sub> powder (Fig. 1). The amount of photocatalyst can be changed by using different coating methods. Fig. 9 shows the degradation of CH<sub>3</sub>CHO on Cr-TiO<sub>2</sub>-TK, Cr-TiO<sub>2</sub>-SC ( $n = 5$ ), and Cr-TiO<sub>2</sub>-DC, in which the content of Cr ion is 0.8 atom%. Under the irradiation of LED of 6.5 mW cm<sup>-2</sup>, the most transparent Cr-TiO<sub>2</sub>-DC film shows the slowest degradation rate ( $r_0 = 0.295$  ppmv min<sup>-1</sup>) and the Cr-TiO<sub>2</sub>-SC ( $n = 5$ ) exhibits 1.35 ppmv min<sup>-1</sup> which is higher by a factor of 4.6. Such a high degradation rate is obtained with the Cr-TiO<sub>2</sub>-TK film even under the LED intensity of 0.1 mW cm<sup>-2</sup>. A tolerable concentration of CH<sub>3</sub>CHO in air has been evaluated to be 300  $\mu$ g m<sup>-3</sup> by World Health Organization,<sup>38</sup> which is equivalent to 0.17 ppmv at 25 °C. The Cr-TiO<sub>2</sub> film can be used to degrade CH<sub>3</sub>CHO in indoor air by changing the film thickness and the LED intensity depending on the degree of the indoor contamination.

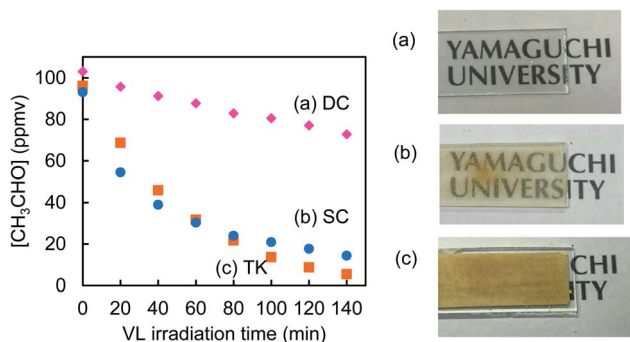


Fig. 9 Photocatalytic degradation of CH<sub>3</sub>CHO on (a) Cr-TiO<sub>2</sub>-DC and (b) Cr-TiO<sub>2</sub>-SC ( $n = 5$ ) films under the irradiation of LED (6.5 mW cm<sup>-2</sup>) and on (c) Cr-TiO<sub>2</sub>-TK film under LED (0.1 mW cm<sup>-2</sup>).

## Conclusions

This study has demonstrated that chromium ion is the best dopant among ten different metal ions for the degradation of CH<sub>3</sub>CHO under white LED irradiation because Cr-TiO<sub>2</sub> exhibits high photocatalytic activity over a wide range of the doping amount. Furthermore, the physicochemical property and the photocatalytic activity of Cr-TiO<sub>2</sub>, Pt-TiO<sub>2</sub> and V-TiO<sub>2</sub> were compared. We prepared these photocatalysts by conducting the dialysis in the sol-gel synthesis. This synthetic method enables us to elucidate the true effect of the metal ion dopants because a homogeneous aqueous sol containing TiO<sub>2</sub> nanoparticles and



metal ions is dried and sintered after all impurities are removed by the dialysis. Furthermore, metal ions having similar ionic size as Ti(IV) interact with TiO<sub>2</sub> nanoparticles because they remain but larger metal ions such as Cu(II) are lost in the TiO<sub>2</sub> sol during the dialysis. Our findings indicate that the different dependence of the degradation rate of CH<sub>3</sub>CHO on the doping amounts of Cr–TiO<sub>2</sub>, Pt–TiO<sub>2</sub> and V–TiO<sub>2</sub> is attributable to their main valence states which are correlated with the formation of the oxygen vacancies. Recently, the oxygen vacancies have attracted much attention because they are believed to play an important role to improve the photocatalytic activity. They can be created by sintering TiO<sub>2</sub> at high temperatures in an oxygen-poor atmosphere but disappear slowly when being exposed to air.<sup>28</sup> However, it is very difficult to discuss the oxygen vacancies in TiO<sub>2</sub> doped with other elements because crystal lattice might be distorted by forming several point defects such as Ti interstitial, oxygen vacancies, and interstitial or substitutional impurities including dopant ions. The present results suggest that Cr(III) in Cr–TiO<sub>2</sub> stabilizes the formation of oxygen vacancies. The Cr–TiO<sub>2</sub> powder synthesized in this study might be promising to elucidate the role of oxygen vacancies in photocatalysis.

## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

This work was supported by JSPS KAKENHI Grant 18K05298. We thank Yamaguchi University Science Research Center for the ICP-OES and XRD measurements. We appreciate Mr T. Tonosaki for the technical support on the XPS measurements at Collaborative Center for Engineering Research Equipment, Faculty of Engineering, Yamaguchi University.

## Notes and references

- 1 E. S. Karafas, M. N. Romanias, V. S. Stefanopoulos, V. Binas, A. Zachopoulos, G. Kiriakidis and P. Papagiannakopoulos, *J. Photochem. Photobiol., A*, 2019, **371**, 255–263.
- 2 S. Izadyar and S. Fatemi, *Ind. Eng. Chem. Res.*, 2013, **52**, 10961–10968.
- 3 T. Takigawa, B. Wang, Y. Saijo, K. Morimoto, K. Nakayama, M. Tanaka, E. Shibata, T. Yoshimura, H. Chikara, K. Ogino and R. Kishi, *Int. Arch. Occup. Environ. Health*, 2010, **83**, 225–235.
- 4 F. Salvadores, R. I. Minen, J. Carballada, O. M. Alfano and M. M. Ballari, *Chem. Eng. Technol.*, 2016, **39**, 166–174.
- 5 H. Ichimura, T. Seike and A. Kozu, *Chemosphere*, 2020, **256**, 127143.
- 6 S. Weon and W. Choi, *Environ. Sci. Technol.*, 2016, **50**, 2556–2563.
- 7 V. Kumar, Y. Lee, J. Shin, K. Kim, D. Kukkar and Y. F. Tsang, *Environ. Int.*, 2020, **135**, 105356.
- 8 I. Bravo, F. Figueroa, M. I. Swasy, M. F. Attia, M. Ateia, D. Encalada, K. Vizueté, S. Galeas, V. H. Guerrero, A. Debut, D. C. Whitehead and F. Alexis, *RSC Adv.*, 2020, **10**, 7967–7975.
- 9 W. Qu, P. Wang, M. Gao, J. Hasegawa, Z. Shen, Q. Wang, R. Li and D. Zhang, *Environ. Sci. Technol.*, 2020, **54**, 9693–9701.
- 10 R. Magudieswaran, J. Ishii, K. Chandar, N. Raja, C. Terashima, R. Venkatachalam, A. Fujishima and S. Pitchaimuthu, *Mater. Lett.*, 2019, **239**, 40–44.
- 11 A. H. Mamaghani, F. Haghighat and C. Lee, *Chemosphere*, 2019, **219**, 804–825.
- 12 I. Wysocka, A. Markowska-Szczupak, P. Szweda, J. Ryl, M. Endo-Kimura, E. Kowalska, G. Nowaczyk and A. Zielinska-Jurek, *Indoor Air*, 2019, **29**, 979–992.
- 13 V. Menendez-Flores and T. Ohno, *Catal. Today*, 2014, **230**, 214–220.
- 14 X. Yang, C. Cao, K. Hohn, L. Erickson, R. Maghirang, D. Hamal and K. Klabunde, *J. Catal.*, 2007, **252**, 296–302.
- 15 N. Nishiyama, Y. Fujiwara, K. Adachi, K. Inumaru and S. Yamazaki, *Appl. Catal., B*, 2015, **176–177**, 347–353.
- 16 S. Yamazaki, D. Takaki, N. Nishiyama, and Y. Yamazaki, in *Current Developments in Photocatalysis and Photocatalytic Materials*, ed. X. Wang, M. Anpo, and X. Fu, Elsevier, 2019, pp. 23–38.
- 17 P. Makula, M. Pacia and W. Macyk, *J. Phys. Chem. Lett.*, 2018, **9**, 6814–6817.
- 18 T. T. Loan, V. H. Huong, V. T. Tham and N. N. Long, *Phys. B*, 2018, **532**, 210–215.
- 19 X. Yu, J. Xie, H. Dong, Q. Liu and Y. Li, *Chem. Phys. Lett.*, 2020, **754**, 137732.
- 20 S. P. Takle, O. A. Apine, J. D. Ambekar, S. L. Landge, N. N. Bhujbal, B. B. Kale and R. S. Sonawane, *RSC Adv.*, 2019, **9**, 4226–4238.
- 21 G. Rossi, L. Pasquini, D. Catone, A. Piccioni, N. Patelli, A. Paladini, A. Molinari, S. Caramori, P. O’Keeffe and F. Boscherini, *Appl. Catal., B*, 2018, **237**, 603–612.
- 22 S. Kim, S. Hwang and W. Choi, *J. Phys. Chem. B*, 2005, **109**, 24260–24267.
- 23 R. D. Shannon, *Acta Crystallogr., Sect. A: Cryst. Phys., Diffraction, Theor. Gen. Crystallogr.*, 1976, **32**, 751–767.
- 24 X. Chen, C. Meng, Y. Wang, Q. Zhao, Y. Li, X. Chen, D. Yang, Y. Li and Y. Zhou, *ACS Sustainable Chem. Eng.*, 2020, **8**, 1095–1101.
- 25 F. Yang, R. Yang, L. Yan, X. Liu, X. Luo and L. Zhang, *Catal. Sci. Technol.*, 2020, **10**, 5659–5665.
- 26 J. Li, H. Zhuo, Z. Wei, G. Zhuang, X. Zhong, S. Deng, X. Li and J. Wang, *J. Mater. Chem. A*, 2018, **6**, 2264–2272.
- 27 B. B. Adormaa, W. K. Darkwah and Y. Ao, *RSC Adv.*, 2018, **8**, 33551–33563.
- 28 Q. Wu, Q. Zheng and R. Krol, *J. Phys. Chem. C*, 2012, **116**, 7219–7226.
- 29 A. Naldoni, M. Altomare, G. Zoppellaro, N. Liu, S. Kment, R. Zboril and P. Schmuki, *ACS Catal.*, 2019, **9**, 345–364.
- 30 F. Ren, H. Li, Y. Wang and J. Yang, *Appl. Catal., B*, 2015, **176–177**, 160–172.
- 31 N. Nishiyama and S. Yamazaki, *ACS Omega*, 2017, **2**, 9033–9039.
- 32 B. D. Mukri, U. V. Waghmare and M. S. Hegde, *Chem. Mater.*, 2013, **25**, 3822–3833.

- 33 W. Kim, T. Tachikawa, H. Kim, N. Lakshminarasimhan, P. Murugan, H. Park, T. Majima and W. Choi, *Appl. Catal., B*, 2014, **147**, 642–650.
- 34 M. Takeuchi, J. Deguchi, S. Sakai and M. Anpo, *Appl. Catal., B*, 2010, **96**, 218–223.
- 35 K. Ishibashi, A. Fujishima, T. Watanabe and K. Hashimoto, *Electrochem. Commun.*, 2000, **2**, 207–210.
- 36 H. Li, S. Yin, Y. Wang and T. Sato, *Environ. Sci. Technol.*, 2012, **46**, 7741–7745.
- 37 B. Hauchecorne, D. Terrens, S. Verbruggen, J. A. Martens, H. V. Langenhove, K. Demeestere and S. Lenaerts, *Appl. Catal., B*, 2011, **106**, 630–638.
- 38 World Health Organization, *IPCS Environmental Health Criteria 167, ACETALDEHYDE*, Geneva, 1996.

