


 Cite this: *RSC Adv.*, 2020, 10, 40690

Use of pyrazoles as ligands greatly enhances the catalytic activity of titanium iso-propoxide for the ring-opening polymerization of L-lactide: a cooperation effect†

 Tzu-Fang Wang,^a Someswara Rao Kosuru,^a Shu-Chun Yu,^a Yung-Chi Chang,^a Hsin-Yu Lai,^a Yu-Lun Chang,^a Kuo-Hui Wu,^{b,c} Shangwu Ding^{ad} and Hsuan-Ying Chen^{ib*ade}

Using TiO^iPr_4 with a pyrazole ligand for one-pot LA polymerization improved catalytic activity compared with using TiO^iPr_4 only. At 60 °C, TiO^iPr_4 with $^{\text{fur}}\text{Pz}$ exhibited a higher catalytic activity (approximately 3-fold) than TiO^iPr_4 . At room temperature, TiO^iPr_4 with $^{\text{Bu}}\text{Pz}$ exhibited a higher catalytic activity (approximately 17-fold) than TiO^iPr_4 . High molecular mass PLA ($M_{n,\text{GPC}} = 51\,100$, and $D = 1.10$) could be produced by using TiO^iPr_4 with $^{\text{fur}}\text{Pz}$ in melt polymerization ($[\text{TiO}^i\text{Pr}_4] : [^{\text{fur}}\text{Pz}] = 1000 : 1 : 1$ at 100 °C, 240 min). The crystal structure of $^{\text{Me}}\text{Pz}_2\text{Ti}_2\text{O}^i\text{Pr}_7$ revealed the cooperative activation between two Ti atoms during LA polymerization.

Received 12th September 2020

Accepted 22nd October 2020

DOI: 10.1039/d0ra07824g

rsc.li/rsc-advances

1. Introduction

Petrochemical plastics are extensively used in modern society; however, widely discarded plastic waste pollutes the environment continually^{1–4} because bacteria cannot decompose it naturally within a short period. To accelerate the environmental degradation of polymers, biodegradable polylactide (PLA)^{5–7} has been developed for creating a sustainable society. PLA-based biomaterials are used in various fields^{8–18} because of their biocompatible^{19,20} and permeable²¹ physical properties. One of the methods of PLA synthesis is the Lewis acidic metal-catalyzed ring-opening polymerization (ROP) of cyclic esters.^{22–31}

For biomaterials, metal residuals present in resulting PLA are a serious problem, and using catalysts with non-cytotoxic metals is a straightforward approach to solving this problem. Because of the non-cytotoxic property and strong Lewis acidity of titanium, Ti

complexes^{22,23,30–33} are commonly used catalysts in LA ROP. Numerous Ti complexes bearing various ligands such as calix[4] arene,^{33,34} Schiff base,^{35–39} salen,^{40–42} salan,^{43–46} phenolate,^{47–50} aminophenolate,^{51,52} benzotriazole phenolate,^{53–55} phosphinophenolate,⁵⁶ thiophenolate,^{57,58} bis-phenolate-N-heterocyclic carbene,⁴⁵ pyridonate,^{59,60} and pyrrolide⁶¹ have been reported to exhibit considerable catalytic activity or controllability, which is contributed by ligands. However, for most studies, focusing on materials is inconvenient, because the synthesis and purification of Ti catalysts are time-consuming processes. An efficient method of fabricating PLA without time-consuming Ti catalyst-base synthesis and purification is necessary. Herein, commercially available Ti alkoxides was also used catalysts for cyclic esters polymerization.^{62–65} Recently, dinuclear Ti complexes³⁸ bearing hydrazine-bridging Schiff base ligands (Fig. 1) were reported to exhibit

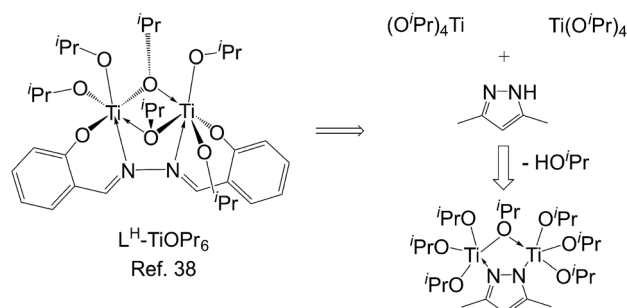


Fig. 1 Strategy of dinuclear Ti complexes in LA polymerization inspired by the literature.

^aDepartment of Medicinal and Applied Chemistry, Drug Development and Value Creation Research Center, Kaohsiung Medical University, Kaohsiung, Taiwan, 80708, Republic of China. E-mail: hchen@kmu.edu.tw; Fax: +886-7-3125339; Tel: +886-7-3121101 ext. 2585

^bDepartment of Chemistry, Graduate School of Science, The University of Tokyo, Tokyo 113-0033, Japan

^cDepartment of Chemistry, Tamkang University, Tamsui 251, Taiwan, Republic of China

^dDepartment of Chemistry, National Sun Yat-sen University, Kaohsiung, Taiwan, 80424, Republic of China

^eDepartment of Medical Research, Kaohsiung Medical University Hospital, Kaohsiung 80708, Taiwan, Republic of China

† Electronic supplementary information (ESI) available. CCDC 1568213. For ESI and crystallographic data in CIF or other electronic format see DOI: 10.1039/d0ra07824g



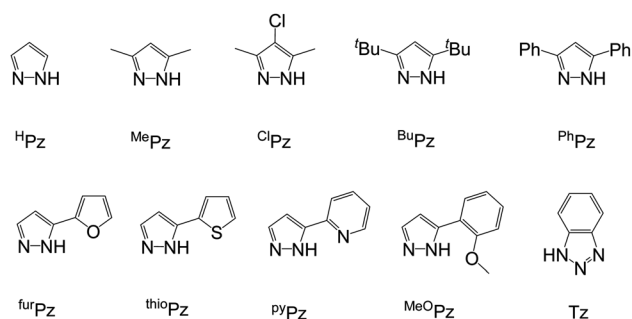


Fig. 2 Pyrazole derivatives used in this study.

a high catalytic activity of LA polymerization because of the cooperation between two Ti atoms. Based on this study, if pyrazole is added to LA polymerization with titanium iso-propoxide (TiO^iPr_4) as a catalyst, bringing two Ti atoms close together to enable dinuclear cooperation is possible. Following this strategy, several pyrazole derivatives (Fig. 2) were added to LA polymerization with a TiO^iPr_4 catalyst to investigate dinuclear cooperation relative to the mixture of TiO^iPr_4 and pyrazole.

2. Experimental section

2.1 Chemicals

Standard Schlenk techniques and a N_2 -filled glovebox were used all over the isolation and treatment of all the compounds. Solvents, L-lactide (LA), and deuterated solvents were purified prior to use. LA,

$^i\text{H}\text{Pz}$, $^{\text{Me}}\text{Pz}$, $^{\text{Bu}}\text{Pz}$, $^{\text{Ph}}\text{Pz}$, $^{\text{fur}}\text{Pz}$, $^{\text{thio}}\text{Pz}$, Tz, $^{\text{py}}\text{Pz}$, and $^{\text{MeO}}\text{Pz}$ were purchased from Aldrich. $^{\text{Cl}}\text{Pz}$ ⁶⁶ were prepared following literature procedures. ^1H and ^{13}C NMR spectra were recorded on a Varian Gemini 2000-200 (200 MHz for ^1H and 50 MHz for ^{13}C) spectrometer. Chemical shifts (in ppm) of ^1H NMR spectra were referenced to tetramethylsilane ($\delta = 0$ ppm) in CDCl_3 as an internal standard, and chemical shifts of ^{13}C NMR spectra were reported in ppm referenced to the center line of a triplet at 77.0 ppm of CDCl_3 . Microanalyses were performed using a Heraeus CHN-O-RAPID instrument. The gel permeation chromatography (GPC) measurements were performed on a Jasco PU-2080 PLUS HPLC pump system equipped with a differential Jasco RI-2031 PLUS refractive index detector using THF (HPLC grade) as an eluent (flow rate 1.0 mL min^{-1} , at 40°C). The chromatographic column was JORDI Gel DVB 10^{-3} \AA , and the calibration curve was made by primary polystyrene standards to calculate molar masses of PLA. Values of $M_{n,\text{GPC}}$ were obtained through gel permeation chromatography (GPC) times 0.58.

2.2 Synthesis of $^{\text{Me}}\text{Pz}_2\text{Ti}_2\text{O}^i\text{Pr}_7$

A mixture of $^{\text{Me}}\text{Pz}$ (0.96 g, 10 mmol) and TiO^iPr_4 (2.84 g, 10 mmol) in toluene (20 mL), was stirred at room temperature for 24 h. Volatile materials were removed under vacuum to give light yellow mud, and then hexane was transferred to be the suspension. The light-yellow powder was obtained after filtering, and was recrystallized in toluene to form the crystal. Yield: 1.15 g (33%). ^1H NMR spectrum (CDCl_3 , 200 MHz, Fig. S1†) was complex, but it could be assigned that two β -Hs were at 5.59 and 5.43 ppm, and the methine protons of

Table 1 L-Lactide polymerization with the mixture of TiO^iPr_4 and pyrazole derivatives as catalysts in toluene^a

Entry	Ligand ($\text{TiO}^i\text{Pr}_4 : \text{L}$)	Time (min)	Conv. ^b (%)	$M_{n,\text{GPC}}^c$ (g mol^{-1})	$M_{n,\text{NMR}}^b$ (g mol^{-1})	D^c	k_{obs} (min^{-1})
1 ^d	$^{\text{thio}}\text{Pz}$ (1 : 0.5)	50	85	3900	3300	1.30	0.035
2 ^d	$^{\text{thio}}\text{Pz}$ (1 : 1)	45	86	4700	4600	1.51	0.036
3 ^d	$^{\text{thio}}\text{Pz}$ (1 : 2)	125	84	7000	6000	2.10	0.008
4 ^d	$^{\text{thio}}\text{Pz}$ (1 : 4)	220	99	7400	6500	2.02	0.013
5	$^{\text{thio}}\text{Pz}$ (1 : 1)	10	87	2300	2200	1.27	0.232
6	L free	22	92	2100	1600	1.75	0.161
7	$^{\text{H}}\text{Pz}$ (1 : 1)	8	88	2600	2100	1.31	0.285
8	$^{\text{Me}}\text{Pz}$ (1 : 1)	13	94	7100	4400	1.68	0.233
9	$^{\text{Cl}}\text{Pz}$ (1 : 1)	14	89	1900	1800	1.13	0.166
10	$^{\text{Bu}}\text{Pz}$ (1 : 1)	9	95	2100	1700	1.23	0.394
11	$^{\text{Ph}}\text{Pz}$ (1 : 1)	10	94	2500	2000	1.25	0.334
12	$^{\text{fur}}\text{Pz}$ (1 : 1)	5	86	2200	2100	1.23	0.418
13	$^{\text{py}}\text{Pz}$ (1 : 1)	15	88	2000	2200	1.18	0.152
14	$^{\text{MeO}}\text{Pz}$ (1 : 1)	10	92	6500	3000	1.38	0.288
15	Tz (1 : 1)	20	87	1900	1800	1.12	0.120
16 ^e	$^{\text{Me}}\text{Pz}$ (1 : 1)	16	88	1800	1700	1.10	—
17 ^f	$^{\text{Me}}\text{Pz}$ (1 : 1)	25	89	3900	3600	1.27	—
18 ^g	$^{\text{Me}}\text{Pz}$ (1 : 1)	24	80	5500	5200	1.27	—
19 ^h	$^{\text{Me}}\text{Pz}$ (1 : 1)	45	87	8500	7900	1.32	—
20 ⁱ	$^{\text{Me}}\text{Pz}$ (1 : 1)	95	90	13 100	12 500	1.49	—
21 ^j	$^{\text{L}}\text{H-TiO}^i\text{Pr}_6$ ³⁸	50	89	3100	—	1.25	0.065

^a In general, the reaction was carried out in 5 mL toluene with $[\text{LA}] = 2 \text{ M}$ at 60°C for LA polymerization ($[\text{LA}] : [\text{TiO}^i\text{Pr}_4] = 50 : 1$). ^b The data were determined using ^1H NMR analysis. ^c Values of $M_{n,\text{GPC}}$ were corrected considering Mark-Houwink factor (0.58) from polystyrene standards in THF. ^d $[\text{LA}] = 1 \text{ M}$, in 5 mL toluene, $[\text{LA}] : [\text{TiO}^i\text{Pr}_4] = 100 : 1$. ^e $[\text{LA}] : [\text{TiO}^i\text{Pr}_4] : [^{\text{Me}}\text{Pz}] = 50 : 1 : 1$, $[\text{TiO}^i\text{Pr}_4] = 13.4 \text{ mM}$ in toluene 15 mL. ^f $[\text{LA}] : [\text{TiO}^i\text{Pr}_4] : [^{\text{Me}}\text{Pz}] = 100 : 1 : 1$, $[\text{TiO}^i\text{Pr}_4] = 13.4 \text{ mM}$ in toluene 15 mL. ^g $[\text{LA}] : [\text{TiO}^i\text{Pr}_4] : [^{\text{Me}}\text{Pz}] = 150 : 1 : 1$, $[\text{TiO}^i\text{Pr}_4] = 13.4 \text{ mM}$ in toluene 15 mL. ^h $[\text{LA}] : [\text{TiO}^i\text{Pr}_4] : [^{\text{Me}}\text{Pz}] = 200 : 1 : 1$, $[\text{TiO}^i\text{Pr}_4] = 13.4 \text{ mM}$ in toluene 15 mL. ⁱ $[\text{LA}] : [\text{TiO}^i\text{Pr}_4] : [^{\text{Me}}\text{Pz}] = 300 : 1 : 1$, $[\text{TiO}^i\text{Pr}_4] = 13.4 \text{ mM}$ in toluene 15 mL. ^j $[\text{LA}] : [^{\text{L}}\text{H-TiO}^i\text{Pr}_6] = 100 : 1$, $[\text{LA}] = 2.0 \text{ mM}$ in toluene 5 mL at 60°C .



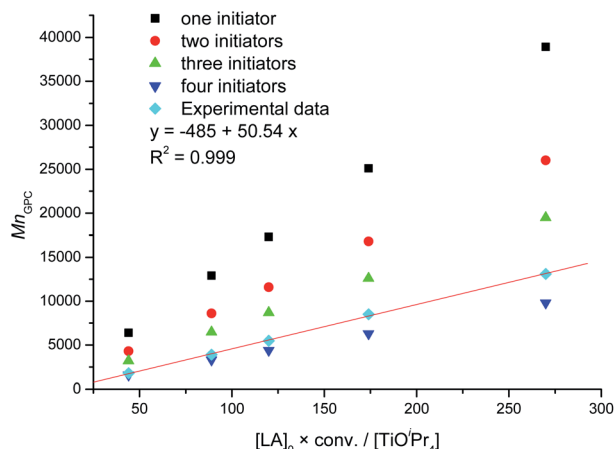


Fig. 3 Linear plot of various $M_{n,cal}$ with the supposed initiators and $M_{n,gpc}$ against $[LA]_0 \times \text{conv.} / [TiO^iPr_4]$ (Table 1, entries 16–20).

isopropyl oxide were at 4.92–4.28 ppm, and dimethyl groups of $MePz$ were at 2.39 and 2.14 ppm.

3. Results and discussion

3.1 Polymerization of LA

Table 1 presents the conditions for optimizing LA polymerization by using a mixture of TiO^iPr_4 and $thioPz$ as the catalyst. Entries 1–5 in Table 1 reveal that the 1 : 1 ratio of TiO^iPr_4 and

$thioPz$ ($[LA] = 1$ M, $[TiO^iPr_4] = 10$ mM) exhibited the fastest polymerization rate. When $[LA]$ was increased to 2 M with 40 mM of $[TiO^iPr_4]$, after 10 min, the conversion became 87%. Under this condition ($[LA] = 2$ M, $[LA] : [TiO^iPr_4] : [thioPz] = 50 : 1 : 1$ in 5 mL toluene), various pyrazole derivatives were used to analyze LA polymerization, and all pyrazole derivatives improved the catalytic activity of TiO^iPr_4 , except $pyPz$ and Tz in the following order: $furPz > BuPz > PhPz > MeOPz > H^iPz > MePz = thioPz > ClPz > pyPz > Tz$. Although $MePz$ improved the catalytic activity of TiO^iPr_4 , it provided low controllability (dispersity, $D = 1.68$). To solve this problem, the TiO^iPr_4 concentration was decreased from 20 to 13.4 mM, and the D value was decreased to 1.10. LA polymerization using TiO^iPr_4 (13.4 mM) as a catalyst with $MePz$ was systematically investigated with the $[LA]/[TiO^iPr_4]$ ratio ranging from 50 to 300 (entries 16–20). The results revealed that LA polymerization was controllable, confirmed by the linear relationship between $[LA]_0/[TiO^iPr_4]$ and $M_{n,gpc}$ (Fig. 3). However, the controllability in the $[LA]/[TiO^iPr_4]$ ratio of 300 ($D = 1.49$, entry 20 in Table 1) was low, and it may be ascribed to transesterification⁶⁷ because of the long polymerization time at 60 °C. Fig. 3 revealed that four isopropoxides of TiO^iPr_4 could be initiators to initiate LA. TiO^iPr_4 with $thioPz$ exhibited a higher catalytic activity (3.5 folds) in LA polymerization than $L^H-TiOPr_6$ (entry 21)³⁸ did.

A survey of LA ROP using Ti complexes as catalysts revealed that few Ti catalysts could polymerize LA at room temperature. Therefore, LA polymerization was conducted at room temperature (Table

Table 2 L-Lactide polymerization with the mixture of TiO^iPr_4 and pyrazole derivatives as catalysts in CH_2Cl_2 at room temperature^a

Entry	Ligand ($TiO^iPr_4 : L$)	Time (min)	Conv. ^b (%)	$M_{n,gpc}$ ^c (g mol ⁻¹)	$M_{n,NMR}$ ^b (g mol ⁻¹)	D^f	$k_{obs} \times 10^3$ (min ⁻¹)
1	L free	4290	85	1600	1700	1.25	0.3
2	H^iPz	450	80	900	1000	1.12	3.0
3	$MePz$	1670	85	1300	1200	1.08	0.9
4	$ClPz$	720	85	1100	1200	1.08	2.0
5	$BuPz$	370	88	1100	1000	1.07	5.0
6	$PhPz$	1335	89	1400	1200	1.12	1.0
7	$furPz$	540	90	1000	1100	1.08	4.0
8	$thioPz$	660	84	1200	1200	1.08	2.0
9	$pyPz$	660	87	1000	1100	1.08	2.4
10	$MeOPz$	660	85	1200	1200	1.08	2.0
11	Tz	1670	87	1400	1300	1.11	0.7
12 ^d	$furPz$	315	95	1400	1200	1.08	—
13 ^e	$furPz$	310	88	1600	1500	1.09	—
14 ^f	$furPz$	450	88	1800	1800	1.11	—
15 ^g	$furPz$	510	89	2100	2200	1.27	—
16 ^h	$furPz$	390	84	700	800	1.13	—
17 ⁱ	+100 LA	895	92	1800	1900	1.09	—
18 ^j	+100 LA	1495	83	2300	2200	1.16	—
19 ^k	+100 LA	2000	72	2600	2600	1.14	—
20 ^l	$furPz$	240	93	51 100	—	1.10	—
21 ^m	L free	240	52	31 600	—	1.26	—

^a In general, the reaction was carried out in 2.5 mL CH_2Cl_2 with $[LA] = 2$ M at room temperature for LA polymerization ($[LA] : [TiO^iPr_4] = 25 : 1$).

^b The data were determined using 1H NMR analysis. ^c Values of $M_{n,gpc}$ were corrected considering Mark–Houwink factor (0.58) from polystyrene standards in THF. ^d $[LA] : [TiO^iPr_4] : [furPz] = 37.5 : 1 : 1$, $[TiO^iPr_4] = 0.08$ M in 2.5 mL CH_2Cl_2 . ^e $[LA] : [TiO^iPr_4] : [furPz] = 43.75 : 1 : 1$, $[TiO^iPr_4] = 0.08$ M in 2.5 mL CH_2Cl_2 . ^f $[LA] : [TiO^iPr_4] : [furPz] = 50 : 1 : 1$, $[TiO^iPr_4] = 0.08$ M in 2.5 mL CH_2Cl_2 . ^g $[LA] : [TiO^iPr_4] : [furPz] = 62.5 : 1 : 1$, $[TiO^iPr_4] = 0.08$ M in 2.5 mL CH_2Cl_2 . ^h $[LA] : [TiO^iPr_4] : [furPz] = 25 : 1 : 1$, $[TiO^iPr_4] = 0.08$ M in 2.5 mL $CDCl_3$. ⁱ After the conversion of the reaction (entry 16) was 84%, LA (0.72 g) was transferred into the solution. ^j After the conversion of the reaction (entry 17) was 92%, LA (0.72 g) was transferred into the solution. ^k After the conversion of the reaction (entry 17) was 83%, LA (0.72 g) was transferred into the solution. ^l $[TiO^iPr_4] : [furPz] = 1000 : 1 : 1$, melt reaction at 100 °C. ^m $[LA] : [TiO^iPr_4] = 1000 : 1$, melt reaction at 100 °C.



2) to determine whether the addition of pyrazole ligands can enhance the catalytic ability of TiO^iPr_4 at room temperature. In addition, reducing the polymerization temperature may improve the controllability of Ti catalysts.

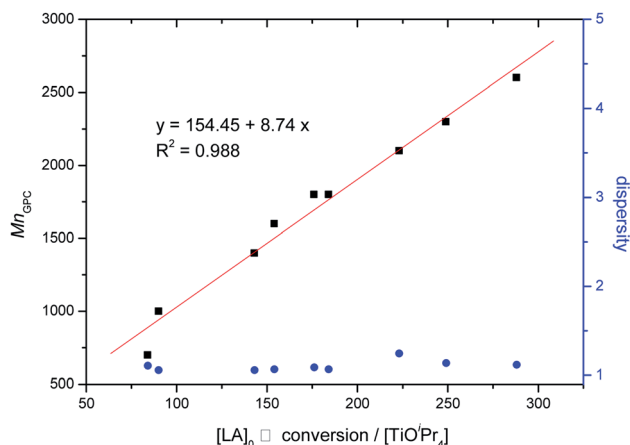


Fig. 4 Linear plots of $M_{n,\text{GPC}}$ versus $([\text{LA}]_0 \times \text{conv.})/[\text{TiO}^i\text{Pr}_4]$. Blue solid dots indicate \bar{D} s.

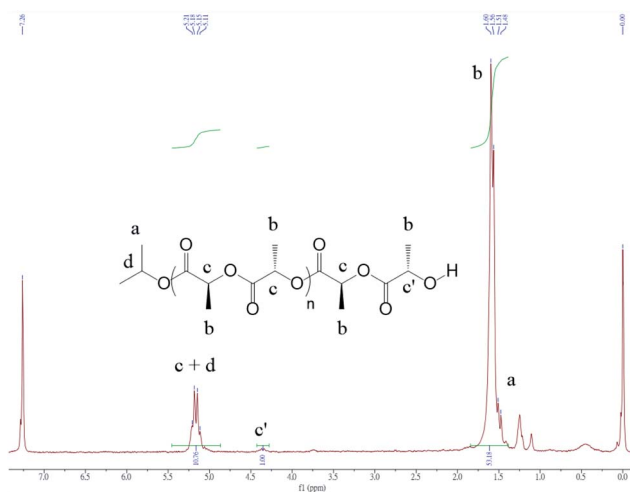


Fig. 5 ^1H NMR spectrum of PLA (entry 13 in Table 2).

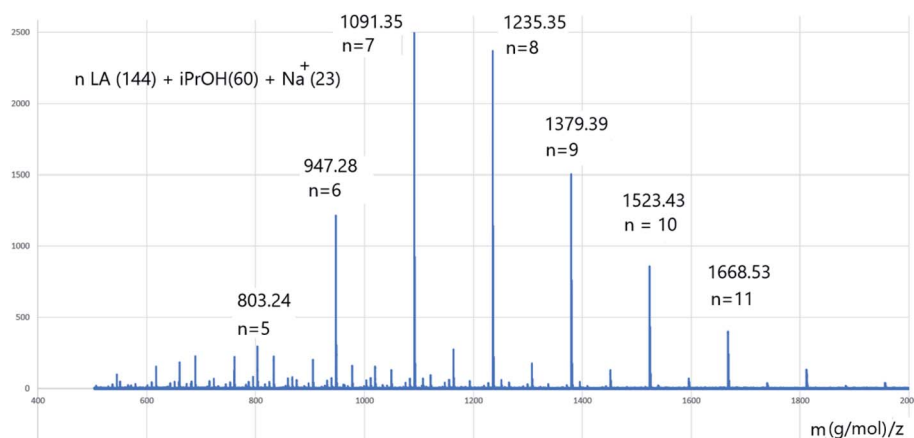


Fig. 6 MALDI-TOF spectrum of PLA (entry 13 in Table 2).

All pyrazole derivatives improved the catalytic activity of TiO^iPr_4 in the following order: $^{\text{Bu}}\text{Pz} > ^{\text{fur}}\text{Pz} > ^{\text{H}}\text{Pz} > ^{\text{py}}\text{Pz} > ^{\text{Cl}}\text{Pz} = ^{\text{thio}}\text{Pz} = ^{\text{MeO}}\text{Pz} > ^{\text{Ph}}\text{Pz} > ^{\text{Me}}\text{Pz} > \text{Tz}$ (Table 2). In the CH_2Cl_2 solution, the pyrazole ligand provided the benefit of considerable improvement of the catalytic reaction. For example, k_{obs} of TiO^iPr_4 with $^{\text{Bu}}\text{Pz}$ was 17 times higher than that of TiO^iPr_4 , and k_{obs} of TiO^iPr_4 with $^{\text{fur}}\text{Pz}$ was 13 times higher than that of TiO^iPr_4 . In addition, the controllability of TiO^iPr_4 with all pyrazole derivatives was improved ($\bar{D} = 1.07\text{--}1.12$). Although TiO^iPr_4 with $^{\text{Bu}}\text{Pz}$ revealed the highest polymerization rate, $^{\text{Bu}}\text{Pz}$ is overly expensive. Therefore, $^{\text{fur}}\text{Pz}$ was used as a ligand with TiO^iPr_4 as a catalyst to polymerize LA with various ratios of $[\text{LA}]/[\text{TiO}^i\text{Pr}_4]$ (entries 12–19, Table 2). The $[\text{LA}]/[\text{TiO}^i\text{Pr}_4]$ ratio from 37.5 to 62.5 was investigated, and the molecular mass ($M_{n,\text{GPC}}$) of PLA increased from 1400 to 2100. According to the solubility of LA in CH_2Cl_2 , the limit of the $[\text{LA}]/[\text{TiO}^i\text{Pr}_4]$ ratio is 62.5 (1.80 g of LA in 2.5 mL CH_2Cl_2), and PLA with high molecular mass PLA cannot be synthesized by increasing the $[\text{LA}]/[\text{TiO}^i\text{Pr}_4]$ ratio.

To investigate the living property^{68,69} of TiO^iPr_4 with the pyrazole ligand in LA polymerization, first, LA was polymerized ($[\text{LA}] : [\text{TiO}^i\text{Pr}_4] : [^{\text{fur}}\text{Pz}] = 100 : 4 : 4$ in CDCl_3 , entry 16 in Table 2). After 390 min, the conversion was 84%, and 100 equivalents of LA were reloaded into the solution (entry 17 in Table 2). However, the polymerization time increased to 895 min with a 92% conversion. Subsequently, 100 equivalents of LA were reloaded into the solution (entry 18 in Table 2), and the polymerization rate decreased. After 1495 min, the conversion was 83%, and 100 equivalents of LA were reloaded into the solution (entry 19 in Table 2). The solution could not be stirred after 2000 min with a 72% conversion. The slower LA polymerization rate can be ascribed to the higher viscosity of the polymerized solution. On the basis of the linear relationship between $M_{n,\text{GPC}}$ and $([\text{LA}]_0 \times \text{conv.})/[\text{TiO}^i\text{Pr}_4]$ (entries 7, and 12–19 in Table 2 and Fig. 4), TiO^iPr_4 with the pyrazole ligand demonstrated a high controllability with narrow \bar{D} for LA polymerization. To confirm that PLA with high molecular mass can be synthesized using TiO^iPr_4 with the pyrazole ligand, LA was polymerized using TiO^iPr_4 with $^{\text{fur}}\text{Pz}$ ($[\text{LA}] : [\text{TiO}^i\text{Pr}_4] : [^{\text{fur}}\text{Pz}] = 1000 : 1 : 1$ at 100 °C without solvent, entry 20 in Table 2). After 240 min, the conversion was 93%, and PLA ($M_{n,\text{GPC}} =$



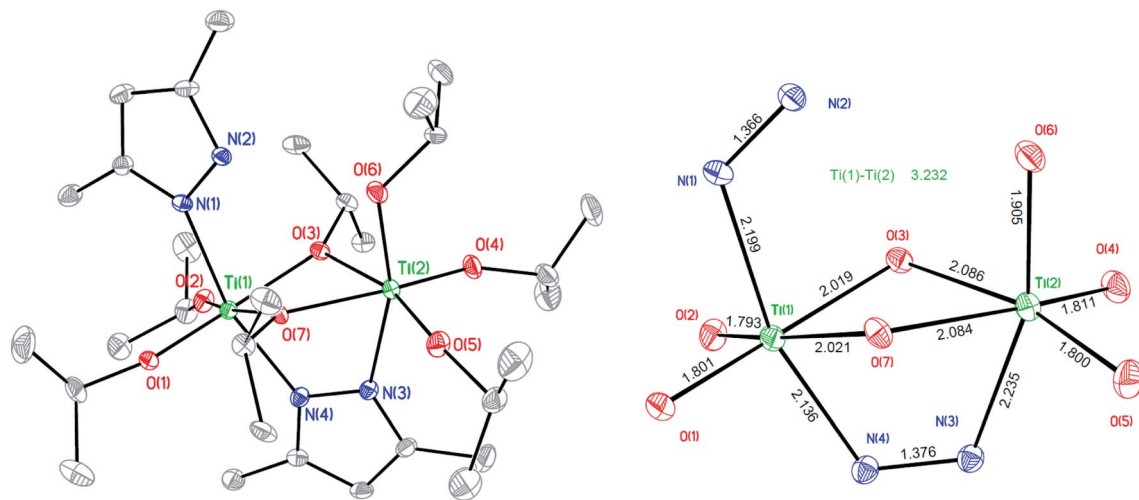


Fig. 7 Molecular plot of $\text{MePz}_2\text{Ti}_2\text{O}^i\text{Pr}_7$ with 20% probability ellipsoids (all hydrogen atoms were omitted for clarity).

51 100, and $D = 1.10$) was obtained. Compared with LA polymerization using TiO^iPr_4 without $\text{f}^{\text{ur}}\text{Pz}$ (240 min, conv. = 52%, $M_{n,\text{GPC}} = 31\ 600$, $D = 1.26$, entry 21 in Table 2), adding $\text{f}^{\text{ur}}\text{Pz}$ to LA polymerization improved the polymerization rate and enhanced the controllability for producing PLA.

The ^1H nuclear magnetic resonance (NMR) spectrum of PLA (entry 2 in Table 2 and Fig. 5) confirmed the presence of one isopropyl oxide group (peak a) and a hydroxyl chain end (peak c'), suggesting that initiation occurred through insertion of an isopropyl oxide into LA. The matrix-assisted laser desorption/ionization time-of-flight (MALDI-TOF) mass spectrum of PLA (entry 5 in Table 2 and Fig. 6) revealed the presence of isopropyl oxide group at the end of the PLA chain.

3.2 Synthesis and characterization of $\text{MePz}_2\text{Ti}_2\text{O}^i\text{Pr}_7$

To determine what was the real catalysis mechanism in the polymerization process, the reaction of MePz and TiO^iPr_4 (1 : 1) in toluene was investigated. Fig. 7 illustrates the crystal of $\text{MePz}_2\text{Ti}_2\text{O}^i\text{Pr}_7$ (CCDC 1568213, Table S4†). However, the ^1H NMR spectrum (Fig. S3†) revealed that $\text{MePz}_2\text{Ti}_2\text{O}^i\text{Pr}_7$ was impure. The crystal data of $\text{MePz}_2\text{Ti}_2\text{O}^i\text{Pr}_7$ indicated that the Ti-Ti distance was 3.2322(14) Å, which is slightly shorter than that of $\text{L}^{\text{Bu}}\text{-TiOPr}_6$ ³⁸ distance (3.242 Å), and it implied the cooperative activation can occur in this system. To prove that $\text{MePz}_2\text{Ti}_2\text{O}^i\text{Pr}_7$ is the real catalyst in LA polymerization, the crystal of impure $\text{MePz}_2\text{Ti}_2\text{O}^i\text{Pr}_7$ was used as a catalyst in LA polymerization with the polymerization condition of entry 17 of Table 1 ([LA] : [$\text{MePz}_2\text{Ti}_2\text{O}^i\text{Pr}_7$] = 100 : 0.5, [$\text{MePz}_2\text{Ti}_2\text{O}^i\text{Pr}_7$] = 6.7 mM at 60 °C in 15 mL toluene). After 16 min, the conversion was 95% with $M_{n,\text{GPC}} = 4900$, $D = 1.56$, and $k_{\text{obs}} = 0.203$ (min^{-1}), and the results were similar to the results of entry 17 of Table 1 (conversion was 89% after 25 min).

4. Conclusions

Our strategy of using TiO^iPr_4 with pyrazole ligand for one-pot LA polymerization successfully improved the catalytic activity

compared with using TiO^iPr_4 only. The crystal structure of $\text{MePz}_2\text{Ti}_2\text{O}^i\text{Pr}_7$ revealed cooperative activation between two Ti atoms during LA polymerization. These results can provide a straightforward approach to synthesize PLA by using TiO^iPr_4 as a catalyst. In future, we intend to investigate the mechanism of LA polymerization.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

This study was supported by the Ministry of Science and Technology of Taiwan (Grant MOST 108-2113-M-037-017) and Kaohsiung Medical University (NSYSUKMU 107-P010 and KMU-DK109004). We thank the Centre for Research Resources and Development at Kaohsiung Medical University for instrumentation and equipment support.

Notes and references

- 1 Y. Mato, T. Osobe, H. Takada, H. Kanehiro, C. Ohtake and T. Kaminuma, *Environ. Sci. Technol.*, 2001, **35**, 318–324.
- 2 D. S. Green, B. Boots, D. J. Blockley, C. Rocha and R. Thompson, *Environ. Sci. Technol.*, 2015, **49**, 5380–5389.
- 3 J. R. Jambeck, R. Geyer, C. Wilcox, T. R. Sieglar, M. Perryman, A. Andrady, R. Narayan and K. L. Law, *Science*, 2015, **347**, 768–771.
- 4 J. Lamb, B. L. Willis, E. A. Fioiorenza, C. S. Couch, R. Howard, D. N. Rader, J. D. True, L. A. Kelly, A. Ahmad, J. Jompa and C. D. Harvell, *Science*, 2018, **359**, 460–462.
- 5 A. P. Gupta and V. Kumar, *Eur. Polym. J.*, 2007, **43**, 4053–4074.
- 6 M. Skotak, A. P. Leonov, G. Larsen, S. Noriega and A. Subramanian, *Biomacromolecules*, 2008, **9**, 1902–1908.



- 7 Y. Zhu, C. Romain and C. K. Williams, *Nature*, 2016, **540**, 354–362.
- 8 N. Kamaly, B. Yameen, J. Wu and O. C. Farokhzad, *Chem. Rev.*, 2016, **116**, 2602–2663.
- 9 K. Liu, X. Jiang and P. Hunziker, *Nanoscale*, 2016, **8**, 16091–16156.
- 10 C. G. Palivan, R. Goers, A. Najer, X. Zhang, A. Car and W. Meier, *Chem. Soc. Rev.*, 2016, **45**, 377–411.
- 11 J. Y. Park, G. Gao, J. Jang and D.-W. Cho, *J. Mater. Chem. B*, 2016, **4**, 7521–7539.
- 12 S. K. Shukla, S. K. Shukla, P. P. Govender and N. G. Giri, *RSC Adv.*, 2016, **6**, 94325–94351.
- 13 A. U. Birnin-Yauri, N. A. Ibrahim, N. Zainuddin, K. Abdan, Y. Y. Then and B. W. Chieng, *Polymers*, 2017, **9**, 165.
- 14 S. Medel, Z. Syrova, L. Kovacic, J. Hrdy, M. Hornacek, E. Jager, M. Hruby, R. Lund, D. Cmarko, P. Stepanek, I. Raska and B. Nyström, *Eur. Polym. J.*, 2017, **93**, 116–131.
- 15 A. Watts, N. Kurokawa and M. A. Hillmyer, *Biomacromolecules*, 2017, **18**, 1845–1854.
- 16 C. Xiang and N. C. Acevedo, *Polymers*, 2017, **9**, 179.
- 17 S. Bhowmick, A. V. Thanusha, A. Kumar, D. Scharnweber, S. Rother and V. Koul, *RSC Adv.*, 2018, **8**, 16420–16432.
- 18 B. Slater, S. O. Wong, A. Duckworth, A. J. P. White, M. R. Hill and B. P. Ladewig, *Chem. Commun.*, 2019, **55**, 7319–7322.
- 19 M. A. Woodruff and D. W. Hutmacher, *Prog. Polym. Sci.*, 2010, **35**, 1217–1256.
- 20 Y. Ramot, M. Haim-Zada, A. J. Domb and A. Nyska, *Adv. Drug Delivery Rev.*, 2016, **107**, 153–162.
- 21 F. Carosio, S. Colonna, A. Fina, G. Rydzek, J. Hemmerlé, L. Jierry, P. Schaaf and F. Boulmedais, *Chem. Mater.*, 2014, **26**, 5459–5466.
- 22 B. H. Huang, C. Y. Tsai, C. T. Chen and B. T. Ko, *Dalton Trans.*, 2016, **45**, 17557–17580.
- 23 C. Redshaw, *Dalton Trans.*, 2016, **45**, 9018–9030.
- 24 Y. Wei, S. Wang and S. Zhou, *Dalton Trans.*, 2016, **45**, 4471–4485.
- 25 Y. A. Chang and R. M. Waymouth, *J. Polym. Sci., Part A: Polym. Chem.*, 2017, **55**, 2892–2902.
- 26 T. Fuoco and D. Pappalardo, *Catalysts*, 2017, **7**, 64.
- 27 K. M. Osten and P. Mehrkhodavandi, *Acc. Chem. Res.*, 2017, **50**, 2861–2869.
- 28 C. Redshaw, *Catalysts*, 2017, **7**, 165.
- 29 R. Ligny, M. M. Hanninen, S. M. Guillaume and J. F. Carpentier, *Chem. Commun.*, 2018, **54**, 8024–8031.
- 30 E. Stirling, Y. Champouret and M. Visseaux, *Polym. Chem.*, 2018, **9**, 2517–2531.
- 31 A. B. Kremer and P. Mehrkhodavandi, *Coord. Chem. Rev.*, 2019, **380**, 35–57.
- 32 M. Chen and C. Chen, *Chin. J. Chem.*, 2020, **38**, 282–286.
- 33 O. Santoro and C. Redshaw, *Catalysts*, 2020, **10**, 210.
- 34 Z. Sun, Y. Zhao, O. Santoro, M. R. J. Elsegood, E. V. Bedwell, K. Zahra, A. Walton and C. Redshaw, *Catal. Sci. Technol.*, 2020, **10**, 1619–1639.
- 35 T. K. Saha, M. Mandal, D. Chakraborty and V. Ramkumar, *New J. Chem.*, 2013, **37**, 949.
- 36 J.-X. He, Y.-L. Duan, X. Kou, Y.-Z. Zhang, W. Wang, Y. Yang and Y. Huang, *Inorg. Chem. Commun.*, 2015, **61**, 144–148.
- 37 D. Mandal, D. Chakraborty, V. Ramkumar and D. K. Chand, *RSC Adv.*, 2016, **6**, 21706–21718.
- 38 H. C. Tseng, H. Y. Chen, Y. T. Huang, W. Y. Lu, Y. L. Chang, M. Y. Chiang, Y. C. Lai and H. Y. Chen, *Inorg. Chem.*, 2016, **55**, 1642–1650.
- 39 C. B. Durr and C. K. Williams, *Inorg. Chem.*, 2018, **57**, 14240–14248.
- 40 L. A. Brown, J. L. Rhinehart and B. K. Long, *ACS Catal.*, 2015, **5**, 6057–6060.
- 41 B. Gao, X. Li, R. Duan and X. Pang, *New J. Chem.*, 2015, **39**, 2404–2408.
- 42 R. Duan, Z. Qu, X. Pang, Y. Zhang, Z. Sun, H. Zhang, X. Bian and X. Chen, *Chin. J. Chem.*, 2017, **35**, 640–644.
- 43 S. H. Kim, J. Lee, D. J. Kim, J. H. Moon, S. Yoon, H. J. Oh, Y. Do, Y. S. Ko, J.-H. Yim and Y. Kim, *J. Organomet. Chem.*, 2009, **694**, 3409–3417.
- 44 A. L. Zelikoff, J. Kopilov, I. Goldberg, G. W. Coates and M. Kol, *Chem. Commun.*, 2009, 6804.
- 45 C. Romain, L. Brelot, S. p. Bellemin-Laponnaz and S. Dagorne, *Organometallics*, 2010, **29**, 1191–1198.
- 46 H.-W. Ou, H.-Y. Chen, H.-C. Tseng, M.-W. Hsiao, Y.-L. Chang, N.-Y. Jheng, Y.-C. Lai, T.-Y. Shih, Y.-T. Lin and H.-Y. Chen, *J. Mol. Catal. A: Chem.*, 2014, **394**, 97–104.
- 47 R. R. Gowda, D. Chakraborty and V. Ramkumar, *Eur. J. Inorg. Chem.*, 2009, 2981–2993.
- 48 H. Y. Chen, M. Y. Liu, A. K. Sutar and C. C. Lin, *Inorg. Chem.*, 2010, **49**, 665–674.
- 49 R. R. Gowda, D. Chakraborty and V. Ramkumar, *Inorg. Chem. Commun.*, 2011, **14**, 1777–1782.
- 50 M. T. Jiang, S. R. Kosuru, Y. H. Lee, W. Y. Lu, J. K. Vandavasi, Y. C. Lai, M. Y. Chiang and H. Y. Chen, *eXPRESS Polym. Lett.*, 2018, **12**, 126–135.
- 51 S. L. Hancock, M. F. Mahon and M. D. Jones, *Dalton Trans.*, 2011, **40**, 2033–2037.
- 52 L. C. Liang, S. T. Lin and C. C. Chien, *Inorg. Chem.*, 2013, **52**, 1780–1786.
- 53 M. Jeong Go, J. Min Lee, K. Mun Lee, C. Hwa Oh, K. H. Park, S. H. Kim, M. Kim, H.-R. Park, M. H. Park, Y. Kim and J. Lee, *Polyhedron*, 2014, **67**, 286–294.
- 54 D.-C. Liu, C.-Y. Li, P.-H. Lin, J.-D. Chen, C.-Y. Tsai, C.-H. Lin and B.-T. Ko, *Inorg. Chem. Commun.*, 2018, **90**, 1–7.
- 55 C.-Y. Li, C.-J. Yu and B.-T. Ko, *Organometallics*, 2012, **32**, 172–180.
- 56 L. C. Liang, Y. L. Hsu and S. T. Lin, *Inorg. Chem.*, 2011, **50**, 3363–3372.
- 57 M. Y. Lowe, S. Shu, S. M. Quan and P. L. Diaconescu, *Inorg. Chem. Front.*, 2017, **4**, 1798–1805.
- 58 X. Xu, G. Luo, Z. Hou, P. L. Diaconescu and Y. Luo, *Inorg. Chem. Front.*, 2020, **7**, 961–971.
- 59 R. L. Webster, N. Noroozi, S. G. Hatzikiriakos, J. A. Thomson and L. L. Schafer, *Chem. Commun.*, 2013, **49**, 57–59.
- 60 D. J. Gilmour, R. L. Webster, M. R. Perry and L. L. Schafer, *Dalton Trans.*, 2015, **44**, 12411–12419.
- 61 J. Liu, Y. Cao, L. Li, H. Pei, Y. Chen, J. Hu, Y. Qin, Y. Li, W. Li and W. Liu, *RSC Adv.*, 2015, **5**, 10318–10325.
- 62 Y. Kim, G. K. Jnaneshwara and J. G. Verkade, *Inorg. Chem.*, 2003, **42**, 1437–1447.



- 63 C. J. Chuck, M. G. Davidson, M. D. Jones, G. Kociok-köhn, M. D. Lunn and S. Wu, *Inorg. Chem.*, 2006, **45**, 6595–6597.
- 64 J.-B. Zeng, M. Srinivansan, Y.-D. Li, R. Narayan and Y.-Z. Wang, *J. Polym. Sci., Part A: Polym. Chem.*, 2010, **48**, 5885–5890.
- 65 A. G. Amador, A. Watts, A. E. Neitzel and M. A. Hillmyer, *Macromolecules*, 2019, **52**, 2371–2383.
- 66 F. Malbosc, V. Chauby, C. S.-L. Berre, M. Etienne, J.-C. Daran and P. Kalck, *Eur. J. Inorg. Chem.*, 2001, 2689.
- 67 Y. Yu, E. J. Fischer, G. Storti and M. Morbidelli, *Ind. Eng. Chem. Res.*, 2014, **53**, 7333–7342.
- 68 O. Dechy-Cabaret, B. Martin-Vaca and D. Bourissou, *Chem. Rev.*, 2004, **104**, 6147–6176.
- 69 N. E. Kamber, W. Jeong, R. M. Waymouth, R. C. Pratt, B. G. G. Lohmeijer and J. L. Hedrick, *Chem. Rev.*, 2007, **107**, 5813–5840.

