



Cite this: *Green Chem.*, 2021, **23**, 6936

Received 13th May 2021,
Accepted 26th August 2021

DOI: 10.1039/d1gc01710a

rs.c.li/greenchem

Ultra-rapid synthesis of the MgCu₂ and Mg₂Cu Laves phases and their facile conversion to nanostructured copper with controllable porosity; an energy-efficient, reversible process†

Zhen Fan,^a Gytis Baranovas,^{a,b} Holly A. Yu,^{id}^a Robert Szczyński,^c Wei-Ren Liu^{id}^d and Duncan H. Gregory^{id}^{*a}

Phase-pure MgCu₂ and high-purity Mg₂Cu have been synthesised within 1 min from elemental powders via the microwave-induced metal plasma (MIMP) approach for the first time. Subsequent room temperature, acidic de-alloying led to 3-dimensional nanoporous (NP) Cu within minutes. Each distinctive metallic matrix exhibited a large surface area with a porosity of either 37.47% (from MgCu₂) or 56.25% (from Mg₂Cu). Both NP Cu powders are composed of crystalline grains ("ligaments") measuring tens of nanometers across, which exhibit rich point- and extended defects. The selection of Laves precursor dictates the form of ligament obtained, which directs the ensuing NP structure. Working electrodes of both types of NP Cu presented reliable linear non-enzymatic sensing properties over glucose concentrations of 0.5–4.5 and 4.5–10.0 mM with high confidence levels (>99%). This study provides a facile, rapid and energy-efficient route to functional NP Cu with eclectic structures, which should be equally applicable to other metals.

with highly-occupied d orbitals, has attracted growing interest in electro-catalysis research, principally due to an attractive combination of low toxicity, relatively low cost, high electrical conductivity and impressive catalytic activity.^{1,4,6,7} Cu nanomaterials adopting distinctive structures that can accommodate various surface oxidation states, have been largely studied for the electrochemical reduction of CO₂ towards value-added multi-carbon products.^{8–13} Such nanomaterials can also exhibit antibacterial properties and provide efficient electro-reduction of nitrate for water treatment.^{6,14,15} Moreover, studies in 2020 have shown that the electrocatalytic reduction of NO and nitrate (pollutants of gas and wastewater, respectively) using Cu foams or nanosheets, offer lower energy-cost alternatives to traditional methods of ammonia synthesis, with significant industrial potential.^{16,17} Among other promising applications, the rapid and reliable detection of glucose concentration in human blood would be an important medical advance. Compared with the high costs, complexities and instabilities of enzyme electrodes, Cu-based nanomaterials have shown good non-enzymatic sensitivity and stability.^{18–22}

Introduction

Nanoporous (NP) metals, typically containing nanosized pores or ligaments less than 100 nm across, combine the physical and chemical properties of bulk metals (*e.g.* electrical conductivity, mechanical strength *etc.*) with unique nanoscale features like large surface-to-volume ratios, low density and abundant defects *etc.*^{1–5} Copper, as an Earth-abundant transition metal

Nanoporous Cu (NP-Cu) materials have universally demonstrated a particularly impressive performance in the context of the above applications.^{7,18,23–26} A variety of synthesis methods have been proposed for NP metals, including thermal decomposition and reduction of metal salts/oxides (*e.g.* by H₂ gas),^{27,28} electrochemical reduction of metal oxides (which are typically pre-synthesised in solution),²³ organo-lithium reduction of metal/lithium halide nano-composites in nonpolar solvents,² and chemical de-alloying of alloys by corrosive liquids (typically acidic or basic solutions).^{24,29–32} Of these methods, chemical de-alloying is proposed to be a readily scalable approach, in which relatively active elements are sacrificed and noble elements are reorganised into NP structures by surface diffusion.^{4,5,24,33} Mn–Cu, Al–Cu, Ca–Cu and Mg–Cu binary alloys (or related ternary systems), either glassy or crystalline, have been successfully utilised for the fabrication of NP-Cu.^{1,4,6,24,34,35} The synthesis of these alloys usually requires heating for long durations under inert conditions and/or

^aWestCHEM, School of Chemistry, Joseph Black Building, University of Glasgow, Glasgow, G12 8QQ, UK. E-mail: Duncan.Gregory@glasgow.ac.uk; Tel: +44-141-330-8128

^bInstitute of Chemistry, Faculty of Chemistry and Geosciences, Vilnius University, Naugarduko str. 24, LT-03225, Vilnius, Lithuania

^cFaculty of Chemistry, Nicolaus Copernicus University in Toruń, ul. Gagarina 7, 87-100 Toruń, Poland

^dDepartment of Chemical Engineering, Chung Yuan Christian University, R&D Center for Membrane Technology, Research Center for Circular Economy, 32023, No. 200, Chun Pei Rd., Chung Li District, Taoyuan City 32023, Taiwan

†Electronic supplementary information (ESI) available. See DOI: 10.1039/d1gc01710a




eutectic melting at high temperature with dedicated high power equipment such as high frequency induction furnaces.^{6,24} For larger scale processing (kg to tonnes) such equipment requires typical input powers of 10 kW–42 MW and production can require several cycles to avoid oxide contamination. Subsequent alloys are typically melt-spun under protective fluxes (which, themselves can incur considerable expense).^{4,6,24,34,35} These multi-step processes can thus be highly energy-intensive and non-trivial (ESI; Table S1†). Glassy metallic ribbons are commonly employed as alloy precursors in the majority of cases.^{1,4,6,24,34,35} Perhaps surprisingly, de-alloying processes from crystalline precursors are uncommon and remain far less studied.

Herein, we describe an energy-efficient microwave-induced-metal-plasma (MIMP) method³⁶ to synthesise crystalline alloys in the binary Mg–Cu system; yielding the Laves phase, MgCu₂ and the corresponding *anti*-Laves phase, Mg₂Cu. Each high purity alloy is obtained from mixtures of the elemental powders within 1 min by applying a microwave (MW) power of merely 200 W *in vacuo* (and hence without the requirement or expense of protective fluxes). De-alloying of the intermetallic powders can be achieved over minute timescales in 0.5 M HCl. De-alloying leads to 3D open NP-Cu materials with two different microstructures that we can relate directly to those of the respective precursors. Whereas both materials clearly show nano-pores/nano-grains of a few tens of nanometres or less coupled with rich stacking faults and lattice defects, NP-Cu from MgCu₂ exhibits branch-like nano-ligaments as a principal feature while NP-Cu from Mg₂Cu takes the form of quasi-spherical nano-ligaments. The high porosities of the Cu materials (37.47% and 56.25% from MgCu₂ and Mg₂Cu, respectively) are precursor-dependent, allowing the surface area and pore volume to be controlled. Working electrodes of both NP-Cu reliably exhibited linear non-enzymatic glucose sensing properties over concentration ranges of 0.5–4.5 mM and 4.5–10.0 mM with confidence levels close to 100% and with exceptional sensitivity.

Results and discussion

The known binary phase diagram of the Mg–Cu system (Fig. S1, ESI†) indicates that two solid intermetallic compounds exist, *i.e.* the Cu-rich Laves phase MgCu₂ and the Mg-rich *anti*-Laves phase Mg₂Cu.^{37–39} We focused on preparing these phases by employing our previously developed MIMP route for intermetallics.³⁶ Both binary Mg–Cu intermetallics were successfully synthesised from mixtures of fine metal powders (used to ensure MW penetration)³⁶ at an incident power of 200 W under a static vacuum of $P < 10^{-6}$ mbar for 1 min (Scheme 1; full details in ESI;†). A 15 mol% excess of Mg powder was found to be necessary in each synthesis in order to compensate for the volatility of Mg.³⁶ The generation of metal plasma could be observed within a few seconds of the onset of MW irradiation, indicating the efficient ohmic coupling between the fine metal powders and the MW field (Videos

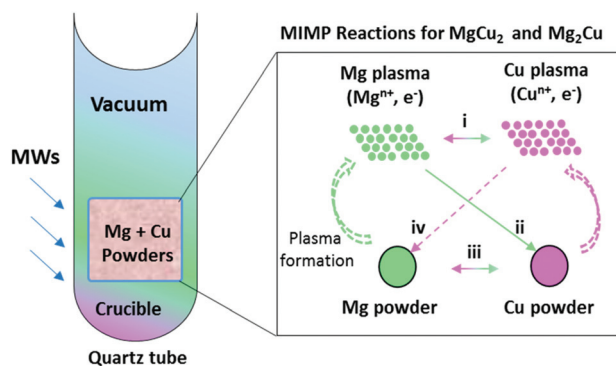

Scheme 1 Proposed reaction pathways (i–iv) that can occur in the ultra-fast MIMP syntheses of Mg–Cu intermetallics.

1–3, Fig. S6, ESI†). The observed plasma gradually transformed from an initial pink colour to a steady green colour (Videos 2 & 3, ESI†). The initial pink plasma that prevails for the first *ca.* 25–30 s might be attributed chiefly to Cu (Video 1, ESI†), whereas the steady green plasma observed later in the reaction is likely to originate from the vaporised and ionised Mg source.³⁶ Considering that long durations are required for the conventional high-temperature synthesis of Mg–Cu alloys,^{24,34,35} we propose that the ultra-rapid MW alloy reactions occur largely *via* MIMP phase(s) to enable completion within 1 min (routes i, ii, iv, Scheme 1).³⁶ Nevertheless, a solid-state reaction route between Mg and Cu particles (Scheme 1, route iii) cannot be completely excluded given the elevated temperature of the synthesis.³⁶

This repeatable MIMP approach afforded phase-pure, sub-micron to micron-sized MgCu₂ powders in 1 min as determined by powder X-ray diffraction (PXRD) and scanning electron microscopy (SEM), respectively (Fig. 1a; Fig. S2a, ESI†). Phase matching of PXRD patterns and subsequent Rietveld refinement against the lab diffraction data confirmed the formation of cubic MgCu₂ (space group $Fd\bar{3}m$ (No. 227), $a = 7.0439(1)$ Å; Fig. 1a and d; Tables S2–4, ESI†). Although the MIMP method involves ultrafast reaction kinetics and changes of state – notably through the formation of metal plasma in the 2.45 GHz electromagnetic field – there was no evidence of impurities in the products. The C15 Laves phase of MgCu₂ forms with a structure consisting of an interconnected 3D framework formed from Cu₄ tetrahedral clusters with Mg in the tetrahedral sites of a diamond-like sublattice. The Cu atoms can also be considered to form a Kagomé net of regular triangles and hexagons.⁴⁰ One interesting and important result from the structure refinement of MgCu₂ concerns the Cu 16d site, which was found to have a refined occupancy of 0.962(4), implying a stoichiometry of MgCu_{1.92} (Fig. 1d; Table S3, ESI†). This result suggests that MgCu₂ is not, in fact, a line phase (and the binary phase diagram also indicates a region of variable stoichiometry) or at least that a non-stoichiometric metastable phase is favoured by the kinetically-driven conditions of the MIMP synthesis. Interestingly, both the chemical and mechanical properties of Laves phases can be



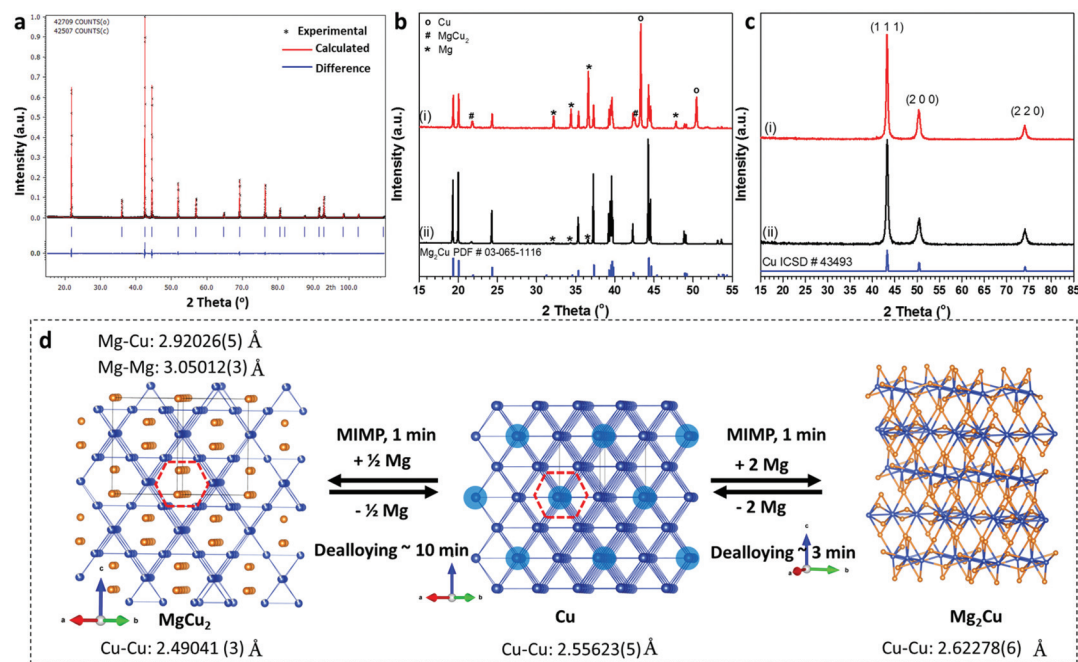


Fig. 1 (a) Rietveld profile plot for as-synthesised MgCu_2 ; (b) PXD patterns of Mg_2Cu powders synthesized after (i) 30 s and (ii) 60 s, respectively; (c) PXD patterns of NP-Cu de-alloyed from (i) MgCu_2 and (ii) Mg_2Cu , respectively and (d) reaction scheme from/to (NP-)Cu and the MgCu_2 and Mg_2Cu Laves phases. The crystal structure of each reactant/product is shown. (The MgCu_2 and Mg_2Cu structures are taken from this work, while the Cu structure is from ref. 38.) Cu atoms are shown as royal blue spheres and Mg atoms as orange spheres. The Cu atoms in copper metal that are replaced by Mg in MgCu_2 are highlighted in lighter blue and the Kagomé hexagons in Cu and MgCu_2 are indicated with red dashes.

tuned *via* small stoichiometric modifications.⁴¹ The implications of copper deficiency in MIMP-synthesised MgCu_2 would be an interesting avenue to explore in further studies. The Mg-rich environment of the synthesis (15 mol% excess of Mg metal) would certainly not disadvantage the formation of Cu vacancies and the formation of an intense Cu plasma in the microwave field is likely to promote Cu loss in the MgCu_2 product. Given that the necessary advanced temporally- and spatially-resolved techniques to probe such a reaction *in situ* are extremely challenging to set up, it remains problematic to establish a reaction mechanism and to unequivocally identify a driving force for the non-stoichiometry.^{36,42}

Considering again the crystal structure, MgCu_2 crystallises in a cubic structure that is ostensibly very similar to that of face-centred-cubic Cu, which can also be considered as a 3D framework composed of Cu_4 tetrahedral clusters (Fig. 1d). From the (110) projections of the respective structures, the copper network in Cu metal is largely preserved in MgCu_2 and Mg atoms can be regarded as substituting for a proportion of the Cu atoms (within the dashed hexagonal channels indicated in Fig. 1d). Like Cu, MgCu_2 is metallic with excellent electrical and thermal conductivity.^{37,43} This is perhaps not unexpected given the similarity of the Cu framework to that in Cu metal and, in fact, the Cu–Cu distance of 2.49041(3) Å in MgCu_2 is smaller than the equivalent distance of 2.55623(5) Å in Cu metal itself.³⁸ Indeed, DFT calculations suggest that the electronic DOS at the Fermi level of MgCu_2 largely originates from Cu 3d contributions.^{37,43}

It should be noted for the MIMP reaction of MgCu_2 that although pink plasma is observable continuously for an initial period >30 s (Video 2, ESI†), a reaction performed for only 30 s led to negligible formation of Mg–Cu alloys, leaving only unreacted Mg and Cu starting materials (Fig. S2h†). From these findings, although clearly Cu interacts strongly with MWs, readily forming a plasma under vacuum, we can intimate that Mg in the plasma phase plays a likely pivotal role in the ultra-fast synthesis of Mg–Cu alloys.

Fig. 1b shows the *ex situ* PXD patterns of the Mg_2Cu products synthesised using a MW irradiation time of 30 s and 60 s, respectively. A reaction under irradiation for 30 s formed a considerable amount of Mg_2Cu , with evidence of unreacted Mg and Cu starting materials present and a suggestion of the presence of MgCu_2 (at 42.5°, 2 θ). The incidence of MgCu_2 is perhaps not surprising given its higher thermal stability over Mg_2Cu (Fig. S1†) and it is also possible that the phase acts as a kinetically-favoured intermediate which reacts further with Mg to produce Mg_2Cu . Based on PXD patterns and the results of subsequent Rietveld refinement (Fig. 1b; Fig. S2g, ESI†), irradiation for 60 s yielded high purity Mg_2Cu containing only minor amounts of Mg (up to *ca.* 3.6(2) wt%; Fig S2g, Tables S5–7, ESI†). Irradiation times exceeding 60 s did not improve the purity significantly and extended reaction times (>90 s) led to increased Mg and/or MgCu_2 impurities. The anti-Laves phase, Mg_2Cu forms a complex layered orthorhombic structure in space group *Fddd* (No. 70) in which Cu atoms are coordinated by eight Mg atoms in a square antiprismatic geome-



try. Two of the rectangular faces of the square antiprism are further capped by Cu atoms. The layered structure is then constituted by the stacking of different types of five-atom layer thick “slabs” along the crystallographic *c*-axis (Fig. 1d).³⁹ Unlike in MgCu₂ and Cu itself, the copper atoms in Mg₂Cu form quasi-linear chains rather than Kagomé nets. SEM images indicate the synthesised powders contain particles ranging from sub-micron sizes to those measuring a few tens of microns across, which exhibit crystalline facets. Sub-micron scale textures appear to be common in the Mg₂Cu sample (Fig. S2b and c, ESI†). Energy dispersive X-ray (EDX) spectra and spatially resolved elemental mapping further confirm the uniform elemental distributions of Mg and Cu within the synthesised micron-sized powders (Fig. S2d–f, ESI†).

Following their characterisation, MW-synthesised MgCu₂ and Mg₂Cu powders were converted into NP-Cu materials by immersion into 0.5 M aqueous HCl solutions at room temperature, until no further gas bubbles evolved. This chemical de-alloying process was typically complete within ~10 min for MgCu₂ and within ~3 min for Mg₂Cu. The two different NP-Cu samples in this study are thus referred to as “NP-Cu_MgCu₂” and “NP-Cu_Mg₂Cu” from this point forward. PXD patterns of the de-alloyed Cu samples could be indexed to the expected *fcc* structure of Cu without the presence of any peaks from copper oxides or other impurities (Fig. 1c). Both Cu samples were composed of micron-sized particles with three-dimensional porous structures (Fig. 2–4; Fig. S3, ESI†). EDX spectra (Fig. S3, ESI†) confirmed the exclusion of residual Mg and copper oxides, while the trace amount of oxygen observed could very likely be attributed to the short period of air exposure during sample mounting for SEM-EDX characterisation.

Fig. 2a shows that the sponge-like NP-Cu_MgCu₂ material is composed of uniform interconnected ligaments (from a few to ~50 nm) as the principal structural feature (Fig. 2b), which is further confirmed in low-resolution transmission electron microscopy (TEM) images (Fig. 2c; Fig. S3e and f, ESI†). Parallel lines characteristic of Moiré fringes with periodicity from 0.8 nm to 1.3 nm could be observed within these ligaments (Fig. 2d). The Moiré fringes (caused by the interference between diffracted and transmitted electron beams), can be attributed to overlapping crystalline sections of the sample which might arise from Cu₂O at the surface caused by the oxidation of the Cu sample during the TEM specimen preparation. Alternatively, local structure variations and uneven twisting and strains of the nano-grains in NP-Cu_MgCu₂ might be responsible.^{44–46} The thorough distribution of phase contrast in Fig. 2c would also suggest that Moiré fringes would not be uncommon across regions of NP-Cu_MgCu₂ samples. The high magnification inverse-fast-Fourier-Transform (iFFT) image (Fig. 2e) of the Moiré fringes reveals a lattice distance of 0.208 nm that matches well to the *d*-spacing from the Cu (111) plane. The corresponding selected area electron diffraction (SAED) pattern in Fig. 2f shows sharp single crystalline spots matching the Cu (111) and Cu (133) planes, that are superimposed over polycrystalline rings (also from Cu). Additionally, broad spots are observed that originate from Cu₂O located at

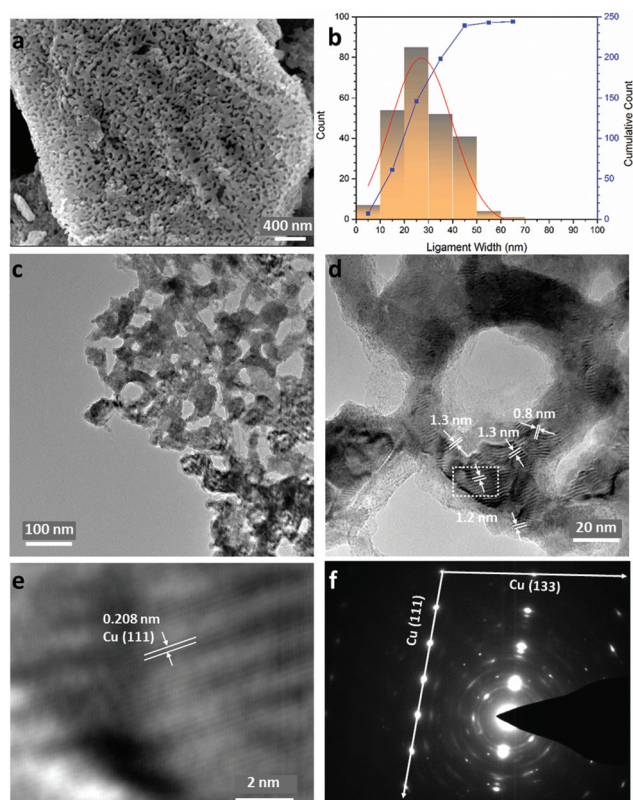


Fig. 2 Characterisation of NP-Cu_MgCu₂ by electron microscopy, showing: (a) an SEM image of a single NP particle; (b) the size distribution of the Cu ligaments taken from the image in (a); (c) a TEM image at lower magnification; (d) a TEM image at higher magnification, highlighting Moiré fringes; (e) inverse-fast-Fourier-Transform (iFFT) image taken from the enclosed area of the image shown in (d); (f) a selected area electron diffraction (SAED) pattern taken from (d).

certain positions throughout the samples (Fig. 2f; Table S8, ESI†). Considering the thermodynamic surface energy of nano-grains of Cu,^{4,12,44} the oxidation can be attributed to the probable surface oxidation of the material during the preparation and transfer of the TEM specimen into the microscope.

Indeed, high-resolution TEM images show the presence of Cu₂O at the outer edges of the ligaments (area A in Fig. 3a and c). An amorphous surface layer appears to form in places, beneath which exists a poorly-crystalline layer with a thickness of ~3–5 nm. The bulk of the Cu particle shown in Fig. 3a contains nano-grains in which the (110) and (111) planes are more clearly visible, but which also exhibits an apparent abundance of lattice dislocations, grain boundaries and vacancies (Fig. 3a and c), suggesting the presence of highly defective and micro-strained nano-ligaments in the NP-Cu_MgCu₂ material, which readily form during the room temperature de-alloying process. The diffuse electron diffraction spots and powder rings that originate from the (110) reflection from the Cu particle (Fig. 3b) are consistent with its component defective grains, as seen in Fig. 3a.

In contrast to NP-Cu_MgCu₂, the structure of NP-Cu_Mg₂Cu (Fig. 4a and b; Fig. S3h, ESI†) is not so sponge-



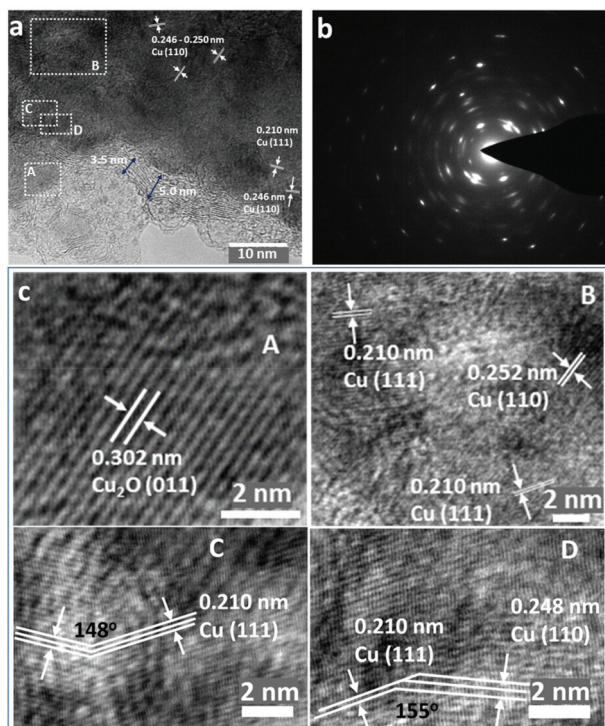


Fig. 3 High-resolution TEM characterisation of NP Cu₂MgCu₂: (a) a high-resolution TEM image illustrating individual nano-grains; (b) the corresponding SAED pattern taken from (a); (c) iFFT images of the respective enclosed labelled areas in (a) (areas, A, B, C, D respectively).

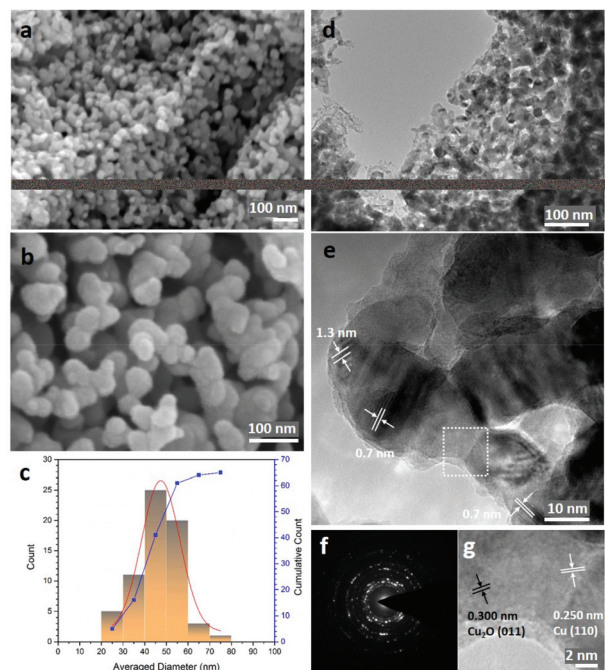


Fig. 4 Characterisation of NP-Cu₂MgCu₂ by electron microscopy, showing: (a and b) SEM images at different magnification; (c) the size distribution of quasi-spherical nano-ligaments in (b); (d and e) TEM images of the matrix of the nano-ligaments; (f) a corresponding SAED pattern taken from (e) and (g) a high-resolution TEM image of the enclosed dashed region shown in (e).

like and appears still less dense. The material is seemingly composed of clusters of nanoparticles, which at higher magnification are revealed to be interconnected quasi-spherical nano-ligaments, apparently ranging from 20–80 nm across (Fig. 4c). Ostensibly, the nano-grains resemble fragments of the ligaments that comprise the NP-Cu₂MgCu₂ microstructure. These morphological differences between the NP-Cu materials and the fact that the sponge-like matrix observed for NP-Cu₂MgCu₂ appears to be disrupted, can almost certainly be attributed to differences in the Laves phase precursors at the atomic level. Given the much higher Mg content in the lattice, the *anti*-Laves Mg₂Cu crystal structure resembles that of copper far less than MgCu₂ (Fig. 1d). Not only is proportionally far more Mg required to be removed from Mg₂Cu than MgCu₂, but also the former does not retain the Kagomé net of copper atoms that dominates the structure of Cu and adopts an entirely different stacking sequence to the Cu-rich phase. The de-alloying process in Mg₂Cu requires significantly more atomic diffusion, structural transformation and mass transfer than does that for MgCu₂. Low magnification TEM images confirm the structure and distribution of the quasi-spherical nano-ligaments, revealing that the smallest of these angular particles are only few nm across, with most 30–45 nm in size (Fig. 4d). Moiré fringes are observed at higher magnification, just as in NP-Cu₂MgCu₂ and are arguably even more prevalent in the particles derived from the Mg-rich precursor (Fig. 4e). This prevalence suggests abundant stacking faults and lattice defects in NP-Cu₂MgCu₂, which is not surprising, given the large crystal structure change during the rapid room temperature de-alloying process. Diffraction spots superimposed over powder rings were observed in SAED patterns taken from a small cluster of the quasi-spherical nano-ligaments (Fig. 4f; Table S8, ESI[†]). These patterns represented a mixture of single crystals (principally Cu) and polycrystals (mainly Cu₂O but also Cu). High-resolution TEM images (Fig. 4g) also demonstrate that the bulk of the nano-grains are comprised of Cu, with the (110) spacing clearly defined. As seen in the NP-Cu₂MgCu₂ samples, Cu₂O grows as a surface layer on the Cu grains, with the (011) spacing discernible and likely forms as the samples are prepared and transferred to the microscope.

Brunauer–Emmett–Teller (BET) analysis of nitrogen adsorption data was performed at 77 K to estimate the surface area, pore size distribution and porosity of the respective NP-Cu samples (Table 1, Fig. 5a–c). Both samples present type IV N₂ physisorption isotherms. NP-Cu₂MgCu₂ has an H1 hysteresis, suggesting capillary condensation at well-defined cylindrical mesopores (2–50 nm).⁴⁷ By contrast, NP-Cu₂Mg₂Cu has an H3 hysteresis, indicating the presence of exceptionally small pores, *i.e.*, micropores (<2 nm).⁴⁷ The corresponding measured BET surface areas are 7.923 and 10.728 m² g⁻¹ for NP-Cu₂MgCu₂ and NP-Cu₂Mg₂Cu, respectively. The microporous surface area of NP-Cu₂Mg₂Cu is approximately three times larger than that of NP-Cu₂MgCu₂, as might be inferred from the shape of the isotherms. The Barrett–Joyner–Halenda (BJH) analysis of the desorption curve in Fig. 5c demonstrates that the pore size distribution in NP-Cu₂MgCu₂ is relatively



Table 1 Surface area and porosity information from BET measurements

Sample	BET surface area/m ² g ⁻¹	Micro-pore area/m ² g ⁻¹	External surface area/m ² g ⁻¹	Micro-pore area/BET surface area/%	Porosity/%
NP-Cu_MgCu ₂	7.923	0.820	7.103	10.35	37.47
NP-Cu_Mg ₂ Cu	10.728	2.495	8.233	23.26	56.25

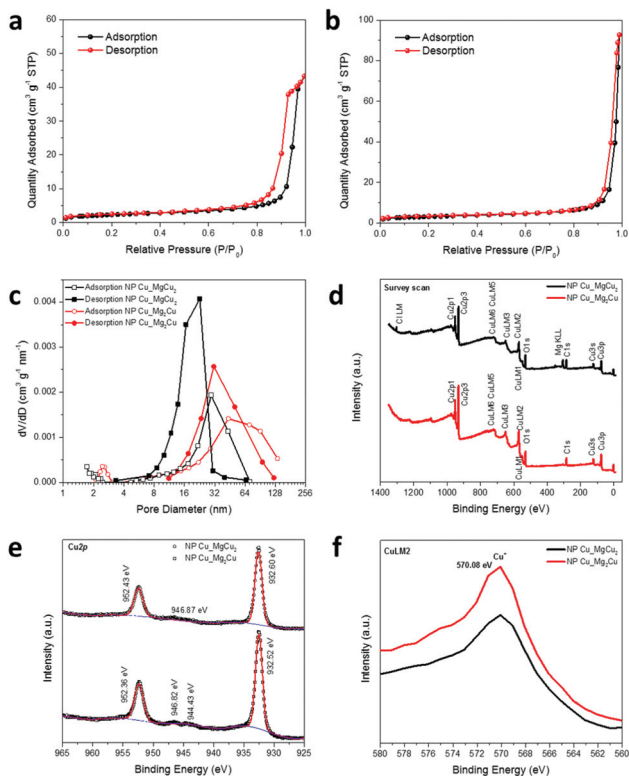


Fig. 5 BET N₂ physisorption isotherms of: (a) NP-Cu₁MgCu₂ and (b) NP-Cu₁Mg₂Cu; (c) pore size distributions for NP-Cu₁MgCu₂ (black) and NP-Cu₁Mg₂Cu (red) as derived from Barrett–Joyner–Halenda (BJH) analysis of adsorption/desorption data; and (d–f) wide survey scan, Cu2p, and CuL2M2 XPS spectra, respectively, taken from the NP-Cu samples.

narrow, sharp and uniform and lies predominantly in a region between 8–32 nm, with a maximum of approximately 20 nm, which corresponds to an internal structure dominated by mesopores.⁴⁷ Although the BJH analysis of the adsorption curve for NP-Cu₁MgCu₂ shows relatively larger pore sizes, the results also confirm the dominant mesopores in this sample. By stark contrast, NP-Cu₁Mg₂Cu exhibits a relatively wide pore size distribution, covering sizes over an order of magnitude embracing both mesopores and macropores (Fig. 5c; Fig. S3h, ESI†).⁴⁷ Consistent with all the above findings, the total porosity was more than half as much again in NP-Cu₁Mg₂Cu than in NP-Cu₁MgCu₂ (Table 1).

The mechanisms for the formation of porous metal structures by de-alloying have been the topic of extensive investigations, which have examined many facets of the process including the dissolution of the active component elements

into solution, the surface diffusion processes and the self-organisation of the more inert (often noble) metal elements.^{24,34,48} Due to the high surface energy of the de-alloyed products, the coarsening of the NP metal particles in liquids is unavoidable.⁴⁸ It should be noted that in a previous study NP-Cu prepared by de-alloying Mg₆₅Cu₂₅Y₁₀ glass ribbons in 0.04 M H₂SO₄ (vs. 0.5 M HCl in our work) for 10 min only exhibited a porosity of ~30%, which is even lower than the porosity of the NP-Cu produced from a Cu-rich precursor (MgCu₂) herein. This contrast can be potentially attributed to the profound differences in structure between glass metallic ribbons and crystalline alloy powders combined with the degree of nano-grain coarsening observed in different acid solutions (H₂SO₄ vs. HCl).⁴⁹ Indeed, NP Cu samples with finer ligaments, smaller pores, larger surface areas and higher porosity can potentially be prepared *via* de-alloying using organic acids, which could decelerate atomic diffusion rates.²⁴ Interestingly, a previous study reported that melt spun alloys of nominal composition Mg₃₃Cu₆₇ (essentially shown to be MgCu₂ with evidence of a minor impurity of Cu metal present) could not be fully de-alloyed when using 5 wt% HCl solution.³⁴ In fact, Mg could only be successfully removed from the surface of the copper-rich Mg–Cu alloy in this earlier study and it was proposed that entirely different mechanisms were responsible for de-alloying Mg₂Cu and MgCu₂ in aqueous HCl solution. It was hypothesised that Mg atoms from Mg₂Cu could continuously dissolve into solution, whereas Mg dissolution in MgCu₂ might be accompanied by the formation of aqueous CuCl₂⁻ during dealloying. As Cu is formed, CuCl₂⁻ is contended to accumulate in the porous channels in a passivating capacity preventing further de-alloying. It is inherently extremely challenging experimentally to study the de-alloying of metals in solution and to probe the removal of magnesium from MgCu₂ in aqueous HCl is no exception. Nevertheless, it is apparent from a comparison of the respective products that HCl-treated melt-spun Mg₃₃Cu₆₇ samples present a very different morphology to NP-Cu₁MgCu₂ (e.g. Fig. 2a and c in our study). To some extent these differences could arise from the divergent particle shapes and sizes of the alloy precursors. Alternatively, the Cu sub-stoichiometry (vacancies) in our MW-synthesised MgCu₂ is an important distinction to be made between the NP-Cu₁MgCu₂ precursor and other copper-rich Mg–Cu materials. Potentially less thermodynamically stable than the stoichiometric C-15 phase, the de-alloying reaction in aqueous HCl is likely more favourable. Moreover, the vacancies in the Cu sublattice should facilitate diffusion and promote the relatively minor reorganisation of the 3D Cu net in MgCu₂ to the equivalent array in similarly structured Cu (Fig. 1d).



Fig. 5d–f shows the wide survey scan, Cu2p, and CuLM2 X-ray photoelectron spectroscopy (XPS) spectra, respectively, of our NP-Cu samples. The spectra indicate the same electronic state of Cu in the two NP-Cu samples. Both Cu2p spectra are characteristic of copper metal with peaks at binding energies of *ca.* 952.4 eV ($2p_{1/2}$) and *ca.* 933.6 eV ($2p_{3/2}$). This is also consistent with those taken from other samples of NP-Cu, such as the spectrum originating from electrochemically reduced NP-Cu.²³ The spectrum of Cu₂O is very similar to that of Cu, however, with the presence of weak satellites and a slight broadening of the $2p_{3/2}$ peak usually the only distinguishing features.^{23,24} The presence of weak satellites at *ca.* 945 eV might suggest that Cu₂O is also present. CuLM2 Auger spectra (Fig. 5f) show peaks at 570.08 eV, corresponding to Cu⁺ in Cu₂O.¹⁸ This is unsurprising given the tendency for the NP-Cu nano-grain surfaces to oxidise readily in air (Fig. 2–4); the presence of Cu₂O could arise from surface oxidation during preparation and transfer of the XPS specimens. Indeed, it is not unusual for Cu nanostructures to oxidise easily on air exposure (or when heated in the presence of oxygen).^{4,9,12,14} *Ex situ* PXD experiments confirm that our NP-Cu samples can be very easily oxidised under a range of conditions, with full oxidation to CuO occurring at elevated temperature (Fig. S4, ESI†). Interestingly, SEM images of CuO powders formed by heating NP-Cu_Mg₂Cu in air suggest that the morphology and porosity of the material is retained after oxidation (Fig. S5, ESI†). However, the oxidation of NP-Cu_MgCu₂ to CuO is not similarly pseudomorphic (Fig. S5, ESI†). It appears that the lower density, higher porosity NP-Cu_Mg₂Cu is able to more easily

accommodate the volume change associated with oxidation, but this and associated phenomena will be the topic of a subsequent study.

In light of the well-defined open pores and defect-rich nano-grains found in our NP-Cu materials, we wished to explore the possibility that the nanogranular metals could serve as electrochemical catalysts with large surface areas, abundant active sites and high electrical conductivity as the prerequisites. A working electrode was prepared with NP-Cu_MgCu₂ and NP-Cu_Mg₂Cu on glassy carbon, respectively, for the non-enzymatic electrochemical sensing of glucose with 0.1 M NaOH aqueous solution as the electrolyte. Fig. 6a shows CV curves (−0.1–0.8 V *vs.* Ag/AgCl) of the working electrodes in the presence of 0.5 mM glucose at scanning rates of 20–100 mV s^{−1}. Oxidation currents could be seen in the voltage range of 0.35–0.5 V *vs.* Ag/AgCl. Since the oxidation potential of Cu(0) to Cu(I) and Cu(I) to Cu(II) are both lower than 0.2 V,¹⁸ the oxidation peak could be attributed to the oxidation of glucose.^{18,20} The possible sensing mechanism of NP-Cu and its oxides has been proposed to involve a Cu(III) intermediate, which catalyses the oxidation of glucose to gluconolactone.^{18,20,50} Thus, the mechanism of the process we observe is likely to proceed according to the following steps: (1) progressive surface Cu(0) oxidation to Cu(I) and then to Cu(II) in alkaline NaOH solution under positive potentials; (2) CuO + OH[−] = CuOOH + e[−]; (3) CuOOH + e[−] + glucose = CuO + OH[−] + gluconolactone.^{18,20} Because the oxidation reaction of glucose is irreversible, the reduction current observed at 0.55–0.6 V likely corresponds to Cu(III)–Cu(II) reduction, while

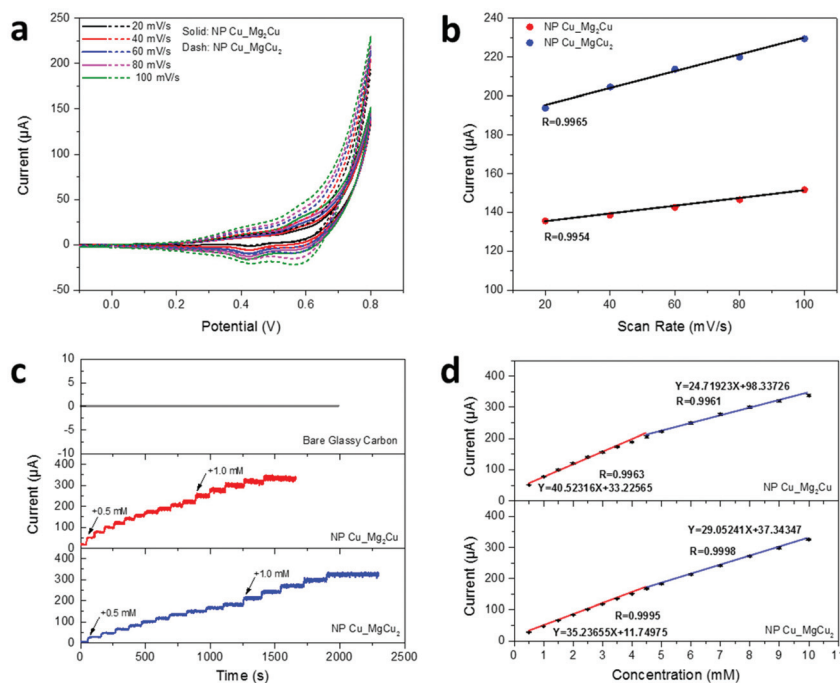


Fig. 6 (a) CV curves of the working electrode in 0.5 mM glucose at scanning rates from 20 to 100 mV s^{−1} (−0.1–0.8 V *vs.* Ag/AgCl); (b) plot of max current *vs.* scanning rate for (a); (c) amperometric responses of the working electrodes and the bare glassy carbon electrode at +0.62 V *vs.* Ag/AgCl at different glucose concentrations and (d) the calibration plot of current responses *vs.* glucose concentration for (c).



the current at 0.4–0.45 V likely corresponds to the mild reduction of Cu(n).^{18,20,21} The calibration plot of max current vs. scanning rate presented in Fig. 6b exhibited linear relationships, *i.e.* $R = 0.9965$ and 0.9954 for NP-Cu_MgCu₂ and NP-Cu_Mg₂Cu, respectively, indicating a typical surface-controlled electrochemical process with fast electron-transfer behavior, which is ideal for quantitative sensing applications.^{18–20,45}

The amperometric measurements were performed with step-wise addition of glucose into the electrolyte and both working electrodes demonstrated rapid responses to glucose concentration variations from 0.5 to 10.0 mM. By comparison, no responses were observed from the bare glassy-carbon electrode (Fig. 6c). The calibration plots of current response vs. glucose concentration confirmed two linear regions over 0.5–4.5 mM and 4.5–10.0 mM, respectively, for both working electrodes (Fig. 6d) with confidence levels close to 100%. The calculated sensing sensitivities were 573.3 and 349.7 $\mu\text{A mM}^{-1} \text{cm}^{-2}$ over 0.5–4.5 and 4.5–10.0 mM, respectively, for NP-Cu_MgCu₂; while 498.5 and 411.0 $\mu\text{A mM}^{-1} \text{cm}^{-2}$ over 0.5–4.5 and 4.5–10.0 mM, respectively, for NP-Cu_Mg₂Cu. The results confirmed that non-enzymatic glucose-sensing could be performed by both NP Cu samples with both high precision and high sensitivity (Table S9, ESI†). Considering these very promising initial results, it will be interesting to explore the performance of NP-Cu samples more widely to serum samples and to investigate NP-Cu prepared under different de-alloying conditions. Similarly, the use of NP-Cu made *via* the MIMP-de-alloying method in other electrochemical applications that rely on nanoscale porosity and an abundance of point and extended defects certainly warrants further study.^{8,9,11–13,51} Moreover, given the likely high surface energy of NP-Cu produced by the MIMP method, it will be very interesting to monitor the morphological evolution of these materials during the course of electrochemical processes such as, but not exclusively, chemical sensing. Quite apart from the surface properties, which relate more specifically to catalytic processes for example, since the NP-Cu samples contain nano-grains with a high density of grain boundaries and defects, their mechanical stability could be especially interesting to unravel at the nanoscale.^{48,52} Significantly, Fig. S7† suggests that our NP-Cu products can be reacted with Mg powder using the MIMP method to form the intermetallic phase once again. This indicates that the reactants and products of Cu could potentially be (re)cycled multiple times, while Mg could be regenerated from MgCl₂ leach solutions electrochemically.

Conclusions

The ultra-fast and energy efficient MIMP syntheses of MgCu₂ and Mg₂Cu provide a unique basis for the sustainable fabrication of functional NP-Cu over a matter of minutes. The choice of alloy precursor – either MgCu₂ or Mg₂Cu; each with distinct crystal structures – directs the morphologies and porosity of the de-alloyed copper metal. Both de-alloyed materials exhibit

matrices of nano-grains rich in stacking faults and lattice defects, yet each offers a bespoke distribution of micro-, meso- and macropores, which are ideal for surface-controlled catalysis. Both NP-Cu samples demonstrate extremely promising linear electrochemical non-enzymatic glucose sensing over concentration ranges of 0.5–4.5 and 4.5–10.0 mM with high sensitivity. The facile, rapid, and energy-efficient route to functional NP-Cu disclosed here should be readily extendable to other metals, metal oxides and oxide-metal composites. Potentially a multitude of applications that benefit from high concentrations of nano-pores and/or defects are accessible to such easily produced materials.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

DHG and ZF thank the University of Glasgow and the China Scholarship Council for the co-funding of a studentship for ZF. DHG and W-RL thank the Royal Society and MOST for joint funding under grants IEC\R3\183040 and MOST 109-2911-I-033-502. The authors acknowledge Mr Hsi-Nien Ho, Mr Cheng-Yi Lin and Ms Mei-Chun Lin (Chung Yuan Christian University) for assistance with XPS, SEM and BET measurements, respectively. Mr Hao Yang & Professor Peter Skabara and Mr Peter Chung & Mr James Gallagher (University of Glasgow) are acknowledged for providing electrochemical support and assistance with SEM measurements, respectively. DHG and ZF acknowledge Mr Patrick McHugh (University of Glasgow) for assistance with the electrochemical experiments.

References

- 1 Y. Zhang, X. Sun, N. Nomura, *et al.*, *Small*, 2019, **15**, 1805432.
- 2 C. Coaty, H. Zhou, H. Liu, *et al.*, *ACS Nano*, 2018, **12**, 432–440.
- 3 B. C. Tappan, S. A. Steiner III and E. P. Luther, *Angew. Chem., Int. Ed.*, 2010, **49**, 4544–4565.
- 4 K. Nishimoto, M. Krajčí, T. Sakurai, *et al.*, *Inorg. Chem.*, 2018, **57**, 2908–2916.
- 5 J. Erlebacher, M. J. Aziz, A. Karma, *et al.*, *Nature*, 2001, **410**, 450–453.
- 6 X. Zhang, K. Turcheniuk, B. Zusmann, *et al.*, *Chem. Commun.*, 2018, **54**, 5446–5449.
- 7 S. Nitopi, E. Bertheussen, S. B. Scott, *et al.*, *Chem. Rev.*, 2019, **119**, 7610–7672.
- 8 C. T. Dinh, T. Burdyny, M. G. Kibria, *et al.*, *Science*, 2018, **360**, 783–787.
- 9 Y. Li, D. Kim, S. Louisia, *et al.*, *Proc. Natl. Acad. Sci. U. S. A.*, 2020, **117**, 9194–9201.



- 10 M. Ebaid, K. Jiang, Z. Zhang, *et al.*, *Chem. Mater.*, 2020, **32**, 3304–3311.
- 11 G. M. Tomboc, S. Choi, T. Kwon, *et al.*, *Adv. Mater.*, 2020, 1908398.
- 12 Q. Lei, H. Zhu, K. Song, *et al.*, *J. Am. Chem. Soc.*, 2020, **142**, 4213–4222.
- 13 W. Luc, B. H. Ko, S. Kattel, *et al.*, *J. Am. Chem. Soc.*, 2019, **141**, 9902–9909.
- 14 M. Raffi, S. Mehrwan, T. M. Bhatti, *et al.*, *Ann. Microbiol.*, 2010, **60**, 75–80.
- 15 X. Wang, M. Zhu, G. Zeng, *et al.*, *Nanoscale*, 2020, **12**, 9385–9391.
- 16 J. Long, S. Chen, Y. Zhang, *et al.*, *Angew. Chem.*, 2020, **59**, 2–10.
- 17 X. Fu, X. Zhao, X. Hu, *et al.*, *Appl. Mater. Today*, 2020, **19**, 100620.
- 18 Y. Gao, F. Yang, Q. Yu, *et al.*, *Microchim. Acta*, 2019, **186**, 192.
- 19 S. Y. Tee, E. Ye, P. H. Pan, *et al.*, *Nanoscale*, 2015, **7**, 11190–11198.
- 20 Y. Zhong, T. Shi, Z. Liu, *et al.*, *Sens. Actuators, B*, 2016, **236**, 326–333.
- 21 W. Zhu, J. Wang, W. Zhang, *et al.*, *J. Mater. Chem. B*, 2018, **6**, 718–724.
- 22 Z. Wang, X. Cao, D. Liu, *et al.*, *Chem. – Eur. J.*, 2017, **23**, 4986–4989.
- 23 J. J. Lv, M. Jouny, W. Luc, *et al.*, *Adv. Mater.*, 2018, **30**, 1803111.
- 24 H. Xu, S. Pang, Y. Jin, *et al.*, *Nano Res.*, 2016, **9**, 2467–2477.
- 25 T. N. Huan, P. Simon, G. Rousse, *et al.*, *Chem. Sci.*, 2017, **8**, 742–747.
- 26 T. T. H. Hoang, S. Ma, J. I. Gold, *et al.*, *ACS Catal.*, 2017, **7**, 3313–3321.
- 27 L. Lu, P. Andela, J. T. M. De Hosson, *et al.*, *ACS Appl. Nano Mater.*, 2018, **1**, 2206–2218.
- 28 L. Lu, F. Pei, T. Abeln, *et al.*, *Carbon*, 2020, **157**, 437–447.
- 29 X. Guo, J. Han, P. Liu, *et al.*, *ChemNanoMat*, 2016, **2**, 176–181.
- 30 T. Wang, D. Ren, Z. Huo, *et al.*, *Green Chem.*, 2017, **19**, 716–721.
- 31 H. Xu, S. Pang and T. Zhang, *J. Power Sources*, 2018, **399**, 192–198.
- 32 S. Liu, F. Pang, Q. Zhang, *et al.*, *Appl. Mater. Today*, 2018, **13**, 135–143.
- 33 S. Liu, J. Feng, X. Bian, *et al.*, *Energy Environ. Sci.*, 2016, **9**, 1229–1236.
- 34 C. Zhao, Z. Qi, X. Wang, *et al.*, *Corros. Sci.*, 2009, **51**, 2120–2125.
- 35 D. Liu, Z. Yang, P. Wang, *et al.*, *Nanoscale*, 2013, **5**, 1917–1921.
- 36 Z. Fan, M. D. Cappelluti and D. H. Gregory, *ACS Sustainable Chem. Eng.*, 2019, **7**, 19686–19698.
- 37 A. Takeuchi, K. Yubuta and A. Inoue, *Intermetallics*, 2008, **16**, 1273–1278.
- 38 H. M. Otte, *J. Appl. Phys.*, 1961, **32**, 1536–1546.
- 39 F. Gingl, P. Selvam and K. Yvon, *Acta Crystallogr., Sect. B: Struct. Sci.*, 1993, **49**, 201–203.
- 40 T. Ohba, Y. Kitano and Y. Komura, *Acta Crystallogr., Sect. C: Cryst. Struct. Commun.*, 1984, **40**, 1–5.
- 41 F. Stein and A. Leineweber, *J. Mater. Sci.*, 2020, 1–107.
- 42 H. J. Kitchen, S. R. Vallance, J. L. Kennedy, *et al.*, *Chem. Rev.*, 2014, **114**, 1170–1206.
- 43 P. Mao, Y. U. Bo, L. I. U. Zheng, *et al.*, *Trans. Nonferrous Met. Soc. China*, 2014, **24**, 2920–2929.
- 44 Y. Zhao, Y. Zhang, H. Zhao, *et al.*, *Nano Res.*, 2015, **8**, 2763–2776.
- 45 Y. Liao, W. Cao, J. W. Connell, *et al.*, *Sci. Rep.*, 2016, **6**, 1–10.
- 46 J. F. Tu, *Carbon*, 2018, **4**, 19.
- 47 K. S. W. Sing, *Pure Appl. Chem.*, 1985, **57**, 603–619.
- 48 I. McCue, E. Benn, B. Gaskey, *et al.*, *Annu. Rev. Mater. Res.*, 2016, **46**, 263–286.
- 49 X. Luo, R. Li and T. Zhang, *Corros. Sci.*, 2013, **67**, 100–108.
- 50 R. Ahmad, N. Tripathy, M. S. Ahn, *et al.*, *Sci. Rep.*, 2017, **7**, 1–10.
- 51 C. An, Z. Wang, W. Xi, *et al.*, *J. Mater. Chem. A*, 2019, **7**, 15691–15697.
- 52 X. Y. Li, X. Zhou and K. Lu, *Sci. Adv.*, 2020, **6**, eaaz8003.

