

Cite this: *Mater. Adv.*, 2021,
2, 7482

Simultaneous phase control and carbon intercalation of MoS₂ for electrochemical hydrogen evolution catalysis†

Jun Xu,^{‡abc} Xinjiao Cui,^{‡abc} Zhengwen Fan,^a Xinxin Zhu,^a Wei Guo,^{bd} Zhizhong Xie,^a Dan Liu,^{id a} Deyu Qu,^a Haolin Tang,^{id bd} and Junsheng Li^{id *abd}

Molybdenum sulfide is considered to be an alternative material to commercial platinum catalysts for the electrocatalytic hydrogen evolution reaction (HER). 1T-MoS₂ has higher hydrophilicity and electronic conductivity than 2H-MoS₂ and is more favorable for the HER. However, 1T-MoS₂ is not stable and easily transformed into a more stable 2H phase during the synthesis process. Therefore, it is crucial to find a suitable method to synthesize highly active MoS₂ HER electrocatalysts. In this work, a carbon intercalated 1T-MoS₂ electrocatalyst (MoS₂-2C) is synthesized via a glucose-assisted hydrothermal approach. The introduction of glucose in the synthesis not only induces the formation of active 1T-MoS₂ but also modifies the electronic structure of the in-plane sites of 1T-MoS₂. The electronic status of MoS₂-2C is studied in detail. Our results show that the free energy of HER at the optimal adsorption site of MoS₂-2C is as low as 0.10 eV. Therefore, it shows promising HER catalytic activity ($\eta = 217$ mV@10 mA cm⁻²) and stability in 0.5 M H₂SO₄.

Received 3rd August 2021,
Accepted 13th September 2021

DOI: 10.1039/d1ma00681a

rsc.li/materials-advances

1. Introduction

MoS₂ is considered a potential catalyst for the hydrogen evolution reaction (HER). The practical HER activity of MoS₂ is largely determined by its phase structure. A typical MoS₂ material has 5 common phase structures, namely 1H, 2H, 1T, 1T', and 3R phases.¹⁻⁴ The most thermodynamically stable MoS₂ phase is the 2H phase.⁵ However, only the edge sites of 2H-MoS₂ display good HER catalytic activity, and a large number of in-plane sites are catalytically inert.^{6,7} In comparison, 1T-MoS₂ shows better electronic conductivity^{8,9} and higher hydrophilicity.¹⁰ In addition, it has a unique electronic structure that is favorable for the HER. Unfortunately, 1T-MoS₂ is thermodynamically unstable and thus difficult to prepare with routine synthetic approaches.¹¹

It is of great interest to obtain stable 1T-MoS₂ through a simple and controllable method for the development of high-performance

MoS₂-based HER catalysts. Typical methods for the synthesis of 1T-MoS₂ can be divided into “top-down” and “bottom-up” methods. The “top-down method” mainly includes the ion-intercalation method.^{2,9,12-17} A commonly used method is lithium-intercalation,^{13,17} where Li⁺ can be used as an electron donor after intercalation, promoting the transformation of the 2H phase to the 1T phase. However, the synthetic process is complicated. Moreover, the conversion rate of 1T-MoS₂ obtained by this process is generally lower than 80%.^{11,13} The “bottom-up method” consists of hydro-/solvothermal methods,¹⁸⁻²⁵ the Chemical Vapor Deposition (CVD) method,^{26,27} etc. Many studies have recently reported the synthesis of 1T-MoS₂ by solvothermal methods, such as that by Yang *et al.* who grew vertically aligned 2H-1T MoS₂ in DMF in a Teflon-lined stainless steel autoclave.¹⁹ This method mainly relies on the growth of MoS₂ in a solvent at low temperatures.^{19,28,29} The HER activity of 1T-MoS₂ can be further boosted by the introduction of a secondary synergistic phase that tunes the electronic status and regulates the conductive pathways of 1T-MoS₂. Intercalation of MoS₂ with carbon-based materials has been attempted to improve the HER performance.^{22,24,30-32} However, most of the reported approaches could not simultaneously achieve a high 1T phase yield, effective modulation of the electronic structure and improvement in the electronic conductivity.

In this work, carbon-intercalated 1T-MoS₂ (MoS₂-2C) was synthesized by hydrothermal treatment and subsequent carbonization with glucose as the carbon source. By control over the amount of glucose used in the synthesis, an almost pure 1T-MoS₂ phase was formed. The glucose-derived carbon did not only

^a School of Chemistry, Chemical Engineering and Life Sciences, Wuhan University of Technology, Wuhan 430070, P. R. China. E-mail: li_j@whut.edu.cn

^b Foshan Xianhu Laboratory of the Advanced Energy Science and Technology Guangdong Laboratory, Xianhu hydrogen Valley, Foshan 528200, P. R. China

^c Research Center for Materials Genome Engineering, Wuhan University of Technology, Wuhan 430070, P. R. China

^d Hubei provincial key laboratory of fuel cell, Wuhan University of Technology, 122 Luoshi Road, Wuhan 430070, P. R. China

† Electronic supplementary information (ESI) available. See DOI: 10.1039/d1ma00681a

‡ These authors contributed equally.



stabilize the 1T phase but also suppressed the stacking of MoS₂ layers, thereby increasing the exposure of catalytically active sites. Besides, the synergy of C and MoS₂ effectively modifies the electronic structure of the S sites, thus further improves the activity of MoS₂-2C. As a result of these favorable features, MoS₂-2C exhibits a promising HER performance in the acid system.

2. Experimental section

2.1 Synthetic procedures

Synthesis of MoS₂-xC. 0.62 g ammonium molybdate tetrahydrate ((NH₄)₆Mo₇O₂₄·4H₂O, *M* = 1235.8575, 0.5 mmol) and 1.14 g thiourea (CH₄N₂S, *M* = 76.12, 15 mmol) were dissolved in 35 mL deionized water, and stirred vigorously to form a uniform solution. To prepare MoS₂ intercalated with different amounts of carbon, glucose precursors with different amounts (0 g, 0.63 g, 1.26 g, 3.15 g) were added into the above mixture. After ultrasonication for 30 min, the mixture was transferred to a 50 mL PPL-stainless steel hydrothermal kettle, which was then heated to 220 °C for 18 h. After the hydrothermal reaction, the product was collected, washed with deionized water and absolute ethanol several times to remove other impurity ions, followed by drying at 60 °C in a vacuum. Next, the products were carbonized at 700 °C in an argon atmosphere (ramping rate of 5 °C min⁻¹) for 3 h. The samples prepared with different amounts of glucose precursors were denoted as MoS₂, MoS₂-1C, MoS₂-2C, and MoS₂-5C, respectively.

Synthesis of carbon (C). 0.63 g glucose (C₆H₁₂O₆, *M* = 180.16, 3.5 mmol) was dissolved in 35 mL deionized water, followed by ultrasonication for 30 min. The mixture was then transferred to a 50 mL PPL-stainless steel hydrothermal kettle and hydrothermally treated and cleaned with the procedures described above.

2.2 Characterization

Raman spectroscopy was used to characterize the chemical composition and chemical state. The measurement range was 20–3000 cm⁻¹ (532 nm). The XRD pattern was obtained with the Empyrean X-ray diffractometer manufactured by Malvern Panalytical Company in the Netherlands. The wide-angle X-ray diffraction test was performed and the scanning range was 5–90°. The scanning electron microscope testing was conducted using a JSM-IT300 field emission scanning electron microscope manufactured by JEOL Co., Ltd and the accelerating voltage was 20.0 kV. The transmission electron microscope testing was performed using a JEM-2100F transmission electron microscope made by JEOL Ltd. The XPS spectrum was obtained from Thermo Scientific K-Alpha from ThermoFisher (Mono Al K α). The nitrogen adsorption-desorption curves were measured by the ASAP2460 analyzer from Micromeritics, USA, and the test was performed under 77 K liquid nitrogen. The sample was degassed at 200 °C for 12 h before testing. The Elementar vario MICRO cube was used to analyze the content of C, H, N, and S in the sample.

2.3 Electrochemical Measurement

5 mg sample was evenly dispersed in 900 μ L isopropanol, 100 μ L deionized water, and 20 μ L of Nafion solution (5 wt%). 20 μ L of the above ink was transferred to the rotating disk electrode (5 mm). 20 wt% commercial Pt/C was chosen to make a comparison. After naturally drying, the film was applied to test. All electrochemical tests were completed by the Correst Electrochemical Workstation in a three-electrode system in 0.5 M H₂SO₄. The rotating disk electrode coated with the catalyst acted as the working electrode, the saturated calomel electrode (SCE) was selected as the reference electrode, and the graphite electrode was applied as the counter electrode. The electrode was activated firstly by CV scanning during -0.3 to 0.4 V (*vs.* SCE) and the scan speed was set as 500 mV s⁻¹. The polarization curve was obtained by linear sweep voltammetry (LSV), the rotating disk electrode speed was set to 1600 rpm, the potential scanning range was -1 to 0 V (*vs.* SCE), and the scanning speed was 2 mV s⁻¹. To obtain the *C*_{dl} value, CV scans were performed at scan speeds of 20, 40, 60, 80, and 100 mV s⁻¹, and the scan potential window was set to -0.25 to -0.05 V (*vs.* SCE). The ECSA can be calculated using eqn (1).³³ The electrochemical impedance spectrum (EIS) test was measured at a potential of -0.5 V (*vs.* SCE). The frequency test range is 0.1 to 10⁵ Hz and the amplitude is 5 mV. The stability was tested by the CV method, the scan range was set to -0.3–0.1 V (*vs.* RHE), the number of cycles was set to 2000, and the changes in the LSV curve were compared before and after 2000 cycles. The chronoamperometry test was also applied under an overpotential of 260 mV (without *iR* correction) to explore the stability. *iR* compensation (100%) was applied using the solution resistance measured by the EIS tests. The potential was converted by eqn (2), and the value was obtained by calibration test.

$$\text{ECSA} = \frac{C_{dl}}{60 \mu\text{F cm}^{-2} \text{ per cm}_{\text{ECSA}}^2} \quad (1)$$

$$E_{\text{RHE}} = E_{\text{SCE}} + 0.269 \text{ V} \quad (2)$$

2.4 Theoretical calculations

The 1T-MoS₂ unit cell was imported from the crystal structure database, and the unit cell constant was optimized. A slab model was built toward (002), the vacuum layer was set to 15 Å, and the cell constant was 13.33 Å. The structure of V_S-1T-MoS₂ with sulfur defects was obtained by deleting an S atom based on the above structure. To simulate the effect of carbon (C) on the hydrogen evolution activity of 1T-MoS₂, a heterojunction structure of 1T-MoS₂/C was constructed in which C was simulated by the graphite structure. The hydrogen adsorption model was built by adding H atoms about 1.41 Å above the S atoms on the corresponding structure surface.

All model optimization and energy calculation were completed by the DMol3 module of Materials Studio.^{34,35} The generalized gradient approximation method (GGA) and



Perdew–Burke–Ernzerhof (PBE) function were used to deal with the exchange–correlation energy,³⁶ and the DSPP (DFT Semi-core Pseudopotentials) method was used to process the core electrons.³⁷ The basis set chosen was DNP. The convergence criteria for energy change, max force and displacement of atoms were set to 1×10^{-5} Ha, 2×10^{-3} Ha \AA^{-1} and 5×10^{-3} \AA , respectively. After a convergence test, the accuracy of orbital cutoff was set to 4.9 \AA and the k points for structural optimization and calculation of electronic structure properties were set to $4 \times 4 \times 1$ and $6 \times 6 \times 1$, respectively. To simulate the aqueous environment, the Conductor-like Screening Model (COSMO) model³⁸ was introduced when calculating the hydrogen adsorption energy, the solvent was water and the electrostatic constant was set to 78.54. Besides, considering the existence of van der Waals forces in two-dimensional materials, Grimme's DFT-D method was used to correct van der Waals forces in the calculation process.³⁹ The calculation and analysis of electron density differences were completed by the CASTEP module.⁴⁰ The calculation formulas were as follows.

$$\Delta G_{H^*} = \Delta E_H + 0.25 \text{ eV} \quad (3)$$

$$\Delta E_H = E(\text{MoS}_2 + \text{H}) - E(\text{MoS}_2) - 1/2E(\text{H}_2) \quad (4)$$

where ΔG_{H^*} represents the free energy of the reaction and it can be calculated using eqn (3),⁴¹ ΔE_H represents the energy of adsorption, $E(\text{MoS}_2 + \text{H})$ represents the energy of the surface with an H adsorbed, $E(\text{MoS}_2)$ represents the energy of the MoS₂ surface, and $E(\text{H}_2)$ represents the energy of hydrogen.

Results and discussion

The samples were prepared with a simple hydrothermal process, followed by a carbonization procedure as shown in Scheme 1. By varying the glucose content used in the hydrothermal process, we synthesized MoS₂-1C, MoS₂-2C, MoS₂-5C, pure MoS₂, and pure C (only glucose was added).


Then, the effect of glucose on the structure of MoS₂, especially the phase structure, was explored through characterizations and theoretical calculations. As we can see from the Raman spectrum (Fig. 1(a)), the pure MoS₂ sample only has the in-plane vibration E_{2g}^1 peak (378 cm^{-1}) and the out-of-plane vibration A_{1g} peak (404 cm^{-1}), which are assigned to 2H-MoS₂. Characteristic peaks of 1T-MoS₂, J_1 (142 cm^{-1}), J_2 (232 cm^{-1}), and J_3 (330 cm^{-1}) peaks can be observed in the spectra of MoS₂-1C and MoS₂-2C samples. In addition, the obvious E_{1g} peak at 278 cm^{-1} can also be seen that is related to the octahedral structure of 1T-MoS₂.¹¹ These results

indicated glucose assisted the formation of 1T-MoS₂. The Raman spectra of MoS₂-1C, MoS₂-2C, and MoS₂-5C also showed peaks assigned to the carbon (D band at 1360 cm^{-1} and G band at 1580 cm^{-1}) in Fig. 1(a).⁴² Particularly, only peaks from the carbon could be identified in the Raman spectra of MoS₂-5C, which resulted from the excess glucose used in the synthesis.

XRD measurements were conducted to further analyze the crystal structure of the catalysts. It's noted in Fig. 1(b) that pristine MoS₂ showed peaks at 14.38° , 32.68° , 33.51° , and 39.54° , corresponding to (002), (100), (101), and (103) of 2H-MoS₂ (JCPDS card number: 37-1492), respectively. While for MoS₂-xC, the (002) peak shifted negatively, which appeared at 9.83° , 9.04° , and 8.85° for MoS₂-1C, MoS₂-2C, and MoS₂-5C, respectively. These interplanar spacings were calculated to be 0.90 nm, 0.98 nm, and 1.00 nm. Besides, a second diffraction peak of the MoS₂-2C was present at $2\theta = 17.75^\circ$. These results further proved that 1T-MoS₂ was successfully synthesized with the addition of glucose.¹¹

The porous features of the samples were investigated with a N₂ adsorption–desorption isotherm. As shown in Fig. 1(c), MoS₂, MoS₂-1C, MoS₂-2C, and MoS₂-5C exhibit typical IV isotherm characteristics. The hysteresis loop is attributed to common features of the seam structure of two-dimensional MoS₂. The pore size distribution curves were obtained by the BJH method (Fig. S1, ESI[†]), and MoS₂-1C, MoS₂-2C and raw carbon display plenty of micropores and mesopores. The BET surface area and pore volume were analyzed from isotherms and are shown in Table S1 (ESI[†]). Among them, MoS₂-2C displays the largest specific surface area ($130 \text{ m}^2 \text{ g}^{-1}$) and pore volume ($0.39 \text{ cm}^3 \text{ g}^{-1}$), which may be related to its high 1T phase ratio and less stacked structures. Since additional precursors were introduced in the synthesis of MoS₂-xC, the morphology of the thus-formed carbon is distinct from the pristine carbon (synthesized using identical hydrothermal conditions). Therefore, the measured BET surface area of MoS₂-xC was largely different from that of pristine carbon. Compared to MoS₂-xC, pristine carbon has an abundant microporous structure, which contributed to its large specific surface area.

The relative contents of different elements in different samples were estimated through organic element analysis (Fig. 1(d) and Table S2 ESI[†]). The mass percentage of C in the MoS₂-2C sample is about 23.8 wt%. Parts of carbon were intercalated to the interlayer of MoS₂ which was proved by the increased interlayer spacing determined from XRD (Fig. 1(b)) and HRTEM (Fig. 2(b)) analysis. In addition, carbon aggregates also formed between MoS₂ nanoparticles (Fig. S9(b), ESI[†]). The proportion of these two types of carbon is difficult to identify and will be investigated in future studies. It is worth noting that the sample may contain a small amount of O element, but no obvious oxide species were observed in the test and through characterization such as XRD, indicating that the O content is extremely low. Assuming that oxygen is absent in MoS₂-xC, the atomic percentage of Mo and S can be calculated. The n_S/n_{Mo} in all MoS₂-xC samples is less than 2, which indicates these samples contain S vacancy defects that may result from the excess thiourea.⁴³

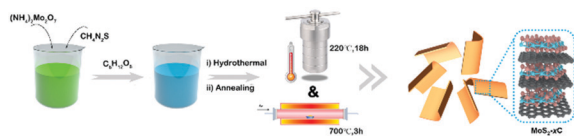

Scheme 1 Schematic illustration for the synthesis of MoS₂-xC.



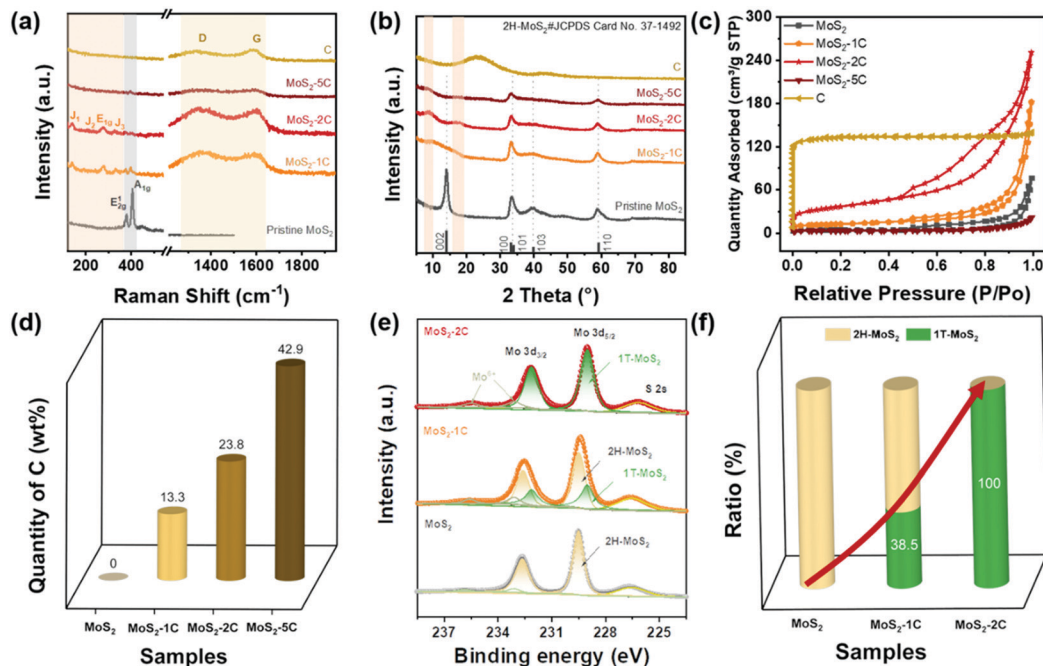


Fig. 1 (a) Raman spectrum, (b) XRD pattern for $\text{MoS}_2\text{-xC}$ and C, (c) N_2 adsorption–desorption type IV isotherms measured at 77 K of $\text{MoS}_2\text{-xC}$ and C, (d) the comparison of carbon content in $\text{MoS}_2\text{-xC}$, and (e and f) XPS spectra comparisons among MoS_2 , $\text{MoS}_2\text{-1C}$, and $\text{MoS}_2\text{-2C}$.

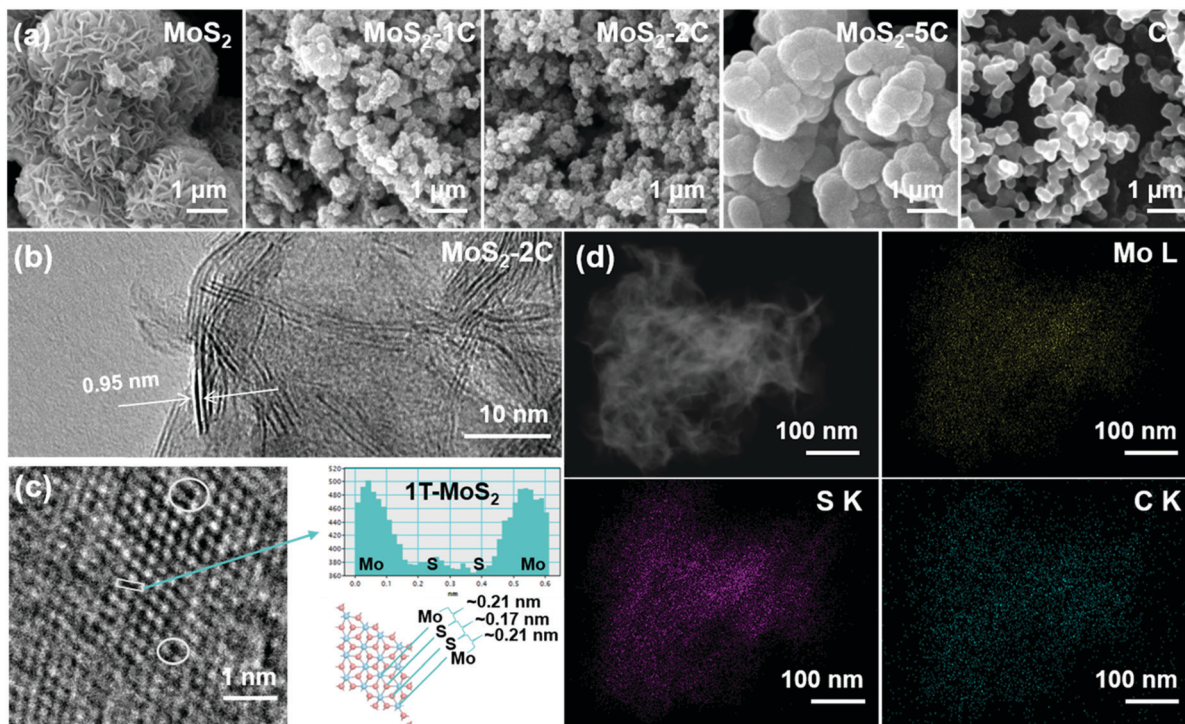


Fig. 2 (a) SEM image of MoS_2 , $\text{MoS}_2\text{-xC}$ and C. (b) TEM image of $\text{MoS}_2\text{-2C}$. (c) The enlarged HRTEM image of $\text{MoS}_2\text{-2C}$ (the white circles represent the region of S vacancy). (d) High-Angle Annular Dark Field TEM images of the nanoflake and corresponding element mapping of $\text{MoS}_2\text{-2C}$.

The element and phase composition of $\text{MoS}_2\text{-2C}$, $\text{MoS}_2\text{-1C}$, and MoS_2 were further analyzed by the XPS spectra (Fig. 1(e), and Fig. S2 and S3, ESI[†]). As shown in Fig. 1(e), the binding

energies of Mo $3d_{5/2}$ and $3d_{3/2}$ peaks are located at 229.0 eV and 232.1 eV in 1T- MoS_2 , respectively.¹¹ The binding energies of Mo $3d_{5/2}$ and $3d_{3/2}$ peaks are 229.5 eV and 232.6 eV in 2H- MoS_2 ,



respectively.¹¹ In addition, there are Mo⁶⁺ peaks at binding energies of 233.1 eV and 235.6 eV, and S 2s peaks can be seen at 226.5 eV. The proportion of the 1T phase in MoS₂-x C can be calculated by the ratio of integrated peak areas of the 1T phase and 2H phase (Fig. 1(f)). The proportion of the 1T phase in MoS₂, MoS₂-1C, and MoS₂-2C was calculated to be 0%, 38.5%, and 100%, respectively. Combined with the analysis of Raman and XPS data, it can be concluded reasonably that the phase structure in MoS₂-x C can be effectively adjusted by controlling the amount of glucose in the hydrothermal synthesis. The S vacancy was further verified by the XPS results (eqn (S2) and Table S3, ESI[†]). The values of $n_{(S)}/n_{(Mo)}$ in 1T-MoS₂ for MoS₂-1C and MoS₂-2C are both smaller than 2.0 while the values in 2H-MoS₂ for MoS₂-1C and MoS₂ are very close to 2.0, which indicates that S vacancies preferably existed in the 1T phase of MoS₂-1C and MoS₂-2C. Furthermore, it was proved by the smaller formation energy of the S vacancy in 1T-MoS₂ obtained by DFT calculations (Fig. S5 and eqn (S1), ESI[†]). The existence of S vacancies may enhance the intrinsic hydrogen evolution activity of 1T-MoS₂.

The morphology of MoS₂-x C was observed using a scanning electron microscope (SEM, Fig. 2(a)). Pristine MoS₂ seems like nanoflowers with abundant nanoflakes on the surface. The morphology of MoS₂-1C and MoS₂-2C is similar to that of pristine MoS₂, but their size is significantly smaller, which suggests that glucose effectively inhibits the layer stacked during the growth of MoS₂. The nanostructures of MoS₂-1C and MoS₂-2C can provide abundant reaction sites for the hydrogen evolution reaction. With the amount of glucose increasing in the synthesis, carbon is the main component wrapping MoS₂ layer by layer. The surface of the MoS₂-5C nanoparticle is smooth and similar to that of pristine C (Fig. 2(a)). TEM and EDS were carried out on MoS₂-2C to further explore the internal structure and composition of the sample. In the HRTEM image of MoS₂-2C (Fig. 2(b)), the interlayer spacing was measured to be 0.95 nm. This value is close to the layer spacing of 0.98 nm measured by XRD (Fig. 1(b)), which also proved that the 1T phase structure was successfully obtained. The distance between atoms was also analyzed with

an HRTEM image, and the relative atomic coordinate position 1T-MoS₂ structure can be observed (Fig. 2(c)). The atomic signal was projected into the same plane, and the distance between the Mo atom and S atom is about 0.21 nm, while the atomic distance between S and S is about 0.17 nm, which is quite different from the overlap of the projection signals of two S atoms in the 2H phase structure. Moreover, some defects can be observed in HRTEM images (marked with white circles in Fig. 2(c)). Fig. 2(d) shows High-Angle Annular Dark Field TEM images and corresponding element mapping of MoS₂-2C. As can be seen in the figure, the Mo, S, and C elements are evenly distributed in the structure, which suggests the even intercalation of carbon in the 1T-MoS₂ layers.

To analyze the synergy between carbon and 1T-MoS₂, a series of theoretical calculations were carried out. Different structural models, including 1T-MoS₂, 1T-MoS₂ with S vacancy (Vs-1T-MoS₂) and carbon intercalated 1T-MoS₂ with S vacancy (Vs-1T-MoS₂/C) (shown in Fig. S4, ESI[†]). Firstly, the electron density difference of Vs-1T-MoS₂/C was calculated and the result is shown in Fig. 3(a). The red region indicates the electron-rich area, and the purple region indicates the lack of electrons. This result suggests electron transfer from intercalated C to 1T-MoS₂. This kind of electron transfer process may enhance the structural stability of 1T-MoS₂.¹¹ Such a modification on the electronic structure of 1T-MoS₂ may enhance its electrocatalytic activity. The free energy of HER was calculated on 1T-MoS₂, Vs-1T-MoS₂ and Vs-1T-MoS₂/C (Fig. 3(b)). For the pure 1T-MoS₂, the value is determined to be -0.95 eV which means the H atom could be easily adsorbed onto the S site. However, the hydrogen generation and desorption process are kinetically difficult. After an S-vacancy is introduced in 1T-MoS₂, the free energy is reduced to -0.32 eV, which is closer to the ideal value of 0 eV, while the value of Vs-1T-MoS₂/C is only 0.10 eV, which suggests that a carbon-intercalated structure can modify the electron structure of 1T-MoS₂ and is beneficial for the HER process.

Based on the above discussion, MoS₂-2C has a high proportion of 1T phase, a large specific surface area, and favorable electronic structures. Therefore, its better HER activity can be

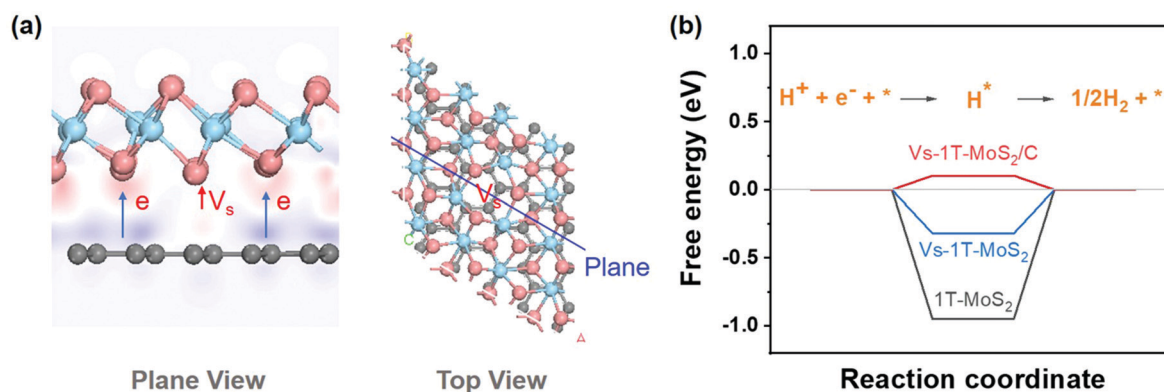


Fig. 3 (a) Diagram of electron density difference (pink atoms represent S, blue atoms represent Mo, and gray atoms represent C). (b) The diagram of free energy change of the HER.



expected. A series of electrochemical tests were performed to explore the electrochemical performance of MoS₂-x/C and the test device is shown in Fig. S6 (ESI†). Fig. 4(a) shows the LSV polarization curves of different samples. The onset overpotentials of MoS₂, MoS₂-1C, MoS₂-2C, MoS₂-5C, and C were 220, 203, 120, 242, and 382 mV, respectively. When the current density reached 10 mA cm⁻², the overpotential values were 366, 291, 217, 461, and 620 mV, respectively. Among all the samples, MoS₂-2C had the best electrochemical performance. The HER Tafel slope of MoS₂-2C was only 94 mV dec⁻¹, which indicates faster kinetics, while the Tafel slopes of MoS₂, MoS₂-1C, MoS₂-5C, and C were 144, 98, 207, and 258 mV dec⁻¹, respectively (Fig. 4(b)).

To exclude the influence of varying MoS₂ content in different samples when assessing their electrochemical performance, the measured LSV curves were normalized to the weight of MoS₂ by the results of elemental analysis (Fig. S7, ESI†). The same performance trend was observed among these samples and MoS₂-2C still exhibited the highest activity. To explore the role of carbon in the HER, MoS₂ synthesized under the same synthesis conditions was directly mixed with the same quantity of carbon as MoS₂-2C. The electrochemical performance of this composite sample (termed MoS₂@2C) is also characterized. When the current density reached 10 mA cm⁻², the overpotential of MoS₂@2C is 118 mV higher than MoS₂-2C (Fig. 4(c)), indicating that the excellent HER performance of MoS₂-2C not only stems from the improved electronic conductivity due to the incorporation of carbon but mostly originates from the higher composition of an active 1T phase.

CV measurements were conducted to discuss the electrochemical surface area of the samples. Fig. S8 (ESI†) displays the

CV curves obtained for each sample at different scanning speeds in the non-faradaic current region and Fig. 4(d) shows capacitive currents as a function of scanning rate in a non-faradaic region. The electric double layer capacitances C_{dl} of MoS₂, MoS₂-1C, MoS₂-2C, MoS₂-5C, and carbon are respectively obtained as 1.36, 10.3, 15.0, 0.955, and 7.22 mF cm⁻². The capacitance value of the electric double layer of the ideal smooth oxide electrode is 60 μF cm^{-2.33} so that the ECSA value of MoS₂, MoS₂-1C, MoS₂-2C, MoS₂-5C, and C was 22.7, 172, 250, 15.9, and 120 cm_{ECSA}², respectively. This result agrees well with the BET surface area result and MoS₂-2C had the highest electrochemically active surface area. Besides, the sample also showed little attenuation (Fig. 4(e)) after 2000 cycles of CV scanning from -0.3 V to 0.1 V (vs. RHE). The SEM and XPS tests of MoS₂-2C were conducted after the chronoamperometry test was conducted under an overpotential of 260 mV (vs. RHE) for 10 hours. There was no obvious change in the morphology of MoS₂-2C after 10 h stability test, which still retained the nanoflower-like shape in Fig. S9 (ESI†). We compared the high-resolution XPS spectra of Mo 3d and S 2p of MoS₂-2C after and before the stability test (Fig. S10, ESI†), which did not display obvious element state and composition changes that happened after the stability test. Therefore, MoS₂-2C developed in this work was proved to exhibit promising stability.

The electrochemical impedance spectroscopy test and analysis were also performed (Fig. 4(f)) and the charge transfer resistance (R_{ct}) was obtained by fitting. MoS₂-2C also has the smallest charge transfer resistance value (only 35 Ω). The relevant electrochemical performance data are summarized in Table S4 (ESI†). Such a low R_{ct} of MoS₂-2C can be correlated to its unique electronic structure, as outlined in the theoretical

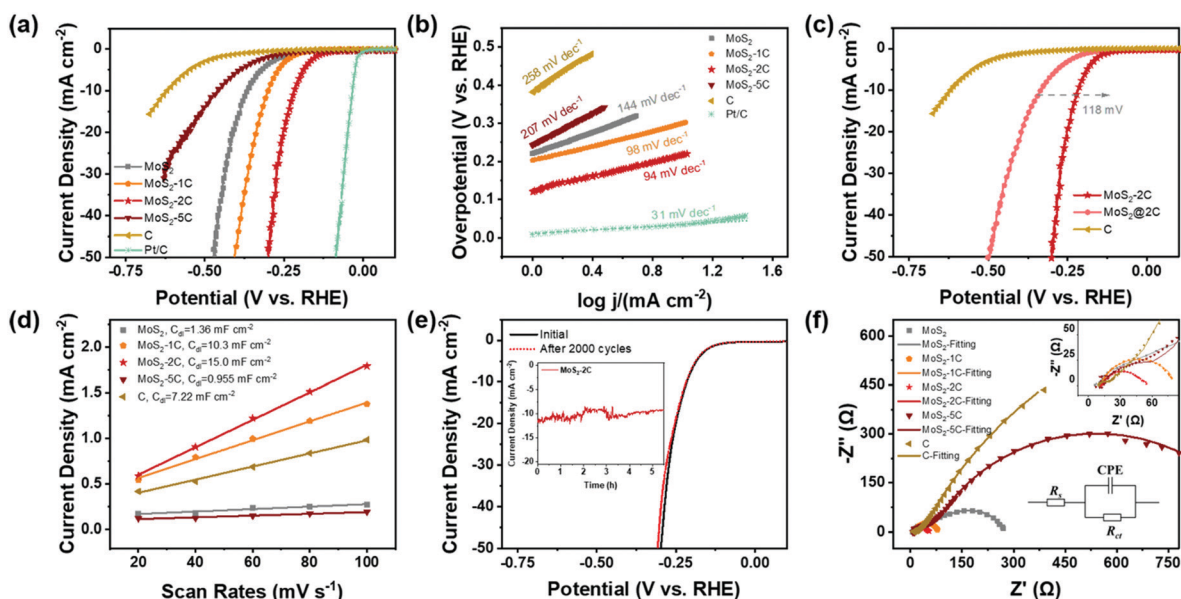


Fig. 4 (a) LSV curves (100% *iR*-corrected), (b) Tafel plots (calculated from *iR* corrected lines), and (c) LSV curves of different samples. (d) Capacitive currents of the samples as a function of scanning rate in a non-faradaic region. (e) LSV curves of MoS₂-2C before and after 2000 CV cycles (chronoamperometry test under an overpotential of 260 mV without *iR* correction inserted). (f) EIS spectra of MoS₂-x/C and C in 0.5 M H₂SO₄ at -0.5 V versus SCE.



calculations. A brief comparison of the electrochemical performance of MoS₂-2C with representative HER catalysts reported recently is also provided (Table S5, ESI†). It can be seen from the table that MoS₂-2C has promising HER catalytic activity among many similar materials reported.

Conclusions

In this paper, a carbon intercalated 1T-MoS₂ electrocatalyst (MoS₂-2C) was synthesized as an HER electrocatalyst. The structure and performance characterizations show that MoS₂-2C has a high content of catalytically active 1T phase. Besides, it displays abundant S vacancies and a big electrochemical surface area. The intercalated carbon can not only increase the electron density of MoS₂ to stabilize 1T-MoS₂ but can also modify the electronic structure of the S site, leading to an optimized HER free energy (as low as 0.10 eV). Therefore, MoS₂-2C shows promising HER activity ($\eta = 217$ mV@10 mA cm⁻²) and stability in 0.5 M H₂SO₄. We expect that the synthetic approach and the understanding of the performance of MoS₂-2C can provide insight into the future development of advanced HER catalysts.

Author contributions

Jun Xu and Xinjiao Cui contributed equally. Jun Xu, Xinjiao Cui, and Zhengwen Fan performed the conceptualization, data curation and formal analysis; Xinxin Zhu conducted the investigation; Wei Guo and Junsheng Li contributed to the funding acquisition, project administration and supervision; Dan Liu, Deyu Qu, Zhizhong Xie and Haolin Tang contributed to the methodology; Jun Xu and Junsheng Li contributed to the visualization and writing.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

The authors thank the National Natural Science Foundation of China (Grant No. 51972254), Foshan Xianhu Laboratory of the Advanced Energy Science and Technology Guangdong Laboratory (XHD2020-002-04) and Fundamental Research Funds for the Central Universities (WUT: 2020IB025) for the financial support.

Notes and references

- M. Chhowalla, D. Voiry, J. Yang, H. S. Shin and K. P. Loh, *MRS Bull.*, 2015, **40**, 585–591.
- Z. He and W. Que, *Appl. Mater. Today*, 2016, **3**, 23–56.
- A. P. Nayak, T. Pandey, D. Voiry, J. Liu, S. T. Moran, A. Sharma, C. Tan, C.-H. Chen, L.-J. Li, M. Chhowalla, J.-F. Lin, A. K. Singh and D. Akinwande, *Nano Lett.*, 2015, **15**, 346–353.
- T. Heine, *Acc. Chem. Res.*, 2015, **48**, 65–72.
- W. Zhao and F. Ding, *Nanoscale*, 2017, **9**, 2301–2309.
- T. F. Jaramillo, K. P. Jorgensen, J. Bonde, J. H. Nielsen, S. Horch and I. Chorkendorff, *Science*, 2007, **317**, 100–102.
- B. Hinnemann, P. G. Moses, J. Bonde, K. P. Jørgensen, J. H. Nielsen, S. Horch, I. Chorkendorff and J. K. Nørskov, *J. Am. Chem. Soc.*, 2005, **127**, 5308–5309.
- S. S. Chou, Y.-K. Huang, J. Kim, B. Kaehr, B. M. Foley, P. Lu, C. Dykstra, P. E. Hopkins, C. J. Brinker, J. Huang and V. P. Dravid, *J. Am. Chem. Soc.*, 2015, **137**, 1742–1745.
- M. Acerce, D. Voiry and M. Chhowalla, *Nat. Nanotechnol.*, 2015, **10**, 313–318.
- A. B. Farimani, K. Min and N. R. Aluru, *ACS Nano*, 2014, **8**, 7914–7922.
- Z. Lei, J. Zhan, L. Tang, Y. Zhang and Y. Wang, *Adv. Energy Mater.*, 2018, **8**, 1703482.
- R. Zhang, I. L. Tsai, J. Chapman, E. Khestanova, J. Waters and I. V. Grigorieva, *Nano Lett.*, 2016, **16**, 629–636.
- Y. Yin, J. Han, Y. Zhang, X. Zhang, P. Xu, Q. Yuan, L. Samad, X. Wang, Y. Wang, Z. Zhang, P. Zhang, X. Cao, B. Song and S. Jin, *J. Am. Chem. Soc.*, 2016, **138**, 7965–7972.
- S. Yan, W. Qiao, X. He, X. Guo, L. Xi, W. Zhong and Y. Du, *Appl. Phys. Lett.*, 2015, **106**, 012408.
- P. Gao, L. Wang, Y. Zhang, Y. Huang and K. Liu, *ACS Nano*, 2015, **9**, 11296–11301.
- D. Kiriya, M. Tosun, P. Zhao, J. S. Kang and A. Javey, *J. Am. Chem. Soc.*, 2014, **136**, 7853–7856.
- Y. Li, L. Wang, S. Zhang, X. Dong, Y. Song, T. Cai and Y. Liu, *Catal. Sci. Technol.*, 2017, **7**, 718–724.
- Y. Li, H. Wang, L. Xie, Y. Liang, G. Hong and H. Dai, *J. Am. Chem. Soc.*, 2011, **133**, 7296–7299.
- J. Yang, K. Wang, J. Zhu, C. Zhang and T. Liu, *ACS Appl. Mater. Interfaces*, 2016, **8**, 31702–31708.
- Z. Liu, Z. Gao, Y. Liu, M. Xia, R. Wang and N. Li, *ACS Appl. Mater. Interfaces*, 2017, **9**, 25291–25297.
- D. Wang, X. Zhang, S. Bao, Z. Zhang, H. Fei and Z. Wu, *J. Mater. Chem. A*, 2017, **5**, 2681–2688.
- S. Jayabal, G. Saranya, Y. Liu, D. Geng and X. Meng, *Sustainable Energy Fuels*, 2019, **3**, 2100–2110.
- Z. Liu, L. Zhao, Y. Liu, Z. Gao, S. Yuan, X. Li, N. Li and S. Miao, *Appl. Catal., B*, 2019, **246**, 296–302.
- N. Wang, Y. Zhou, S. Yousif, T. Majima and L. Zhu, *ACS Appl. Mater. Interfaces*, 2019, **11**, 34430–34440.
- H. Niu, Z. Zou, Q. Wang, K. Zhu, K. Ye, G. Wang, D. Cao and J. Yan, *Chem. Eng. J.*, 2020, **399**, 125672.
- D. Voiry, M. Salehi, R. Silva, T. Fujita, M. Chen, T. Asefa, V. B. Shenoy, G. Eda and M. Chhowalla, *Nano Lett.*, 2013, **13**, 6222–6227.
- L. Tao, X. Duan, C. Wang, X. Duan and S. Wang, *Chem. Commun.*, 2015, **51**, 7470–7473.
- L. Cai, J. He, Q. Liu, T. Yao, L. Chen, W. Yan, F. Hu, Y. Jiang, Y. Zhao, T. Hu, Z. Sun and S. Wei, *J. Am. Chem. Soc.*, 2015, **137**, 2622–2627.
- S. Shi, D. Gao, B. Xia, P. Liu and D. Xue, *J. Mater. Chem. A*, 2015, **3**, 24414–24421.



- 30 A. R. P. Santiago, T. He, O. Eraso, M. A. Ahsan, A. N. Nair, V. S. N. Chava, T. Zheng, S. Pilla, O. Fernandez-Delgado, A. Du, S. T. Sreenivasan and L. Echegoyen, *J. Am. Chem. Soc.*, 2020, **142**, 17923–17927.
- 31 J. He, G. Hartmann, M. Lee, G. S. Hwang, Y. Chen and A. Manthiram, *Energy Environ. Sci.*, 2019, **12**, 344–350.
- 32 H. Deng, C. Zhang, Y. Xie, T. Tumlin, L. Giri, S. P. Karna and J. Lin, *J. Mater. Chem. A*, 2016, **4**, 6824–6830.
- 33 C. Wei, S. Sun, D. Mandler, X. Wang, S. Z. Qiao and Z. J. Xu, *Chem. Soc. Rev.*, 2019, **48**, 2518–2534.
- 34 B. Delley, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 2002, **66**, 155125.
- 35 B. Delley, *J. Chem. Phys.*, 2000, **113**, 7756–7764.
- 36 J. P. Perdew, K. Burke and M. Ernzerhof, *Phys. Rev. Lett.*, 1996, **77**, 3865–3868.
- 37 B. Delley, *J. Chem. Phys.*, 1990, **92**, 508–517.
- 38 A. Klamt and G. Schüürmann, *J. Chem. Soc., Perkin Trans. 2*, 1993, 799–805.
- 39 E. R. McNellis, J. Meyer and K. Reuter, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 2009, **80**, 205414.
- 40 M. D. Segall, P. J. D. Lindan, M. J. Probert, C. J. Pickard, P. J. Hasnip, S. J. Clark and M. C. Payne, *J. Phys.: Condens. Matter*, 2002, **14**, 2717–2744.
- 41 Q. Tang and D.-E. Jiang, *ACS Catal.*, 2016, **6**, 4953–4961.
- 42 A. C. Ferrari and J. Robertson, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 2000, **61**, 14095–14107.
- 43 J. Xie, H. Zhang, S. Li, R. Wang, X. Sun, M. Zhou, J. Zhou, X. W. Lou and Y. Xie, *Adv. Mater.*, 2013, **25**, 5807–5813.

