


Cite this: *RSC Adv.*, 2021, **11**, 29156

Received 14th May 2020  
Accepted 20th August 2021

DOI: 10.1039/d0ra04324a

rsc.li/rsc-advances

# Elucidating the influence of molten salt chemistries on the synthesis and stability of perovskites oxides†

Benjamin Levitas,<sup>a</sup> Spencer Piligian,<sup>b</sup> Thomas Ireland<sup>c</sup> and Srikanth Gopalan<sup>\*ad</sup>

In this work, we investigate the synthesis of  $(\text{La}_{0.8}\text{Sr}_{0.2})\text{MnO}_3$  (LSM) in various molten salts to gain insight on the influence of molten salt ions for synthesizing materials critical for energy applications. LSM nanoparticles with a size range of  $\sim 10$ – $200$  nm and with target stoichiometries were formed from oxide precursors *via* feeding into  $\text{KNO}_3$ . Furthermore, feeding precursors into the melt compared to mixing and heating from room temperature results in complete formation of LSM that was otherwise unattainable using conventional molten salt synthesis methods. In  $\text{LiCl}$ – $\text{KCl}$  eutectic, the high Lux acidity of  $\text{Li}^+$  and  $\text{Cl}^-$  establishes a thermodynamic barrier that impedes Sr from reacting with other precursors in solution and increases Sr stability in the melt compared to the perovskite phase. As a result, LSM will not form in a  $\text{LiCl}$ – $\text{KCl}$  eutectic under ambient conditions. Thus, this study further explicates the molten salt synthesis for perovskites and can serve as a guide for future syntheses.

## Introduction

Perovskite type oxides (PTOs) are prevalent in numerous applications such as superconductors, catalysts, electronics, magnets, and fuel cells.<sup>1–4</sup> In particular,  $\text{La}_{1-x}\text{Sr}_x\text{MnO}_{3-\delta}$  (LSM) is a widely used oxygen electrode material for solid oxide fuel cells (SOFCs) and solid oxide electrolysis cells (SOECs). Synthesizing LSM, however, requires sintering temperatures above  $1000^\circ\text{C}$  for as long as 10 hours.<sup>5–8</sup> The molten salt synthesis (MSS) method is a viable option to form PTOs at reduced temperatures. The reaction occurs in the liquid state and proceeds rapidly since diffusion in a liquid is orders of magnitude faster than in a solid and thus induces intimate and rapid contact of the precursor species. For example, the diffusion coefficient for solid state sintering of gadolinium doped ceria ranges from  $10^{-12}$  to  $10^{-8}$   $\text{cm}^2 \text{s}^{-1}$  from  $800$ – $1100^\circ\text{C}$ .<sup>9</sup> On the other hand, in a molten  $\text{LiCl}$ – $\text{KCl}$  eutectic at  $500^\circ\text{C}$ , the diffusion coefficients for lanthanides and actinides range from  $10^{-3}$  to  $10^{-5}$   $\text{cm}^2 \text{s}^{-1}$ .<sup>10</sup> By contrast, at  $500^\circ\text{C}$ , diffusion in the solid state in inorganic oxides is immeasurably slow. The rapid diffusion and reaction in the liquid solvent results in reduced temperatures and times required to form PTOs.<sup>11,12</sup> One limitation of the MSS is that the

salt system be chemically inert and have a low (but non-zero) solubility for the precursors and the product.

Molten salt systems have been widely studied and are known to contain rich and diverse chemical environments. For example, species such as superoxides and dissolved metals, which are usually nonexistent in a solid-state PTO synthesis, can be found in the MSS.<sup>13</sup> The overarching chemical basis of molten salt chemistry and synthesis is understood through the Lux-Flood acid base theory:<sup>14</sup>



The base is the oxygen ion donor and the acid the oxygen ion acceptor. The fundamental thermodynamic principles driving the formation of the product phase in the molten salt are thoroughly described by Kimura.<sup>15</sup> Essentially, reactions occur between the dissolved species in the molten salt and products precipitate out of solution once the concentration of the product species in solution in the molten salt exceeds its solubility limit. Solubilities of species within the solvent are dependent on their acidity and the oxygen ion concentration (basicity) within the melt.<sup>16</sup> Many studies have been done to synthesize perovskites using the MSS,<sup>17–19</sup> including LSM,<sup>20–22</sup> but how a particular molten salt influences the thermodynamics and kinetics of nucleation and growth has not been explicitly studied to the best of our knowledge. Moreover, studies that have presented the MSS of LSM using salts such as  $\text{LiCl}$ – $\text{KCl}$ <sup>23</sup> do not provide elemental analysis of the formed powders to determine if LSM of the target composition truly forms.

This study investigates the thermodynamic influence of molten salt cations and anions to synthesize the PTO, LSM, in five different salt systems. These salts include halide and oxo-salt eutectics such as  $\text{LiCl}$ – $\text{KCl}$ ,  $\text{LiNO}_3$ – $\text{KNO}_3$ , and  $\text{Li}_2\text{CO}_3$ – $\text{K}_2\text{CO}_3$ , as well as single oxosalts such as  $\text{LiNO}_3$  and  $\text{KNO}_3$ .

<sup>a</sup>Division of Materials Science and Engineering, Boston University, Brookline, Massachusetts 02445, USA. E-mail: sgopalan@bu.edu

<sup>b</sup>Department of Electrical and Computer Engineering, Boston University, Boston, Massachusetts 02215, USA

<sup>c</sup>Department of Earth and Environment, Boston University, Boston, Massachusetts 02215, USA

<sup>d</sup>Department of Mechanical Engineering, Boston University, Boston, Massachusetts 02215, USA

† Electronic supplementary information (ESI) available. See DOI: 10.1039/d0ra04324a



Oxosalts directly provide oxygen ions to the precursors in solution and thus increase the basicity, whereas halides do not provide oxygen ions and increase the acidity. The cations are thus varied between  $\text{Li}^+$  and  $\text{K}^+$  to directly compare the high acidity of  $\text{Li}^+$  to the more basic  $\text{K}^+$ .<sup>24</sup> This study focuses on using oxide precursors for LSM. Past studies detailing LSM MSS use nitrate precursors,<sup>20–22</sup> which are hygroscopic, require specific storing conditions, and lack easy bulk preparation for scalable production of LSM. Furthermore, we apply a feeding procedure that has been previously employed to synthesize  $\text{LaCoO}_3$  nanoparticles with dramatically reduced particle size compared to when  $\text{LaCoO}_3$  precursors were heated up to the dwell temperature<sup>25</sup> (see ESI† for all methodologies). However, the present study also highlights how effectively this feeding procedure facilitates the formation of LSM. Moreover, the feeding procedure provides a way to bypass certain pitfalls of conventional MSS methods for LSM production. A combination of X-ray diffraction (XRD), Energy Dispersive X-ray Spectroscopy (EDX), and Inductively Coupled Plasma Mass Spectrometry (ICP-MS) reveals that PTO structures can form in all salts tested, but the increased Lux acidity of a molten salt impedes pure phase formation of LSM. In doing so, we present a deeper understanding of molten salt chemistries in the context of LSM formation, which can be applied to synthesize other relevant highly ordered, complex PTOs for energy applications.


## Results and discussion

### Influence of molten salt anion on LSM formation

The XRD patterns for high temperature calcined (HTC) LSM, molten salt attempted synthesis in  $\text{Li}_2\text{CO}_3\text{--K}_2\text{CO}_3$  eutectic,

$\text{LiNO}_3\text{--KNO}_3$  eutectic, and  $\text{LiCl--KCl}$  eutectic are shown together in Fig. 1. Each of the three attempted MSS LSM patterns contain peaks that correspond to LSM when compared to the HTC pattern, yet there are a significant number of peaks matched to secondary phases besides LSM. In particular, when the synthesis was performed in  $\text{Li}_2\text{CO}_3\text{--K}_2\text{CO}_3$  and  $\text{LiNO}_3\text{--KNO}_3$ , peaks for leftover  $\text{SrCO}_3$  are present.  $\text{Li}_2\text{CO}_3$  is identified in the  $\text{Li}_2\text{CO}_3\text{--K}_2\text{CO}_3$  pattern since  $\text{Li}_2\text{CO}_3$  has an extremely low solubility in water<sup>26</sup> and remained in the powder mixture even after washing for more than 20 times. While the  $\text{LiCl--KCl}$  synthesis pattern does not contain any leftover reactants, there are peaks matched to  $\text{Li}_2\text{MnO}_3$ . In fact,  $\text{Li}_2\text{MnO}_3$  is indexed for all three of the patterns of molten salt synthesized powders. Since the  $\text{LiCl--KCl}$  synthesized powder did not contain any leftover  $\text{SrCO}_3$  based on XRD, this powder was analyzed using SEM EDX to compare the elemental composition to HTC LSM. As shown in Fig. 1b and c, the Sr L-line around 1.8 keV in the  $\text{LiCl--KCl}$  synthesized powder is substantially lower than the corresponding peak for HTC LSM. Moreover, the major Mn K-line around 5.9 keV for  $\text{LiCl--KCl}$  synthesized powder is diminished to that in the HTC LSM spectrum. These two results indicate that (1) LSM does not appreciably form in any of the eutectic molten salts analyzed under these conditions and (2) the  $\text{La}_{1-x}\text{MnO}_3$  perovskite that forms in  $\text{LiCl--KCl}$  is Mn-deficient compared to HTC LSM perovskite as a result of the  $\text{Li}^+$  reacting with the leftover  $\text{Mn}_2\text{O}_3$  precursor.

The molten salt syntheses were repeated, but instead the amount of molten salt eutectics was adjusted relative to the LSM oxide precursors. The XRD patterns are presented Fig. S2–S4.† Adjusting the amount of  $\text{Li}_2\text{CO}_3\text{--K}_2\text{CO}_3$  has no apparent effect on the formation of LSM, since amorphous  $\text{SrCO}_3$  is present in

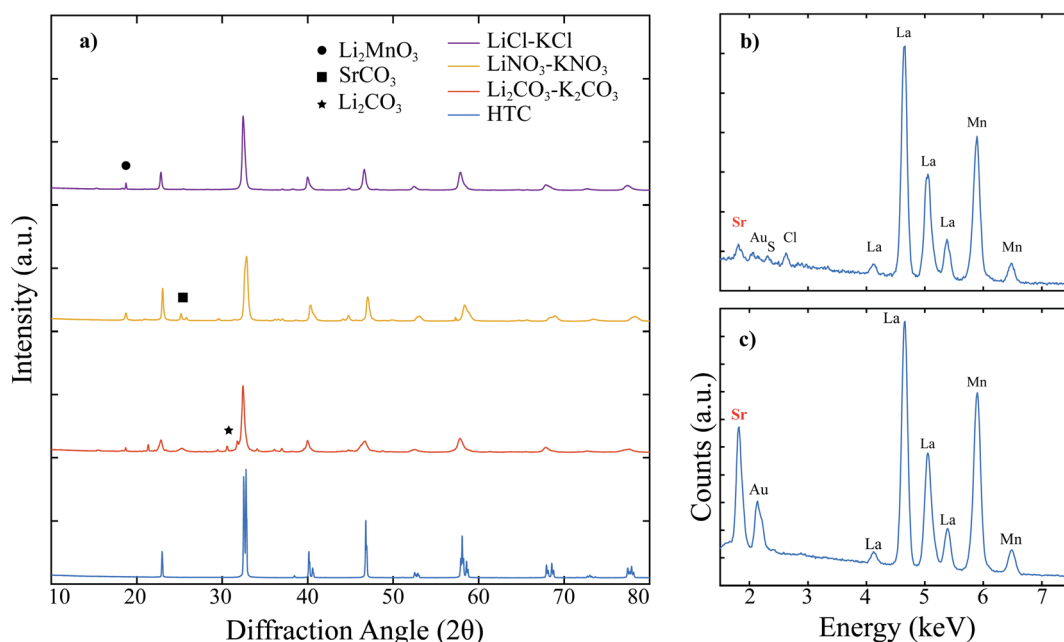

**Fig. 1** (a) XRD patterns of attempted molten salt synthesized (MSS) LSM powders in different molten salts at 600 °C for 2 hours compared to LSM synthesized via high temperature calcination (HTC) at 1200 °C for 10 hours. The precursor powders were mixed oxides in stoichiometric amounts, and the powder to salt mass ratio was 1 : 8. (b) EDX spectra for the  $\text{LiCl--KCl}$  attempted MSS and (c) EDX spectra for the HTC LSM, which compare the intensities of the Sr L-line highlighted in red to show LSM does not appreciably form when  $\text{LiCl--KCl}$  is used.

all three patterns and pure phase LSM is not present. The peaks for  $\text{Li}_2\text{CO}_3$  are present in all three patterns for the same reasoning as described above. Again,  $\text{Li}_2\text{CO}_3$  requires a significant amount of water to completely separate the product powders from salt and thus is not a suitable candidate for large scale productions using the MSS. As a result, this salt system was not investigated further. Adjusting the amount of  $\text{LiNO}_3\text{--KNO}_3$  relative to LSM oxide precursors yields many secondary phases coinciding with the perovskite peaks. As seen in Fig. S3,<sup>†</sup> pure phase LSM is not achieved for any salt amount tested. The patterns for attempted LSM in  $\text{LiNO}_3\text{--KNO}_3$  contain numerous peaks besides those corresponding to LSM as shown in the HTC pattern. When the amount of  $\text{LiCl--KCl}$  was varied relative to LSM precursors, the XRD patterns indicate small peaks corresponding to  $\text{Li}_2\text{MnO}_3$ . However, no peaks for  $\text{SrCO}_3$  are present, which suggests that LSM may form to some extent as opposed to  $\text{LiNO}_3\text{--KNO}_3$  or  $\text{Li}_2\text{CO}_3\text{--K}_2\text{CO}_3$ , which had  $\text{SrCO}_3$  peaks present in the respective XRD patterns. As a result, additional syntheses were conducted for 8 hours to further investigate the possibility of LSM formation in  $\text{LiCl--KCl}$ . Nonetheless, the EDX spectra for each attempted synthesis shown in Fig. S4b–e<sup>†</sup> shows that the Sr L-lines in each are substantially lower in intensity than HTC LSM. Therefore, despite the XRD patterns suggesting LSM formation in  $\text{LiCl--KCl}$ , EDX confirms that the perovskite that forms is Sr-deficient. Since  $\text{SrCO}_3$  is not present in the XRD pattern of the collected powder, it is possible that this precursor was dissolved and washed away with the salt, post synthesis.

Pure LSM was determined to be unable to form in any of the eutectic molten salt systems tested thus far. To gain more insight on the thermodynamics and interactions of LSM

perovskite within the molten salts, HTC LSM was dwelt in  $\text{LiNO}_3\text{--KNO}_3$  and  $\text{LiCl--KCl}$  respectively, washed, and collected for XRD measurements. The XRD patterns shown in Fig. 2a indicate that LSM is not stable when exposed to either molten salt. Specifically,  $\text{SrCO}_3$  is present after dwelling in  $\text{LiNO}_3\text{--KNO}_3$ , and  $\text{Li}_2\text{MnO}_3$  is present after dwelling in both  $\text{LiNO}_3\text{--KNO}_3$  and  $\text{LiCl--KCl}$ . The SEM images and EDX spectra for the HTC powder, post dwell  $\text{LiNO}_3\text{--KNO}_3$ , and post dwell  $\text{LiCl--KCl}$  in Fig. 2b–g. After dwelling in  $\text{LiNO}_3\text{--KNO}_3$ , the particle surfaces are significantly more faceted than the as is and dwell-LSM in  $\text{LiCl--KCl}$ . Nonetheless, the Sr L-lines in both the dwell powders have diminished Sr L-lines compared to the HTC LSM as indicated by the red dashed lines. The difference in surface morphology in the  $\text{LiNO}_3\text{--KNO}_3$ -dwell powder could be a result of the  $\text{NO}_3^-$  ions in solution stabilizing different crystal facets<sup>27</sup> after Sr is leached out of the perovskite. The  $\text{LiCl--KCl}$ -dwell spectrum has an even lower Sr L-line intensity compared to that of the  $\text{LiNO}_3\text{--KNO}_3$ -dwell spectrum, which indicates that the chloride containing salt (the more Lux acidic molten salt) leaches out more Sr from the perovskite lattice. The more acidic solution would dissolve the segregated  $\text{SrCO}_3$  to then be removed from the powder during the washing step as outlined in the experimental procedures (see ESI<sup>†</sup>), and thus not appear in the XRD pattern in Fig. 2. As a result, LSM of a target  $\text{La}_{0.8}\text{--Sr}_{0.2}\text{MnO}_3$  stoichiometry is not stable in any of the molten salt solvents used to determine the influence of the anionic character of the salts. Pure phase LSM was also found to not form in any of the above investigated molten salts. Thus, while the anion does play a role in the MSS of LSM, it is not the deciding factor.

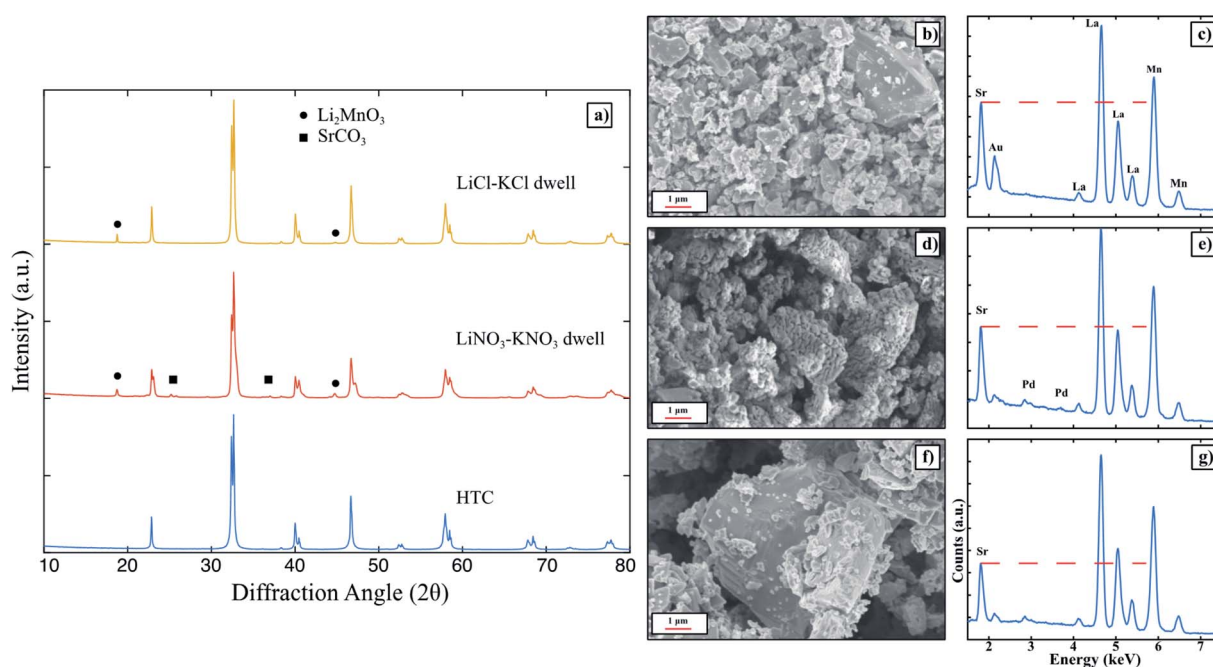


Fig. 2 (a) XRD patterns of HTC LSM compared to HTC LSM dwelt in  $\text{LiNO}_3\text{--KNO}_3$  and  $\text{LiCl--KCl}$  eutectics at 600 °C for 2 hours. The mass ratio of powder to salt was 1 : 8. SEM images and EDX patterns of (b and c) HTC LSM, (d and e)  $\text{LiNO}_3\text{--KNO}_3$  dwelt LSM, and (f and g)  $\text{LiCl--KCl}$  dwelt LSM. The dashed red lines indicate diminishing Sr L-line intensities compared to HTC LSM.



## Influence of molten salt cation on LSM formation

In this section, the molten salts investigated were single salt nitrate systems ( $\text{LiNO}_3$  and  $\text{KNO}_3$ ) since each of these salts had desirably low melting points and would give direct insight on the influence of the cation on LSM formation. HTC LSM was dwelt in  $\text{LiNO}_3$  and  $\text{KNO}_3$  to determine any influence on the acidic character of the cation on LSM perovskite. The XRD patterns in Fig. 3 clearly indicate identical patterns for the HTC LSM as is, and the HTC LSM dwelt in  $\text{KNO}_3$ . When dwelt in  $\text{LiNO}_3$ , the corresponding pattern contains peaks for  $\text{Li}_2\text{MnO}_3$  and  $\text{SrCO}_3$  as identified before for the LSM dwelt in  $\text{Li}^+$ -containing molten salts. The EDX spectrum for  $\text{LiNO}_3$ -dwelt LSM clearly identifies a diminished Sr L-line compared to that in the HTC LSM spectrum (Fig. 3e and g). However, while the  $\text{KNO}_3$ -exposed LSM has a significantly more intense Sr L-line, it is still slightly lower than the Sr-L line for HTC LSM (Fig. 3b and g). These results indicate that the molten salt cation has a significant effect on the retention of Sr in the LSM perovskite. Even though HTC LSM experienced slight Sr depletion when exposed to the  $\text{KNO}_3$  melt, it is possible that prolonged exposure during the heat up and cool down furnace steps exacerbated the salt leaching Sr from the LSM lattice. Furthermore, a small peak for the potassium K-line around 3.3 keV is present, which suggests that Sr near the surface of the perovskite has been replaced by a  $\text{K}^+$ . We do not expect this to be detrimental for LSM from the standpoint of application in solid state devices such as fuel cells and electrolyzers, since the incorporation of a small amount of  $\text{K}^+$  into the melt-synthesized perovskites would be incorporated in either the A (La) or B (Mn) sublattice as acceptor dopants, resulting in the formation of oxygen vacancies or holes, which

are already part of the native point defect structure of LSM.<sup>28,29</sup> Nonetheless,  $\text{KNO}_3$  is the most promising molten salt to preserve LSM perovskite phase with a desired stoichiometry and was then investigated further for the MSS of LSM.

The XRD patterns for the attempted LSM MSS in  $\text{KNO}_3$  are shown in Fig. S5.† The mass ratio of LSM oxide precursors to  $\text{KNO}_3$  was varied from 3 : 1 (mass powder to mass  $\text{KNO}_3$ ) up to 1 : 12, yet pure phase LSM was not obtained in any instance. At greater amounts of salt to LSM precursor ratios (the 1 : 8 and 1 : 12 samples), the  $\text{SrMnO}_3$  phase is observed. In all patterns, a  $\text{K}_{0.5}\text{Mn}_2\text{O}_4 \cdot 2\text{H}_2\text{O}$  phase is present with variable intensity. Since the HTC LSM was shown to remain stable in  $\text{KNO}_3$  at the same temperature and time in a 1 : 8 powder to salt mass ratio, the most thermodynamically stable phase at such conditions is LSM perovskite. The experimental conditions of mixing stoichiometric amounts of  $\text{La}_2\text{O}_3$ ,  $\text{Mn}_2\text{O}_3$ , and  $\text{SrCO}_3$  precursors with  $\text{KNO}_3$ , heating to 600 °C, dwelling, then cooling back down to room temperature, may instead facilitate the reaction between  $\text{K}^+$  and  $\text{Mn}_2\text{O}_3$  at a lower temperature to form a complex. This is observed in Fig. S6† with varying the amount of  $\text{Mn}_2\text{O}_3$  precursor dwelt in  $\text{KNO}_3$  at 600 °C for 2 hours, and collecting XRD patterns of the resulting powder. Counterintuitively, when the amount of  $\text{KNO}_3$  relative to  $\text{Mn}_2\text{O}_3$  decreases a far greater amount of  $\text{K}_{0.5}\text{Mn}_2\text{O}_4 \cdot 2\text{H}_2\text{O}$  forms, whereas  $\text{Mn}_2\text{O}_3$  is the major phase when the amount of  $\text{KNO}_3$  relative to  $\text{Mn}_2\text{O}_3$  increases. The  $\text{SrMnO}_3$  phase may form at greater amounts of  $\text{KNO}_3$  to LSM precursors as a result of this change in  $\text{Mn}_2\text{O}_3$  solubility and consistently high  $\text{La}_2\text{O}_3$  solubility in  $\text{KNO}_3$ .<sup>20</sup>

Given that mixing and heating from room temperature may provide avenues for undesired secondary phases to form, there

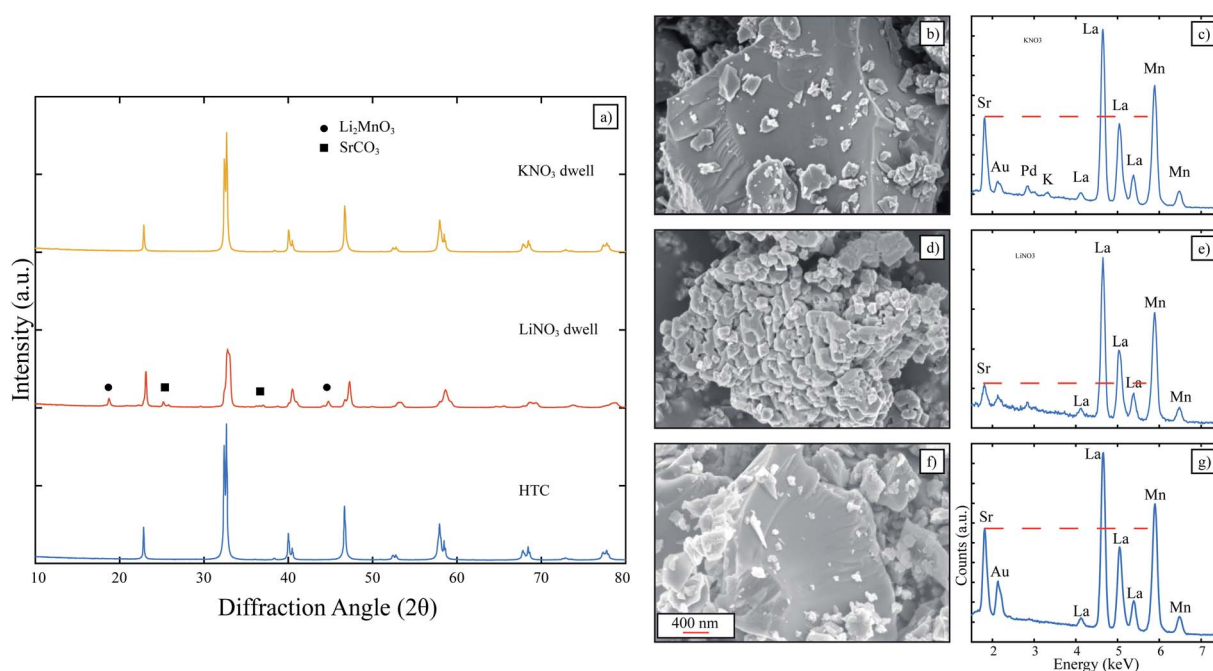


Fig. 3 (a) XRD patterns of HTC LSM compared to HTC LSM dwelt in  $\text{LiNO}_3$  and  $\text{KNO}_3$ . The dwell conditions were 600 °C for 2 hours, and the mass ratio of powder to salt was 1 : 8. SEM images and EDX spectra are presented for (b and c)  $\text{KNO}_3$ -dwelt HTC LSM, (d and e)  $\text{LiNO}_3$ -dwelt HTC LSM, and (f and g) HTC LSM. The dotted red line shows a direct comparison between the Sr L-line intensities for each spectrum.



is a need to instead introduce the mixed LSM precursors at the same time directly into equilibrated  $\text{KNO}_3$  at 600 °C. This feeding procedure<sup>25</sup> was followed as described in the ESI.† The XRD pattern (see Fig. S7†) for the fed LSM into equilibrated  $\text{KNO}_3$  shows completely pure phase LSM formation after dwelling for 1 hour before removing the crucible from the hot plate. SEM/EDX also show a particle size distribution ranging from ~10 to 200 nm, with the majority of particles spanning 15–45 nm in diameter (see Fig. S8†), and a comparable Sr L-line intensity to that of HTC LSM with a slight peak for K that may be substituted for Sr near the surface of the perovskite. Thus, the feeding procedure is the more successful method to expeditiously form pure phase LSM nanoparticles of desired stoichiometry, when the appropriate molten salt  $\text{KNO}_3$  is identified.

### Thermodynamic basis for molten salt chemistry: LSM formation in $\text{KNO}_3$ and not LiCl–KCl

Of the molten salt systems tested for the MSS of LSM, LiCl–KCl and  $\text{KNO}_3$  were the closest to successful considering the extent of secondary phases that formed and EDX analysis. The failure to form LSM in the LiCl–KCl eutectic melt can be understood from the context of supersaturation in the molten salt. The driving thermodynamic factor regarding nucleation and perovskite formation within a molten salt is heavily influenced by solubilities within the melt.<sup>15,30</sup> Specifically, the central equations are as follows:

$$\Delta G^* = \Delta G_{\text{homo}}^* f(m, x) \quad (2)$$

$$\Delta G_{\text{homo}}^* = \frac{16\pi}{3} \frac{\Omega^2 \gamma_{\text{cf}}^3}{\Delta \mu^2} \quad (3)$$

$$\Delta \mu = kT \ln(1 + \sigma) \quad (4)$$

$$\sigma = \frac{X_A}{X_A^0} \quad (5)$$

Explanations of the above equations along with key thermodynamic parameters for nucleation can be found elsewhere.<sup>30</sup> Briefly,  $\Delta G^*$  is the nucleation energy barrier,  $\Delta G_{\text{homo}}^*$  is the homogeneous nucleation energy barrier,  $f(m, x)$  is the heterogeneous nucleation shape factor which is a function of nucleus radius and wettability,  $\Omega$  is the volume of a nucleus,  $\gamma_{\text{cf}}$  is the interfacial free energy between the crystal nucleus and the molten salt phase, and  $\sigma$  is the supersaturation. The actual solubility of component A in a mixture comprising the molten salt and A is denoted as  $X_A$ . When a product, P, is formed by the reaction between reactants A and B,  $X_A^0$  is the solubility of A in the molten salt when equilibrium is achieved between P, B, A, and the molten salt. Here, we focus on the change in chemical potential between the actual and equilibrium state,  $\Delta \mu$ , and the supersaturation,  $\sigma$ . Regarding the formation of LSM, it is more useful and elucidating to apply this formulation to each reactant and calculate respective supersaturation values. Fig. 4

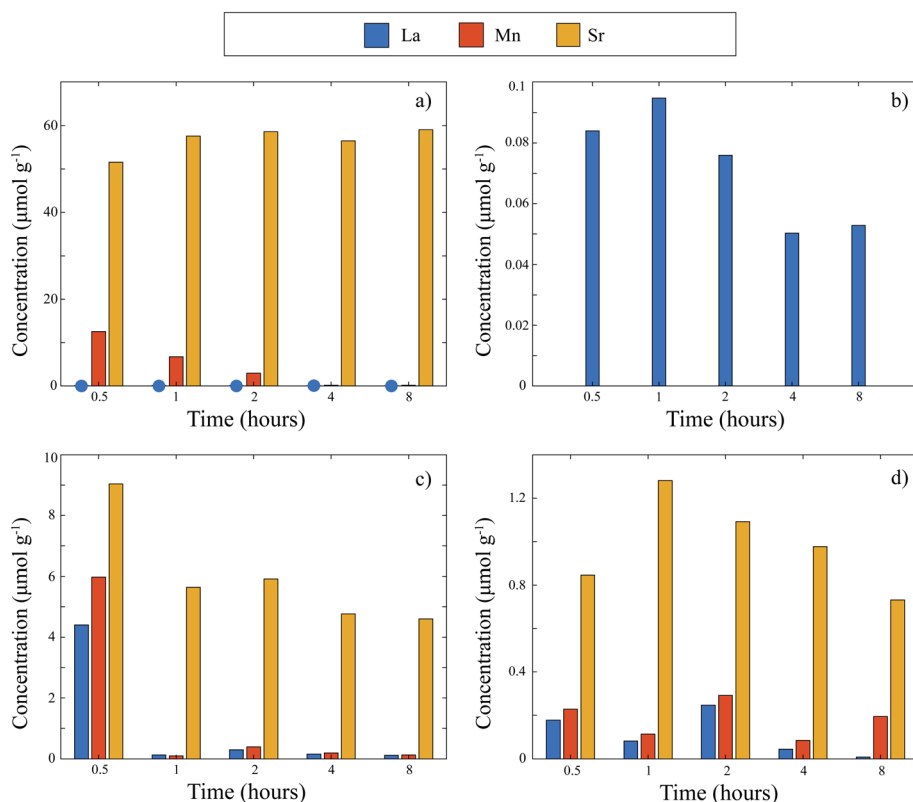


Fig. 4 Concentrations of metal ions present during MSS of LSM. (a) LiCl–KCl eutectic at 550 °C. Blue circles indicate La concentrations. (b) Concentrations of La in LiCl–KCl at 550 °C plotted on a magnified scale. (c)  $\text{KNO}_3$  at 600 °C. (d) Feed into  $\text{KNO}_3$  at 600 °C.



shows the measured concentrations of ions in the melt (samples drawn from the melt) as a function of time. These concentrations are the respective equilibrium concentrations,  $X_A^0$ , for each reactant and were collected at the 8 h mark since the measured concentrations were relatively stable. The actual solubilities, equilibrium solubilities in the molten salt in the presence of the desired product phase, and calculated supersaturations are presented in Table 1. The  $\sigma_{La}$  and  $\sigma_{Mn}$  values are around 2 orders of magnitude larger than  $\sigma_{Sr}$ , which indicates that there is much less of a thermodynamic driving force to incorporate Sr into the perovskite lattice. This is observed in Fig. 4a and b where La and Mn concentrations in the salt melt over the course of perovskite formation are significantly lower than Sr, which was expected as less La and Mn would be solubilized as more product perovskite precipitates out of solution. Sr concentrations in the salt melt remained relatively constant throughout the duration of the synthesis, which further demonstrates Sr is not reacting with the other precursors and therefore not being accommodated in the product perovskite phase. However, since Sr L-lines were observed in the EDX spectra in Fig. 1b and S4b-e† for the LiCl–KCl MSS samples, it is possible that the non-zero supersaturation for Sr allows for trace amounts of Sr to react with the other precursors and incorporate into the perovskite lattice.

While a high solubility of a component in the molten salt,  $X_A$ , may appear favorable for a larger supersaturation, it is important that the  $X_A^0$  value be lower than  $X_A$  to drive the reaction forward. In other words, the chemical potential of the component in the desired product phase must be lower than the chemical potential of the precursor phase A alone in equilibrium with the molten salt. If this is satisfied, the change in chemical potential of A will be negative and indicate a favorable reaction (Fig. S9†). The greater this difference, the more spontaneous the reaction and hence, a smaller nucleation activation energy barrier prevails as shown in eqn (2) and (3). In LiCl–KCl eutectic, the high concentration of Sr in the melt can be attributed to the Lux acidity of both the  $Li^+$  and  $Cl^-$ , which have been shown to significantly solubilize alkaline earth metals and oxides.<sup>31,32</sup> Furthermore, the Lux-acidic environment induces a less favorable environment for Sr within the perovskite lattice. Fig. S10† shows XRD patterns for HTC  $La_{0.6}Sr_{0.4}Co_{0.2}Fe_{0.8}O_3$

(LSCF) as synthesized, dwelt in LiCl–KCl eutectic, and in  $KNO_3$  at 600 °C for 4 hours. The patterns for as-synthesized and  $KNO_3$ -dwelt LSCF are nearly identical, yet noticeable down-shifted peaks appear on the shoulders of the main LSCF peaks in the LiCl–KCl pattern. These down-shifted peaks indicate lattice relaxation<sup>33</sup> and suggest Sr is leached out of the lattice when exposed to an acidic molten salt. Elemental analysis *via* ICP-MS indicates that Sr concentrations are indeed diminished for the LiCl–KCl eutectic-dwelt LSCF, whereas the  $KNO_3$ -dwelt and as-synthesized LSCF are similar (ESI Table 1†). Since Sr is less stable in the perovskite lattice, these results suggest that  $\mu_{Sr}^{Product}$  in the LiCl–KCl eutectic is increased compared to  $\mu_{Sr}^{Product}$  in the  $KNO_3$  melt. As a result, the magnitude of  $\Delta\mu_{Sr}$  in LiCl–KCl eutectic is smaller than that in  $KNO_3$  so there is less of a driving force for Sr to nucleate into the perovskite phase in LiCl–KCl. Stated another way, the partition coefficient of Sr between LiCl–KCl and the perovskite phase is very high and thus, LSM does not form.

$KNO_3$  is a desirable molten salt since  $K^+$  has the lowest acidity among alkali metals according to Lux-Flood theory, and nitrates are less acidic than chlorides. Thus,  $KNO_3$  is overall less acidic than LiCl–KCl eutectic.<sup>32</sup> Therefore, it was expected that more of the Sr would be retained in the perovskite phase when equilibrated in the less acidic  $KNO_3$  melt. From Fig. 4c, it is readily apparent that Sr melt solubility is indeed drastically reduced in the  $KNO_3$  melt compared to LiCl–KCl eutectic over the course of LSM formation. Moreover, the decreasing concentration of each metal as time progressed reflects that each precursor is able to react and form LSM. The XRD patterns of  $KNO_3$ -dwelt HTC LSM and LSCF demonstrate that the less acidic properties of  $KNO_3$  favor Sr remaining in the perovskite phase instead of Sr in solution, as opposed to the more acidic properties of LiCl–KCl eutectic, and are essential for the successful synthesis of phase pure perovskite (Fig. 3, S10 and Table S1†). Thus, the formation of LSM in a  $KNO_3$  melt gives credence to the greater stability of Sr in the LSM phase in the molten salt compared to Sr in the molten salt. It is postulated that the supersaturation of Sr,  $\sigma_{Sr}$ , is now higher than that in the LiCl–KCl eutectic. As a result, it is clear from eqn (3) and (4) that the nucleation activation energy barrier for LSM in a  $KNO_3$  melt will be lower in magnitude than that in a LiCl–KCl eutectic. The

**Table 1** (Top) Molar ratios of each element in LSM powders analyzed *via* ICP-MS. (Bottom) Supersaturations of each element calculated for LiCl–KCl LSM

LSM	La mole ratio	Sr mole ratio	Sr/La mole ratio	Mn mole ratio
HTC LSM	0.81 ± 0.09	0.206 ± 0.002	0.25 ± 0.01	1.1 ± 0.1
LiCl–KCl	0.76 ± 0.09	0.019 ± 0.002	0.025 ± 0.001	1.0 ± 0.1
$KNO_3$ feed	0.74 ± 0.04	0.183 ± 0.009	0.247 ± 0.001	1.00 ± 0.05
LiCl–KCl LSM	La	Sr		Mn
$X_A$ ( $\mu\text{mol g}^{-1}$ salt)	8.28	174.62		41.54
$X_A^0$ ( $\mu\text{mol g}^{-1}$ salt)	0.053	59.044		0.155
$\sigma$	160	2.9575		268



chemistry of the molten salt and how it affects the reactants and products is thus an important aspect in the MSS of LSM.

When the oxide precursors were fed to the  $\text{KNO}_3$  melt equilibrated at 600 °C, the concentrations of each metal in the melt were drastically lower than those in the experiment where the precursors and salt mixtures were mixed and heated together from room temperature. Specifically, Fig. 4d indicates each of the precursors have relatively stabilized in solution even at the first sample collection at 30 minutes. Thus, the precursors are rapidly reacting and forming the target perovskite when introduced to the melt at 600 °C, which drastically accelerates LSM formation compared to heating from room temperature. The higher concentrations of Sr that prevail in the mix and heat method may be a result of the precursors being exposed to and reacting at lower temperatures in the molten salt during the ramp schedule as explained earlier. The marked decrease in precursor concentrations displayed in Fig. 4c at the 1 h mark, and then consistent concentrations from there on, suggest a lag where the melt was still heating to 600 °C despite the heating program reaching 600 °C earlier. By contrast, since all precursors in the feed method are directly introduced to the melt at 600 °C, all three can rapidly react to form the desired perovskite phase. In this case, Fig. 4d shows no drastic decrease in precursor concentrations, indicating firstly that melt is indeed at 600 °C upon drawing the first sample, and secondly that the reaction has likely already occurred and equilibrated in the molten salt. This rapid kinetics of formation of PTO has important implications to not only further elucidate critical factors for PTO formation in molten salts, but also facilitate mass production of PTOs for industrial applications.

## Conclusions

In conclusion, the synthesis of  $\text{La}_{0.8}\text{Sr}_{0.2}\text{MnO}_3$  from oxide precursors in various molten salts was investigated to determine the influence of molten salt chemistry on the efficacy of LSM formation. It was determined that varying the molten salt anion alone did not facilitate LSM formation and thus indicates that the molten salt anion is not the critical factor. The less acidic  $\text{K}^+$  cation compared to  $\text{Li}^+$  is preferred for the MSS of LSM, but pure phase LSM was only obtained by feeding oxide precursors into an equilibrated  $\text{KNO}_3$  melt. The size distribution of the LSM formed *via* feeding and dwelling for 1 hour spanned from ~10–200 nm, with the majority of particles ranging from 15–45 nm in diameter. LSM did not form in  $\text{LiCl-KCl}$  as a result of the large thermodynamic barrier impeding LSM formation due to high acidity of the salt ions in solution creating a more favorable environment for Sr in the molten salt instead of the product perovskite phase. The reaction mixture instead resulted in the formation of A-site deficient lanthanum manganite perovskite phase. Conversely, the relatively low acidic  $\text{KNO}_3$  has a lower nucleation barrier and thus results in a lower partition coefficient of Sr between the melt and the perovskite phase. Phase pure LSM with the desired composition can therefore rapidly form when fed into in this molten salt medium. Essentially, an appropriate molten salt for LSM and other perovskite synthesis requires the molten salt ions, with an

emphasis on the cation, to be less acidic than the precursors. In a broader context for the MSS of other PTOs, researchers should consider the inherent chemistry of each salt system and, if necessary, select those with low Lux acidity.

## Disclaimer

This work was prepared as an account of work sponsored by an agency of the United States Government. Neither the United States Government nor any agency thereof, nor any of their employees, nor any of their contractors, subcontractors or their employees, makes any warranty, express or implied, or assumes any legal liability or responsibility for the accuracy, completeness, or any third party's use or the results of such use of any information, apparatus, product, or process disclosed, or represents that its use would not infringe privately owned rights. Reference herein to any specific commercial product, process, or service by trade name, trademark, manufacturer, or otherwise, does not necessarily constitute or imply its endorsement, recommendation, or favoring by the United States Government or any agency thereof or its contractors or subcontractors. The views and opinions of authors expressed herein do not necessarily state or reflect those of the United States Government or any agency thereof, its contractors or subcontractors.

## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

The authors gratefully acknowledge the Department of Energy, National Energy Technology Laboratory for funding this project through cooperative agreement numbers DE-FE0031205 and DE-FE0031652. The authors also acknowledge the Boston University Materials Science and Engineering Core Research Facility for access to XRD instrumentation, which was funded by NSF Award Number 1337471. The authors thank Professor Katsuyoshi Kakinuma at the University of Yamanashi for his insight and assistance in TEM analysis of the formed nanoparticles (not included in this paper).

## References

- 1 E. Grabowska, *Appl. Catal., B*, 2016, **186**, 97.
- 2 C. Moure and O. Peña, *Prog. Solid State Chem.*, 2015, **43**, 123.
- 3 A. Chronos, R. V. Vovk, I. L. Goulatis and L. I. Goulatis, *J. Alloys Compd.*, 2010, **494**, 190.
- 4 J. Shi and L. Guo, *Prog. Nat. Sci.: Mater. Int.*, 2012, **22**, 592.
- 5 S. C. Singhal, *Solid State Ionics*, 2012, **152**, 405.
- 6 Y. Jiang, S. Z. Wang, Y. H. Zhang, J. W. Yan and W. Z. Li, *Solid State Ionics*, 1998, **110**, 111.
- 7 S. P. Simner, M. D. Anderson, M. H. Engelhard and J. W. Stevenson, *Electrochem. Solid-State Lett.*, 2006, **9**, A479.



- 8 A. Mai, M. Becker, W. Assenmacher, F. Tietz, D. Hathiramani, E. Ivers-Tiffée, D. Stover and W. Mader, *Solid State Ionics*, 2006, **177**, 1965.
- 9 E. Jud, C. B. Huwiler and L. J. Gauckler, *J. Am. Ceram. Soc.*, 2005, **88**, 3013.
- 10 D. Yamada, T. Murai, K. Moritani, T. Sasaki, I. Takagi, H. Moriyama, K. Kinoshita and H. Yamana, *J. Alloys Compd.*, 2007, **444**, 557.
- 11 X. Liu, N. Fechner and M. Antonietti, *Chem. Soc. Rev.*, 2013, **42**, 8237.
- 12 R. H. Arendt, J. H. Rosolowski and J. W. Szymaszek, *Mater. Res. Bull.*, 1979, **14**, 703.
- 13 J. T. S. Irvine, *Faraday Discuss.*, 2016, **190**, 551.
- 14 H. Flood and T. Forland, *Acta Chem. Scand.*, 1947, **1**, 592.
- 15 T. Kimura, in *Molten Salt Synthesis of Ceramic Powders*, ed. C. Sikalidis, IntechOpen, London, United Kingdom, 2011, ch. 4, pp. 75–100.
- 16 P. Afanasiev and C. Geantet, *Coord. Chem. Rev.*, 1998, **178**, 1725.
- 17 H. Zhou, Y. Mao and S. S. Wong, *Chem. Mater.*, 2007, **19**, 5238.
- 18 R. E. Rojas-Hernandez, F. Rubio-Marcos, R. H. Gonçalves, M. A. Rodriguez, E. Véron, M. Allix, C. Bessade and J. F. Fernandez, *Inorg. Chem.*, 2015, **54**, 9896.
- 19 H. L. T. N'Goc, L. D. N. Mouafo, C. Etrillard, A. Torres-Pardo, J. F. Dayen, S. Rano, G. Rousse, C. Laberty-Robert, J. G. Calbet, M. Drillon, C. Sanchez, B. Doudin and D. Portehault, *Adv. Mater.*, 2017, **29**, 1604745.
- 20 C. Matei, D. Berger, P. Marote, S. Stoleriu and J. P. Deloume, *Prog. Solid State Chem.*, 2007, **35**, 203.
- 21 M. Kačenka, O. Kama, Z. Jiráček, M. Maryško, P. Žvátora, S. Vratislav and I. Lukeš, *J. Appl. Phys.*, 2014, **115**, 17B525.
- 22 F. Luo, Y. H. Huang, C. H. Yan, S. Jiang, X. H. Li, Z. M. Wang and C. S. Liao, *J. Magn. Magn. Mater.*, 2003, **260**, 173.
- 23 S. Gu, H. Shin, Y. Hong, D. Yeo, J. Kim, S. Nahm and S. Yoon, *Met. Mater. Int.*, 2012, **18**, 723–726.
- 24 A. M. Shams el Din and A. A. El Hosary, *J. Electroanal. Chem. Interfacial Electrochem.*, 1968, **16**, 551–562.
- 25 L. Vradman, E. Friedland, J. Zana, R. Vidruk-Nehemya and M. Herskowitz, *J. Mater. Sci.*, 2017, **52**, 11383.
- 26 K. Othmer, *Encyclopedia of Chemical Technology*, John Wiley and Sons, New York, NY, 1991.
- 27 X. Wang, K. Huang, L. Yuan, S. Li, W. Ma, Z. Liu and S. Feng, *ACS Appl. Mater. Interfaces*, 2018, **10**, 28219–28231.
- 28 N. Miniajluk, J. Trawczyński, M. Zawadzki and W. Tylus, *Adv. Mater. Phys. Chem.*, 2018, **8**, 193.
- 29 S. Royer, H. Alamdari, D. Duprez and S. Kaliaguine, *Appl. Catal., B*, 2005, **58**, 273.
- 30 X. Y. Liu, *J. Cryst. Growth*, 2002, **237**, 1806.
- 31 V. N. Gaprindashvili and N. V. Kanashvili, *Soobshch. Akad. Nauk Gruz. SSR*, 1970, **58**, 357.
- 32 V. L. Cherginets and T. P. Rebrova, *Zh. Fiz. Khim.*, 1999, **70**, 687.
- 33 M. Pajot, V. Diffort, E. Capoen, A. S. Mamede and R. N. Vannier, *J. Power Sources*, 2020, **450**, 227649.

